

AFFDL-TR-79-3036
Volume II

LEVEL
A072386

(2)
SC


17
8
3
AD A072386
**IMPROVED METHODS FOR PREDICTING SPECTRUM
LOADING EFFECTS - PHASE I REPORT**

Volume II - Test Data

J. B. Chang

J. H. Stolpestad

Rockwell International Corporation
Los Angeles Division
P. O. Box 92098
Los Angeles, California 90009



March 1978

Phase I Technical Report
February 1978-January 1979

Approved for public release; distribution unlimited.

Prepared for

AIR FORCE FLIGHT DYNAMICS LABORATORY
Air Force Wright Aeronautical Laboratories
Air Force Systems Command
Wright-Patterson Air Force Base, Ohio 45433

79 08 2 065

DDC FILE COPY

NOTICE


When Government drawings, specifications or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

This report has been reviewed by the Information Office (OI) and is releasable to the National Technical Information Service (NTIS). At NTIS, it will be available to the general public, including foreign nations.

This technical report has been reviewed and is approved for publication.



ROBERT M. ENGLE, JR.
Project Engineer



LARRY G. KELLY, Chief
Structural Integrity Branch

FOR THE COMMANDER



RALPH L. KUSTER, JR., Col, USAF
Chief, Structures & Dynamics Division

"If your address has changed, if you wish to be removed from our mailing list, or if the addressee is no longer employed by your organization please notify AFFDL/FBE, W-PAFB, OH 45433 to help us maintain a current mailing list."

Copies of this report should not be returned unless return is required by security considerations, contractual obligations, or notice on a specific document.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

(19) REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
(18) SECURITY CLASSIFICATION AFFDL TR-79-3036 + VOL -2	2. GOVT ACCESSION NO. NA-78-491-3- VOL -2	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and subtitle) Improved Methods for Predicting Spectrum Loading Effects - Phase I Report. Volume II. Test Data.	5. TYPE OF REPORT & DATES COVERED Interim Report 15 Feb 1978- 15 Jan 1979	6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(S) B. Chang & H. Stolpestad - Rockwell International <i>James J. Chang</i>	8. CONTRACT OR GRANT NUMBER(S) F33615-77-C-3121 <i>(15)</i>	9. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS <i>(12) 330 P.1</i>
10. PERFORMING ORGANIZATION NAME AND ADDRESS Los Angeles Division Rockwell International International Airport, Los Angeles, CA 90009	11. CONTROLLING OFFICE NAME AND ADDRESS Structural Integrity Branch (AFFDL/PBE) Air Force Flight Dynamics Laboratory Wright-Patterson Air Force Base, Ohio 45433 <i>(11)</i>	12. REPORT DATE 31 Jan 1979
13. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)	14. NUMBER OF PAGES 328	15. SECURITY CLASS. (of this report) Unclassified
16. DISTRIBUTION STATEMENT (of this Report) Approved for public release; distribution unlimited	17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)	18. DECLASSIFICATION/DOWNGRADING SCHEDULE
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) constant amplitude loading, fatigue crack growth, flight-by-flight loading, overload, underload, 2219-T851 aluminum, cycle-by-cycle spectrum	20. ABSTRACT (Continue on reverse side if necessary and identify by block number) This report presents the interim status of a program which is aiming to upgrade the crack growth prediction technology required for the implementation of the damage-tolerance and durability control procedures throughout the life cycle of any weapon system. The controlling damage parameters in flight-by-flight loading for all classes of aircraft have been identified. Methodologies which characterize the flight spectra have been developed. Guidelines for development	

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

of three levels of crack growth analysis used for detail design, individual aircraft tracking, and preliminary design have been established. Crack growth data generated from the test program has been summarized.


UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

FOREWORD

Volume II of this report presents the test results of phase I - identification of controlling damage parameters of a research program entitled "Improved Methods for Predicting Spectrum Loading Effects". This program is being administered by the Air Force Flight Dynamics Laboratory, Air Force Systems Command, Wright-Patterson Air Force Base, Ohio, under contract F33615-77-C-3121. Mr. Robert M. Engle (AFFDL/FBE) is the air Force project engineer.

The test data included in this volume were performed primarily by personnel from the Fatigue and Fracture Mechanics Group, Dynamics Technology, and Structures Systems, supervised by George E. Fitch, Jr., Supervisor, Joseph S. Rosenthat, Manager, and Dr. George P. Haviland, Director. The program manager and principal investigator is James B. Chang. The deputy program manager is John A. Stolpestad. Principal contributors to the test program include Ko-Wei Liu, Fatigue and Fracture Mechanics, Wally Ferentz, Structural Testing Laboratory, and Howard Ross, Manufacturing Engineering.



SUMMARY

An experimental and analytical investigation is being performed under contract F33615-77-C-3121 with the objective of upgrading crack-growth prediction methodology as it is impacted by spectrum loading effects. This report deals with the phase I studies of this program. Three interrelated tasks have been performed in phase I. The first task included an evaluation of the state-of-the-art of currently used methods for analyzing fatigue crack-growth behavior under flight-by-flight loading. The second task dealt with the development of a general methodology for characterizing flight-by-flight loading such that the requirement of a cycle-by-cycle crack-growth analysis could be eliminated. The third task called for the definition of guidelines for the development of crack-growth analyses for preliminary design, for detail design, and for individual aircraft tracking.

To aid in formulation of methodology for the second task, an experimental testing program was conducted. This volume contains tabulations and plots of basic data collected during this experimental program. Data tabulations are presented for 106 tests ranging in complexity from simple baseline da/dN tests to sophisticated randomized cycle-by-cycle fighter and transport spectrum tests. In between these extremes were test groups that studied the influence of single and periodic overloads and underloads, multiple overloads and underloads, and simplified flight spectra. The text preceding the data provides a discussion of test purposes, specimen design and fabrication, testing procedures, and data presentation.

GENERAL

A portion of the phase I effort of the IMPSLE program called for an evaluation of the state-of-the-art of present methods for analyzing fatigue crack growth under flight-by-flight loading. The results and conclusions of this study are documented in Volume I of this report. Following the completion of this study, it was planned that a general methodology would be developed for characterizing flight-by-flight loading, eliminating the necessity for a cycle-by-cycle analysis while predicting equivalent crack growth behavior. To aid in the formulation of this methodology, an experimental program was planned to study the significant stress parameters which control the rate of damage on a flight-by-flight basis. The following paragraphs describe the approach taken in planning and carrying out this test program, and present tabulations and graphical presentations of the test data.

TEST DESCRIPTION

The methodology development test program consisted of a series of eight baseline tests to develop basic fatigue crack growth rate properties, plus

five groups of methodology development test specimens varying in complexity from simple constant-amplitude tests to complex random cycle-by-cycle spectrum tests.

The baseline tests (see Table 1) applied a common maximum stress of 20 ksi with variations in the R-factor ranging + 0.70 to -0.30. One special static test was conducted on a precracked specimen to verify the fracture toughness of the material. In this test, the calculated stress intensity factor at failure using the plane strain stress intensity formula, $K_I = \sigma \sqrt{\pi C} \times W_C$, was 49,000 psi $\sqrt{\text{inch}}$, an acceptable value for this material.

The methodology development tests consisted of the following five groups:

Group I - Constant-amplitude loads - 10 tests (Table 10)

Group II - Single or periodical overload/underload - 20 tests (Table 21)

Group III - Multiple overload/underload - 30 tests (Table 42)

Group IV - Simplified flight spectrum - 25 tests (Table 73)

Group V - Random cycle-by-cycle spectrum - 13 tests (Tables 99, 103, 107, 110, and 114)

Details of the loading conditions for each test are shown in the referenced tables. The selected magnitudes of the maximum stresses, the stress ratios, and the number of cycles for each test segment were predicated on design limit load levels for typical fighter and transport aircraft.

MATERIALS AND SPECIMENS

All tests were performed on plates from a single heat of 2219-T851 aluminum alloy, specification QQ-A-250/30. The plate material was purchased from Ti-Con Industries, Huntington Beach, California. A description of the material, including the chemical and physical properties, follows:

2219-T851 aluminum QQ-A-250/30,
1/4 x 48 x 144 inches

Mill source: Reynolds

Chemical properties									
Heat no.	Al	Mg	Mn	Zn	Ar	Si	Fe	Cu	Ni
743025D			0.20	0.02		0.05	0.10	5.8	
		0.02	.40	.10		.15	.25	6.8	
	Cr	Ti	Th	Ca	c	S	P	Others	
		0.20				.		Each 0.05 max Total	
	0.10	.30							

Physical properties			
Heat no.	Yield strength	Tensile strength	% Elong.
743025D	46,000 min (psi)	62,000 min (psi)	8 min

The physical properties were verified by a tensile coupon test at Rockwell during which a load/strain curve was recorded. (See Figure 1.) Yield strength, ultimate strength, and elongation properties exceeded minimum requirements.

The test specimen blanks were machined from two full plates and a small portion of a third plate. Each blank was uniquely serialized to identify the plate from which it came and its location within that plate. (See Figure 2.) The blanks were then finish-machined to the configuration of Figure 3. All test section thicknesses were 0.250 inch, and the longitudinal grain was oriented parallel to the loading direction. The center notches were installed by EDM Laboratories, Garden Grove, California, employing the wire electrical discharge machining process. The center-notch configuration was selected in order to minimize the geometric considerations in the calculation of the stress intensity factor.

TESTING PROCEDURES

All tests were conducted in the Rockwell LAD Structures Test Laboratory, employing the 500 and 1,500 K MTS fatigue testing systems. An MTS load tower (Figure 4) consists of a rigid load frame and incorporates a dual bridge load cell and hydraulic actuator. Applied loads are controlled through a closed loop servo system and load programmer test system, with load cells and servo uses a digital PDP 8E computer for program control. All tests except the randomized cycle-by-cycle spectrum tests were controlled by the MTS system. The randomized tests were controlled by the Datum servo system 70, a computer-controlled fatigue test system selected for this application because of its capability to handle much longer waveforms than is possible with the integral MTS computer equipment. As used on the random spectrum tests, the Datum system acts as a waveform generator and provides a command signal output to the MTS servo controller. The MTS system returns a load cell feedback signal to the Datum system which was used for "desired versus actual load" error checking. The only other interfaces between the two systems are discrete signals providing test control, including hold, run, and ramp on servo controller error detection. A schematic of the interrelationship of the MTS and Datum 70 systems is shown in Figure 5. Loads were transmitted from the test machine head to the specimens through hydraulically actuated friction grips.

In most cases, the EDM crack starter slot in the specimen was precracked to produce an initial crack length, $2a$, of 0.30 inch approximately. Precracking was performed under constant-amplitude cycling at an R-factor of zero and with maximum cyclic stresses of 8 or 10 ksi, but in no case exceeding the maximum stress applied in the subsequent test. All tests were run in ambient laboratory air at room temperature. The cyclic rate for constant amplitude testing was approximately 6 Hz, and for spectrum testing between 4 and 6 Hz, depending on such factors as load level, load range, and the presence of compression loads. Crack growth was measured by visual optics reading from precision scales attached to each side of the specimen adjacent to the EDM slot. Measurements were made and recorded after approximately each 0.05-inch increment of growth. The long edges of the specimens were restrained against lateral motion when subjected to compression loads.

DATA TABULATIONS AND PLOTS

The raw data tabulations were initially made in laboratory log books. For the dual purposes of data reduction and of presentation in this report, the data were coded into program PLOTRATE, resulting in a computer printout of the data for each test together with a graphical figure of crack length versus applied cycles. Data tabulations and plots in this report are copies of the computer output. Figure 6 shows a typical data tabulation together with explanatory remarks concerning the K-max and delta K columns, the numbers in which are inappropriate for all except the constant amplitude baseline tests. The remaining columns are correct and pertinent to all other tests.

The data tabulations are organized by test groups as follows:

Group	Type load	Test Description Table	Test Data	
			Tables	Figures
Baseline	Constant amplitude (for da/dN)	1	2-9	7-14
I	Constant amplitude	10	11-20	15-24
II	Single or periodical overload/underload	21	22-41	25-44
III	Multiple overload/underload	42	43-72	45-74
IV	Simplified flight spectrum	73	74-98	75-99
V	Random fighter spectrum, air-to-air mission	99	100-102	100-102
V	Random fighter spectrum, air-to-ground mission	103	104-106	103-105
V	Random fighter spectrum, instr & nav mission	107	108-109	106-107
V	Random fighter spectrum, composite mission	110	111-113	108-110
V	Random transport spectrum, composite mission	114	115-116	111-112

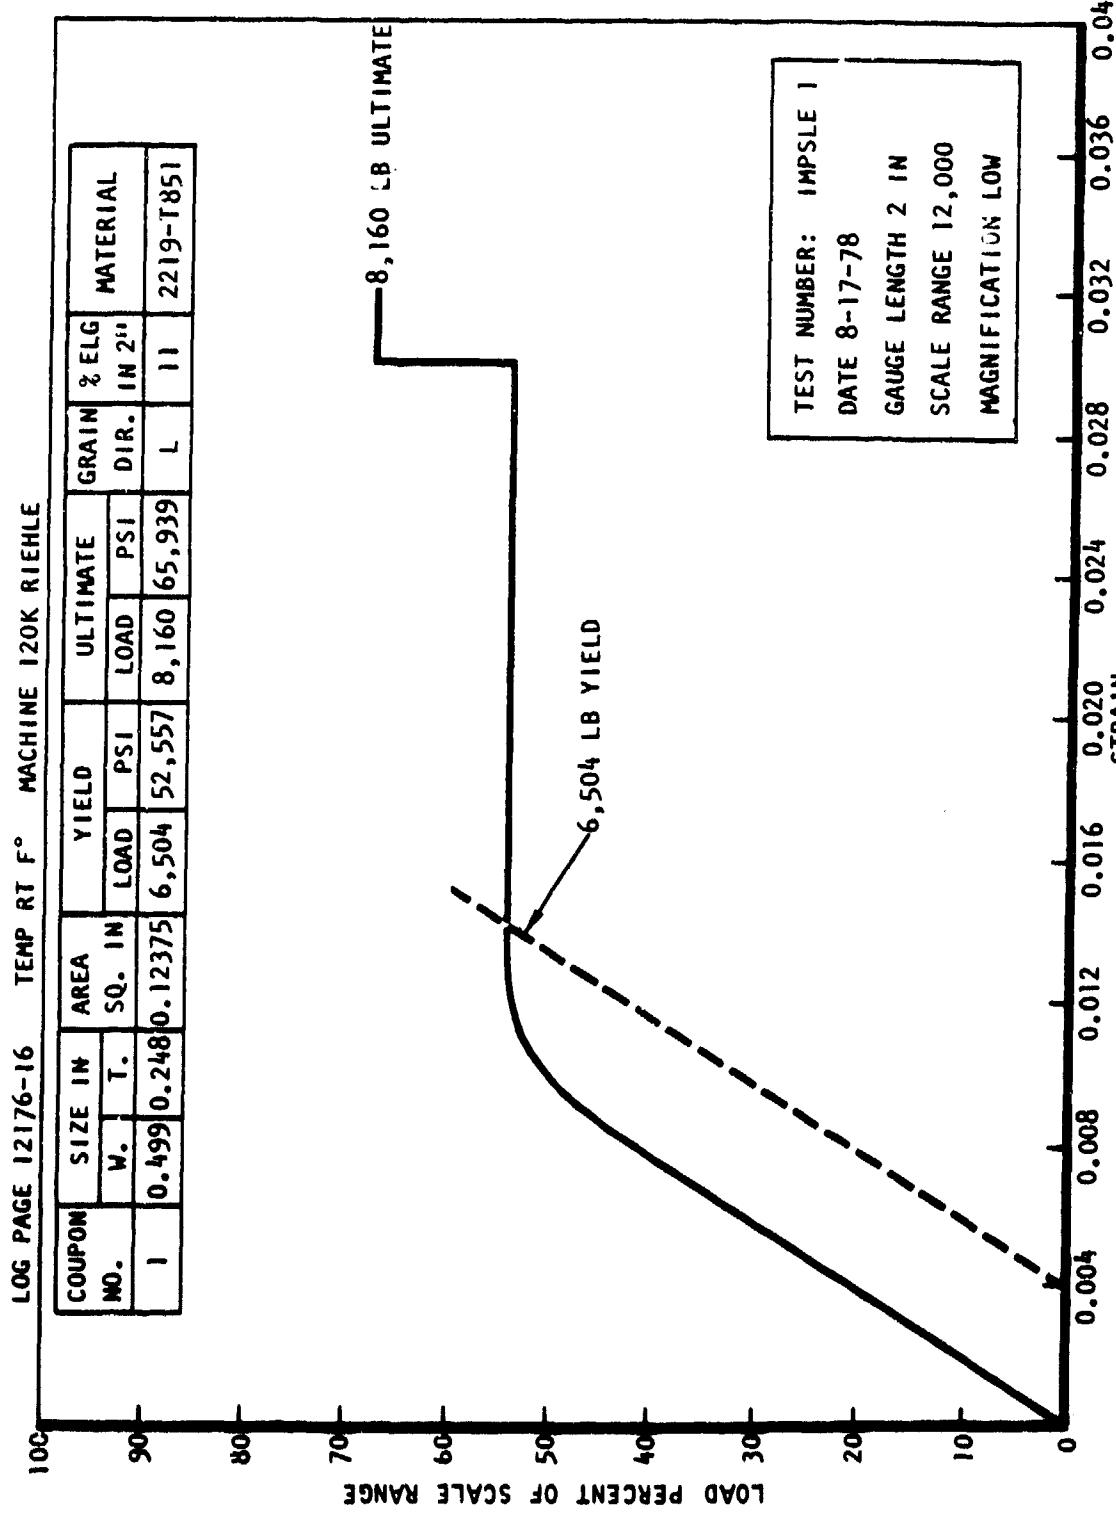


Figure 1. Load/strain curve for tensile coupon test.

MATERIAL: 2219-T851 AL ALLOY PLATE, QQ-A-250/30

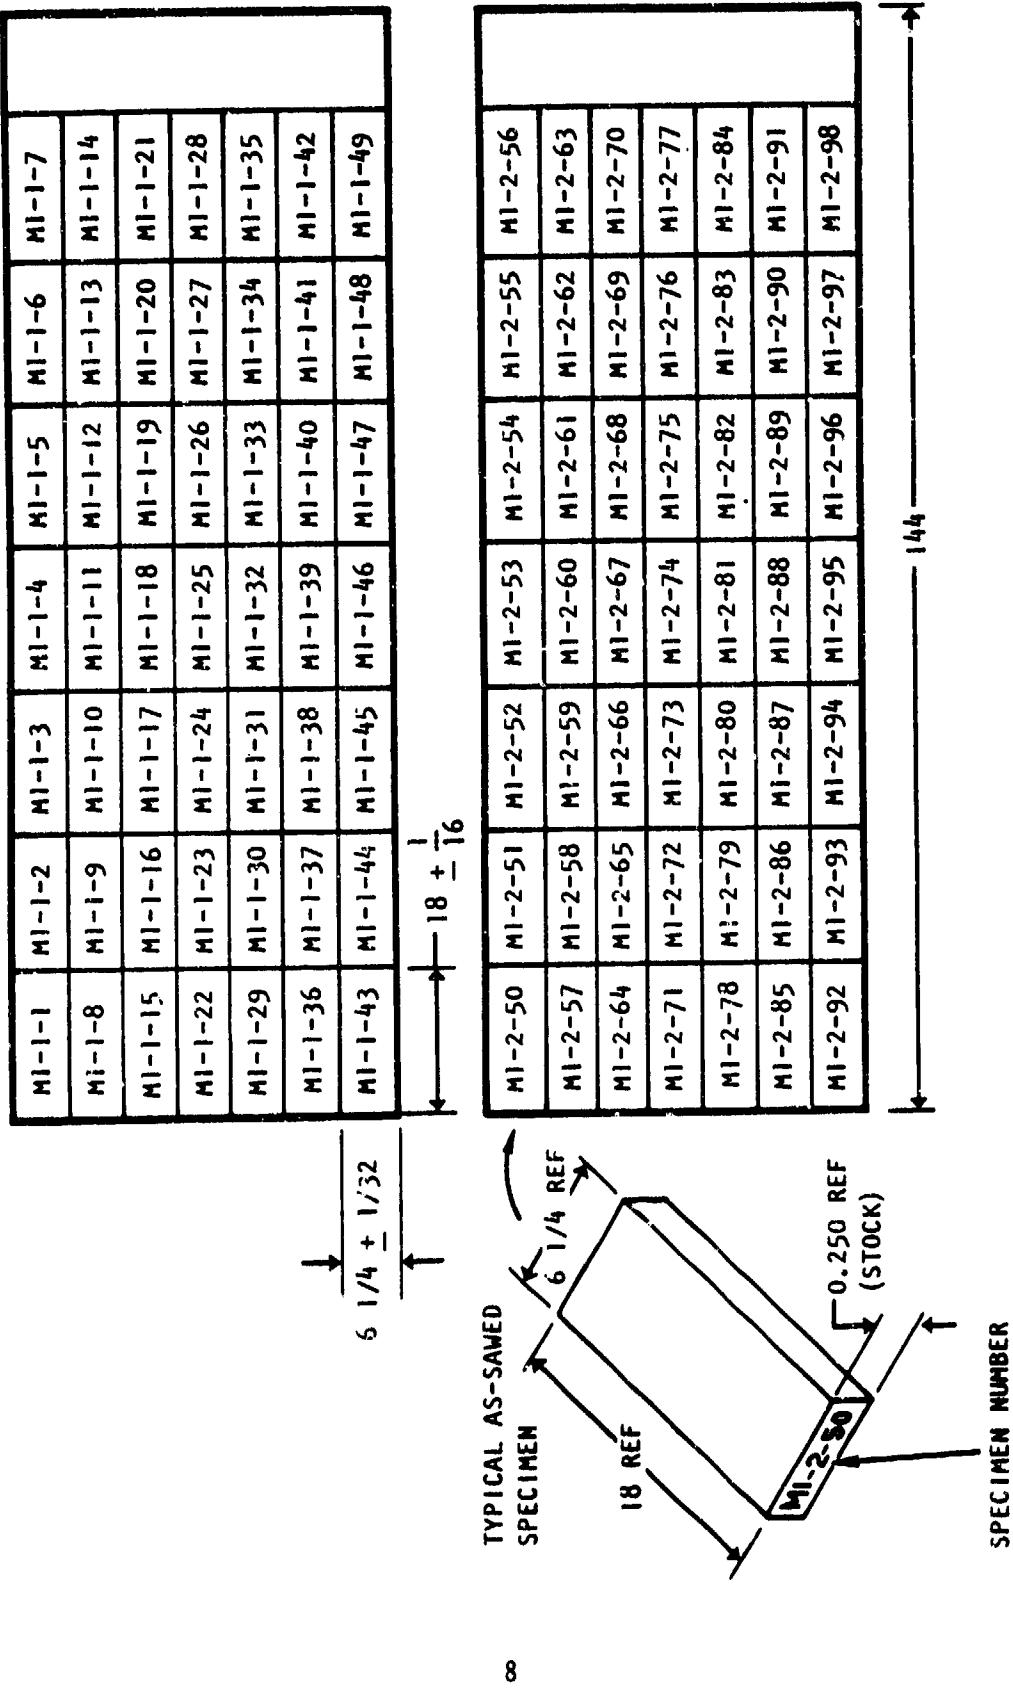


Figure 2. Test specimen location and identification system.


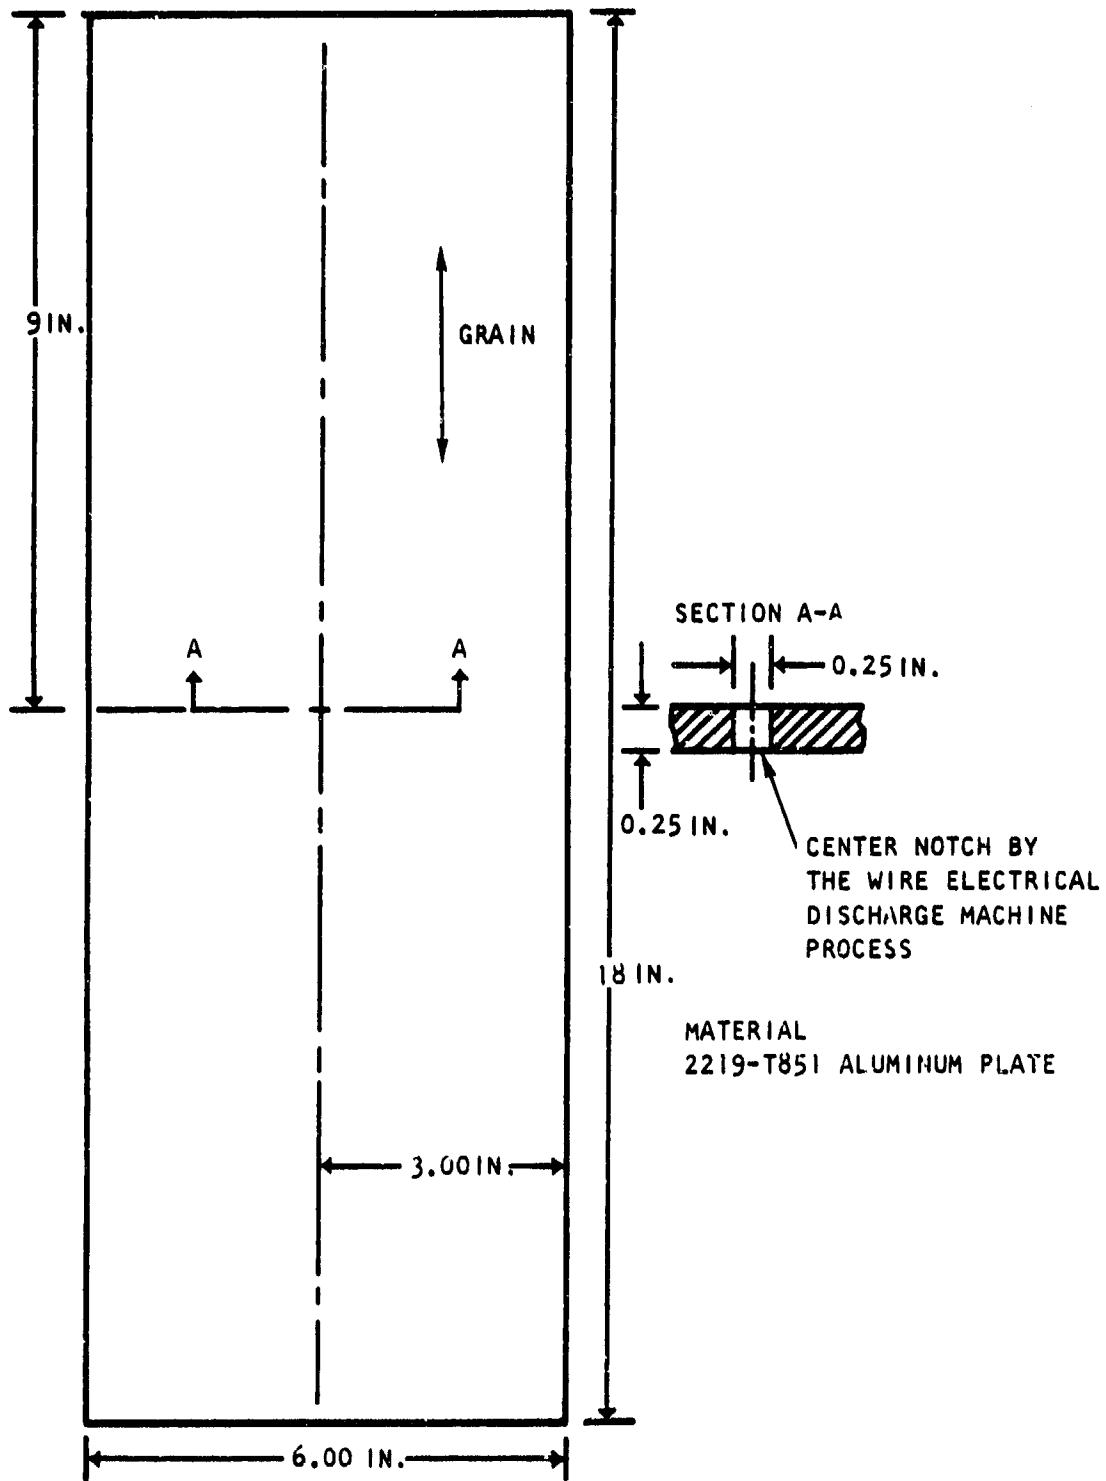


Figure 3. Test specimen configuration.

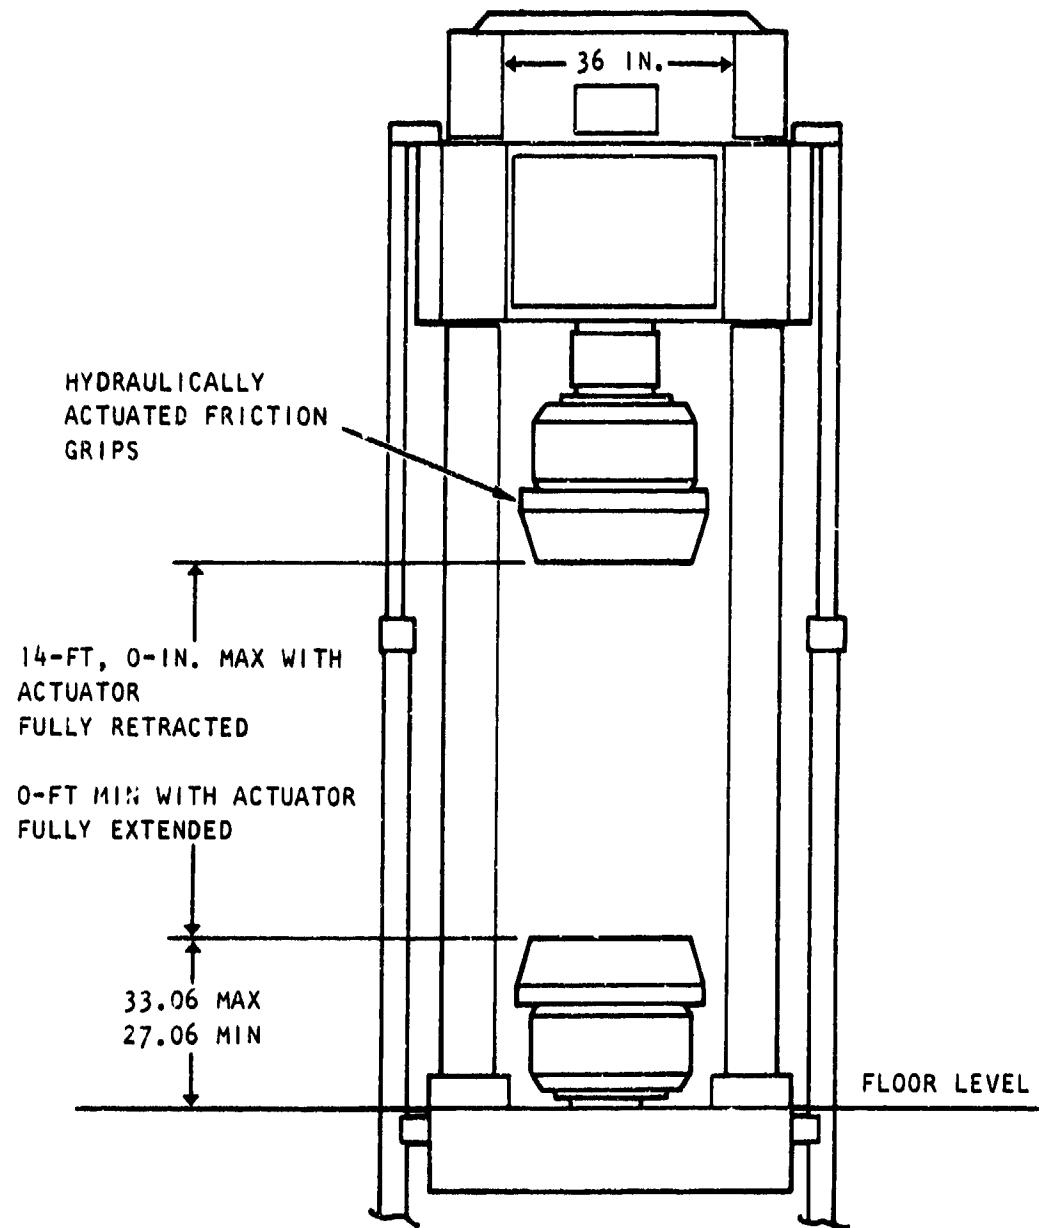

MAXIMUM FATIGUE LOAD:
 $\pm 500,000$ LB

MAXIMUM STATIC LOAD:
600,000-LB TENSION
600,000-LB COMPRESSION

Figure 4. 500-KIP materials test system.

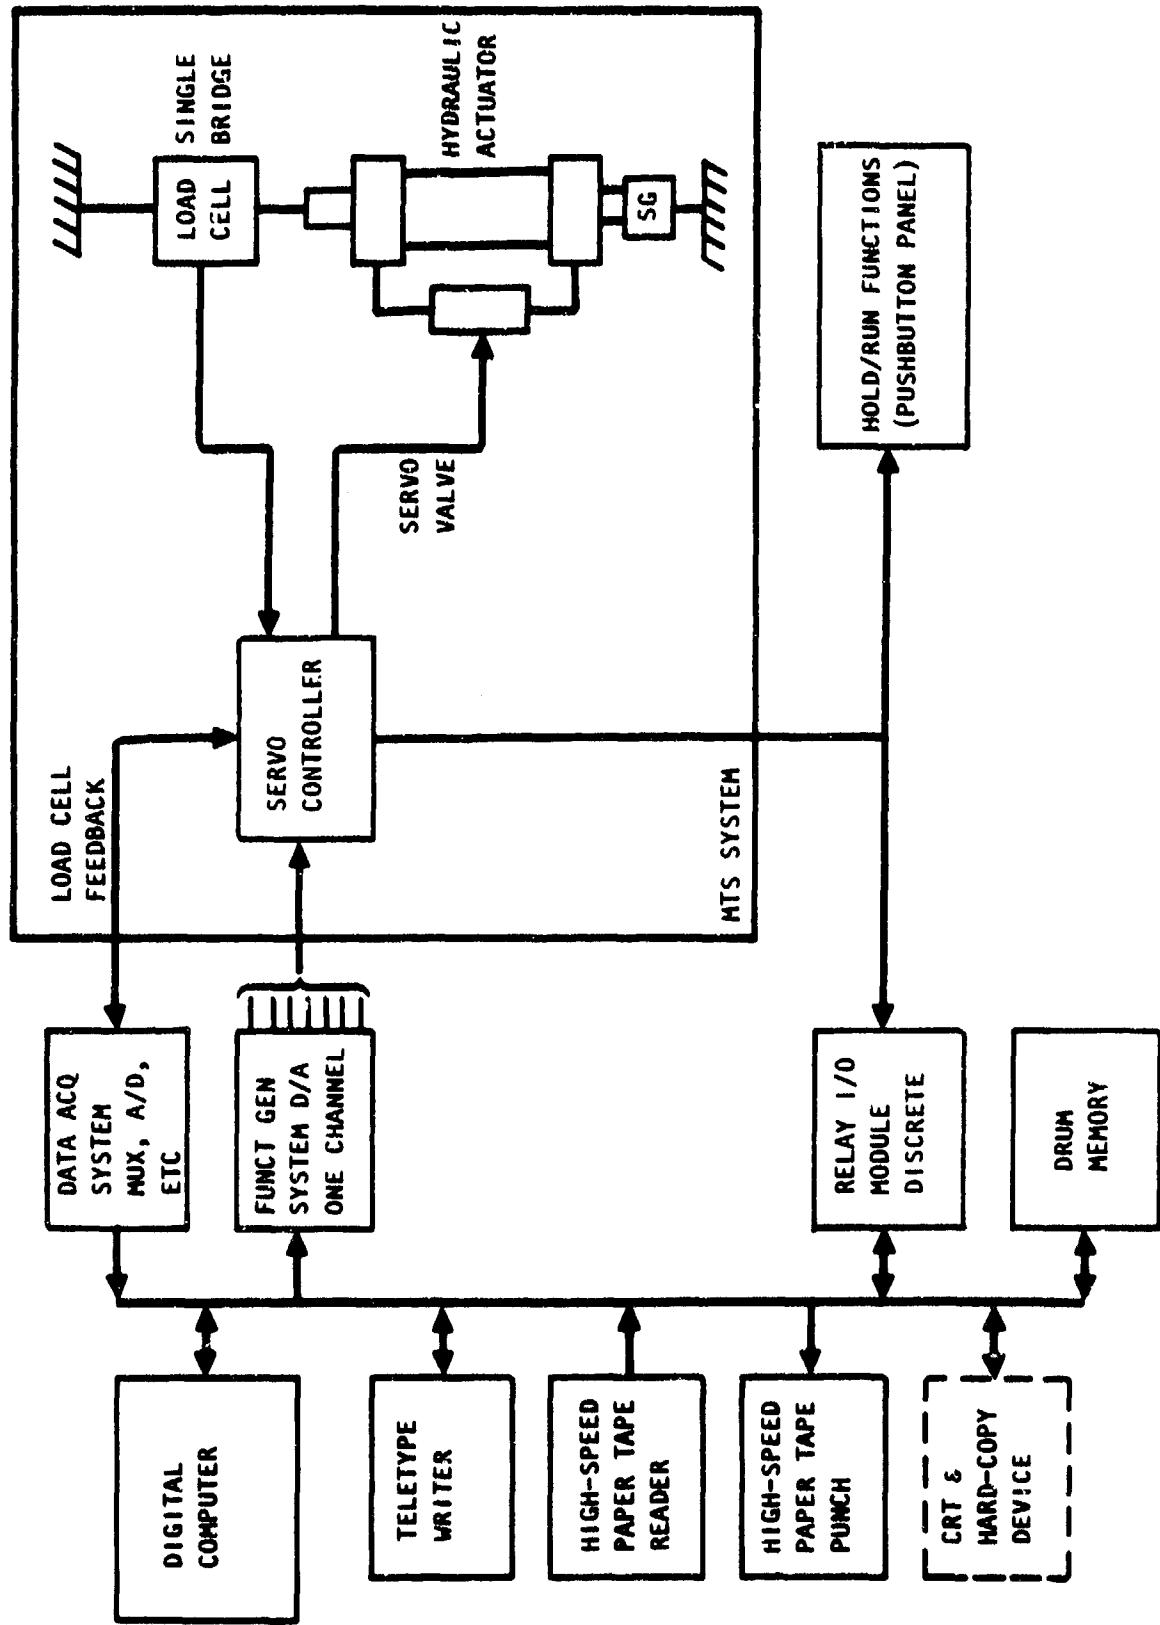


Figure 5. Schematic of MIS system/Datum system 70.

SPECIMEN NO.: M1-2-B¹ BASELINE, 10 KSI STRESS

SCT SPECIMEN R= 0.151 IN. W= 6.00 IN. AN= 0.0 IN.

P_{MIN}= 0.15KIPS P_{MAX}= 15.00KIPS R= 0.010 TEST FREQ= 6.000HZ.

ENVIRONMENT CONDITION: ROOM AMBIENT

NO.	CYCLES	LINEASURED		MULT. COEFF	CORR. COEFF	K-MAX	DA/DN	DELTA K
		1	2					
1	0.	0.317	J.317	1.00000	1.00000	7.07	1.240E-07	7.00
2	5,000.	0.312	0.324	0.997810	0.997810	7.14	6.167E-07	7.07
3	10,000.	0.327	0.337	0.996029	0.996029	7.29	1.446E-06	7.22
4	15,000.	0.315	0.354	0.995179	0.995179	7.47	1.705E-06	7.40
5	20,000.	0.275	0.373	0.998334	0.998334	7.68	2.027E-06	7.60
6	25,000.	0.345	0.394	0.997320	0.997320	7.59	2.339E-06	7.51
7	30,000.	0.415	0.417	0.998800	0.998800	8.12	2.696E-06	8.04
8	35,000.	0.445	0.445	0.999693	0.999693	8.39	3.134E-06	8.31
9	40,000.	0.480	0.460	0.999689	0.999689	8.71	3.625E-06	8.63
10	45,000.	0.520	0.520	0.999969	0.999969	9.07	4.098E-06	8.98
11	50,000.	0.563	0.567	0.999954	0.999954	9.45	5.527E-06	9.35
12	55,000.	0.610	0.610	0.999919	0.999919	9.85	4.971E-06	9.75
13	60,000.	0.660	0.661	0.999950	0.999950	10.26	5.449E-06	10.16
14	65,000.	0.717	0.716	0.999952	0.999952	10.71	6.032E-06	10.60
15	65,000.	0.755	0.755	0.949546	0.949546	10.99	6.493E-06	10.68

Laboratory
measurementsNeglect these
columns for all
but baseline tests

Figure 6. Typical data tabulation.

TABLE 1. BASELINE TESTS FOR FATIGUE CRACK GROWTH RATE DATA

Test No.	Specimen No.	Stress (ksi)		R-Factor	Remarks
		Max	Min		
B-1-1	MI-1-47	20	0.2	+0.01	Conventional EDM
B-1-2	MI-1-14	20	4	+0.20	Conventional EDM
B-2	MI-2-64	20	6	+0.30	Conventional EDM
B-3	MI-1-26	20	14	+0.70	Conventional EDM
B-4	MI-2-90	20	-6	-0.30	Conventional EDM
B-5	MI-1-8	20	-2	-0.10	Conventional EDM
B-6-1	MI-2-88	20	0.2	+0.01	Slot by wire EDM method
B-6-2	MI-1-31	20	0.2	+0.01	Conventional EDM
Special	MI-2-89	10	0.1	+0.01	da/dN growth to 2c = 0.75, then static load to failure

NOTE:

1. All tests in ambient laboratory air.
2. Maximum cyclic rate 360 cpm.
3. Lateral restraints used in compression load tests.

TABLE 2. DATA TABULATION FOR TEST B-1-1

SPECIMEN NO.: B-1-1 BASELINE = 20 KSI STRESS

CCT SPACING b= 6.750 IN. W= 6.000 IN. ANG= 0.0 IN.

PULSE= 0.3 KIPS MAX= 30.0 KIPS R= 0.010 TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: ROOM AMBIENT

NO.	CYCLES	MEASUREMENTS	AIRREGRESSION	MULT. COEF. COEFF	K-MAX	DELTA K	DATA
1	0.	0.515	0.520	0.995528	10.96	-2.405E-05	
2	1000.	0.650	0.590	0.997529	19.18	-3.801E-05	
3	2000.	0.670	0.661	0.998349	20.84	-5.252E-05	
4	2700.	0.765	0.761	0.992515	22.05	-6.103E-05	
5	3300.	0.840	0.838	0.996716	23.22	-22.98	7.049E-05
6	3601.	0.923	0.929	0.997935	24.51	-24.26	8.222E-05
7	4502.	1.020	1.028	0.998659	25.86	-25.60	9.429E-05
8	5106.	1.145	1.151	0.998482	27.50	-27.22	1.238E-04
9	3406.	1.221	1.223	0.999855	28.42	-28.14	1.375E-04
10	5704.	1.365	1.369	0.999509	29.51	-29.22	1.500E-04
11	6006.	1.410	1.403	0.998617	30.49	-30.39	1.657E-04
12	6306.	1.515	1.513	0.945900	32.05	-31.76	2.227E-04
13	6656.	1.675	1.676	0.997954	34.04	-33.72	2.901E-04
14	6956.	1.660	1.633	0.988259	35.97	-35.61	4.141E-04
15	7256.	2.010	2.019	0.992581	39.24	-38.95	5.445E-04
16	7556.	2.345	2.463	0.955918	43.45	-43.05	7.826E-04
17	7856.	3.015	3.012	0.998516	51.17	-51.17	1.144E-03

PLOT RATE CRACK GROWTH ANALYSIS
B-1-1 BASELINE, 20 KSI STRESS R = .01

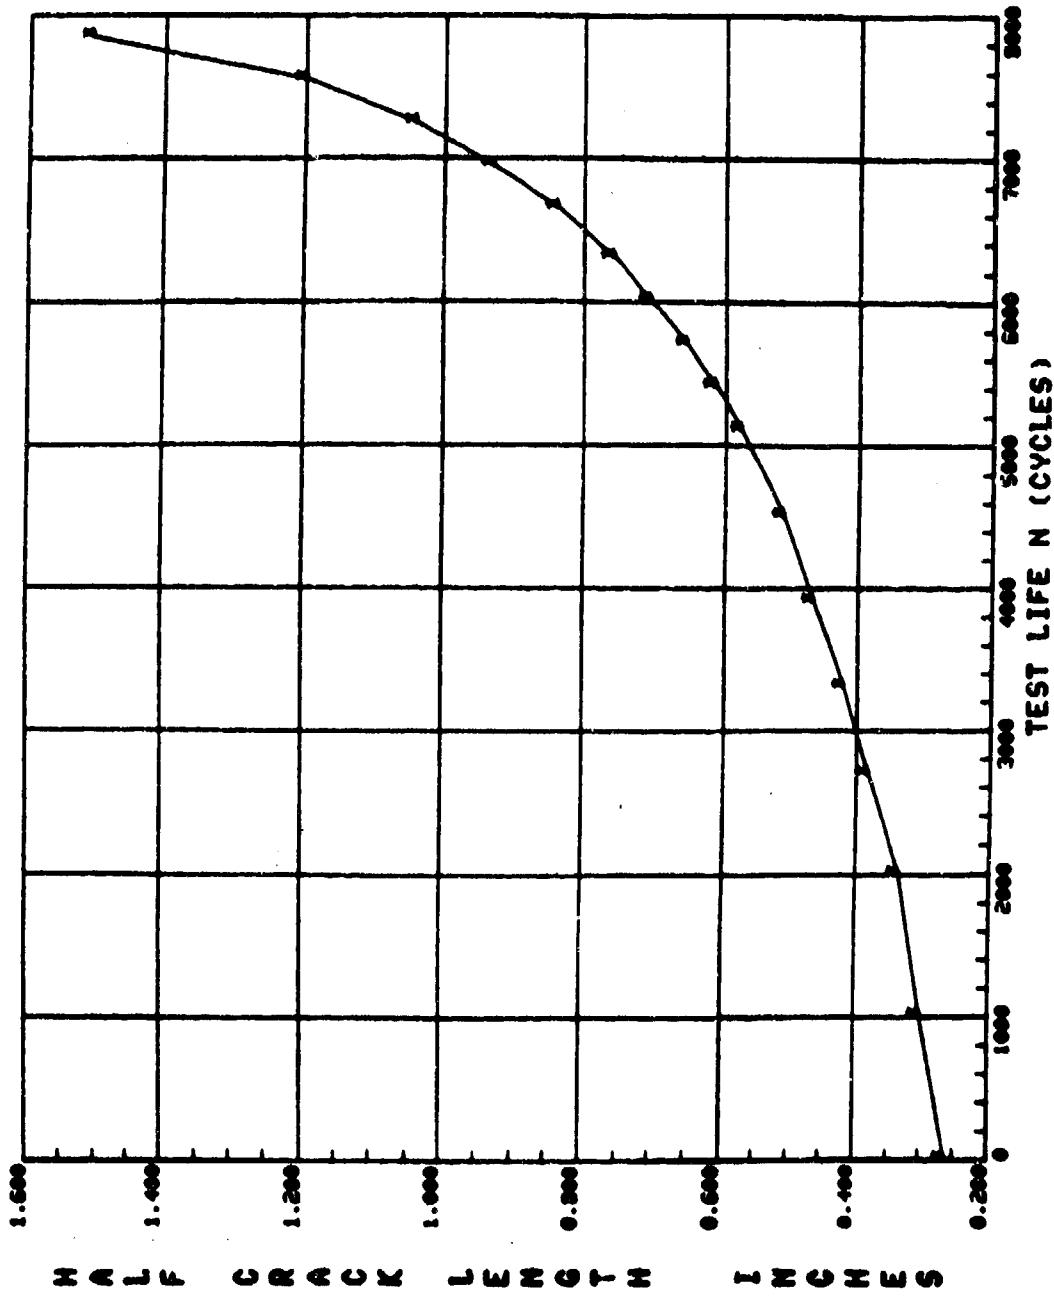


Figure 7. Crack growth curve for test B-1-1.

TABLE 3. DATA TABULATION FOR TEST B-1-2

CCT	SPECIMEN	S= 0.750 IN.		W= 6.000 IN.		A= 0.0 IN.	
		PRIME	6.0 KIPS	PMAX=	30.0 KIPS	A= 0.200	TEST FREQ= 6.00 Hz
ENVIRONMENT CONDITION: ROOM AMBIENT							
NO.	CYCLES	AI(MEASURED)	AI(REGRESSION)	MULT.	CURR.	C(GEFF)	K-MAX
1	0.	0-360	0-360	0.999921		15.07	12.50
2	1300.	0-420	0-412	0.999609		16.24	13.01
3	2600.	0-490	0-486	0.997126		17.59	14.97
4	3800.	0-560	0-564	0.999376		18.92	15.14
5	4700.	0-630	0-626	0.999053		19.94	15.99
6	5500.	0-690	0-694	0.997522		21.06	16.86
7	6200.	0-760	0-766	0.992615		22.16	17.73
8	6800.	0-840	0-840	0.999660		23.25	18.60
9	7300.	0-920	0-915	0.999736		24.31	19.45
10	7700.	0-963	0-962	0.997782		25.24	20.12
11	8100.	1-053	1-057	0.998147		26.26	21.01
12	8450.	1-135	1-135	0.999794		27.45	21.83
13	8750.	1-220	1-220	0.999956		28.39	22.71
14	9000.	1-303	1-302	0.999766		29.43	23.54
15	9200.	1-375	1-370	0.999596		30.29	24.43
16	9400.	1-445	1-444	0.999172		31.21	24.97
17	9600.	1-520	1-515	0.994461		32.63	25.77
18	9800.	1-615	1-614	0.996665		33.30	26.64
19	9950.	1-695	1-692	0.999494		34.25	27.43
20	1C100.	1-775	1-781	0.999501		35.93	28.23
21	10250.	1-840	1-861	0.995975		36.55	29.24
22	1C350.	1-960	1-957	0.999877		37.65	29.95
23	10450.	2-040	2-043	0.999844		38.54	30.83
24	10550.	2-125	2-136	0.999663		39.70	31.76
25	10600.	2-165	2-186	0.999593		40.23	32.26
26	10650.	2-245	2-241	0.999242		41.05	32.82
27	10700.	2-295	2-305	0.997356		39.47	33.47
28	10750.	2-375		0.997761		42.73	34.19

TABLE 3. DATA TABULATION FOR TEST B-1-2 (CONCL)

SPECIMEN NO.:	TEST CONDITIONS			TEST FREQUENCIES			ENVIRONMENT CONDITIONS: ROOM AMBIENT	NO.	CYCLES	A(MEASURD)	A(MEGRSSION)	MULT. CUMUL. CUFF	K-MAX	DELTA K	DA/DK	
	CCT	SPECIMEN	R= 0.20 IN.	M= 6.000 IN.	Ak= 0.0 IN.	P MAX= 30.0 KIPS										
PHIN= 6.0 KIPS																
29	10800.	2.460	2.448	0.949052	43.69	34.96	7.6466E-04									
30	10850.	2.520	2.528	0.998284	44.74	35.81	8.411E-04									
31	10980.	2.610	2.609	0.996598	45.45	36.68	9.266E-04									
32	10950.	2.705	2.700	0.996934	47.10	37.63	1.022E-03									
33	11000.	2.810	2.814	0.996716	48.73	38.99	1.309E-03									
34	11050.	2.945	2.947	0.995621	50.70	40.56	1.694E-03									
35	11100.	3.150	3.129	0.969060	53.54	42.83	2.509E-03									
36	11125.	3.225	3.267	0.979333	55.82	44.86	3.850E-03									
37	11150.	3.345	3.463	0.969225	59.32	47.46	5.370E-03									
38	11175.	3.760	3.776	0.997748	65.70	52.56	8.623E-03									

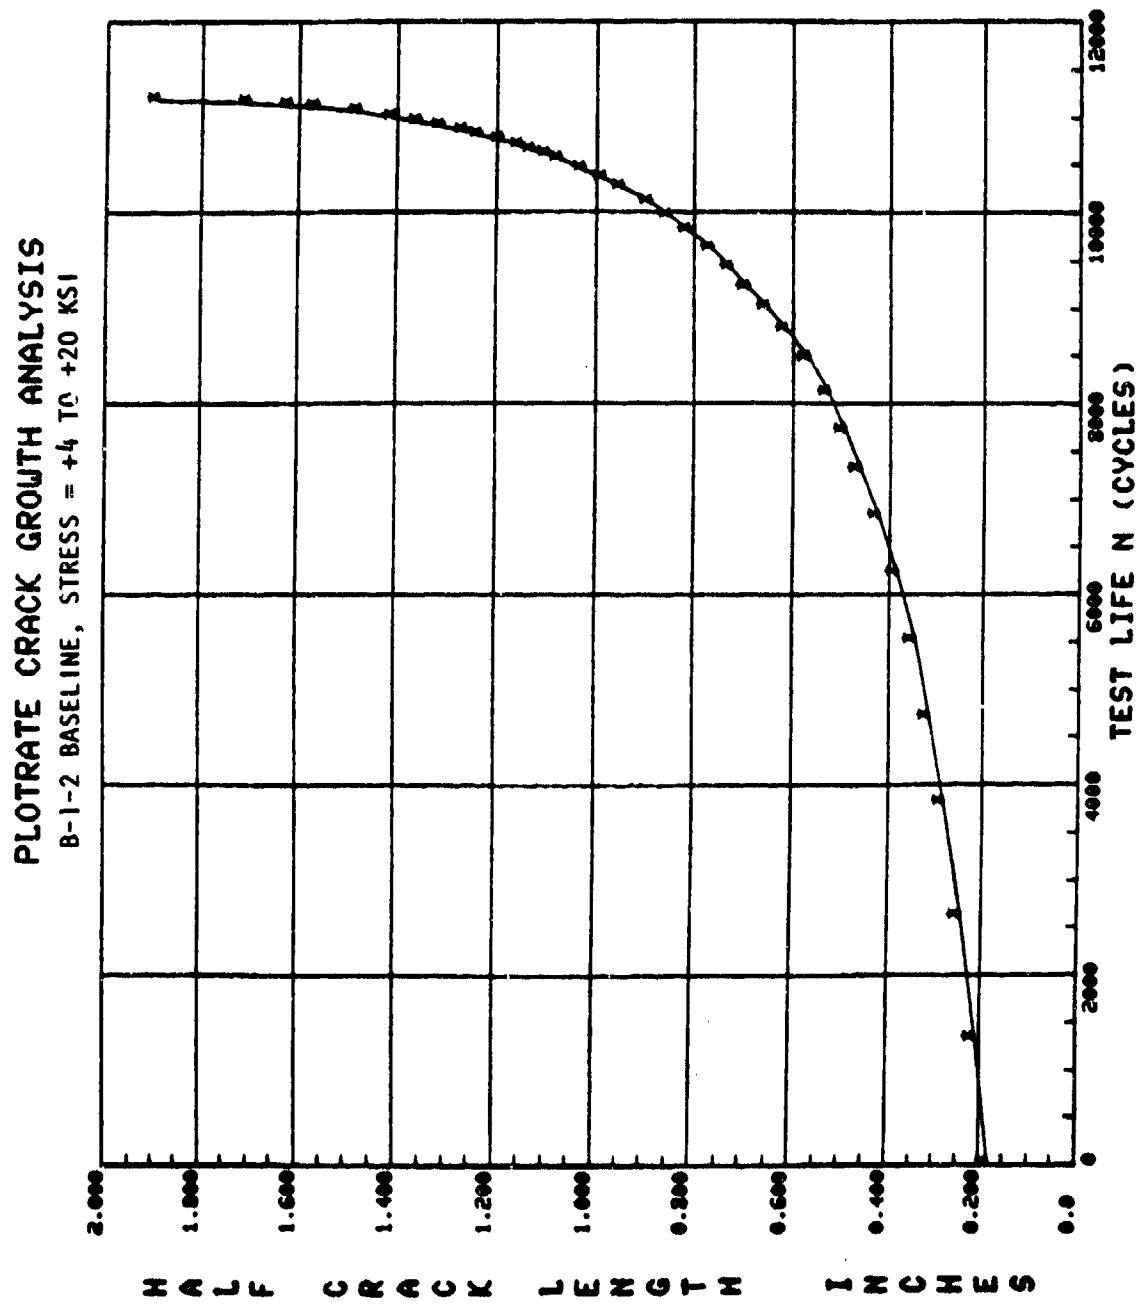


Figure 8. Crack growth curve for test B-1-2.

TABLE 4. DATA TABULATION FOR TEST B-2

SPECIMEN NO.:	CCT	SPECIMEN	B= 0.550 IN.	H= 6.000 IN.	AN= 0.0	IN.	ENVIRONMENT CONDITION: ROOM AMBIENT		MULT. CORR. COEFF	K-MAX	DELTA K	DAFM
							MIN-	MAX-				
1	C-	679E-0	0.376	0.326	0.999898	14.20	9.94	7.72E-06				
2		679E-0	0.420	0.419	0.999913	16.26	11.38	1.312E-05				
3		6500-	0.465	0.467	0.999906	17.19	12.03	1.479E-05				
4		7400-	0.495	0.494	0.999186	17.69	12.38	1.659E-05				
5		9400-	0.565	0.562	0.999192	18.90	13.23	1.943E-05				
6		10900-	0.620	0.624	0.999404	19.93	13.95	2.326E-05				
7		17400-	0.698	0.698	0.999283	21.11	14.74	2.790E-05				
8		13700-	0.772	0.774	0.999629	22.27	15.59	3.265E-05				
9		14600-	0.873	0.836	0.999703	23.19	16.23	3.592E-05				
10		15400-	0.696	0.855	0.999243	24.03	16.82	4.026E-05				
11		16100-	0.955	0.953	0.998670	24.84	17.39	4.509E-05				
12		16700-	1.001	1.006	0.997031	25.57	17.90	5.252E-05				
13		17300-	1.072	1.073	0.998645	26.43	18.50	5.904E-05				
14		17900-	1.140	1.146	0.996167	27.43	19.20	6.639E-05				
15		18500-	1.243	1.232	0.997193	28.56	19.95	7.752E-05				
16		19000-	1.310	1.313	0.996695	29.57	20.70	8.553E-05				
17		19400-	1.370	1.374	0.995225	30.46	21.32	9.321E-05				
18		19700-	1.450	1.440	0.997316	31.15	21.81	1.096E-04				
19		19800-	1.440	1.463	0.995368	31.44	22.01	1.089E-04				
20		19900-	1.455	1.487	0.997248	31.74	22.22	1.143E-04				
21		20100-	1.575	1.526	0.997185	32.24	22.57	1.145E-04				
22		20300-	1.575	1.576	0.998051	32.85	23.00	1.284E-04				
23		20500-	1.625	1.630	0.996730	33.50	23.45	1.366E-04				
24		20700-	1.695	1.666	0.998161	34.17	23.92	1.570E-04				
25		20900-	1.754	1.754	0.997484	35.30	24.50	1.745E-04				
26		21100-	1.620	1.827	0.996286	35.96	25.13	1.815E-04				
27		21200-	1.895	1.882	0.994339	36.57	25.60	2.026E-04				
28		21350-	1.925	1.924	0.994436	37.08	25.96	2.255E-04				

TABLE 4. DATA TABULATION FOR TEST B-2 (CONCL)

SPECIMEN NO.: B-2		STRESS = +6 TO +20 KSI			
CYCLES	SPECIMEN	b= 0.250 IN.	H= 6.000 IN.	A= 0.3	IN.
NO.		9.0 KIPS	MAX= 30.0 KIPS	R= 0.30	TEST FREQ= 6.00HZ
ENVIRONMENT CONDITION: ROOM AMBIENT					
NO.	CYCLES	ALMEASUR'D	ALREGRESSION	MULT. CORR.	COEFF
29	21450.	1.953	1.970	0.991164	37.64
30	21550.	2.020	2.018	0.984652	38.24
31	21650.	2.080	2.070	0.990643	36.89
32	21750.	2.110	2.116	0.982527	39.45
33	21850.	2.120	2.154	0.969361	39.92
34	21950.	2.190	2.197	0.998651	40.47
35	22050.	2.255	2.254	0.998263	41.19
36	22150.	2.321	2.321	0.999251	42.05
37	22250.	2.395	2.396	0.999692	43.01
36	22350.	2.473	2.469	0.994211	43.92
39	22450.	2.555	2.549	0.996233	45.04
40	22550.	2.635	2.635	0.998456	46.49
41	22650.	2.715	2.719	0.997349	48.23
42	22750.	2.795	2.915	0.997465	50.72
43	22850.	3.135	3.166	0.997513	54.13
44	22950.	3.435	3.434	0.998825	58.77
					41.14
					1.595E-03
					2.343E-04
					2.289E-04
					2.302E-04
					2.350E-04
					2.384E-04
					2.607E-04
					2.911E-04
					3.429E-04
					3.714E-04
					4.286E-04
					5.096E-04
					6.125E-04
					7.812E-04
					9.797E-04
					1.207E-03
					1.595E-03

PLOT RATE CRACK GROWTH ANALYSIS
B-2 STRESS = +670 +20 KSI

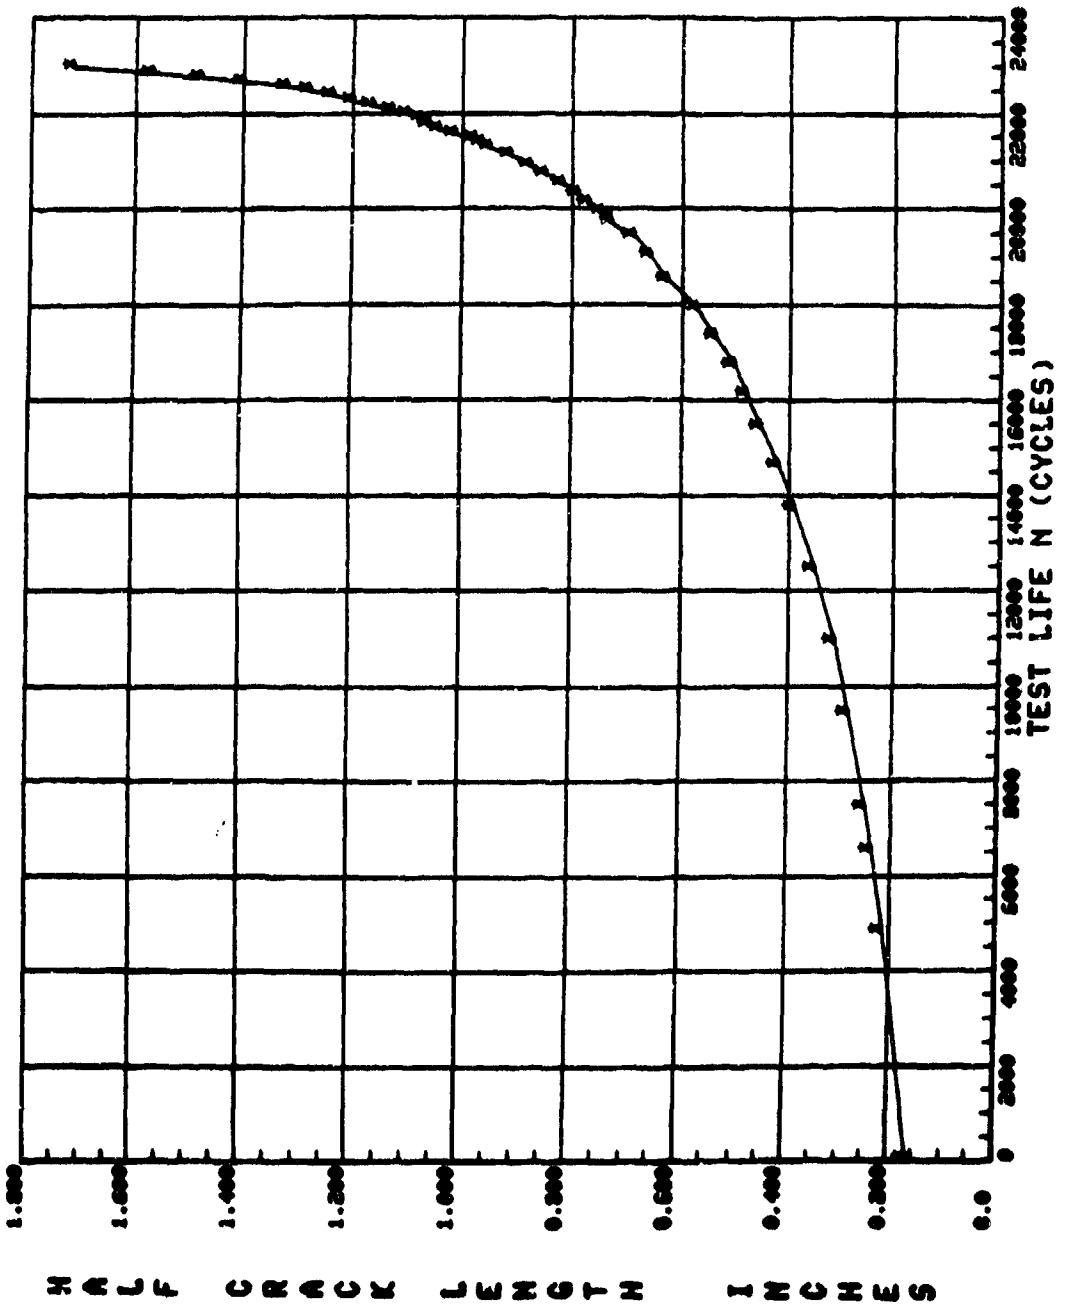


Figure 9. Crack growth curve for test B-2.

TABLE 5. DATA TABULATION FOR TEST B-3

SPECIMEN NO.: B-3		STRESS +14 TO +20 KSI					
CCT	SPECIMEN	b= 1.250 IN.	W= 6.000 IN.	A= 0.0	IN.		
PHASE	21.0 KIPS	P _{MAX} = 30.0 KIPS	K= 0.70	TEST FREQ= 6.00HZ.			
ENVIRONMENT CONDITIONS: ROOM AMBIENT							
NO.	CYCLES	AM(MEASURED)	AM(PREDICTION)	MULT. CORR.	G _{EFF}	K-MAX	DELTA, K
1	0-	0-310	0-310	0.999592	13.58	4.19	1.345E-06
2	11700.	0-340	0-340	0.999662	14.65	4.39	1.215E-06
3	30000.	0-380	0-377	0.992143	15.46	4.63	1.052E-06
4	50000.	0-415	0-419	0.952096	16-27	4.88	1.320E-06
5	55000.	0-420	0-431	0.957805	16.50	4.95	1.350E-06
6	60000.	0-445	0-444	0.991061	16.77	5.03	1.366E-06
7	70000.	0-465	0-476	0.996260	17.35	5.21	1.646E-06
8	87000.	0-530	0-531	0.996253	18.35	5.50	1.646E-06
9	105000.	0-545	0-546	0.998092	19.47	5.84	2.119E-06
10	120000.	0-560	0-661	0-999315	20.53	6.16	2.598E-06
11	132000.	0-725	0-726	0-996404	21.55	6.47	3-261E-06
12	143000.	0-745	0-800	0.997134	22.67	6.60	4-017E-06
13	153000.	0-875	0-866	0.997652	23.91	7.17	5-075E-06
14	158700.	0-950	0-949	0.998425	24.79	7.44	6-341E-06

PLOTRATE CRACK GROWTH ANALYSIS
B-3 STRESS = +14 TO +20 KSI

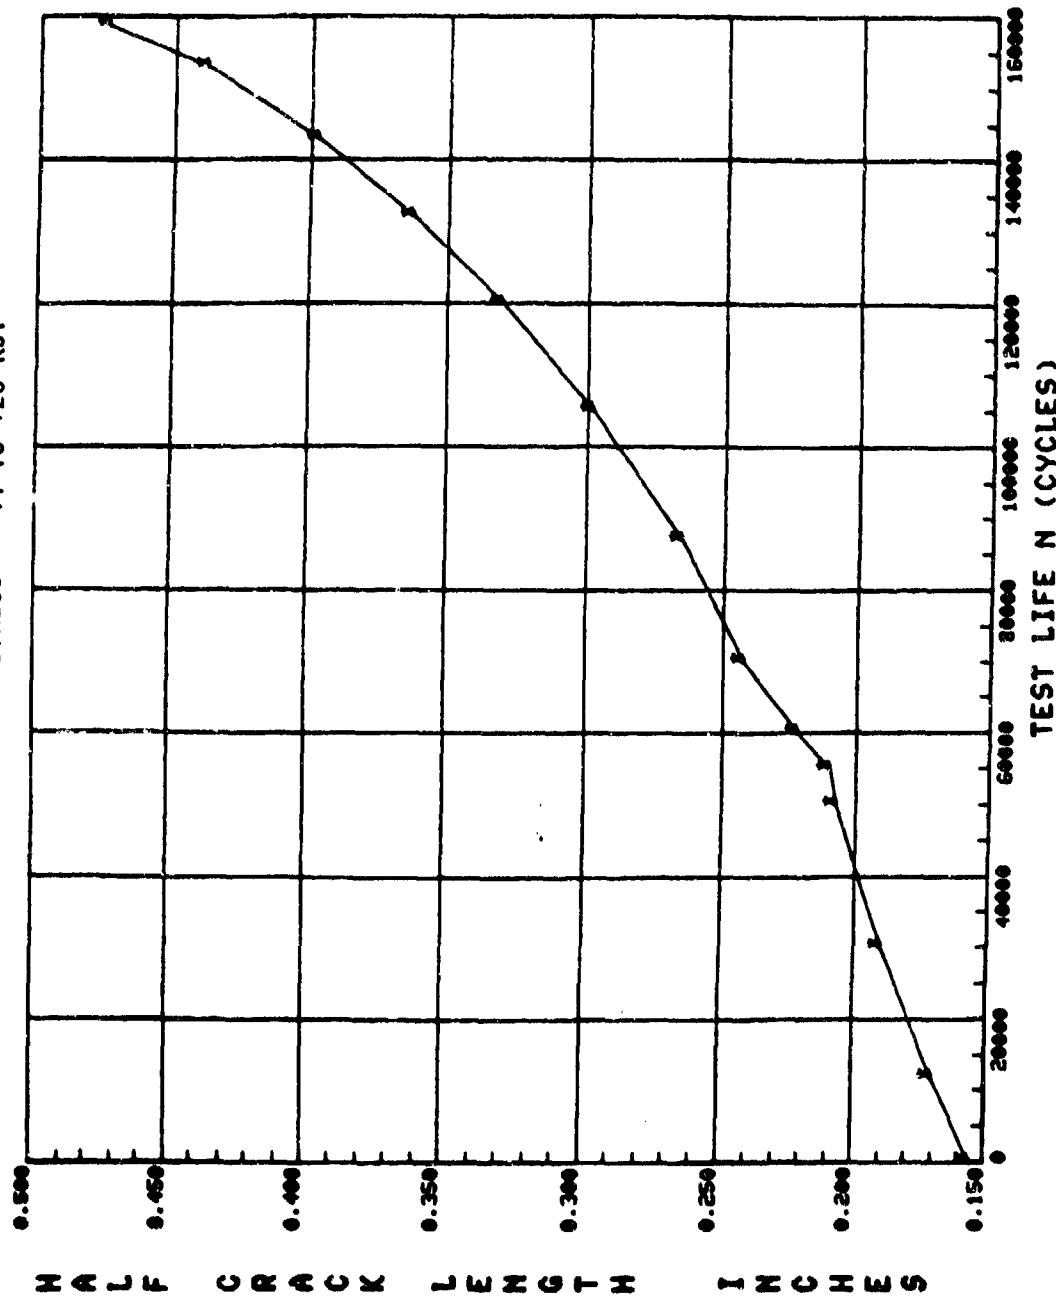


Figure 10. Crack growth curve for test B-3.

TABLE 6. DATA TABULATION FOR TEST B-4

SPECIMEN NO.: B-4		STRESS -6 +20 KSI		W= 6.000 IN.		A= 0.0 IN.		TEST FREQ= 6.00HZ.		DATA	
PCN#	SPECIMEN	P MAX=	30.0KIPS	R= -0.30						DELTA K	
1	0-	0.325	0.324	0.997473	14.30	16.59	1.69E-05				
2	832-	0.353	0.354	0.996965	14.94	19.42	1.96E-05				
3	2000+	0.415	0.405	0.997054	16.00	20.60	2.78E-05				
4	3006-	0.460	0.470	0.996535	17.25	22.42	3.432E-05				
5	4000-	0.545	0.546	0.996795	18.61	24.20	4.191E-05				
6	4700-	0.620	0.607	0.998567	19.65	25.54	4.926E-05				
7	5200-	0.650	0.660	0.994199	20.51	26.66	5.747E-05				
8	5700-	0.710	0.716	0.995468	21.38	27.80	6.374E-05				
9	6200-	0.760	0.779	0.997431	22.35	29.06	7.567E-05				
10	6600-	0.855	0.846	0.996236	23.34	30.34	8.615E-05				
11	6900-	0.870	0.899	0.997632	24.69	31.32	9.644E-05				
12	7200-	0.960	0.957	0.996455	24.90	32.37	1.126E-04				
13	7470-	1.015	1.017	0.998371	25.72	33.44	1.263E-04				
14	7730-	1.065	1.069	0.996610	26.62	34.64	1.473E-04				
15	7970-	1.170	1.162	0.999088	27.63	35.92	1.661E-04				
16	8170-	1.225	1.232	0.998465	28.54	37.10	1.870E-04				
17	8370-	1.310	1.309	0.998836	25.51	38.37	2.118E-04				
18	8540-	1.380	1.381	0.999762	30.42	39.54	2.375E-04				
19	8790-	1.460	1.462	0.999477	31.44	40.85	2.712E-04				
20	8850-	1.545	1.545	0.999913	32.45	42.15	3.044E-04				
21	8980-	1.625	1.622	0.999166	33.46	43.50	3.407E-04				
22	9080-	1.750	1.698	0.999815	34.32	44.61	3.731E-04				
23	9170-	1.765	1.767	0.999651	35.16	45.71	4.074E-04				
24	9240-	1.825	1.825	0.998199	35.66	46.62	4.594E-04				
25	9310-	1.890	1.890	0.998374	36.66	47.66	4.953E-04				
26	9370-	1.945	1.952	0.998329	37.43	48.66	5.360E-04				
27	9430-	2.030	2.019	0.998167	38.25	49.72	5.647E-04				
28	9480-	2.075	2.079	0.998002	38.99	>0.69	6.314E-04				

TABLE 6. DATA TABULATION FOR TEST B-4 (CONCL.)

SPECIMEN NO.:	B-4	STRESS -6 TO +20 KSI		W= 6.000 IN.	A= 0.0 IN.	TEST FREQ= 6.00HZ.
		GUT SPECIMEN	6x 0.250 IN.			
PLATE=	-9.0 KIPS	P MAX=	30.0 KIPS	R=-6.30		
ENVIRONMENT CONDITION: ROOM AMBIENT						
NU.	CYCLES	MEASUREMENTS	AIRREGRESSION	MULT. CORR. COEFF	K-MAX	DATA
29	9530.	2-140	2-144	0.997312	39.80	51.74 7.007E-04
30	9570.	2-260	2-197	0.99762	40.47	52.61 7.479E-04
31	9610.	2-260	2-264	0.999461	41.31	53.71 6.391E-04
32	9650.	2-335	2-334	0.999398	42.21	54.67 9.164E-04
33	9680.	2-345	2-390	0.999405	42.94	55.82 9.712E-04
34	9710.	2-445	2-449	0.996436	43.71	56.63 1.067E-03
35	9740.	2-515	2-511	0.996434	44.23	57.89 1.198E-03
36	9770.	2-5fc	2-586	0.998758	45.54	59.20 1.329E-03
37	9800.	2-670	2-671	0.998843	46.71	60.73 1.517E-03
38	9820.	2-7fc	2-749	0.998264	47.80	62.14 1.729E-03
39	9850.	2-670	2-839	0.997525	49.09	63.82 2.024E-03
40	9870.	2-915	2-919	0.998356	50.42	65.26 2.325E-03
41	9890.	3.015	3.012	0.997922	51.69	67.19 2.889E-03
42	9910.	3.130	3.137	0.994764	53.67	69.77 3.919E-03
43	9920.	3.200	3.212	0.995675	54.90	71.37 4.941E-03
44	9930.	3.365	3.310	0.999147	56.57	73.54 5.986E-03
45	9940.	3.435	3.436	0.999976	58.82	76.46 7.416E-03
46	9950.	3.600	3.600	0.999969	61.96	80.54 8.921E-03

PLOTRATE CRACK GROWTH ANALYSIS
B-4 STRESS = -6 TG +20 KSI

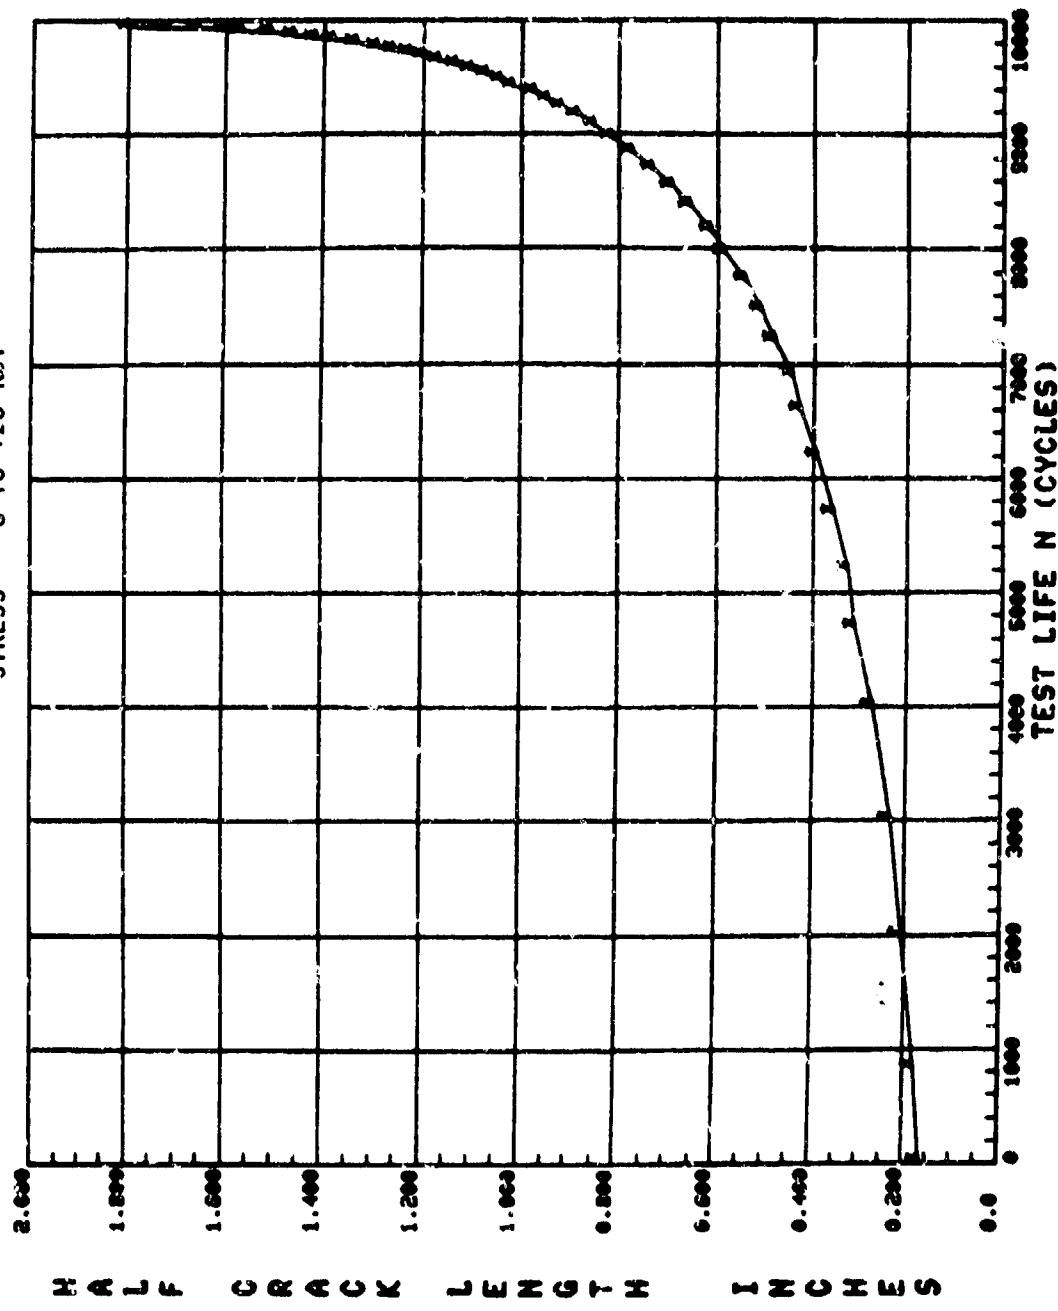


Figure 11. Crack growth curve for test B-4.

TABLE 7. DATA TABULATION FOR TEST B-5

SPECIMEN NO.: B-5		BASELINE STRESS = -2 TO 20 KSI		TEST FREQ= 6.00HZ.	
CCT SPECIMEN	B= 0.250 IN.	W= 6.000 IN.	AH= 0.0	IN.	
PHI=	-3.0 KIPS	RMAX=	30.0 KIPS	R=-6.10	
ENVIRONMENT CONDITION: ROOM AMBIENT					
NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR. COEFF	R-MAX
1	0.	0.303	0.303	0.997602	13.51
2	2700.	0.365	0.380	0.998558	15.49
3	4200.	0.440	0.447	0.998669	16.82
4	5400.	0.510	0.517	0.998426	18.10
5	6400.	0.580	0.584	0.999107	19.26
6	7100.	0.640	0.642	0.998891	20.22
7	7800.	0.705	0.705	0.999165	21.22
8	8400.	0.770	0.772	0.999040	22.25
9	8700.	0.805	0.808	0.997117	22.78
10	9000.	0.855	0.851	0.997588	23.40
11	9300.	0.840	0.898	0.997732	24.07
12	9600.	0.960	0.953	0.999766	24.85
13	9900.	1.010	1.014	0.997786	25.63
14	10200.	1.065	1.061	0.994902	26.58
15	10400.	1.130	1.129	0.996807	27.21
16	10600.	1.175	1.168	0.995594	27.97
17	10800.	1.260	1.252	0.996429	28.80
18	10902.	1.295	1.292	0.995766	29.30
19	11000.	1.330	1.330	0.997423	29.79
20	11100.	1.365	1.363	0.997622	30.20
21	11200.	1.400	1.408	0.996536	30.76
22	11300.	1.450	1.452	0.997946	31.30
23	11400.	1.510	1.497	0.998382	31.84
24	11600.	1.595	1.598	0.998033	32.09
25	11800.	1.715	1.715	0.998865	34.53
26	11950.	1.820	1.821	0.999360	35.82
27	12104.	1.955	1.957	0.998720	37.48
28	12256.	2.110	2.115	0.996903	39.43

TABLE 7. DATA TABULATION FOR TEST B-5 (CONCL)

SPECIMEN NO.: B-5		BASELINE STRESS = -2 TO 20 KSI					
CCT	SPECIMEN	E= 0.250 IN.	W= 6.000 IN.	A _N = 0.0	I _N .		
P _{MIN} =	-3.0 KIPS	P _{MAX} = 30.0 KIPS	R=-0.10	H _{S1}	FREQ= .6.00HZ.		
ENVIRONMENT CONDITIONS FROM AMBIENT							
NO.	CYCLES	AI(MEASURED)	AI(REGRESSION)	MULT. CORR.	COEFF	K-MAX	DELTA,K.
29	12356.	2.245	2.243	0.991703	41.65	45.15	9.031E-04
30	12496.	2.465	2.416	0.984603	43.27	47.60	1.263E-03
31	12556.	2.640	2.674	0.991253	46.75	51.43	1.499E-03
32	12656.	3.015	3.085	0.994741	52.84	58.12	2.469E-03
33	12706.	3.296	3.386	0.996767	57.86	63.65	3.547E-03

PLOTRATE CRACK GROWTH ANALYSIS
B-5 BASELINE STRESS = -2 TO 20 ksi

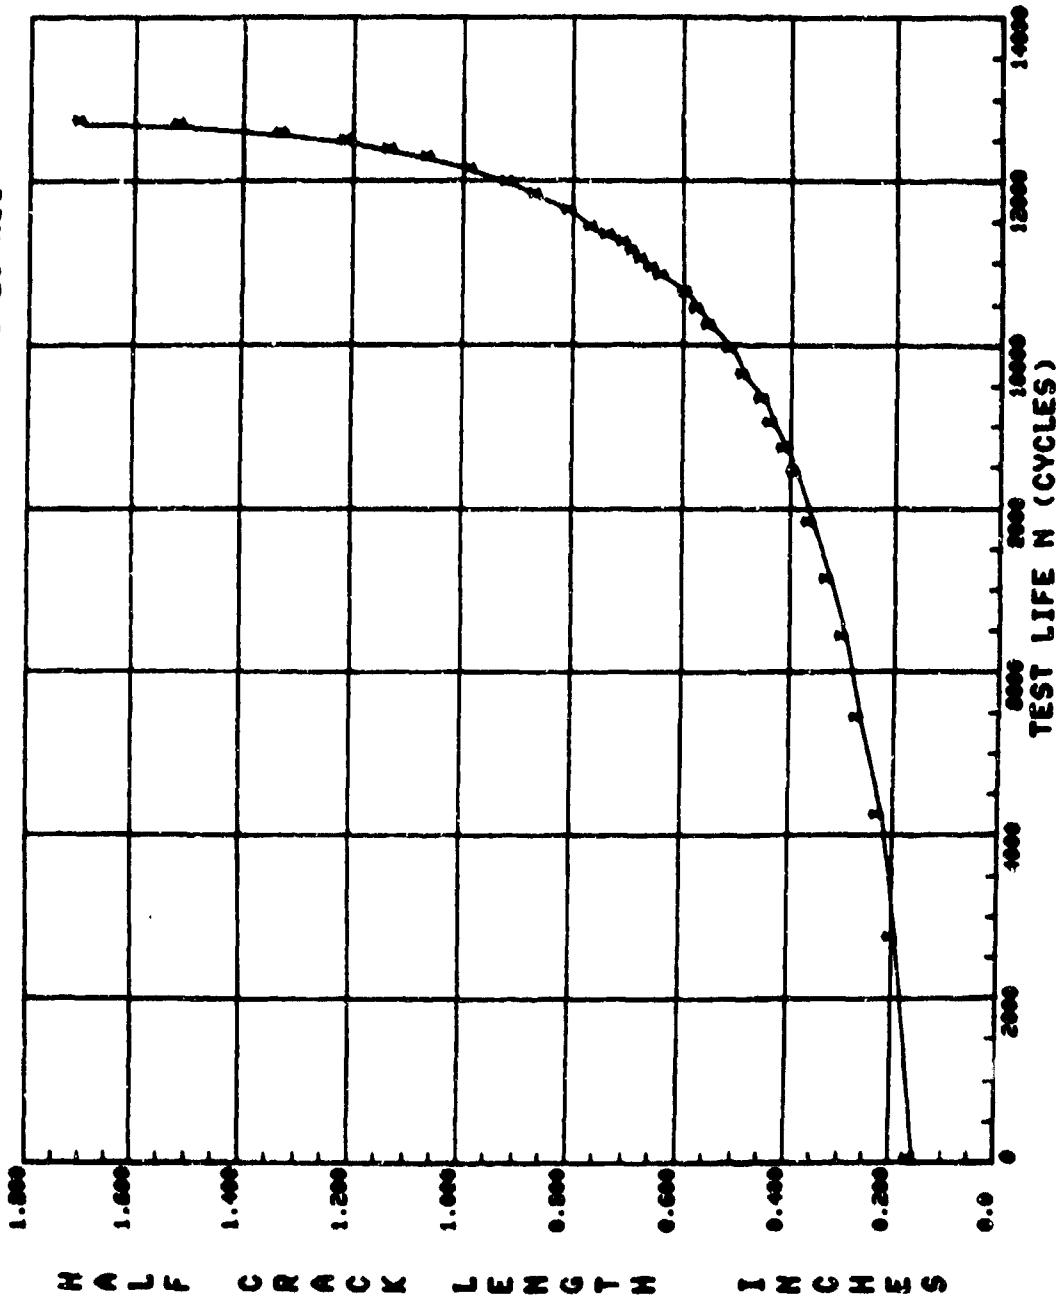


Figure 12. Crack growth curve for test B-5.

TABLE 8. DATA TABULATION FOR TEST B-6-1

SPECIMEN NO.: B-6-1		BASELINE, 20 KSI STRESS		TEST FREQ= 3.00HZ.	
LCT	SPECIMEN	B= 0.250 IN.	M= 6.000 IN.	AH= 0.0	IN.
MIN=	0.3KIPS -	PMAX=	30.0KIPS	R= 0.01	
ENVIRONMENT CONDITION:	ROOM AMBIENT				
NO.	CYCLES	AM MEASURED!	AM REGRESSION!	MULT. COEF.	COEFF
1	0.	0.305	0.305	0.999714	13.87
2	600.	0.335	0.331	0.994295	14.45
3	1200.	0.355	0.354	0.995726	14.94
4	1800.	0.370	0.375	0.996185	15.38
5	2400.	0.395	0.391	0.993533	15.71
6	3000.	0.410	0.406	0.979309	16.02
7	3600.	0.425	0.430	0.969235	16.50
8	4200.	0.451	0.462	0.991599	17.10
9	4800.	0.510	0.503	0.991654	17.85
10	5400.	0.550	0.547	0.997509	18.64
11	6000.	0.590	0.591	0.997705	19.38
12	6600.	0.630	0.631	0.999243	20.05
13	7200.	0.680	0.678	0.997720	20.79
14	7800.	0.720	0.733	0.998432	21.65
15	8400.	0.795	0.801	0.998109	22.67
16	9700.	0.865	0.839	0.998054	23.22
17	9000.	0.685	0.681	0.996250	23.83
18	9300.	0.960	0.929	0.995754	24.50
19	9600.	0.975	0.978	0.997125	25.16
20	9900.	1.045	1.033	0.997334	25.93
21	10200.	1.046	1.046	0.9997690	26.76
22	10500.	1.160	1.164	0.998277	27.67
23	10800.	1.241	1.260	0.999386	28.64
24	11100.	1.330	1.334	0.999330	29.34
25	11200.	1.365	1.368	0.994216	30.26
26	11300.	1.405	1.403	0.99154	30.69
27	11400.	1.445	1.442	0.999043	31.16
28	11500.	1.490	1.462	0.999076	31.68

TABLE 8. DATA TABULATION FOR B-6-1 (CONCL.)

SPECIMEN NO.: B-6-1		EASELINE, 20 KSI STRESS		TEST FREQU= 3.00HZ		TEST FREQ= 3.00HZ	
CC1	SPECIMEN	R= 0.250 IN.	W= 6.000 IN.	AH= 0.0	IN.	AH= 0.0	IN.
PWHS=	0.3 KIPS	P MAX=	30.0 KIPS	R= 0.01			
ENVIRONMENT CONDITION: ROOM AMBIENT							
NO.	CYCLES	AM MEASUR (D)	AL REGRESSION	MULT. COEF	K-MAX	DELTA K	DA/DN
29	11600.	1.520	1.523	0.995222	32.16	31.86	2.069E-04
30	11700.	1.570	1.565	0.996611	32.69	32.36	2.434E-04
31	11800.	1.610	1.611	0.996954	33.26	32.94	2.402E-04
32	11900.	1.655	1.640	0.997320	33.86	33.52	2.536E-04
33	12000.	1.715	1.711	0.999326	34.48	34.13	2.714E-04
34	12100.	1.770	1.768	0.999563	35.16	34.82	2.955E-04
35	12200.	1.825	1.830	0.999457	35.93	35.57	3.125E-04
36	12300.	1.625	1.893	0.999520	36.70	36.33	3.321E-04
37	12400.	1.965	1.960	0.999640	37.52	37.14	3.661E-04
38	12500.	2.030	2.036	0.999232	38.46	38.07	4.006E-04
39	12600.	2.115	2.116	0.999389	39.45	39.05	4.662E-04
40	12700.	2.215	2.206	0.999060	40.54	40.18	5.214E-04
41	12800.	2.310	2.316	0.999037	41.99	41.57	6.137E-04
42	12900.	2.440	2.444	0.999448	43.65	43.21	7.283E-04
43	13000.	2.600	2.599	0.999314	45.12	45.26	9.144E-04
44	13050.	2.690	2.642	0.997334	46.99	46.53	1.094E-03
45	13100.	2.790	2.798	0.996463	48.51	48.00	1.245E-03
46	13150.	2.925	2.895	0.974989	49.92	49.42	2.004E-03
47	13200.	3.100	3.105	0.985610	53.14	52.63	2.931E-03
48	13250.	3.330	3.423	0.991047	58.57	57.99	4.275E-03
49	13300.	3.940	3.936	0.995574	69.35	68.66	6.070E-03

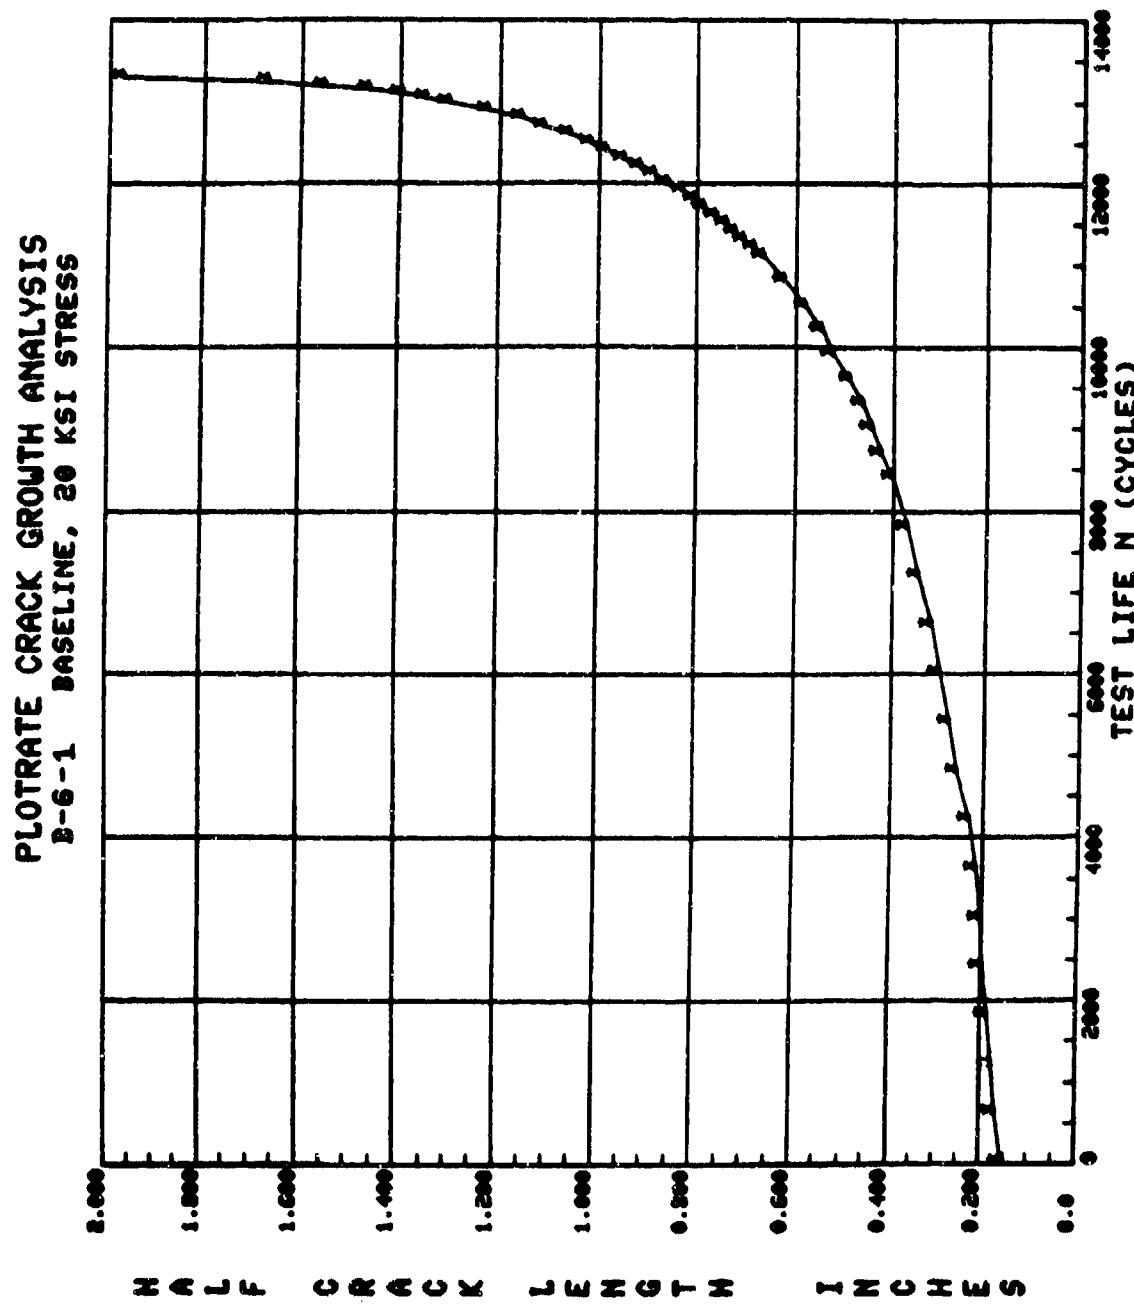


Figure 13. Crack growth curve for test B-6-1.

TABLE 9. DATA TABULATION FOR TEST B-6-2

SPECIMEN NO.: B-6-2 BASELINE: 20 KSI STRESS

GCT SPECIMEN B= 0.250 IN. H= 6.000 IN. A= 0.0 IN.
 PMIN= 0.3 KIPS PHAX= 30.0KIPS R= 0.01 TEST FREQ= 6.00HZ.

ENVIRONMENT CONDITION: ROOM AMBIENT

NO.	CYCLES	A MEASURED	A REGRESSION	MULT. CORR. COEFF	K-MAX	DELTA K	DA/DN
1	0.	0.315	0.315	0.999996	14.09	13.95	1.322E-05
2	1200.	0.350	0.345	0.997148	14.76	14.61	1.527E-05
3	2850.	0.410	0.409	0.998022	16.08	15.92	2.308E-05
4	3800.	0.450	0.457	0.998263	17.01	16.64	2.813E-05
5	4600.	0.510	0.504	0.997000	17.87	17.69	3.474E-05
6	5200.	0.550	0.555	0.995774	18.77	18.58	3.855E-05
7	5900.	0.600	0.605	0.996069	19.61	19.41	4.304E-05
8	6400.	0.660	0.648	0.996507	20.31	20.11	4.704E-05
9	6900.	0.690	0.699	0.996865	21.12	20.91	5.093E-05
10	7400.	0.750	0.751	0.996584	21.42	21.70	5.439E-05
11	7900.	0.610	0.604	0.996651	22.72	22.49	6.376E-05
12	8200.	0.840	0.845	0.996698	23.31	23.06	7.068E-05
13	8500.	0.880	0.886	0.998172	23.90	23.66	7.966E-05
14	68000.	0.940	0.933	0.995229	24.57	24.32	9.167E-05
15	9100.	0.990	0.995	0.998674	25.41	25.16	1.036E-04
16	9400.	1.060	1.061	0.998746	26.31	26.05	1.145E-04
17	9700.	1.140	1.133	0.996105	27.25	26.98	1.348E-04
18	9900.	1.180	1.189	0.994884	26.00	27.72	1.513E-04
19	10000.	1.210	1.216	0.991552	26.37	26.08	1.527E-04
20	10100.	1.260	1.249	0.985752	28.76	28.48	1.522E-04
21	10200.	1.290	1.263	0.953696	26.19	26.90	1.732E-04
22	10300.	1.310	1.317	0.984885	29.62	29.32	1.768E-04
23	10400.	1.340	1.349	0.992984	30.02	29.72	1.839E-04
24	10500.	1.400	1.389	0.992549	36.52	36.22	2.000E-04
25	10600.	1.430	1.434	0.996342	31.06	30.77	2.174E-04
26	10700.	1.460	1.476	0.995842	31.62	31.30	2.321E-04
27	10800.	1.520	1.523	0.997411	32.18	31.66	2.321E-04
28	10900.	1.570	1.571	0.997828	32.77	32.45	2.536E-04

TABLE 9. DATA TABULATION FOR TEST B-6-2 (CONCL)

SPECIMEN NO.: B-6-2		BASELINE, 20 KSI STRESS			
ST. SPECIMEN	t= 0.250 IN.	W= 6.000 IN.	A= 0.0	IN.	
MIN=	0.3KIPS	P MAX=	30.0KIPS	R= 0.01	TEST FREQ= 6.00HZ.
ENVIRONMENT CONDITION: ROOM AMBIENT					
NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR. COEFF	K-MAX
29	11000.	1.630	1.623	0.997649	33.41
30	11100.	1.670	1.677	0.997411	34.06
31	11200.	1.740	1.730	0.995129	34.72
32	11300.	1.790	1.799	0.993988	35.56
33	11400.	1.870	1.875	0.994862	36.48
34	11500.	1.980	1.960	0.994856	37.43
35	11580.	2.020	2.035	0.993374	38.45
36	11660.	2.120	2.116	0.992165	39.46
37	11740.	2.190	2.198	0.993056	40.49
38	11790.	2.280	2.265	0.993673	41.33
39	11836.	2.310	2.324	0.993808	42.08
40	11844.	2.400	2.384	0.992463	43.04
41	11910.	2.440	2.435	0.996196	43.52
42	11940.	2.490	2.495	0.998033	44.32
43	11970.	2.550	2.556	0.997835	45.13
44	12000.	2.630	2.620	0.997198	46.00
45	12035.	2.710	2.706	0.997495	47.20
46	12060.	2.760	2.769	0.994954	48.06
47	12090.	2.870	2.863	0.998477	49.44
48	12120.	2.970	2.962	0.999077	51.23
49	12150.	3.140	3.133	0.998959	53.60
50	12180.	3.310	3.311	0.998783	56.58
					56.01
					3.311E-03

PLOTRATE CRACK GROWTH ANALYSIS
B-6-2 BASELINE, 20 KSI STRESS

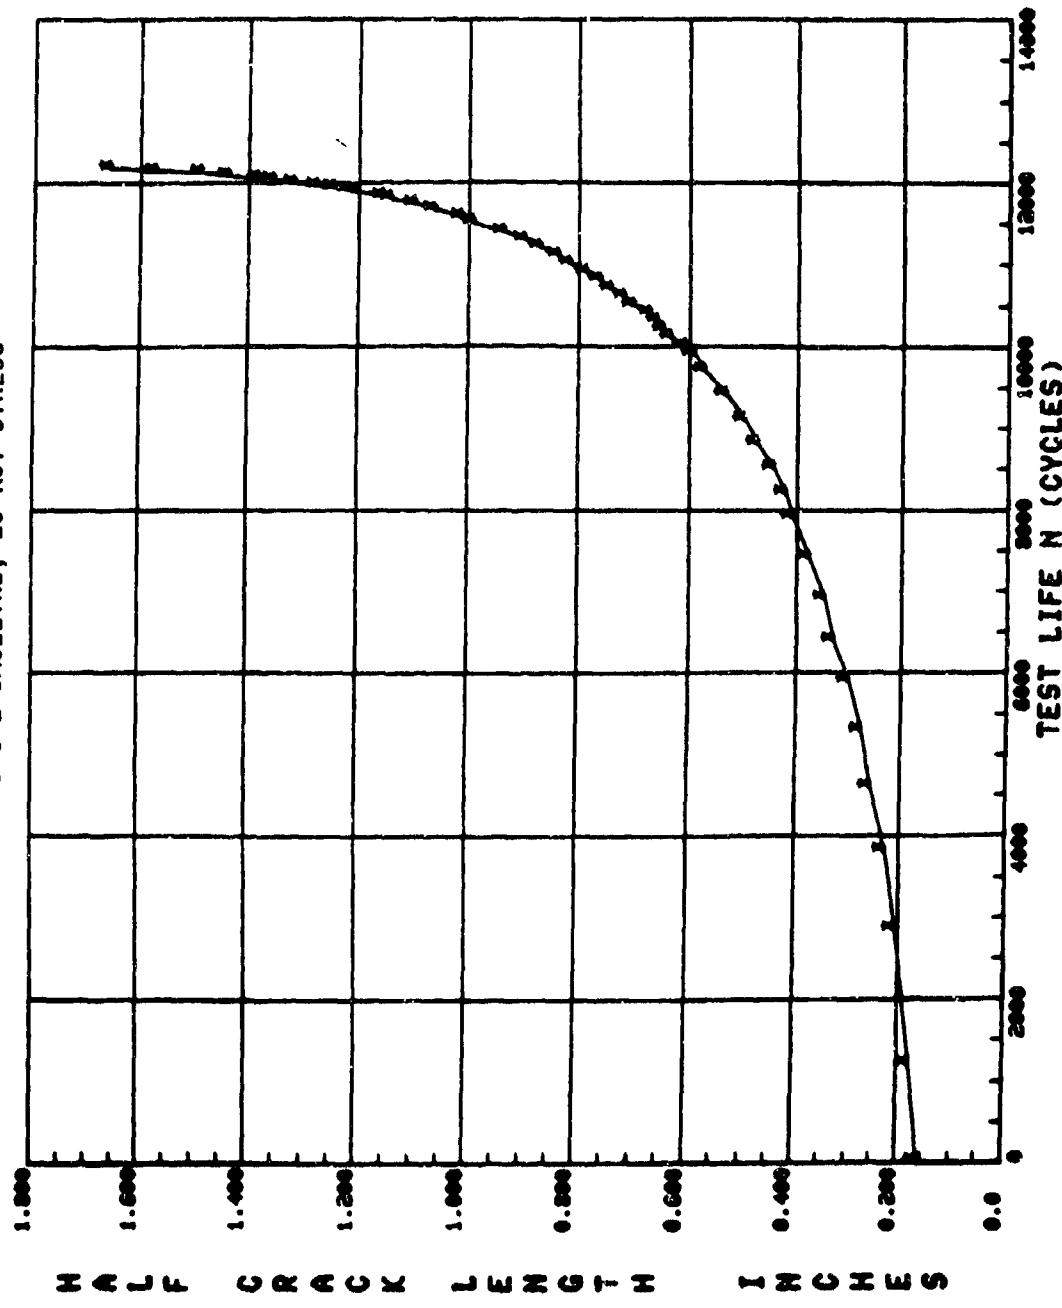


Figure 14. Crack growth curve for test B-6-2.

TABLE 10. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP I -
CONSTANT-AMPLITUDE LOAD

Test No.	Applied Base Load			Over-/Under-load		N_I Cycle	N_{II} Cycle	Comments
	Loading Profile	σ_{Max} Ksi	σ_{Min} Ksi	σ_{Max} Ksi	σ_{Min} Ksi			
M-1		8	0					da/dn at low ΔK range, $R = 0$
M-2		8	2.4					da/dn at low ΔK range, $R = 0.3$
M-3		8	-8					da/dn at $R = -1$
M-4		8	-2.4					da/dn of negative stress ratio at low ΔK range
M-5		40	0					da/dn at high ΔK range, $R = 0$
M-6		40	12					da/dn at high ΔK range, $R = 0.5$
M-7		40	28					da/dn at high ΔK range, $R = 0.7$
M-8		40	-4					da/dn of negative stress ratio at high ΔK range
M-9		8	-0.8					da/dn of negative stress ratio at low ΔK range, $R = -0.1$
M-10		20	-6					da/dn of negative stress ratio at high ΔK range, $R = -0.3$

TABLE II. DATA TABULATION FOR TEST M-1

SPF INDEX NO.:	M-1	CENTER CHECKED PARTL. STRESS = 8KSI. R = .1		
TEST SPECIMEN	R = 0.250 IN.	b = 1.000 IN.	A = 0.0 IN.	
PWIND =	0.0 KIPS	PMAX = 12.0 KIPS	P = 0.0	TEST FREQ = 6.000HZ.
ENVIRONMENT CONDITION: ROOM AMBIENT				
NO.	CYCLES	Δ (MEASURED)	Δ (PREGRESSION)	MULT. CORR. CORFF
1	0.	0.280	0.280	0.99551
2	750000	0.345	0.344	0.995652
3	1050000	0.380	0.386	0.995188
4	1200000	0.420	0.412	0.995980
5	1400000	0.445	0.453	0.995300
6	1550000	0.485	0.485	0.996613
7	1700000	0.525	0.526	0.99092
8	1970000	0.565	0.564	0.99658
9	2060000	0.660	0.667	0.999294
10	2230000	0.730	0.736	0.998019
11	2330000	0.785	0.788	0.998827
12	2410000	0.825	0.827	0.999794
13	2480000	0.850	0.846	0.999688
14	2550000	0.940	0.942	0.999463
15	2620000	1.000	1.000	0.998011
16	2680000	1.060	1.055	0.998767
17	2740000	1.110	1.118	0.998638
18	2800000	1.155	1.150	0.998988
19	2860000	1.270	1.273	0.999077
20	2910000	1.355	1.343	0.999252
21	2940000	1.400	1.400	0.999144
22	2970000	1.455	1.452	0.999334
23	3000000	1.500	1.502	0.999487
24	3030000	1.555	1.556	0.999412
25	3060000	1.615	1.615	0.990750
26	3090000	1.680	1.680	0.999741
27	3120000	1.755	1.751	0.999582
28	3150000	1.825	1.830	0.996518

TABLE 11. DATA TABULATION FOR TABLE M-1 (CONCL)

SPECIMEN NO.:	CCT	SPECIMEN	R = 0.250 IN.	W = 6.000 IN.	AN = 0.01	IN.	TEST FREQ = 6.000 Hz.	
							POLY = 0.0 KIPS	PHASE = 12.0 KIPS
ENVIRONMENT CONDITION: ROOM AIR/VENT								
NO.	CYCLES	A(FEASIBLE)	A(POSSIBLE)	W(HZ)	TEST FREQ	EFF	K-MAX	DA/DN
29	318000.	1.915	1.915	0.999486	14.79	14.79	1.503E-05	
30	321000.	2.012	2.011	0.998789	15.26	15.26	1.589E-05	
31	324000.	2.105	2.113	0.999308	15.76	15.76	1.673E-05	
32	327000.	2.222	2.211	0.997773	16.26	16.26	1.601E-05	
33	330000.	2.315	2.317	0.998149	16.80	16.80	1.970E-05	
34	333000.	2.425	2.475	0.998353	17.41	17.41	2.247E-05	
35	336000.	2.560	2.573	0.997740	18.14	18.14	2.565E-05	
36	339000.	2.725	2.717	0.999653	19.05	19.05	3.033E-05	
37	242000.	2.925	2.920	0.996976	20.12	20.12	3.729E-05	
38	245000.	3.145	3.146	0.994730	21.51	21.51	4.775E-05	
39	248000.	3.415	3.415	0.996111	23.62	23.62	6.219E-05	
40	251000.	3.820	3.911	0.967938	27.03	27.03	8.493E-05	
41	352400.	4.125	4.122	0.7950174	29.67	29.67	1.050E-04	

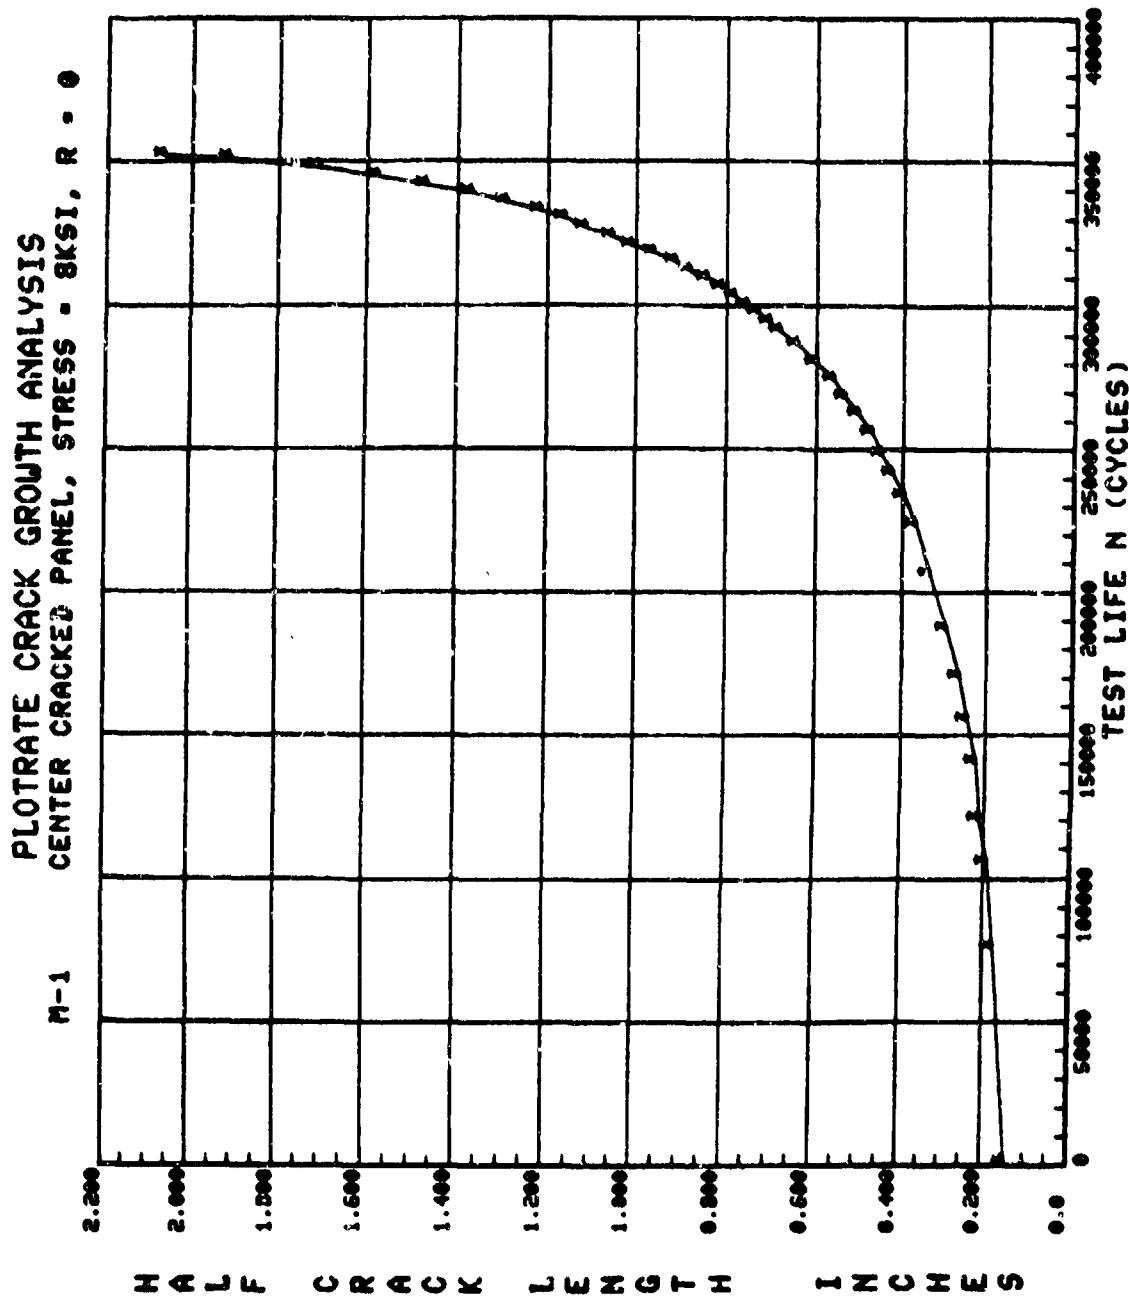


Figure 15. Crack growth curve for test M-1.

TABLE 12. DATA TABULATION FOR TEST M-2

SPECIMEN NO.: 2		CENTER SPACK PANEL STRESS = 2.4 TO 8.0 KSI			
CCT	SPECIMEN	A = 0.750 IN.	B = 1.000 IN.	E _N = 0.01	I _N
P _{MIN}	3.6 KIPS	P _{MAX} = 12.0 KIPS	R = 0.30	TEST F _{FF0} = 6.00 '47.	
ENVIRONMENT CONDITION: ROOM AMBIENT					
No.	CYCLES	ALMATERIAL	ALMATERIAL	MULT.	CF _{EF} , CF _{EFF}
1	0.	0.305	0.305	0.959434	5.51
2	45000.	0.346	0.326	0.98735	5.32
3	96000.	0.375	0.374	0.998455	5.11
4	145000.	0.420	0.423	0.998877	6.54
5	195000.	0.480	0.479	0.999243	6.97
6	237000.	0.540	0.535	0.998766	7.37
7	245000.	0.545	0.546	0.998164	7.44

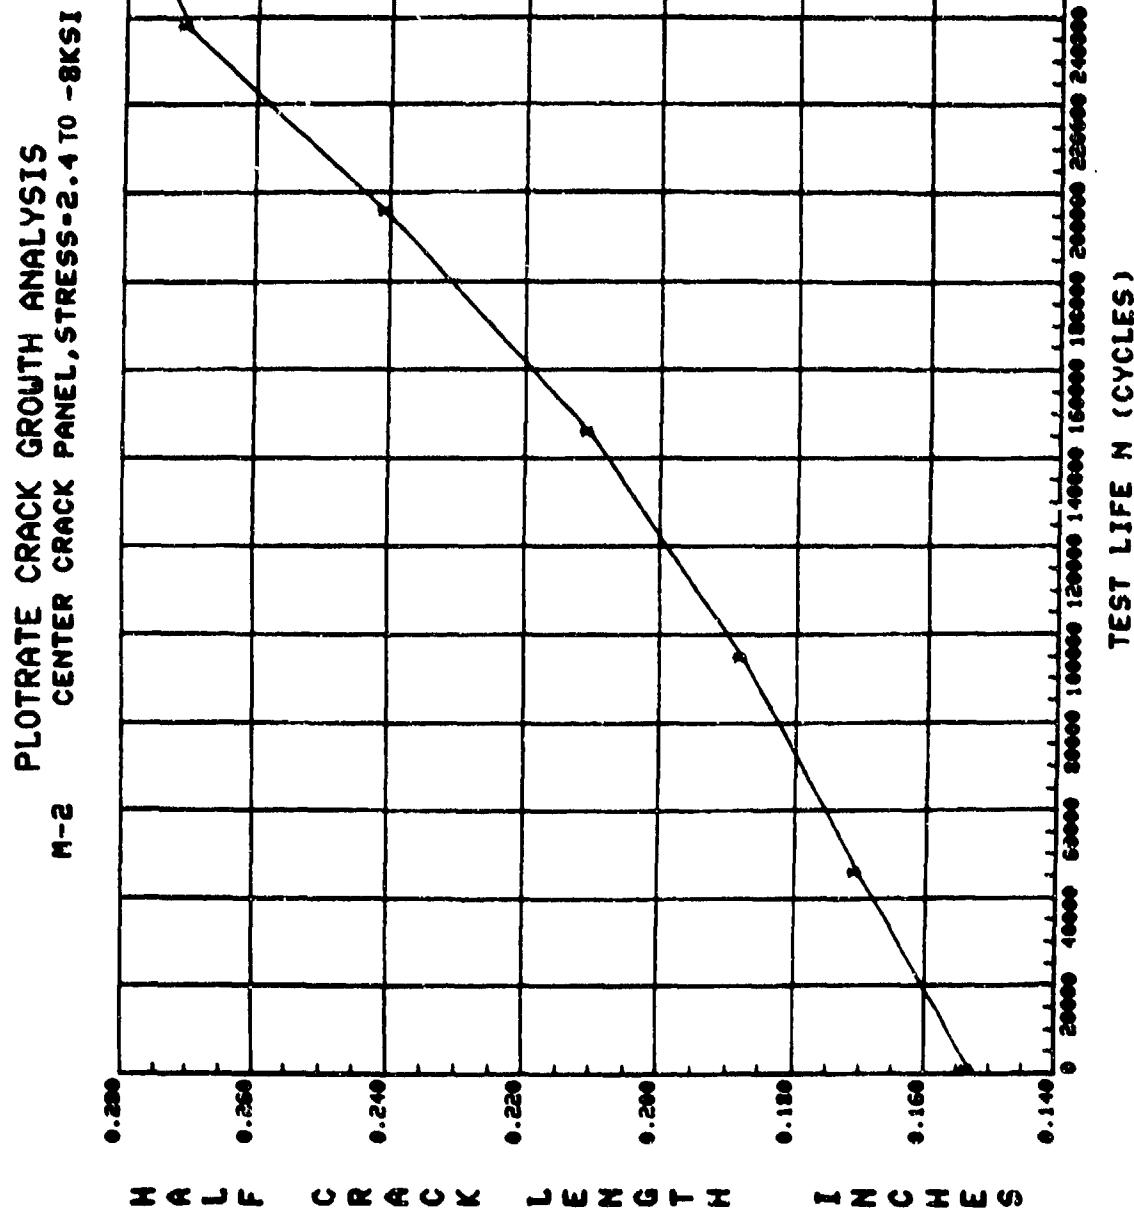


Figure 16. Crack growth curve for test M-2.

TABLE 13. DATA TABULATION FOR TEST M-3

TEST NUMBER	SPECIMEN	A = 0.250 IN.	W = 6.000 IN.	AA = 0.0	TEST FREQU. 6.00 Hz.	ENVIRONMENT CONDITIONS: AMBIENT AIR	
						R = -1.0 KIPS	P MAX = 12.0 KIPS
1	CYCLES	0.305	0.3HS	MULT.	Coeff.	K-MAX	DA/HN
2	13000.	0.415	0.413	0.99846	6.24	12.47	9.75E-07
3	18100.	0.425	0.427	0.987542	6.46	12.92	1.61E-06
4	28100.	0.470	0.488	0.974382	6.58	13.15	2.25E-06
5	33107.	0.520	0.577	0.968056	7.93	14.06	2.78E-06
6	39100.	0.585	0.56	0.974799	7.31	14.63	2.87E-06
7	510877.	0.635	0.636	0.981746	7.58	15.16	2.876E-06
8	600877.	0.660	0.673	0.965216	8.05	16.09	2.40E-06
9	658377.	0.680	0.696	0.981950	8.37	16.53	2.275E-06
10	701837.	0.707	0.711	0.998900	8.57	15.74	2.916E-06
11	754377.	0.750	0.751	0.998992	8.77	17.05	3.669E-06
12	800877.	0.803	0.801	0.999235	9.07	17.54	4.476E-06
13	851773.	0.851	0.851	0.999199	9.36	18.14	5.344E-06
14	89000.	0.867	0.901	0.499154	9.65	18.73	6.183E-06
15	92000.	0.940	0.962	0.999132	9.88	19.29	6.732E-06
16	95500.	1.000	0.996	0.998662	10.17	20.35	7.822E-06
17	99000.	1.050	1.053	0.998493	10.49	21.97	8.541E-06
18	102500.	1.120	1.114	0.998436	10.81	21.61	9.414E-06
19	106000.	1.175	1.180	0.998925	11.15	22.30	1.055E-05
20	109500.	1.255	1.256	0.998976	11.55	23.10	1.183E-05
21	112000.	1.320	1.318	0.999384	11.85	23.71	1.282E-05
22	114500.	1.350	1.349	0.999780	12.20	24.41	1.376E-05
23	116800.	1.450	1.449	0.998348	12.51	25.02	1.4e1F-05
24	119800.	1.545	1.517	0.977744	12.94	25.83	1.703E-05
25	122955.	1.625	1.645	0.998742	13.47	26.94	1.979E-05
26	125855.	1.770	1.772	0.998717	14.09	28.17	2.329E-05
27	129414.	1.910	1.897	0.998439	14.70	29.40	2.731E-05
28	129233.	1.940	1.942	0.998433	14.92	29.84	2.537E-05

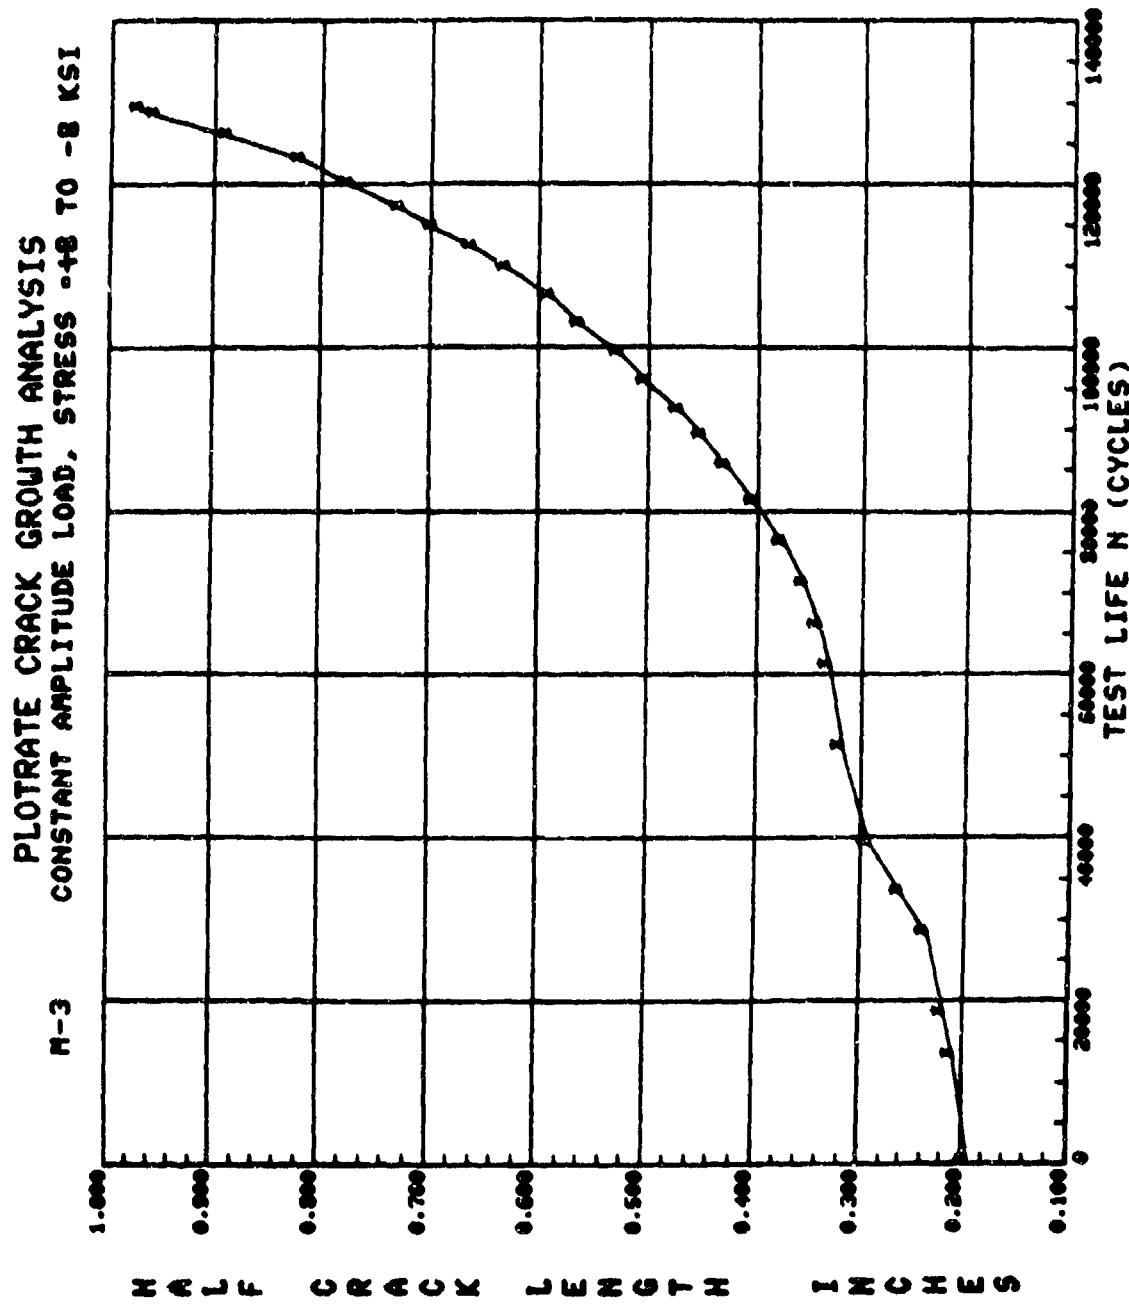


Figure 17. Crack growth curve for test M-3.

TABLE 14. DATA TABULATION FOR TEST M-4

SPECIMEN NO.: 4-4 CENTER CRACK SAWN-1 STRESS -2.4 TO +8 KSI
 CCT SPECIMEN R = 0.250 IN. W = 4.0000 IN.
 PMIN = -3.6 KIPS PMAX = 12.0 KIPS R = -0.30 TEST FREQ = 6.000 Hz.
 ENVIRONMENT CONDITION: ROOM AMBIENT

NR.	CYRLES	AIRFASLIPFD	AIRPRESSURE	PULTR. CTEPP.	CTEFF	K-MAX	DA/DW	DELTA K
1	0.	0.305	0.999560	5.54	7.21	8.49E-07		
2	1.75001.	0.325	0.998614	5.83	7.58	1.09E-06		
3	4.00000.	0.327	0.998614	5.83	7.58	1.09E-06		
4	4.00000.	0.400	0.997569	6.32	8.21	1.69E-06		
5	5.50000.	0.445	0.998181	6.77	8.80	2.15E-06		
6	6.50000.	0.455	0.998794	7.10	9.23	2.54E-06		
7	7.50000.	0.550	0.949285	7.47	9.71	2.97E-06		
8	8.50000.	0.610	0.998611	7.93	10.27	3.54E-06		
9	9.50000.	0.685	0.999133	8.38	10.89	4.16E-06		
10	10.20001.	0.745	0.999836	8.74	11.37	4.732E-06		
11	10.80000.	0.810	0.997751	9.10	11.84	5.30E-06		
12	11.30000.	0.860	0.999294	9.42	12.25	5.94E-06		
13	11.80001.	0.920	0.998017	9.76	12.69	6.940E-06		
14	12.20001.	0.975	0.999254	10.07	13.09	7.746E-06		
15	12.60000.	1.040	0.997133	10.43	13.56	8.237E-06		
16	12.90000.	1.105	0.997711	10.72	13.93	8.543E-06		
17	13.20000.	1.155	0.997131	10.99	14.29	9.063E-06		
18	13.50000.	1.198	0.997131	11.27	14.65	9.464E-06		
19	13.80001.	1.255	0.997240	11.55	15.01	1.001E-05		
20	14.10000.	1.325	0.999201	11.86	15.42	1.17E-05		
	14.40000.	1.350	0.999576	12.22	15.88	1.161E-05		

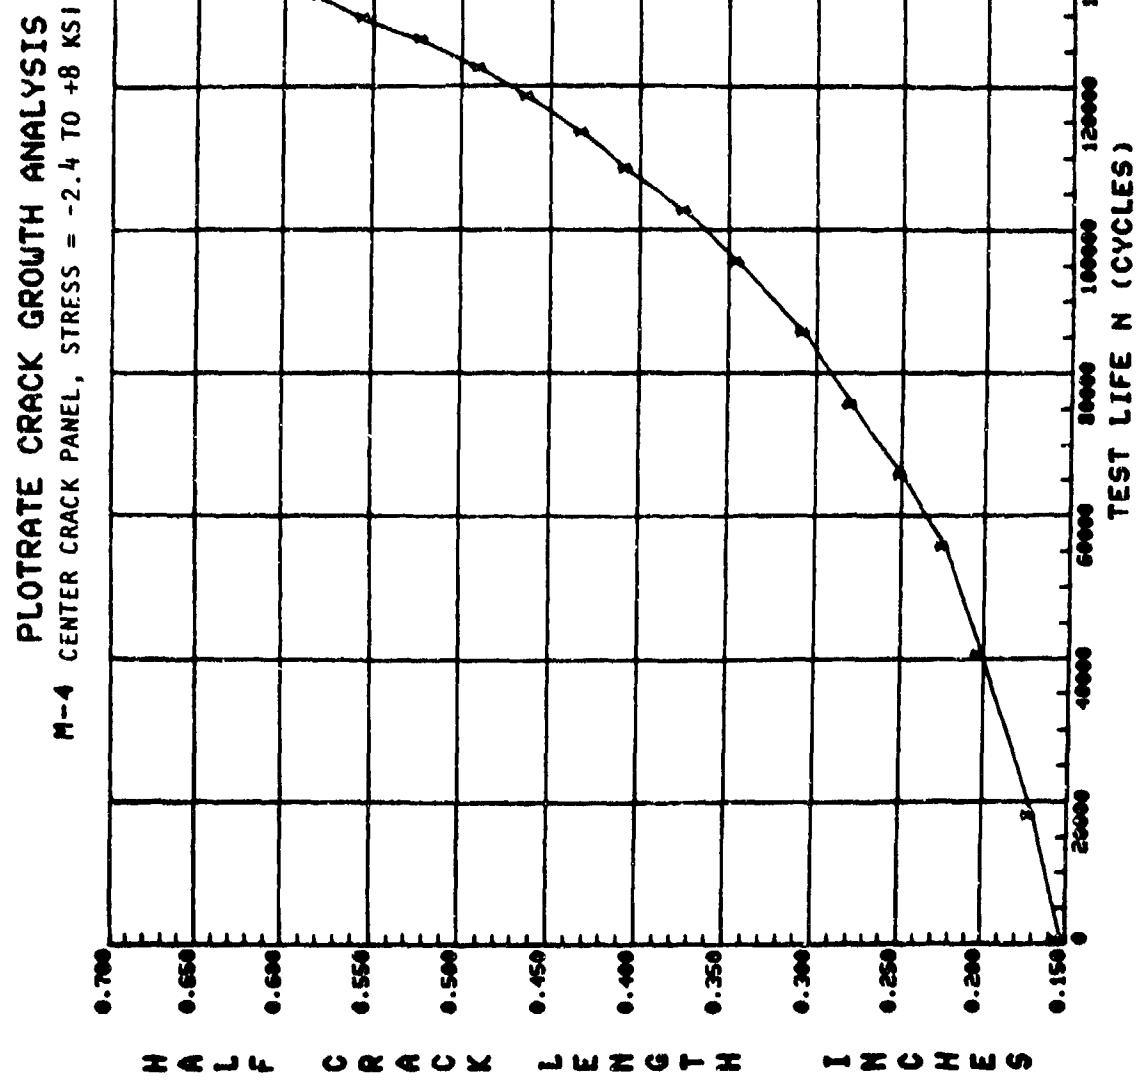


Figure 18. Crack growth curve for test M-4.

TABLE 15. DATA TABULATION FOR TEST M-5

SPECIMEN NO.: 4-5		CENTER CRACKED PANEL, STRESS=40 KSI			
CCT	SPCIMEN	R = 0.250 IN.	b = 6.000 IN.	AA = (1,1)	IN.
P(MN)	0.6 KIPS	P(MAX) = 60.0 KIPS	P = 0.01	TEST FREQ = 6.000 Hz	
ENVIRONMENT CONDITION: ROOM AMBIENT					
NO.	CYCLES	AS PEA SUGGESTED	AS REGRESSION (IN)	MULT. COEFF.	K-MAX
1	0.	0.3C ²	0.306	0.984567	27.80
2	47.	0.335	0.313	0.991650	28.09
3	416.	0.433	0.455	0.992547	33.16
4	506.	0.505	0.505	0.987906	35.76
5	616.	0.585	0.619	0.990902	39.37
6	656.	0.655	0.665	0.996444	41.18
7	716.	0.755	0.749	0.998657	42.80
8	726.	0.750	0.752	0.998390	45.08
9	746.	0.820	0.829	0.998081	46.65
10	766.	0.855	0.858	0.998818	47.86
11	786.	0.945	0.945	0.998362	49.46
12	806.	1.010	1.012	0.978207	51.29
13	826.	1.080	1.084	0.999716	53.23
14	846.	1.175	1.175	0.999621	55.05
					DATA
					K
					0.140E-05
					6.209E-05
					3.178E-04
					4.583E-04

PLOTRATE CRACK GROWTH ANALYSIS
M-5 CENTER CRACKED PANEL, STRESS=40KSI

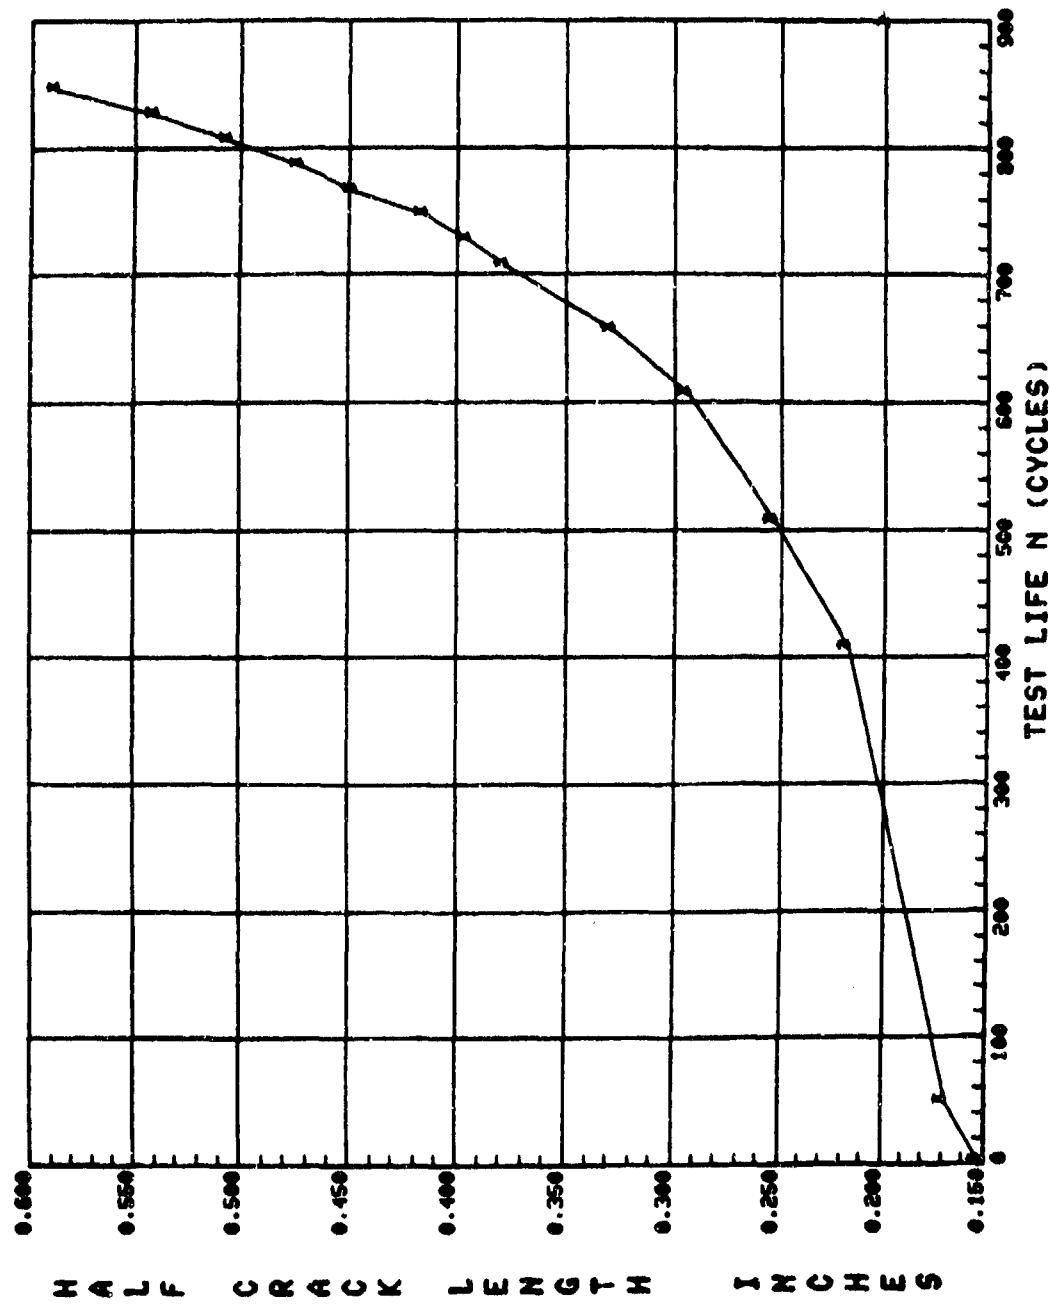


Figure 19. Crack growth curve for test M-5.

TABLE 16. DATA TABULATION FOR TIST M-6

SPECIMEN NO.: 4-6 CENTER CRACKED PANEL. STRESS 12 TO 40 KSI
 CCT SPFCIMEN A = 0.750 IN. W = 6.000 IN. ΔH = 0.1)
 PMIN = 18.00 KIPS PHMAX = 60.0 KIPS R = 0.36 TEST FREQ = 6.00HZ

ENVIRONMENT CONDITION:	ROOM AMBIENT	DA/DN	DELTA K				
NO.	CYCLFS	AL(MEASLREN)	AL(REFLSSION)	MULT.	CORR.	COEFF	K-MAX
1	0.	0.310	0.310	0.998037	27.97	14.58	1.545E-05
2	460	0.355	0.353	0.998356	29.86	20.90	7.343E-05
3	793	0.410	0.413	0.998016	32.32	22.62	1.221E-04
4	993	0.470	0.470	0.984147	34.49	24.14	1.753E-04
5	1143	0.505	0.522	0.981790	36.37	25.46	2.487E-04
6	1293	0.560	0.567	0.99304	38.97	27.28	3.520E-04
7	1393	0.665	0.668	0.99780	41.27	28.89	4.544E-04
8	1443	0.730	0.716	0.99590	42.79	29.95	4.755E-04
9	1493	0.770	0.770	0.997314	44.42	31.10	5.170E-04
10	1543	0.820	0.820	0.995630	45.91	32.13	5.661E-04
11	1593	0.870	0.874	0.999563	47.46	33.22	6.261E-04
12	1643	0.940	0.940	0.999647	49.34	34.54	7.363E-04
13	1693	1.020	1.020	0.999878	51.52	36.07	8.904E-04

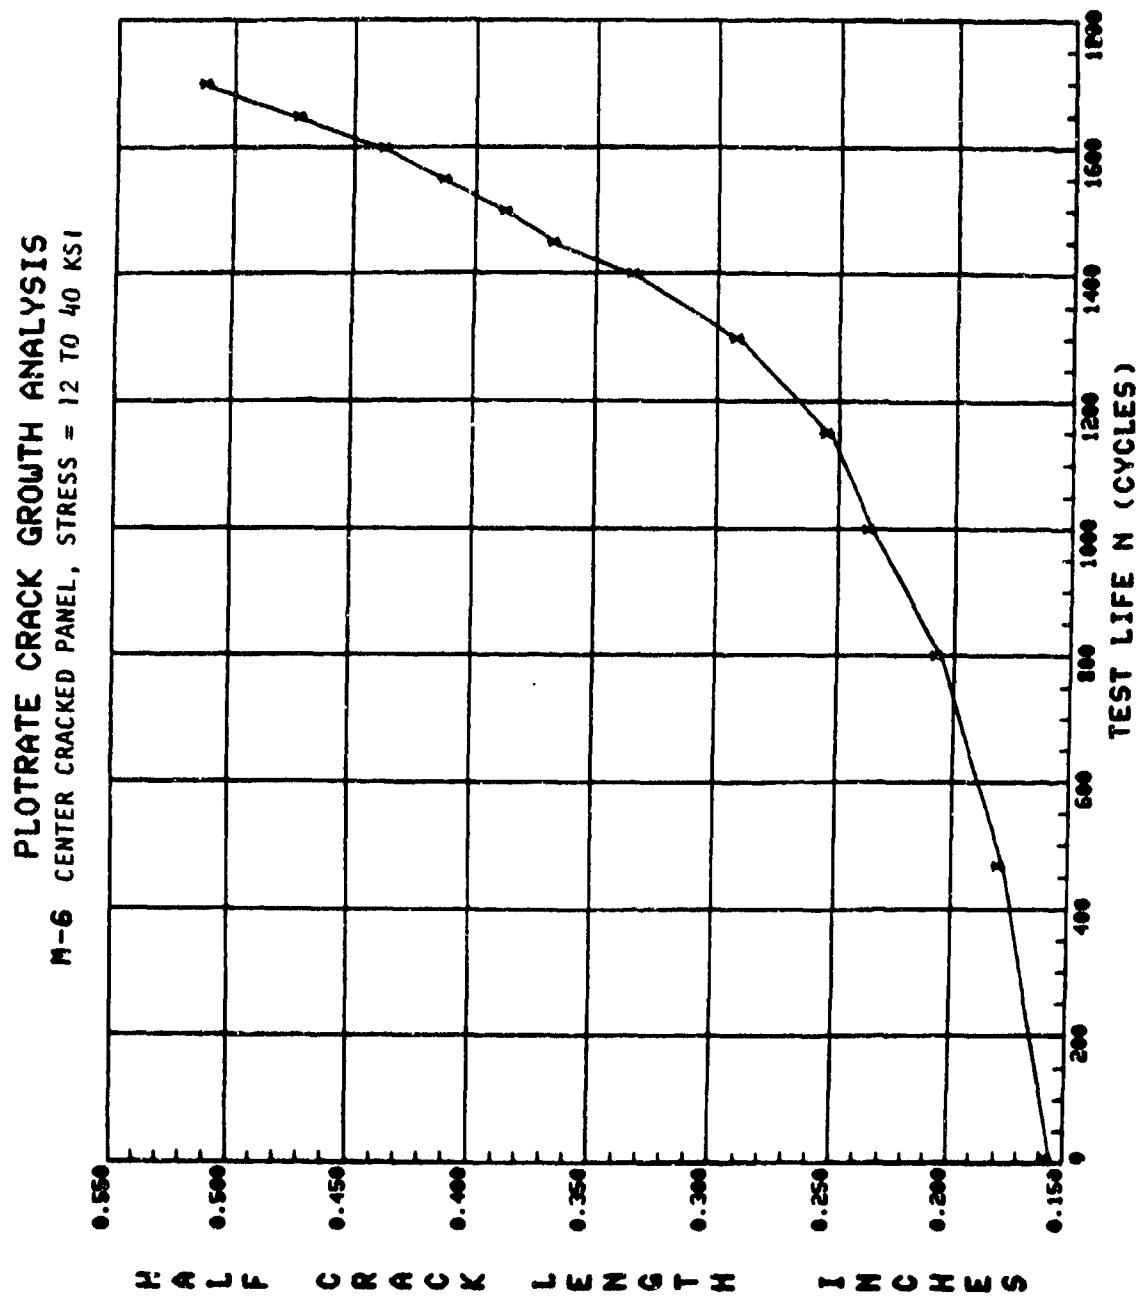


Figure 20. Crack growth curve for test M-6.

TABLE 17. DATA TABULATION FOR TEST M-7

SPECIMEN NO.:	CRT	SPECIMEN	B= 0.250 IN.		W= 6.000 IN.		A= 0.0 IN.		TEST FREQ= 6.00 Hz.	
			P MIN	42.0 KIPS	P MAX	60.0 KIPS	R	0.70		
ENVIRONMENT CONDITION: ROOM AMBIENT										
vn.	CYCLES	A (MEASRED)	A (REGRESSION)		MULT.	CORR.	K-MAX		DELTA K	
1	0.	0.310	0.310		0.999985		27.96		0.39	3.04E-07
2	5629.	0.350	0.392		0.999716		31.46		9.44	1.413E-05
3	7379.	0.450	0.449		0.999387		33.69		10.11	1.910E-05
4	8490.	0.455	0.497		0.993622		35.48		10.64	2.412E-05
5	9380.	0.530	0.538		0.991939		36.94		11.08	3.063E-05
6	10380.	0.550	0.600		0.996221		39.07		11.72	3.091E-05
7	10880.	0.645	0.640		0.996758		40.37		12.11	4.337E-05
8	11380.	0.655	0.697		0.997052		41.89		12.57	4.923E-05
9	11880.	0.735	0.740		0.993243		43.51		13.05	5.741E-05
10	12380.	0.790	0.796		0.995719		45.21		13.56	7.108E-05
11	12680.	0.835	0.838		0.999489		46.43		13.93	8.414E-05
12	12930.	0.885	0.882		0.998062		47.71		14.31	9.104E-05
13	13130.	0.925	0.922		0.998531		48.83		14.65	9.960E-05
14	13330.	0.965	0.963		0.997419		49.95		14.99	1.079E-04
15	13530.	1.000	1.006		0.998677		51.14		15.34	1.187E-04
16	13730.	1.055	1.054		0.998968		52.43		15.73	1.350E-04
17	13930.	1.115	1.110		0.999070		53.93		16.18	1.573E-04
18	14110.	1.165	1.171		0.999185		55.52		16.66	1.783E-04
19	14270.	1.230	1.229		0.999407		57.02		17.10	2.003E-04
20	14420.	1.295	1.290		0.994267		58.55		17.57	2.477E-04
21	14550.	1.350	1.357		0.989612		60.24		18.07	3.172E-04
22	14660.	1.410	1.428		0.986253		62.02		18.61	4.384E-04
23	14750.	1.500	1.515		0.988043		64.16		19.25	6.692E-04
24	14790.	1.555	1.570		0.995054		65.51		19.65	9.165E-04
25	14810.	1.605	1.618		0.971657		66.44		19.93	1.409E-03
26	14830.	1.655	1.656		0.981175		67.62		20.28	1.835E-03
27	14850.	1.700	1.730		0.985381		69.42		20.83	2.516E-03
28	14870.	1.850	1.879		0.991119		72.32		21.70	3.940E-03

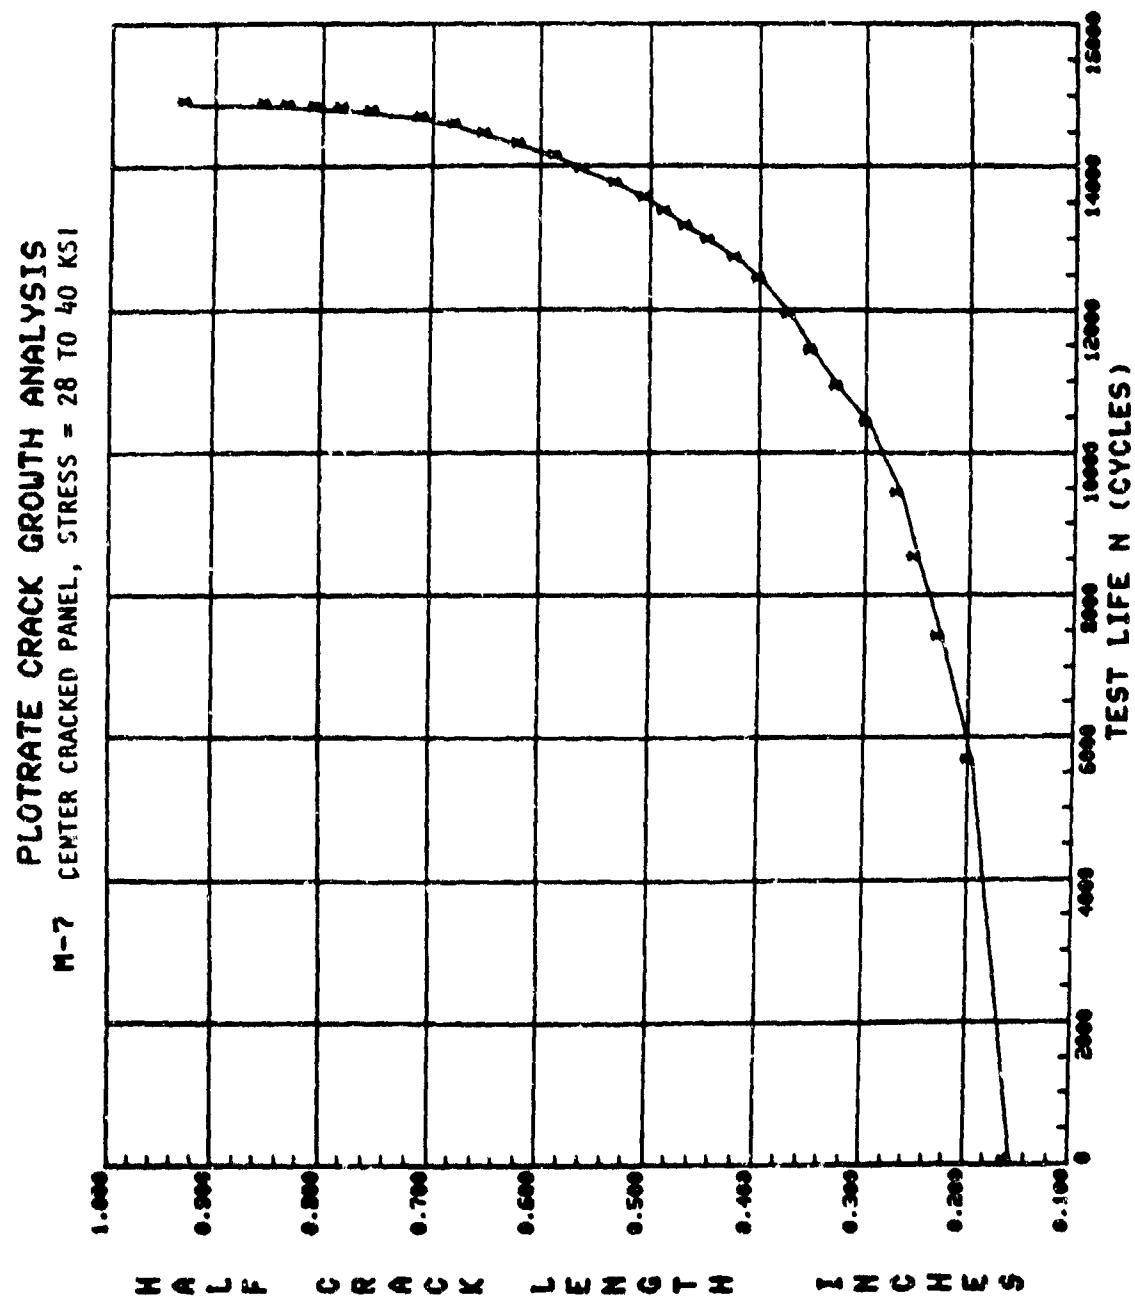


Figure 21. Crack growth curve for test M-7.

TABLE 18. DATA TABULATION FOR TEST M-8

TEST NUMBER	SPECIMEN NO.:	R = 0.250 IN.	CENTER CRACKED PANEL STRESS -4 TO 40 KSI			TEST FREQUENCY = 6.0000 HZ.	TEST FREQUENCY = 6.0000 HZ.
			P MIN = -6.00KIPS	P MAX = 6.00KIPS	R = -0.1IN)		
ENVIRONMENT CONDITION: ROOM AMBIENT							
NO.	CYCLES	ALMATERIAL	AIRAGRESSION	MHT. CORR.	COEFF	K-MAX	DAWN
1	0.	0.310	0.310	0.999934	27.96	30.75	3.552E-05
2	200.	0.410	0.412	0.999815	32.26	35.50	5.238E-04
3	240.	0.460	0.457	0.998581	34.01	37.41	6.754E-04
4	280.	0.515	0.517	0.995239	36.21	39.83	8.633E-04
5	320.	0.575	0.581	0.995998	38.43	42.28	1.106E-03
6	360.	0.670	0.675	0.998361	41.51	45.66	1.475E-03
7	390.	0.765	0.770	0.998967	44.42	48.86	1.922E-03
8	410.	0.850	0.851	0.998622	46.82	51.50	2.331E-03
9	425.	0.915	0.924	0.998343	48.89	53.78	2.824E-03
10	435.	0.960	0.984	0.995601	50.54	55.59	3.592E-03
11	440.	1.015	1.017	0.996460	51.44	56.59	4.547E-03
12	445.	1.055	1.062	0.997902	52.65	57.91	5.259E-03
13	450.	1.115	1.116	0.997829	54.09	59.49	5.983E-03
14	455.	1.150	1.151	1.996910	55.78	61.36	7.222E-03
15	458.	1.225	1.224	0.980635	56.87	62.55	9.631E-03
16	461.	1.265	1.278	0.969738	58.25	64.07	1.348E-02
17	464.	1.325	1.349	0.975776	60.04	66.04	2.183E-02
18	467.	1.465	1.513	0.985814	63.86	70.25	3.647E-02
19	468.	1.565	1.576	0.993064	65.65	72.22	4.758E-02
20	469.	1.685	1.645	0.999936	68.33	75.16	6.778E-02

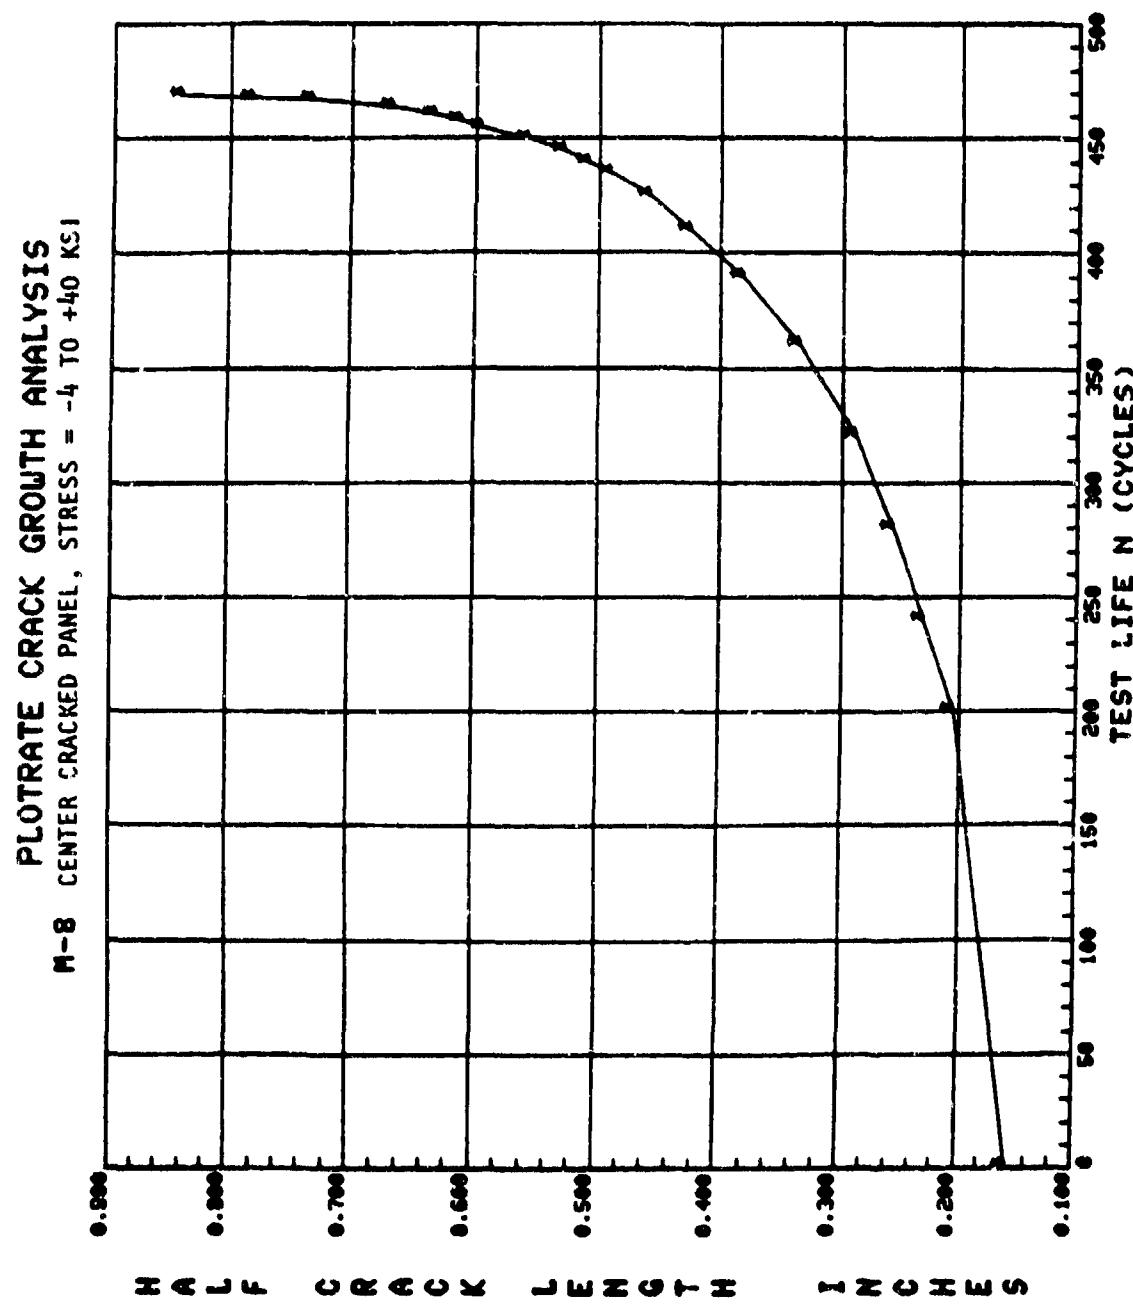


Figure 22. Crack growth curve for test M-8.

TABLE 19. DATA TABULATION FOR TEST M-9

SPECIMEN NO.: 4-9		CENTER CRACKED PANEL, STRESS -8 TO +8 KSI				TEST FREQ= 6.00 HZ.					
CCT	SPECIMEN	B= 0.250 IN.	W= 6.000 IN.	Ah= 0.01	IN.	R= -0.10	MULT.	CORR. COEFF	K-MAX	DA/DN	DELTA K
PMIN=	-1.2 KIPS	P MAX=	12.0 KIPS								
ENVIRONMENT CONDITION: ROOM AIR IVENT											
NO.	CYCLES	A (MEASURED)	A (REGRESSION)								
1	0.	0.308	0.307					0.998623	5.57	6.12	1.249E-07
2	30000.	0.332	0.335					0.999348	5.81	6.39	8.052E-07
3	50000.	0.380	0.376					0.999588	6.17	6.78	1.283E-06
4	70000.	0.425	0.437					0.999693	6.65	7.32	1.759E-06
5	85000.	0.455	0.495					0.999292	7.08	7.79	2.176E-06
6	97000.	0.550	0.549					0.999469	7.47	8.22	2.596E-06
7	107000.	0.600	0.603					0.998408	7.83	8.62	3.092E-06
8	117000.	0.665	0.667					0.999192	8.25	9.07	3.720E-06
9	125000.	0.725	0.729					0.999446	8.63	9.50	4.243E-06
10	131000.	0.765	0.762					0.999323	8.96	9.85	4.761E-06
11	136000.	0.835	0.832					0.999037	9.25	10.17	5.266E-06
12	141000.	0.880	0.886					0.998999	9.56	10.52	5.783E-06
13	146000.	0.945	0.946					0.999341	9.90	10.89	6.201E-06
14	150000.	1.000	0.997					0.999454	10.18	11.20	6.676E-06
15	154000.	1.055	1.049					0.994642	10.46	11.51	7.496E-06
16	162000.	1.170	1.175					0.995914	11.12	12.23	9.704E-06
17	166000.	1.240	1.255					0.996434	11.53	12.69	1.063E-05
18	169000.	1.335	1.321					0.995348	11.87	13.06	1.178E-05
19	172000.	1.410	1.400					0.994419	12.26	13.49	1.203E-05
20	175000.	1.470	1.473					0.999973	12.61	13.67	8.410E-06

PLOTRATE CRACK GROWTH ANALYSIS
M-9 CENTER CRACKED PANEL, STRESS = - .8 TO +8 KSI

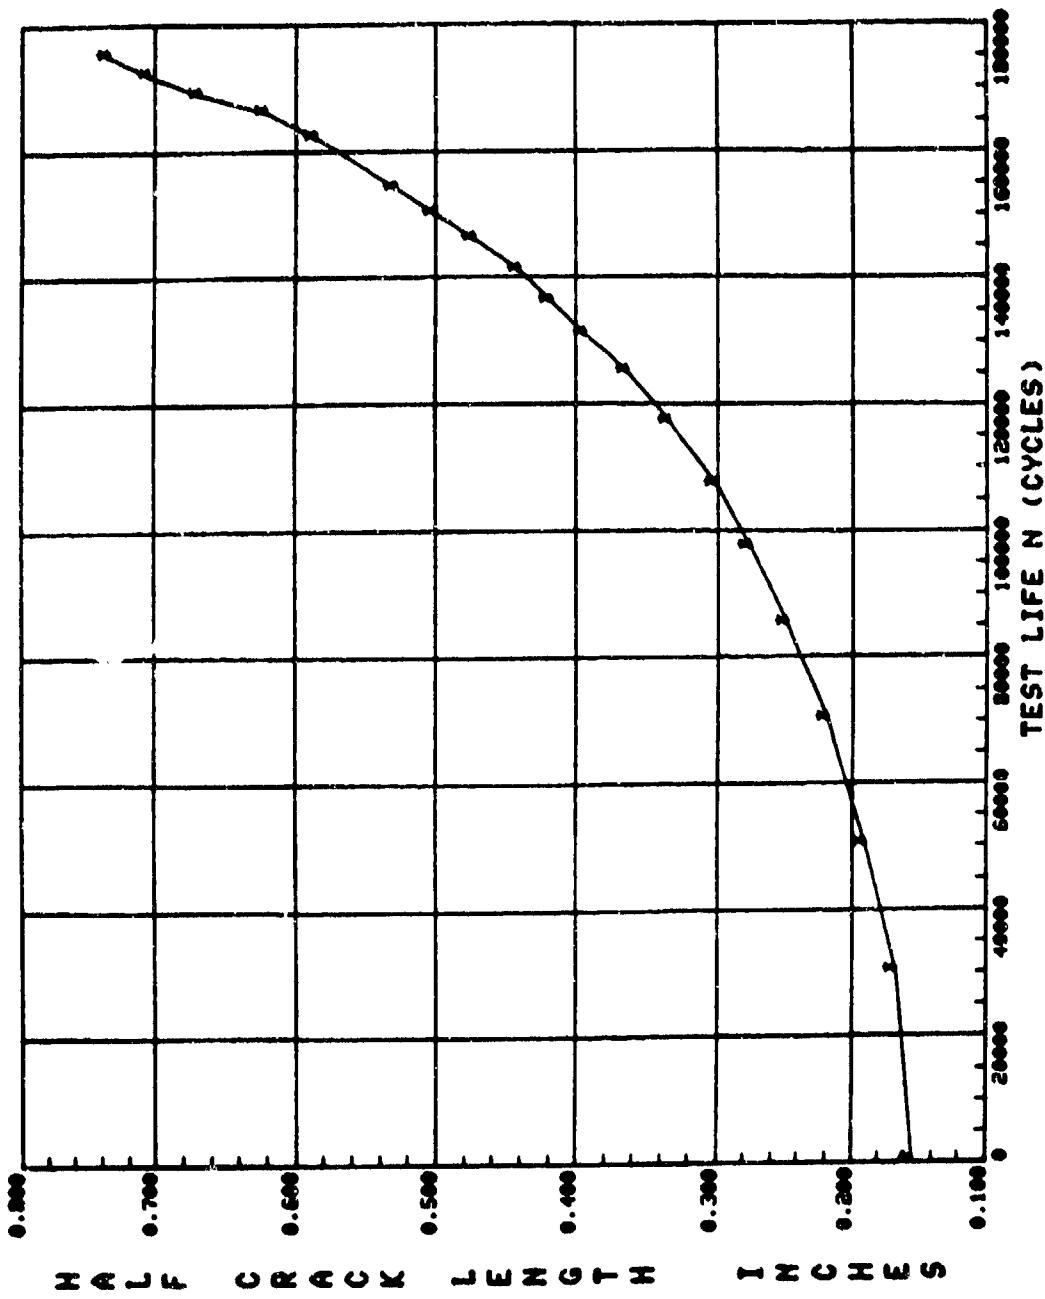


Figure 23. Crack growth curve for test M-9.

TABLE 20. DATA TABULATION FOR TEST M-10

SPECIMEN NO.: 4-10 CENTER CRACK (ANFL. STRESS=12 TO 40 KSI)

CCT SPECIMEN# B= 0.250 IN. R= 6.000 IN. ΔR= 0.01 IN.

PIV= -18.0 KIPS P_{MAX}= 60.0 KIPS R= -0.30 TEST FREQ= 0.00 Hz.

ENVIRONMENT CONDITION: ROOM AMBIENT

NO.	CYCLES	TIME MEASURED	REGRESSION	MULT. CORR. COEFF	K-MAX	DELTA K
1	0.	0.320	0.320	0.996380	28.39	36.90
2	34.	0.375	0.381	0.997593	31.02	9.603E-04
3	64.	0.435	0.423	0.992860	32.72	8.457E-04
4	92.	0.465	0.464	0.987368	34.29	7.983E-04
5	120.	0.500	0.509	0.988557	35.91	44.57
6	148.	0.565	0.566	0.997573	37.90	46.68
7	174.	0.645	0.649	0.998784	40.66	1.053E-03
8	194.	0.730	0.736	0.998493	43.41	4.555E-03
9	208.	0.810	0.813	0.998240	45.64	52.85
10	218.	0.875	0.881	0.993111	47.69	2.012E-03
11	226.	0.940	0.950	0.995107	49.27	2.610E-03
12	232.	1.005	1.015	0.996317	50.66	3.294E-03
13	236.	1.060	1.071	0.996626	52.88	6.956E-03
14	240.	1.130	1.143	0.990846	54.77	8.527E-03
15	243.	1.205	1.211	0.991814	56.54	1.135E-02
16	245.	1.260	1.261	0.968979	57.83	1.543E-02
17	247.	1.350	1.345	0.981197	60.18	2.619E-02
18	249.	1.445	1.470	0.990317	63.56	3.327E-02
19	251.	1.725	1.723	0.913434	69.24	4.866E-02
					90.02	7.472E-02

PLOT RATE CRACK GROWTH ANALYSIS
M-10 CENTER CRACK PANEL, STRESS = -12 TO +40 KSI

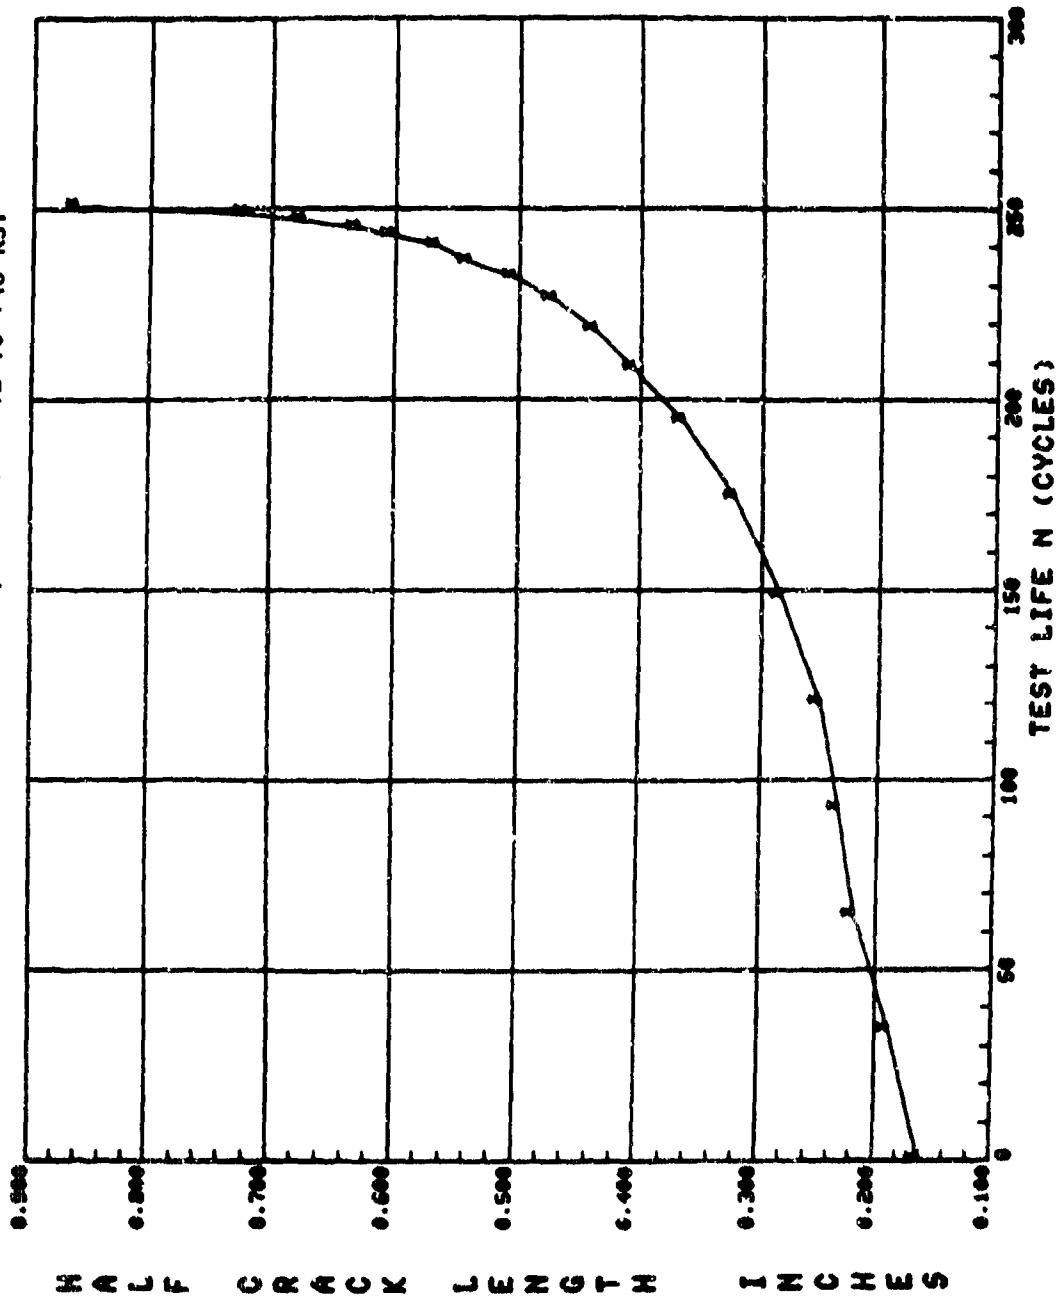


Figure 24. Crack growth curve for test M-10.

TABLE 21. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP II -
SINGLE OR PERIODICAL OVERLOAD/COMP LOAD


Test No.	Applied Base Load				Overload/Underload		N_I Cycle	N_{II} Cycle	Comments
	Loading Profile	Max Ksi	Min Ksi	Max Ksi	Min Ksi				
M-11		20	0	30	0	2,500	To failure		Single over-load effect
M-12		20	0	30	0	2,500	2,500		Periodically applied single load effect, $R_I = 0, R_{OL} = 1.5$
M-13		20	0	45	0	2,500	2,500		Periodically applied single load effect, $R_I = 0, R_{OL} = 2.25$
M-14		20	6	40	6	2,500	2,500		Periodically applied single load effect, $R_I = 0.3, R_{OL} = 2$
M-15		30	21	40	21	2,500	2,500		Periodically applied single load effect, $R_I = 0.7, R_{OL} = 1.33$
M-16		20	0	20	-6.0	2,500	2,500		Periodically applied comp load effect $R_I = 0$
M-17		20	6	20	-6.0	2,500	2,500		Periodically applied comp load effect $R_I = 0.3$
M-18		40	28	40	-12	2,500	2,500		Periodically applied comp load effect $R_I = 0.7$
M-19		20	0	30	-6.0	2,500	To failure		Single overload/comp load effect $R_I = 0, R_{OL} = 1.5$

TABLE 21. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP II -
SINGLE OR PERIODICAL OVERLOAD/COMP LOAD (CONT)




Test No.	Applied Base Load			Overload/ Underload		N_I Cycle	N_{II} Cycle	Comments
	Loading Profile	σ_{Max} Ksi	σ_{Min} Ksi	σ_{Max} Ksi	σ_{Min} Ksi			
M-20		20	0	30	-6.0	2,500	2,500	Periodically applied overload-comp load effect
M-21		20	0	40	-12	2,500	2,500	Periodically applied overload-comp load effect
M-22		20	0	30	-6.0	2,500	To failure	Single comp load-overload effect
M-23		20	0	30	-6.0	2,500	2,500	Periodically applied comp load-overload effect
M-24		20	-6	30	-6	2,500	2,500	Periodically applied overload effect, $R < 0$
M-25		20	-6	40	-6	2,500	2,500	Periodically applied overload effect, $R < 0$, higher stress
M-26		8	-2.4	8	-16	2,500	To failure	Single comp-overload effect $R < 0$
M-27		8	-2.4	8	-16	2,500	2,500	Periodically applied comp-overload effect
M-28		20	-6	30	-15	2,500	2,500	Periodically applied tension-comp over-load effect

TABLE 21. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP II -
SINGLE OR PERIODICAL OVERLOAD/COMP LOAD (CONCL)


Test No.	Applied Base Load			Overload/Underload		N_I Cycle	N_{II} Cycle	Comments
	Loading Profile	σ_{Max} Ksi	σ_{Min} Ksi	σ_{Max} Ksi	σ_{Min} Ksi			
M-29		20	-6	40	-15	2,500	2,500	Periodically applied tension-comp overload effect, higher stress
M-30		20	-6	40	-15	2,500	2,500	Periodally applied comp-tension overload effect

TABLE 22. DATA TABULATION FOR TEST M-11

SPECIMEN NO.: M-11 BASE STRESS 0 TO 20 KSI, SINGLE OVERLOAD 0 TO 30 KSI

CCT SPECIMEN R= 0.250 IN. W= 6.000 IN.

AN= 0.0 IN.

TEST FREQ= 6.00 Hz.

PHASE=

ENVIRONMENT CONDITION: ROOM AMBIENT

NO.	CYCLES	AI(MEASURED)	AI(REGRESSION)	MULT. CORR. COEFF	K-4 MAX	DA/DN
1	0.	0.295	0.295	0.999001	13.64	1.569E-05
2	1510.	0.345	0.335	0.995194	14.53	1.343E-05
3	3500.	0.355	0.369	0.994400	15.68	1.615E-05
4	5500.	0.450	0.457	0.986019	17.00	2.258E-05
5	7500.	0.543	0.556	0.990916	18.78	3.362E-05
6	8453.	0.605	0.619	0.996911	19.85	4.363E-05
7	9300.	0.700	0.696	0.998435	21.08	5.271E-05
8	9700.	0.745	0.740	0.998078	21.76	5.647E-05
9	10100.	0.760	0.789	0.998637	22.50	6.104E-05
10	10500.	0.831	0.837	0.999291	23.19	6.407E-05
11	10900.	0.850	0.868	0.998617	23.93	7.238E-05
12	11300.	0.950	0.947	0.998232	24.76	8.529E-05
13	11600.	0.992	1.001	0.998314	25.50	9.646E-05
14	11900.	1.060	1.061	0.999149	26.29	1.114E-04
15	12100.	1.110	1.106	0.999192	26.90	1.220E-04
16	12290.	1.153	1.156	0.999733	27.56	1.320E-04
17	12480.	1.208	1.204	0.997382	29.19	1.450E-04
18	12670.	1.262	1.263	0.998240	28.93	1.650E-04
19	12850.	1.317	1.327	0.998186	29.74	1.809E-04
20	13030.	1.405	1.396	0.998312	30.60	1.945E-04
21	13210.	1.470	1.470	0.998901	31.53	2.082E-04
22	13390.	1.545	1.548	0.999131	32.49	2.172E-04
23	13570.	1.625	1.623	0.999101	33.40	2.341E-04
24	13750.	1.710	1.710	0.996694	34.47	2.801E-04
25	13850.	1.755	1.765	0.997603	35.14	3.036E-04
26	13950.	1.825	1.828	0.997413	35.90	3.259E-04
27	14050.	1.910	1.897	0.997528	36.75	3.625E-04
28	14150.	1.970	1.974	0.997944	37.70	3.961E-04

TABLE 22. DATA TABULATION FOR TEST M-11 (CONCL)

SPT: IMIN NO.:		4-11		BASE STRESS 0 TO 20 KSI, SINGLE OVERLOAD 0 TO 30 KSI			
RTT	SFC14FN	R =	0.250 IN.	w =	6.000 lb.	AN =	0.0 J IN.
0414=	P MAX=					TEST FREQ =	6.000 Hz.
ENVIRONMENT CONDITION: ROOM AIRPENT							
YC.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. COEFF	K-MAX	DELTA K	DA/DN
29	14250.	2.045	2.054	0.997580	38.66	38.68	4.135E-04
30	14350.	2.145	2.137	0.995985	39.71	39.71	4.218E-04
31	14400.	2.190	2.183	0.997636	40.30	40.30	4.149E-04
32	14450.	2.225	2.226	0.994590	40.84	40.84	4.362E-04
33	14500.	2.260	2.263	0.997327	41.30	41.30	4.536E-04
34	14550.	2.305	2.309	0.999201	41.89	41.89	4.964E-04
35	14600.	2.365	2.364	0.998110	42.60	42.60	5.411E-04
36	14650.	2.425	2.423	0.999281	43.37	43.37	5.750E-04
37	14700.	2.465	2.463	0.999748	44.16	44.16	5.946E-04
38	14750.	2.540	2.541	0.999599	44.93	44.93	6.089E-04
39	14800.	2.600	2.549	0.998633	45.72	45.72	6.571E-04
40	14850.	2.665	2.663	0.998940	46.60	46.60	7.429E-04
41	14900.	2.735	2.738	0.999241	47.65	47.65	8.750E-04
42	14950.	2.830	2.827	0.998848	48.91	48.91	1.073E-03
43	15000.	2.940	2.936	0.998586	50.54	50.54	1.357E-03
44	15050.	3.075	3.083	0.999208	52.79	52.79	1.692E-03
45	15100.	3.260	3.265	0.999793	55.19	55.19	2.112E-03
46	15150.	3.500	3.510	0.999996	60.01	60.01	2.655E-03

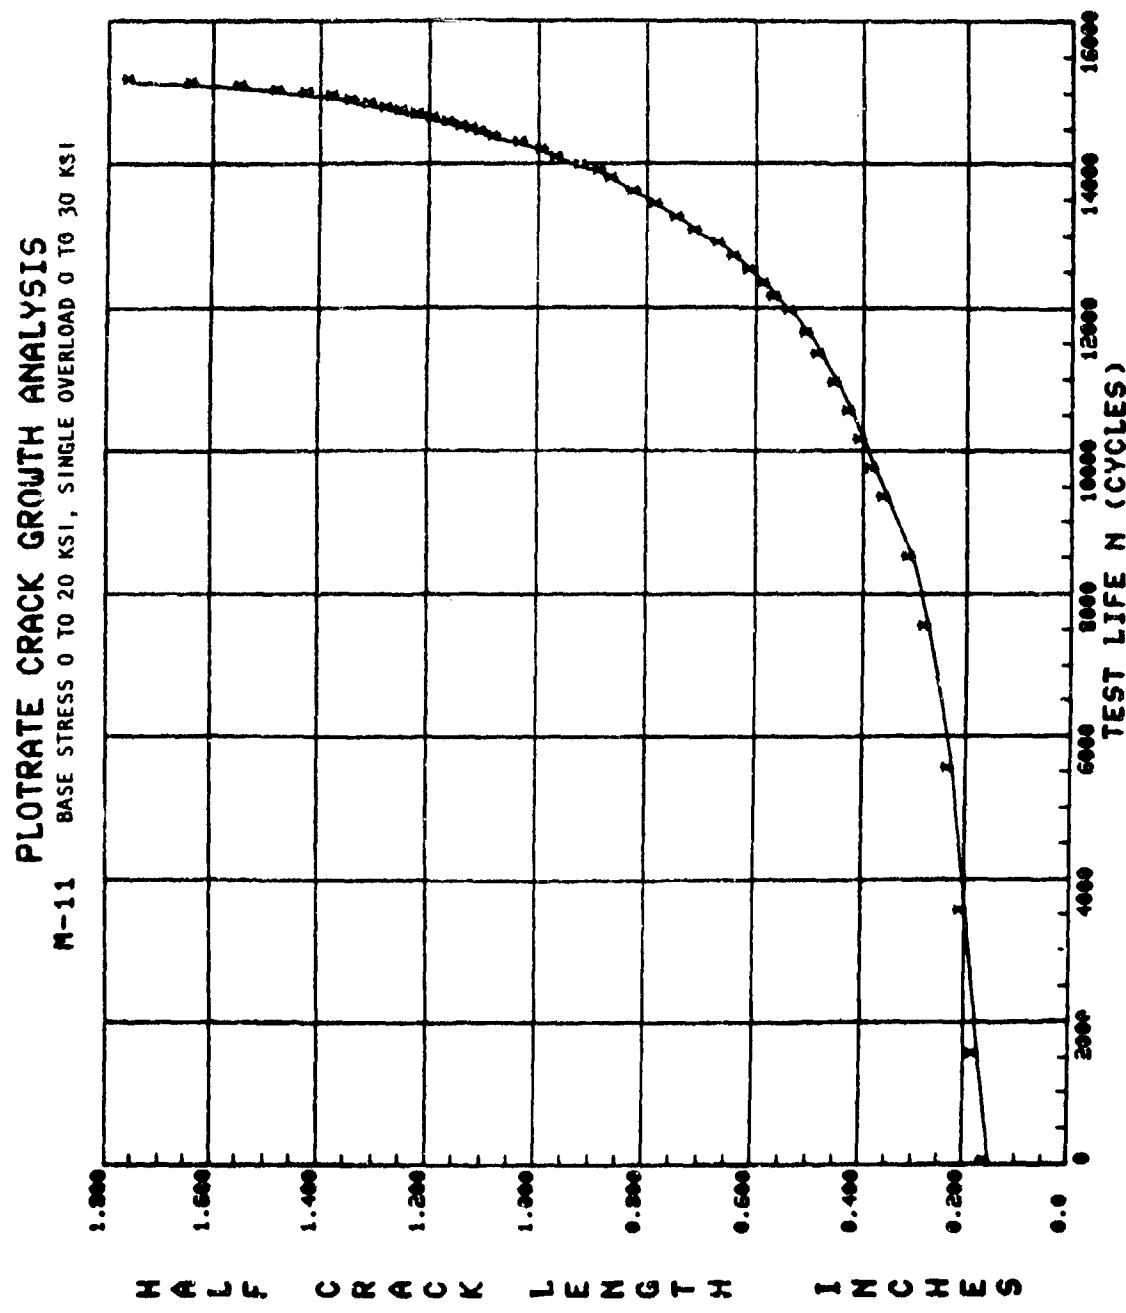


Figure 25. Crack growth curve for test M-11.

TABLE: 23. DATA TABULATION FOR TEST M-12

SPE Cimen N CCT	SPECIMEN N-12	A= 0.250 IN.		W= 6.000 IN.		AN= 0.0 IN.		TEST FREQ= 6.00 Hz.	
		P MIN=	P MAX=	ENVIRONMENT CONDITION:	ROOM AMBIENT	A (MEASURED)	A (REGRESSION)	MULT. COEFF	K-MAX
1	1	0.	0.250	0.298	0.298	0.998715	13.70	13.70	9.732E-06
2	1598.	0.	0.340	0.341	0.341	0.998889	14.66	14.66	1.526E-05
3	4108.	0.	0.425	0.429	0.429	0.998953	16.47	16.47	2.083E-05
4	5000.	0.	0.475	0.468	0.468	0.998861	17.21	17.21	2.324E-05
5	7120.	0.	0.570	0.577	0.577	0.998740	19.15	19.15	2.076E-05
6	8000.	0.	0.620	0.630	0.630	0.998281	20.02	20.02	3.212E-05
7	6500.	0.	0.645	0.661	0.661	0.999074	20.53	20.53	3.400E-05
8	9000.	0.	0.655	0.678	0.678	0.999543	21.11	21.11	3.559E-05
9	9500.	0.	0.725	0.732	0.732	0.999136	21.64	21.64	3.768E-05
10	10000.	0.	0.770	0.771	0.771	0.999450	22.22	22.22	4.018E-05
11	10500.	0.	0.810	0.812	0.812	0.999492	22.84	22.84	4.375E-05
12	11000.	0.	0.860	0.854	0.854	0.996476	23.44	23.44	5.071E-05
13	11500.	0.	0.905	0.906	0.906	0.997414	24.18	24.18	6.016E-05
14	12000.	0.	0.960	0.970	0.970	0.997843	25.97	25.97	6.962E-05
15	12500.	0.	1.050	1.044	1.044	0.997047	26.09	26.09	7.830E-05
16	12900.	0.	1.120	1.113	1.113	0.998000	27.00	27.00	8.329E-05
17	13200.	0.	1.165	1.167	1.167	0.998661	27.70	27.70	8.808E-05
18	13500.	0.	1.215	1.215	1.215	0.996898	28.33	28.33	9.665E-05
19	13800.	0.	1.270	1.269	1.269	0.997616	29.02	29.02	1.130E-04
20	14100.	0.	1.335	1.338	1.338	0.997845	29.89	29.89	1.426E-04
21	14400.	0.	1.425	1.430	1.430	0.999184	31.03	31.03	1.839E-04
22	14600.	0.	1.505	1.506	1.506	0.999919	31.97	31.97	2.188E-04
23	14800.	0.	1.600	1.602	1.602	0.996569	33.14	33.14	2.821E-04
24	14900.	0.	1.655	1.658	1.658	0.995654	33.83	33.83	3.013E-04
25	15000.	0.	1.710	1.723	1.723	0.988892	34.62	34.62	2.980E-04
26	15100.	0.	1.810	1.792	1.792	0.989597	35.47	35.47	2.911E-04
27	15200.	0.	1.855	1.852	1.852	0.992110	36.20	36.20	2.670E-04
26	15300.	0.	1.895	1.900	1.900	0.987773	36.79	36.79	2.366E-04

TABLE 23. DATA TABULATION FOR TEST M-12 (CONCL)

SPHERICAL: M-12 BASE STRESS 0 TO 20 KSI, PERIODIC OVERLOAD 0 TO 30 KSI

CYCLE	SPECI-FN	R= 0.250 IN.	W= 6.000 LB.	A= 0.0	TEST FREQ= 6.000 Hz.	ENVIRONMENT CONDITION: ROOM APRIENT					
						CYCLES	MEASLED	REGRESSION	MULT. COEFF	COEFF.	K-MAX
29	15400.	1.935	1.935	0.999142	37.21	37.21					2.08E-04
30	15500.	1.975	1.975	0.999538	37.70	37.70					2.14E-04
31	15600.	2.015	2.017	0.999775	38.23	38.23					2.27E-04
32	15700.	2.065	2.064	0.999913	38.80	38.80					2.45E-04
33	15800.	2.115	2.114	0.999588	39.43	39.43					2.72E-04
34	15900.	2.170	2.167	0.996875	40.09	40.09					3.205E-04
35	16000.	2.230	2.229	0.997125	40.87	40.87					3.93E-04
36	16100.	2.305	2.310	0.999166	41.93	41.93					4.94E-04
37	16200.	2.415	2.412	0.998652	43.22	43.22					6.455E-04
38	16300.	2.555	2.528	0.985241	44.76	44.76					9.558E-04
39	16400.	2.720	2.733	0.990843	47.58	47.58					1.346E-03
40	16500.	2.965	3.027	0.994633	51.91	51.91					1.909E-03
41	16600.	3.480	3.478	0.998138	59.59	59.59					2.861E-03

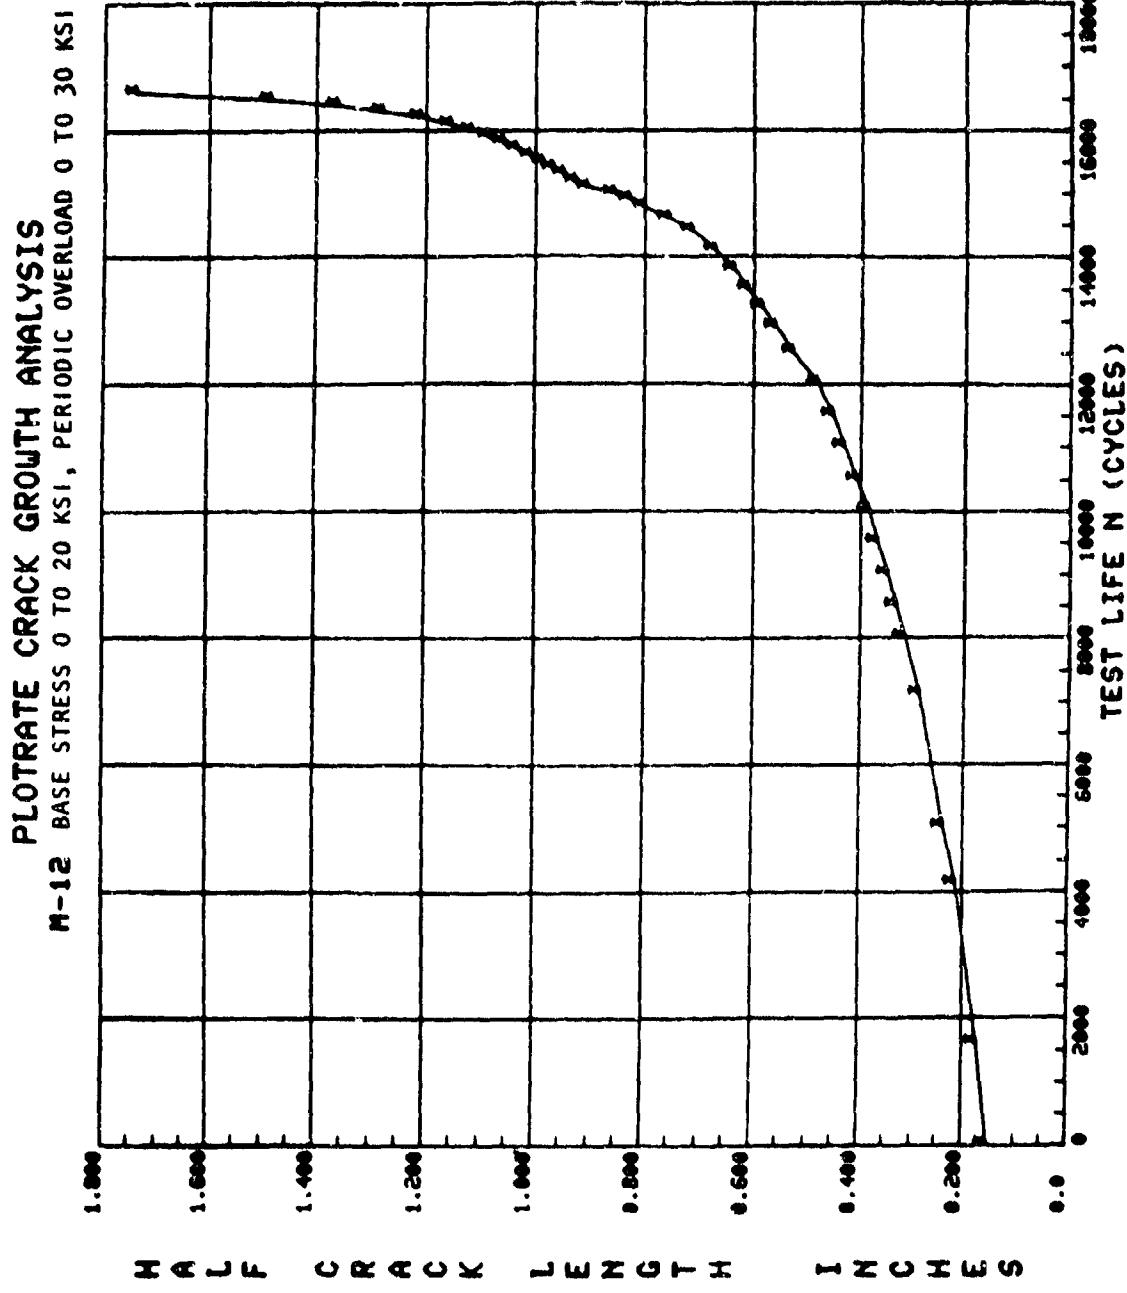


TABLE 24. DATA TABULATION FOR TEST M-13

NO.	CYCLES	A(MEASURED)	A(PREGRESSIVEN)	MULT. CORR. COEFF	K-MAX	DA/DN
1	0.	0.295	0.295	0.999788	13.63	1.477E-05
2	2000.	0.350	0.354	0.998803	14.95	1.382E-05
3	4000.	0.405	0.405	0.99903	15.99	1.147E-05
4	6000.	0.450	0.442	0.991809	16.73	1.013E-05
5	8000.	0.475	0.477	0.989418	17.38	9.330E-06
6	10000.	0.500	0.511	0.990720	18.10	9.437E-06
7	12000.	0.550	0.544	0.789619	18.58	8.036E-06
8	14000.	0.585	0.580	0.961214	19.19	7.723E-06
9	16000.	0.605	0.612	0.995374	19.73	6.607E-06
10	18000.	0.635	0.632	0.990529	20.06	5.4C2E-06
11	20000.	0.655	0.648	0.973712	20.32	4.402E-06
12	22000.	0.660	0.659	0.977973	20.65	5.625E-06
13	24000.	0.685	0.691	0.975601	21.01	5.536E-06
14	26000.	0.725	0.714	0.976767	21.41	5.561E-06
15	28000.	0.745	0.739	0.968637	21.74	5.294E-06
16	30000.	0.760	0.760	0.973757	22.06	6.300E-06
17	34000.	0.795	0.808	0.990253	22.78	9.477E-06
18	36000.	0.855	0.836	0.981283	23.19	1.312E-05
19	38000.	0.885	0.894	0.992315	24.01	1.704E-05
20	40000.	0.945	0.968	0.994644	25.05	2.103E-05
21	42500.	1.110	1.075	0.985892	26.49	2.954E-05
22	45300.	1.260	1.275	0.985767	29.09	29.09
23	46800.	1.355	1.411	0.984426	30.79	30.79
24	48000.	1.575	1.531	0.981658	32.27	32.27
25	48200.	1.585	1.560	0.969951	32.63	32.63
26	48800.	1.630	1.641	0.987913	33.63	33.63
27	49000.	1.635	1.646	0.974998	33.69	33.69
28	49200.	1.680	1.665	0.962926	33.93	33.93

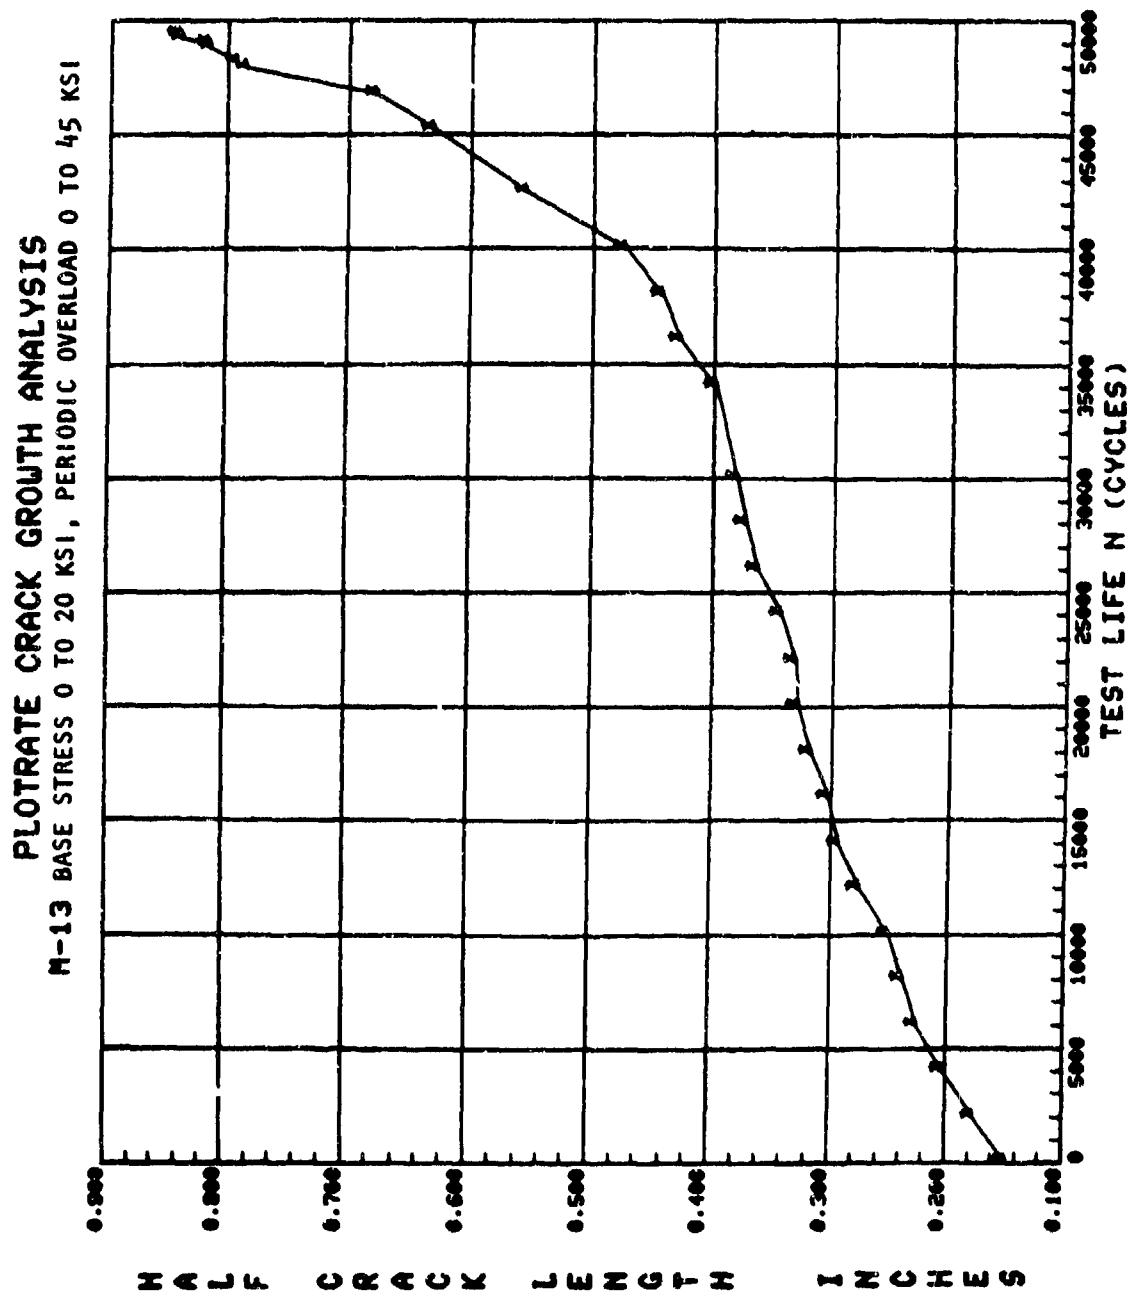


Figure 27. Crack growth curve for test M-13.

TABLE 25. DATA TABULATION FOR TEST M-14

SPECIMEN NO.: 4-14 BASE STRESS = 6 TO 20 KSI. PERIODIC OVERLOAD = 6 TO 40 KSI

CCT SPECIMEN B= 0.250 IN. h = 6.000 IN. Δε = 0.01 IN.

P_{MIN}= P_{MAX}= TEST FREQ= 6,000 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A(MEASMED)	A(REGRESSION)	MULT. CORR. COEFF	K-MAX	DA/DN
1	0.	0.310	0.315	0.965969	14.09	9.86
2	2505.	0.345	0.323	0.981299	14.28	1.358E-06
3	29500.	0.355	0.393	0.988968	15.74	11.02
4	51700.	0.445	0.448	0.993772	16.84	1.254E-06
5	70100.	0.455	0.493	0.998563	17.68	11.79
6	90200.	0.550	0.548	0.998972	18.64	12.37
7	112800.	0.610	0.607	0.994322	19.66	13.05
8	121000.	0.625	0.629	0.994012	20.92	14.01
9	131000.	0.650	0.658	0.995351	20.49	14.34
10	141000.	0.700	0.693	0.994295	21.03	14.72
11	151000.	0.720	0.728	0.991544	21.57	15.10
12	161000.	0.775	0.771	0.993158	22.23	15.56
13	171000.	0.810	0.818	0.997247	22.92	16.04
14	184500.	0.915	0.914	0.997971	24.29	17.01
15	192000.	0.975	0.977	0.994242	25.17	17.62
16	200000.	1.070	1.066	0.993236	26.38	18.47
17	208000.	1.145	1.171	0.991918	27.76	19.43
18	211370.	1.235	1.229	0.991829	28.50	19.95
19	214000.	1.275	1.280	0.995167	29.15	20.41
20	216500.	1.345	1.342	0.962644	29.93	20.95
21	219000.	1.420	1.434	0.986178	31.09	21.76
22	220900.	1.510	1.543	0.989359	32.42	22.70
23	222600.	1.715	1.670	0.989440	33.98	23.79
24	224100.	1.810	1.813	0.984663	35.73	25.01

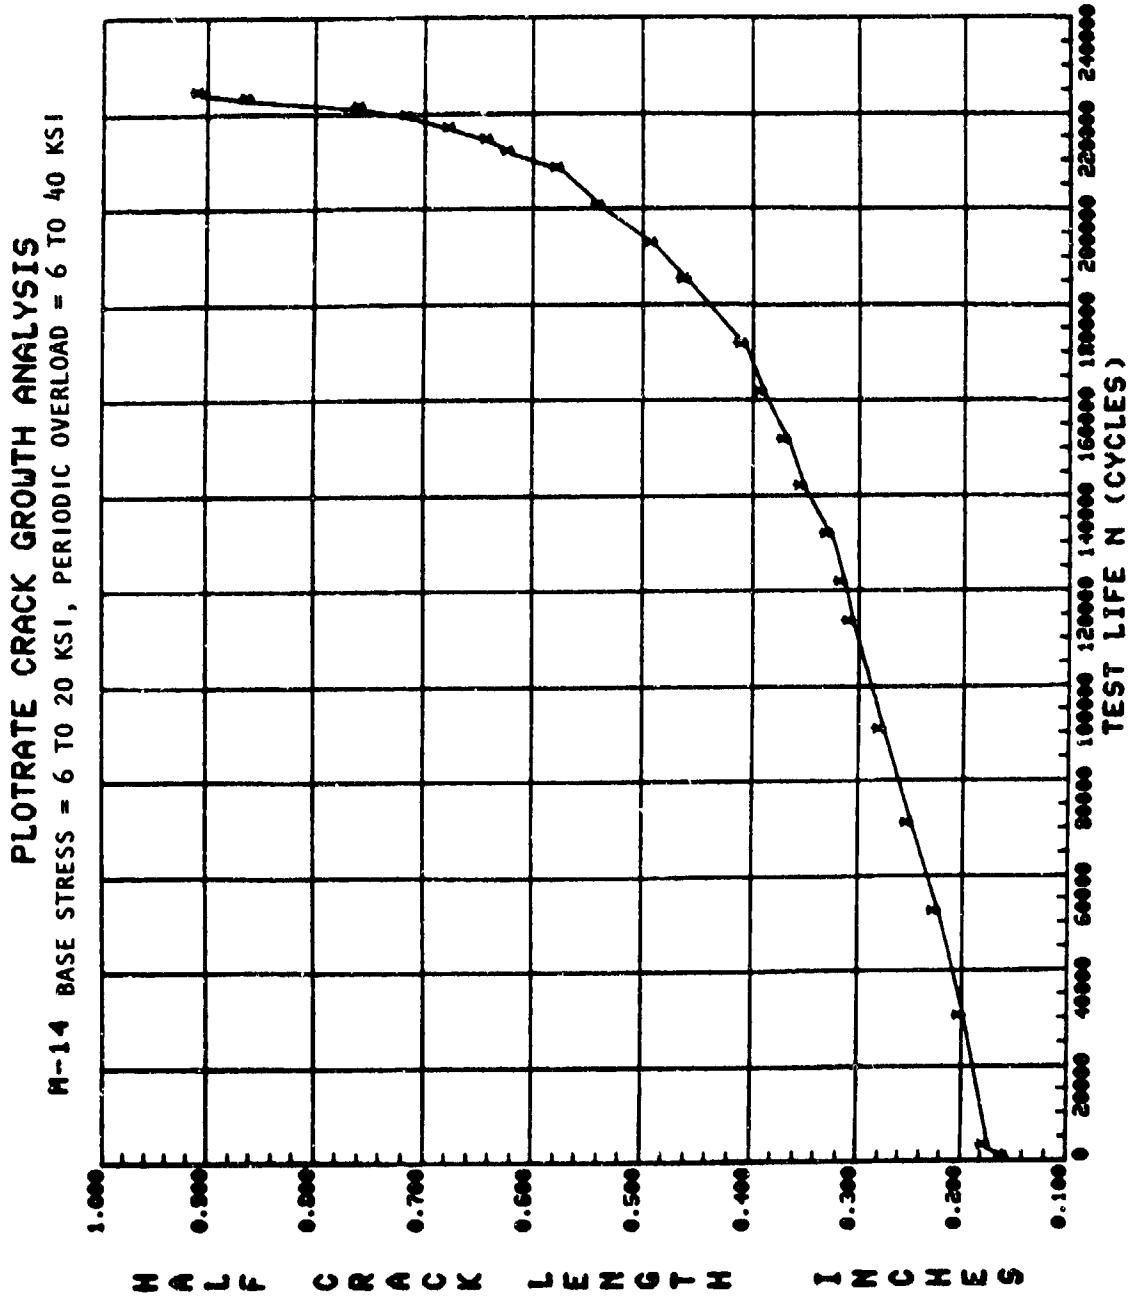


Figure 28. Crack growth curve for test M-14.

TABLE 26. DATA TABULATION FOR TEST M-15

SPECIMEN NO.: M-15 RASE = 21 TO 30 KSI PERIODIC OVERLOAD = 21 TO 40 KSI

EECT SP FREQ	g = 0.250 IN.	W = 6.000 IN.	AN = 0.0 IN.	P MAX =	TEST FREQ = 6.00 Hz.					
					No.	CYCLES	A MEASURED	A (REGRESSION)	MULT. CORR. COEFF	%-MAX
ENVIRONMENT CONDITION: ROOM AMBIENT										
1	0.	0.313	0.314	0.991682	21.12	6.34	2.778E-06			
2	5500.	0.355	0.340	0.991384	21.97	6.59	2.103E-06			
3	24500.	0.415	0.406	0.990727	24.02	7.21	1.782E-06			
4	41000.	0.460	0.462	0.992130	25.64	7.69	1.904E-06			
5	57070.	0.515	0.522	0.998202	27.28	8.18	2.137E-06			
6	73500.	0.595	0.594	0.997203	29.15	8.74	2.775E-06			
7	83500.	0.655	0.651	0.997523	30.56	9.17	3.281E-06			
8	94000.	0.710	0.723	0.995701	32.24	9.67	4.144E-06			
9	104001.	0.810	0.807	0.996264	34.15	10.25	5.472E-06			
10	109001.	0.855	0.862	0.989216	35.34	10.60	6.905E-06			
11	117000.	0.965	0.988	0.986656	37.98	11.39	9.351E-06			
12	120000.	1.030	1.065	0.939224	39.55	11.87	1.744E-05			
13	120500.	1.080	1.090	0.933219	40.05	12.02	2.778E-05			
14	121000.	1.075	1.107	0.972333	40.39	12.12	4.431E-05			
15	121500.	1.160	1.152	0.973995	41.26	12.38	5.554E-05			
16	122000.	1.210	1.211	0.977290	42.41	12.72	6.444E-05			
17	122500.	1.265	1.291	0.975680	43.94	13.18	6.694E-05			
18	123000.	1.380	1.353	0.968828	45.12	13.54	6.266E-05			
19	123300.	1.410	1.396	0.975443	45.92	13.78	6.883E-05			
20	123600.	1.420	1.435	0.966886	46.63	13.99	7.399E-05			
21	124300.	1.470	1.476	0.996353	47.40	14.22	8.103E-05			
22	124400.	1.555	1.549	0.998859	48.75	14.62	1.150E-04			
23	124700.	1.625	1.625	0.999415	50.15	15.05	1.347E-04			

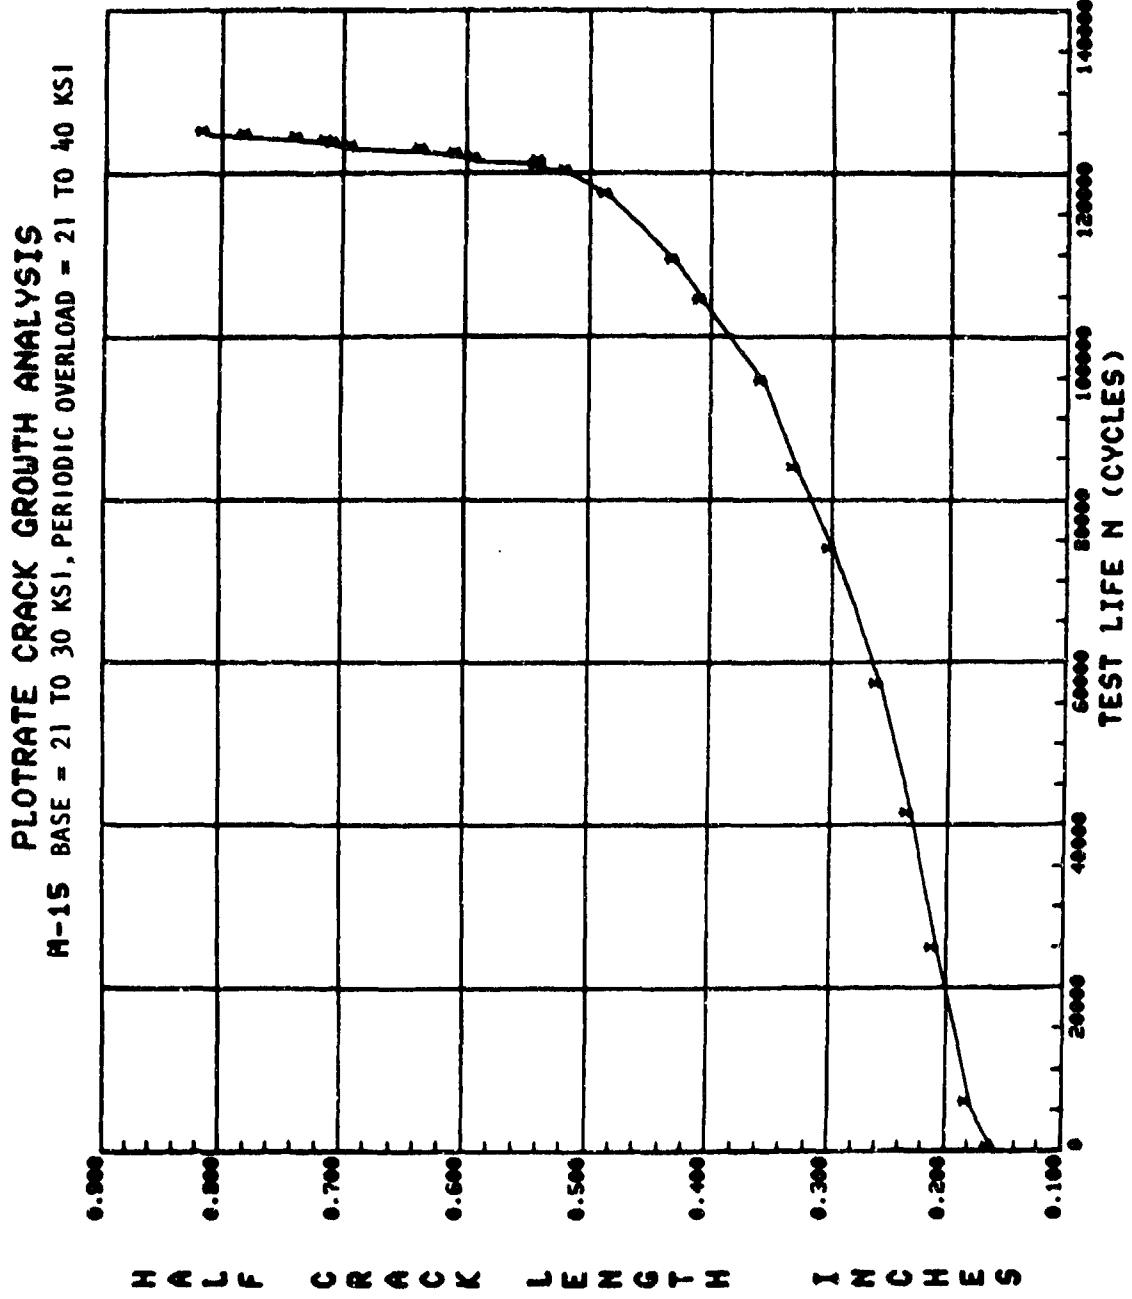


Figure 29. Crack growth curve for test M-15.

TABLE 27. DATA TABULATION FOR TEST M-16

SPECIMEN NO.:	M-16	B= 0.250 IN.	H= 6.000 IN.	A= 0.0 IN.	P MAX=	ENVIRONMENT CONDITION:	AMBIENT AIR	TEST FREQ= 6.00 Hz.
NO.	CYCLES	A(MEASURED)	A(AGGRESSION)	MULT. CONV.	COEFF.	K-MAX	DELTA K	DATA
1	0-	0.303	0.303	0.993037	13.81	17.96	1.834E-05	
2	2000.	0.375	0.383	0.995056	15.54	20.21	2.205E-05	
3	2500.	0.415	0.404	0.993297	15.28	20.77	2.395E-05	
4	3500.	0.450	0.455	0.994935	16.97	22.07	2.768E-05	
5	4000.	0.480	0.483	0.993698	17.48	22.73	3.092E-05	
6	4500.	0.515	0.512	0.992600	18.02	23.62	3.452E-05	
7	5000.	0.550	0.551	0.999746	16.70	24.30	3.947E-05	
8	5500.	0.590	0.590	0.999274	19.36	25.17	4.389E-05	
9	6500.	0.690	0.686	0.992105	20.92	27.20	5.653E-05	
10	7050.	0.745	0.750	0.998860	21.91	28.49	6.714E-05	
11	7600.	0.825	0.828	0.998353	23.07	29.99	8.129E-05	
12	E050.	0.900	0.901	0.992752	24.12	31.36	9.468E-05	
13	8450.	0.960	0.962	0.999191	25.25	32.82	1.129E-04	
14	6750.	1.055	1.051	0.999256	26.18	34.03	1.283E-04	
15	5000.	1.110	1.117	0.999325	27.05	35.11	1.443E-04	
16	9240.	1.190	1.168	0.999123	27.96	36.37	1.654E-04	
17	9450.	1.260	1.259	0.999540	28.89	37.56	1.851E-04	
18	9640.	1.330	1.335	0.992632	29.84	38.80	2.022E-04	
19	9810.	1.410	1.405	0.999002	30.72	39.93	2.283E-04	
20	9950.	1.470	1.471	0.998996	31.54	41.00	2.496E-04	
21	10060.	1.530	1.538	0.998771	32.37	42.06	2.666E-04	
22	10200.	1.610	1.603	0.998745	33.15	43.10	2.914E-04	
23	10360.	1.665	1.663	0.998691	33.90	44.07	3.165E-04	
24	10390.	1.715	1.722	0.993577	34.62	45.00	3.409E-04	
25	10480.	1.765	1.782	0.999666	35.35	45.96	3.654E-04	
26	10560.	1.845	1.844	0.999683	36.10	46.93	3.997E-04	
27	10640.	1.910	1.909	0.998763	36.90	47.97	4.490E-04	
28	10720.	1.980	1.981	0.999433	37.78	49.12	5.052E-04	

TABLE 27. DATA TABULATION FOR TEST M-16 (CONCL)

SPECIMEN NO.: M-16		BASE STRESS 0 TO 20 KSI, OVERLOAD -6 KSI TO +20 KSI		A= 0.0 IN.		A= 0.0 IN.		TEST FREQ= 6.00 Hz.		
LCT - SPECIMEN	PHASE	W= 6.000 IN.	PHASE	ENVIRONMENT CONDITION:	AMBIENT AIR	A (MEASURED)	A (REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K
29	10790.	2.050	2.050			0.999672	0.999672	39.69	50.30	5.619E-04
30	10860.	2.140	2.138			0.998936	0.998936	39.73	51.65	6.067E-04
31	10920.	2.220	2.216			0.999262	0.999262	40.70	52.92	6.504E-04
32	10970.	2.285	2.284			0.999366	0.999366	41.56	54.03	6.619E-04
33	11020.	2.345	2.350			0.998316	0.998316	42.44	55.14	7.346E-04
34	11070.	2.425	2.422			0.996653	0.996653	43.36	56.37	8.382E-04
35	11110.	2.465	2.490			0.999557	0.999557	44.26	57.53	9.454E-04
36	11150.	2.570	2.570			0.999463	0.999463	45.32	58.92	1.055E-03
37	11180.	2.640	2.636			0.998875	0.998875	46.22	60.09	1.263E-03
38	11210.	2.710	2.716			0.998881	0.998881	47.33	61.53	1.444E-03
39	11240.	2.660	2.805			0.994426	0.994426	48.59	63.17	1.684E-03
40	11260.	2.860	2.874			0.999634	0.999634	49.60	64.48	1.869E-03
41	11280.	2.950	2.953			0.999213	0.999213	50.79	66.02	2.114E-03
42	11300.	3.040	3.041			0.997916	0.997916	52.14	67.79	2.499E-03
43	11310.	3.035	3.089			0.999366	0.999366	52.90	68.76	2.640E-03
44	11320.	3.145	3.147			0.998919	0.998919	53.82	69.96	3.300E-03
45	11330.	3.215	3.213			0.999604	0.999604	54.91	71.38	3.786E-03
46	11340.	3.290	3.282			0.997512	0.997512	56.06	72.91	5.071E-03
47	11350.	3.390	3.388			0.991337	0.991337	57.93	75.31	6.621E-03
48	11360.	3.495	3.529			0.994162	0.994162	60.57	78.74	8.979E-03
49	11370.	3.740	3.738			0.995866	0.995866	64.63	84.28	1.299E-02

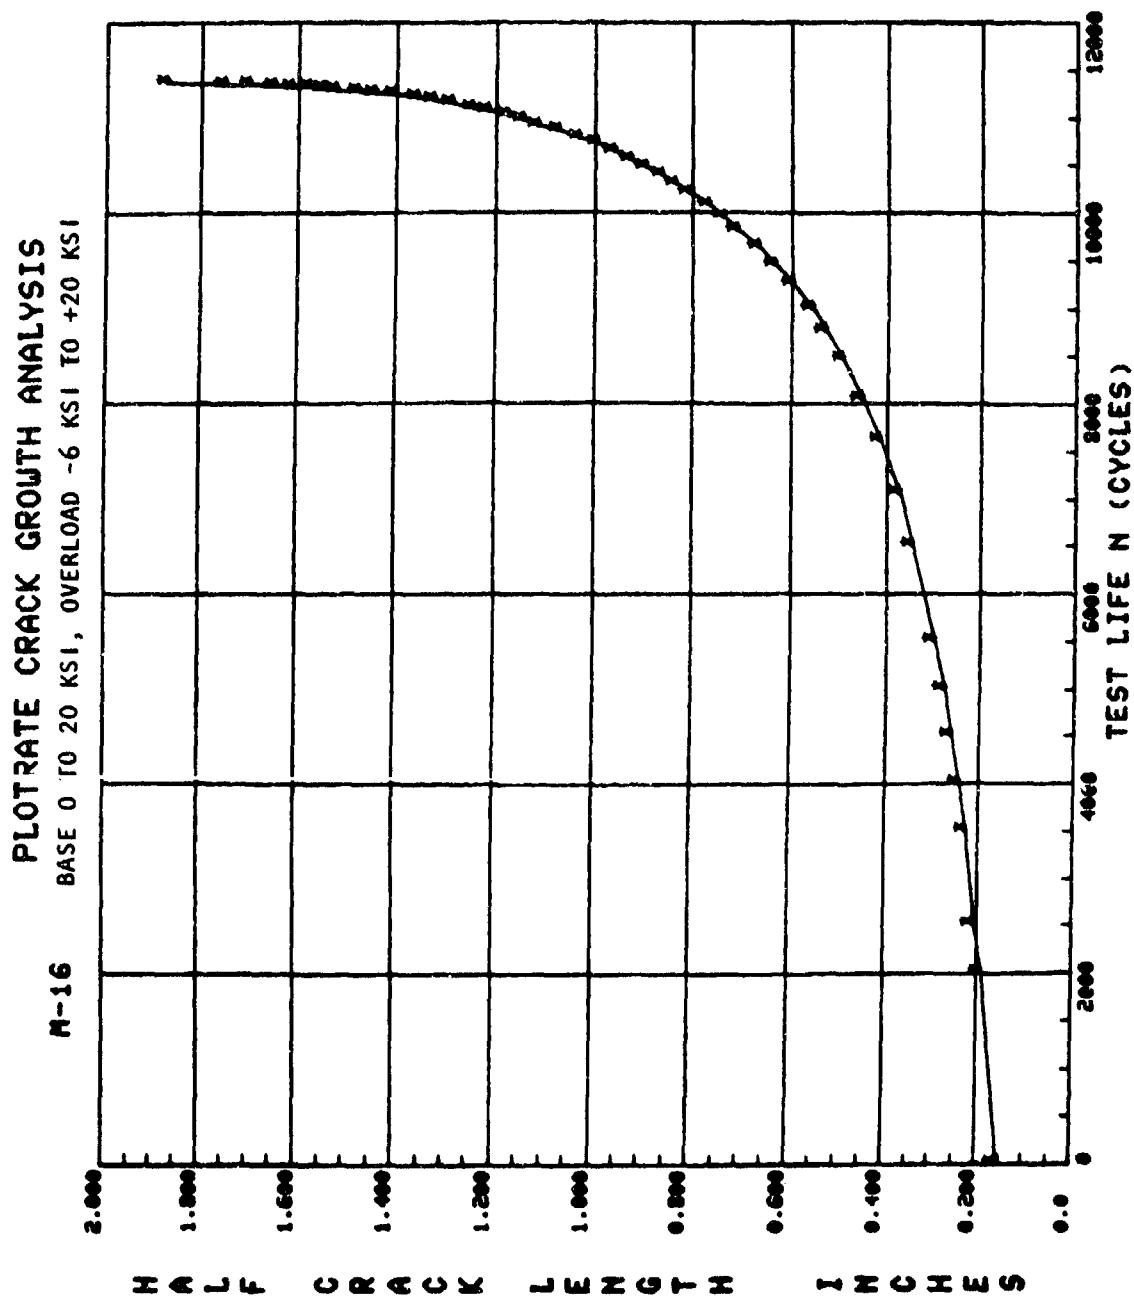


Figure 30. Crack growth curve for test M-16.

TABLE 28. DATA TABULATION FOR TEST M-17

SPECIMEN NO.: 4-17 BASE STRESS = 6 TO 20 kSI. PERIODIC OVERLOAD = -6 kSI TO +20 kSI

CCT SPECIMEN B= 0.250 IN. W= 6.000 IN. A= 0.0 IN.
 P MIN= P MAX=

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A (MEASURED)	AIR PRESSURE (PSI)	MULT. CORR. CUEFF	K-MAX	DA/DN
1	0.	0.305	0.305	0.999958	13.86	9.71
2	5000.	0.355	0.396	0.999899	15.81	11.06
3	5900.	0.440	0.437	0.997064	16.62	2.346E-05
4	6200.	0.455	0.450	0.994487	16.88	11.81
5	6400.	0.465	0.463	0.961774	17.12	11.98
6	6600.	0.465	0.474	0.959726	17.32	12.12
7	7000.	0.485	0.492	0.969851	17.65	12.35
8	7000.	0.505	1.448	0.967877	17.57	12.30
9	8600.	0.545	0.551	0.968787	18.1	13.09
10	9000.	0.560	0.563	0.977275	18.5	13.24
11	9500.	0.555	0.563	0.986447	19.25	13.48
12	10000.	0.600	0.607	0.987656	19.65	13.75
13	10300.	0.630	0.627	0.983531	19.97	13.98
14	11000.	0.650	0.649	0.995477	20.34	14.23
15	11500.	0.675	0.682	0.995881	20.85	14.60
16	12000.	0.720	0.718	0.993017	21.42	14.99
17	12500.	0.760	0.756	0.996744	22.01	15.40
18	13000.	0.795	0.796	0.997403	22.50	15.82
19	13500.	0.825	0.825	0.982298	23.03	16.12
20	14000.	0.870	0.863	0.988799	23.57	16.50
21	14500.	0.850	0.907	0.992907	24.20	16.94
22	15000.	0.975	0.964	0.990496	24.99	17.49
23	15500.	1.025	1.026	0.990687	25.83	18.08
24	16000.	1.105	1.100	0.993929	26.83	18.78
25	16200.	1.115	1.125	0.995739	27.16	19.01
26	16500.	1.175	1.171	0.995806	27.76	19.43
27	16700.	1.205	1.202	0.996146	28.15	19.71
28	17000.	1.250	1.254	0.997348	28.82	20.18

SPECIMEN NO.: 4-17 BASE STRESS = 6 TO 20 KSI, PERIODIC CYCLOAD = -6 KSI TO +20 KSI
 CCT SPFCMEN R= 0.250 IN. W= 6.000 IN.
 PNTS PMAX= TEST FREQ= 6.00 Hz.

NO.	CYCLES	A(MEASURED)	A(REFGRESSIGN)	MULT. COEFF	K-MAX	DELTA K	DA/DN
ENVIRONMENT CONDITION: AMBIENT AIR							
29	17300.	1.310	1.308	0.999823	29.51	20.66	1.037E-04
30	17510.	1.350	1.352	0.999852	30.06	21.04	1.132E-04
31	17800.	1.425	1.424	0.999595	30.96	21.67	1.313E-04
32	18000.	1.480	1.481	0.998179	31.66	22.16	1.376E-04
33	18300.	1.565	1.567	0.997413	32.72	22.90	1.559E-04
34	18500.	1.640	1.632	0.996383	33.52	23.46	1.601E-04
35	18700.	1.685	1.695	0.995185	34.28	24.00	1.779E-04
36	18900.	1.790	1.764	0.995978	35.12	24.59	1.973E-04
37	19100.	1.830	1.844	0.997792	36.10	25.27	2.195E-04
38	19400.	1.950	1.991	0.998217	37.91	26.54	2.655E-04
39	19600.	2.110	2.101	0.998738	39.26	27.48	2.963E-04
40	19790.	2.220	2.223	0.999242	40.79	28.55	3.357E-04
41	19970.	2.340	2.341	0.998239	42.30	29.61	3.857E-04
42	20140.	2.470	2.473	0.999355	44.03	30.82	4.483E-04
43	20300.	2.615	2.621	0.998221	46.02	32.22	5.521E-04
44	20440.	2.765	2.783	0.997312	48.29	33.80	6.949E-04
45	20540.	2.905	2.926	0.997882	50.38	35.26	8.425E-04
46	20630.	3.075	3.087	0.995708	52.86	37.01	1.092E-03
47	20680.	3.155	3.196	0.995809	54.62	38.23	1.406E-03
48	20720.	3.285	3.314	0.991717	56.64	39.65	1.834E-03
49	20750.	3.410	3.421	0.963003	58.54	40.97	3.103E-03
50	20770.	3.510	3.531	0.981054	60.59	42.42	4.226E-03
51	20790.	3.640	3.704	0.988243	64.09	44.86	5.909E-03
52	20810.	3.985	3.983	0.995522	70.51	49.36	9.423E-03

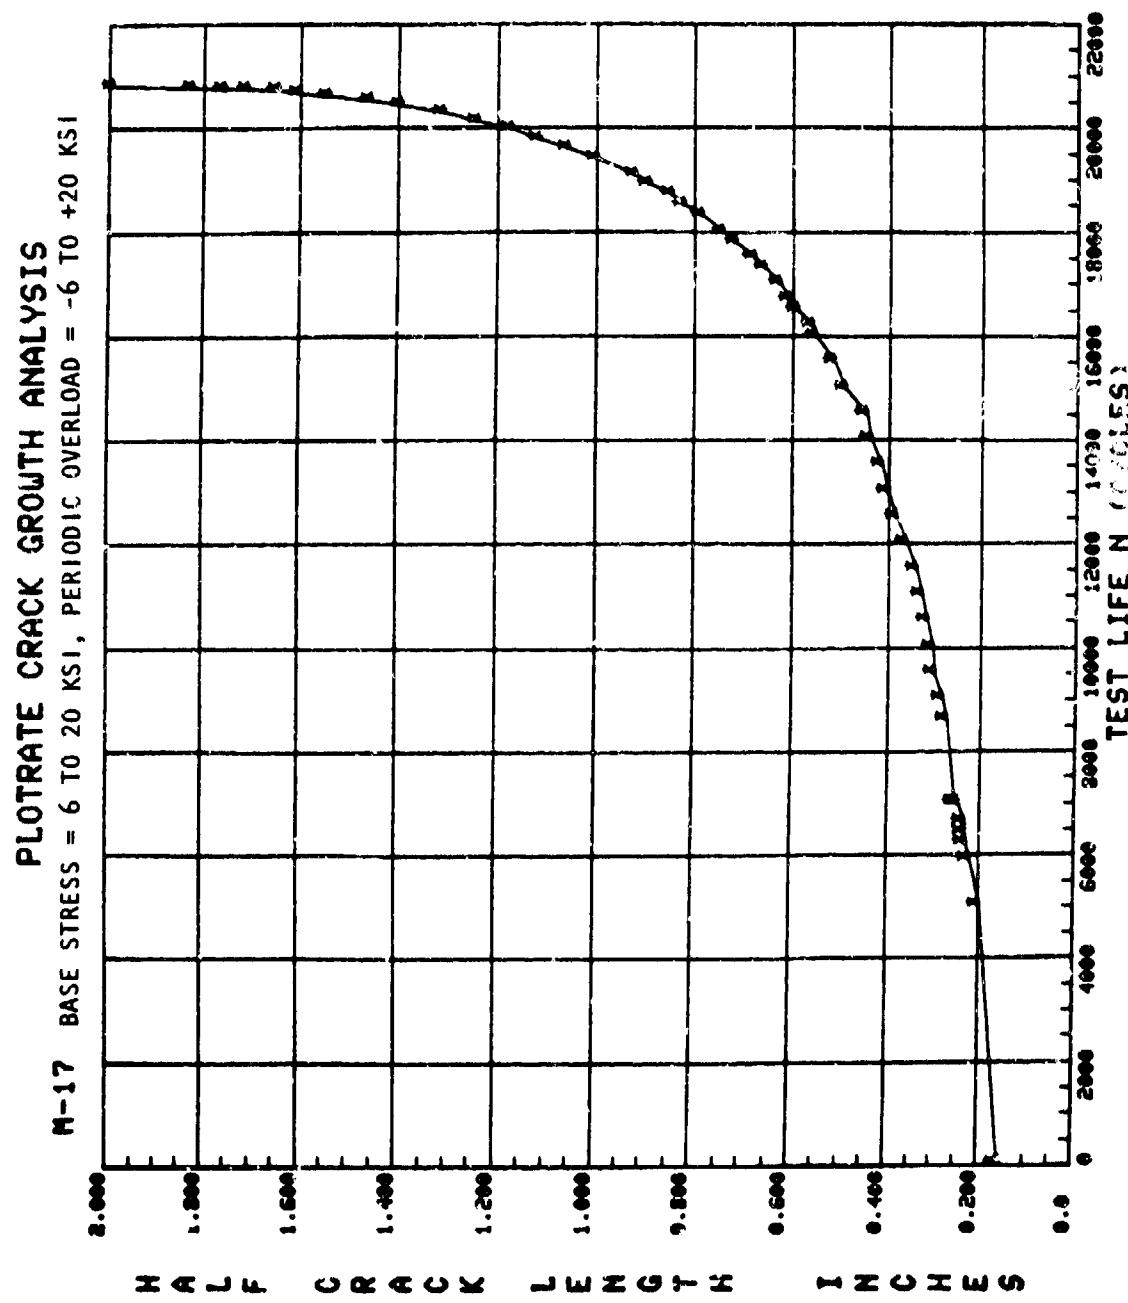


Figure 31. Crack growth curve for test M-17.

TABLE 29. DATA TABULATION FOR TEST M-18

SPECIMEN NO.	TEST SPECIMEN	R = 0.250 IN.	k = 6.000 IN.	A = 0.0 IN.	TEST FREQUENCY = 6.000 Hz.	ENVIRONMENT CONDITION: AMBIENT AIR		DATA
						P MIN	P MAX	
1	0.	0.250	0.291	0.985698	27.06	8.12	3.843E-05	
2	500.	0.330	0.318	0.962512	28.31	8.49	2.273E-05	
3	1000.	0.340	0.320	0.959551	28.81	8.64	1.481E-05	
4	2000.	0.355	0.356	0.980147	29.96	8.99	1.322E-05	
5	3000.	0.373	0.373	0.995097	30.69	9.21	1.225E-05	
6	5000.	0.440	0.432	0.996104	33.07	9.92	2.026E-05	
7	6500.	0.450	0.450	0.995784	35.60	10.68	2.902E-05	
8	7800.	0.580	0.585	0.995644	38.55	11.57	3.919E-05	
9	9800.	0.660	0.660	0.998101	41.28	12.39	5.371E-05	
10	9300.	0.720	0.728	0.989783	43.14	12.94	7.167E-05	
11	9600.	0.760	0.766	0.996037	44.30	13.29	8.563E-05	
12	9900.	0.810	0.817	0.996326	45.83	13.75	1.032E-04	
13	10200.	0.855	0.863	0.995960	47.72	14.31	1.202E-04	
14	10400.	0.925	0.933	0.994227	49.14	14.74	1.423E-04	
15	10600.	0.955	0.963	0.993029	50.78	15.24	1.694E-04	
16	10700.	1.015	1.023	0.995312	51.59	15.48	1.773E-04	
17	10900.	1.105	1.105	0.981683	53.78	16.13	1.716E-04	
18	11000.	1.155	1.142	0.980473	54.75	16.42	1.747E-04	
19	11100.	1.185	1.177	0.979442	55.67	16.70	1.786E-04	
20	11200.	1.185	1.203	0.976929	56.35	16.91	1.763E-04	
21	11350.	1.260	1.253	0.992437	57.62	17.29	2.313E-04	
22	11450.	1.300	1.303	0.994275	58.88	17.66	2.935E-04	
23	11500.	1.335	1.337	0.997423	59.74	17.92	3.150E-04	
24	11600.	1.405	1.405	0.999213	61.45	18.43	4.146E-04	

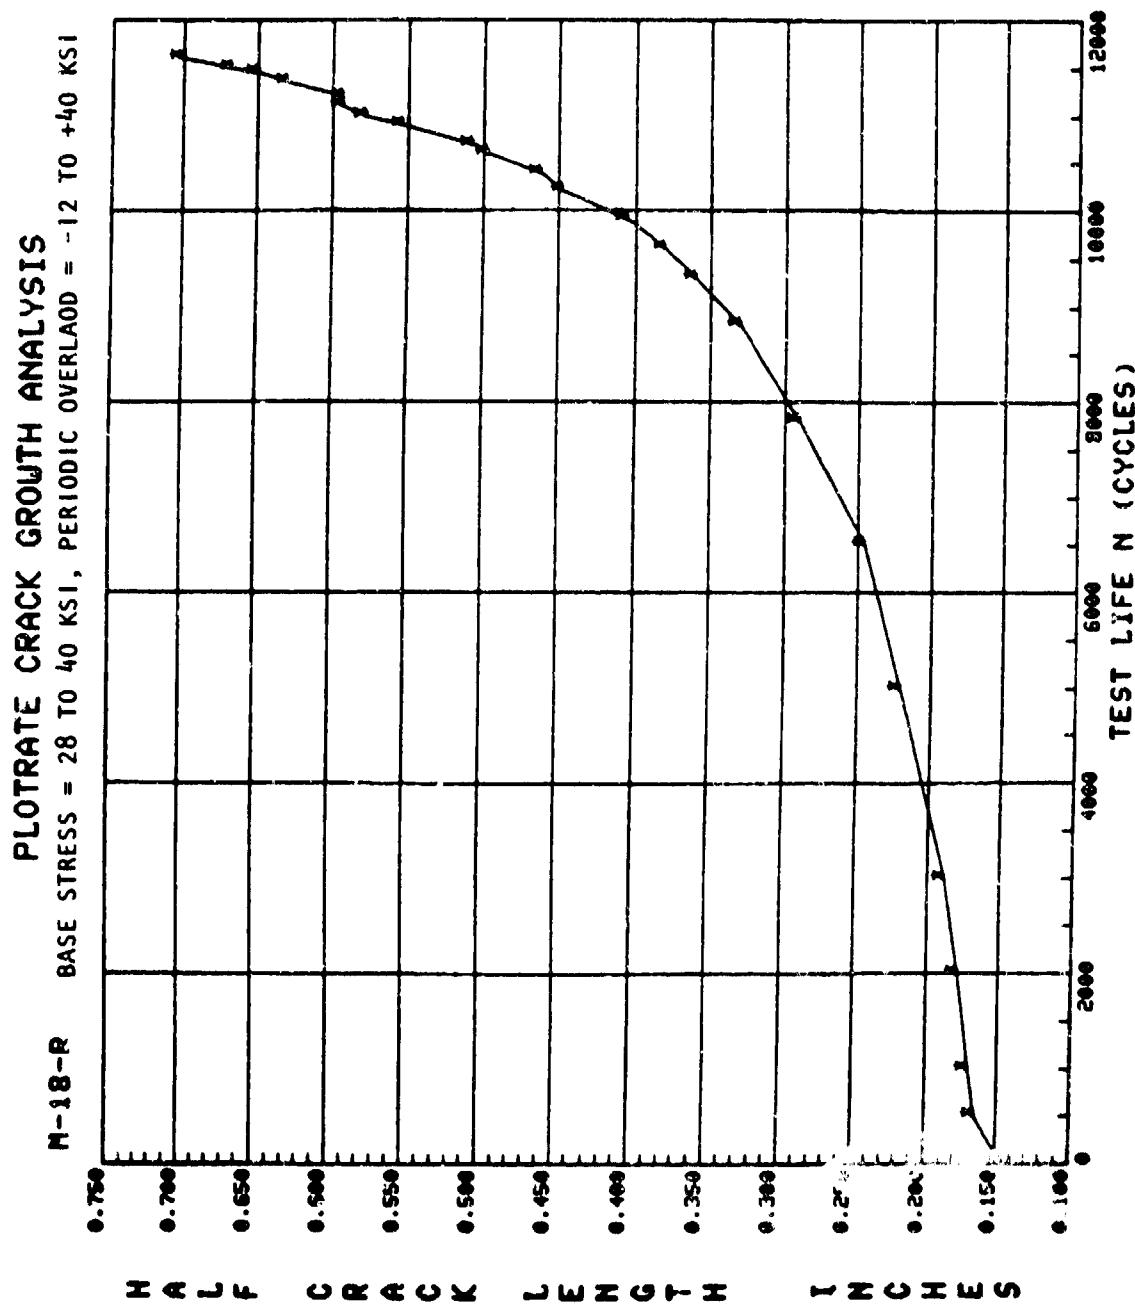


Figure 32. Crack growth curve for test M-18-R.

TABLE 30. DATA TABULATION FOR TEST M-19

SPECIMEN NO.: 4-19 BASE STRESS = 0 TO 20 KSI, SINGLE OVERLOAD +30 KSI to -6 KSI

CCT SPECIMEN $\alpha = 0.250$ IN. $W = 6.000$ IN. $\Delta\Lambda = 0.0$ IN. $P_{MIN} = P_{MAX}$

TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	ALMEASREDI	ALREGRESSCHI	MULT. CORR.	CDEFF	K-MAX	DA/DN	DELTA K
1	0.	0.250	0.290	0.997767	20.28	24.34	1.278E-05	
2	824.	0.315	0.311	0.996318	21.01	25.20	1.543E-05	
3	1550.	0.335	0.337	0.996127	21.87	26.25	2.096E-05	
4	2000.	0.355	0.358	0.977831	22.55	27.05	1.904E-05	
5	2500.	0.385	0.379	0.978077	23.19	27.83	1.697E-05	
6	2501.	0.385	0.376	0.966317	23.10	27.72	1.756E-05	
7	3101.	0.395	0.392	0.980926	23.60	28.32	1.380E-05	
8	4501.	0.430	0.433	0.995246	24.92	29.78	2.063E-05	
9	5501.	0.485	0.483	0.994702	26.24	31.49	2.638E-05	
10	6001.	0.515	0.512	0.995362	27.02	32.42	2.959E-05	
11	6501.	0.550	0.545	0.996066	27.89	33.47	3.333E-05	
12	7001.	0.570	0.576	0.993440	28.69	34.43	3.854E-05	
13	7501.	0.615	0.615	0.995983	29.66	35.59	4.677E-05	
14	8001.	0.660	0.664	0.977178	30.95	37.03	5.672E-05	
15	8301.	0.705	0.701	0.996347	31.74	38.08	5.777E-05	
16	8501.	0.720	0.725	0.995194	32.30	38.76	6.127E-05	
17	8701.	0.750	0.752	0.992181	32.90	39.48	6.616E-05	
18	8901.	0.770	0.775	0.996394	33.44	40.13	7.000E-05	
19	9101.	0.805	0.805	0.993535	34.10	40.92	7.249E-05	
20	9201.	0.825	0.821	0.996442	34.46	41.35	7.599E-05	
21	9401.	0.855	0.853	0.997629	35.15	42.18	7.966E-05	
22	9601.	0.880	0.882	0.998393	35.78	42.94	8.067E-05	
23	9801.	0.915	0.916	0.996770	36.49	43.79	8.109E-05	
24	10001.	0.950	0.947	0.989656	37.14	44.57	9.413E-05	
25	10201.	0.990	0.987	0.988977	37.97	45.57	1.019E-04	
26	10351.	1.005	1.019	0.988465	38.61	46.33	1.059E-04	
27	10501.	1.065	1.051	0.987719	39.27	47.12	1.153E-04	
28	10651.	1.085	1.087	0.987051	39.98	47.98	1.261E-04	

TABLE 30. DATA TABULATION FOR TEST M-19 (CONT)

CYCLES	AMBIENT AIR	AMBIENT AIR	TEST FREQ= 6.00 Hz.	ENVIRONMENT CONDITION:		TEST FREQ= 6.00 Hz.	AMBIENT AIR	AMBIENT AIR	TEST FREQ= 6.00 Hz.
				NO.	PHASE				
29	10401.	1.120	1.128	0.987798	K-MAX	40.80	48.96	1.296E-04	
30	10401.	1.155	1.150	0.994530	41.23	49.47	1.374E-04		
31	11001.	1.185	1.182	0.993867	41.85	50.22	1.393E-04		
32	11101.	1.205	1.211	0.987620	42.40	50.88	1.496E-04		
33	11201.	1.245	1.238	0.986925	42.93	51.52	1.638E-04		
34	11301.	1.260	1.271	0.986344	43.57	52.28	1.837E-04		
35	11351.	1.295	1.291	0.982466	43.94	52.73	1.826E-04		
36	11401.	1.315	1.308	0.979623	44.27	53.12	1.967E-04		
37	11451.	1.320	1.311	0.990745	44.69	53.63	2.162E-04		
38	11500.	1.345	1.353	0.977170	45.12	54.14	1.901E-04		
39	11550.	1.375	1.370	0.974356	45.44	54.52	2.004E-04		
40	11690.	1.440	1.429	0.976594	46.53	55.83	2.203E-04		
41	11750.	1.435	1.456	0.975584	47.03	56.43	2.251E-04		
42	11800.	1.485	1.478	0.971796	47.44	56.93	2.113E-04		
43	11850.	1.505	1.498	0.982762	47.81	57.37	2.192E-04		
44	11900.	1.525	1.522	0.991651	48.24	57.89	2.471E-04		
45	12000.	1.560	1.566	0.999177	49.07	58.88	2.310E-04		
46	12200.	1.675	1.670	0.999380	50.96	61.16	2.886E-04		
47	12300.	1.735	1.731	0.999496	52.08	62.49	3.168E-04		
48	12400.	1.795	1.798	0.999663	53.31	63.98	3.509E-04		
49	12500.	1.870	1.869	0.999942	54.61	65.53	3.804E-04		
50	12600.	1.950	1.950	0.999951	56.10	67.31	4.143E-04		
51	12700.	2.035	2.034	0.999528	57.66	69.19	4.562E-04		
52	12800.	2.130	2.127	0.999535	59.38	71.26	5.053E-04		
52	12900.	2.225	2.229	0.999327	61.31	73.58	5.763E-04		
54	13000.	2.350	2.349	0.999644	63.60	76.32	6.670E-04		
55	13090.	2.470	2.474	0.999867	66.05	79.26	7.712E-04		
56	13170.	2.605	2.633	0.999406	68.66	82.39	8.984E-04		

TABLE 30. DATA TABULATION FOR TEST M-19 (CONCL)

SPECIMEN NO.:		BASE STRESS = 0 TO 20 KSI, SINGLE OVERLOAD +30 KSI TO -6 KSI			
CYCLES	SPECIMEN	R = 0.750 IN.	W = 6.000 IN.	AH = 0.0	IN.
P _{MIN} = P _{MAX} =					TEST FREQ = 6.00 Hz.
ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLES	A(MEASLED)	A(REFGRESSCN)	MULT. COEFF	K-MAX
57	13240.	2.730	2.710	0.995597	71.31
58	13301.	2.655	2.866	0.994589	74.23
59	13350.	2.985	3.007	0.992298	77.42
60	13390.	3.155	3.165	0.991471	81.16
61	13420.	3.255	3.334	0.990728	85.47
62	13440.	3.465	3.491	0.993712	89.77
63	13450.	3.525	3.588	0.999784	92.57
64	13460.	3.725	3.725	0.999994	96.82
					116.18
					7.598E-03
					1.112E-03
					1.407E-03
					1.909E-03
					2.656E-03
					3.771E-03
					4.985E-03
					6.346E-03
					7.598E-03

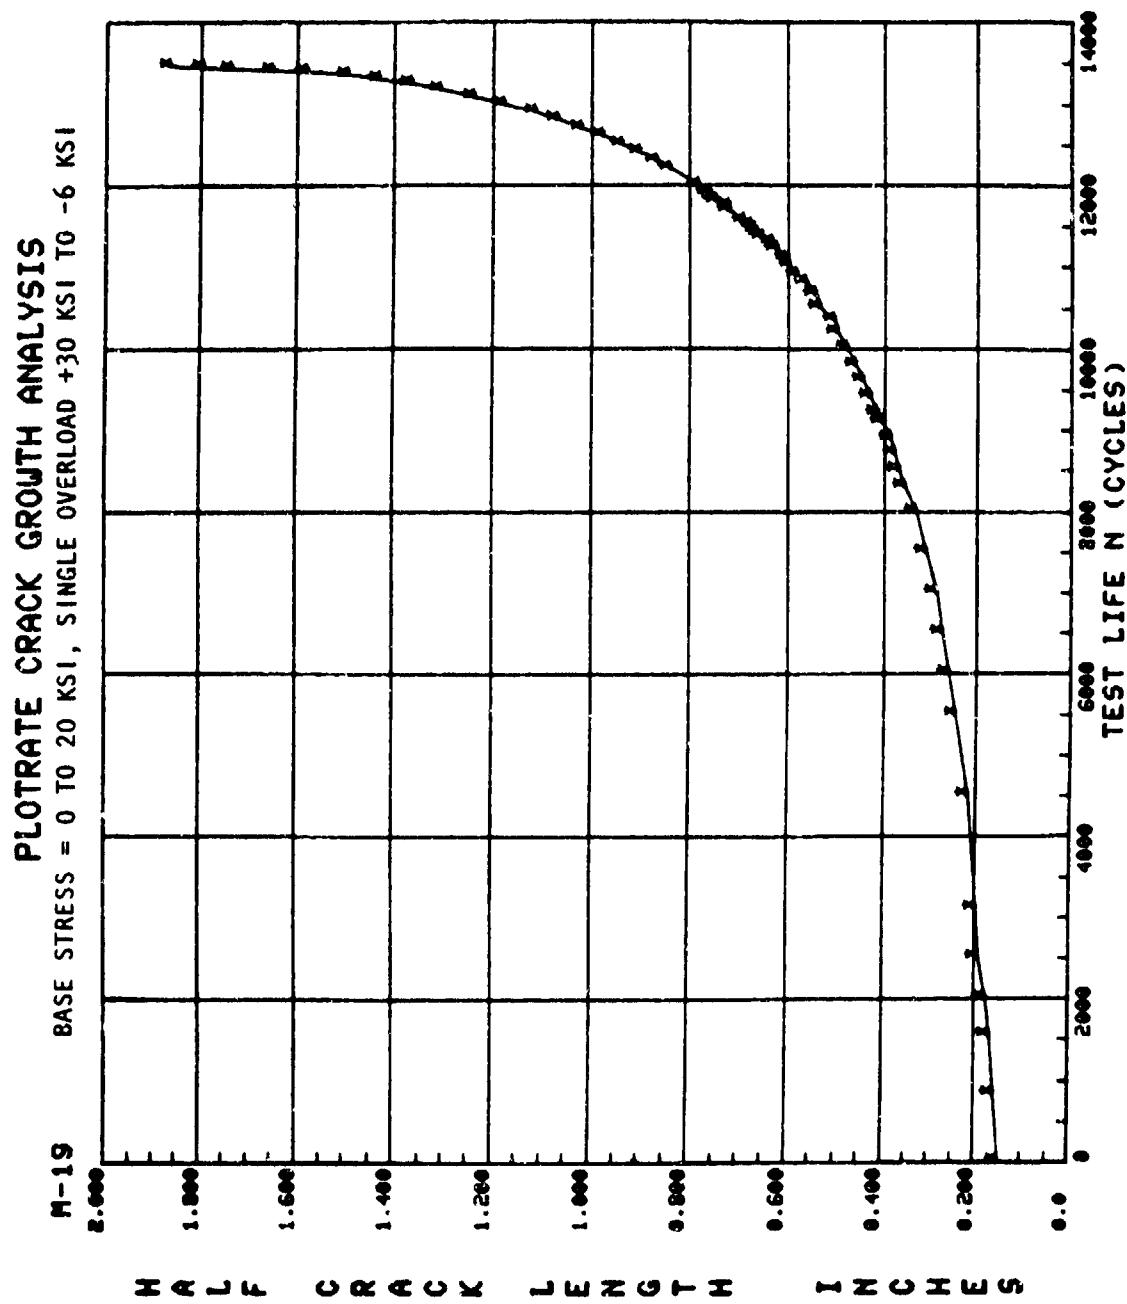


Figure 33. Crack growth curve for test M-19.

TABLE 31. DATA TABULATION FOR TEST M-20

SPECIMEN NO.: M-20-R PAGE STRESS = 0 - 20 KSI, MULTIPLE LOAD RETARD. = -6.0 - 30 KSI

P_{MIN} = -9.00 KIPS P_{MAX} = 45.00 KIPS R = -0.200 TEST FREQ = 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	ALMFA(SIREN) AIRREGRESSION)	MULT. CORR. COEFF.	K-MAX	DELTA K	DA/DK	
1	0.	0.301	0.994308	20.66	24.79	1.159E-05	
2	1000.	0.230	0.916249	21.11	25.33	6.084E-07	
3	2500.	0.214	0.959168	21.09	25.31	-5.885E-07	
4	18000.	0.410	0.966123	24.30	29.15	9.787E-06	
5	23200.	0.520	0.987358	27.74	33.29	1.609E-05	
6	24500.	0.570	0.994109	28.86	34.63	1.816E-05	
7	25999.	0.650	0.985610	30.20	36.25	2.518E-05	
8	27600.	0.710	0.944279	32.16	38.60	3.346E-05	
9	28400.	0.745	0.968584	33.34	40.01	3.928E-05	
10	29300.	0.840	0.989604	34.90	41.87	4.512E-05	
11	30000.	0.920	0.993038	36.49	43.79	4.863E-05	
12	30500.	0.980	0.995672	37.83	45.39	5.185E-05	
13	31100.	1.020	0.992801	38.65	46.37	5.912E-05	
14	31700.	1.090	0.995804	40.12	48.14	6.873E-05	
15	32230.	1.155	0.9946713	41.56	49.87	7.814E-05	
16	32940.	1.270	0.997233	43.54	52.25	9.393E-05	
17	33360.	1.345	1.268	0.994615	45.39	54.46	1.127E-04
18	33900.	1.470	1.486	0.992164	47.58	57.10	1.401E-04
19	34200.	1.585	1.593	1.945551	49.56	59.47	1.915E-04
20	34500.	1.705	1.714	0.997527	51.77	62.12	2.455E-04
21	34710.	1.800	1.814	0.989061	53.60	64.33	3.334E-04
22	34900.	1.945	1.953	0.992311	56.16	67.39	4.435E-04
23	35000.	2.010	2.037	0.992039	57.71	69.26	5.107E-04
24	35100.	2.175	2.143	0.986646	59.69	71.63	5.321E-04
25	35150.	2.205	2.215	0.981710	60.90	73.08	4.579E-04
26	35200.	2.245	2.259	0.990651	61.37	74.25	4.547E-04
27	35250.	2.295	2.291	0.999166	62.49	74.98	3.459E-04
28	35350.	2.350	2.348	0.995031	63.60	76.31	3.136E-04

TABLE 31. DATA TABULATION FOR TEST M-20 (CONCL.)

SPECIMEN NO.: 4-20-R BASE STRESS = 0 - 20 KSI, MULTIPLE LOAD RETARD. = -6.0 - 30 KSI		P _{MIN} = -9.00 KIPS P _{MAX} = 45.00 KIPS R = -0.200 TEST FREQ = 6.00 Hz		ENVIRONMENT CONDITION: AMBIENT AIR		NO.		CYCLES		A(MEASURES) AIRFRGSSION)		MULT. CORR. COEFF.		K-MAX		DELTA K		DA/DK	
29	35450.	2.410	2.406	0.994586	64.73	77.67	3.365E-04												
30	35500.	2.430	2.438	0.997320	65.35	78.42	3.567E-04												
31	35500.	2.510	2.512	0.996876	66.83	80.20	4.544E-04												
32	35650.	2.565	2.558	0.998241	67.74	81.29	5.190E-04												
33	35700.	2.605	2.614	0.998686	68.89	82.66	5.946E-04												
34	35750.	2.690	2.675	0.998851	70.14	84.17	6.720E-04												
35	35800.	2.745	2.744	0.999269	71.60	85.92	7.750E-04												
36	35950.	2.825	2.925	0.997875	73.34	88.01	9.309E-04												
37	35900.	2.920	2.917	0.997048	75.37	90.44	1.125E-03												
38	35950.	3.020	3.039	0.997090	76.17	93.80	1.509E-03												
39	35990.	3.155	3.166	0.996057	81.20	97.44	2.012E-03												
40	36020.	3.295	3.294	0.994727	84.42	101.30	2.712E-03												
41	36040.	3.385	3.405	0.995114	87.38	104.65	3.560E-03												
42	36055.	3.500	3.513	0.997930	90.37	108.45	4.427E-03												
43	36065.	3.405	3.601	0.999874	92.97	111.56	5.327E-03												
44	36075.	3.715	3.715	0.999789	96.51	115.61	6.085E-03												

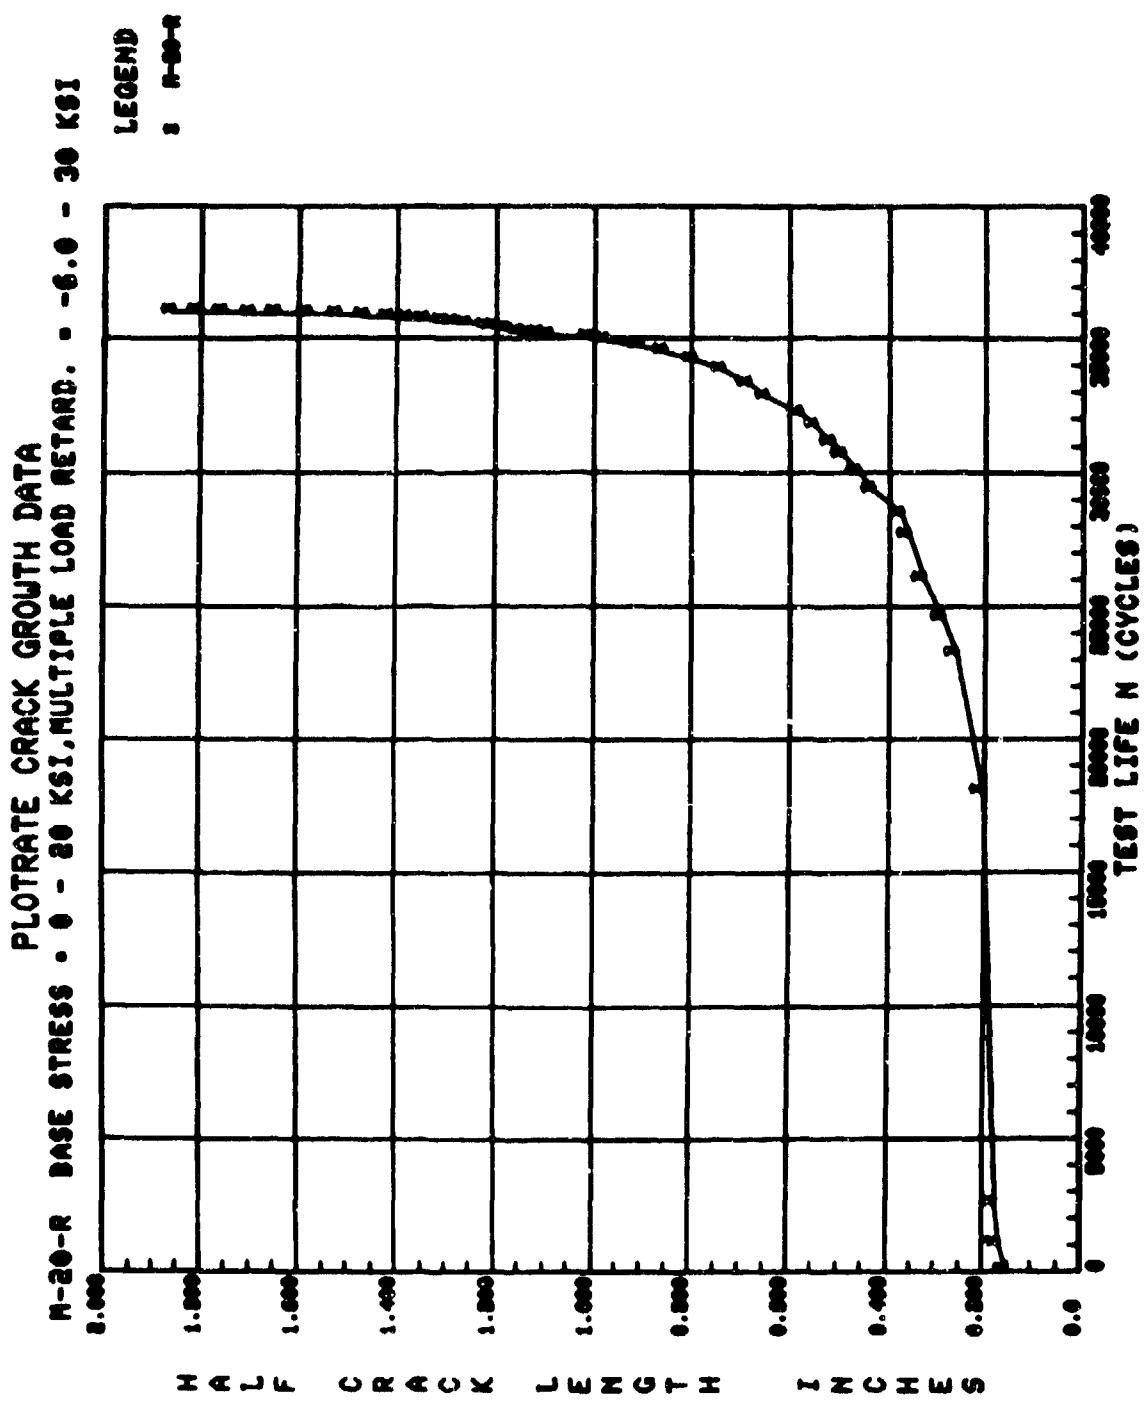


Figure 34. Crack growth curve for test M-20.

TABLE 32. DATA TABULATION FOR TEST M-21

SPECIMEN NO.: M-21		BASE STRESS = 0 TO 20 KSI, PERIODIC OVERLOAD +40 KSI TO -12 KSI		TEST FREQ= 6.000 Hz.	
CCT	SPECIMEN	B= 0.250 IN.	w= 6.000 IN.	Ah= 0.0	IN.
P MIN=	P MAX=				
ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLES	ALIMEASURED)	ALIREGRESSION)	MULT. CORR. COEFF	K-MAX
1	0.	0.320	0.320	0.999984	18.94
2	2000.	0.375	0.370	0.995668	20.38
3	3000.	0.405	0.410	0.984296	21.46
4	4000.	0.435	0.442	0.986748	22.28
5	5025.	0.455	0.478	0.987782	23.20
6	6500.	0.515	0.526	0.989047	24.35
7	7525.	0.560	0.559	0.987805	25.12
8	9000.	0.600	0.594	0.987397	25.91
9	10500.	0.645	0.641	0.989029	26.95
10	12000.	0.670	0.683	0.991426	27.84
11	13500.	0.745	0.733	0.992718	28.87
12	14500.	0.765	0.773	0.993936	29.68
13	15500.	0.820	0.816	0.985533	30.56
14	16500.	0.875	0.874	0.988940	31.64
15	17501.	0.925	0.934	0.982561	32.77
16	18501.	1.045	1.019	0.988872	34.33
17	19500.	1.055	1.116	0.986280	36.49
18	20500.	1.300	1.277	0.982479	38.82
19	21000.	1.375	1.349	0.977100	40.03
20	21500.	1.420	1.433	0.995450	41.42
21	22000.	1.475	1.481	0.996438	42.22
22	22500.	1.540	1.540	1.000000	43.19
					59.39
					6.999E-05

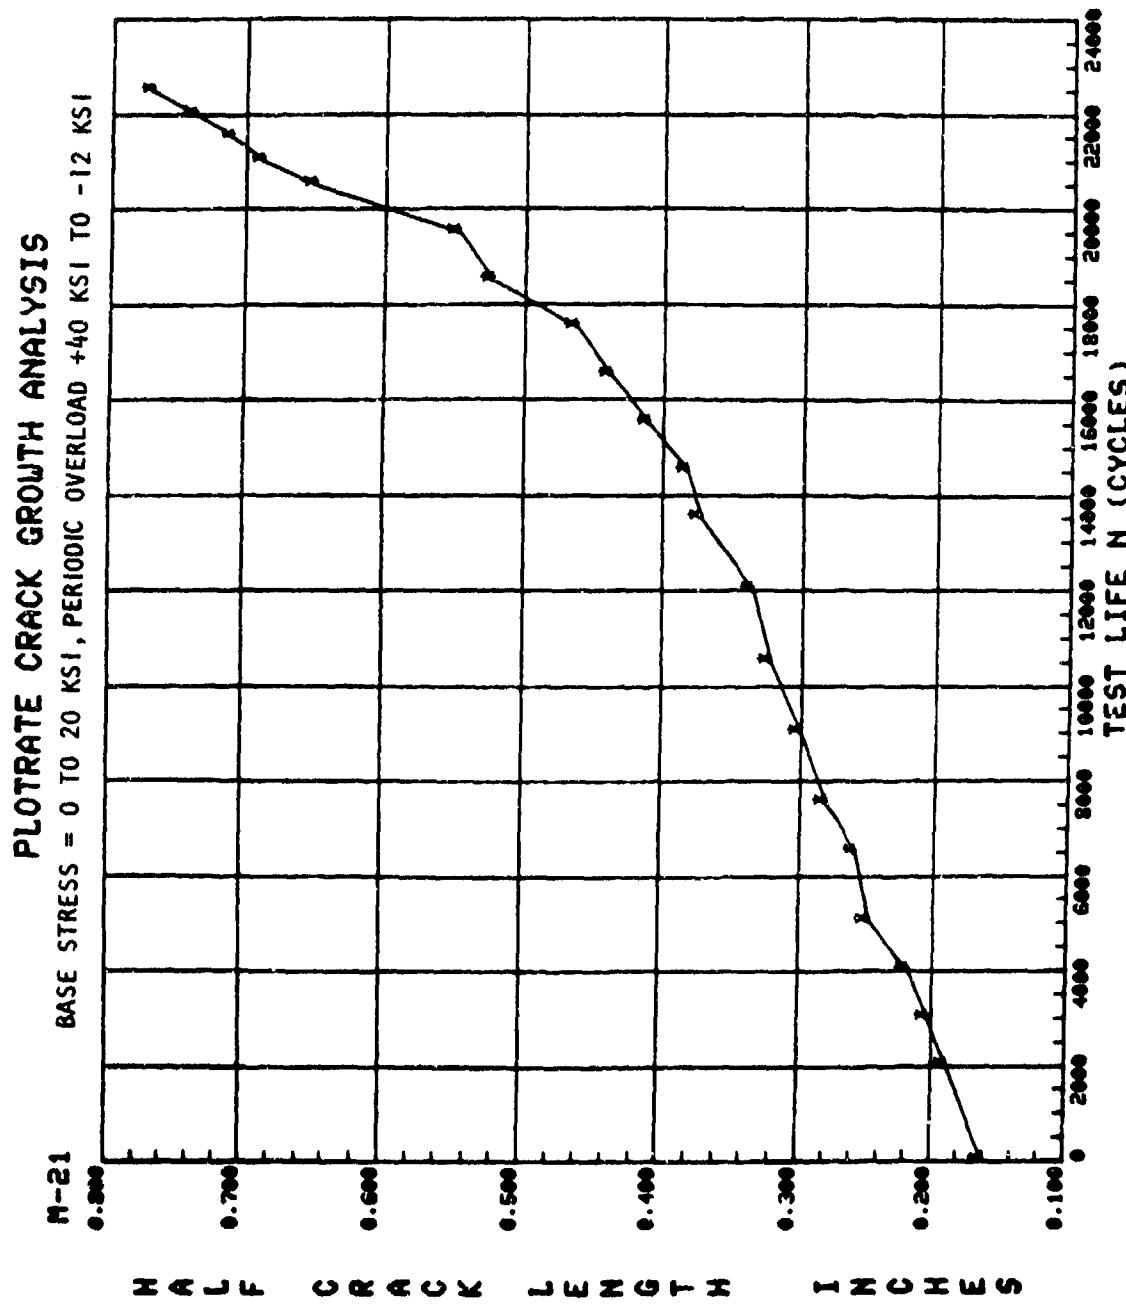


Figure 35. Crack growth curve for test M-21.

TABLE 33. DATA TABULATION FOR TEST M-22

TEST SPECIMEN NO.:	M-22	BASE STRESS = 0-20 KSI, SINGLE OVERLOAD = -6 TO +30 KSI		
TEST SPECIMEN	R = 0.250 IN.	W = 4.0000 IN.	ΔR = 0.0 IN.	TEST FREQ = 6.00 Hz.
P MIN =	P MAX =			
ENVIRONMENT CONDITION: AMBIENT AIR				
NO.	CYCLES	Δ MEASURED (1)	Δ REGRESSION (1)	MULT. CORR. COEFF
1	0.	0.315	0.315	0.998749
2	1830.	0.365	0.370	0.998842
3	2500.	0.395	0.391	0.998143
4	3700.	0.440	0.436	0.997344
5	5350.	0.505	0.510	0.997115
6	6470.	0.575	0.576	0.997730
7	7360.	0.640	0.640	0.998027
8	8050.	0.705	0.710	0.999387
9	8630.	0.775	0.763	0.994534
10	11130.	1.210	1.213	0.993944
11	11630.	1.255	1.346	0.994775
12	12130.	1.520	1.525	0.994865
13	12230.	1.470	1.558	0.996096
14	12330.	1.615	1.615	0.998723
15	12430.	1.655	1.663	0.994270
16	12500.	1.705	1.643	0.991361
17	12570.	1.725	1.723	0.988220
18	12640.	1.745	1.756	0.991075
19	12710.	1.750	1.789	0.996726
20	12810.	1.855	1.848	0.998426
21	12910.	1.910	1.913	0.998683
22	13010.	1.985	1.989	0.996900
23	13110.	2.065	2.065	0.997104
24	13210.	2.165	2.150	0.997564
25	13310.	2.225	2.239	0.997571
26	13410.	2.340	2.335	0.997967
27	13510.	2.450	2.444	0.998180
28	13610.	2.585	2.580	0.995084

DELTA K	DELTA N
14.09	1.196E-05
15.28	1.656E-05
15.71	1.804E-05
16.60	2.154E-05
17.98	2.823E-05
19.14	3.638E-05
20.19	4.958E-05
21.29	5.684E-05
22.11	6.418E-05
28.29	1.316E-04
29.98	1.650E-04
32.20	1.998E-04
32.61	2.564E-04
33.30	2.354E-04
33.90	2.204E-04
34.26	2.240E-04
34.62	2.415E-04
35.93	2.506E-04
35.43	2.595E-04
36.15	3.082E-04
36.95	3.540E-04
37.88	3.714E-04
38.82	4.045E-04
39.88	4.446E-04
40.99	4.902E-04
42.23	5.558E-04
43.64	6.777E-04
45.46	8.911E-04

TABLE 33. DATA TABULATION FOR TEST M-22 (CONCL)

SPECIMEN NO.: M-22 BASE STRESS = 0-20 KSI. SINGLE OVERLOAD = -6 TO +30 KSI

CCT SPECIMEN R = 0.250 IN. W = 6.000 IN. A = 0.01 IN.

PMT = TEST FREQU = 6.000 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	MEASURFD1	REGRESSION	MULT. COEFF.	K-MAX	DA/DN
29	13710.	2.755	2.765	0.998127	48.03	1.137E-03
30	13810.	2.955	3.013	0.999233	51.70	1.484E-03
31	13910.	3.350	3.349	0.999837	57.25	1.971E-03

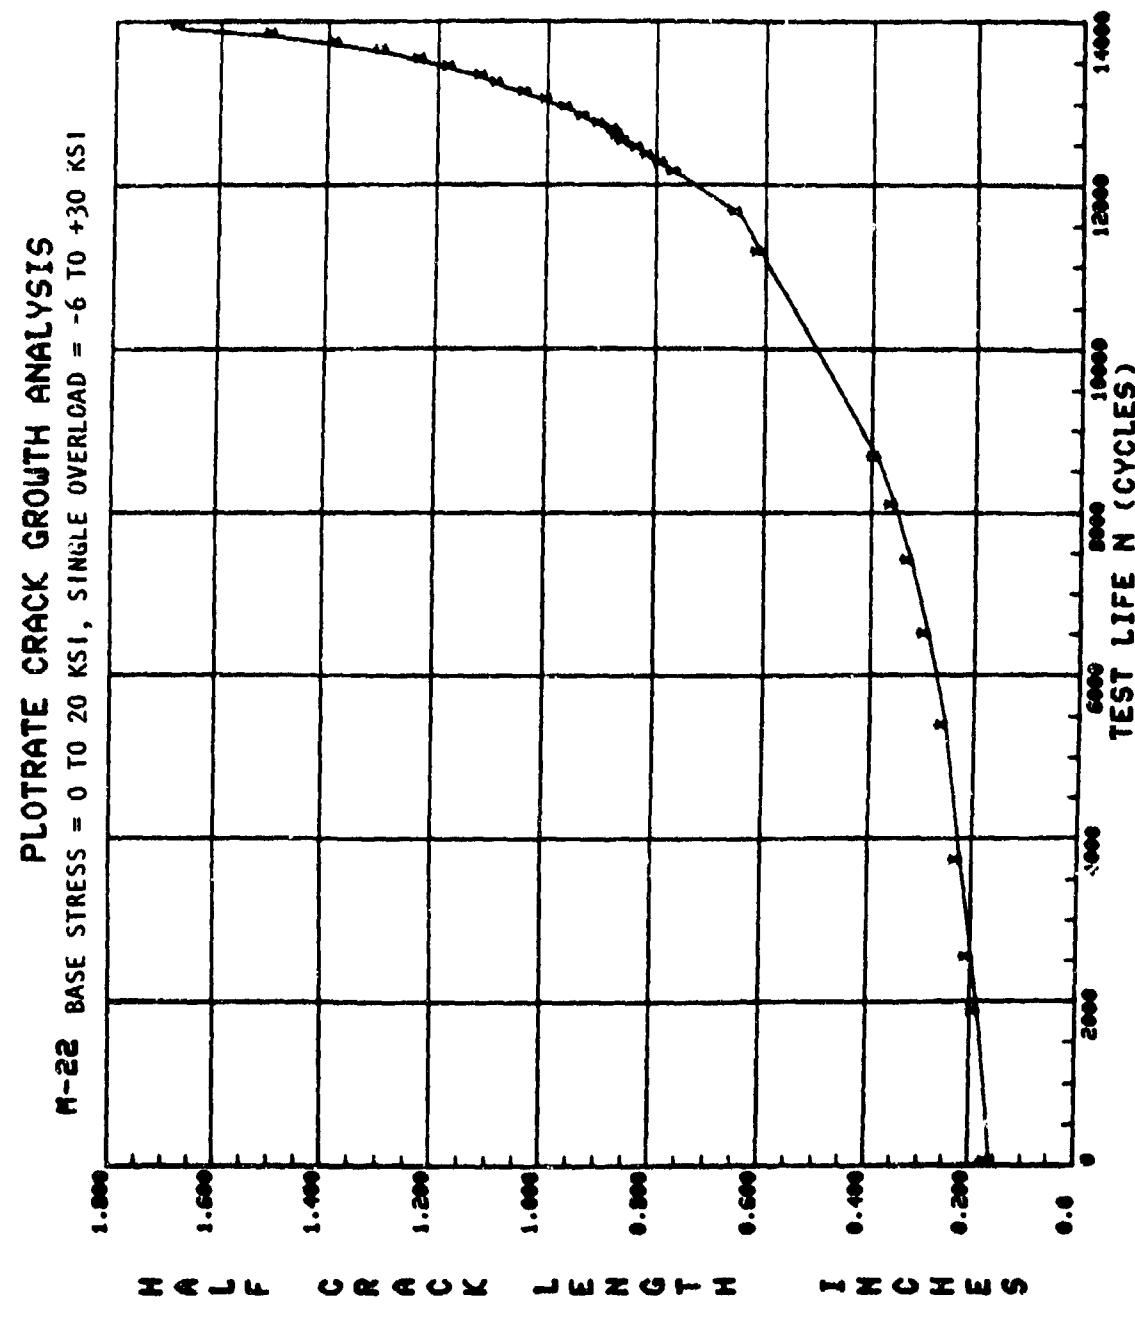


Figure 36. Crack growth curve for test M-22.

TABLE 34. DATA TABULATION FOR TEST M-23

SPECIMEN NO.: M-23 BASE STRESS 0 TO +20 KSI, PERIODIC OVERLOAD = -6 TO +30 KSI
 CCT. SPECIMEN B= 0.250 IN. w= 0.0001 IN. A= 0.01 IN.
 PMIY= P MAX= TEST FREQ= 6.000 Hz.

NO.	CYCLES	A(MFASLFFDI)	A(REFGRESSICN)	MULT. COEF	COEFF	K-MAX	DETA K	
							DA/DN	DA/DN
1	0.	0.303	0.302	0.994853	13.80	13.80	1.602E-05	1.602E-05
2	1000.	0.320	0.337	0.995219	14.59	14.59	1.743E-05	1.743E-05
3	2000.	0.375	0.367	0.992651	15.23	15.23	1.724E-05	1.724E-05
4	3000.	0.405	0.404	0.993911	15.97	15.97	1.791E-05	1.791E-05
5	4000.	0.430	0.438	0.991913	16.64	16.64	1.982E-05	1.982E-05
6	5004.	0.465	0.478	0.994462	17.39	17.39	2.090E-05	2.090E-05
7	6000.	0.515	0.523	0.995605	18.20	18.20	2.322E-05	2.322E-05
8	7060.	0.580	0.572	0.996403	19.05	19.05	2.599E-05	2.599E-05
9	8000.	0.620	0.622	0.997744	19.90	19.90	2.855E-05	2.855E-05
10	9000.	0.680	0.683	0.997982	20.88	20.88	3.266E-05	3.266E-05
11	10000.	0.750	0.747	0.998887	21.86	21.86	3.858E-05	3.858E-05
12	10900.	0.820	0.820	0.998203	22.96	22.96	4.702E-05	4.702E-05
13	11700.	0.850	0.846	0.999089	24.08	24.08	5.535E-05	5.535E-05
14	12400.	0.900	0.979	0.999477	25.20	25.20	6.362E-05	6.362E-05
15	13000.	1.065	1.061	0.997852	26.30	26.30	6.712E-05	6.712E-05
16	13400.	1.120	1.116	0.994735	27.06	27.06	7.583E-05	7.583E-05
17	13800.	1.180	1.175	0.989396	27.80	27.80	8.967E-05	8.967E-05
18	14200.	1.225	1.238	0.991485	28.61	28.61	1.161E-04	1.161E-04
19	14600.	1.330	1.339	0.992011	29.90	29.90	1.404E-04	1.404E-04
20	14900.	1.430	1.436	0.985602	31.10	31.10	1.485E-04	1.485E-04
21	15200.	1.570	1.542	0.993914	32.41	32.41	1.574E-04	1.574E-04
22	15500.	1.640	1.676	0.991815	33.57	33.57	1.663E-04	1.663E-04
23	15800.	1.715	1.721	0.983036	34.60	34.60	1.903E-04	1.903E-04
24	16100.	1.815	1.821	0.995603	35.82	35.82	2.408E-04	2.408E-04
25	16380.	1.950	1.960	0.993492	37.53	37.53	3.494E-04	3.494E-04
26	16630.	2.140	2.150	0.993528	39.88	39.88	5.058E-04	5.058E-04
27	16800.	2.255	2.332	0.993928	42.18	42.18	6.877E-04	6.877E-04
28	16940.	2.515	2.541	0.994684	44.93	44.93	9.485E-04	9.485E-04

TABLE 34. DATA TABULATION FOR TEST M-23 (CONCL.)

SPECIMEN NO.: 4-23 BASE STRESS 0 TO +20 KSI, PERIODIC OVERLOAD = -6 TO +30 KSI

CCT	SPECIMEN	R = 0.250 IN.	W = 0.000 IN.	AN = 0.01 IN.	TEST FREQ = 6.00 Hz.	
					P MAX	
ENVIRONMENT CONDITION: AMBIENT AIR						
40.	CYCLES	A (MEASURED)	A (REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K
29	17010.	2.660	2.676	0.997957	46.77	1.262E-03
30	17050.	2.770	2.778	0.996840	48.22	1.552E-03
31	17090.	2.690	2.902	0.996394	50.02	1.998E-03
37	17120.	3.010	3.021	0.995740	51.83	2.647E-03
33	17140.	3.120	3.125	0.994022	53.46	3.426E-03
34	17160.	3.250	3.256	0.940157	55.64	5.875E-03
35	17180.	3.430	3.503	0.958807	60.07	9.810E-03
36	17190.	3.585	3.697	0.975031	63.94	1.415E-02
37	17210.	4.040	4.034	0.991930	71.84	2.275E-02

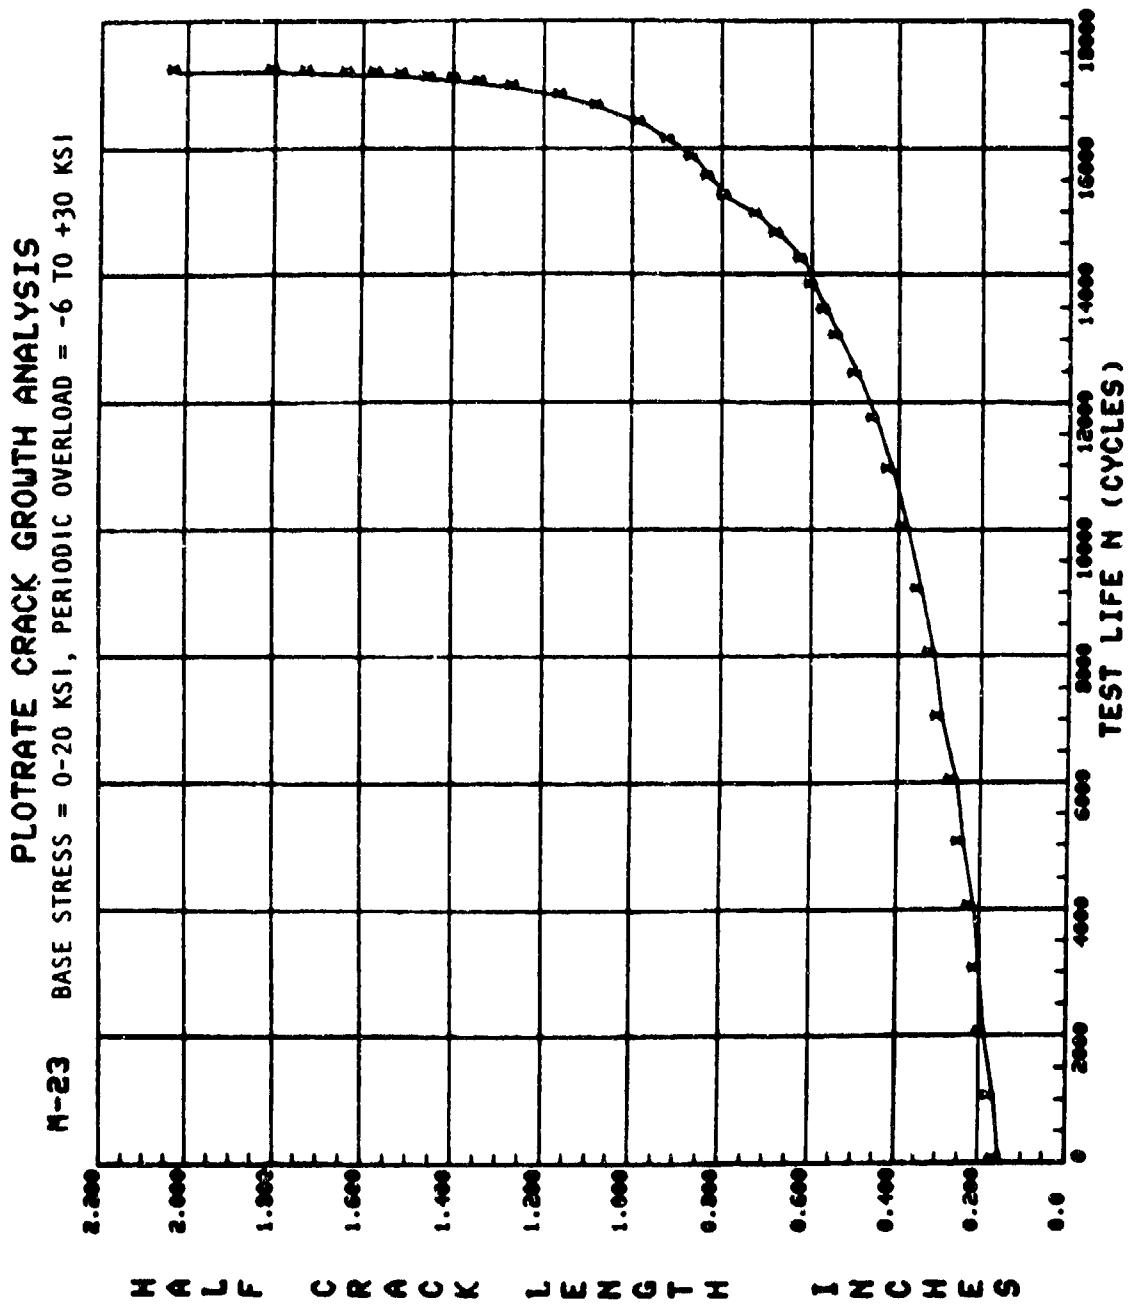


Figure 37. Crack growth curve for test M-23.

TABLE 35. DATA TABULATION FOR TEST M-24

SPECIMEN NO.:	4-24	BASE STRESS -6 TO +20 KSI, PERIODIC OVERLOAD -6 TO +30 KSI		TEST FREQ= 6.0000HZ.
		R= 0.250 IN.	W= 6.000 IN.	
ENVIRONMENT CONDITION: AMBIENT AIR				
No.	CYCLES	ALMFA SLRED1 0.440	ALREGRESSION1 0.440	MULT. CORR. COEFF
1	0.	0.460	0.999624	K-MAX 11.12
2	1850.	0.460	0.999616	14.45 6.67E-06
3	3000.	0.530	0.997414	15.12 1.59E-05
4	4154.	0.580	0.997558	15.63 2.40E-05
5	4943.	0.635	0.998523	16.72 3.19E-05
6	5522.	0.650	0.998871	13.47 3.86E-05
7	6043.	0.735	0.997965	16.44 4.38E-05
8	6583.	0.785	0.994700	15.00 5.062E-05
9	7000.	0.825	0.998448	15.49 6.130E-05
10	7354.	0.890	0.997528	16.00 7.231E-05
11	7611.	0.945	0.997927	20.81 7.98E-05
12	7906.	0.995	0.998625	21.36 8.424E-05
13	8212.	1.045	0.998227	22.00 9.070E-05
14	8590.	1.115	0.996625	17.41 9.558E-05
15	8823.	1.170	0.996311	18.04 1.110E-04
16	9104.	1.235	0.993809	18.49 2.404 1.319E-04
17	9187.	1.280	0.996286	19.19 2.404 1.763E-04
18	9325.	1.330	0.991863	19.40 2.522 2.049E-04
19	9416.	1.385	0.995091	19.90 2.587 2.172E-04
20	9499.	1.430	0.996036	20.28 26.37 2.616E-04
21	9657.	1.490	0.990549	20.61 26.79 2.507E-04
22	9727.	1.545	0.993992	21.25 27.62 3.054E-04
23	9900.	1.650	0.987748	21.52 27.98 3.418E-04
24	10010.	1.785	0.989172	22.71 29.52 4.227E-04
25	10082.	1.890	0.990166	23.61 30.70 4.431E-04
26	10235.	1.995	0.991515	24.18 31.44 4.412E-04
27	10363.	2.095	0.990490	26.10 32.93 4.495E-04
28	10514.	2.205	0.993498	27.21 35.37 5.619E-04

TABLE 35. DATA TABULATION FOR TEST M-24 (CONCL)

SPECIMEN NO.: 4-24		BASE STRESS -6 TO +20 KSI, PERIODIC OVERLOAD -6 TO +30 KSI		TEST FREQ= 6.00 Hz.
CCT	SPECIMEN	R = 0.250 IN.	W = 6.000 IN.	
P MIN	P MAX	ENVIRONMENT CONDITION: AMBIENT AIR		
40.	CYCLES	A(MEASLPFD)	A(REGRESSION)	MULT. CORR. COEFF
29	10619.	2.320	2.330	0.995920
30	10678.	2.425	2.431	0.999758
31	10733.	2.535	2.534	0.998225
32	10785.	2.650	2.651	0.997174
33	10830.	2.760	2.770	0.995115
34	10862.	2.885	2.891	0.997622
35	10886.	2.950	2.999	0.995688
36	10905.	3.110	3.111	0.991907
37	10922.	3.215	3.242	0.993138
38	10936.	3.375	3.392	0.995767
39	10945.	3.514	3.520	0.999822
40	10950.	3.615	3.615	0.999878
				41.50
				53.95
				1.013E-02
				DA/DN
				36.54
				7.296E-04
				37.68
				8.967E-04
				1.094E-03
				38.85
				40.24
				1.354E-03
				41.78
				1.756E-03
				43.21
				2.218E-03
				44.62
				2.908E-03
				46.14
				3.817E-03
				48.00
				5.138E-03
				50.26
				6.807E-03
				52.34
				8.859E-03

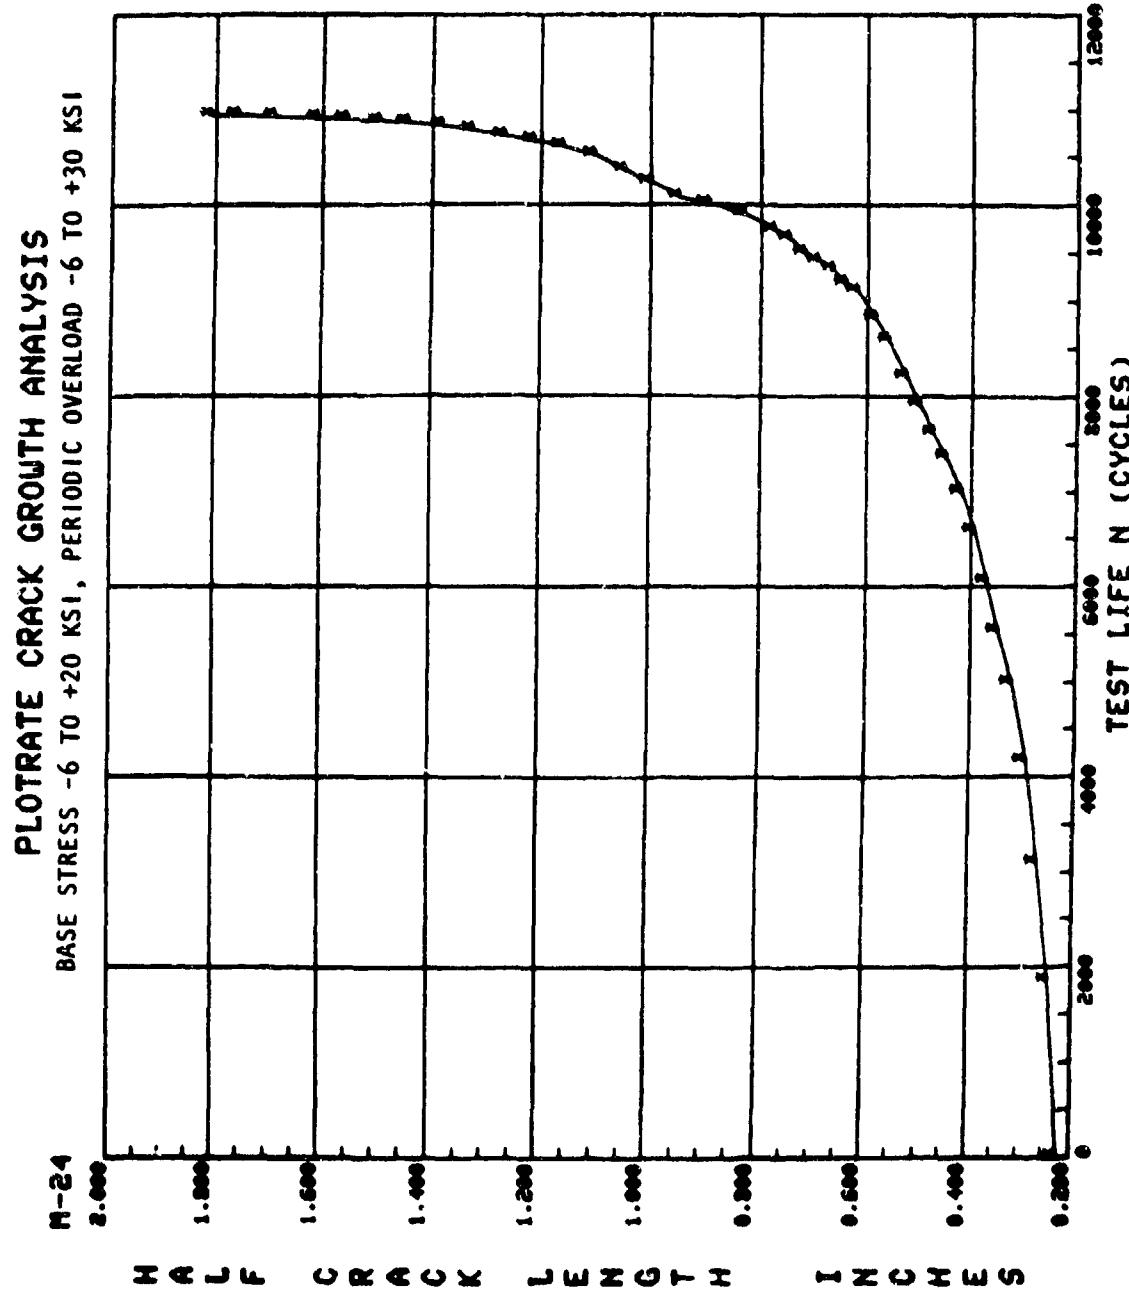


Figure 38. Crack growth curve for test M-24.

TABLE 36. DATA TABULATION FOR TEST M-25

TEST SPHERICAL R= 0.250 IN. BASE STRESS = -6 TO +20 KSI, PERIODIC OVERLOAD -6 TO +40 KSI									
NOD.	CYCLES	ENVIRONMENT CONDITION: AMBIENT AIR		MULT. COEFF	K-YAX	DELTA K	DA/DIN		
		AMBIASREDI	AIREGRESSION				TEST FREQU = 6.0(H) 42.	TEST FREQU = 6.0(H) 42.	TEST FREQU = 6.0(H) 42.
1	0	0.303	0.301	0.965102	13.78	17.91	1.406E-05	1.638E-05	1.958E-05
2	1250	0.327	0.338	0.983122	14.60	18.98			
3	2502	0.460	0.387	0.986153	15.64	20.33			
4	3750	0.428	0.435	0.988950	16.59	21.57	1.938E-05	2.077E-05	
5	5002	0.455	0.447	0.991583	17.56	22.82			
6	6250	0.520	0.517	0.990642	18.45	23.99	1.941E-05		
7	7505	0.585	0.592	0.991796	19.40	25.22	1.851F-05		
8	8755	0.651	0.633	0.987733	20.04	26.11		1.726E-05	
9	10006	0.675	0.676	0.986969	20.76	26.99	1.651E-05		
10	11260	0.700	0.709	0.984932	21.29	27.67	1.754E-05		
11	12510	0.755	0.747	0.997959	21.86	28.42	1.968E-05		
12	13760	0.755	0.814	0.992463	22.71	29.53	2.267E-05		
13	15320	0.885	0.881	0.990136	23.83	30.98	2.964E-05		
14	16260	0.950	0.916	0.991912	24.61	32.00	3.520E-05		
15	17000	0.965	0.901	0.992907	25.37	32.98	3.935E-05		
16	18120	1.050	1.073	0.965007	26.47	34.41	6.140E-05		
17	18760	1.155	1.147	0.981769	27.44	35.68	7.831F-05		
18	19600	1.235	1.309	0.968793	29.52	38.38	8.722E-05		
19	20200	1.475	1.433	0.970206	31.07	40.40	9.126E-05		
20	20800	1.600	1.560	0.975803	32.64	42.43	9.340F-05		
21	21700	1.700	1.747	0.985782	34.92	45.39	6.652E-05		
22	22400	1.825	1.825	0.992774	35.85	46.60	7.352E-05		

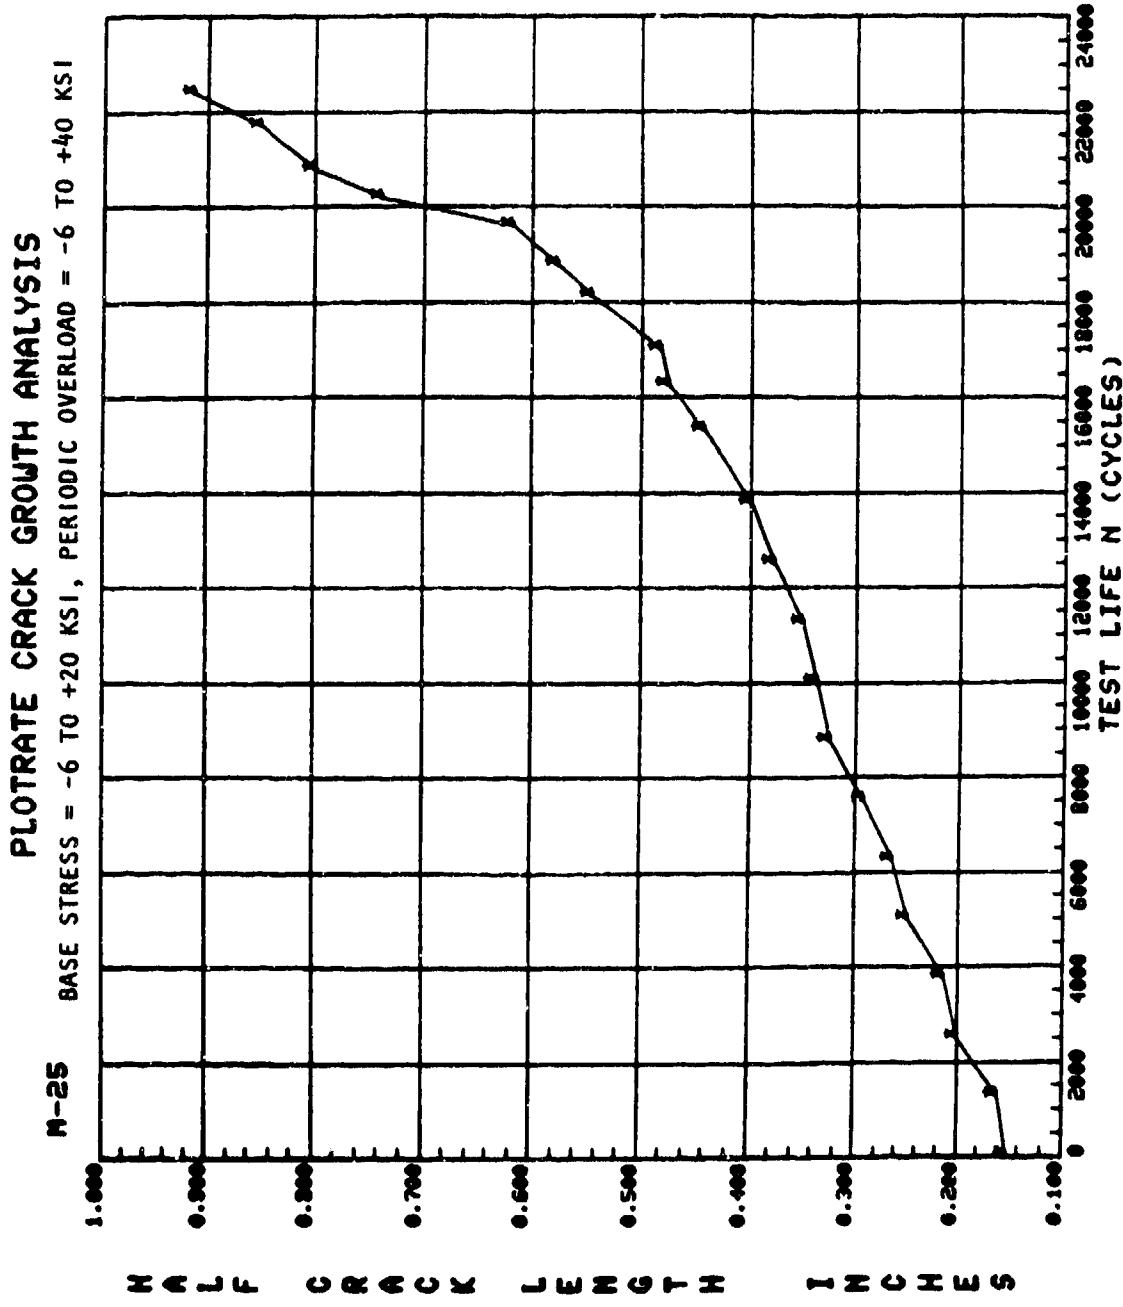


Figure 39. Crack growth curve for test M-25.

TABLE 37. DATA TABULATION FOR TEST M-26

SPECIMEN NO.:	N-26	BASE STRESS = -2.4 TO 8 KSI, SINGLE OVERLOAD = +8 TO -16 KSI	W = 6.000 IN.	A _N = 0.0 J	IN.	TEST FREQ = 6.000 Hz.
CCT	SPECIMEN	R = 0.250 IN.	P _{MAX}			
PIN#	ENVIRONMENT CONDITION:	AMBIENT AIR		MULT.	CORR. COEFF	K-MAX
-	NO.	CYCLES	(MEASUREMENT)	(REGRESSION)		DA/DN
1	0.	0.	0.303	0.302	0.999987	5.52
2	20015.	0.327	0.378	0.999955	5.76	5.487E-07
3	53000.	0.385	0.383	0.999266	6.22	7.284E-07
4	80000.	0.445	0.444	0.997847	6.70	1.015E-06
5	100000.	0.455	0.502	0.997924	7.13	1.353E-06
6	115000.	0.550	0.553	0.999156	7.49	1.669E-06
7	127000.	0.605	0.601	0.998483	7.82	1.944E-06
8	137000.	0.650	0.648	0.999017	8.13	2.117E-06
9	145000.	0.685	0.686	0.998886	8.37	2.313E-06
10	155000.	0.730	0.732	0.993547	8.66	2.424E-06
11	161000.	0.770	0.766	0.995967	8.86	2.913E-06
12	169000.	0.810	0.820	0.996510	9.18	3.206E-06
13	177000.	0.855	0.886	0.995131	9.56	3.774E-06
14	181000.	0.920	0.971	0.964578	9.76	4.151E-06
15	185000.	0.960	0.959	0.996428	9.97	4.335E-06
16	189000.	0.990	0.992	0.99905	10.15	4.651E-06
17	193000.	1.030	1.030	0.998283	10.36	5.209E-06
18	197000.	1.075	1.072	0.999317	10.58	5.706E-06
19	200513.	1.110	1.115	0.999429	10.81	6.251E-06
20	204513.	1.170	1.170	0.998202	11.10	6.546E-06
21	208500.	1.225	1.223	0.998302	11.37	6.954E-06
22	212500.	1.285	1.279	0.997324	11.66	7.408E-06
23	218500.	1.360	1.369	0.998386	12.11	8.251E-06
24	222500.	1.435	1.435	0.998854	12.44	9.358E-06
25	225300.	1.495	1.499	0.999416	12.70	1.016E-05
26	229750.	1.580	1.586	0.999507	13.18	1.175E-05
27	233750.	1.685	1.682	0.999597	13.65	1.332E-05
28	237460.	1.785	1.785	0.999817	14.15	1.513E-05

TABLE 37. DATA TABULATION FOR TEST M-26 (CONT)

SPECIMEN NO.:	M-26	BASE STRESS = -2.4 TO 8 KSI, SINGLE OVERLOAD = +3 TO -16 KSI					
CCT	SPECIMEN	B = 0.250 IN.	W = 6.000 IN.	A = 0.0 IN.	TEST FREQU = 6.00 Hz.		
PIN#		MAX=					
ENVIRONMENT CONDITION: AMBIENT AIR							
NO.	CYCLES	A1(MEASURED)	A1(REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K	DATA N
-29	240860.	1.890	1.894	0.999823	14.69	19.09	1.692E-05
30	243560.	1.950	1.967	0.999909	15.14	19.69	1.857E-05
31	246060.	2.025	2.083	0.999629	15.62	20.30	2.060E-05
32	248660.	2.150	2.195	0.999663	16.18	21.03	2.250E-05
33	250870.	2.295	2.296	0.999483	16.69	21.70	2.500E-05
34	252770.	2.400	2.395	0.999535	17.20	22.36	2.728E-05
35	254770.	2.500	2.509	0.999519	17.80	23.14	2.958E-05
36	256170.	2.600	2.593	0.999466	18.26	23.73	3.156E-05
37	257880.	2.705	2.703	0.998782	18.86	24.52	3.514E-05
38	259380.	2.805	2.812	0.998754	19.48	25.33	3.840E-05
39	260630.	2.905	2.908	0.999436	20.55	26.06	4.213E-05
40	261680.	3.010	3.009	0.994017	20.65	26.85	4.102E-05
-41	262740.	3.055	3.107	0.973869	21.27	27.65	4.562E-05
42	263790.	3.210	3.213	0.951206	21.90	28.47	5.177E-05
43	265790.	3.325	3.439	0.944438	23.55	30.61	7.852E-05
44	265490.	3.420	3.382	0.948956	23.13	30.61	7.933E-05
45	266120.	3.525	3.483	0.952970	23.87	31.04	9.259E-05
46	266710.	3.625	3.610	0.954452	24.86	32.32	1.084E-04
-47	267250.	3.730	3.734	0.999164	25.90	33.67	1.123E-04
48	267710.	3.840	3.829	0.999563	26.83	34.87	1.256E-04
49	268160.	3.955	3.961	0.999564	27.99	36.39	1.529E-04
50	268460.	4.055	4.054	0.998818	28.94	37.62	1.780E-04
51	268760.	4.160	4.164	0.995359	30.14	39.19	2.081E-04
52	269000.	4.260	4.266	0.999232	31.36	41.77	2.435E-04
53	269200.	4.370	4.366	0.998854	32.65	42.44	2.881E-04
54	269360.	4.455	4.461	0.998675	33.97	44.16	3.363E-04
55	269520.	4.565	4.574	0.996410	35.72	46.43	4.283E-04
56	269610.	4.650	4.647	0.994646	36.94	48.02	5.364E-04

TABLE 37. DATA TABULATION FOR TEST M-26 (CONCL)

SPECIMEN NO.: M-26 BASE STRESS = -2.4 TO 8 KSI. SINGLE OVERLOAD = +8 TO -16 KSI					
CCT	SPECIMEN	R= 0.250 IN.	W= 6.000 IN.	ΔA= 0.01 IN.	TEST FREQ= 6.00 Hz.
P MIN=	P MAX=				
ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLES	A(MEASURFD)	A(REFGRESSCN)	WULT. CORR. COEFF	K-MAX
57	269713.	4.745	4.764	0.995246	39.12
58	269790.	4.860	4.873	0.996680	41.64
59	269840.	4.970	4.970	0.999672	43.78
					50.86
					53.87
					56.91
					6.819E-04
					8.799E-04
					1.149E-03
					DA/DN

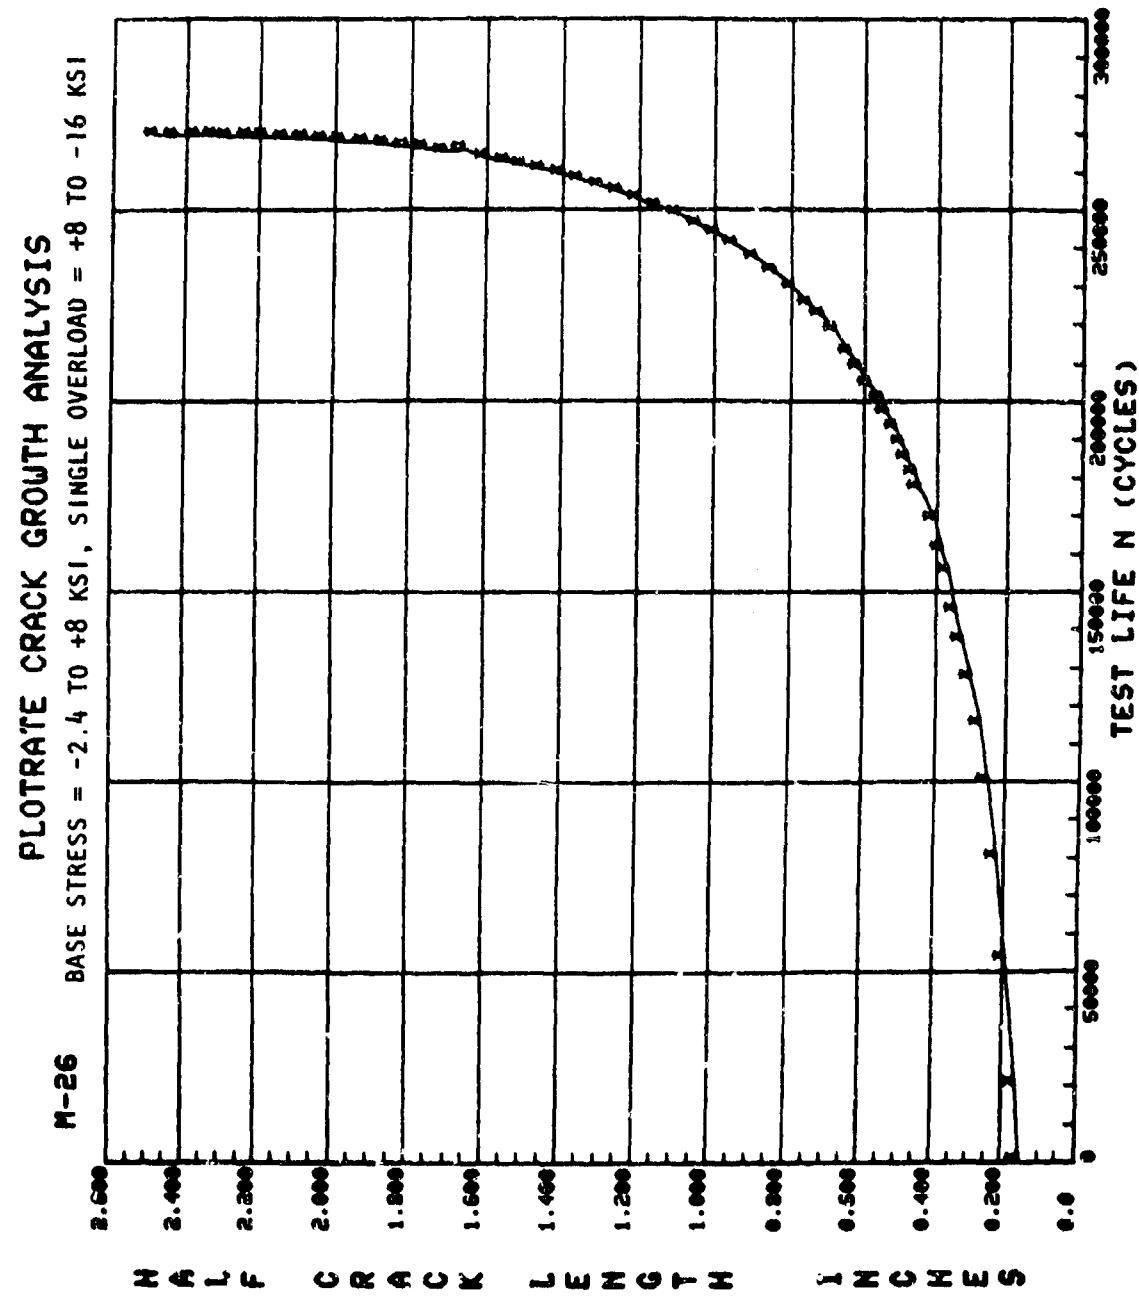


Figure 40. Crack growth curve for test M-26.

TABLE 38. DATA TABULATION FOR TEST M-27 (CONCL)

SPECIMEN '10.: 4-27 BASE STRESS = -2.4 TO +8 KSI, PERIODIC OVERLOAD = +8 TO -16 KSI

CCT P4THz	SPECIMEN #	R= 0.250 IN.	W= 6.000 IN.	AN= 0.0	IN.	TEST FREQ= 6.00 Hz.	
						D MAX	
ENVIRONMENT CONDITION: AMBIENT AIR							
NO.	CYCLES	AS MEASURED	A(REGRESSION)	MULT.	CURR.	COEFF	K-MAX
29	185029.	2.500	2.520	0.998671	17.86		23.22
30	187008.	2.720	2.714	0.998825	16.92		24.60
31	189000.	2.975	2.951	0.996900	20.30		26.39
32	191000.	3.220	3.257	0.989541	22.26		28.93
33	192026.	3.415	3.449	0.993349	23.62		30.71
34	193002.	3.655	3.682	0.998936	25.46		33.09
35	194016.	4.020	4.029	0.999662	28.68		37.28
							2.023E-04

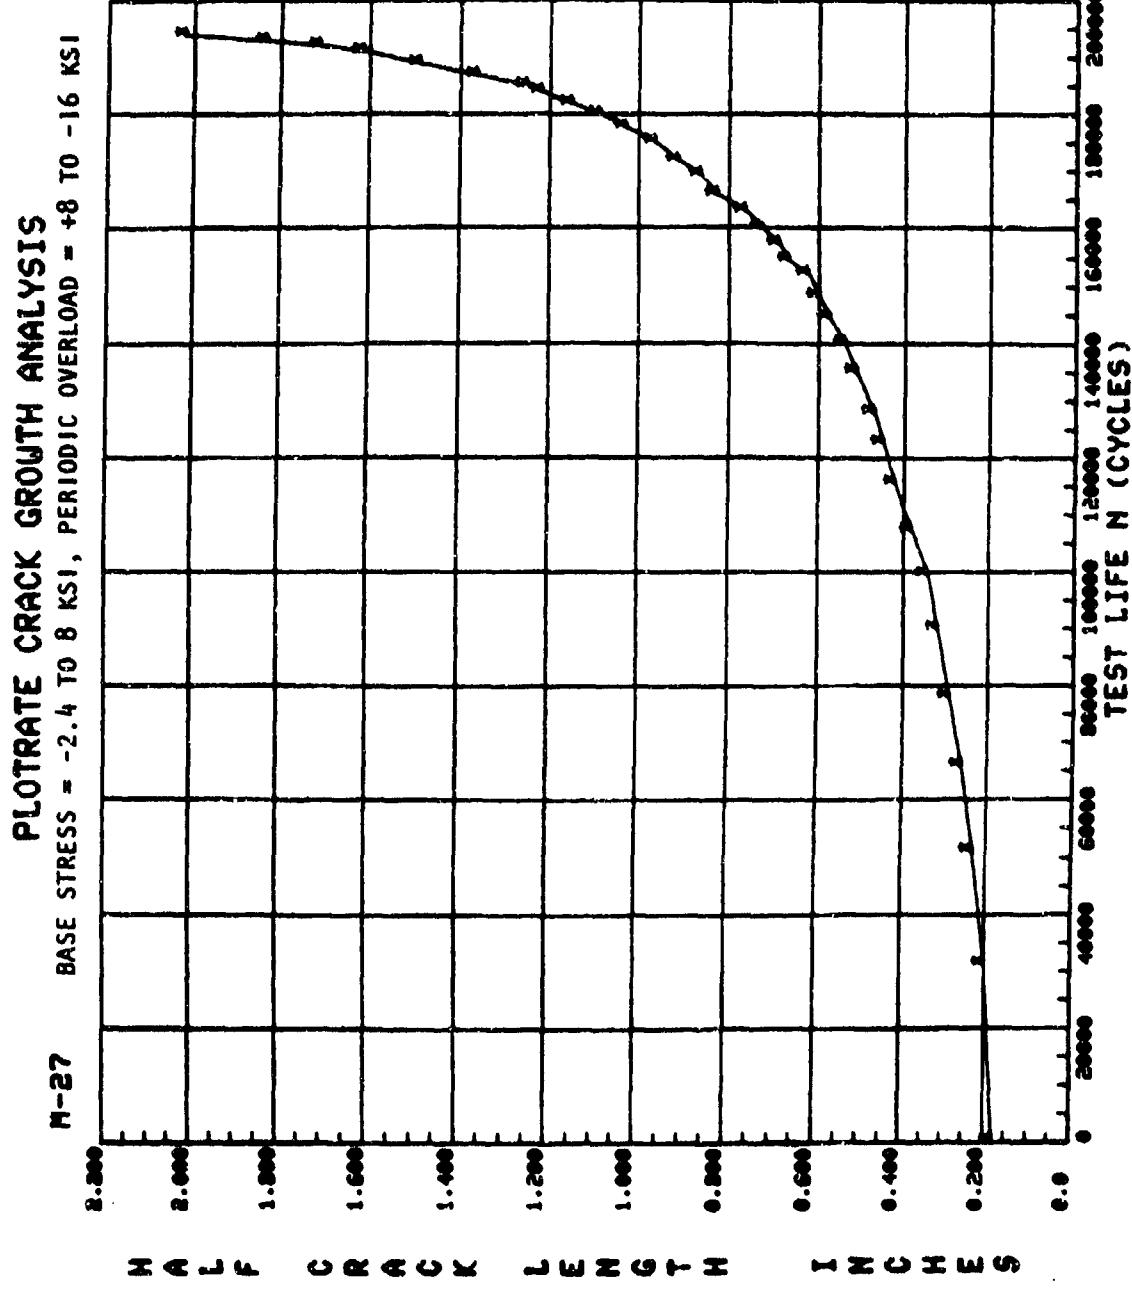


Figure 41. Crack growth curve for test M-27.

TABLE 39. DATA TABULATION FOR TEST M-28

SPECIMEN #0.: 4-2A BASE STRESS -6 TO +20 KSI. PERIODIC OVERLOAD +30 TO -15 KSI

CCT SPECIMEN $\eta = 0.250$ IN. $b = 6.000$ IN. $\Delta t = 0.0$ IN.

PWTR = PMAX = TEST FREQ= 6.00 Hz

ENVIRONMENT CONDITION: AMBIENT AIR

NU.	CYCLES	AIMEASLFFDI	AIRPRESSURE(PSI)	MULT. CIRR. COEFF	K-MAX	DELTA K	DA/DN
1	0.	0.465	0.465	0.999841	11.44	20.01	1.19E-05
2	1.300	0.500	0.495	0.994162	11.81	20.66	1.542E-05
3	2.300	0.520	0.533	0.992550	12.26	21.46	1.89E-05
4	2.700	0.545	0.549	0.993813	12.45	21.78	2.05E-05
5	3.200	0.580	0.570	0.992744	12.69	22.20	2.28E-05
6	4.000	0.605	0.610	0.987842	13.13	22.99	2.82E-05
7	4.500	0.635	0.619	0.966965	13.45	23.54	4.23E-05
8	4.850	0.660	0.608	0.988639	13.76	24.08	5.615E-05
9	5.005	0.680	0.685	0.986667	13.94	24.40	5.826E-05
10	5.250	0.730	0.719	0.986849	14.29	25.01	6.324E-05
11	5.500	0.755	0.757	0.996515	14.68	25.69	6.467E-05
12	5.750	0.785	0.787	0.994514	14.97	26.21	5.905E-05
13	6.000	0.815	0.812	0.998639	15.22	26.64	5.357E-05
14	6.250	0.835	0.815	0.984021	15.45	27.03	6.143E-05
15	6.500	0.864	0.864	0.991806	15.73	27.52	7.000E-05
16	6.750	0.850	0.898	0.995678	16.05	28.08	8.786E-05
17	7.000	0.955	0.952	0.984647	16.55	28.96	9.821E-05
18	7.250	1.000	1.009	0.986134	17.07	29.68	1.039E-04
19	7.500	1.065	1.067	0.992887	17.60	30.80	1.041E-04
20	7.750	1.110	1.116	0.987862	18.03	31.55	1.055E-04
21	8.000	1.160	1.165	0.978795	16.46	32.30	1.070E-04
22	8.200	1.195	1.202	0.997300	18.77	32.85	1.372E-04
23	8.300	1.230	1.232	0.995331	19.93	33.30	1.394E-04
24	8.400	1.265	1.261	0.995359	19.28	33.73	1.515E-04
25	8.500	1.300	1.294	0.996807	19.55	34.22	1.692E-04
26	8.740	1.370	1.377	0.998119	20.25	35.44	1.925E-04
27	8.840	1.400	1.396	0.997678	20.61	35.71	2.068E-04
28	8.960	1.470	1.467	0.998823	20.99	36.73	2.675E-04

TABLE 39. DATA TABULATION FOR TEST M-28 (CONCL)

SPECIMEN NO.: M-28 BASE STRESS -6 TO +20 KSI, PERIODIC OVERLOAD +30 TO -15 KSI					
RCT	SPECIMEN	A= 0.250 IN.	W= 6.000 IN.	AA= 0.0 IN.	
PM14= PMAX=					TEST FREQ= 6.00 Hz.
ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLES	ALMEASUREMENT	ALIREGRESSION	MULT. CURR. COEFF	K-MAX
29	9188.	1.525	1.533	0.999090	21.53
30	9234.	1.625	1.620	0.999493	22.24
31	9357.	1.710	1.710	0.999516	22.98
32	9472.	1.805	1.807	0.999032	23.77
33	9571.	1.900	1.901	0.999848	24.53
34	9670.	2.005	2.006	0.999457	25.41
35	9753.	2.115	2.113	0.999080	26.28
36	9829.	2.220	2.220	0.999044	27.24
37	9983.	2.320	2.323	0.999453	28.05
38	9935.	2.430	2.430	0.999983	28.98
39	9974.	2.525	2.525	0.999986	29.81
					DELTA K DA/DN
					37.68 2.87E-04
					38.92 3.38E-04
					40.22 3.952E-04
					41.59 4.611E-04
					42.93 5.259E-04
					44.46 6.168E-04
					45.98 7.272E-04
					47.67 8.668E-04
					49.09 9.900E-04
					50.71 1.154E-03
					52.17 1.263E-03

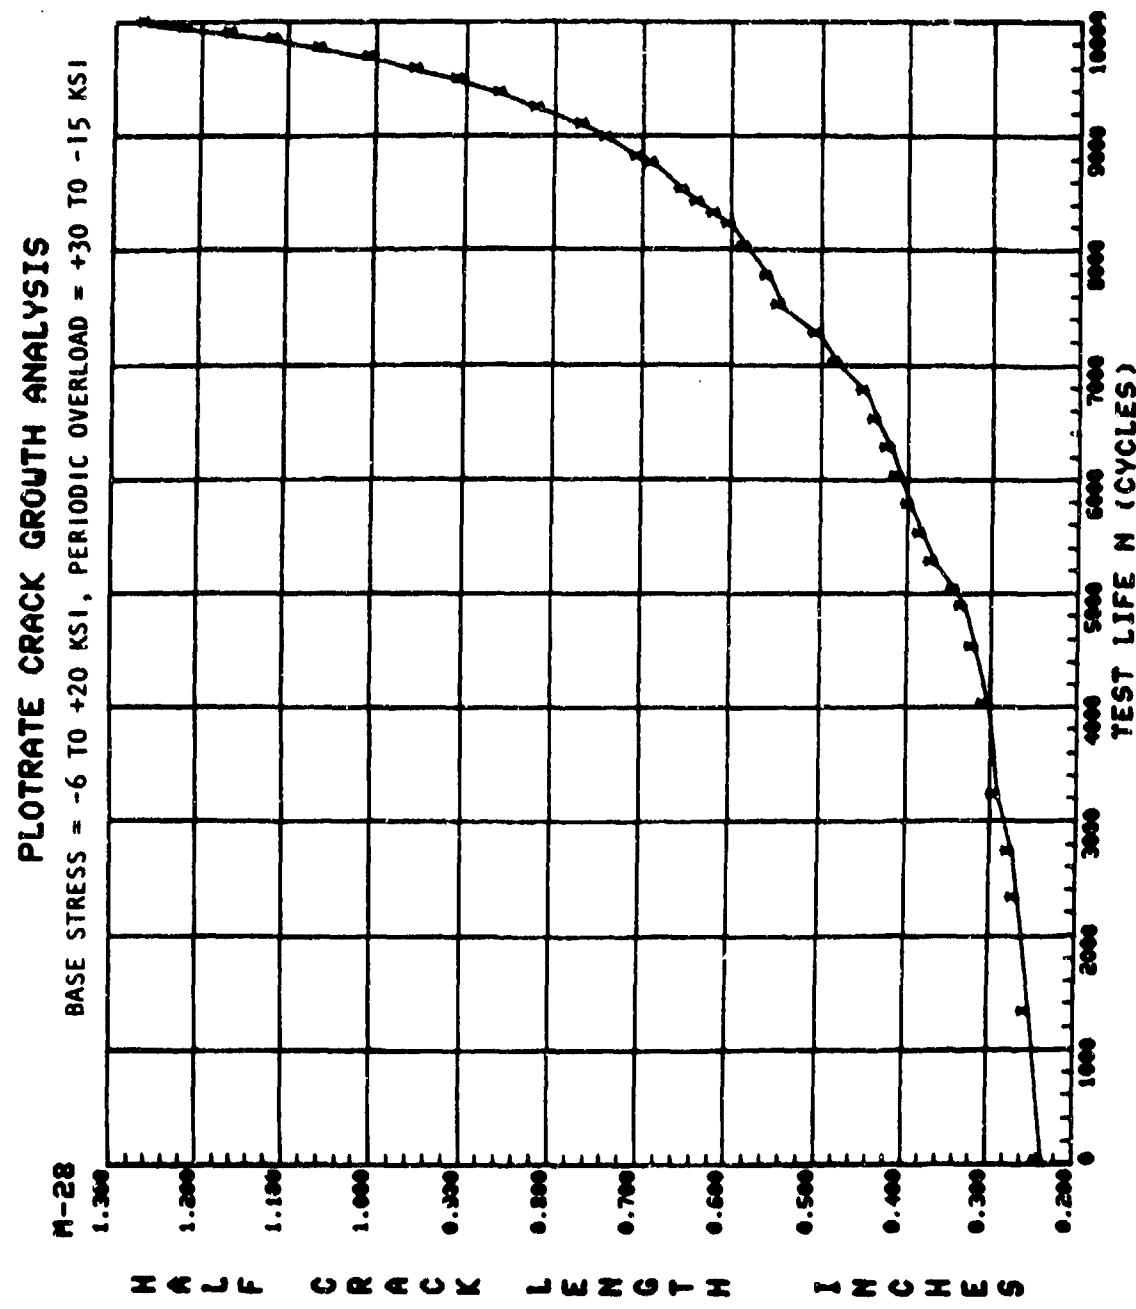


Figure 42. Crack growth curve for test M-28.

TABLE 40. DATA TABULATION FOR TEST M-29

SPECIMEN NO.: 4-29 BASE STRESS = -6 TO +20 KSI. PERIODIC OVERLOAD = +40 TO -15 KSI

CCT SPECIMEN B= 0.250 IN. W= 6.000 IN. A= 0.01 IN.

P_{MAX}= TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A(MEAS)REDI	AIRPRESSURE(CN)	MULT. CORR. COEFF	X-MAX	DA/DYK
1	0.	0.320	0.120	0.999960	14.21	2.215E-05
2	1000.	0.365	0.363	0.999861	15.14	2.172E-05
3	2501.	0.420	0.429	0.999926	16.47	2.141
4	3500.	0.475	0.477	0.999870	17.37	2.304E-05
5	5001.	0.550	0.543	0.995226	18.55	2.400E-05
6	6000.	0.605	0.610	0.984448	19.70	2.861E-05
7	7510.	0.665	0.710	0.984965	21.30	2.957E-05
8	10000.	0.925	1.889	0.984234	23.94	3.278E-05
9	11300.	0.955	0.960	0.932655	25.35	3.236E-05
10	11900.	1.010	1.056	0.881468	26.24	3.375E-05
11	12500.	1.035	1.121	0.924874	27.10	3.411
12	12683.	1.205	1.155	0.932257	27.55	3.523
13	12900.	1.250	1.219	0.898432	28.37	3.112
14	13150.	1.303	1.316	0.949495	29.61	3.095
15	13301.	1.335	1.327	0.993056	29.75	3.067
16	13450.	1.340	1.351	0.993450	30.04	3.030
17	13600.	1.380	1.367	0.958643	31.25	3.003E-05
18	14000.	1.425	1.419	0.968140	30.89	6.967E-05
19	14600.	1.450	1.525	0.967826	32.21	4.016
20	14700.	1.570	1.543	0.965492	32.43	7.488E-05
21	14900.	1.555	1.597	0.943554	33.09	41.87
					42.16	1.056E-04
					43.01	1.591E-04

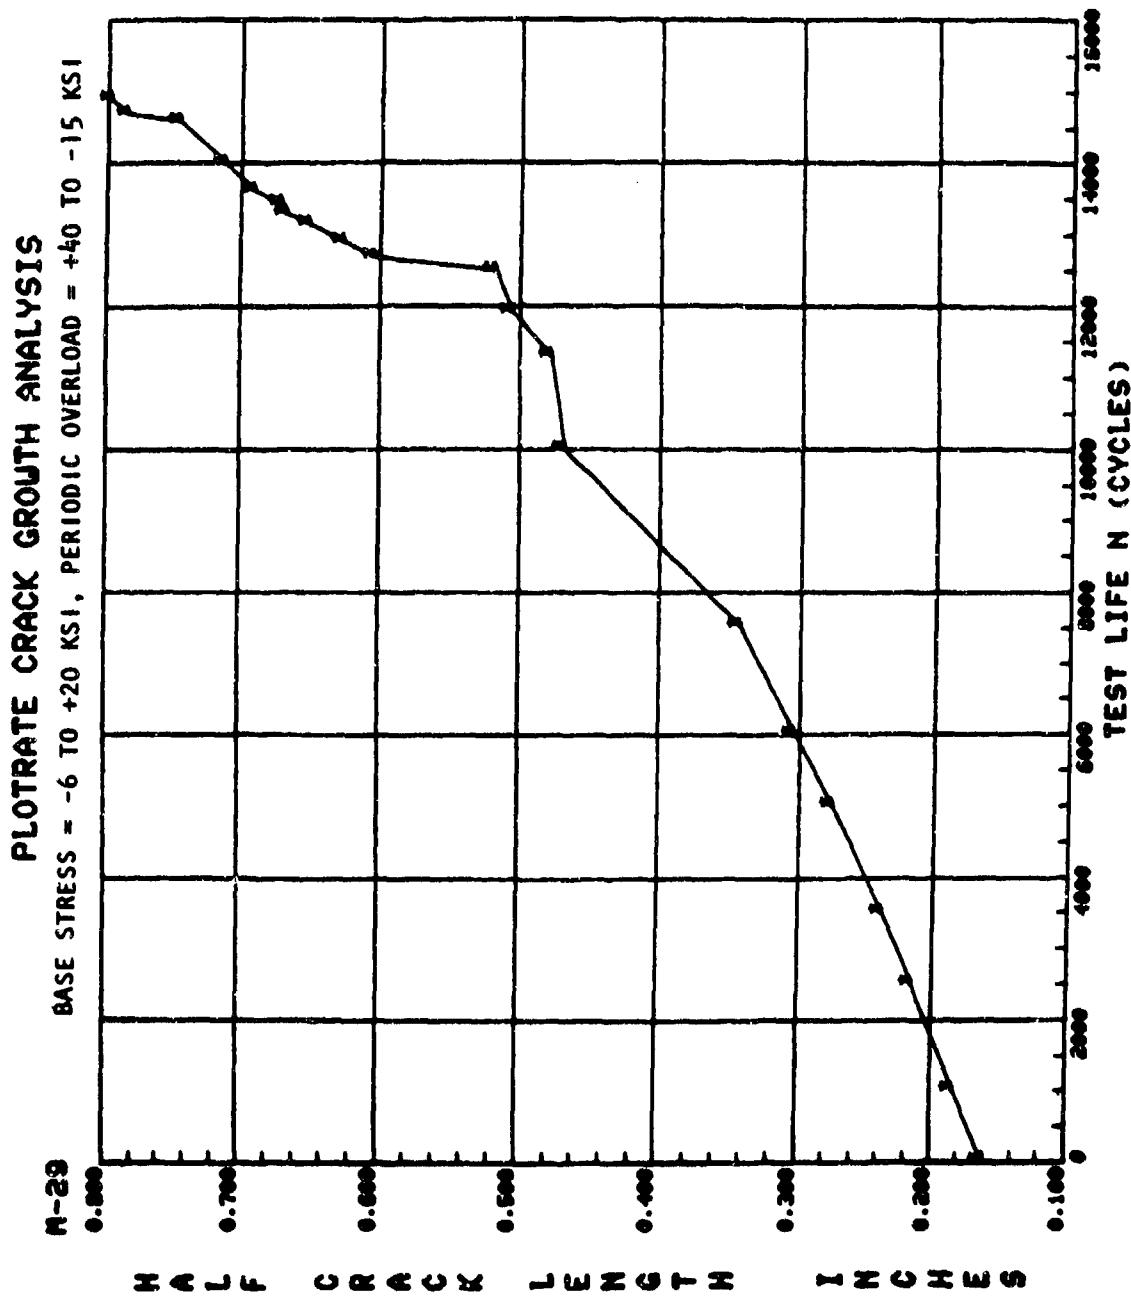


Figure 43. Crack growth curve for test M-29.

TABLE 41. DATA TABULATION FOR TEST M-30

SPECIMEN NO.: 4-30 BASE STRESS = -6 TO +20 KSI. PERIODIC OVERLOAD = -15 TO +40 KSI

CCT SPECIMEN B= 0.250 IN. W= 6,000 IN. A_h= 0.0 IN.

P_{MAX}= TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A(MEASRED)	A(REGRESSION)	MULT. CORR. COEFF.	K-MAX	DELTA K	DA/DN
1	0.	0.290	0.290	0.999967	13.52	17.57	1.800E-05
2	1000.	0.330	0.336	0.995936	14.55	18.91	2.247E-05
3	2200.	0.385	0.387	0.996536	15.64	20.33	2.192E-05
4	3200.	0.440	0.432	0.996694	16.53	21.49	2.1C9E-05
5	4550.	0.480	0.487	0.995143	17.57	22.84	2.071E-05
6	5480.	0.530	0.524	0.995018	18.24	23.71	1.992E-05
7	7000.	0.575	0.581	0.995907	19.22	24.99	1.981E-05
8	7890.	0.625	0.617	0.994171	19.81	25.76	2.114E-05
9	9180.	0.665	0.671	0.995863	20.68	26.89	2.168E-05
10	10320.	0.720	0.723	0.994282	21.50	27.95	2.451E-05
11	10910.	0.760	0.749	0.995459	21.90	28.47	2.729E-05
12	12130.	0.810	0.824	0.993946	23.01	29.92	3.047E-05
13	12780.	0.865	0.863	0.993194	23.5H	30.66	3.319E-05
14	13490.	0.925	0.910	0.985774	24.24	31.51	3.909E-05
15	14550.	0.980	1.000	0.983990	25.49	33.14	5.196E-05
16	15060.	1.046	1.053	0.985294	26.20	34.06	5.478E-05
17	15340.	1.100	1.086	0.979459	26.64	34.64	5.302E-05
18	15810.	1.160	1.131	0.940565	27.23	35.40	6.971E-05
19	16460.	1.220	1.211	0.967860	28.27	36.75	9.313E-05
20	17090.	1.280	1.350	0.974819	30.04	39.05	1.195E-04
21	17515.	1.355	1.468	0.972754	31.5n	40.95	1.298E-04
22	18000.	1.660	1.621	0.981440	33.38	43.40	1.460E-04
23	18500.	1.770	1.794	0.987316	35.59	46.15	1.524E-04
24	19000.	1.905	1.926	0.990662	37.1:	48.24	1.659E-04
25	19241.	1.995	2.007	0.998014	38.13	49.53	2.300E-04
26	19409.	2.085	2.081	0.999809	39.12	50.73	2.569E-04
27	19700.	2.245	2.248	0.999792	41.11	53.45	3.201E-04
28	19914.	2.395	2.395	0.999720	43.00	55.90	3.6C3E-04

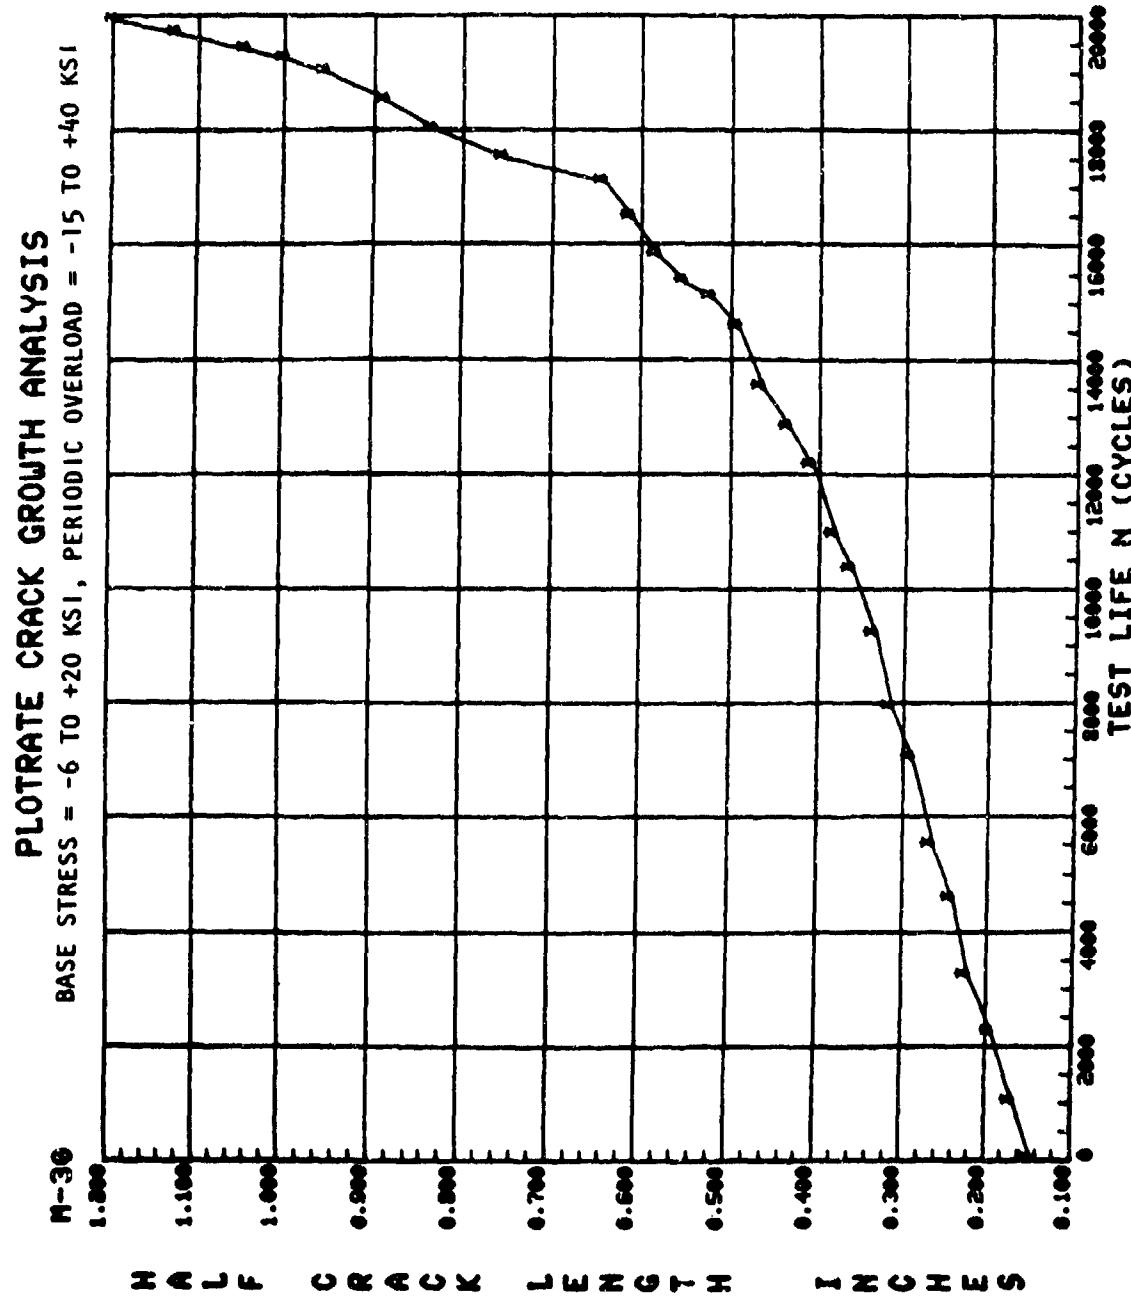


Figure 44. Crack growth curve for test M-30.

TABLE 42. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP III -
MULTIPLE OVERLOAD/UNDERLOAD






Test No.	Loading Profile	STEP I		STEP II		N_I Cycle	N_{II} Cycle	Comments
		Max Ksi	Min Ksi	Max Ksi	Min Ksi			
M-31		8	0	20	0	10,000	To failure	Underload effect, low stress level
M-32		20	0	40	0	5,000	To failure	Underload effect, high stress level
M-33		8	2.4	20	2.4	10,000	To failure	Underload effect, low stress level
M-34		20	6	40	12	5,000	To failure	Underload effect, high stress level
M-35		8	0	20	14	10,000	To failure	Underload effect, two-level stress ratios, low stress
M-36		20	0	40	28	5,000	To failure	Underload effect, high stress level
M-37		8	-2.4	20	0	10,000	To failure	Comp/tension load effect, low stress level
M-38		20	-6	40	0	5,000	To failure	Underload effect, high stress level
M-39		0	-6	20	0	5,000	To failure	Comp - comp-load effect, low stress level
M-40		0	-12	40	0	5,000	To failure	Comp-comp load effect, high stress level

TABLE 42. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP III
MULTIPLE OVERLOAD/UNDERLOAD (CONT)

Test No.	Loading Profile	STEP I		STEP II		N_I Cycle	N_{II} Cycle	Comments
		Max Ksi	Min Ksi	Max Ksi	Min Ksi			
M-41		-5	-6	20	10	500	To failure	Comp-comp load effect
M-42		-3	-12	20	10	5,000	To failure	Comp-comp load effect
M-43		30	0	20	0	500	To failure	Multiple load retardation, R = 0
M-44		40	0	20	0	500	To failure	Multiple load retardation, R = 0
M-45		30	9	20	6	3,370	To failure	Multiple load retardation, R = 0.3
M-46		40	12	20	6	500	To failure	Multiple load retardation, R = 0.3
M-47		20	6	20	14	500	To failure	Stress ratio effect
M-48		40	12	40	28	500	To failure	Stress ratio effect
M-49		20	14	20	6	500	To failure	Stress ratio effect
M-50		40	28	40	12	500	To failure	Stress ratio effect
M-51		8	0	20	0	2,500	500	Repeat steps 1 & 2
M-52		20	0	40	0	500	50	Repeat steps 1 & 2
M-53		8	2.4	20	2.4	2,500	500	Repeat steps 1 & 2
M-54		20	6	40	6	500	50	Repeat steps 1 & 2

TABLE 42. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP III -
MULTIPLE OVERLOAD/UNDERLOAD (CONCL)





Test No.	Loading Profile	STEP I		STEP II		N_I Cycle	N_{II} Cycle	Comments
		Max Ksi	Min Ksi	Max Ksi	Min Ksi			
M-55		8	0	20	0	2,500	50	Repeat steps 1 & 2
				0	-6		50	
M-56		20	0	40	0	2,500	50	Repeat steps 1 & 2
				0	-12		50	
M-57		20	0	0	-12	2,500	50	Repeat steps 1 & 2
				40	0		50	
M-58		20	-6	40	-6	2,500	500	Repeat steps 1 & 2
M-59		8	-2.4	30	-2.4	5,000	2,500	Repeat steps 1 & 2
M-60		8	-2.4	8	-16	2,500	2,500	Repeat steps 1 & 2

TABLE 43. DATA TABULATION FOR TEST M-31

SPECIMEN NO.: M-31	CCT SPECIMEN	R = 0.250 IN.	W = 6.000 IN.	A _N = 0.0 IN.	TEST FREQ = 6.00 Hz.	ENVIRONMENT CONDITION: AMBIENT AIR		MULT. CURR. COEFF	K-MAX	DELTA K	DA/DN
						P MIN =	P MAX =				
1	CYCLES	A(MEASLRED)	A(REGRESSION)					0.864219	13.63	13.63	1.59E-05
2	0.	0.295	0.295					0.882522	14.20	14.20	1.251E-05
3	10000.	0.255	0.320					0.919649	14.80	14.80	1.417E-05
4	11000.	0.380	0.347					0.941843	15.44	15.44	1.629E-05
5	12000.	0.380	0.378					0.955811	16.23	16.23	1.867E-05
6	13000.	0.405	0.417					0.995861	16.70	16.70	1.916E-05
7	13900.	0.445	0.441					0.999590	17.59	17.59	2.430E-05
8	14900.	0.450	0.488					0.999673	18.53	18.53	2.831E-05
9	15900.	0.540	1.541					0.998843	19.52	19.52	3.335E-05
10	16900.	0.600	0.599					0.997928	20.54	20.54	4.061E-05
11	17800.	0.660	0.662					0.998640	21.56	21.56	4.868E-05
12	18570.	0.720	0.727					0.998777	22.21	22.21	5.289E-05
13	19010.	0.770	0.770					0.998480	22.88	22.88	5.608E-05
14	19410.	0.820	0.815					0.999568	23.59	23.59	5.990E-05
15	19810.	0.865	0.864					0.999055	24.25	24.25	6.317E-05
16	20210.	0.910	0.911					0.997264	24.92	24.92	7.137E-05
17	20610.	0.960	0.958					0.998598	25.71	25.71	8.204E-05
18	21010.	1.015	1.017					0.998213	26.64	26.64	1.018E-04
19	21710.	1.155	1.149					0.998808	27.47	27.47	1.182E-04
20	22020.	1.220	1.228					0.998519	28.49	28.49	1.370E-04
21	22220.	1.290	1.286					0.998581	29.22	29.22	1.469E-04
22	22400.	1.340	1.339					0.997234	29.89	29.89	1.660E-04
23	22580.	1.400	1.402					0.997082	30.68	30.68	1.867E-04
24	22680.	1.430	1.438					0.998496	31.14	31.14	1.926E-04
25	22780.	1.485	1.477					0.998252	31.61	31.61	2.097E-04
26	22980.	1.570	1.569					0.998360	32.74	32.74	2.382E-04
27	23180.	1.650	1.671					0.998610	33.99	33.99	2.591E-04
28	23330.	1.760	1.747					0.997778	34.92	34.92	2.856E-04

TABLE 43. DATA TABULATION FOR TEST M-31 (CONT'D.)

SPFC ID#	SPCimen	R = 0.250 IN.	W = 6.000 IN.	AR = 0.0	IN.	TEST FREQ = 6.000 Hz.
		P MAX =				
ENVIRONMENT CONDITION: AMBIENT AIR						
NU.	CYCLES	ALIMEASURFN	AIRPRESSCN	MULT.	CORR. CNEFF	K-MAX
29	23400.	1.035	1.835	0.996776	35.99	35.99
30	23630.	1.920	1.935	0.996942	37.21	37.21
31	23740.	2.020	2.016	0.999634	38.21	4.340E-04
32	23860.	2.130	2.128	0.999653	39.60	5.066E-04
33	23960.	2.235	2.237	0.998224	40.98	5.922E-04
34	24040.	2.330	2.334	0.998322	42.21	6.949E-04
35	24095.	2.400	2.411	0.998215	43.21	7.557E-04
36	24135.	2.480	2.473	0.997916	44.03	8.065E-04
37	24175.	2.550	2.539	0.995606	44.91	9.142E-04
39	24215.	2.605	2.607	0.986537	45.83	1.127E-03
39	24255.	2.665	2.791	0.996106	47.13	1.251E-03
40	24295.	2.800	2.809	0.987203	48.66	48.66
41	24325.	2.950	2.907	0.985824	50.09	50.09
42	24355.	2.985	3.020	0.980090	51.81	51.81
42	24375.	3.080	3.101	0.974199	53.09	53.09
44	24390.	3.180	3.174	0.974402	54.26	54.26
45	24403.	3.270	3.288	0.95214	56.17	56.17
46	24415.	3.405	3.471	0.997270	58.53	58.53
47	24425.	3.575	3.575	0.999817	61.46	61.46
						9.348E-03

PLATE CRACK GROWTH ANALYSIS

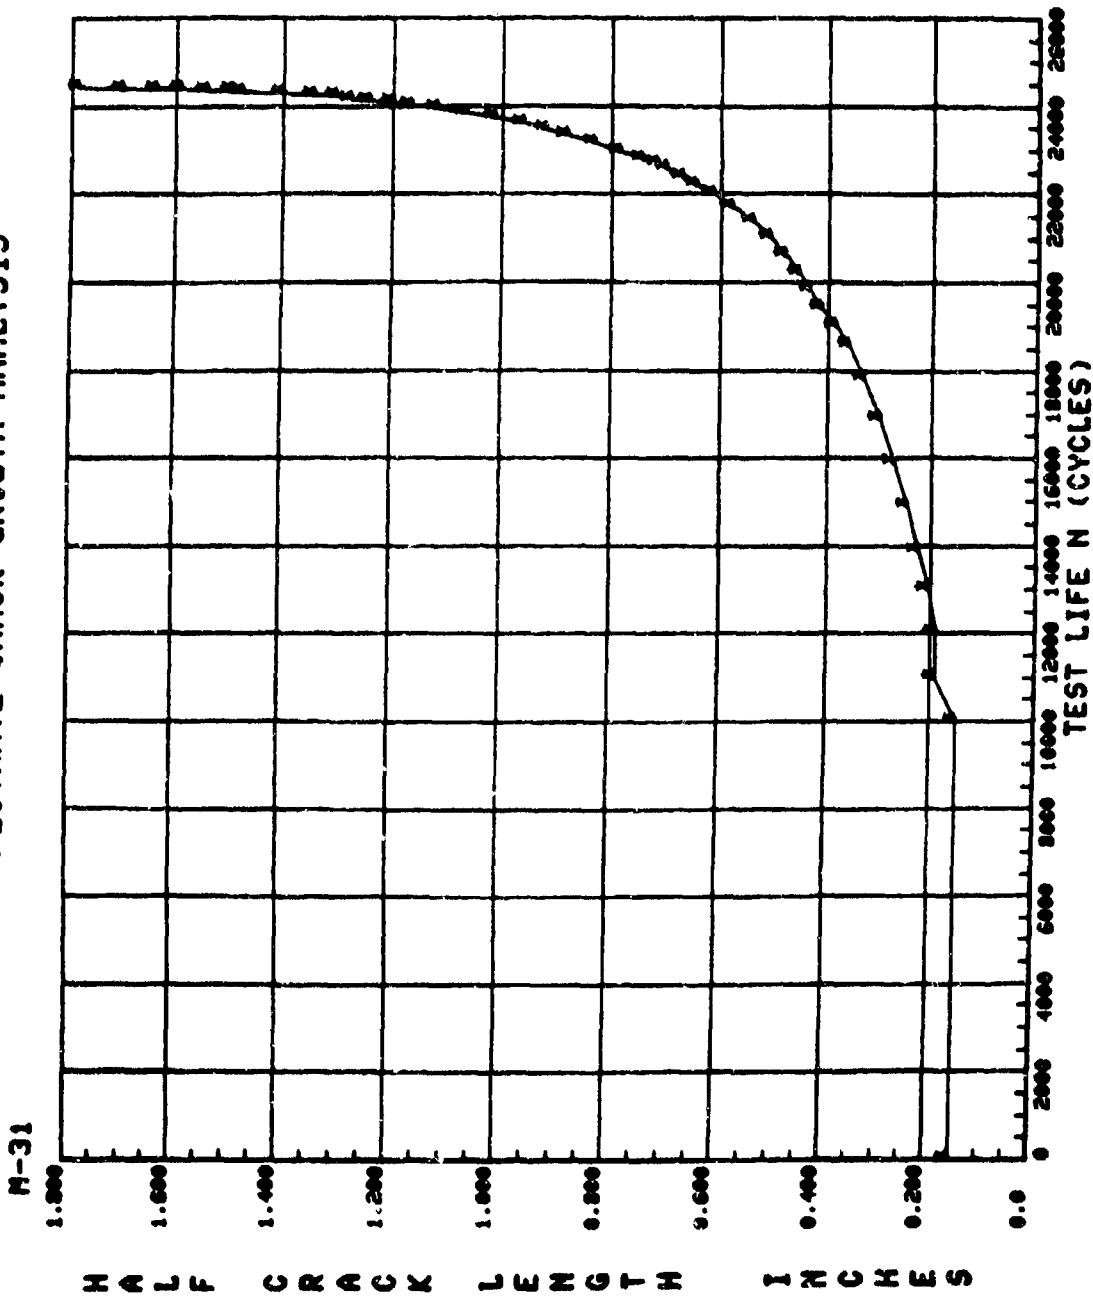


Figure 45. Crack growth curve for test M-31.

TABLE 44. DATA TABULATION FOR TEST M-32

SPECIMEN NO.: 4-32

CCT SPeCIMeNt R= 0.250 IN.
PmIN= Pmax=

ENVIRONMENT CONDITION: AMBIENT AIR

W= 6.000 IN.

TEST FREQ= 6.00 Hz.

NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR.	Coeff	K-MAX	DELTAK	DA/DN
1	9.	0.310	0.310	0.993925	27.95	27.95	1.200E-06	
2	1836.	0.355	0.365	0.977725	30.37	30.37	1.804E-05	
3	2100.	0.380	0.375	0.985007	30.78	30.78	1.854E-05	
4	2600.	0.405	0.395	0.987231	31.59	31.59	1.910E-05	
5	3100.	0.410	0.411	0.986374	32.24	32.24	2.374E-05	
6	4100.	0.460	0.467	0.788436	34.40	34.40	4.959E-05	
7	5000.	0.455	0.611	0.751012	39.41	39.41	1.211E-04	
8	5075.	0.590	0.656	0.699947	40.91	40.91	1.826E-04	
9	5100.	0.685	0.677	0.984620	41.56	41.56	1.106E-03	
10	5125.	0.730	0.725	0.992849	43.05	43.05	1.321E-03	
11	5150.	0.760	0.795	0.992674	45.18	45.18	1.525E-03	
12	5175.	0.875	0.866	0.999105	47.23	47.23	1.734E-03	
13	5200.	0.960	0.952	0.990406	49.67	49.67	2.360E-03	
14	5225.	1.070	1.070	0.959214	52.87	52.87	3.848E-03	
15	5245.	1.180	1.224	0.971578	56.88	56.88	5.670E-03	
16	5265.	1.355	1.401	0.980553	63.33	63.33	9.901E-03	
17	5275.	1.695	1.686	0.994664	68.40	68.40	1.351E-02	

PLOTRATE CRACK GROWTH ANALYSIS

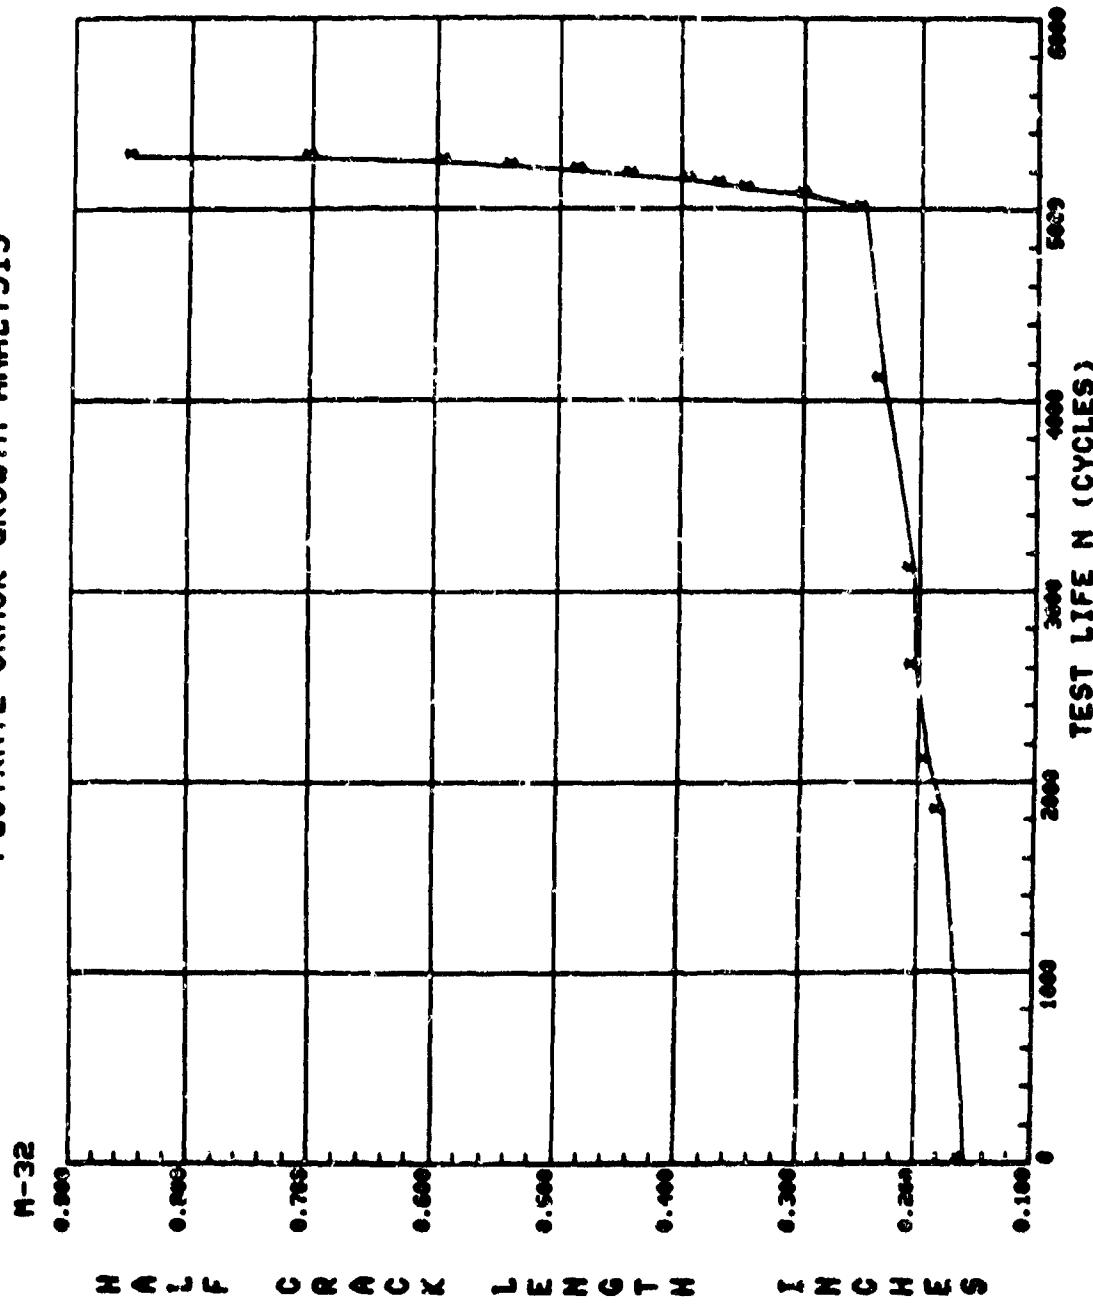


Figure 46. Crack growth curve for test M-32.

FIGURE 15. DYNAMIC VIBRATION FOR HSI M 55

SPECIMEN NO.: 4-13

CCY SPECIMEN B = 0.250 IN. h = 0.0001 IN. AN = 0.1 T₄.

P41N = PMAX = TFSF FREQ = f_{0.1} Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	ALMEASUREMENT	AIRPRESSURE	MULT. COEF. COEFF	V-MAX	DELTA K	DA/DN
1	0.	0.265	0.265	0.999494	13.53	12.00	6.202E-06
2	10000.	0.313	0.308	0.991451	13.93	12.26	1.054E-05
3	11000.	0.330	0.321	0.995578	14.45	12.71	1.234E-05
4	12000.	0.350	0.358	0.997516	15.02	13.22	1.451E-05
5	13500.	0.410	0.405	0.996970	16.04	14.08	1.701E-05
6	15000.	0.460	0.460	0.996128	17.06	15.92	2.077E-05
7	16500.	0.530	0.527	0.995913	18.29	16.09	2.481E-05
8	17500.	0.565	0.576	0.997479	19.12	16.83	2.922E-05
9	18500.	0.640	0.637	0.997944	20.14	17.72	3.481E-05
10	19200.	0.685	0.686	0.998798	20.92	18.41	3.907E-05
11	19900.	0.745	0.746	0.999421	21.95	19.23	4.434E-05
12	20600.	0.810	0.809	0.999749	22.78	20.04	4.974E-05
13	21300.	0.880	0.881	0.998884	23.33	20.97	5.844E-05
14	21900.	0.950	0.953	0.999636	24.45	21.97	6.671E-05
15	22400.	1.020	1.022	0.999689	25.79	22.69	7.615E-05
16	22800.	1.060	1.066	0.999469	26.64	21.44	8.224E-05
17	23100.	1.125	1.137	0.998416	27.31	24.03	9.107E-05
18	23400.	1.195	1.192	0.998392	28.03	24.66	9.997E-05
19	23700.	1.245	1.251	0.999315	28.79	25.33	1.107E-04
20	24000.	1.325	1.321	0.996467	29.68	26.12	1.254E-04
21	24300.	1.400	1.400	0.999671	30.66	26.98	1.411E-04
22	24600.	1.490	1.489	0.999348	31.77	27.95	1.622E-04
23	24900.	1.590	1.589	0.999836	32.99	29.03	1.827E-04
24	25200.	1.700	1.700	0.997454	34.35	30.23	2.190E-04
25	25500.	1.840	1.840	0.997656	36.06	31.73	2.513E-04
26	25800.	1.985	2.001	0.997915	38.02	33.46	2.962E-04
27	26000.	2.150	2.122	0.997085	39.53	34.79	3.422E-04
28	26200.	2.245	2.262	0.997036	41.29	36.34	3.941E-04

TABLE 45. DATA TABULATION FOR TEST M-33 (CONCL.)

SPECIMEN NO.: 4-33

C.C. SPECIMEN R = 0.250 IN. W = 6.000 IN.

P4IN = PMAX = TEST FREQ = 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	MEASUREMENT	REGRESSION	MULT. CORR. COEFF	K-MAX	DELTA K	DA/DN
29	26400.	2.415	2.425	0.996611	43.39	38.16	4.683E-04
30	26600.	2.620	2.616	0.984351	45.01	40.31	7.647E-04
31	26700.	2.735	2.753	0.990615	47.85	42.11	9.348E-04
32	26800.	2.875	2.930	0.995889	50.43	44.38	1.149E-03
33	27000.	3.500	3.449	0.999342	60.00	52.80	1.958E-03

PLOT RATE CRACK GROWTH ANALYSIS

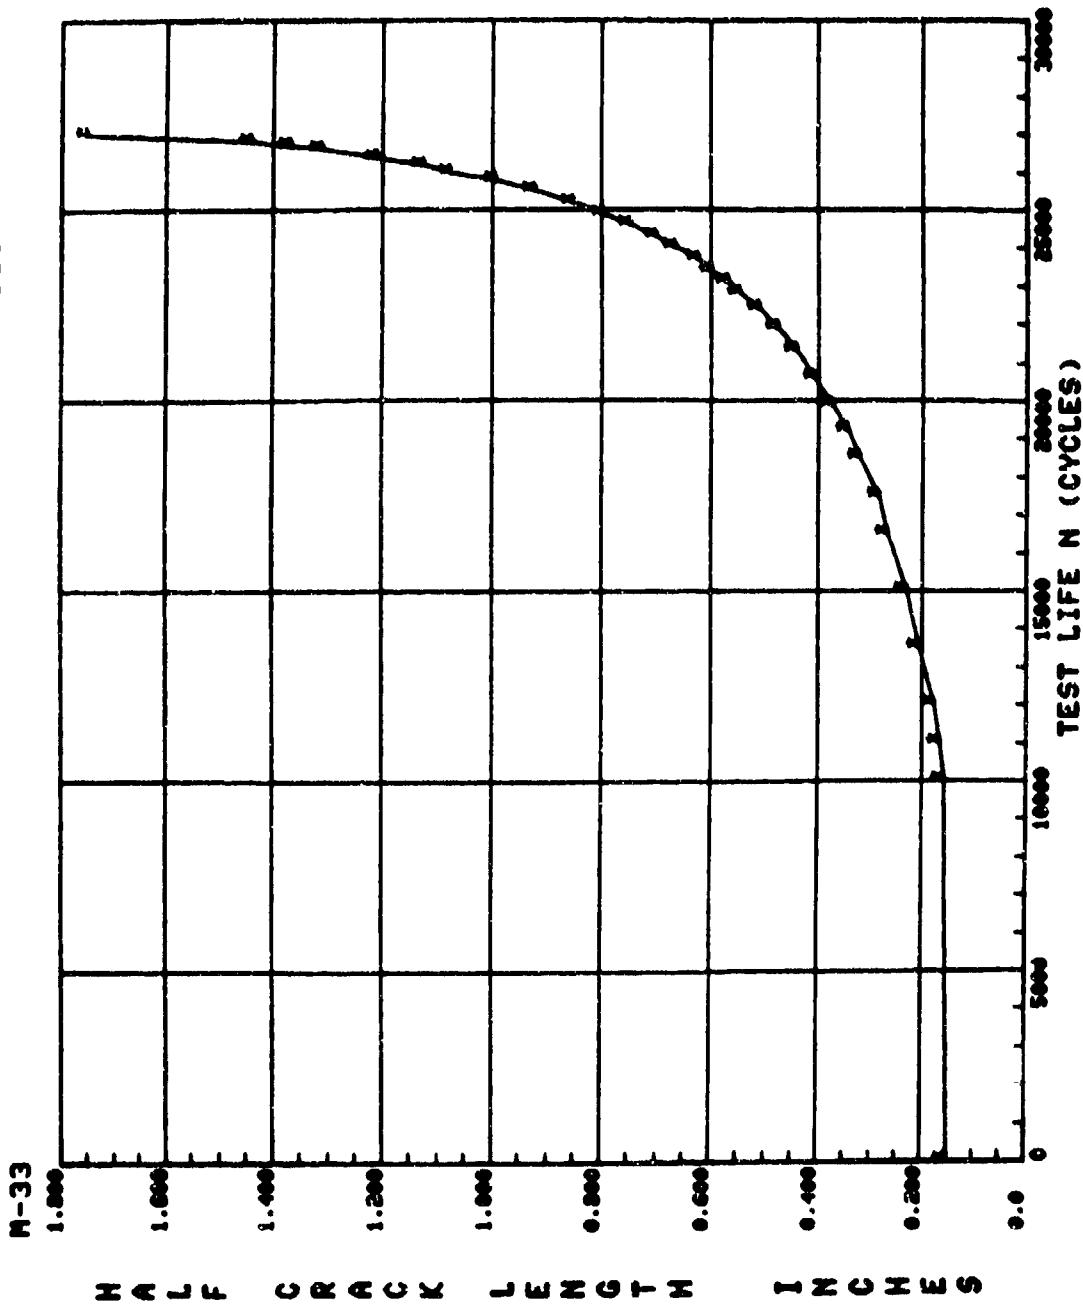


Figure 47. Crack growth curve for test M-33.

SPECTRUM NO.: 4-34

TABLE 46. DATA TABULATION FOR TEST M-34

NO.	CYCLES	AM MEASUREMENT		AGGRESSIVENESS		MULT. CURE	COEFF	K-MAX	DELTA K	DA/DN
		A	B	C	D					
ENVIRONMENT CONDITION: AMBIENT AIR										
1	0.	0.300	0.300	0.300	0.300	0.998633	0.998633	27.50	19.25	7.89E-04
2	2725.	0.345	0.345	0.345	0.345	0.998714	0.998714	29.62	20.73	6.75E-04
3	3304.	0.360	0.360	0.355	0.355	0.998802	0.998802	30.05	21.04	6.852E-04
4	4225.	0.375	0.377	0.377	0.377	0.998729	0.998729	30.86	21.60	1.204E-03
5	5725.	0.400	0.429	0.429	0.429	0.998261	0.998261	32.92	23.04	2.669E-03
6	5925.	0.405	0.451	0.451	0.451	0.9987694	0.9987694	33.77	23.64	4.854E-03
7	5951.	0.455	0.460	0.460	0.460	0.9980723	0.9980723	34.12	23.89	1.86E-04
8	5976.	0.485	0.464	0.464	0.464	0.9985204	0.9985204	34.27	23.99	2.067E-04
9	6001.	0.495	0.483	0.483	0.483	0.9984622	0.9984622	34.99	24.49	3.156E-04
10	6041.	0.500	0.498	0.498	0.498	0.998593	0.998593	35.51	24.86	1.604E-04
11	6101.	0.510	0.511	0.511	0.511	0.9986851	0.9986851	36.06	25.20	1.260E-04
12	6201.	0.545	0.542	0.542	0.542	0.9988402	0.9988402	37.09	25.96	1.781E-04
13	6301.	0.580	0.583	0.583	0.583	0.999198	0.999198	38.49	26.94	2.403E-04
14	6401.	0.640	0.625	0.625	0.625	0.997177	0.997177	40.22	28.16	3.187E-04
15	6501.	0.700	0.703	0.703	0.703	0.997299	0.997299	42.37	29.66	4.189E-04
16	6601.	0.785	0.796	0.796	0.796	0.994668	0.994668	45.19	31.63	5.820E-04
17	6658.	0.860	0.862	0.862	0.862	0.997803	0.997803	67.12	32.99	7.400E-04
18	6708.	0.930	0.940	0.940	0.940	0.997494	0.997494	49.33	34.53	9.633E-04
19	6735.	0.955	0.960	0.960	0.960	0.998426	0.998426	50.70	35.49	1.121E-03
20	6769.	1.069	1.065	1.065	1.065	0.998833	0.998833	52.72	36.90	1.351E-03
21	6906.	1.175	1.173	1.173	1.173	0.989939	0.989939	55.58	38.90	1.866E-03
22	6835.	1.275	1.288	1.288	1.288	0.987149	0.987149	58.50	40.95	2.695E-03
23	6956.	1.370	1.426	1.426	1.426	0.930705	0.930705	61.95	43.37	4.702E-03
24	6866.	1.480	1.509	1.509	1.509	0.947289	0.947289	63.99	44.79	7.049E-03
25	6879.	1.605	1.715	1.715	1.715	0.960018	0.960018	69.06	48.34	1.161E-02
26	6884.	1.865	1.853	1.853	1.853	0.961027	0.961027	72.41	50.59	1.822E-02

PLOT RATE CRACK GROWTH ANALYSIS

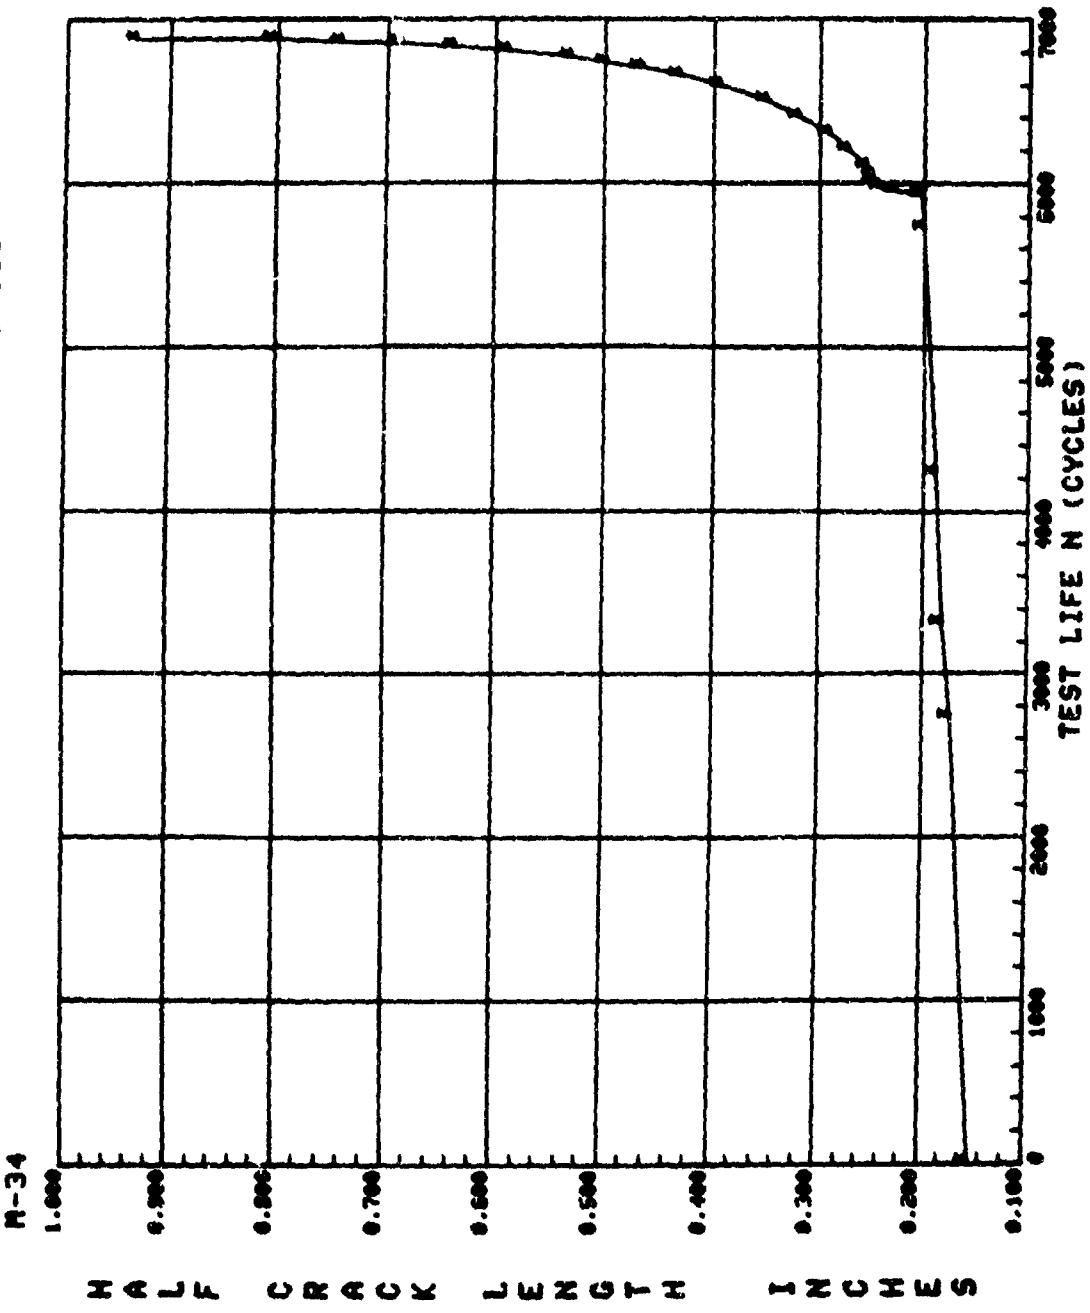


Figure 48. Crack growth curve for test N-34.

TABLE 47. DATA TABULATION FOR TEST M-35

SPECIMEN NO.:	CCT SPECIMEN	B= 0.250 IN.	W= 0.000 IN.	AA= 0.0 IN.	TEST FREQ= 6.000 Hz.
PIN#	PIN#				
ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLES	MEASURED	REGRESSION	MULT. COEFF	K-MAX
1	0.	0.290	0.290	0.975000	13.51
2	10000.	0.320	0.330	0.986665	14.42
3	11000.	0.345	0.330	0.988675	14.44
4	28500.	0.350	0.386	0.987367	15.66
5	40000.	0.425	0.429	0.991373	16.46
6	50000.	0.470	0.474	0.998544	17.33
7	56000.	0.510	0.507	0.995176	17.92
8	61500.	0.540	0.540	0.996890	18.52
9	67000.	0.580	0.575	0.997854	19.11
10	73000.	0.605	0.609	0.997682	19.69
11	78000.	0.640	0.641	0.99484	20.21
12	83000.	0.670	0.667	0.990050	20.63
13	88000.	0.705	0.700	0.991218	21.14
14	93000.	0.720	0.733	0.992463	21.05
15	98000.	0.775	0.768	0.993576	22.18
16	103000.	0.810	0.806	0.994598	22.75
17	108000.	0.845	0.851	0.996706	23.40
18	113000.	0.855	0.894	0.999722	24.01
19	118000.	0.945	0.943	0.999278	24.70
20	123000.	1.000	1.001	0.999428	25.53
21	126000.	1.060	1.064	0.999696	26.35
22	133000.	1.140	1.135	0.999183	27.28
23	136000.	1.215	1.219	0.999163	28.37
24	141000.	1.270	1.274	0.998505	29.08
25	144000.	1.340	1.334	0.998251	29.83
26	147000.	1.395	1.405	0.997649	30.72
27	148000.	1.430	1.430	0.997655	31.03
28	149000.	1.460	1.456	0.997763	31.36

SPECIMEN NO.: 4-35

TABLE 47. DATA TABULATION FOR TEST M-35 (CONCL)

CCT	SPECIMEN	R= 0.250 IN.	W= 6.000 IN.	A= 0.0	IN.	P MIN=		P MAX=		TEST FREQ= 6.00 Hz.	
						NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. COEFF	K-MAX
ENVIRONMENT CONDITION: AMBIENT AIR											
29	150500.	1.500	1.500	0.999232	31.89	9.57	1.478E-05				
30	153000.	1.575	1.572	0.999725	32.78	9.83	1.545E-05				
31	155500.	1.650	1.652	0.999901	33.76	10.13	1.645E-05				
32	158000.	1.740	1.741	0.999931	34.84	10.45	1.865E-05				
33	160500.	1.840	1.837	0.999749	36.01	10.60	2.075E-05				
34	163000.	1.945	1.945	0.999535	37.34	11.20	2.330E-05				
35	165592.	2.055	2.060	0.999493	38.76	11.63	2.656F-05				
36	167131.	2.155	2.153	0.999679	39.92	11.98	2.994E-05				
37	168831.	2.255	2.258	0.998911	41.24	12.37	3.498E-05				
38	170148.	2.350	2.352	0.999152	42.45	12.73	3.933E-05				
39	171544.	2.460	2.467	0.999174	43.94	13.18	4.354E-05				
40	172344.	2.550	2.541	0.999155	44.93	13.49	4.631E-05				
41	173144.	2.620	2.618	0.999194	45.98	13.79	4.903E-05				
42	173944.	2.655	2.696	0.997850	47.06	14.12	5.318E-05				
43	174844.	2.750	2.790	0.999530	48.38	14.51	5.883E-05				
44	175669.	2.885	2.860	0.999313	49.84	14.95	6.880E-05				
45	176352.	2.950	2.986	0.998073	51.29	15.39	9.204E-05				
46	177041.	3.055	3.104	0.995341	53.13	15.94	1.053E-04				
47	177548.	3.200	3.213	0.996854	54.91	16.47	1.257E-04				
48	177906.	3.300	3.306	0.998821	56.50	16.95	1.588E-04				
49	178173.	3.405	3.304	0.998903	58.05	17.41	1.822E-04				
50	178423.	3.480	3.491	0.998385	59.84	17.95	2.043E-04				
51	178673.	3.600	3.599	0.997152	61.94	18.58	2.273E-04				

PLOTRATE CRACK GROWTH ANALYSIS

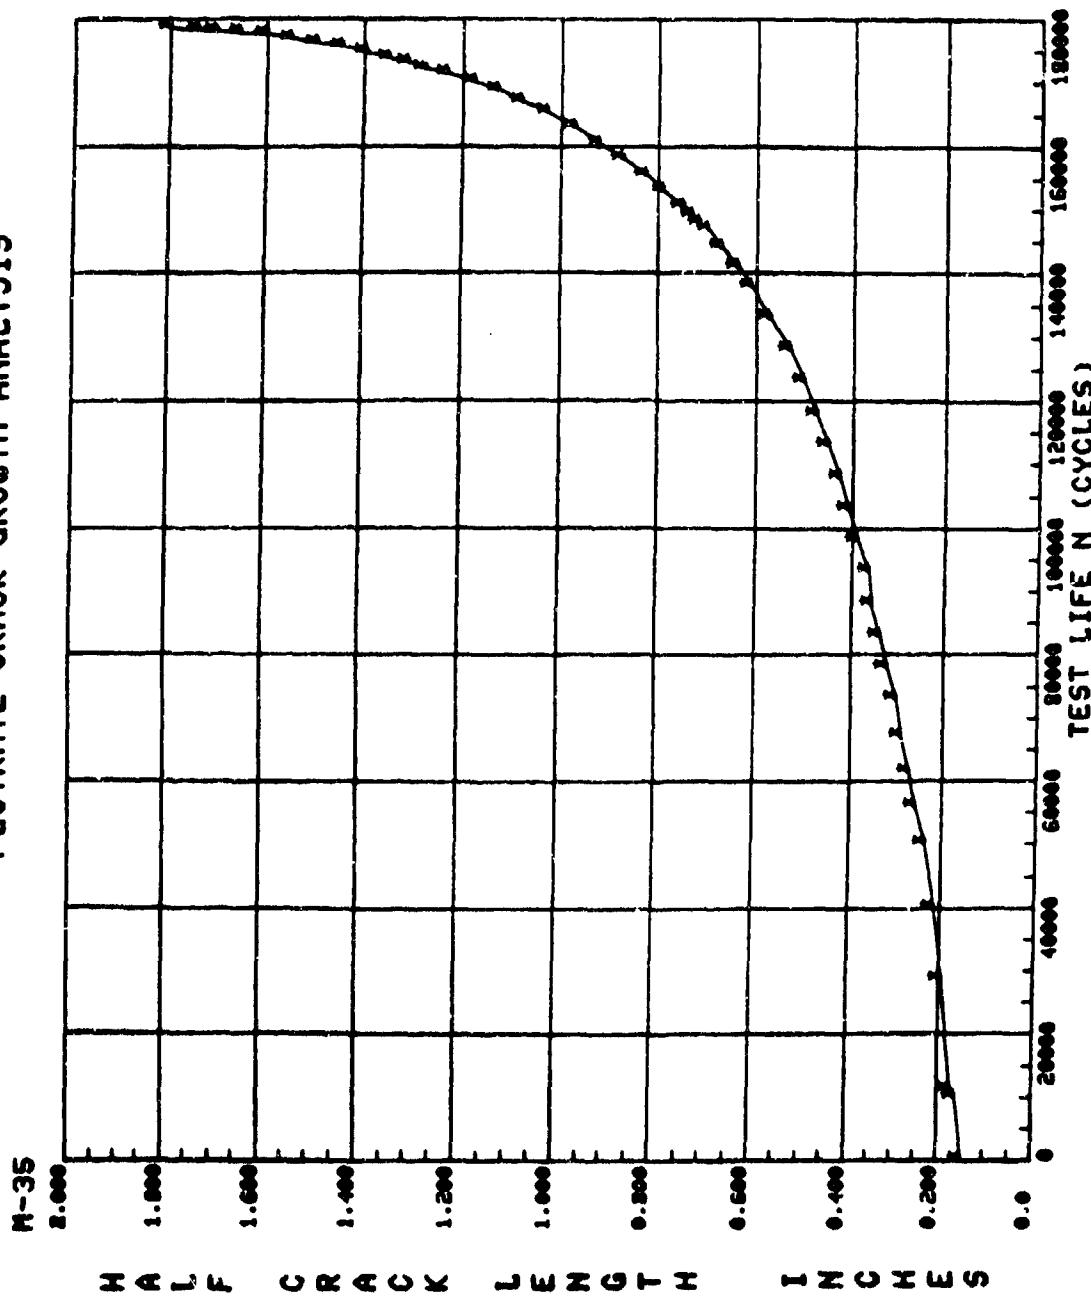


Figure 49. Crack growth curve for test M-35.

SPECIMEN NO.: 4-36

TABLE 48. DATA TABULATION FOR TEST M-36

CYCLES	AIMEASLRFN	AIRPRESSURE	FULT.	CORR.	COEFF	K-MAX	DELTA K	DA/DN
ENVIRONMENT CONDITION: AMBIENT AIR								
1	0.	0.300	0.300	0.999886	27.50	8.25	6.884E-06	
2	2000.	0.350	0.355	0.998338	29.91	8.97	1.781E-05	
3	3000.	0.395	0.395	0.998520	31.59	9.48	2.130E-05	
4	3950.	0.445	0.429	0.998397	33.31	9.99	2.541E-05	
5	5000.	0.455	0.407	0.996380	35.48	10.64	3.110E-05	
6	5790.	0.540	0.546	0.994088	37.21	11.16	3.940E-05	
7	6400.	0.550	0.593	0.996185	38.82	11.65	5.048E-05	
8	6962.	0.645	0.651	0.993874	40.72	12.22	6.414E-05	
9	7416.	0.710	0.712	0.998992	42.65	12.60	8.111E-05	
10	7754.	0.770	0.769	0.998325	44.39	13.32	1.003E-04	
11	8007.	0.815	0.821	0.997306	45.94	13.78	1.213E-04	
12	8263.	0.880	0.885	0.997981	47.78	14.34	1.533E-04	
13	8411.	0.930	0.930	0.999867	49.04	14.71	1.780E-04	
14	8560.	0.965	0.986	0.999866	50.61	15.18	2.031E-04	
15	8668.	1.035	1.033	0.999733	51.88	15.56	2.175E-04	
16	8793.	1.050	1.069	0.998937	53.37	16.01	2.425E-04	
17	8902.	1.145	1.141	0.995269	54.72	16.42	2.809E-04	
18	9027.	1.205	1.211	0.988986	56.54	16.96	3.709E-04	
19	9133.	1.280	1.291	0.993073	58.58	17.57	5.143E-04	
20	9210.	1.360	1.376	0.970368	60.72	18.22	8.227E-04	
21	9253.	1.440	1.441	0.97603	62.35	18.70	1.076E-03	
22	9316.	1.535	1.593	0.977900	66.09	19.83	1.615E-03	
23	9346.	1.710	1.705	0.978120	68.80	20.64	2.414E-03	

PLOT RATE CRACK GROWTH ANALYSIS

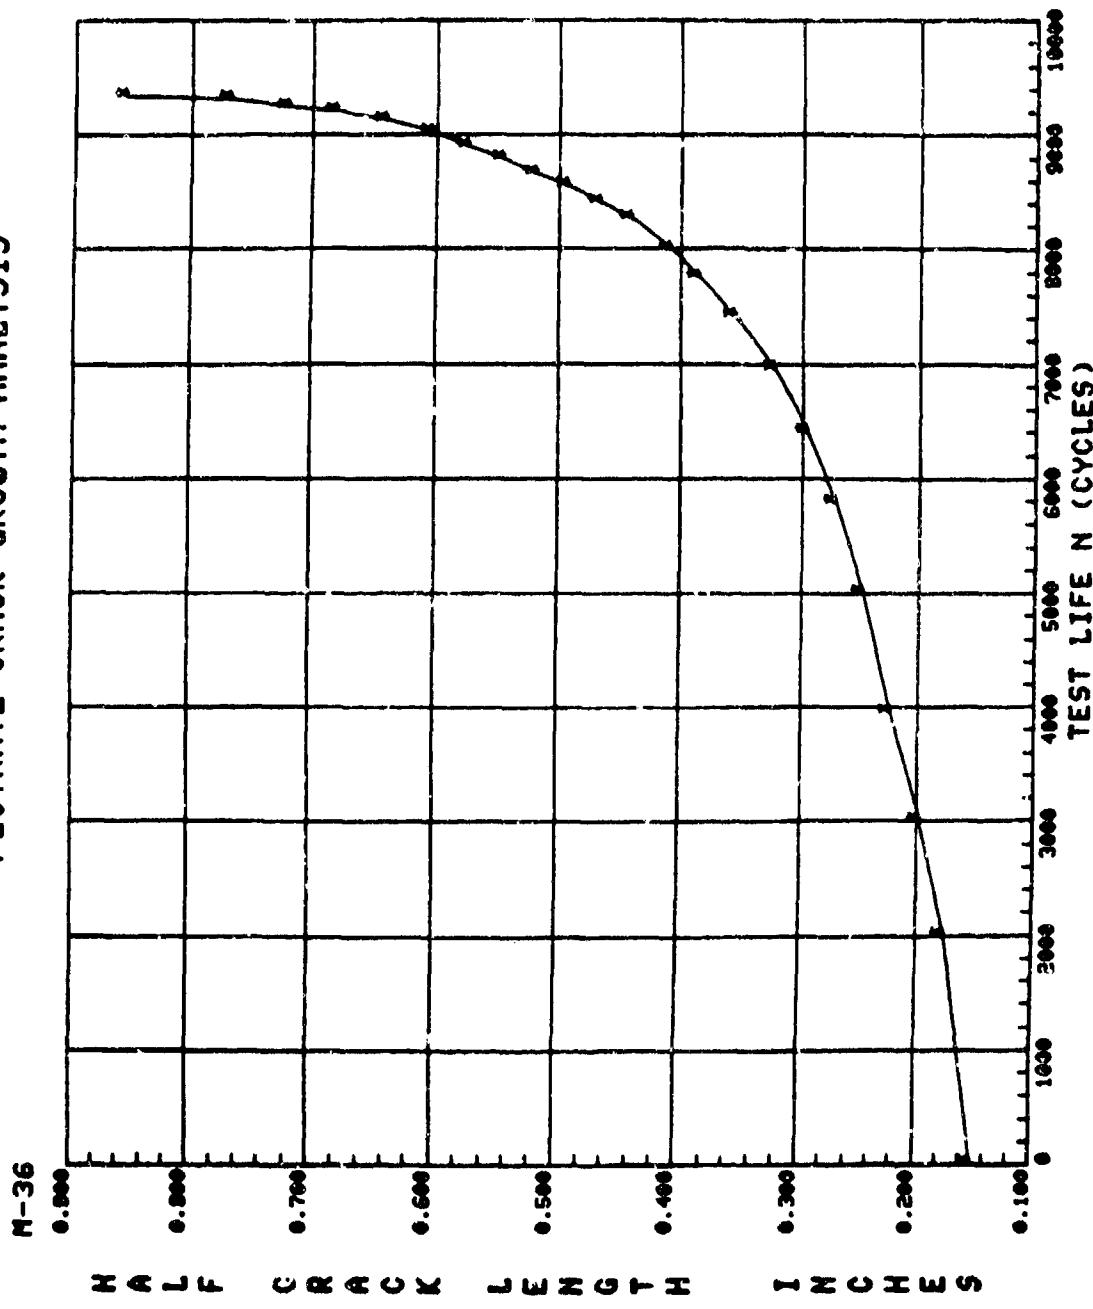


Figure 50. Crack growth curve for test M-36.

TABLE 49. DATA TABULATION FOR TEST M-37

SPECIMEN NO.: 4-37	CCT	SPECIMEN	A = 0.250 IN.	W = 6.000 IN.	AN = 0.0 IN.	TEST FREQ = 6.00 Hz	ENVIRONMENT CONDITION: AMBIENT AIR					
							CYCLES	A (MEASURED)	A (REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K
1	0.	1.0000..	0.316	0.316	0.998182	14.10	14.10	1.034E-05				
2	1.0000..	0.320	0.316	0.316	0.998124	14.12	14.12	1.122E-05				
3	1.2466..	0.380	0.386	0.386	0.995982	15.61	15.61	1.784E-05				
4	1.3740..	0.430	0.438	0.438	0.991933	16.64	16.64	2.224E-05				
5	1.4944..	0.485	0.490	0.490	0.997081	17.62	17.62	2.687E-05				
6	1.5810..	0.540	0.540	0.540	0.995959	18.51	18.51	3.129E-05				
7	1.6342..	0.585	0.575	0.575	0.996048	19.11	19.11	3.388E-05				
8	1.7350..	0.635	0.644	0.644	0.994550	20.31	20.31	4.044E-05				
9	1.7828..	0.650	0.684	0.684	0.996079	20.90	20.90	4.376E-05				
10	1.8576..	0.750	0.753	0.753	0.997603	21.96	21.96	5.169E-05				
11	1.9000..	0.805	0.802	0.802	0.998220	22.68	22.68	5.608E-05				
12	1.9501..	0.855	0.857	0.857	0.997566	23.49	23.49	6.322E-05				
13	2.0000..	0.925	0.924	0.924	0.996030	24.44	24.44	7.542E-05				
14	2.0401..	0.975	0.985	0.985	0.997892	25.29	25.29	8.645E-05				
15	2.0550..	1.015	1.013	1.013	0.996956	25.66	25.66	8.778E-05				
16	2.0850..	1.075	1.068	1.068	0.996929	26.40	26.40	9.657E-05				
17	2.1150..	1.130	1.127	1.127	0.996695	27.19	27.19	1.082E-04				
18	2.1450..	1.185	1.192	1.192	0.998609	28.02	28.02	1.197E-04				
19	2.1750..	1.265	1.265	1.265	0.999729	28.96	28.96	1.391E-04				
20	2.2050..	1.355	1.354	1.354	0.999809	30.08	30.08	1.623E-04				
21	2.22701..	1.406	1.406	1.406	0.999686	30.73	30.73	1.773E-04				
22	2.2350..	1.460	1.459	1.459	0.999785	31.40	31.40	1.905E-04				
23	2.2500..	1.515	1.517	1.517	0.999587	32.11	32.11	2.090E-04				
24	2.2650..	1.585	1.583	1.583	0.999340	32.92	32.92	2.245E-04				
25	2.2800..	1.650	1.651	1.651	0.998362	33.75	33.75	2.512E-04				
26	2.2950..	1.735	1.731	1.731	0.997420	34.73	34.73	2.690E-04				
27	2.3100..	1.805	1.813	1.813	0.996384	35.72	35.72	3.022E-04				
28	2.3250..	1.920	1.917	1.917	0.995857	36.87	36.87	3.528E-04				

TABLE 49. DATA TABULATION FOR TEST M-37 (CONCL.)

SPECIMEN NO.: 4-37

CCT	SPECIMEN	R = 0.250 IN.	W = 0.000 IN.	ΔR = 0.0	TEST FREQ = 6.000 Hz.	ENVIRONMENT CONDITION: AMBIENT AIR		MULT. COEF	K-MAX	DELTA K	DA/DN
						P MIN	P MAX				
29	23350.	1.960	1.976	0.997075	37.72	3.97E-04					
30	23450.	2.060	2.060	0.997436	38.76	6.442F-04					
31	23550.	2.155	2.152	0.997831	39.90	4.848E-04					
32	23650.	2.260	2.257	0.999034	41.23	5.545E-04					
33	23750.	2.370	2.364	0.996721	42.60	6.391E-04					
34	23850.	2.485	2.491	0.996929	44.26	7.819E-04					
35	23950.	2.640	2.650	0.994981	46.42	1.052F-03					
36	24025.	2.810	2.812	0.983416	48.56	1.547F-03					
37	24100.	3.000	3.050	0.988708	52.27	2.179E-03					
38	24150.	3.220	3.269	0.994030	55.95	55.85					
39	24200.	3.605	3.603	0.999145	62.03	62.03					

PLOTRATE CRACK GROWTH ANALYSIS

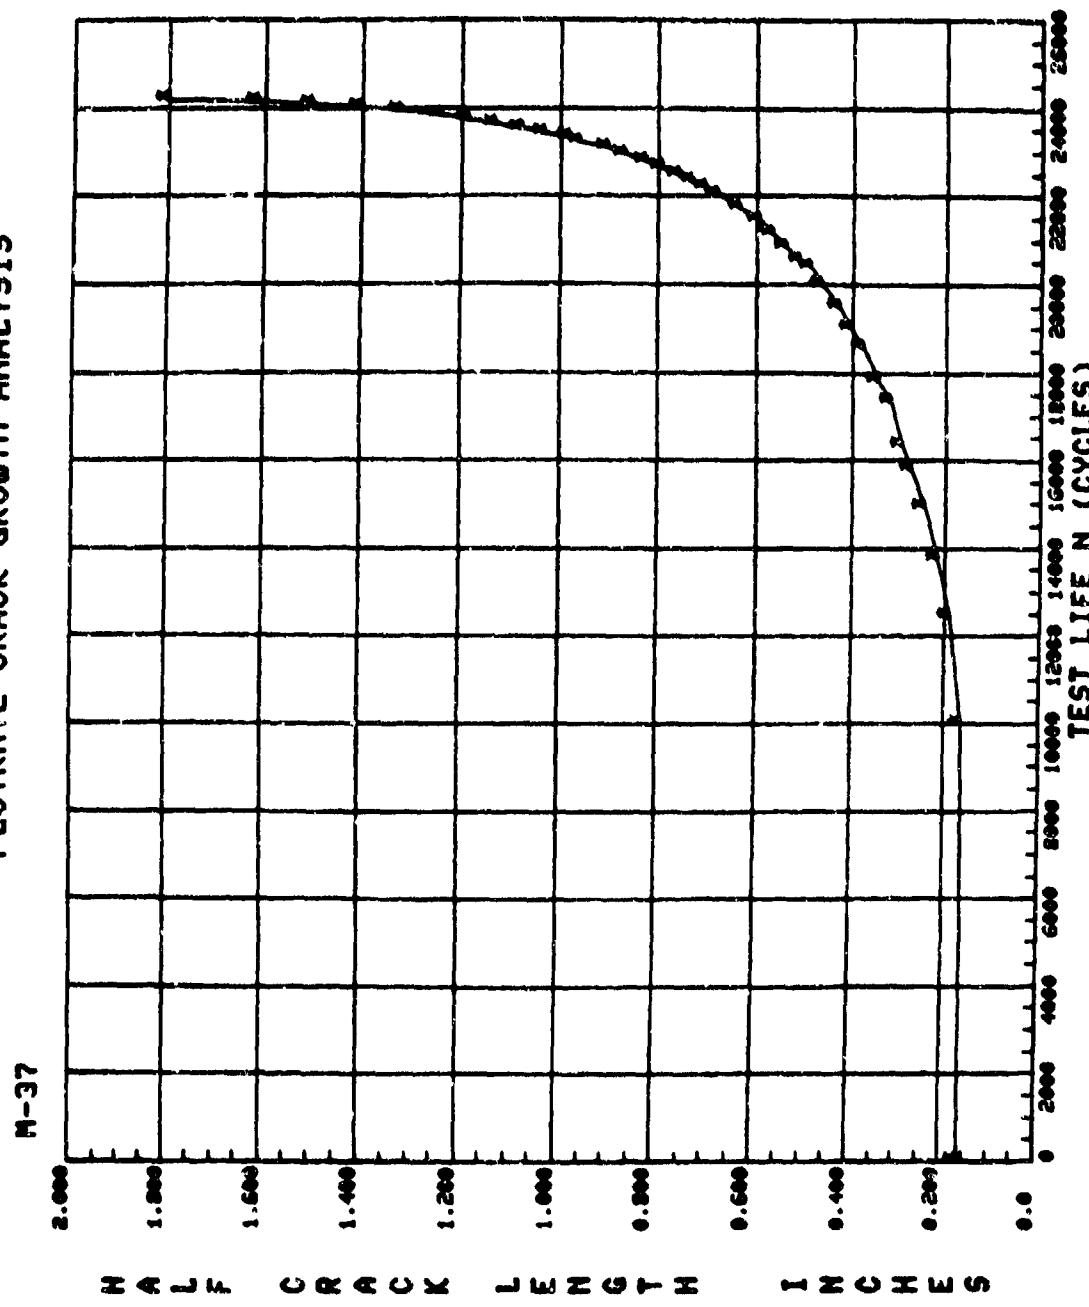


Figure 51. Crack growth curve for test M-37.

TABLE 50. DATA TABULATION FOR TEST M-38

SPECIMEN NO.: 4-38

CCT	SPECIMEN	R = 0.250 IN.	h = 6.000 IN.	AN = 0.0 IN.	TEST FREQ = 6.110 Hz.	ENVIRONMENT CONDITION: AMBIENT AIR						
						PH14:	P MAX:	NO.	CYCLES	A MEASUREMENT	A REGRESSION	WULT.
								1	0.	0.300	0.300	0.998856
								2	1501.	0.325	0.331	0.997097
								3	2501.	0.380	0.379	0.994709
								4	3201.	0.425	0.419	0.994485
								5	3901.	0.470	0.471	0.957958
								6	4702.	0.520	0.552	0.953865
								7	5005.	0.540	0.621	0.759967
								8	5030.	0.605	0.653	0.732514
								9	5055.	0.670	0.665	0.994355
								10	5075.	0.715	0.725	0.994154
								11	5095.	0.775	0.783	0.793851
								12	5105.	0.835	0.812	0.986151
								13	5135.	0.910	0.934	0.961730
								14	5150.	0.985	0.984	0.911771
								15	5156.	1.050	1.007	0.927621
								16	5170.	1.020	1.116	0.967111
								17	5180.	1.230	1.200	0.970730
								18	5190.	1.400	1.414	0.979280

PLOTRATE CRACK GROWTH ANALYSIS

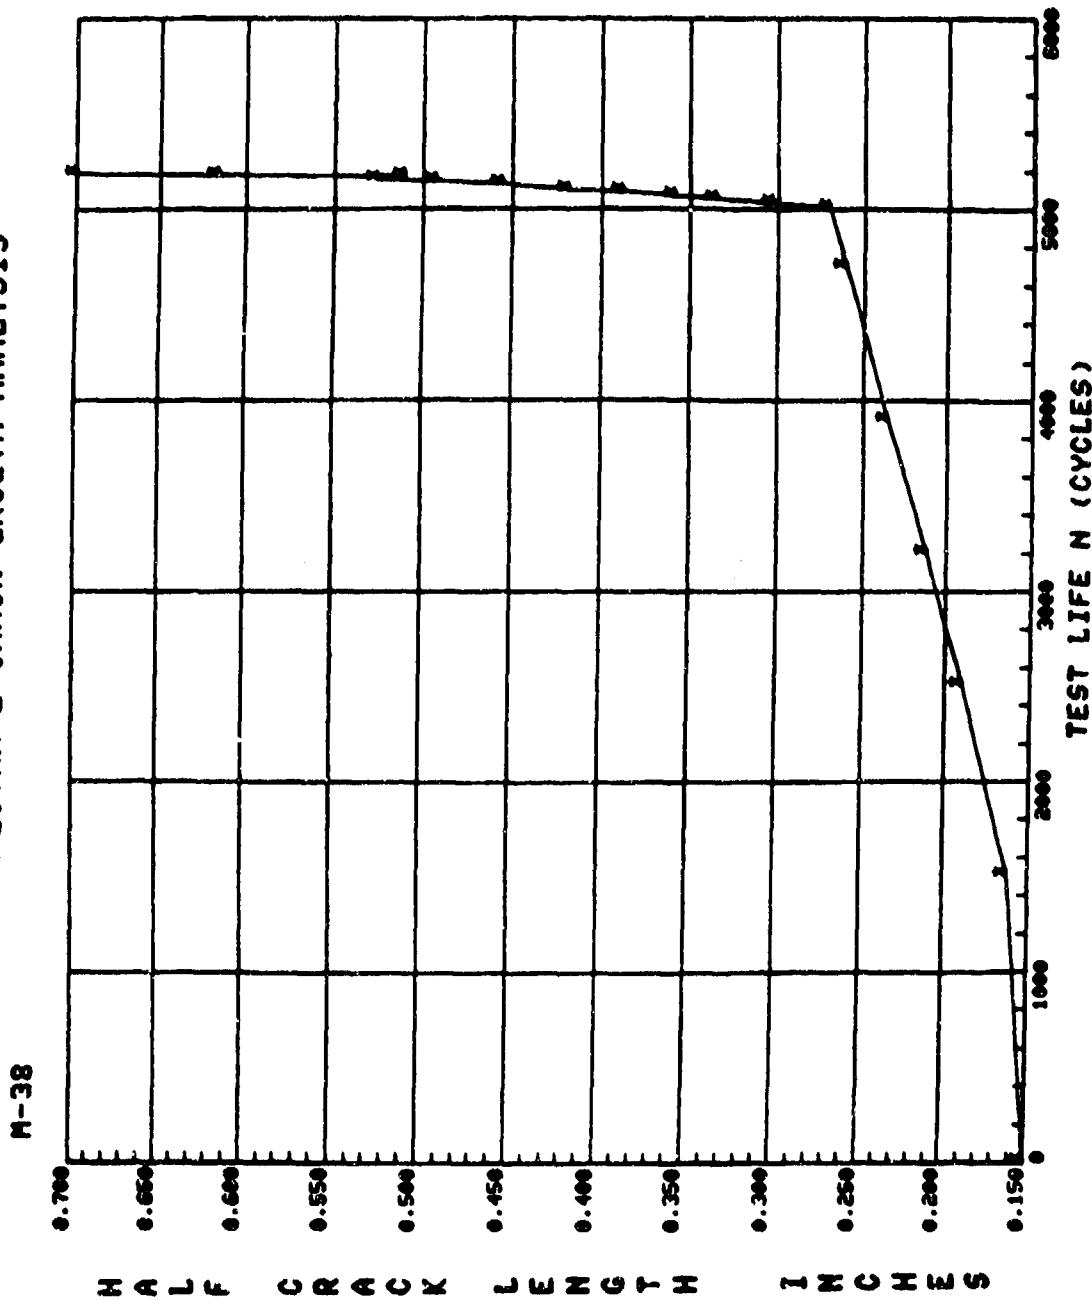


Figure 52. Crack growth curve for test M-38.

TABLE 51. DATA TABULATION FOR TEST M-39

SPECIMEN NO.: M-39

CCF SPECIMEN A = 0.250 IN.
 ρ_{MAX} = 6.000 IN.
 $\mu = 6.000$ IN.
 $\Delta h = 0.0$ IN.
TEST FREQ = 6.000 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLE'S	A MEASURED	A REGRESSION	MULT. COEFF	K-MAX	DELTA K	DA/DH
1	0.	0.300	0.310	0.998979	13.75	9.08E-06	
2	5000.	0.300	0.301	0.999581	13.76	9.34E-06	
3	6500.	0.340	0.338	0.999234	14.61	1.443E-05	
4	Flame.	0.350	0.389	0.999340	15.68	1.942E-05	
5	Oil.	0.435	0.434	0.999831	16.56	2.217E-05	
6	10000.	0.480	0.480	0.998622	17.43	2.593E-05	
7	11000.	0.535	0.534	0.998448	18.40	3.01E-05	
8	12000.	0.550	0.556	0.998867	19.47	3.625E-05	
9	12600.	0.650	0.648	0.999275	20.32	4.148E-05	
10	13100.	0.650	0.691	0.999175	21.00	4.473E-05	
11	13600.	0.740	0.739	0.999474	21.74	4.923E-05	
12	14100.	0.750	0.787	0.998021	22.47	5.335E-05	
13	14600.	0.840	0.844	0.998070	23.30	6.424E-05	
14	15100.	0.895	0.899	0.999053	24.09	7.584E-05	
15	15651.	0.955	0.954	0.999364	26.05	7.99E-05	
16	15750.	1.005	1.005	0.996364	25.56	8.905E-05	
17	16000.	1.060	1.051	0.991734	26.18	9.999E-05	
18	16367.	1.110	1.126	0.992387	27.17	1.176E-04	
19	16567.	1.170	1.173	0.991242	27.79	1.247E-04	
20	16680.	1.215	1.202	0.990036	28.15	1.267E-04	
21	16855.	1.255	1.254	0.996044	28.82	1.400E-04	
22	17030.	1.295	1.299	0.996673	29.40	1.392E-04	
23	17205.	1.345	1.345	0.999259	29.98	1.503E-04	
24	17355.	1.355	1.390	0.997961	30.54	1.76E-04	
25	17505.	1.440	1.447	0.998245	31.25	1.976E-04	
26	17605.	1.495	1.490	0.997065	31.78	2.08E-04	
27	17755.	1.565	1.556	0.998369	32.58	2.298E-04	
28	17955.	1.655		0.998577	33.77	2.58E-04	

TABLE 51. DATA TABULATION FOR TEST M-39 (CONCL)

SPECIMEN NO.: 4-39

RCT SPECIMEN $\theta = 0.250$ IN. $M = 6.000$ IN.
 $P_{MAX} =$

$A_N = 0.0$ IN.
TEST FREQ = 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	TIME ASLIPED	REGRESSION	MULT. CORR. COEFF	K-MAX	DELTAK	DATA
29	18155.	1.750	1.758	0.997910	35.05	35.05	2.971E-06
30	18310.	1.850	1.850	0.994669	36.16	36.16	3.384E-06
31	18444.	1.940	1.944	0.999127	37.33	37.33	3.829E-06
32	18544.	2.030	2.024	0.999343	38.31	38.31	4.281E-06
33	18644.	2.110	2.113	0.999329	39.42	39.42	4.632E-06
34	18744.	2.205	2.209	0.998638	40.62	40.62	5.194E-06
35	18823.	2.300	2.291	0.998986	41.66	41.66	5.695E-06
16	18923.	2.400	2.411	0.997675	43.22	43.22	6.789E-06
37	19083.	2.455	2.493	0.998190	44.29	44.29	7.704E-06
38	19041.	2.575	2.581	0.999142	45.48	45.48	8.955E-06
39	19085.	2.671	2.664	0.996696	46.61	46.61	1.063E-03
40	19135.	2.765	2.773	0.998298	48.14	48.14	1.267E-03
41	19169.	2.855	2.863	0.998286	49.45	49.45	1.516E-03
42	19199.	2.965	2.956	0.997092	50.82	50.82	1.863E-03
43	19227.	3.055	3.065	0.996408	52.52	52.52	2.310E-03
44	19248.	3.150	3.165	0.995244	54.12	54.12	2.928E-03
45	19262.	3.250	3.243	0.996194	55.41	55.41	3.692E-03
46	19277.	3.345	3.360	0.996651	57.44	57.44	4.648E-03
47	19249.	3.465	3.478	0.996615	59.60	59.60	5.786E-03
48	19297.	3.580	3.580	0.999787	61.55	61.55	7.583E-03

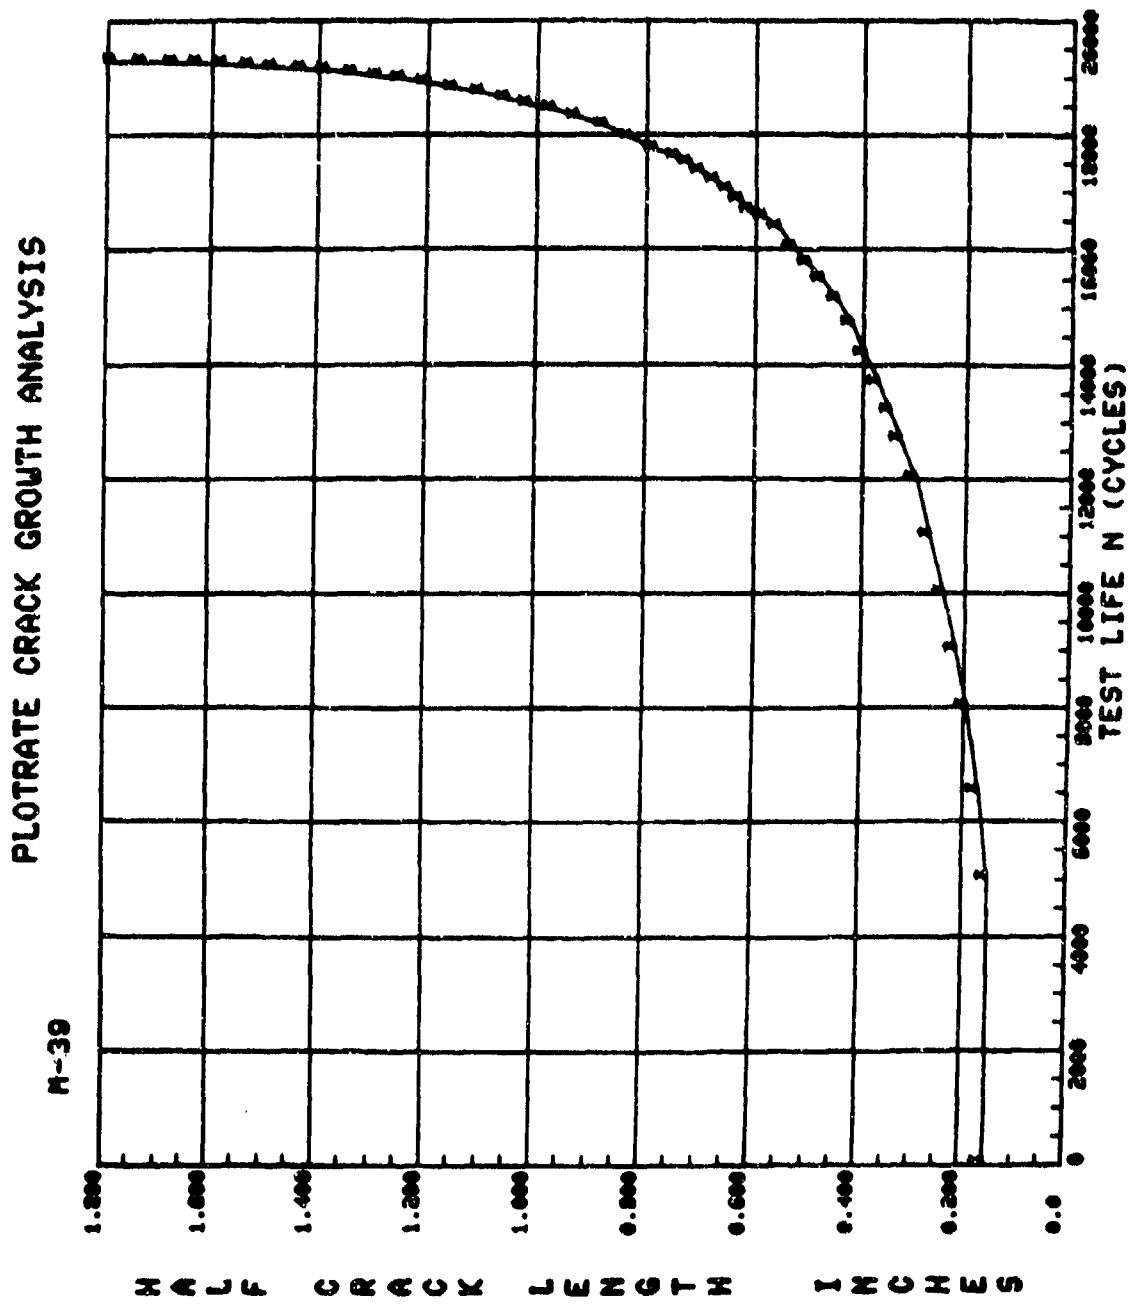


Figure 53. Crack growth curve for test M-39.

TABLE 52. DATA TABULATION FOR TEST M-40

SPECIMEN NO.: 4-40

CCT SPECIMEN $\theta = 0.250$ IN.
 $P_{MAX} =$
ENVIRONMENT CONDITION: AMBIENT AIR
 $k = 6.000$ IN.
 $Ax = 0.0$ IN.

TEST FREQ= 6.00 Hz.

NO.	CYCLES	ALMEASUREMENT	Y (REGRESSION)	MULT. COEFF	K-MAX	DELTA K	DA/DN
1	0.	0.300	0.300	0.983016	27.51	27.51	$2.297E-04$
2	5000.	0.365	0.361	0.985762	27.53	27.53	$2.478E-04$
3	5050.	0.320	0.326	0.993619	28.66	28.66	$2.451E-04$
4	5100.	0.350	0.350	0.993711	29.71	29.71	$2.381E-04$
5	5150.	0.380	0.375	0.995929	30.78	30.78	$2.412E-04$
6	5200.	0.400	0.399	0.995754	31.73	31.73	$2.515E-04$
7	5270.	0.430	0.425	0.986265	32.77	32.77	$2.787E-04$
8	5340.	0.465	0.455	0.979185	33.94	33.94	$3.956E-04$
9	5420.	0.515	0.525	0.981372	36.48	36.48	$6.601E-04$
10	5500.	0.620	0.645	0.991839	40.53	40.53	$1.073E-03$
11	5550.	0.755	0.763	0.996765	44.23	44.23	$1.550E-03$
12	5570.	0.835	0.827	0.993932	46.10	46.10	$2.019E-03$
13	5590.	0.850	0.905	0.986585	48.36	48.36	$2.551E-03$
14	5610.	0.950	0.949	0.981321	50.94	50.94	$3.823E-03$
15	5630.	1.140	1.169	0.973659	55.46	55.46	$6.317E-03$
16	5645.	1.315	1.520	0.927421	61.82	61.82	$1.142E-02$
17	5650.	1.465	1.565	0.920769	65.39	65.39	$1.834E-02$
18	5652.	1.580	1.662	0.956451	67.76	67.76	$3.574E-02$
19	5653.	1.770	1.762	0.981666	70.21	70.21	$6.929E-02$

PLOT RATE CRACK GROWTH ANALYSIS

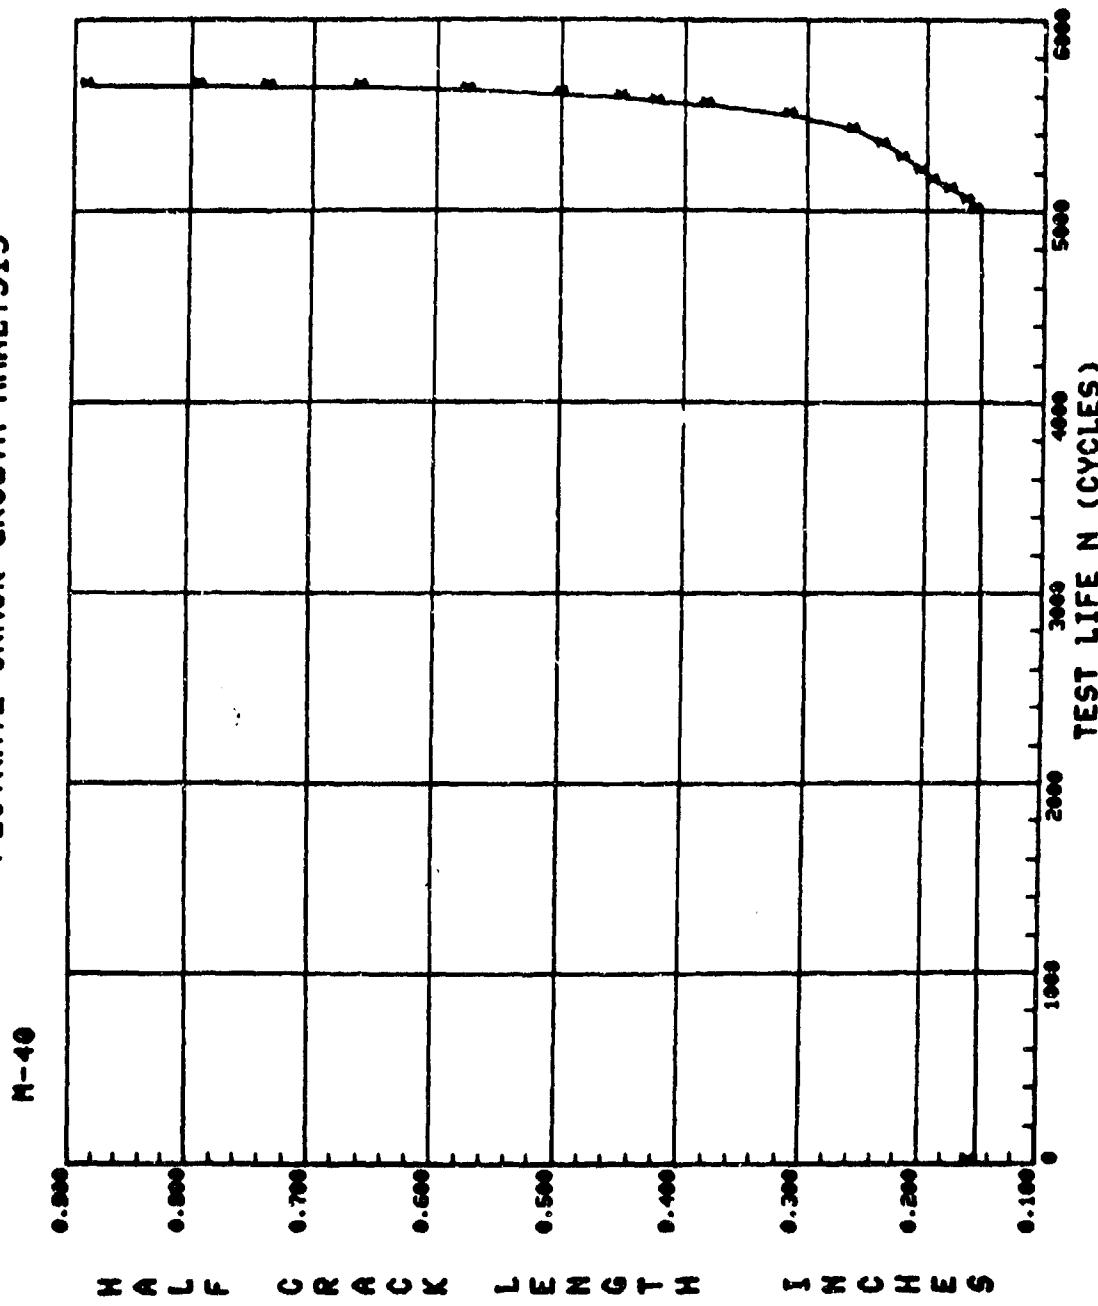


Figure 54. Crack growth curve for test M-40.

TABLE 53. DATA TABULATION FOR TEST M-41

SPECIMEN NO.: 4-41		CCT SPECIMEN R = 0.250 IN.		W = 6.000 IN.		A = 0.01 IN.		TEST FREQ = 6.000 Hz.	
PHASE		PHASE		ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLES	A (MEASURED)	A (REGRESSION)	MULT.	CORR. COEFF	K-MAX	DELTA K	DA/DN	
1	0.	0.300	0.300	0.997107	13.74	6.87	3.330E-07		
2	5000.	0.300	0.307	0.995081	13.91	6.96	1.366E-06		
3	13300.	0.345	0.344	0.997381	14.72	7.36	3.111E-06		
4	19661.	0.395	0.391	0.997439	15.72	7.86	4.227E-06		
5	24911.	0.440	0.445	0.998844	16.77	8.38	5.253E-06		
6	29070.	0.495	0.490	0.997911	17.61	8.81	6.212E-06		
7	33737.	0.545	0.551	0.998561	16.69	9.35	7.449E-06		
8	36751.	0.595	0.596	0.997644	19.47	9.74	8.766E-06		
9	39614.	0.650	0.647	0.999344	20.30	10.15	1.004E-05		
10	42551.	0.705	0.711	0.999369	21.31	10.66	1.150E-05		
11	45051.	0.775	0.771	0.999282	22.22	11.11	1.259E-05		
12	47051.	0.825	0.825	0.999345	23.02	11.51	1.412E-05		
13	49051.	0.880	0.884	0.999079	23.67	11.94	1.566E-05		
14	51051.	0.950	0.944	0.994594	24.72	12.36	1.864E-05		
15	53051.	1.015	1.022	0.995416	25.79	12.89	2.261E-05		
16	54551.	1.080	1.092	0.996028	26.73	13.36	2.702E-05		
17	55550.	1.160	1.146	0.995789	27.44	13.72	2.975E-05		
18	56250.	1.190	1.192	0.995926	28.03	14.02	3.057E-05		
19	56950.	1.240	1.237	0.992488	28.61	14.30	3.357E-05		
20	57650.	1.280	1.283	0.994522	29.19	14.60	3.381E-05		
21	58350.	1.325	1.313	0.996281	29.82	14.91	3.707E-05		
22	59050.	1.400	1.385	0.997347	30.47	15.24	3.939E-05		
23	60750.	1.455	1.464	0.997808	31.45	15.72	4.352E-05		
24	61000.	1.555	1.554	0.997633	32.56	16.28	4.935E-05		
25	62000.	1.655	1.654	0.999357	33.79	16.89	5.771E-05		
26	62650.	1.730	1.735	0.998334	34.77	17.39	6.703E-05		
27	63000.	1.780	1.780	0.999531	35.32	17.66	7.151E-05		
28	63500.	1.850	1.853	0.999121	36.21	18.10	8.222E-05		

TABLE 53. DATA TABULATION FOR TEST M-41 (CONCL.)

SPECIMEN NO.: 4-1	CCT SPECIMEN	$\alpha = 0.250$ IN.	$w = 6.000$ IN.	$A\Delta = 0.0$ IN.	TEST FREQ= 6.00 Hz.
PNTY	P MAX	ENVIRONMENT CONDITION: AMBIENT AIR			
29	CYCLE S	A (MEASUREMENT)	A (REGRESSION)	MULT. CORR. COEFF	K-MAX
29	640000.	1.945	1.934	0.998272	37.20
30	645000.	2.030	2.015	0.997635	38.45
31	650000.	2.155	2.163	0.998227	40.03
32	65637.	2.360	2.365	0.998777	42.61
33	65800.	2.445	2.429	0.998528	43.43
34	66000.	2.500	2.519	0.997897	44.51
35	66200.	2.550	2.592	0.997465	45.63
36	66400.	2.655	2.690	0.999661	46.97
37	66600.	2.805	2.810	0.999592	48.67
38	66800.	2.950	2.945	0.997357	50.66
39	66950.	3.060	3.068	0.997779	52.55
40	67100.	3.200	3.220	0.995234	55.03
+1	67200.	3.345	3.346	0.997829	57.19
42	67250.	3.410	3.425	0.997323	58.61
43	67300.	3.525	3.523	0.997980	60.44
44	67350.	3.630	3.639	0.998833	62.74
45	67400.	3.750	3.789	0.998513	65.94
					32.97
					1.609E-03

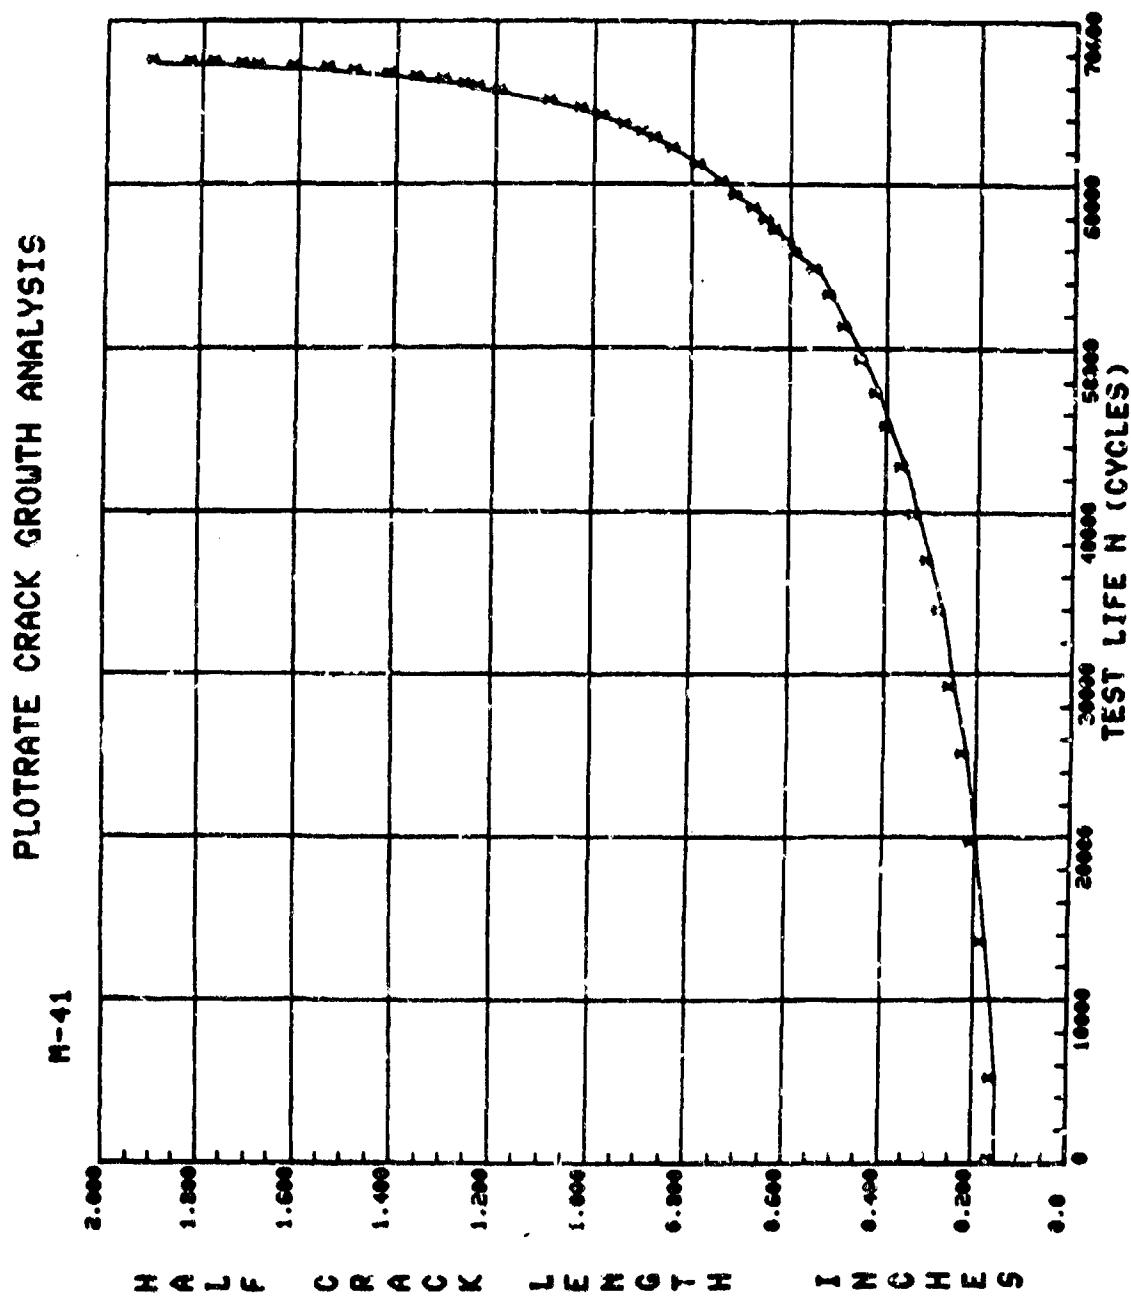


Figure 55. Crack growth curve for test M-41.

TABLE 54. DATA TABULATION FOR TEST M-42

SPECIMEN NO.:	CCT	SPFCMEN	R= 0.250 IN.	H= 0.000 IN.	A= 0.0 IN.	TEST FREQ= 6.00 Hz.
	PWLN=		P MAX=			
ENVIRONMENT CONDITION: AMBIENT AIR						
NO.	CYCLE	AI MEASURED	AI REGRESSION	MULT. CORR.	Coeff	DELTA K
1	0.	0.310	0.309	0.99740	13.97	6.90
2	5000.	0.310	0.315	0.998059	14.09	7.05
3	15000.	0.375	0.371	0.999318	15.31	4.34E-06
4	21000.	0.435	0.435	0.999058	16.58	4.381E-06
5	25500.	0.495	0.500	0.998247	17.80	6.399E-06
6	29100.	0.555	0.558	0.999554	18.82	8.154E-06
7	31800.	0.615	0.616	0.999968	19.79	9.961E-06
8	34200.	0.675	0.674	0.999975	20.74	10.37
9	36400.	0.735	0.735	0.999984	21.68	10.84
10	38400.	0.795	0.795	0.999996	22.58	11.29
11	40300.	0.855	0.854	0.999514	23.45	11.72
12	42100.	0.915	0.914	0.997976	24.31	12.15
13	43800.	0.975	0.980	0.998792	25.22	12.61
14	45100.	1.035	1.039	0.999442	26.00	2.511E-05
15	46200.	1.100	1.095	0.999518	26.77	13.38
16	47350.	1.160	1.162	0.998990	27.64	2.774E-05
17	48260.	1.220	1.218	0.998979	28.37	14.18
18	49350.	1.295	1.301	0.999473	29.41	14.71
19	50090.	1.365	1.361	0.999349	30.17	15.09
20	50640.	1.410	1.409	0.999180	30.77	15.38
21	51280.	1.470	1.473	0.999360	31.57	15.78
22	51860.	1.535	1.534	0.999568	32.31	16.16
23	52690.	1.645	1.641	0.999650	33.62	16.81
24	53480.	1.755	1.761	0.999250	35.09	17.54
25	54160.	1.865	1.865	0.999504	36.60	8.598E-05
26	54670.	1.985	1.989	0.999152	37.88	18.30
27	55050.	2.065	2.079	0.997678	38.99	18.94
28	55580.	2.190	2.202	0.998819	40.53	1.339E-04
						20.26
						1.568E-04

TABLE 54. DATA TABULATION FOR TEST M-42 (CONCL)

SPECIMEN NO.: 4-42

CCT SPECIMEN R = 0.250 IN.

W = 0.000 IN.

A = 0.0 IN.

IN.

P MAX =

TEST FREQ = 6.000 Hz.

ENVIRONMENT CONDITIONS: AMBIENT AIR

NO.	CYCLES	(MEASURED)	(REGRESSION)	MULT. (NRP.)	Coeff	K-MAX	DATA K	DATA N
29	55890.	2.325	2.330	0.999107	42.16	21.08	1.823E-04	
30	56140.	2.435	2.423	0.999283	43.36	21.68	2.027E-04	
31	56510.	2.560	2.566	0.999414	45.55	22.77	2.342E-04	
32	56777.	2.685	2.689	0.998720	46.95	23.48	2.627E-04	
33	56885.	2.775	2.770	0.999458	48.10	24.05	2.966E-04	
34	57148.	2.920	2.929	0.998204	50.42	25.21	3.525E-04	
35	57278.	3.025	3.017	0.998109	51.76	25.88	4.079E-04	
36	57443.	3.145	3.157	0.995756	53.99	27.00	5.157E-04	
37	57591.	3.305	3.309	0.987023	56.54	28.27	7.329E-04	
38	57710.	3.460	3.499	0.990316	59.99	29.99	1.013E-03	
39	57772.	3.555	3.626	0.993110	62.49	31.25	1.259E-03	
40	57829.	3.795	3.794	0.999245	66.05	33.03	1.849E-03	

PLOTRATE CRACK GROWTH ANALYSIS

M-42

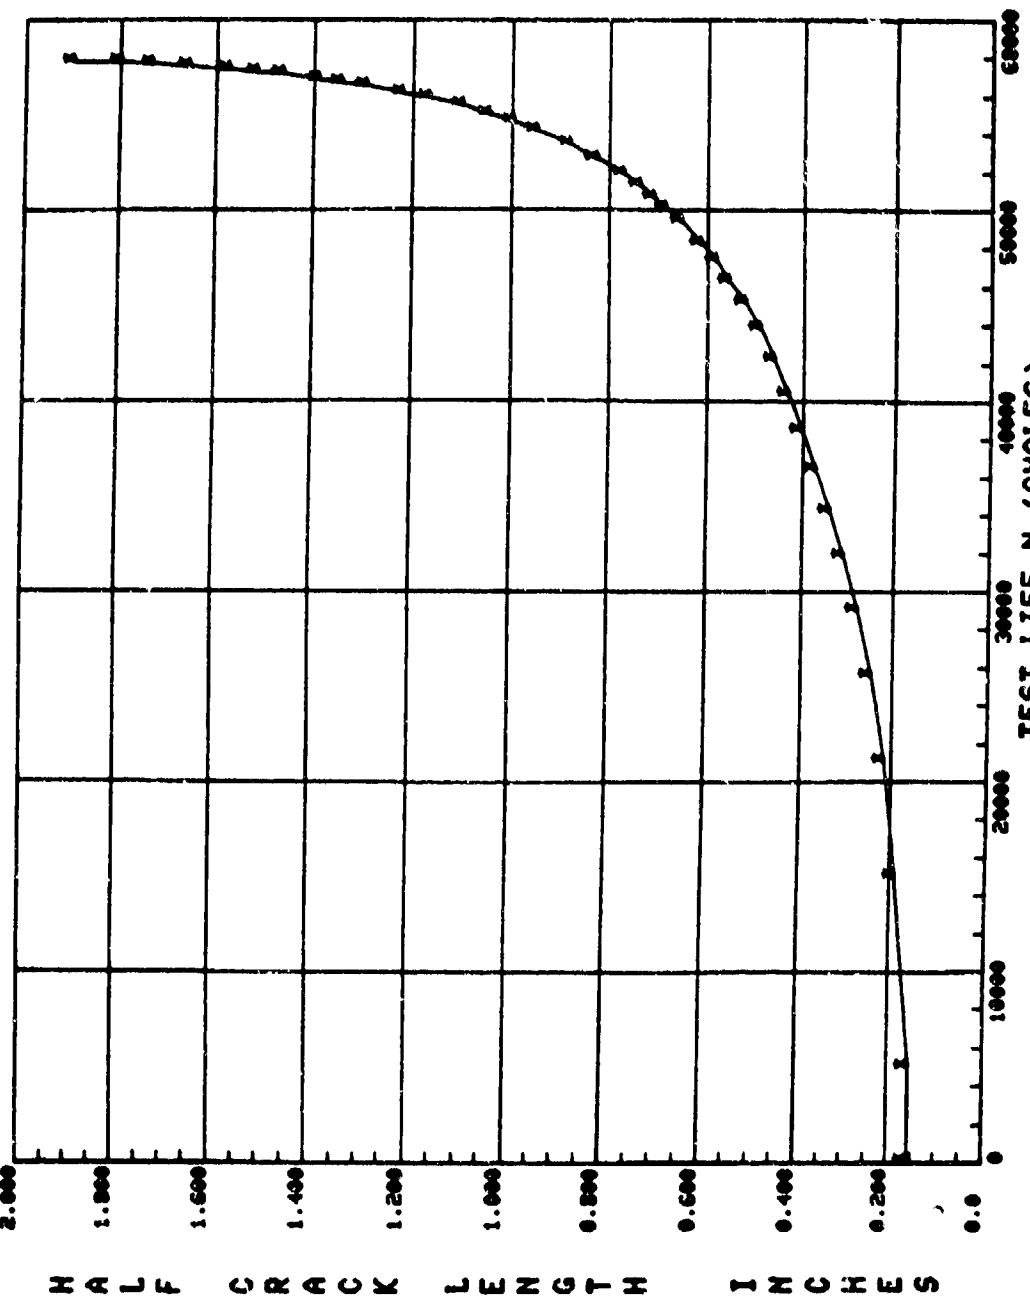


Figure 56. Crack growth curve for test M-42.

TABLE 55. DATA TABULATION FOR TEST M-45

SPECIMEN NO. : M-43

CCT SPECIMEN R = 0.250 IN. W = 6.000 IN. ΔR = 0.1" TEST FREQUENCIES

ENVIRONMENT CONDITION: AMBIENT AIR

CYCLES	AIR MEASURED	AIR FGRESSICN	"ULT.	CIPR.	COEFF	K-MAX	DELTA K	DA/DN
0.	0.315	0.315	0.999543	14.09	14.09	8.613E-06		
7800.	0.400	0.395	0.998735	15.79	15.79	2.018E-05		
9500.	0.475	0.481	0.998202	17.56	17.46	2.863E-05		
10750.	0.545	0.555	0.997091	18.77	18.77	3.472E-05		
11500.	0.605	0.604	0.995119	19.61	19.60	4.238E-05		
12265.	0.670	0.673	0.999533	20.71	20.71	5.032E-05		
12800.	0.725	0.728	0.996337	21.57	21.57	5.705E-05		
13100.	0.775	0.774	0.999572	22.27	22.27	6.102E-05		
13700.	0.840	0.840	0.997654	23.24	23.24	7.074E-05		
13970.	0.880	0.878	0.996506	23.80	23.80	7.786E-05		
14420.	0.940	0.953	0.991879	24.95	24.85	1.041E-04		
14578.	0.985	0.984	0.995449	25.27	25.27	1.034E-04		
14728.	1.015	1.016	0.985974	25.71	25.71	1.114E-04		
14928.	1.085	1.071	0.987821	26.45	26.45	1.184E-04		
15128.	1.100	1.113	0.985305	27.00	27.00	1.177E-04		
15328.	1.170	1.158	1.0984117	27.58	27.58	1.278E-04		
15528.	1.195	1.204	0.961999	28.18	28.18	1.455E-04		
15728.	1.265	1.269	0.992846	29.02	29.02	1.720E-04		
15978.	1.325	1.319	0.995475	29.65	29.65	1.919E-04		
15978.	1.365	1.364	0.998866	30.21	30.21	2.010E-04		
16078.	1.405	1.405	0.999881	30.73	30.73	2.047E-04		
16178.	1.445	1.445	0.999699	31.22	31.22	2.117E-04		
16278.	1.490	1.486	0.999245	31.73	31.73	2.231E-04		
16378.	1.530	1.531	0.999595	32.26	32.26	2.374E-04		
16578.	1.630	1.631	0.999349	33.51	33.51	2.652E-04		
16728.	1.725	1.722	0.998743	34.61	34.61	3.181E-04		
16828.	1.785	1.789	0.998635	35.43	35.43	3.667E-04		
16928.	1.861		0.998222	36.31	36.31	3.772E-04		

SPECIMEN NO.: 4-43

TABLE 55. DATA TABULATION FOR TEST M-43 (CONCL)

No.	CYCLES	A(MEASURED)	A(PERGRSSICNI)	MULT. CORR. COEFF	K-MAX	DELTA K	DATA
ENVIRONMENT CONDITION: AMBIENT AIR							
29	16978.	1.890	1.899	0.998118	36.77	36.77	3.904E-04
30	17053.	1.960	1.959	0.997916	37.51	37.51	4.213E-04
31	17128.	2.025	2.021	0.998410	38.27	38.27	4.591E-04
32	17203.	2.050	2.096	0.999113	39.20	39.20	5.029E-04
33	17251.	2.145	2.145	0.999466	39.92	39.92	5.306E-04
34	17303.	2.205	2.200	0.998200	40.51	40.51	5.899E-04
35	17343.	2.245	2.250	0.996404	41.13	41.13	5.965E-04
36	17380.	2.250	2.293	0.993980	41.69	41.69	6.809E-04
37	17400.	2.330	2.318	0.995436	42.01	42.01	7.258E-04
38	17425.	2.345	2.358	0.993326	42.53	42.53	7.723E-04
39	17470.	2.435	2.433	0.993316	43.50	43.50	8.293E-04
40	17495.	2.485	2.476	0.993124	44.06	44.06	8.305E-04
41	17520.	2.515	2.516	0.990327	44.60	44.60	9.676E-04
42	17545.	2.560	2.566	0.990979	45.26	45.26	9.679E-04
43	17570.	2.600	2.608	0.993317	45.84	45.84	9.981E-04
44	17620.	2.745	2.717	0.995035	47.34	47.34	1.231E-03
45	17670.	2.825	2.862	0.993421	49.14	49.14	1.577E-03
46	17720.	3.010	3.015	0.986681	51.73	51.73	2.272E-03
47	17750.	3.125	3.146	0.979146	53.81	53.81	3.321E-03
48	17780.	3.305	3.367	0.978574	57.57	57.57	6.731E-03
49	17800.	3.510	3.571	0.987560	61.38	61.38	7.203E-03
50	17809.	3.703	3.703	0.991863	64.08	64.08	9.880E-03

PLOT RATE CRACK GROWTH ANALYSIS

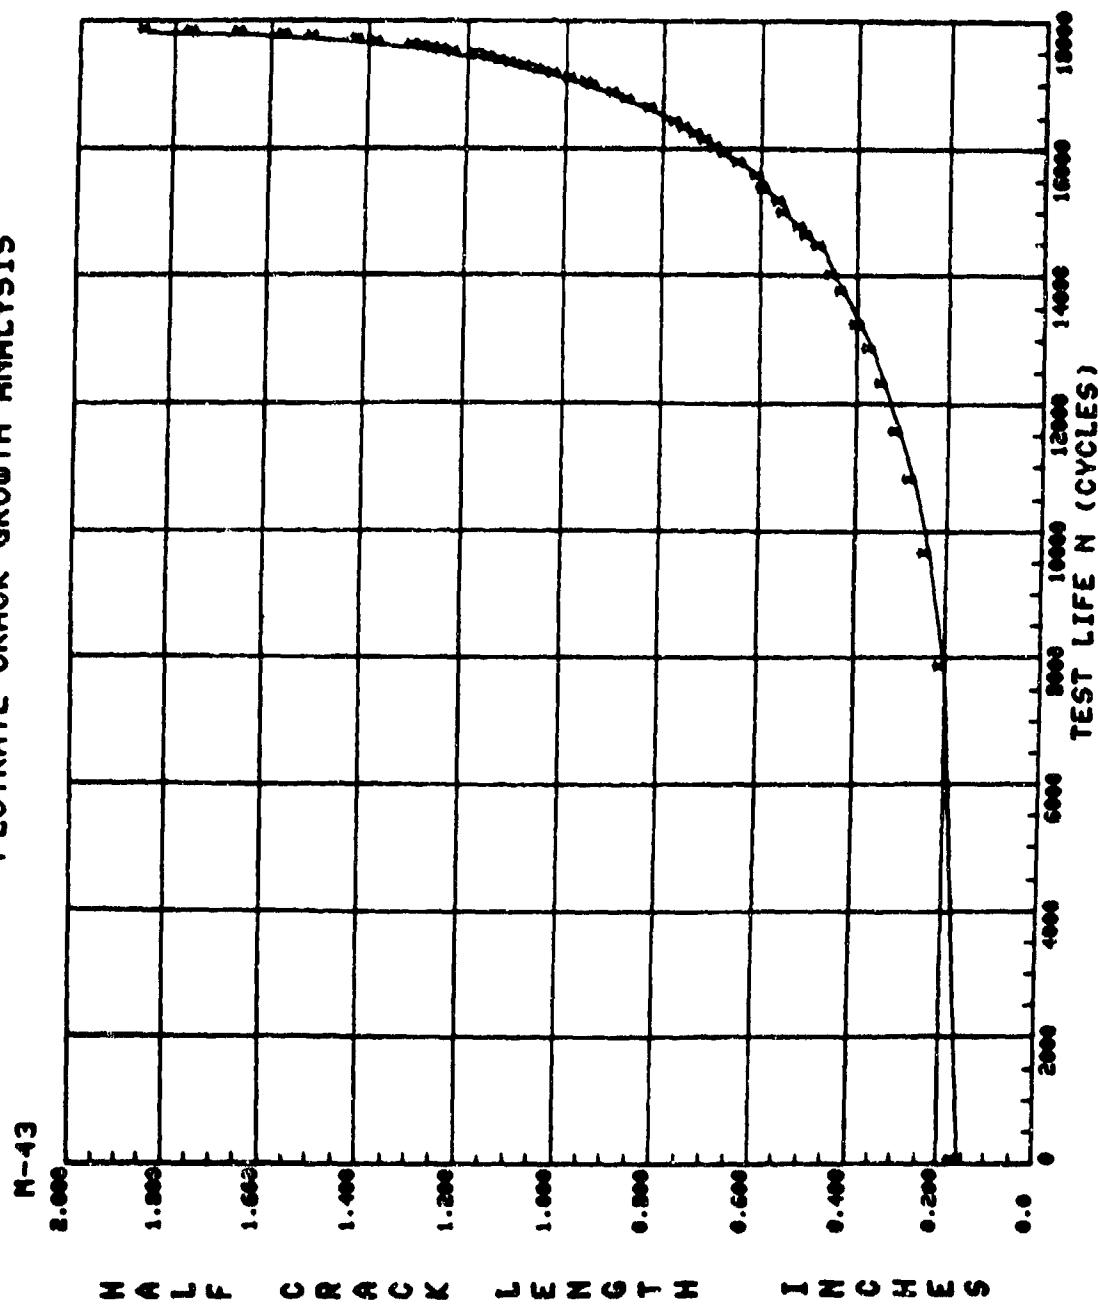


Figure 57. Crack growth curve for test N-43.

TABLE 56. DATA TABULATION FOR LIST N-44

SPECimen No.: N-44

TEST FREQ= 6.00 Hz.

ΔH = 1.0 IN.

w = 6.000 IN.

PMIN=

PMAX=

ENVIRONMENT CONDITION: AMBIENT AIR

No.	CYCLES	TIME AS SPEED	AMBIENT AIR REGRESSION(1)	MULT. CORR. COEFF	K-MAX	DATA
1	1.0	0.305	0.305	0.999992	13.86	2.60E-04
2	5.0	0.330	0.332	0.998255	14.47	2.60E-04
3	12.5	0.365	0.364	0.968082	14.94	1.982E-04
4	22.5	0.405	0.389	0.972113	15.67	2.532E-04
5	32.5	0.420	0.472	0.932581	17.29	17.29
6	42.5	0.515	0.466	0.568418	17.16	2.682E-05
7	50.0	0.610	0.504	0.616340	17.88	4.197E-06
8	51.00	0.620	0.548	0.762981	18.65	18.65
9	741.00	0.635	0.640	0.915411	20.19	20.19
10	381.00	0.755	0.780	0.962777	22.36	22.36
11	413.00	0.810	0.848	0.943919	23.36	23.36
12	424.00	0.965	0.996	0.978235	24.05	24.05
13	451.00	0.950	0.959	0.992579	24.93	24.93
14	462.00	1.020	1.030	1.004586	25.90	25.90
15	468.00	1.075	1.083	0.994864	26.61	5.687E-05
16	474.00	1.145	1.150	0.998810	27.48	7.216E-05
17	479.50	1.230	1.234	0.997552	28.57	9.600E-05
18	482.60	1.255	1.295	0.997684	29.35	1.174E-05
19	485.30	1.350	1.360	0.998789	30.16	1.403E-05
20	487.40	1.425	1.422	0.999094	30.93	1.645E-05
21	489.25	1.485	1.480	0.998477	31.65	1.913E-05
22	491.70	1.575	1.573	0.983098	32.79	2.725E-05
23	493.72	1.675	1.690	0.978641	34.23	3.140E-05
24	495.43	1.785	1.807	0.978117	35.65	3.538E-05
25	496.88	1.950	1.922	0.978558	37.06	3.937E-05
26	498.12	1.955	2.028	0.975703	38.37	4.371E-05
27	499.20	2.100	2.122	0.970063	39.52	4.958E-05
28	500.05	2.200	2.187	0.995798	40.34	5.992E-05

TABLE 56. DATA TABULATION FOR TEST M-44 (CONCL)

SPECIMEN NO.: 4-44	CCT SPECIMEN	θ = 0.250 IN.	W = 6.000 lb.	ΔR = 0.01	IN.	TEST FREQ = 0.001 Hz.	
						P MAX =	
ENVIRONMENT CONDITIONS: AMBIENT AIR							
NO.	CYCLES	AM MEASUPED!	AM REGRESSION!	MULT.	CIPR.	COEFF	K-MAX
29	50086.	2.300	2.302	0.999166	41.80	7.26E-04	
30	50150.	2.350	2.396	0.999013	43.01	8.472E-04	
31	50205.	2.490	2.490	0.999750	44.26	9.771E-04	
32	50255.	2.590	2.591	0.999363	45.61	1.151E-03	
33	50298.	2.655	2.694	0.997710	47.03	1.388E-03	
34	50337.	2.795	2.805	0.997452	48.60	1.727E-03	
35	50365.	2.855	2.903	0.998664	50.03	2.068E-03	
36	50388.	3.000	2.999	0.998954	51.48	2.512E-03	
37	50409.	3.110	3.109	0.996078	53.21	3.142E-03	
38	50427.	3.210	3.225	0.994396	55.12	4.063E-03	
39	50442.	3.335	3.354	0.984738	57.33	6.009E-03	
40	50450.	3.435	3.444	0.990977	58.96	7.725E-03	
41	50459.	3.555	3.593	0.993219	61.81	1.040E-02	
42	50465.	3.735	3.733	0.994362	64.71	1.444E-02	

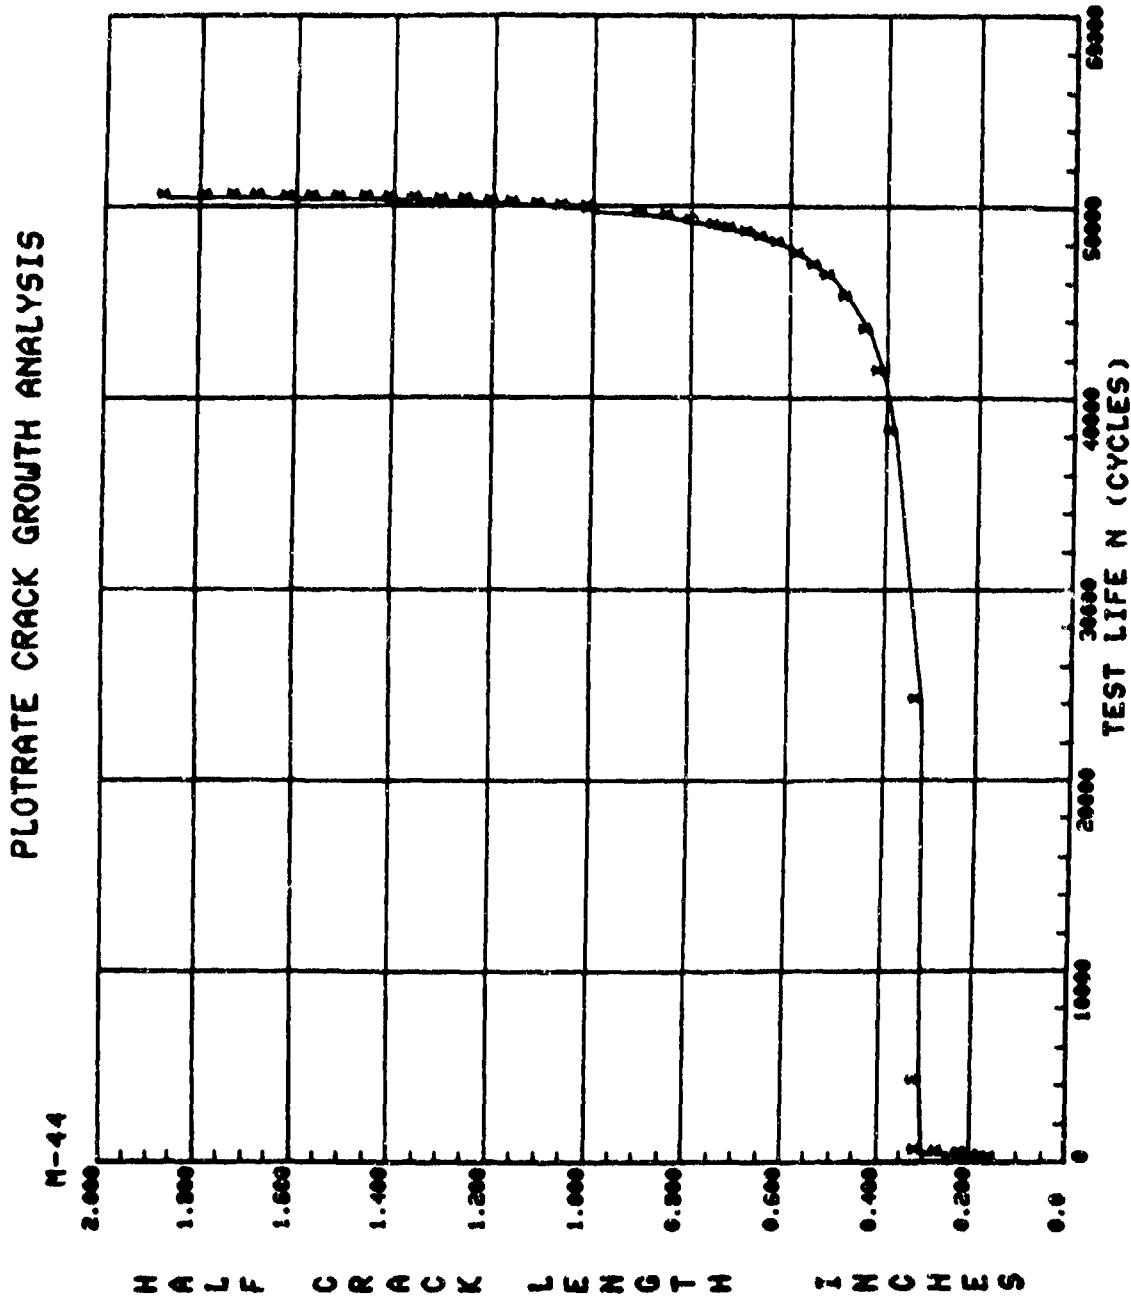


Figure 58. Crack growth curve for test M-44.

TABLE 57. DATA TABULATION FOR TEST M-45

SPECIMEN NO.: 4-45

CCT SPECIMEN R= 0.250 IN. W= 6.000 IN. AN= 0.0 IN.
 P_{MIN} P_{MAX} TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	AM MEASURED	AM REGRSSION	MULT.	CURR. COEFF	K-MAX	DLTA K	DA/DN
1	0.	0.260	0.290	0.998862	13.52	9.47	2.235E-05	
2	800.	0.335	0.330	0.998811	14.43	10.10	2.921E-05	
3	1300.	0.360	0.361	0.999053	15.09	10.56	3.513E-05	
4	2100.	0.440	0.444	0.999121	16.76	11.73	6.851E-05	
5	2800.	0.495	0.516	0.970854	17.91	12.54	3.887E-05	
6	3300.	0.555	0.513	0.714755	18.03	12.62	2.332E-05	
7	3370.	0.565	0.505	0.794342	17.89	12.52	3.056E-06	
8	10961.	0.565	0.544	0.927139	19.26	13.48	2.389E-05	
9	12739.	0.655	0.690	0.991185	20.83	14.58	3.469E-05	
10	13802.	0.755	0.754	0.984280	21.97	15.38	3.744E-05	
11	13902.	0.760	0.771	0.997139	22.23	15.56	3.455E-05	
12	14602.	0.820	0.817	0.996423	22.91	16.04	3.614E-05	
13	15302.	0.860	0.862	0.995665	23.57	16.50	3.594E-05	
14	16302.	0.940	0.917	0.999274	24.62	17.23	4.145E-05	
15	16802.	0.975	0.979	0.999012	25.21	17.64	4.689E-05	
16	17302.	1.030	1.028	0.998610	25.86	18.10	5.358E-05	
17	17802.	1.018	1.000	0.994771	26.56	18.59	6.425E-05	
18	18302.	1.145	1.152	0.989223	27.51	19.26	6.833E-05	
19	18602.	1.220	1.225	0.989128	28.45	19.91	7.357E-05	
20	18902.	1.265	1.241	0.989148	28.66	20.06	7.812E-05	
21	19402.	1.305	1.319	0.986660	29.64	20.75	8.805E-05	
22	19702.	1.365	1.370	0.992458	30.28	21.20	9.216E-05	
23	20002.	1.430	1.426	0.996439	30.50	21.69	1.004E-04	
24	20302.	1.505	1.495	0.998704	31.84	22.29	1.173E-04	
25	20862.	1.625	1.622	0.998622	33.52	23.46	1.389E-04	
26	21197.	1.725	1.726	0.999277	34.67	24.27	1.582E-04	
27	21499.	1.825	1.824	0.999925	35.86	25.10	1.807E-04	
28	21790.	1.935	1.916	0.99988811	37.22	26.06	2.051E-04	

TABLE 57. DATA TABULATION FOR TEST M-45 (CONCL)

CYCLES	A(MEASURFD)	A(RFGRESSION)	#ULT.	CQR,	COEFF	K-MAX	DELTA K	DATA
ENVIRONMENT CONDITION: AMBIENT AIR								
29	22040.	2.040	2.042	0.999907	38.53	26.97	2.303E-04	
30	22286.	2.160	2.159	0.999577	39.99	27.99	2.630E-04	
31	22495.	2.270	2.272	0.999447	41.42	28.99	3.030E-04	
32	22669.	2.375	2.381	0.999663	42.82	29.97	3.361E-04	
33	22818.	2.485	2.483	0.999288	44.16	30.91	3.797E-04	
34	22959.	2.600	2.594	0.998505	45.65	31.95	4.366E-04	
35	23097.	2.705	2.719	0.997754	47.38	33.17	5.182E-04	
36	23192.	2.815	2.818	0.998447	48.79	34.16	5.915E-04	
37	23267.	2.910	2.908	0.998937	50.11	35.08	6.915E-04	
38	23324.	2.995	2.951	0.998748	51.36	35.96	7.714E-04	
39	23388.	3.080	3.052	0.998949	52.94	37.06	8.768E-04	
40	23442.	3.155	3.1P9	0.999226	54.52	38.16	9.946E-04	
41	23484.	3.275	3.273	0.996455	55.93	39.15	1.166E-03	
42	23521.	3.360	3.3t3	0.991345	57.50	40.25	1.458E-03	
43	23561.	3.460	3.480	0.985446	59.64	41.74	2.092E-03	
44	23591.	3.590	3.614	0.989326	62.25	43.57	2.977E-03	
45	23606.	3.685	3.707	0.995235	64.15	44.91	3.936E-03	
46	23617.	3.805	3.804	0.998174	66.27	46.39	5.269E-03	

PLOTRATE CRACK GROWTH ANALYSIS

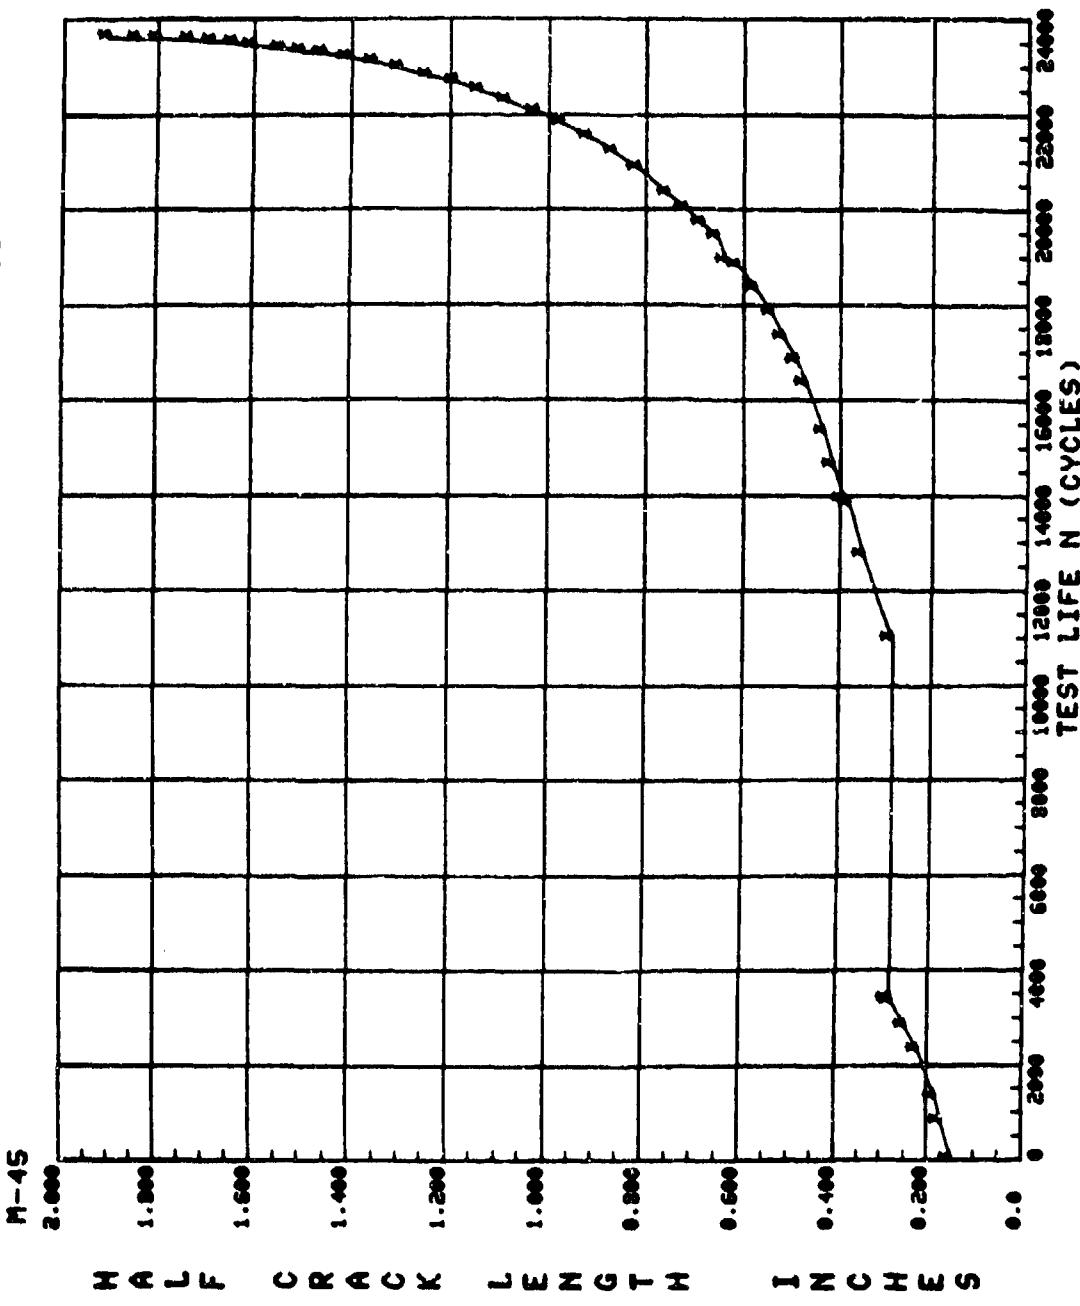


Figure 59. Crack growth curve for test M-45.

TABLE 58. DATA TABULATION FOR TEST M-46

SPECIMEN NO.:	SPFC(MFN)	R= 0.250 IN.	H= 6.000 IN.	AN= 0.0 IN.	TEST FREQ= 6.00 Hz.	ENVIRONMENT CONDITION: AMBIENT AIR		DELTA K	DA/DN
						PIN=	P MAX=		
1	CYCLES	ALMEASUREMENT	REFLECTION	MULT.	CURR. COEFF	K-MAX	9.56	8.52E-05	
1	0.	0.300	0.296	0.996324	13.66	10.06	6.43E-07		
2	370.	0.355	0.329	0.635731	14.40	10.19	4.602E-07		
3	500.	0.390	0.326	0.743231	14.56	12.18	1.297E-06		
4	6760.	0.400	0.329	0.792575	15.87	12.45	1.769E-06		
5	112800.	0.435	0.478	0.751154	17.40	12.38	1.326E-05		
6	114650.	0.465	0.499	0.647542	17.78	13.46	1.747E-05		
7	115650.	0.480	0.494	0.985664	17.69	13.90	1.823E-05		
8	117650.	0.550	0.542	0.994762	18.54	14.11	1.737E-05		
9	118800.	0.575	0.582	0.994726	19.23	14.38	1.939E-05		
10	119800.	0.625	0.619	0.995486	19.85	15.66	2.407E-05		
11	120300.	0.635	0.638	0.990435	20.16	16.18	2.966E-05		
12	121000.	0.665	0.662	0.986527	20.54	14.67	3.544E-05		
13	121100.	0.655	0.658	0.993590	20.96	15.13	2.407E-05		
14	122800.	0.720	0.730	0.994566	21.61	17.24	3.45E-05		
15	123800.	0.785	0.780	0.997297	22.37	16.66	4.531E-05		
16	124600.	0.830	0.831	0.997705	23.11	17.49	4.671E-05		
17	125100.	0.870	0.870	0.996754	23.68	16.58	4.051E-05		
18	125501.	0.900	0.901	0.993434	24.12	16.88	4.180E-05		
19	125900.	0.925	0.937	0.991526	24.63	17.24	4.345E-05		
20	126200.	0.975	0.964	0.992375	24.99	17.49	4.531E-05		
21	126400.	0.975	0.982	0.995410	25.24	17.67	4.482E-05		
22	126500.	0.950	0.950	0.996610	25.35	17.75	5.182E-05		
23	127200.	1.065	1.057	0.997793	26.26	18.38	6.541E-05		
24	128120.	1.145	1.150	0.998505	27.48	19.24	7.163E-05		
25	129420.	1.200	1.204	0.998864	28.18	19.73	7.974E-05		
26	12AB40.	1.275	1.266	0.998798	28.98	20.28	8.458E-05		
27	129130.	1.312	1.316	0.998934	29.61	20.72	9.453E-05		
28	129400.	1.360	1.361	0.996512	30.18	21.12			

TABLE 58. DATA TABULATION FOR TEST M-46 (CONCL.)

SPHERICAL 40.: CYCLES	SPECIMEN NO.	R= 0.750 IN. Pmax=	W= 6.000 LB. TEST Freq = 6.00 Hz.	A _N = 0.0 IN.	ENVIRONMENT CONDITION: AMBIENT AIR		MULT. CORR. COEFF	K-MAX	DEFLA K	DA/DN
					A(MEASURED)	A(PRESSURE)				
79	129660.	1.410	1.409	0.998876	30.77	21.54	1.017E-04			
80	129900.	1.455	1.461	0.999281	31.42	21.99	1.138E-04			
31	130140.	1.525	1.518	0.999467	32.12	22.49	1.242E-04			
32	130570.	1.630	1.633	0.999572	33.53	23.47	1.442E-04			
33	130930.	1.745	1.742	0.999741	34.86	24.40	1.651E-04			
34	131240.	1.845	1.846	0.999434	36.13	25.29	1.887E-04			
35	131520.	1.950	1.956	0.999513	37.47	26.23	2.147E-04			
36	131770.	2.065	2.066	0.999919	38.83	27.18	2.356E-04			
17	132000.	2.185	2.181	0.999672	40.27	28.19	2.718E-04			
18	132200.	2.255	2.292	0.990117	41.67	29.17	3.156E-04			
39	132390.	2.405	2.414	0.998892	43.25	30.27	3.583E-04			
40	132570.	2.540	2.546	0.999495	45.00	31.50	4.119E-04			
41	132750.	2.715	2.705	0.998663	47.18	33.02	5.009E-04			
42	132850.	2.800	2.811	0.996786	48.69	34.08	5.884E-04			
43	132910.	2.865	2.881	0.996669	49.71	34.80	6.599E-04			
44	132970.	2.960	2.956	0.998905	50.84	35.59	7.437E-04			
45	133020.	3.045	3.035	0.997908	52.04	36.43	8.646E-04			
46	133070.	3.120	3.124	0.996897	53.44	37.41	1.012E-03			
47	133120.	3.215	3.221	0.996117	55.05	38.54	1.245E-03			
48	133170.	3.350	3.351	0.995966	57.27	40.09	1.680E-03			
49	133210.	3.475	3.499	0.988853	55.99	41.99	2.391E-03			
50	133235.	3.600	3.625	0.989142	62.47	43.73	3.159E-03			
51	133252.	3.710	3.739	0.993794	64.95	45.40	4.336E-03			
52	133260.	3.820	3.817	0.994577	66.57	46.60	5.740E-03			

PLOTRATE CRACK GROWTH ANALYSIS

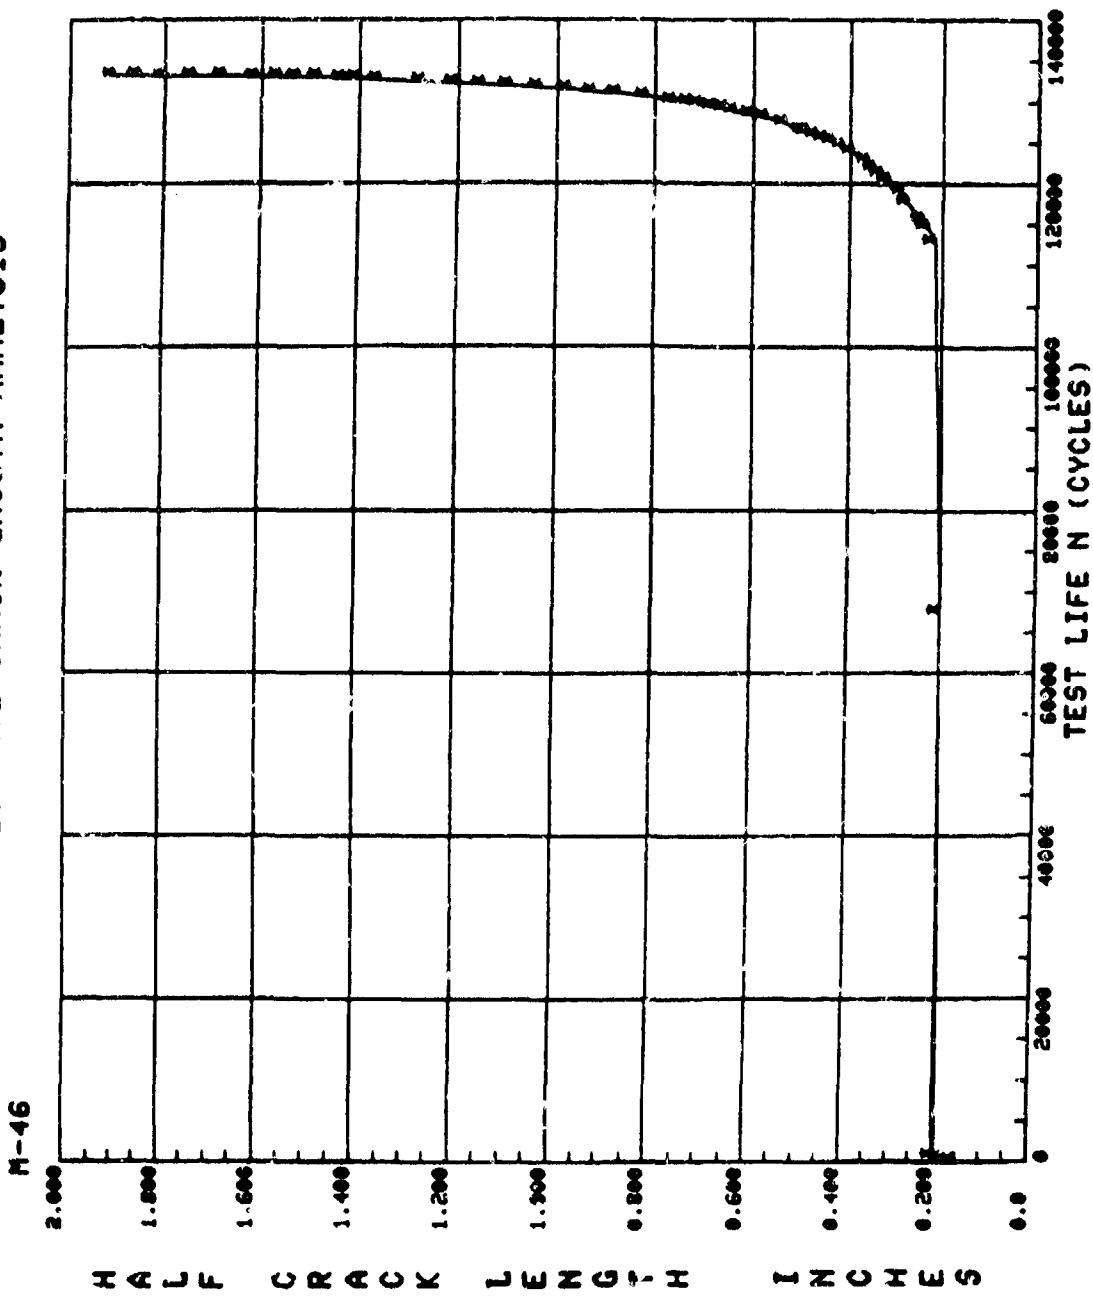


Figure 60. Crack growth curve for test M-46.

TABLE 59. DATA TABULATION FOR TEST M-47

SPECIMEN NO.: 4-47	CCT SPECIFICATION	R= 0.250 IN.	w= 6.000 IN.	AA= 0.01 IN.	TEST FREQ= 6.000 Hz.	ENVIRONMENT CONDITION: AMBIENT AIR		MULT. COEFF	K-MAX	DELTA K	DATA
						PMIN	PMAX				
1	0.	0.305	0.306	0.994298	13.89	4.17	5.352E-05				
2	200.	0.335	0.321	0.734712	14.23	4.27	4.008E-05				
3	500.	0.355	0.332	0.491300	14.48	4.34	2.214E-06				
4	16200.	0.430	0.375	0.902142	15.38	4.61	9.232E-07				
5	89200.	0.475	0.491	0.934685	17.64	5.29	1.147E-06				
6	105700.	0.520	0.529	0.953108	18.31	5.49	1.563E-06				
7	122400.	0.575	0.580	0.993031	19.19	5.76	1.920E-06				
8	132100.	0.625	0.622	0.990729	19.89	5.97	2.219E-06				
9	141200.	0.675	0.664	0.987996	20.58	6.17	2.549E-06				
10	152737.	0.705	0.727	0.985266	21.55	6.47	3.094E-06				
11	157737.	0.760	0.755	0.989668	21.98	6.59	3.612E-06				
12	162737.	0.795	0.790	0.993117	22.51	6.75	4.055E-06				
13	167737.	0.835	0.839	0.997392	23.22	6.97	4.679E-06				
14	172737.	0.885	0.883	0.999916	23.86	7.16	5.004E-06				
15	177737.	0.935	0.936	0.999933	24.61	7.38	5.589E-06				
16	182737.	0.955	0.953	0.998783	25.39	7.62	6.429E-06				
17	187737.	1.060	1.058	0.998631	26.27	7.88	7.509E-06				
18	192737.	1.130	1.137	0.998350	27.31	8.19	9.097E-06				
19	197737.	1.230	1.234	0.998415	28.56	8.57	1.174E-05				
20	200447.	1.295	1.299	0.999466	29.40	9.82	1.402E-05				
21	201951.	1.340	1.343	0.999563	29.94	9.98	1.567E-05				
22	203526.	1.395	1.395	0.999977	30.60	9.18	1.856E-05				

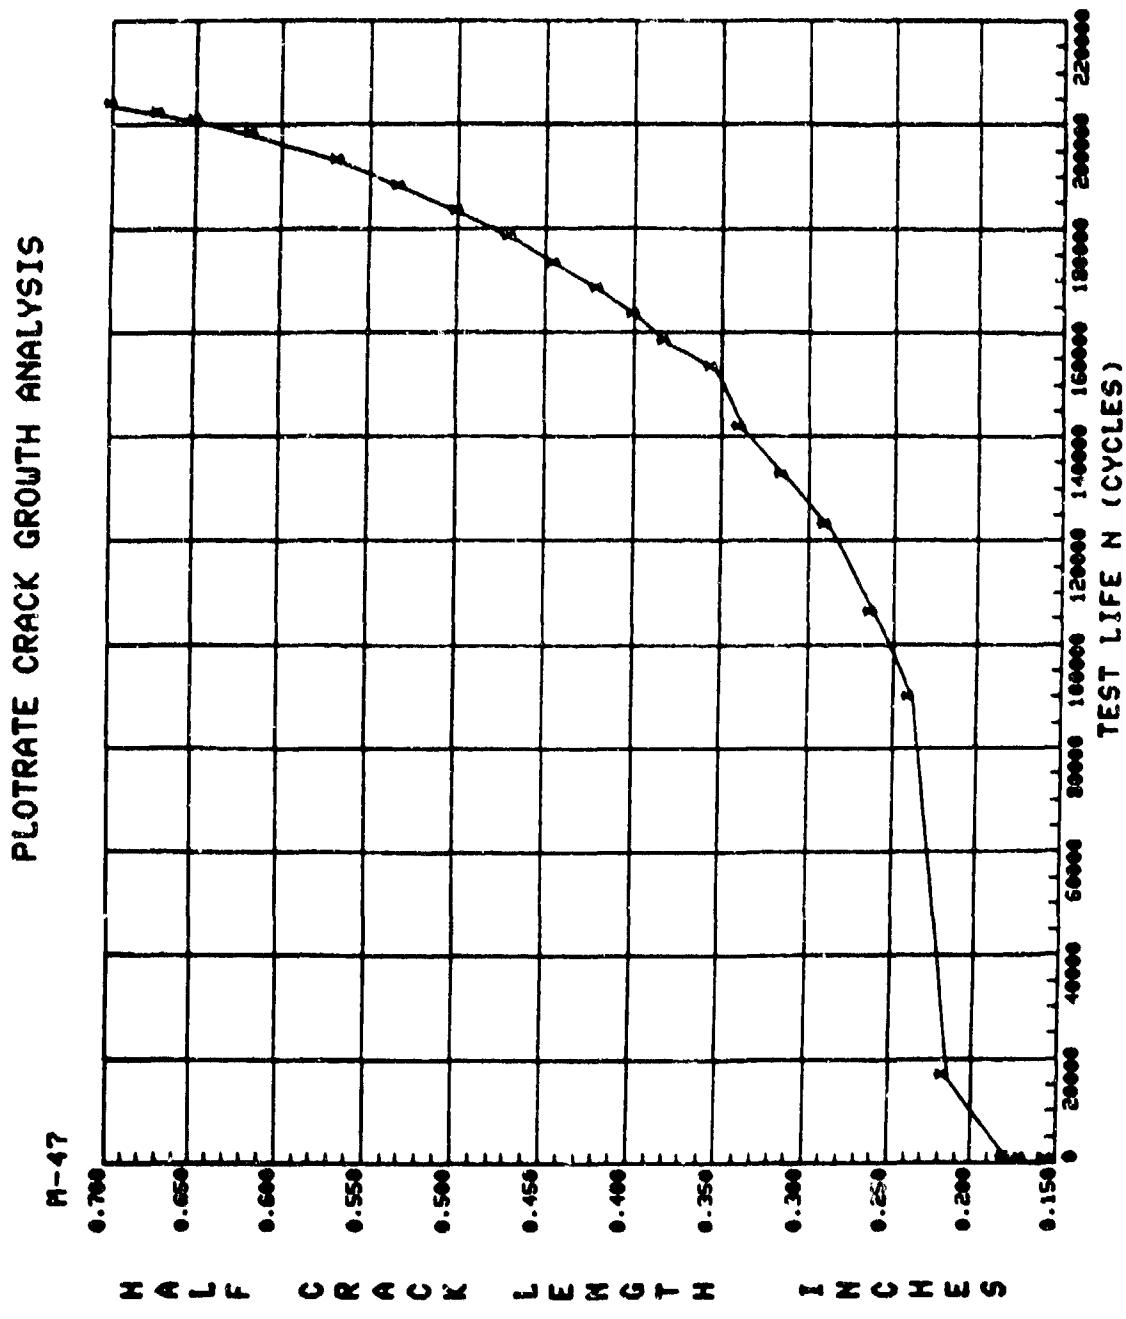


Figure 61. Crack growth curve for test M-47.

TABLE 60. DATA TABULATION FOR TEST M-48

SPECIMEN NO.: 4-4A

CUT SPECIMEN A = 0.250 IN.

P/N=

R MAX=

TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	AS MEASURED	REGRESSION	MULT. COEFF	K-MAX	DELTA K	DA/DN
1	0.	0.315	0.314	0.985385	28.13	6.44	7.76E-05
2	100.	0.345	0.341	0.941692	29.33	8.80	2.48E-05
3	500.	0.350	0.350	0.962777	29.70	8.91	1.77E-05
4	3000.	0.440	0.437	0.977139	33.24	9.97	2.08E-05
5	5000.	0.520	0.529	0.990948	36.63	10.99	2.872E-05
6	6000.	0.590	0.589	0.997955	38.71	11.61	3.612E-05
7	7000.	0.665	0.667	0.997979	41.26	12.38	4.668E-05
8	7500.	0.705	0.713	0.995239	42.69	12.81	5.781E-05
9	8000.	0.710	0.769	0.998356	44.41	13.32	6.917E-05
10	9500.	0.835	0.840	0.999481	46.50	13.95	8.440E-05
11	9000.	0.935	0.933	0.996624	49.13	14.74	1.072E-04
12	9250.	0.985	0.986	0.998441	50.60	15.18	1.254E-04
13	9500.	1.045	1.050	0.994516	52.32	15.70	1.555E-04
14	9750.	1.125	1.121	0.995301	54.21	16.26	1.997E-04
15	10000.	1.215	1.229	0.997046	57.00	17.10	2.646E-04
16	10200.	1.335	1.342	0.998316	59.68	17.96	3.401E-04
17	10350.	1.455	1.455	0.999996	62.68	18.80	4.392E-04

PLOTRATE CRACK GROWTH ANALYSIS

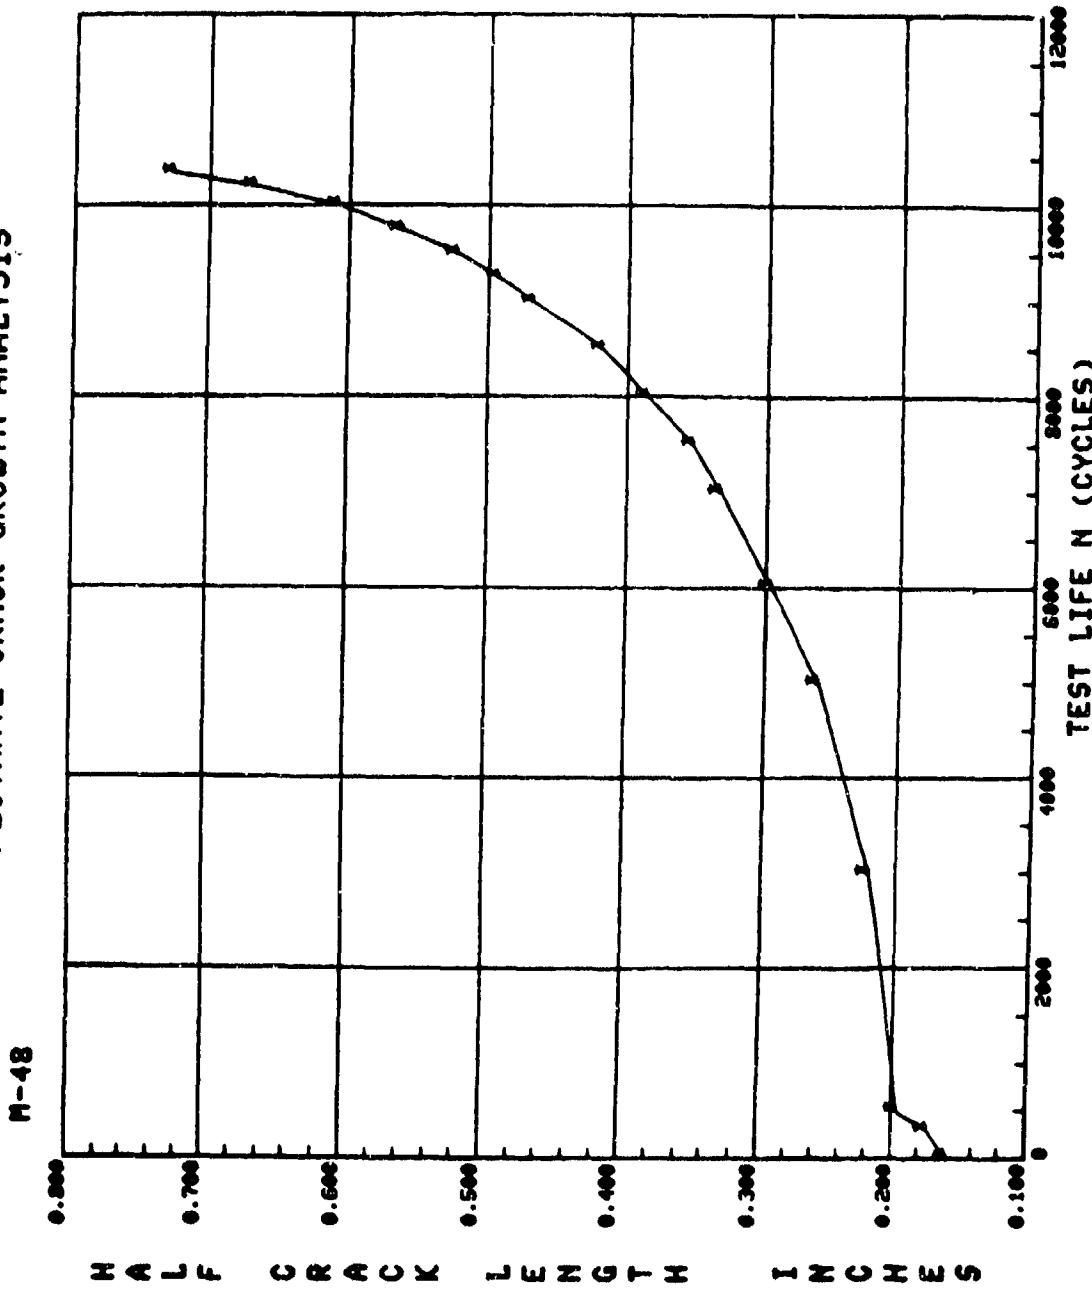


Figure 62. Crack growth curve for test M-48.

TABLE 61. DATA TABULATION FOR TEST M-49

SPECIMEN NO.: M-49

CCV SPECIMEN $\eta = .0250$ IN. $b = 6.000$ IN.
 $\Delta t = 0.0$ IN.
 $\text{PHASE} =$
 $\text{TEST FREQ} = 6.00 \text{ Hz}$.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLFS	ALPHA SUREDI	ALPHASIGN	MULT.	CORR. COEFF	X-MAX	DETAK
1	0.	0.310	0.309	0.997162	13.96	9.77	5.737E-06
2	500.	0.310	0.314	0.998522	14.07	9.85	5.302E-06
3	4057.	0.365	0.359	0.997511	15.04	10.53	6.150E-06
4	7100.	0.415	0.417	0.998045	16.24	11.37	1.154E-05
5	9600.	0.475	0.482	0.997407	17.47	12.23	1.494E-05
6	11120.	0.530	0.527	0.999595	18.28	12.80	1.757E-05
7	12598.	0.580	0.583	0.999588	19.24	13.47	2.019E-05
8	13661.	0.630	0.628	0.999366	19.99	13.99	2.243E-05
9	14821.	0.680	0.681	0.998862	20.84	14.59	2.585E-05
10	15794.	0.730	0.733	0.998935	21.65	15.16	2.864E-05
11	16627.	0.780	0.781	0.999255	22.38	15.67	3.200E-05
12	17270.	0.830	0.825	0.999309	23.02	16.11	3.465E-05
13	18229.	0.850	0.854	0.998529	24.02	16.91	3.975E-05
14	19125.	0.970	0.967	0.998414	25.04	17.53	4.633E-05
15	19197.	1.025	1.031	0.999244	25.91	18.14	5.199E-05
16	20279.	1.085	1.083	0.998004	26.61	18.63	5.824E-05
17	20729.	1.140	1.136	0.998896	27.30	19.11	6.493E-05
18	21208.	1.195	1.202	0.998946	28.16	19.71	7.272E-05
19	21663.	1.270	1.269	0.999420	29.02	20.31	8.166E-05
20	21941.	1.320	1.314	0.998626	29.59	20.71	9.175E-05
21	22329.	1.385	1.389	0.998429	30.52	21.36	1.080E-04
22	22619.	1.445	1.448	0.999514	31.26	21.88	1.214E-04
23	22956.	1.540	1.541	0.998022	32.40	22.68	1.356E-04
24	23323.	1.650	1.649	0.997441	33.72	23.60	1.593E-04
25	23511.	1.720	1.709	0.997297	34.45	24.12	1.732E-04
26	23887.	1.825	1.844	0.997191	36.11	25.27	2.064E-04
27	24115.	1.945	1.937	0.998434	37.24	26.07	2.361E-04
28	24357.	2.055	2.057	0.999135	38.72	27.10	2.762E-04

TABLE 61. DATA TABULATION FOR TEST M-49 (CONTINUED)

SPECIMEN NO.:	CCT	SPECIMEN	R = 0.250 IN.	w = 6.000 IN.	AN = 0.0	IN.	TEST FREQ = 6.000 Hz.	DAY/N	DELTA K
PHI _u		P MAX							
ENVIRONMENT CONDITION: AMBIENT AIR									
NO.	CYCLES	AI(MEASURED)	AI(REGRESS[CN])	MULT.	C _{FR}	C _{EFF}	K-MAX		
29	24531.	2.160	2.160	0.998946	40.01	28.01	3.124E-04		
30	24668.	2.245	2.244	0.999796	41.06	28.74	3.437E-04		
31	24847.	2.370	2.373	0.999255	42.72	29.91	4.044E-04		
32	24993.	2.455	2.495	0.999780	44.32	31.02	4.638E-04		
33	25107.	2.600	2.605	0.999751	45.79	32.06	5.265E-04		
34	25209.	2.720	2.716	0.999668	47.33	33.13	5.936E-04		
35	25302.	2.825	2.828	0.998634	48.94	34.26	6.887E-04		
36	25391.	2.950	2.954	0.998616	50.90	35.56	8.025E-04		
37	25457.	3.055	3.063	0.999511	52.48	35.73	9.242E-04		
38	25504.	3.160	3.151	0.998883	53.91	36.73	1.052E-03		
39	25570.	3.290	3.248	0.989092	56.36	39.45	1.437E-03		
40	25602.	3.375	3.386	0.990037	57.91	40.54	1.754E-03		
41	25639.	3.450	3.523	0.993754	60.46	42.32	2.311E-03		
42	25665.	3.660	3.656	0.996140	63.14	44.20	3.276E-03		

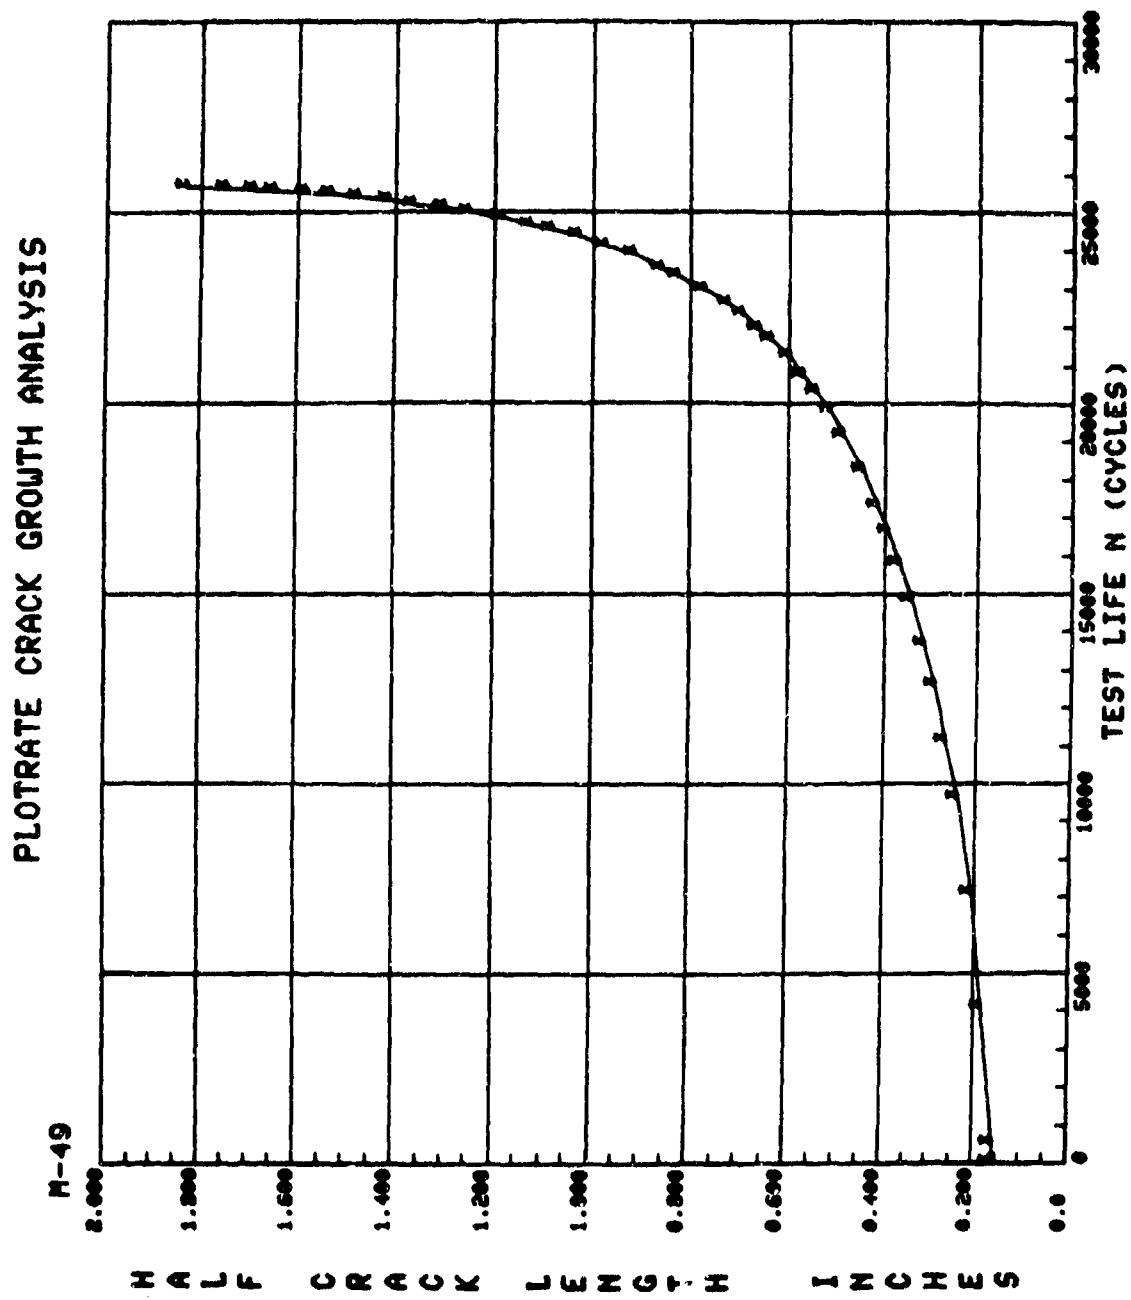


Figure 63. Crack growth curve for test M-49.

TABLE 62. DATA TABULATION FOR TEST M-50

SPECIMEN NO.: M-50	ACT. SPECIMEN	t = 0.760 IN.	W = 6.000 LB IN.	A4 = C.O.	A4 = I.N.	TEST FREQUENCY = 6.00 Hz.	ENVIRONMENT CONDITION: AMBIENT AIR		MULT. CORR. COEFF	K-MAX	DELTA K	DA/DN
							P MIN=	P MAX=				
1	CYCLES	A (MEASURED)	A (REGRESSION)						0.998167	27.96	14.59	7.607E-07
2	0.	0.216	0.310						0.992672	23.54	19.96	3.431E-05
3	500.	0.310	0.323						0.986116	30.85	21.54	9.162E-05
4	1000.	0.375	0.377						0.972000	23.19	23.23	1.447E-04
5	1260.	0.423	0.437						0.960203	34.99	24.48	2.033E-04
6	1430.	0.476	0.483						0.947770	37.30	26.11	2.697E-04
7	1590.	0.545	0.548						0.947814	34.24	27.47	3.195E-04
8	1690.	0.415	0.405						0.947570	40.61	28.57	3.554E-04
9	1750.	0.555	0.653						0.946710	42.23	29.56	3.90E-04
10	1920.	0.550	0.692						0.946153	42.57	20.50	4.606E-04
11	1980.	0.745	0.742						0.946295	44.49	31.49	5.498E-04
12	1990.	0.760	0.759						0.948555	45.71	32.70	6.435E-04
13	2020.	0.910	0.907						0.949100	46.40	33.88	7.541E-04
14	2065.	0.976	0.972						0.949132	40.23	35.14	6.814E-04
15	2100.	1.030	1.037						0.949348	51.99	36.39	1.018E-03
16	2130.	1.100	1.099						0.949060	52.64	37.54	1.191E-03
17	2150.	1.145	1.147						0.949614	54.50	32.43	1.327E-03
18	2165.	1.190	1.189						0.949770	55.96	34.10	1.469E-03
19	2180.	1.270	1.274						0.949156	57.13	34.95	1.620E-03
20	2195.	1.260	1.266						0.949372	52.45	40.91	1.744E-03
21	2210.	1.245	1.239						0.949426	51.80	41.86	1.940E-03
22	2220.	1.300	1.379						0.947522	60.76	42.55	2.134E-03
23	2230.	1.415	1.420						0.944165	51.83	43.25	2.503E-03
24	2240.	1.475	1.491						0.942652	62.60	42.02	3.804E-03
25	2250.	1.525	1.530						0.975227	64.52	45.17	5.655E-03
26	2260.	1.410	1.454						0.946367	67.56	47.29	6.597E-03
27	2270.	1.565	1.562						0.944324	72.67	50.67	1.414E-02

PLOT RATE CRACK GROWTH ANALYSIS

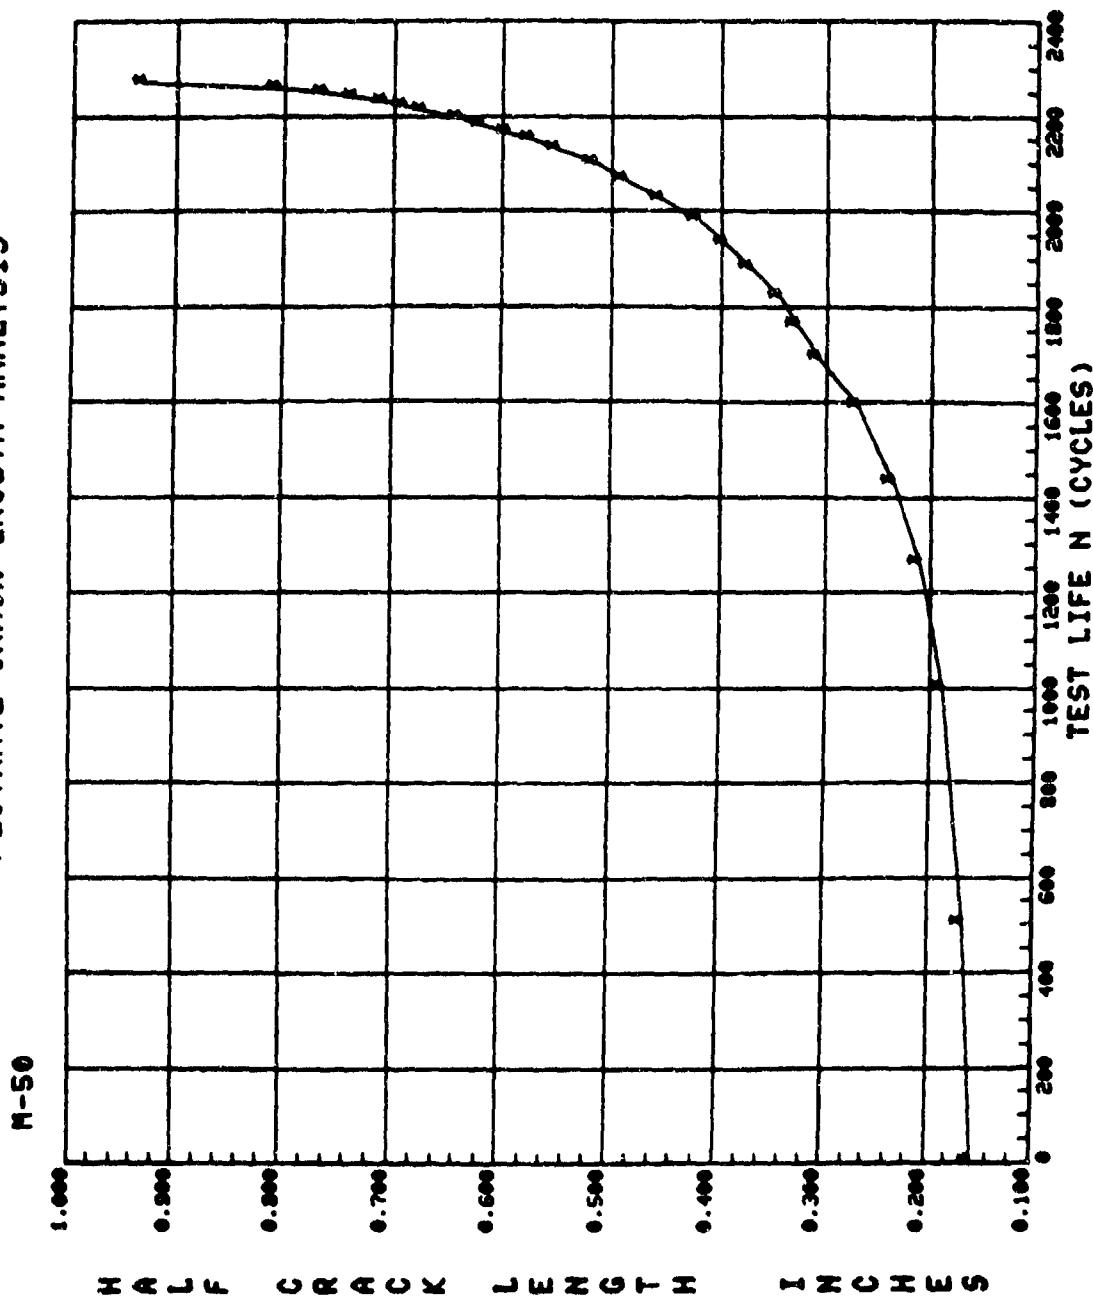


Figure 64. Crack growth curve for test M-50.

SPECIMEN NO.: M-51

TABLE 63. DATA TABULATION FOR TEST M-51

NO.	CYCLES	A(MEASUR'D)		A(REGRESSION)		MULT.	CORR.	COEFF.	K-MAX	DELTA K	DATA/N
		R _{MIN}	R _{MAX}	R	A _N						
ENVIRONMENT CONDITION: AMBIENT AIR											
1	6.	0.305	0.306	0.993106	5.55	5.55	2.108E-06				
2	9000.	0.355	0.347	0.995866	5.91	5.91	2.627E-06				
3	12000.	0.342	0.401	0.997268	6.37	6.37	3.330E-06				
4	14000.	0.445	0.444	0.997917	6.70	6.70	3.784E-06				
5	16000.	0.495	0.490	0.998289	7.04	7.04	4.383E-06				
6	16000.	0.545	0.547	0.998525	7.46	7.46	5.081E-06				
7	42000.	0.405	0.568	0.998978	7.87	7.87	5.952E-06				
8	45000.	0.555	0.684	0.995988	8.36	8.36	7.044E-06				
9	42000.	0.725	0.729	0.999556	6.63	6.63	7.723E-06				
10	44000.	0.710	0.776	0.999516	8.92	8.92	8.307E-06				
11	47000.	0.675	0.827	0.991230	9.22	9.22	9.655E-06				
12	60000.	0.675	0.889	0.990393	9.58	9.58	1.047E-05				
13	62700.	0.945	0.948	0.987738	9.91	9.91	1.233E-05				
14	63200.	0.975	0.957	0.986474	9.96	9.96	1.213E-05				
15	64700.	1.015	1.026	0.982456	10.33	10.33	1.380E-05				
16	65200.	1.070	1.046	0.986402	10.45	10.45	1.480E-05				
17	65750.	1.105	1.115	0.990322	10.81	10.81	1.611E-05				
18	66300.	1.145	1.149	0.987170	10.99	10.99	1.879E-05				
19	71900.	1.245	1.234	0.990769	11.42	11.42	2.186E-05				
20	72600.	1.295	1.304	0.991370	11.80	11.80	2.622E-05				
21	74500.	1.400	1.390	0.994367	12.17	12.17	2.938E-05				
22	76500.	1.470	1.479	0.993630	12.66	12.66	3.626E-05				
23	77760.	1.555	1.569	0.990231	13.10	13.10	4.571E-05				
24	78500.	1.715	1.745	0.978872	13.96	13.96	5.111E-05				
25	80750.	1.595	1.695	0.975904	14.69	14.69	5.234E-05				
26	81920.	2.155	2.031	0.944047	15.36	15.36	6.343E-05				
27	82660.	2.115	2.205	0.874120	16.23	16.23	8.645E-05				
28	83530.	2.165	2.253	0.775431	16.98	16.98	1.799E-04				

TABLE 63. DATA TABULATION FOR TEST M-51 (CONCL.)

SPECIMEN NO.: 4-1		CCT SPECIMEN		t = 0.25C IN.		W = 6.000 IN.		AN = 0.0 IN.		TEST FREQ = 6.00 Hz.	
		PHIN =		PMAX =							
ENVIRONMENT CONDITION: AMBIENT AIR											
NO.	CYCLES	AM(EASUR'D)	A(REGRESSION)	MULT.	CORR.	CUFF	K-MAX	DELTA K	DATA/ON		
29	1.700	2.380	2.424	0.868381			17.35	17.35	4.440E-04		
30	1.800	2.465	2.493	0.956289			17.72	17.72	8.447E-04		
31	2.300	2.615	2.697	0.978571			18.82	18.82	7.386E-04		
32	2.950	2.745	2.762	0.992663			19.31	19.31	6.393E-04		
33	3.400	2.920	2.982	0.974332			19.89	19.89	9.529E-04		
34	3.650	3.125	3.299	0.735525			22.55	22.55	1.293E-04		
35	3.650	3.170	3.267	0.744142			22.46	22.46	2.698E-03		
36	3.650	3.245	3.309	0.984181			22.62	22.62	5.662E-03		
37	3.650	3.625	3.629	0.996329			24.98	24.98	9.414E-03		

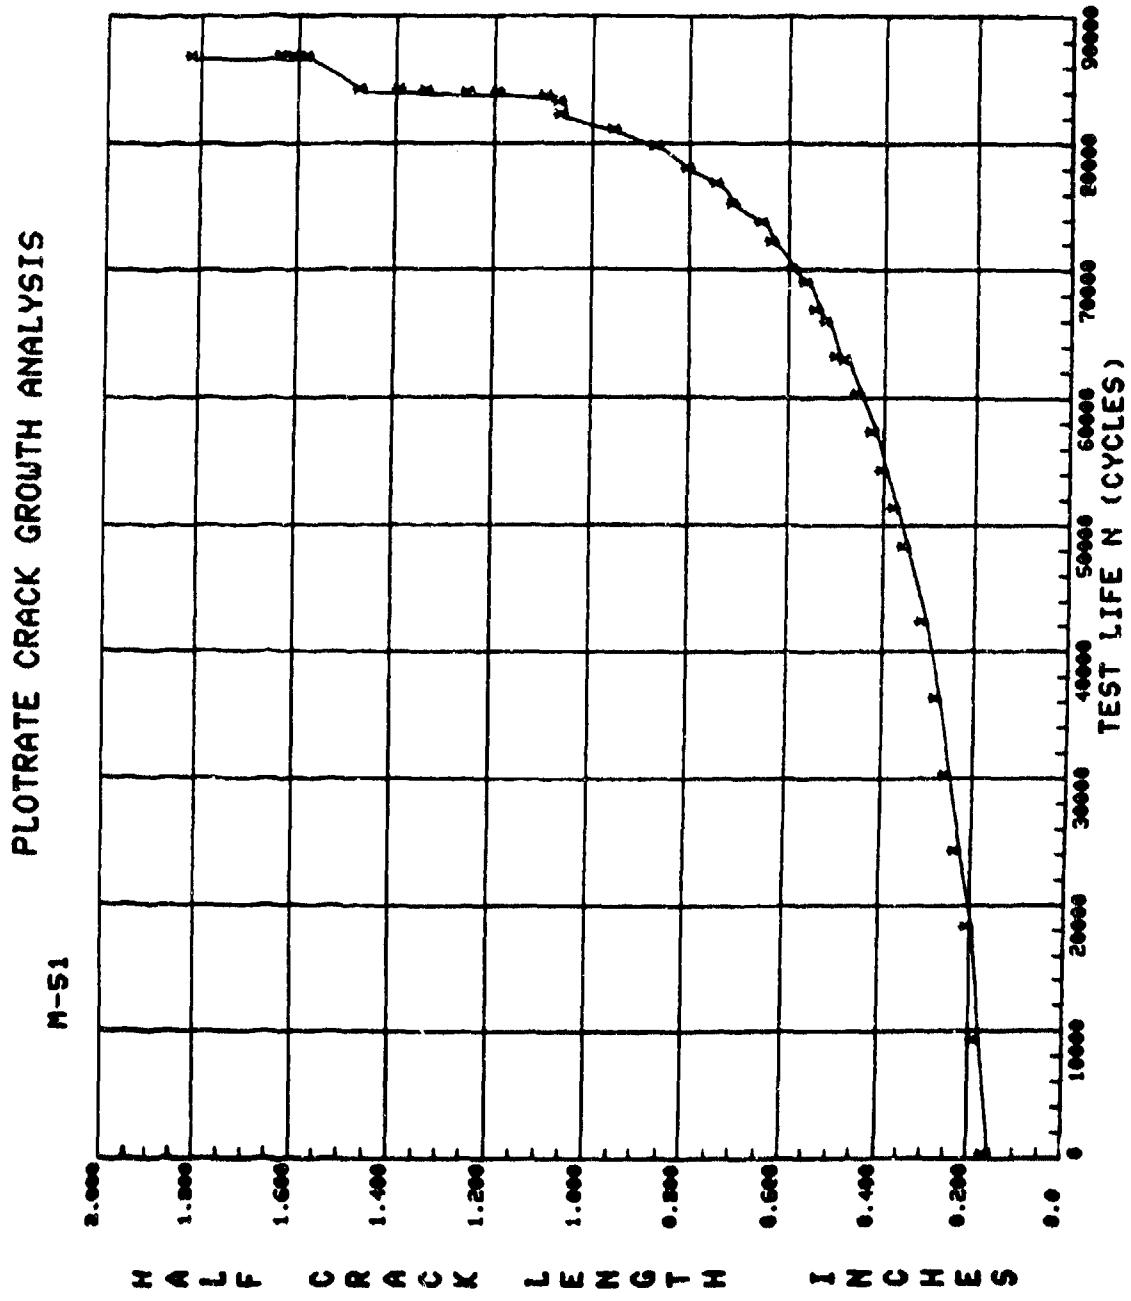


Figure 65. Crack growth curve for test M-51.

SPECIMEN NO.: 4-12

TABLE 64. DATA TABULATION FOR TEST M-52

NO.	CYCLES	A(MEASUR'D)		A(H=GRFSSION)		MULT. CCR. CEFF		K-MAX		DELTA K
		F _{MAX}	F _{MIN}	F _{MAX}	F _{MIN}	F _{TEST}	F _{TEST}	A= G.C	I=N.	
ENVIRONMENT CONDITION: AMBIENT AIR										
1	0.	0.300	0.300	0.300	0.300	1.000000	1.000000	13.75	13.75	1.322E-05
2	1500.	0.246	0.246	0.944557	0.944557	14.78	14.78	2.035E-05	2.035E-05	
3	2600.	0.451	0.451	0.98107	0.98107	15.92	15.92	2.681E-05	2.681E-05	
4	2600.	0.460	0.460	0.95579	0.95579	17.05	17.05	3.501E-05	3.501E-05	
5	4400.	0.517	0.517	0.995620	0.995620	18.10	18.10	4.707E-05	4.707E-05	
6	5200.	0.575	0.575	0.959767	0.959767	19.45	19.45	6.192E-05	6.192E-05	
7	5800.	0.573	0.573	0.940364	0.940364	20.73	20.73	6.144E-05	6.144E-05	
8	6100.	0.740	0.722	0.95775	0.95775	21.48	21.48	8.402E-05	8.402E-05	
9	6574.	0.661	0.518	0.979564	0.979564	22.93	22.93	1.023E-04	1.023E-04	
10	5674.	0.570	0.643	0.977436	0.977436	23.29	23.29	1.008E-04	1.008E-04	
11	7119.	0.916	0.574	0.952064	0.952064	24.58	24.58	1.201E-04	1.201E-04	
12	7146.	0.572	0.925	0.950563	0.950563	24.60	24.60	1.272E-04	1.272E-04	
13	7676.	1.042	1.085	0.952442	0.952442	26.67	26.67	1.519E-04	1.519E-04	
14	7690.	1.125	1.097	0.944265	0.944265	26.79	26.79	1.676E-04	1.676E-04	
15	7975.	1.164	1.164	0.923663	0.923663	27.66	27.66	2.157E-04	2.157E-04	
16	8201.	1.352	1.352	0.762570	0.762570	30.43	30.43	4.206E-04	4.206E-04	
17	6217.	1.375	1.451	0.572259	0.572259	31.29	31.29	9.549E-04	9.549E-04	
18	6225.	1.475	1.474	0.95611	0.95611	31.56	31.56	7.645E-03	7.645E-03	
19	4217.	1.584	1.584	0.93471	0.93471	32.93	32.93	1.224E-02	1.224E-02	
20	8236.	1.722	1.722	0.994653	0.994653	34.62	34.62	1.6666E-02	1.6666E-02	

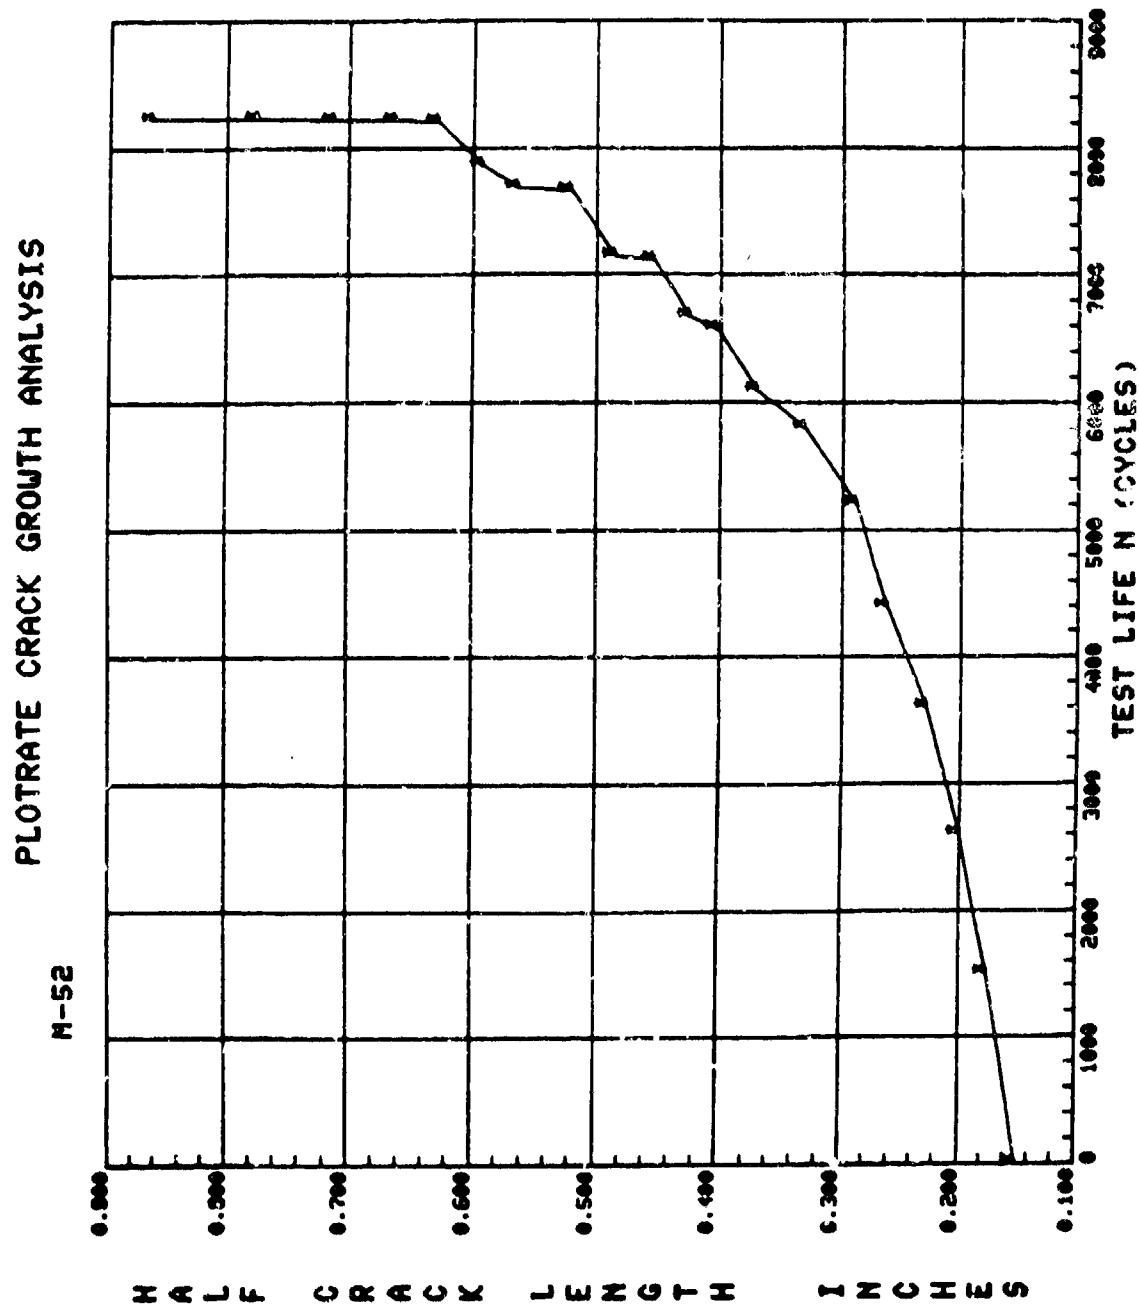


Figure 66. Crack growth curve for test M-52.

TABLE 65. DATA CUMULATION FOR TEST M-53

SPECIMEN NO.: M-53		CCT SPECIMEN L= 0.250 IN.		H= 5.000 IN.		A= 3.0 IN.		TEST FREQUENCY = 6.00 Hz.	
P MIN=		F MAX=		ENVIRONMENT CONDITION: AMBIENT AIR		MEASUREMENT: A DEGRESSION		MULT. CORR. COEFF	
NO.	CYCLES	0.	0.250	0.290	0.316	0.331	0.346	0.361	0.376
1	0.	0.949565	0.949565	0.949565	0.949565	0.949565	0.949565	0.949565	0.949565
2	30000.	0.971477	0.970570	0.970570	0.970570	0.970570	0.970570	0.970570	0.970570
3	55000.	0.972544	0.971477	0.971477	0.971477	0.971477	0.971477	0.971477	0.971477
4	60000.	0.972544	0.972544	0.972544	0.972544	0.972544	0.972544	0.972544	0.972544
5	90000.	0.976442	0.976442	0.976442	0.976442	0.976442	0.976442	0.976442	0.976442
6	150000.	0.989022	0.989022	0.989022	0.989022	0.989022	0.989022	0.989022	0.989022
7	210000.	0.975170	0.975170	0.975170	0.975170	0.975170	0.975170	0.975170	0.975170
8	270000.	0.972776	0.972776	0.972776	0.972776	0.972776	0.972776	0.972776	0.972776
9	325000.	0.977671	0.977671	0.977671	0.977671	0.977671	0.977671	0.977671	0.977671
10	260000.	0.984411	0.984411	0.984411	0.984411	0.984411	0.984411	0.984411	0.984411
11	420000.	0.964541	0.964541	0.964541	0.964541	0.964541	0.964541	0.964541	0.964541
12	475000.	0.977166	0.977166	0.977166	0.977166	0.977166	0.977166	0.977166	0.977166
13	535000.	0.952442	0.952442	0.952442	0.952442	0.952442	0.952442	0.952442	0.952442
14	570000.	0.963579	0.963579	0.963579	0.963579	0.963579	0.963579	0.963579	0.963579
15	595000.	0.949312	0.949312	0.949312	0.949312	0.949312	0.949312	0.949312	0.949312
16	620000.	0.951117	0.951117	0.951117	0.951117	0.951117	0.951117	0.951117	0.951117
17	660000.	0.949414	0.949414	0.949414	0.949414	0.949414	0.949414	0.949414	0.949414
18	693000.	0.948111	0.948111	0.948111	0.948111	0.948111	0.948111	0.948111	0.948111
19	720000.	0.996555	0.996555	0.996555	0.996555	0.996555	0.996555	0.996555	0.996555
20	750000.	0.999656	0.999656	0.999656	0.999656	0.999656	0.999656	0.999656	0.999656
21	790000.	0.995762	0.995762	0.995762	0.995762	0.995762	0.995762	0.995762	0.995762
22	810000.	0.999216	0.999216	0.999216	0.999216	0.999216	0.999216	0.999216	0.999216
23	840000.	1.0016	1.0016	1.0016	1.0016	1.0016	1.0016	1.0016	1.0016
24	870000.	1.0071	1.0071	1.0071	1.0071	1.0071	1.0071	1.0071	1.0071
25	900000.	1.0152	1.0152	1.0152	1.0152	1.0152	1.0152	1.0152	1.0152
26	930000.	1.0263	1.0263	1.0263	1.0263	1.0263	1.0263	1.0263	1.0263
27	958200.	1.0359	1.0359	1.0359	1.0359	1.0359	1.0359	1.0359	1.0359
28	960000.	1.0271	1.0271	1.0271	1.0271	1.0271	1.0271	1.0271	1.0271

TABLE 65. DATA TABULATION FOR TEST M-53 (CONCL)

SPECIMEN NO.: M-53

TEST SPECIMEN	E= 6.250 IN.	W= 6.000 IN.	A= 0.0 IN.	ENVIRONMENT CONDITIONS: AMBIENT AIR		MULT. COEF	COEFF	K-MAX	DELTA K	DA/DN
				P MIN=	P MAX=					
29	98500.	1.340	1.447	0.935646	12.50	2.362E-05	9.75			
30	99891.	1.470	1.463	0.935446	12.58	2.696E-05	8.60			
31	99000.	1.515	1.498	0.923463	12.70	2.503E-05	8.89			
32	101829.	1.530	1.666	0.940569	13.57	3.109E-05	9.50			
33	102000.	1.705	1.654	0.920019	13.56	3.260E-05	9.49			
34	104625.	1.770	1.951	0.929430	14.47	10.13	3.516E-05			
35	104842.	1.460	1.871	0.917119	14.57	10.20	4.005E-05			
36	1C5000.	1.460	1.676	0.889237	14.61	10.23	4.271E-05			
37	107667.	2.070	2.169	0.872125	16.04	11.23	1.201E-04			
38	107632.	2.165	2.217	0.863143	16.29	11.40	4.565E-05			
39	107977.	2.325	2.229	0.845641	16.35	11.44	4.978E-05			
40	108150.	2.325	2.297	0.804021	16.69	11.69	1.460E-04			
41	110666.	2.425	2.571	0.795427	18.14	12.70	2.418E-04			
42	110700.	2.580	2.569	0.923736	16.29	12.60	6.614E-04			
43	110803.	2.725	2.750	0.990328	19.12	13.39	9.340E-04			
44	110853.	2.610	2.619	0.995796	19.52	13.67	1.052E-03			
45	110950.	3.070	3.046	0.997595	20.89	14.62	1.391E-03			
56	111000.	3.200	3.159	0.998707	21.87	15.51	1.633E-03			

PLUTRATE CRACK GROWTH ANALYSIS

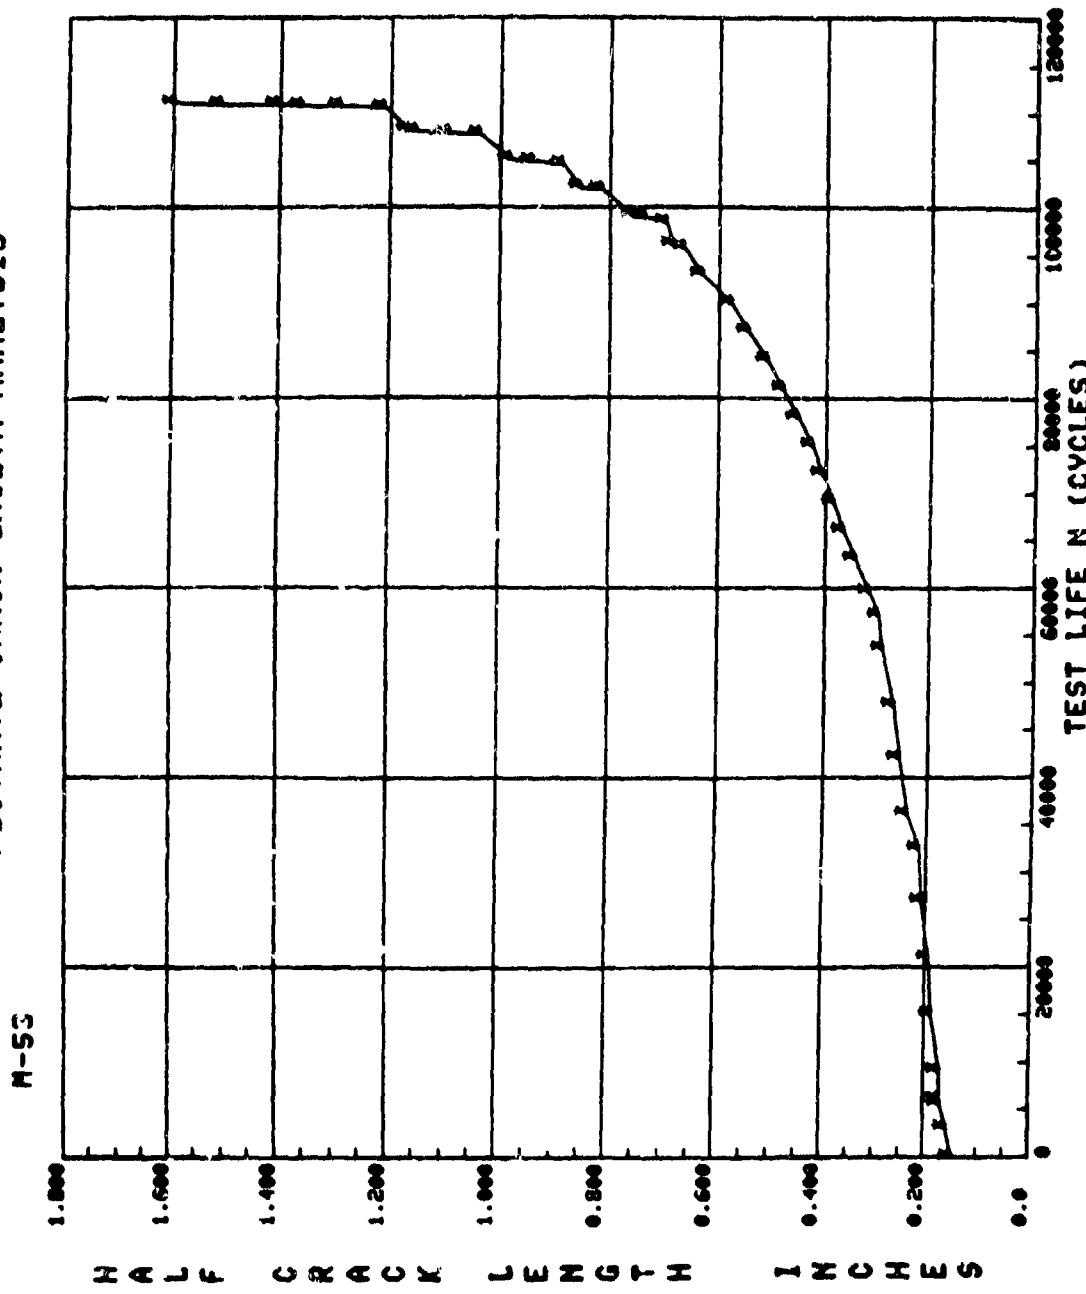


Figure 67. Crack growth curve for test M-53.

TABLE 66. DATA TABULATION FOR TEST M-54

SPECIMEN No.: 4-4

CCT SPECIMEN E= 6.30 IN. W= 5.000 IN. AN= 0.0 IN.
 PMIN= PEAK= TEST FRQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	MEASUREMENT	REGRESSION	MULT.	CORR.	GCEFF	K-MAX	DAVON	DELTA K
1	6.	0.700	0.300	1.00000	12.75	6.62	2.603E-05		
2	500.	0.322	0.996232	14.25	9.98	2.091E-05			
3	1641.	0.365	0.994541	15.19	10.63	2.027E-05			
4	2337.	0.420	0.995462	16.65	11.65	2.280E-05			
5	4421.	0.455	0.974972	17.59	12.31	2.746E-05			
6	4962.	0.515	0.995276	18.13	12.69	3.367E-05			
7	5515.	0.555	0.996225	18.76	13.13	3.627E-05			
8	6064.	0.590	0.986027	19.41	12.56	4.836E-05			
9	6613.	0.649	0.991381	20.33	14.23	5.906E-05			
10	7237.	0.725	0.981365	21.90	15.33	8.687E-05			
11	7709.	0.720	0.975946	22.92	16.04	9.072E-05			
12	8233.	0.600	0.99924	24.42	17.09	1.104E-04			
13	F297.	0.780	0.929213	24.85	17.29	1.254E-04			
14	E761.	1.070	1.104	0.82723	26.87	16.61	2.052E-04		
15	E771.	1.070	1.125	0.691333	27.16	16.01	6.820E-04		
16	E78.	1.140	1.139	0.760936	27.33	19.13	2.122E-04		
17	E742.	1.200	1.195	0.951026	26.07	19.65	2.711E-03		
18	E900.	1.255	1.226	0.905755	28.49	19.94	2.307E-03		
19	E209.	1.405	1.517	0.980679	32.10	22.47	2.322E-04		
20	E314.	1.515	1.530	0.897766	32.26	22.58	5.191E-03		
21	E316.	1.575	1.571	0.998366	32.77	22.94	1.241E-02		

THIS PAGE IS BEP QUALITY PRACTICALLY
 FROM COPY FURNISHED TO DDC

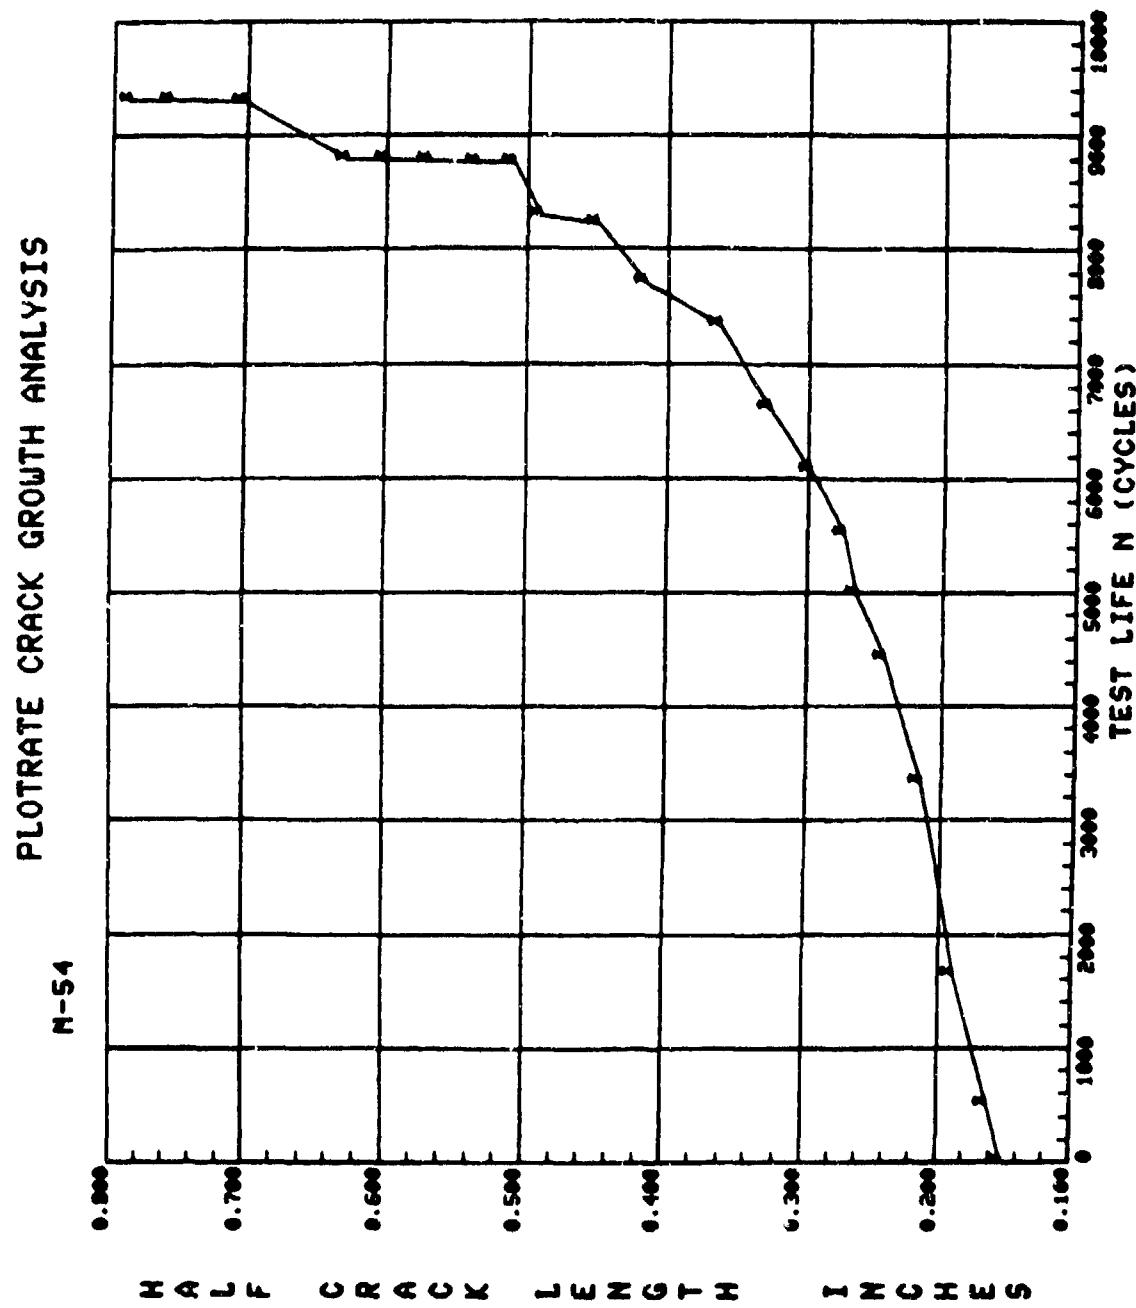


Figure 68. Crack growth curve for test N-54.

TABLE 67. DATA TABULATION FOR TEST M-55

SPECIMEN NO.: M-55

CCI SPECIMEN E= 0.250 IN. W= 0.005 IN. A= C.O. IN.
 PMIN= PMAX= TEST FREQ= 5.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	MEASURED	A (REGRESSION)	MULT. COEF. COEFF	K-MAX	DA/DN
1	0.	0.313	0.313	0.999655	14.04	2.112E-07
2	7900.	0.325	0.334	0.961929	14.51	1.431E-06
3	13000.	0.340	0.339	0.865694	14.62	7.136E-07
4	20000.	0.375	0.342	0.902364	14.65	3.092E-07
5	110000.	0.395	0.395	0.942072	15.80	3.640E-07
6	142000.	0.425	0.418	0.972504	16.26	4.796E-07
7	182000.	0.460	0.460	0.996674	17.07	6.185E-07
8	203000.	0.465	0.458	0.992640	17.58	6.368E-07
9	223000.	0.475	0.516	0.996297	16.09	5.680E-07
10	240000.	0.540	0.537	0.992418	13.42	1.545
11	270000.	0.570	0.582	0.974162	19.25	19.25
12	300000.	0.620	0.623	0.997616	0.07	20.07
13	323000.	0.715	0.706	0.946629	21.24	1.155E-06
14	345166.	0.720	0.726	0.996635	21.72	1.174E-06
15	367300.	0.800	0.793	0.997261	22.55	1.251E-06
16	385000.	0.875	0.825	0.957212	23.17	1.362E-06
17	401000.	0.895	0.889	0.976559	23.94	22.94
18	425000.	0.945	0.943	0.995672	24.71	1.471
19	445900.	1.610	1.614	0.996623	25.65	1.666E-06
20	459000.	1.570	1.069	0.949412	26.41	2.142E-06
21	471000.	1.125	1.121	0.949132	27.10	2.354E-06
22	486200.	1.190	1.194	0.996070	23.05	2.005
23	499600.	1.270	1.273	0.958671	29.06	25.06
24	507000.	1.320	1.324	0.949727	29.76	29.70
25	517400.	1.415	1.412	0.936702	30.80	35.60
26	522600.	1.460	1.466	0.991602	31.48	5.675E-06
27	527800.	1.510	1.525	0.992787	32.24	6.463E-06
28	523000.	1.625	1.595	0.991075	35.06	7.493E-06

THIS PAGE IS BEST QUALITY PRACTICABLE
FROM COPY PUBLISHED TO DDQ

TABLE 67. DATA TABULATION FOR TEST M-55 (CONCL)

SPECIMEN NO.:	N-5*	GCT SPECIMEN	$\theta = 0.750^\circ \text{ IN.}$	$W = 5.000 \text{ IN.}$	$A_N = 0.0 \text{ IN.}$	TEST FREQ = 6.00 Hz.
P MIN=	P MAX=	ENVIRONMENT CONDITION: AMBIENT AIR				
NO.	CYCLES	MEASURED	REGRESSION	MULT. CORR. COEFF	ζ_{MAX}	DELTA K
29	540800.	1.715	1.714	0.990071	34.64	$9.692E-06$
30	544000.	1.915	1.831	0.988442	35.44	$1.173E-05$
31	548600.	1.545	1.889	0.999556	35.65	$1.468E-05$
32	551042.	1.945	1.915	0.969351	37.59	$1.632E-05$

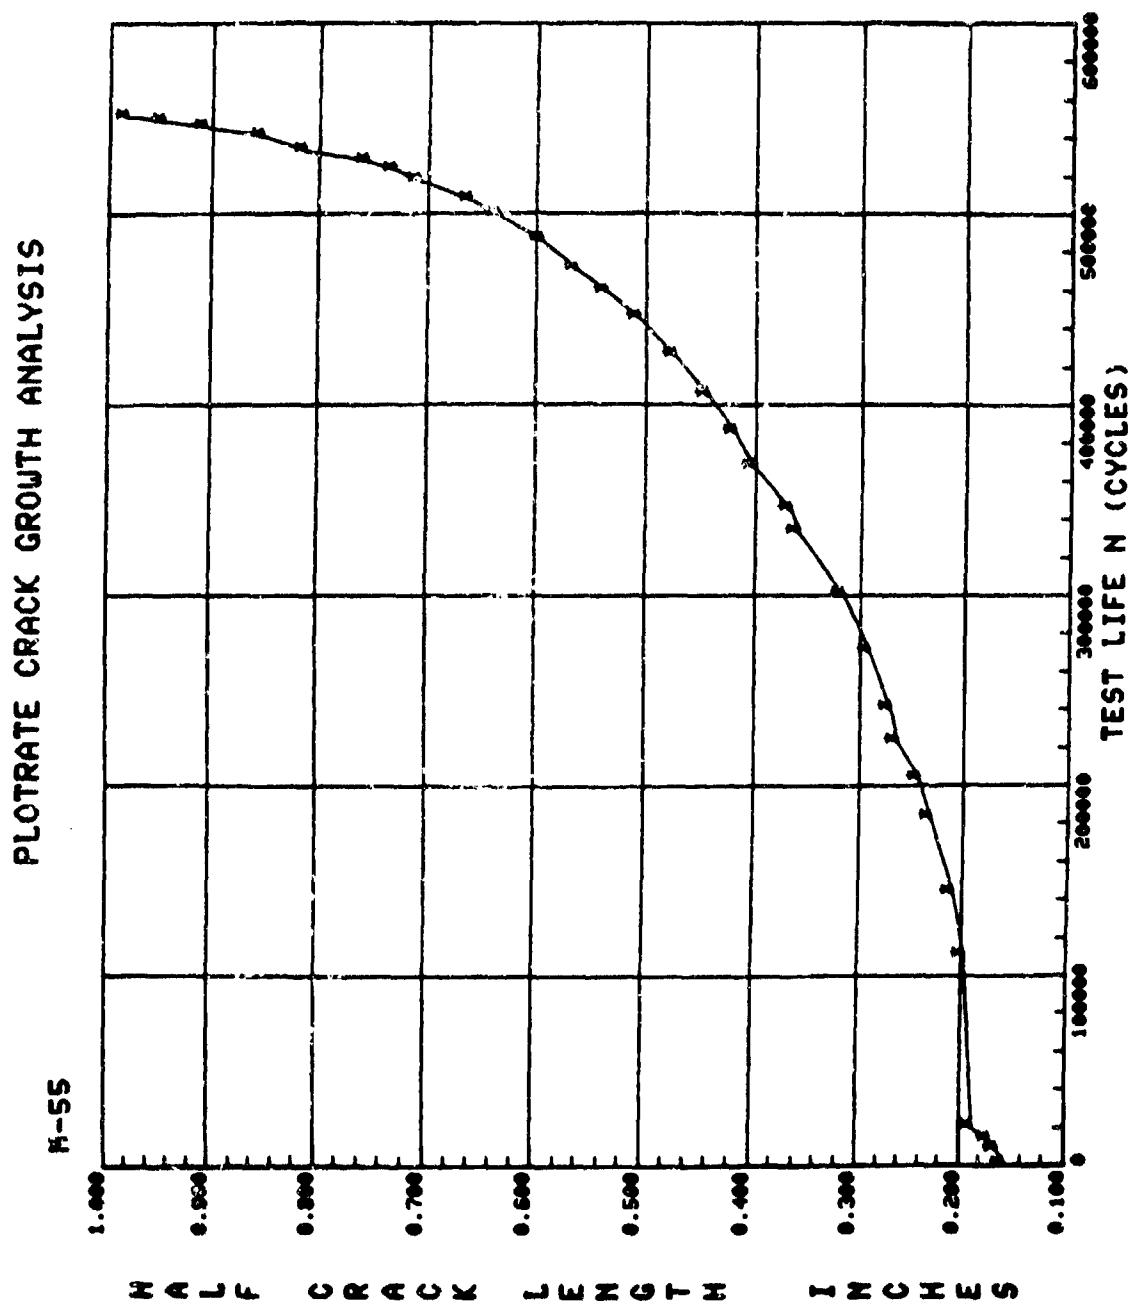


Figure 69. Crack growth curve for test N-55.

TABLE 68. DATA TABULATION FOR TEST M-56

SPECIMEN NO.:	SPECFIM	B= 0.250 IN.	W= 6.000 IN.	A= 0.0	JN.	MAX=		TEST FREQ= 6.00 Hz.		DAY/N	
						P MIN=	P MAX=	MULT.	CORR. COEFF	K MAX	DELTA K
ENVIRONMENT CONDITIONS: AMBIENT AIR											
No.	CYCLES	A(MEASURED)	A(REGRESSION)								
1	0	0.208	0.206	0.954264	13.90	2.391E-05					
2	1600	0.350	0.373	0.932112	15.34	1.968E-05					
3	2545	0.425	0.405	0.987364	16.00	1.872E-05					
4	3112	0.470	0.500	0.990706	17.79	1.781E-05					
5	6604	0.575	0.520	0.989990	19.15	18.15					
6	7745	0.595	0.555	0.982886	19.28	19.28	1.4653E-05				
7	10220	0.575	0.678	0.932847	20.79	20.79	2.133E-05				
8	12452	0.720	0.775	0.952503	22.29	22.29	2.032E-05				
9	12919	0.765	0.801	0.941614	22.68	22.68	3.517E-05				
10	13076	0.845	0.805	0.919589	22.73	22.73	3.795E-05				
11	14520	0.950	1.056	0.936819	26.27	26.27	4.008E-05				
12	15546	1.070	1.056	0.919623	26.24	26.24	4.420E-05				
13	15610	1.175	1.061	0.859168	25.31	26.31	4.590E-05				
14	16104	1.070	1.388	0.738418	30.50	30.50	-1.126E-04				
15	16114	1.275	1.445	0.561292	31.22	31.22	1.128E-03				
16	16136	1.420	1.501	0.947409	31.91	31.91	1.109E-02				
17	16125	1.560	1.579	0.995637	32.67	32.87	1.626E-02				
18	16129	1.724	1.714	0.997467	34.51	34.51	2.080E-02				
19	16137	1.524	1.647	0.995964	36.14	36.14	2.368E-02				

THIS PAGE IS BEST QUALITY FRAGMENT
 THIS PAGE IS BEST QUALITY FRAGMENT
 THIS COPY PUBLISHED TO DDC

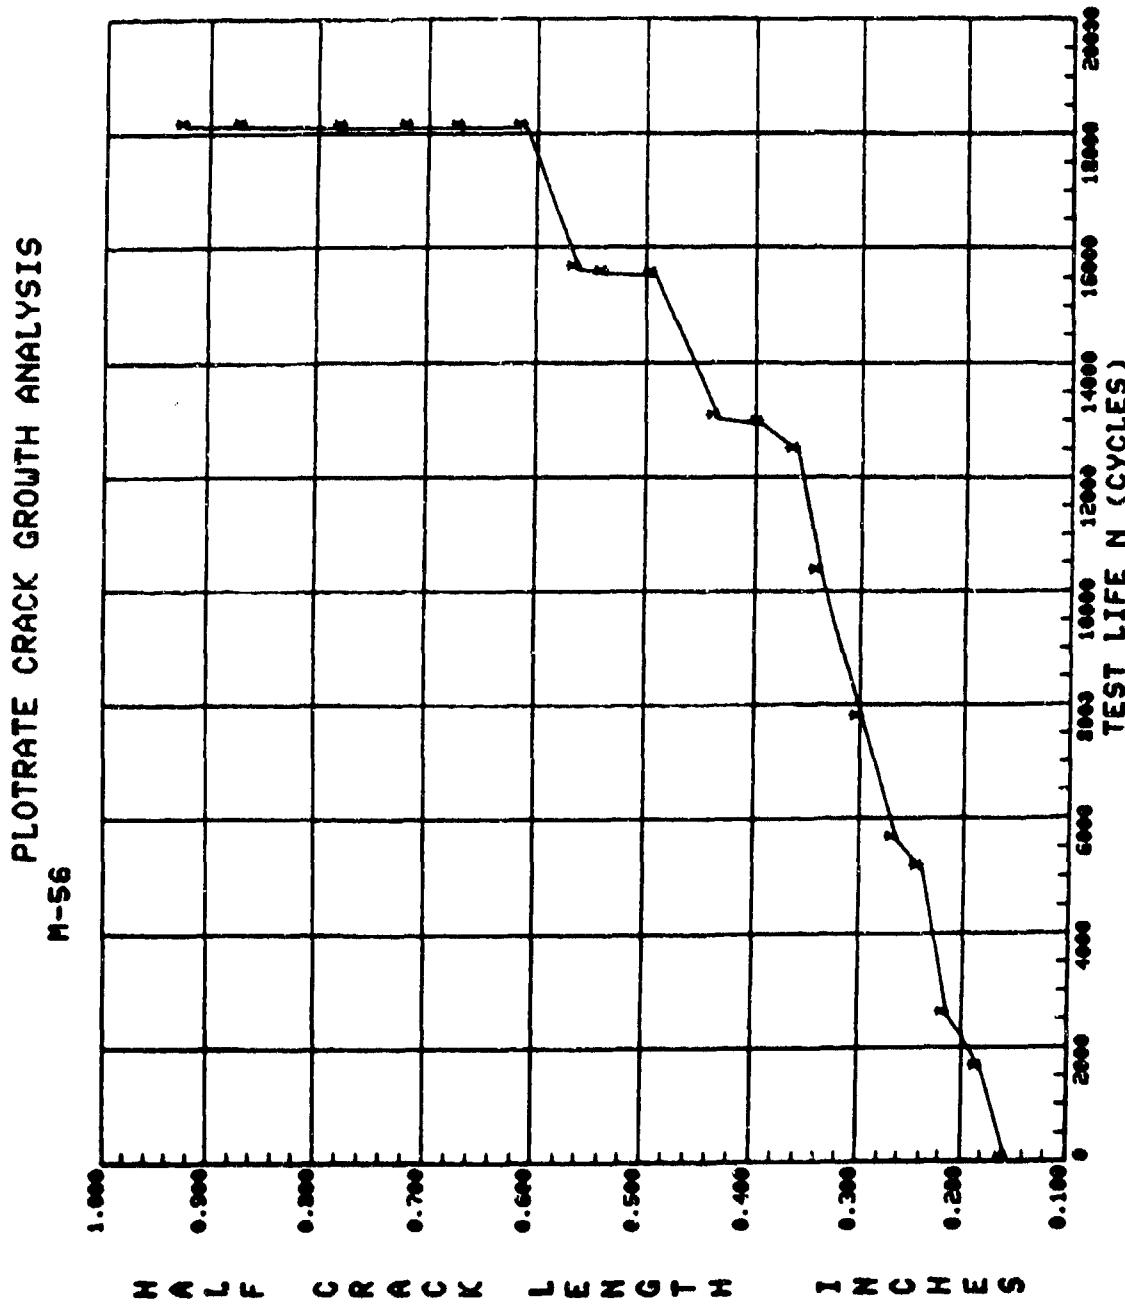


Figure 70. Crack growth curve for test M-56.

TABLE 69. DATA TABULATION FOR TEST M-57

SPECIMEN No.:	f _c = 0.25C IN.	H = 5.000 IN.	AN = 0.0	IN _a	TEST FREQ = 6.00 Hz.			
					P _{IN}	C _{WDX}	MULT. COEFF	K-MAX
ENVIRONMENT CONDITIONS: A931-NL AIP								
NU.	CYCLES	R (REGRESSION)	A (REGRESSION)					
1	0	0.293	0.269	0.979108	26.97	35.07	2.885E-05	
2	1600	0.310	0.364	0.983856	30.30	39.38	2.092E-05	
3	25,800	0.425	0.395	0.981491	31.60	41.08	1.793E-05	
4	46,900	0.461	0.469	0.978818	34.44	44.78	1.551E-05	
5	75,600	0.516	0.537	0.984024	36.91	47.99	1.548E-05	
6	91,100	0.540	0.582	0.995597	38.46	49.99	1.553E-05	
7	105,600	0.545	0.632	0.972610	40.42	52.16	1.907E-05	
8	119,600	0.710	0.715	0.974667	43.35	56.36	2.178E-05	
9	155,700	0.915	0.827	0.965448	46.97	61.06	2.882E-05	
10	156,200	0.930	0.858	0.933910	47.00	61.10	3.365E-05	
11	176,400	0.945	1.067	0.813640	52.77	68.60	6.103E-05	
12	181,700	1.055	1.102	0.824265	53.20	69.81	6.782E-05	
13	181,800	1.105	1.083	0.941338	53.33	69.32	9.271E-05	
14	181,900	1.150	1.090	0.961066	53.38	69.40	5.166E-05	
15	194,400	1.165	1.269	0.963426	58.51	76.06	1.459E-04	
16	207,500	1.205	1.905	0.993216	73.69	95.80	3.342E-04	

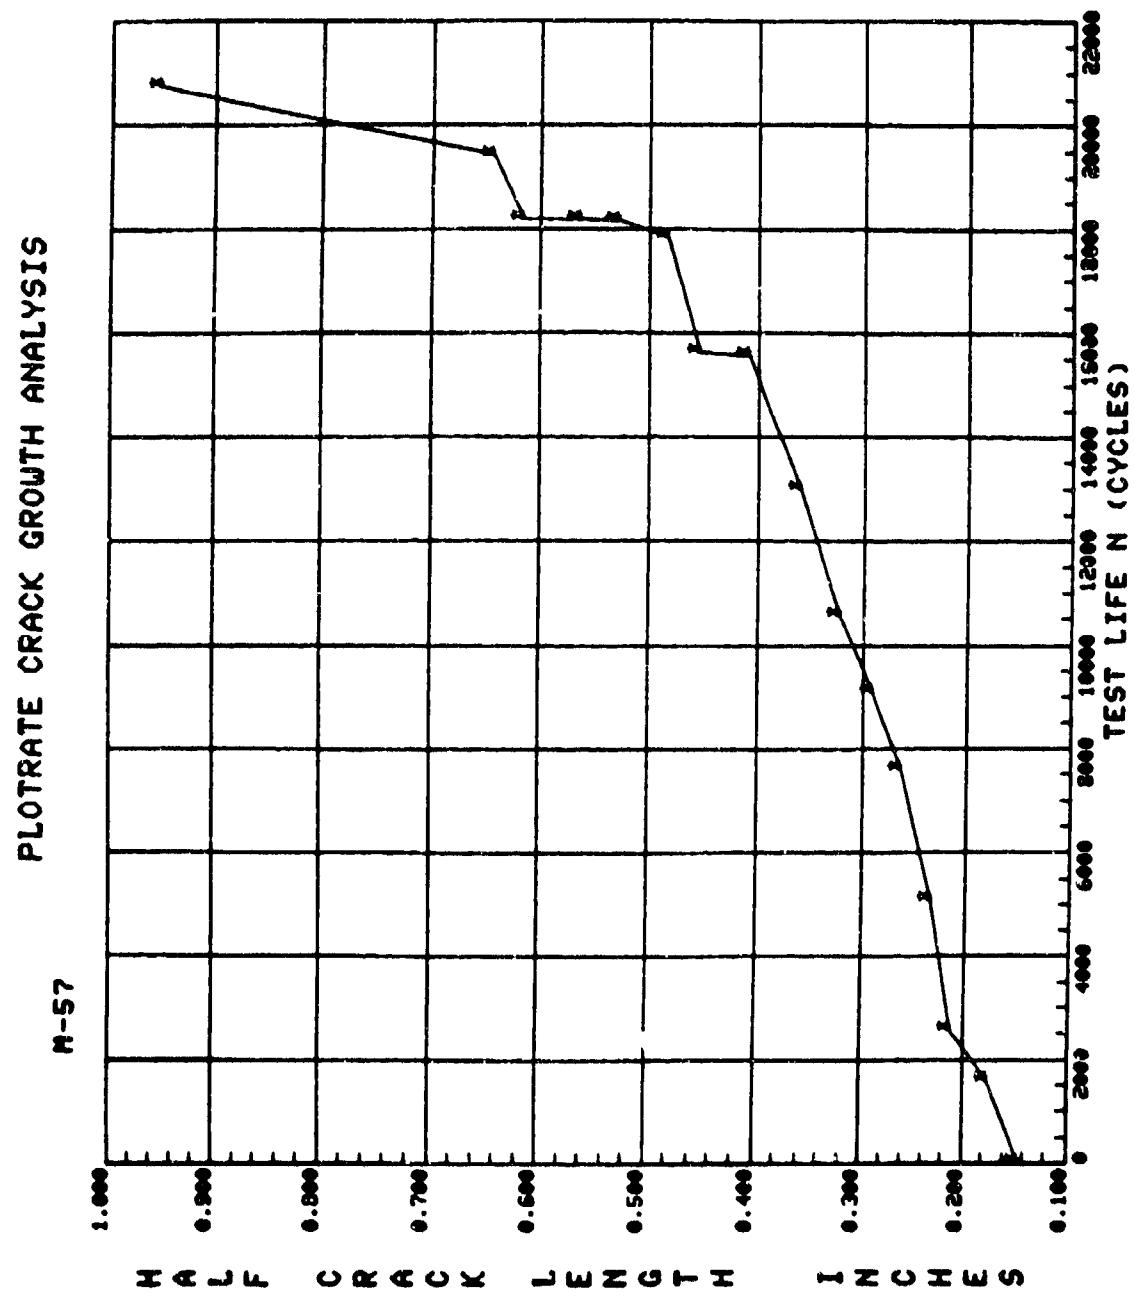


Figure 71. Crack growth curve for test M-57.

TABLE 70. DATA TABULATION FOR TEST M-58

SPECIMEN NO.: M-58

LCL. SPECIMEN = B= 2.250 IN. W= 6.000 IN. AY= 0.0 IN.
 P_{MIN}= P_{MAX}= TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. COEF. CUEFF	K-MAX	DELTA K	DA/DN
1	0-	0.365	0.365	0.947052	27.71	31.87	2.914E-05
2	717-	0.340	0.333	0.917266	25.97	33.32	2.264E-05
3	2000-	0.405	0.416	0.823051	32.42	37.28	5.987E-05
4	2500-	0.415	0.512	0.747817	36.03	41.43	1.101E-04
5	2550-	0.490	0.552	0.709692	37.42	43.04	2.326E-04
6	2600-	0.570	0.579	0.995909	36.33	44.06	9.924E-04
7	2630-	0.630	0.673	0.998026	40.17	46.19	1.186E-03
8	2646-	0.700	0.705	0.998736	42.45	46.61	1.449E-03
9	2690-	0.795	0.797	0.999490	45.62	52.00	1.820E-03
10	2705-	0.850	0.851	0.997774	46.80	53.83	2.197E-03
11	2723-	0.910	0.930	0.995443	44.04	56.40	3.171E-03
12	2735-	0.960	0.989	0.979851	50.63	55.23	4.289E-03
13	2750-	1.100	1.131	0.893295	54.47	62.64	8.118E-03
14	2767-	1.330	1.465	0.902184	63.43	72.95	1.711E-02
15	2772-	1.505	1.690	0.907675	68.44	78.70	2.627E-02
16	2774-	1.675	1.850	0.954914	72.36	73.26	5.170E-02

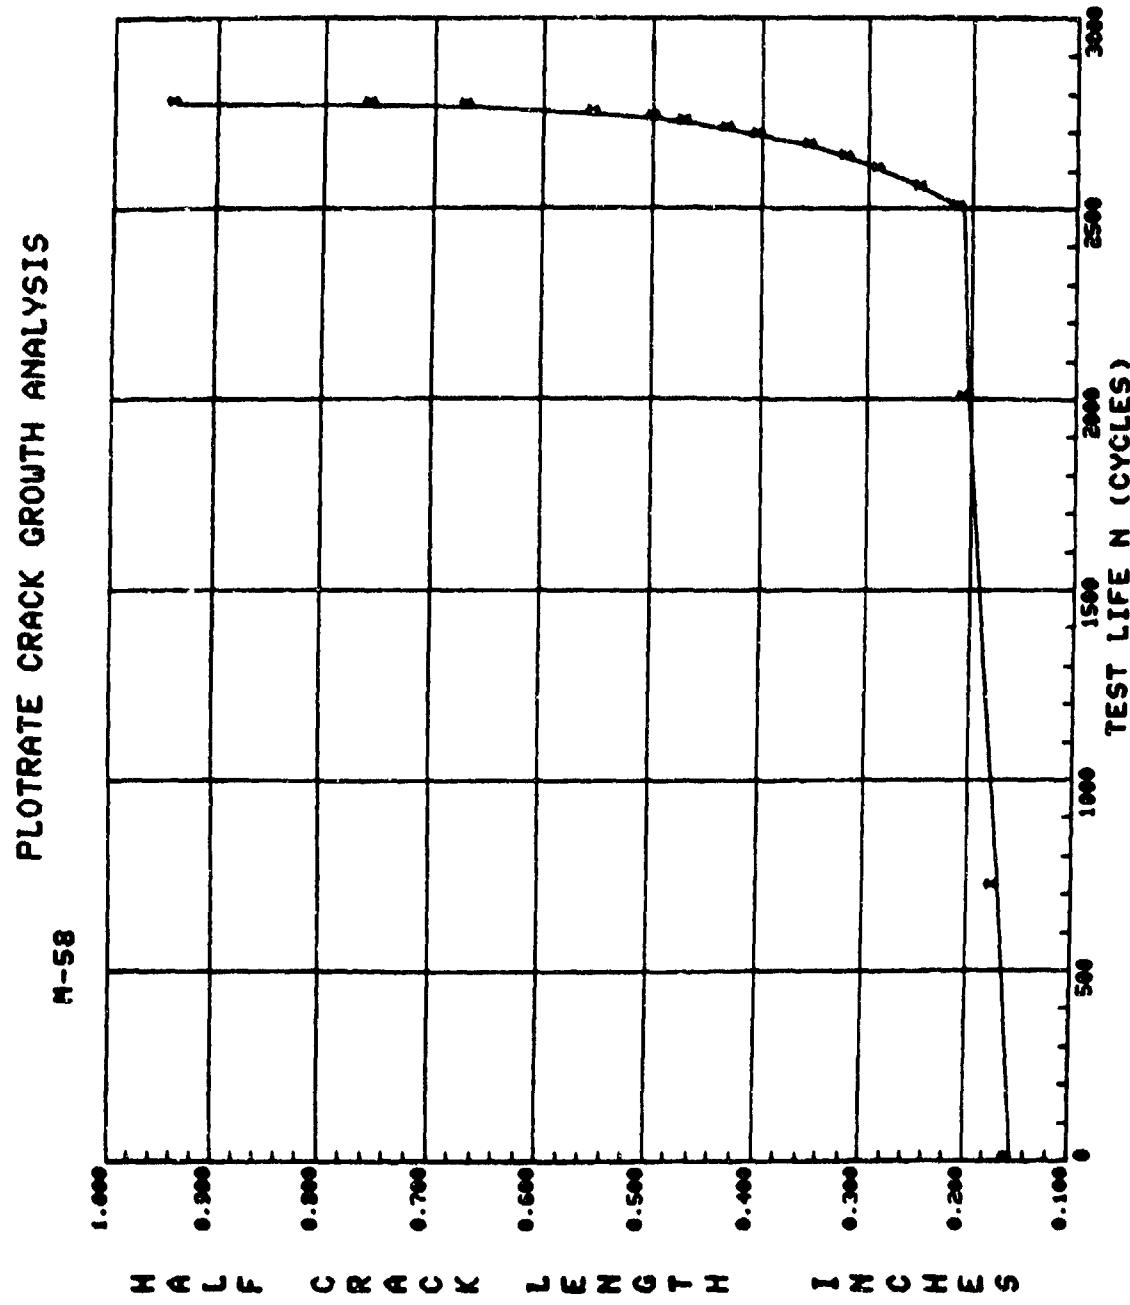


Figure 72. Crack growth curve for test M-58.

TABLE I. DATA TABULATION FOR TEST M-59

SPECIMEN NO. 2

FRTG = 6.03 Hz.

ENVIRONMENT CONCILIATION: AMBIENT AIR

NO.	CYCLES	A(MFAISLURD)		A(REFLECTION)		MULT.	CUMR.	CUFFF	K-KAX	DELTA K	JAD/N
		0.	0.315	0.	0.315						
1	0.	0.315	0.315	0.999991	0.999991	21.14	22.63	6.253E-05	6.253E-05	6.253E-05	
2	5265	0.250	0.251	0.949745	0.949745	22.33	24.12	6.776E-05	6.776E-05	6.776E-05	
3	5751	0.425	0.424	0.995745	0.995745	24.56	26.53	8.668E-05	8.668E-05	8.668E-05	
4	6006	0.445	0.475	0.976232	0.976232	26.02	28.10	1.070E-04	1.070E-04	1.070E-04	
5	6292	0.515	0.531	0.97267	0.97267	27.52	29.73	1.591E-04	1.591E-04	1.591E-04	
6	6500	0.550	0.549	0.962195	0.962195	29.03	31.35	2.171E-04	2.171E-04	2.171E-04	
7	6700	0.470	0.654	0.966515	0.966515	31.35	33.85	3.034E-04	3.034E-04	3.034E-04	
8	6807	0.165	0.73	0.966495	0.966495	32.94	35.57	3.769E-04	3.769E-04	3.769E-04	
9	6978	0.900	0.813	0.98996b	0.98996b	34.26	37.02	4.936E-04	4.936E-04	4.936E-04	
10	6910	0.675	0.644	0.955555	0.955555	34.96	37.75	4.997E-04	4.997E-04	4.997E-04	
11	6940	0.577	0.573	0.956026	0.956026	35.59	38.43	5.102E-04	5.102E-04	5.102E-04	
12	6980	0.540	0.921	0.949640	0.949640	36.60	39.53	5.970E-04	5.970E-04	5.970E-04	
13	7050	0.995	1.002	0.993001	0.993001	38.28	41.34	6.354E-04	6.354E-04	6.354E-04	
14	7100	1.060	1.063	0.942952	0.942952	39.51	42.68	7.334E-04	7.334E-04	7.334E-04	
15	7150	1.125	1.127	0.99524	0.99524	40.97	44.24	8.757E-04	8.757E-04	8.757E-04	
16	7180	1.140	1.192	0.999792	0.999792	42.05	45.41	9.975E-04	9.975E-04	9.975E-04	
17	7210	1.260	1.254	0.994193	0.994193	43.23	46.69	1.144E-03	1.144E-03	1.144E-03	
18	7240	1.320	1.324	0.997441	0.997441	44.56	48.13	1.366E-03	1.366E-03	1.366E-03	
19	7270	1.405	1.410	0.9938593	0.9938593	45.18	49.87	1.605E-03	1.605E-03	1.605E-03	
20	7290	1.475	1.475	0.999372	0.999372	47.33	51.17	1.851E-03	1.851E-03	1.851E-03	
21	7310	1.560	1.549	0.994525	0.994525	48.76	52.66	2.310E-03	2.310E-03	2.310E-03	
22	7330	1.624	1.640	0.993606	0.993606	50.43	54.46	2.867E-03	2.867E-03	2.867E-03	
23	7350	1.745	1.757	0.996695	0.996695	52.57	56.77	3.839E-03	3.839E-03	3.839E-03	
24	7370	1.920	1.923	0.966394	0.966394	55.61	60.06	6.214E-03	6.214E-03	6.214E-03	
25	7380	2.025	2.049	0.977996	0.977996	57.93	62.56	8.797E-03	8.797E-03	8.797E-03	
26	7390	2.170	2.170	0.991655	0.991655	61.36	66.27	1.219E-02	1.219E-02	1.219E-02	
27	7402	2.450	2.510	0.98525	0.98525	66.78	72.13	1.961E-02	1.961E-02	1.961E-02	
28	7402	2.610	2.600	0.992076	0.992076	65.60	74.69	2.648E-02	2.648E-02	2.648E-02	

PLOTRATE CRACK GROWTH ANALYSIS

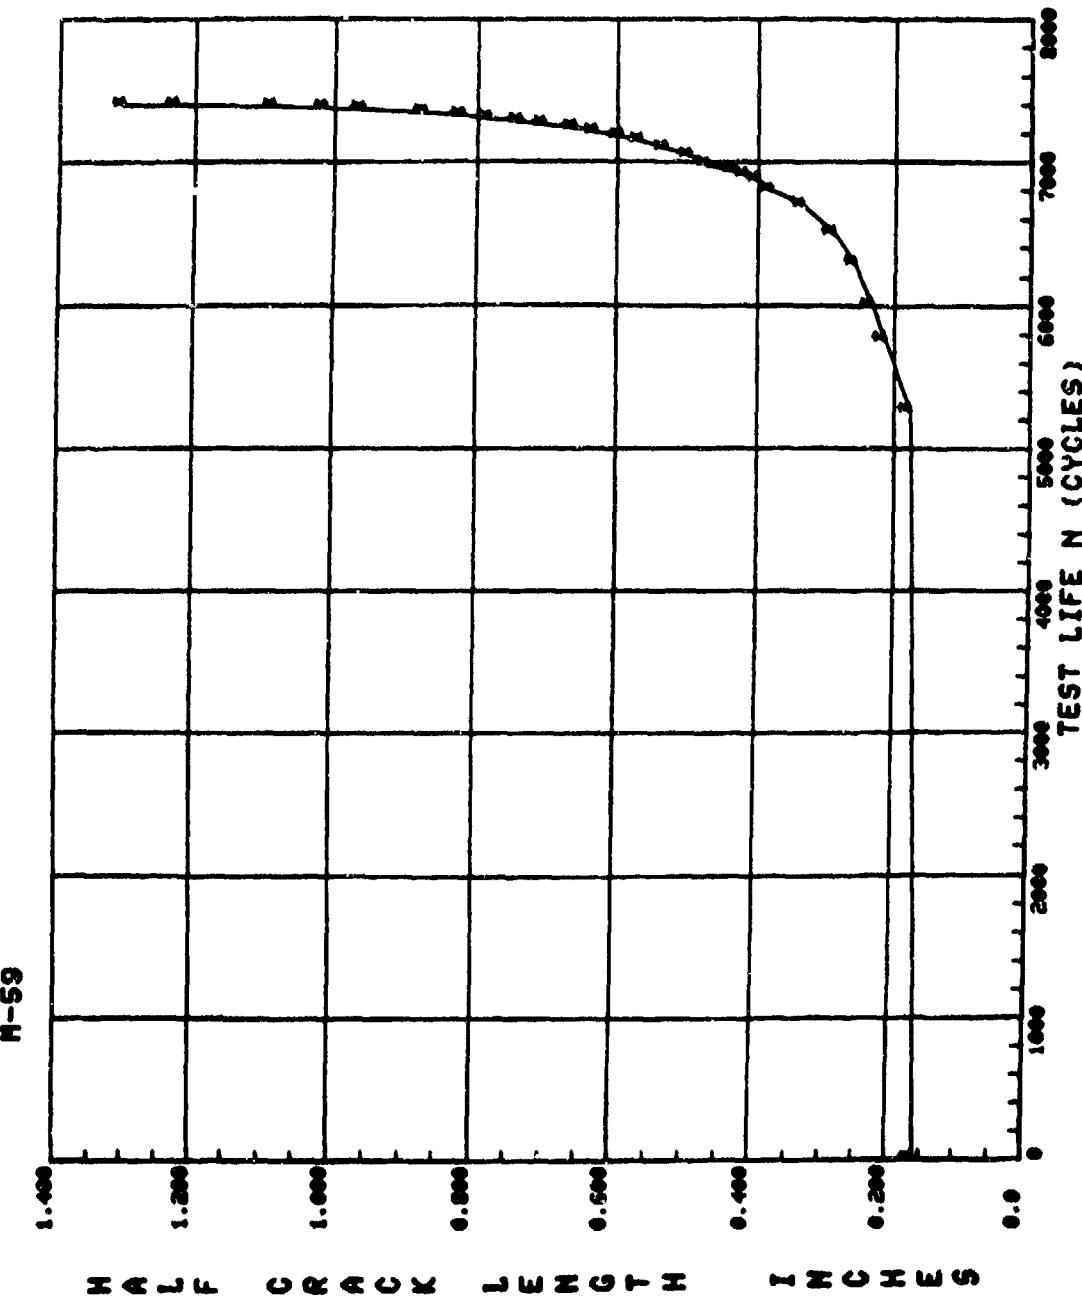


Figure 73. Crack growth curve for test M-59.

TABLE 72. DATA TABULATION FOR TEST M-60

SPECIMEN NO.: M-60	CCT SPECIMEN	b= 0.250 IN.	W= 6.000 IN.	A= 0.0	TEST FREQ= 6.00 Hz	ENVIRONMENT CONDITIONS: AMBIENT AIR					
						MIN=	MAX=	CYCLES	A MEASURED)	A REGRESSION)	MULT. COEF.
1	0.	0-200	0.300	0.999838	5.50	16.50	1.375E-06				
2	21000.	0.360	0.354	0.996260	5.98	17.94	1.413E-06				
3	34250.	0.395	0.391	0.994676	6.28	18.85	1.428E-06				
4	56000.	0.460	0.473	0.994599	6.92	20.76	2.232E-06				
5	68300.	0.525	0.526	0.998991	7.31	21.92	2.779E-06				
6	76000.	0.575	0.571	0.999523	7.61	22.64	3.175E-06				
7	84000.	0.625	0.625	0.997179	7.98	23.94	3.769E-06				
8	91000.	0.675	0.678	0.997562	8.32	24.95	4.415E-06				
9	98000.	0.735	0.741	0.998699	8.71	26.19	5.173E-06				
10	102500.	0.795	0.790	0.993944	9.01	27.02	6.334E-06				
11	107100.	0.820	0.852	0.994227	9.37	28.11	7.196E-06				
12	108612.	0.865	0.877	0.990441	9.51	28.53	8.113E-06				
13	110600.	0.910	0.894	0.991529	9.61	28.82	8.250E-06				
14	116000.	0.945	1.006	0.991253	10.24	30.71	1.144E-05				
15	118055.	1.065	1.057	0.990468	10.50	31.20	1.297E-05				
16	119254.	1.065	1.065	0.993638	10.65	31.95	1.309E-05				
17	120486.	1.123	1.123	0.993644	10.85	32.56	1.374E-05				
18	122163.	1.166	1.166	0.995089	11.00	32.23	1.547E-05				
19	123182.	1.260	1.199	0.992705	11.25	33.74	1.642E-05				

PLOT RATE CRACK GROWTH ANALYSIS
M-60

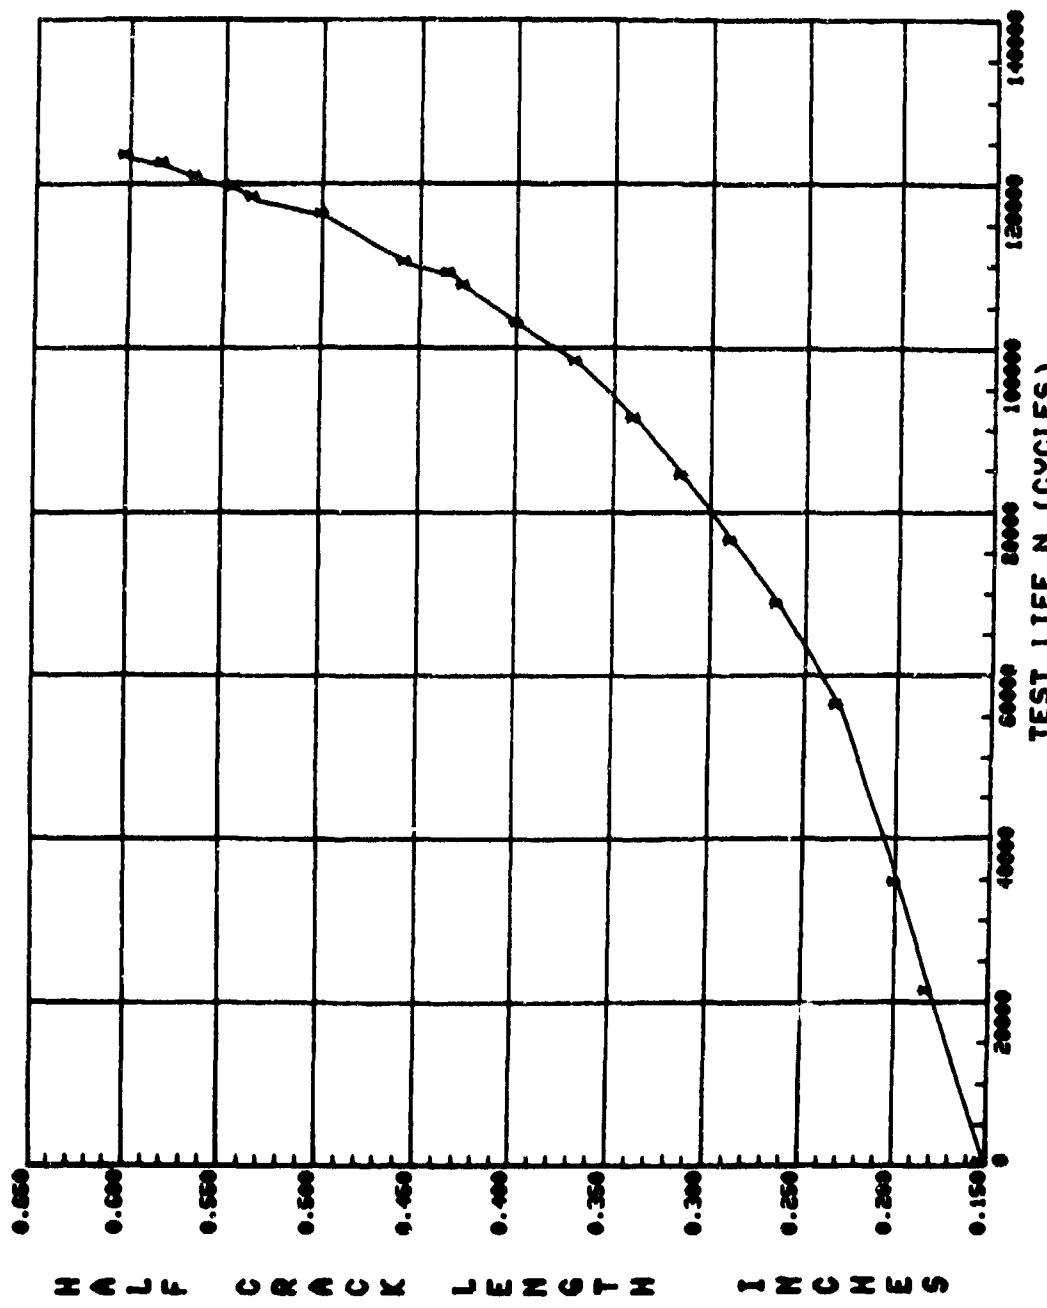


Figure 74. Crack growth curve for test M-60.

TABLE 73. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP IV -
SIMPLIFIED FLIGHT SPECTRUM

Test No.	Loading Profile	G-A-G Step		Flight Step		n_1 Cycle	n_2 Cycle	Comments
		σ_{Max} Ksi	σ_{Min} Ksi	σ' Min Ksi	σ'' Min Ksi			
M-61		20	-2	4		25		Typical fighter, air-to-air σ Lim = 40 Ksi & 30 Ksi
M-61a		15	-2	4		25		
M-62		18	-4	4		20		Typical fighter, air-to-ground σ Lim = 40 Ksi & 30 Ksi
M-62a		14	-4	4		20		
M-63		14	-2	4		10		Typical fighter, instrumentation and navigation σ Lim = 40 Ksi & 30 Ksi
M-63a		10	-2	4		10		
M-64		20	-3	4		22		Typical fighter, composite mission σ Lim = 40, 30 & 20 Ksi
M-64a		15	-3	4		22		
M-64b		10	-3	4		22		
M-65		12	-7.5	11.5		133		Typical transport
M-66		16.8	-10.5	16.1		133		Typical transport
M-69		20	-2	6	8	20	40	Typical fighter, air-to-air σ Lim = 40 Ksi & 30 Ksi
M-69a		12	-2	3	4	20	40	
M-70		18	-4	6	8	15	30	Typical fighter, air-to-ground σ Lim = 40 Ksi & 30 Ksi
M-70a		10	-4	3	4	15	30	

TABLE 73. METHODOLOGY DEVELOPMENT TESTING PROGRAM GROUP IV
SIMPLIFIED FLIGHT SPECTRUM (CONCL)

Test No.	Loading Profile	G-A-G Step		Flight Steps			n_1 Cyc	n_2 Cyc	n_3 Cyc	n_4 Cyc	Comments	
		σ'_{Max} Ksi	σ'_{Min} Ksi	σ''_{Min} Ksi	σ'''_{Min} Ksi							
M-71		14	-2	6	8		10	20			Typical fighter, instrumentation and navigation	
M-72		19	-3	6	8		15	35			Typical fighter, composite mission	
M-72a		14	-3	4	6		15	35			$\sigma'_{\text{Lim}} = 40, 30, \& 20$ Ksi	
M-72b		8	-3	2	3		15	35				
M-74		16.8	-10.5	15.4	16.1		25	108			Typical transport	
M-77		20	-3	-1	6	8	2	4	15	35	Typical fighter	
M-77a		14	-6	1	4	6	4	8	20	40	$\sigma'_{\text{Lim}} = 40$ Ksi & 30 Ksi	
M-78		18	-6	-1	4	8	4	8	20	40	Typical fighter	
						σ'''_{Min} Max	σ'_{Min} Max	n_1 n_5	n_2 n_6	n_3 n_5	n_4	
M-79		12	-7.5	-3.0	10	11.5	3.2	2	4	25	108	Typical transport
M-80		16.8	-10.5	-4.2	14	16.1	4.8	2	4	25	108	Typical transport

TABLE 74. DATA TABULATION FOR TEST M-61

SPECIMEN NO.: M-61		$\delta = 0.750$ IN.		$M = 6,000$ IN.		$A = 0.0$ IN.		TEST FREQ= 6.00 Hz.		
		PHASE		ENVIRONMENT CONDITION: AMBIENT AIR		A(MEASURED)		A(REGRESSION).		
NO.	CYCLES					MULT.	CORR. COEFF	M-MAX	DELTA K	DAY/N
1	0.	0.303	0.304	0.993863	13.83	22.13	7.588E-06			
2	1000.	0.330	0.322	0.996639	14.24	22.79	1.002E-05			
3	2500.	0.350	0.356	0.97810	14.99	23.92	1.221E-05			
4	5500.	0.495	0.451	0.998363	16.90	27.03	1.904E-05			
5	6500.	0.490	0.490	0.998902	17.62	28.20	2.142E-05			
6	7500.	0.525	0.537	0.992920	18.65	29.53	2.613E-05			
7	8500.	0.545	0.584	0.997660	19.26	30.81	2.710E-05			
8	9500.	0.640	0.643	0.98921	20.23	32.38	2.982E-05			
9	10500.	0.705	0.705	0.998700	21.22	33.95	3.347E-05			
10	11200.	0.760	0.752	0.997957	21.94	35.11	3.732E-05			
11	12000.	0.805	0.813	0.998133	22.85	36.57	4.193E-05			
12	12800.	0.880	0.880	0.998120	23.81	38.10	4.950E-05			
13	13600.	0.965	0.962	0.999247	24.97	39.96	6.123E-05			
14	14100.	1.020	1.027	0.999221	25.86	41.37	7.022E-05			
15	14600.	1.099	1.099	0.999623	26.82	42.91	7.887E-05			
16	15100.	1.185	1.184	0.998907	27.92	44.69	8.583E-05			
17	15500.	1.260	1.257	0.998787	28.86	46.18	9.433E-05			
18	15800.	1.315	1.310	0.989222	29.53	47.25	1.159E-04			
19	16100.	1.365	1.376	0.991441	30.38	48.41	1.273E-04			
20	16400.	1.445	1.457	0.991647	31.37	50.19	1.436E-04			
21	16700.	1.580	1.552	0.992069	32.53	52.95	1.603E-04			
22	16900.	1.615	1.623	0.994426	33.40	53.45	1.723E-04			
23	17100.	1.685	1.691	0.992379	34.24	54.78	1.883E-04			
24	17300.	1.760	1.757	0.999587	35.04	56.06	2.056E-04			
25	17500.	1.845	1.847	0.999726	36.14	57.82	2.451E-04			
26	17700.	1.920	1.946	0.998687	37.35	59.76	2.944E-04			
27	17900.	2.070	2.069	0.999050	38.87	62.19	3.567E-04			
28	18100.	2.210		0.999096	40.76	65.22	4.416E-04			

TABLE 74. DATA TABULATION FOR TEST M-61 (CONT.)

ECC. SPECIMEN	H-61	±1F ±1R FIGHTER MAX STRESS = 20 KSI	L= 0.250 IN.	W= 6.000 IN.	AH= 0.0 IN.	TEST FREQ= 6.00 HZ.	PHMAX=							
							NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. COEFF	K-MAX	DELTA K	DA/DK
ENVIRONMENT CONDITION: AMBIENT AIR														
29	19300.		2.410	2.410			0.997559	43.20				69.12		5.868E-04
30	19400.		2.520	2.528			0.998752	44.76				71.61		6.801E-04
31	19500.		2.655	2.670			0.997124	46.69				74.71		6.275E-04
32	19600.		2.690	2.840			0.995190	49.11				78.57		1.119E-03
33	19650.		2.925	2.951			0.995564	50.76				81.21		1.364E-03
34	19700.		3.075	3.090			0.992799	52.91				84.66		1.761E-03
35	19750.		3.265	3.268			0.997656	55.84				89.34		2.382E-03
36	19780.		3.395	3.423			0.996976	58.56				93.72		2.862E-03
37	19800.		3.548	3.548			0.997201	60.92				97.48		3.557E-03

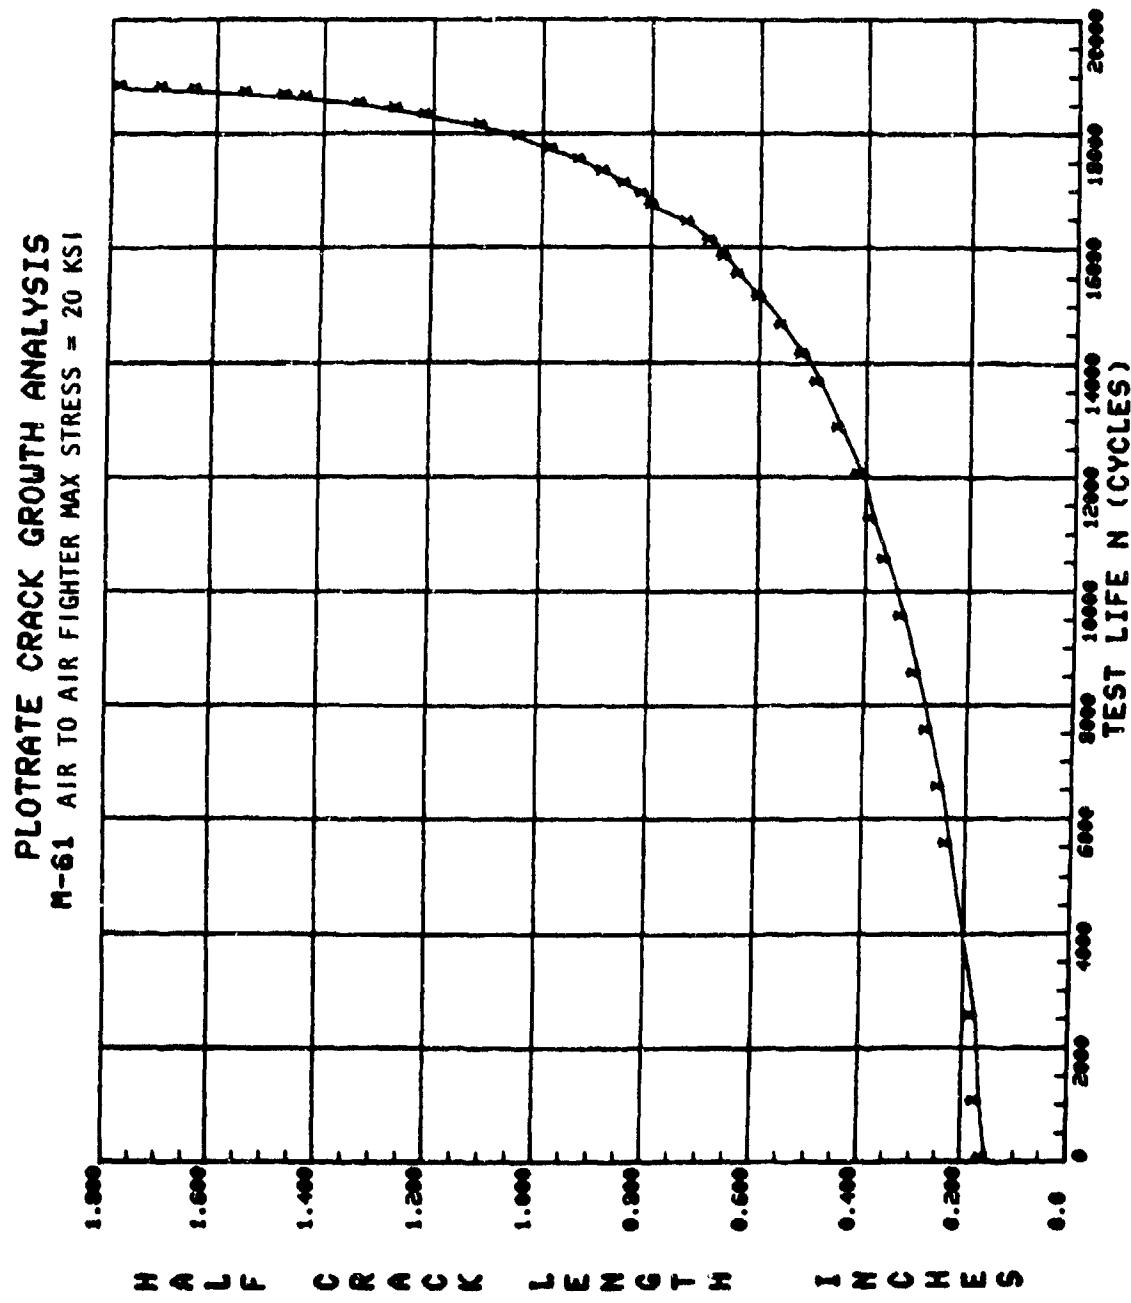


Figure 75. Crack growth curve for test M-61.

TABLE 75. DATA TABULATION FOR TEST M-61A

NO.	SPECIMEN NO.	ENVIRONMENT CONDITIONS:	AMBIENT AIR		TEST FREQ = 6.00 Hz.	
			CYCLES	AI MEASURED)	AI REGRESSION)	
1	0.	0.250 IN.	0.310	0.310	0.998174	10.45
2	5700.	0.355	0.352	0.99873	11.17	2.933E-06
3	11306.	0.402	0.406	0.998016	12.00	4.287E-06
4	25100.	0.455	0.453	0.991713	12.70	5.605E-06
5	18800.	0.502	0.513	0.984474	13.52	7.696E-06
6	21000.	0.550	0.552	0.982699	14.04	8.247E-06
7	23000.	0.615	0.590	0.983134	14.53	9.255E-06
8	26500.	0.645	0.671	0.984361	15.52	1.070E-05
9	26400.	0.725	0.719	0.967962	16.07	1.265E-05
10	30500.	0.789	0.778	0.992302	16.75	1.420E-05
11	32300.	0.845	0.849	0.956843	17.53	1.643E-05
12	36000.	0.972	0.911	0.979495	16.20	1.866E-05
13	35500.	0.975	0.985	0.972593	18.96	2.062E-05
14	36700.	1.030	1.047	0.972365	19.59	2.323E-05
15	36700.	1.090	1.049	0.973126	19.61	2.448E-05
16	34600.	1.135	1.144	0.970966	20.56	2.614E-05
17	39600.	1.190	1.191	0.980270	21.01	2.776E-05
18	39600.	1.222	1.249	0.997804	21.57	2.933E-05
19	41500.	1.315	1.313	0.999498	22.16	3.102E-05
20	42400.	1.377	1.379	0.999458	22.80	3.293E-05
21	43300.	1.450	1.452	0.999677	23.48	4.004E-05
22	44300.	1.567	1.566	0.999819	24.34	4.484E-05
23	45200.	1.645	1.645	0.999864	25.26	5.232E-05
24	46050.	1.750	1.754	0.999889	26.25	6.007E-05
25	46850.	1.870	1.870	0.999020	27.32	6.829E-05
26	47500.	1.970	1.969	0.998797	28.22	7.934E-05
27	49100.	2.075	2.065	0.996676	29.12	8.791E-05
28	49870.	2.195	2.203	0.995949	30.41	1.057E-04

TABLE 75. DATA TABULATION FOR TEST M-61A (CONCL)

SPECIMEN NO.: M-61A	TYP FIGHTER AIR TO AIR. STRESS = 15 KSI MAX	GCT SPECIMEN D= 0.250 IN.	H= 6.000 IN.	A= 0.0	TEST FREQ= 6.00 Hz.
PRIM=	PHAS=	ENVIRONMENT CONDITION: AMBIENT AIR			
NO.	CYCLES	AM(MEASURED)	A(REGRESSION)	MULT. COEF.	B-MAX
29	49270.	2.260	2.285	0.997574	31.19
30	49636-	2.380	2.376	0.999767	32.07
31	49940-	2.475	2.477	0.999704	33.06
32	50252-	2.575	2.579	0.999632	34.06
33	50462-	2.670	2.667	0.999593	34.99
34	50706-	2.765	2.764	0.999546	36.01
35	50919-	2.860	2.867	0.999479	37.13
36	51077-	2.955	2.952	0.999400	38.08
37	51253-	3.060	3.059	0.999367	39.32
38	51400-	3.160	3.163	0.999187	40.56
39	51530-	3.260	3.265	0.999698	41.84
40	51626-	3.355	3.352	0.999071	42.97
41	51722-	3.450	3.452	0.997755	44.34
42	51812-	3.555	3.566	0.998117	45.96
43	51867-	3.645	3.648	0.999321	47.19
44	51913-	3.735	3.730	0.98757	48.48
45	51967-	3.840	3.848	0.997641	50.46
46	52003-	3.935	3.942	0.992746	52.12
47	52033-	4.035	4.042	0.997712	54.02
48	52071-	4.130	4.143	0.998274	56.08
49	52073-	4.230	4.229	0.996647	57.95

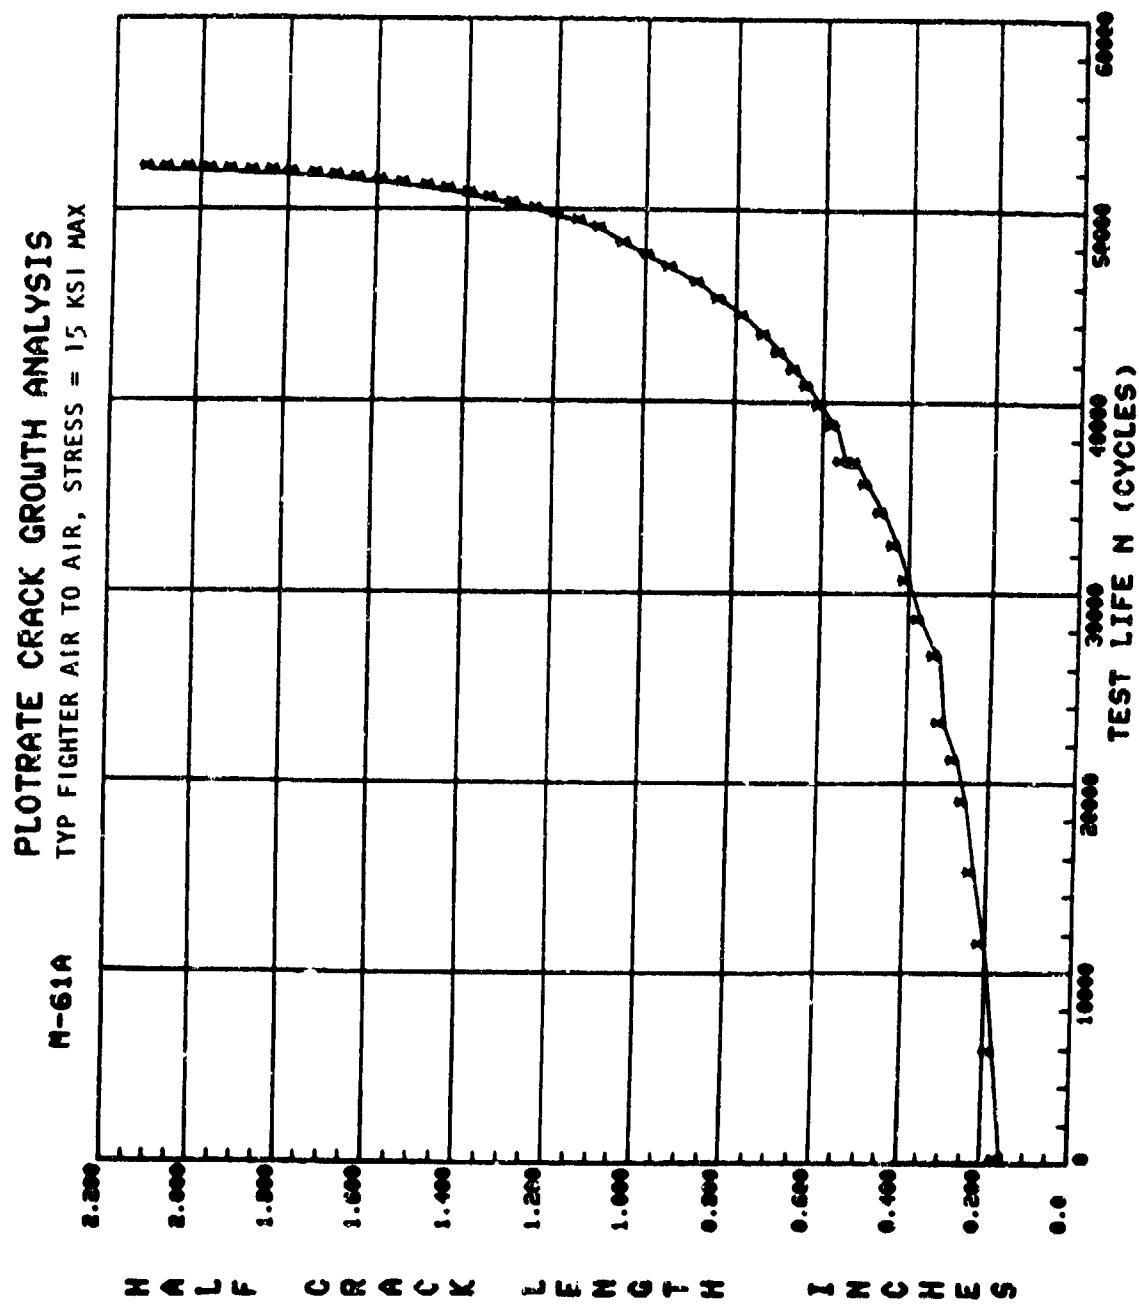


Figure 76. Crack growth curve for test M-61A.

TABLE 76. DATA TABULATION FOR TEST N-62

SPECIMEN NO.:	CCT	SPECIMEN	$R = 0.250$ IN.	$K = 6,000$ IN.	$A_N = 0.0$ IN.	$P_{MAX} =$	TEST FREQ= 6.00 Hz.							
							ENVIRONMENT CONDITION: AMBIENT AIR	A MEASURED	A REGRESSION	MULT. CORR.	Coeff.	R-MAX	DEFLAK	DAM
1	1	0.	0.290	0.290	0.999982	12.17	14.67	0.5302E-05						
2	2	3100.	0.350	0.349	0.999978	13.36	16.33	1.0644E-05						
3	3	5740.	0.410	0.410	0.9999844	14.49	17.70	1.2711E-05						
4	4	7980.	0.470	0.471	0.9999526	15.54	16.99	1.5086E-05						
5	5	9320.	0.510	0.511	0.9999474	16.20	19.90	1.6925E-05						
6	6	11040.	0.570	0.571	0.9972341	17.14	20.75	1.9285E-05						
7	7	12500.	0.630	0.631	0.9996119	18.04	22.05	2.3765E-05						
8	8	13520.	0.680	0.683	0.996316	18.79	22.97	2.4235E-05						
9	9	14390.	0.730	0.728	0.996666	19.42	23.74	2.5915E-05						
10	10	15170.	0.750	0.770	0.995005	19.99	24.43	2.7795E-05						
11	11	16440.	0.830	0.840	0.992956	20.93	25.58	3.2235E-05						
12	12	17130.	0.890	0.892	0.994626	21.47	26.24	3.7315E-05						
13	13	17750.	0.930	0.929	0.991172	22.05	26.95	4.2115E-05						
14	14	18340.	0.985	0.985	0.99754	22.76	27.82	4.6355E-05						
15	15	18935.	1.045	1.043	0.99927	23.46	28.67	5.1971E-05						
16	16	19475.	1.100	1.099	0.998324	24.13	29.50	5.7625E-05						
17	17	20015.	1.155	1.162	0.997952	24.88	30.41	6.7645E-05						
18	18	20362.	1.210	1.209	0.999150	25.42	31.06	7.6515E-05						
19	19	20763.	1.270	1.272	0.999654	26.15	31.96	8.2205E-05						
20	20	21085.	1.335	1.330	0.998767	26.81	32.77	9.1685E-05						
21	21	21385.	1.385	1.384	0.999954	27.42	33.51	9.8335E-05						
22	22	21718.	1.445	1.450	0.998242	28.16	34.41	1.1125E-04						
23	23	21927.	1.500	1.494	0.999662	28.64	35.01	1.1795E-04						
24	24	22371.	1.605	1.610	0.999573	29.92	36.57	1.4365E-04						
25	25	22701.	1.715	1.709	0.999260	31.01	37.90	1.6825E-04						
26	26	23009.	1.815	1.816	0.999688	32.20	39.36	1.9155E-04						
27	27	23300.	1.930	1.934	0.999461	33.49	40.93	2.1295E-04						
28	28	23615.	2.065	2.076	0.999642	35.08	42.88	2.5675E-04						

TABLE 76. DATA TABULATION FOR TEST M-62 (CONCL)

CCT	SPECIMEN	TYPICAL FIGHTER, AIR-TO-GROUND, MAX STRESS = 18 KSI		PHMAX=	W= 6,000 lb.	AN= 0.0	IM=	TtS1 FREQ= 6.00 Hz.	JA/DR
		b= 0.750 in.	W= 6,000 lb.						
ENVIRONMENT CONDITION: AMBIENT AIR									
NU.	CYCLTS	AIRFASURID	AIRFREGRESSION	MULT.	CORR.	COEFF	K-MAX	DELTA K	
29	23903.	2.225	2.233	0.999393			36.84	45.02	3.003E-04
30	24100.	2.315	2.356	0.999241			39.27	45.77	3.024E-04
31	24300.	2.495	2.498	0.999770			39.93	45.80	3.086E-04
32	24400.	2.540	2.579	0.999206			40.90	49.99	4.027E-04
33	24500.	2.670	2.665	0.999127			41.96	51.28	4.709E-04
34	24600.	2.720	2.759	0.999112			43.15	52.74	5.420E-04
35	24700.	2.670	2.860	0.996826			44.46	54.34	6.295E-04
36	24800.	2.990	2.989	0.998482			46.20	56.47	7.647E-04
37	24900.	3.125	3.153	0.997504			48.53	59.41	9.650E-04
38	25000.	3.265	3.360	0.997024			51.70	63.15	1.211E-03
39	25080.	3.556	3.590	0.993817			55.59	67.94	1.136E-03
40	25100.	3.645	3.664	0.987980			56.93	69.58	2.437E-03
41	25120.	3.735	3.741	0.999101			55.40	71.37	4.825E-03
42	25140.	3.820	3.859	0.999476			60.71	74.20	5.343E-03
43	25160.	4.015	4.005	0.999916			63.37	70.18	4.722E-03

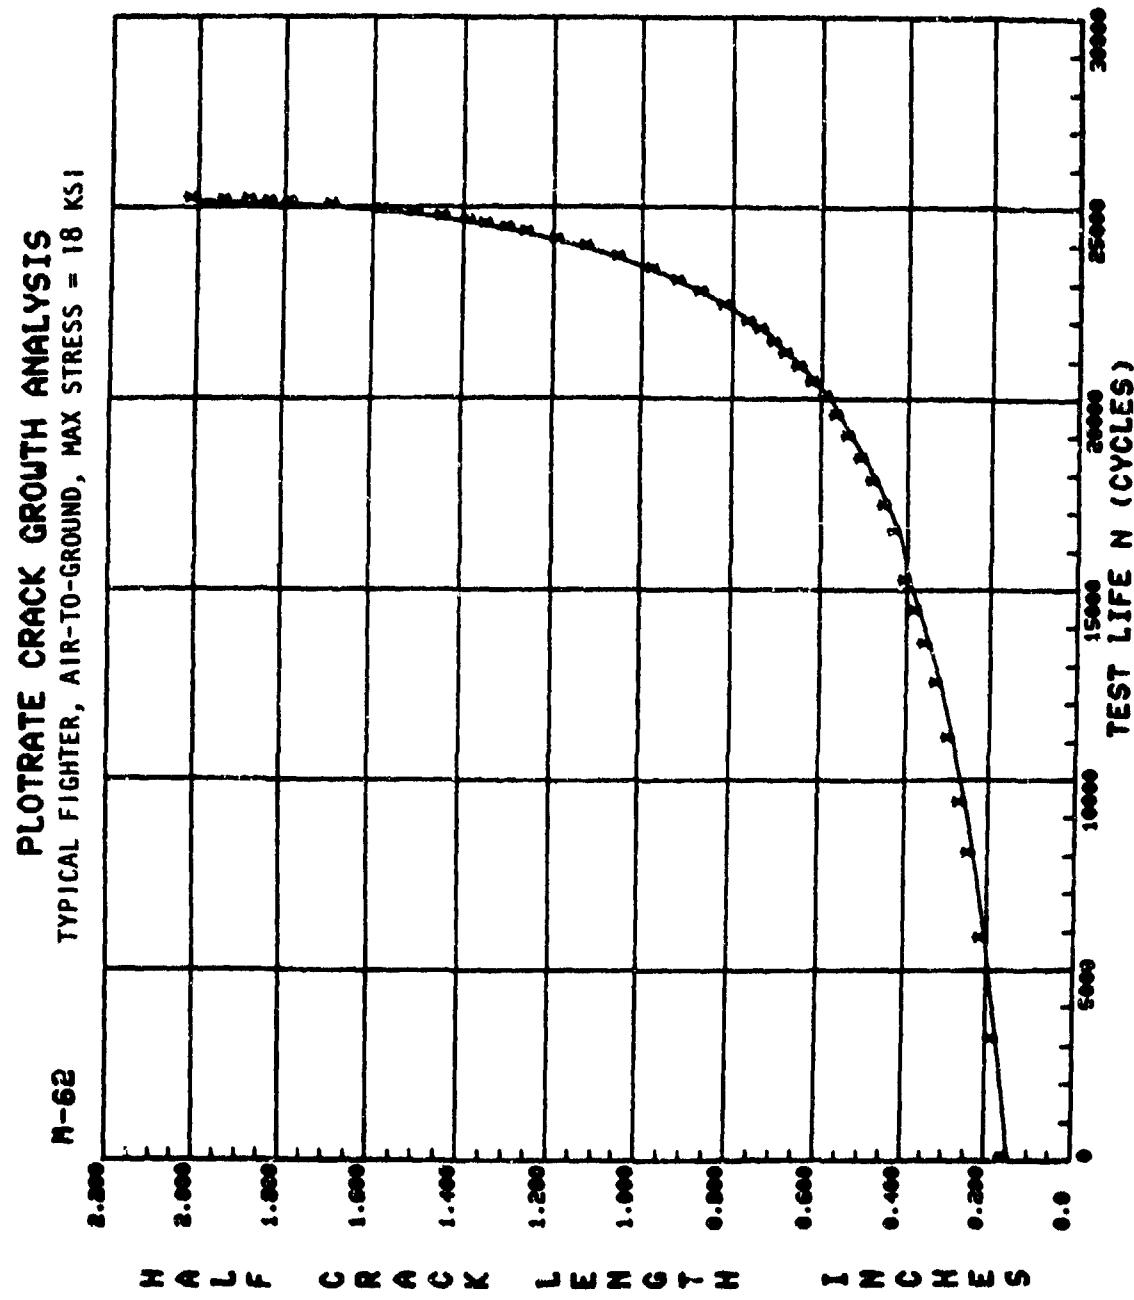


Figure 77. Crack growth curve for test M-62.

TABLE 77. DATA TABULATION FOR TEST M-62A

SPECIMEN NO.: M-62A TYP FIGHTER AIR TO GROUND, STRESS = 14 KSI MAX

CCT	SPECIMEN	E= 0.250 IN.	Y= 6.000 IN.	AHE 0.0 IN.	TEST FREQ= 6.00 Hz.					
					PHASE	ENVIRONMENT CONDITION: AMBIENT AIR	AC(MEASURED)	AIRREGRESSION)	MULT. CORR.	CORR.
NO.	CYCLES								E-MAX	DETAILS
1	0.	0.460	0.460	0.996191	11.95	15.36	4.721E-06			
2	5700.	0.530	0.523	0.997571	12.74	16.38	6.535E-06			
3	9500.	0.570	0.578	0.978299	13.41	17.25	7.922E-06			
4	12500.	0.630	0.629	0.998589	14.01	18.01	9.078E-06			
5	15300.	0.685	0.682	0.998206	14.60	16.78	9.924E-06			
6	18000.	0.740	0.742	0.998823	15.25	19.41	1.081E-05			
7	20250.	0.793	0.790	0.999358	15.75	20.20	1.159E-05			
8	22690.	0.845	0.847	0.999166	16.34	21.01	1.285E-05			
9	24661.	0.695	0.698	0.979341	16.85	21.66	1.432E-05			
10	26429.	0.930	0.949	0.999945	17.35	22.31	1.587E-05			
11	28106.	1.005	1.005	0.999792	17.89	23.60	1.788E-05			
12	29367.	1.052	1.051	0.999997	18.32	23.56	1.922E-05			
13	31000.	1.115	1.120	0.997676	16.95	24.35	2.137E-05			
14	32358.	1.180	1.161	0.997567	19.52	25.10	2.307E-05			
15	33328.	1.238	1.228	0.974448	19.94	25.66	2.377E-05			
16	34658.	1.265	1.293	0.997166	20.53	26.39	2.523E-05			
17	35246.	1.325	1.322	0.997387	20.78	26.71	2.559E-05			
18	36320.	1.375	1.372	0.928218	21.24	27.31	2.780E-05			
19	37305.	1.435	1.430	0.997790	21.72	27.93	3.207E-05			
20	38225.	1.485	1.491	0.999338	22.25	28.61	3.572E-05			
21	39273.	1.570	1.576	0.997361	22.98	29.34	3.964E-05			
22	40373.	1.675	1.676	0.998447	23.78	30.58	4.322E-05			
23	41450.	1.775	1.767	0.997939	24.61	31.64	4.770E-05			
24	42615.	1.870	1.879	0.997627	25.27	32.47	5.280E-05			
25	43550.	1.967	1.975	0.998280	26.40	33.94	6.099E-05			
26	44274.	2.070	2.064	0.999561	27.16	34.92	6.921E-05			
27	45910.	2.165	2.172	0.999357	28.11	36.14	8.037E-05			
28	45580.	2.270	2.262	0.998795	28.94	37.21	9.209E-05			

TABLE 77. DATA TABULATION FOR TEST M-62A (CONCL)

SPECIMEN NO.: M-62A TYP FIGHTER AIR TO GROUND, STRESS = 14 KSI MAX

ENVIRONMENT CONDITION: AMBIENT AIR	TEST FREQ= 6.00 Hz.	AM= 0.0	W= 6.000 IN.	B= 0.750 IN.	CLL SPECIMEN	P <small>MAX</small> =
NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. COEF	K-MAX	DA/DN
29	46079.	2.255	2.359	0.999465	29.77	1.349E-34
30	46557.	2.460	2.465	0.999462	30.74	1.197E-04
31	46895.	2.550	2.546	0.999848	31.50	1.330E-04
32	47269.	2.650	2.651	0.999536	32.50	1.496E-04
33	47566.	2.740	2.742	0.999600	33.39	1.662E-04
34	47835.	2.835	2.833	0.999851	34.31	1.824E-04
35	48137.	2.945	2.946	0.999166	35.50	2.135E-04
36	48345.	3.040	3.039	0.999432	36.48	2.357E-04
37	48565.	3.140	3.140	0.999096	37.66	48.42
38	48712.	3.235	3.227	0.999114	36.60	49.62
39	48947.	3.345	3.374	0.998390	40.38	51.92
40	49114.	3.500	3.499	0.997762	42.00	54.00
41	49228.	3.590	3.601	0.997826	43.39	55.79
42	49319.	3.695	3.700	0.998506	44.81	57.62
43	49389.	3.785	3.787	0.999220	46.13	59.31
44	49461.	3.905	3.902	0.997314	47.96	61.69
45	49520.	4.000	4.015	0.994942	49.93	64.20
46	49528.	4.095	4.107	0.995572	51.64	66.60
47	49587.	4.185	4.192	0.999467	53.32	68.55
48	49604.	4.275	4.275	0.949616	55.06	70.79

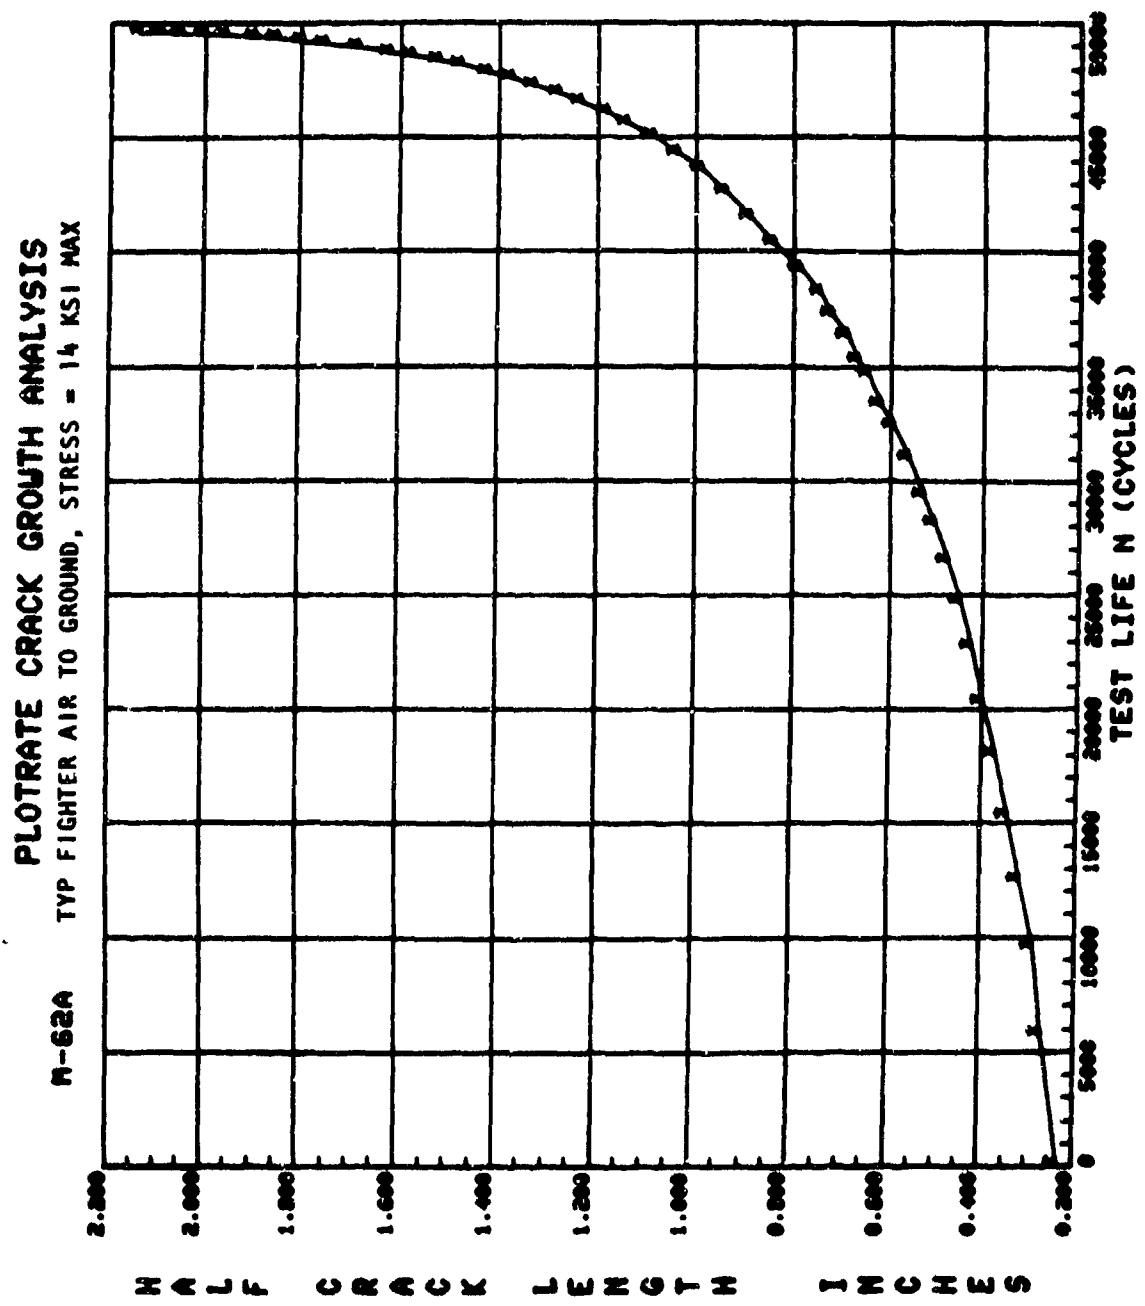


Figure 78. Crack growth curve for test M-62A.

TABLE 78. DATA TABULATION FOR TEST N-63

SPECIMEN NO.:	N-63	TYPICAL FIGHTER, INSTRUMENTATION AND NAVIGATION, MAX STRESS = 14 KSI		
C.C.T. - SPECIMEN	B= 0.250 IN.	M= 0.000 IN.	AW= 0.0 IN.	TEST FREQ= 6.00 HZ.
P MIN=				
ENVIRONMENT CONDITIONS: AMBIENT AIR				
NO.	CYCLES	AI(MEASUR(FD))	AI(REGRESSION)	MULT. CORR. COEFF
1	0.	0.313	0.312	0.999973
2	6350.	0.355	0.352	0.997616
3	13000.	0.403	0.401	0.997158
4	18750.	0.450	0.458	0.9971603
5	22500.	0.500	0.500	0.9999016
6	25200.	0.520	0.545	0.9997646
7	29300.	0.600	0.602	0.9977717
8	32350.	0.650	0.657	0.9996153
9	34500.	0.710	0.701	0.998314
10	36900.	0.755	0.758	0.998381
11	38850.	0.805	0.807	0.998296
12	40400.	0.855	0.851	0.998946
13	42600.	0.910	0.914	0.998164
14	44100.	0.960	0.962	0.997718
15	45200.	1.010	1.002	0.997248
16	46100.	1.030	1.037	0.997264
17	47100.	1.060	1.075	0.995845
18	48100.	1.115	1.116	0.997713
19	49100.	1.160	1.164	0.996480
20	50100.	1.220	1.215	0.999243
21	51100.	1.270	1.273	0.999201
22	52100.	1.335	1.334	0.999555
23	53500.	1.430	1.427	0.999656
24	54100.	1.460	1.461	0.999720
25	55100.	1.535	1.537	0.999082
26	56100.	1.615	1.621	0.999059
27	57100.	1.720	1.709	0.998733
28	58100.	1.605	1.606	0.996709

DAWN	11.46	3.240E-06
DELTA K	12.17	3.463E-06
DELTA K	13.00	4.472E-06
DELTA K	13.90	5.595E-06
DELTA K	14.54	6.428E-06
DELTA K	15.19	7.649E-06
DELTA K	15.90	8.828E-06
DELTA K	16.72	9.950E-06
DELTA K	17.23	1.101E-05
DELTA K	17.99	1.213E-05
DELTA K	18.59	1.317E-05
DELTA K	19.11	1.455E-05
DELTA K	19.84	1.593E-05
DELTA K	20.40	1.762E-05
DELTA K	20.84	1.943E-05
DELTA K	21.23	2.136E-05
DELTA K	21.64	2.095E-05
DELTA K	22.08	2.231E-05
DELTA K	22.50	2.560E-05
DELTA K	23.13	2.677E-05
DELTA K	23.74	2.909E-05
DELTA K	24.36	3.097E-05
DELTA K	25.32	3.402E-05
DELTA K	25.46	3.461E-05
DELTA K	26.42	3.945E-05
DELTA K	27.26	4.284E-05
DELTA K	28.13	4.768E-05
DELTA K	29.10	5.304E-05

TABLE 78. DATA TABULATION FOR TEST M-63 (CONCL)

TEST SPECIMEN	L= 0.250 IN.	W= 6.000 IN.	AM= 0.0 IN.	TEST FREQ= 6.00 Hz.	
				MAX=	ENVIRONMENT CONDITIONS: AMBIENT AIR
No.	CYCLES	AM MEASURED	AIRPRESSURE:	MULT. COEF. - COEFF	K-MAX
29	59100.	1.905	1.91	0.998224	25.85
30	60100.	2.040	2.032	0.999272	26.88
31	61100.	2.180	2.179	0.997905	28.17
32	62100.	2.370	2.355	0.993748	29.74
33	63100.	2.605	2.585	0.974366	31.87
34	64100.	2.940	3.001	0.981186	36.06
35	65100.	3.485	3.670	0.986771	44.37
36	65600.	4.205	4.188	0.991253	53.24
				DAWG	DELTA K
				6.107E-05	30.15
				7.250E-05	31.36
				9.170E-05	32.86
				1.244E-04	34.70
				1.927E-04	37.18
				2.903E-04	42.06
				4.529E-04	51.77
				6.430E-04	62.12

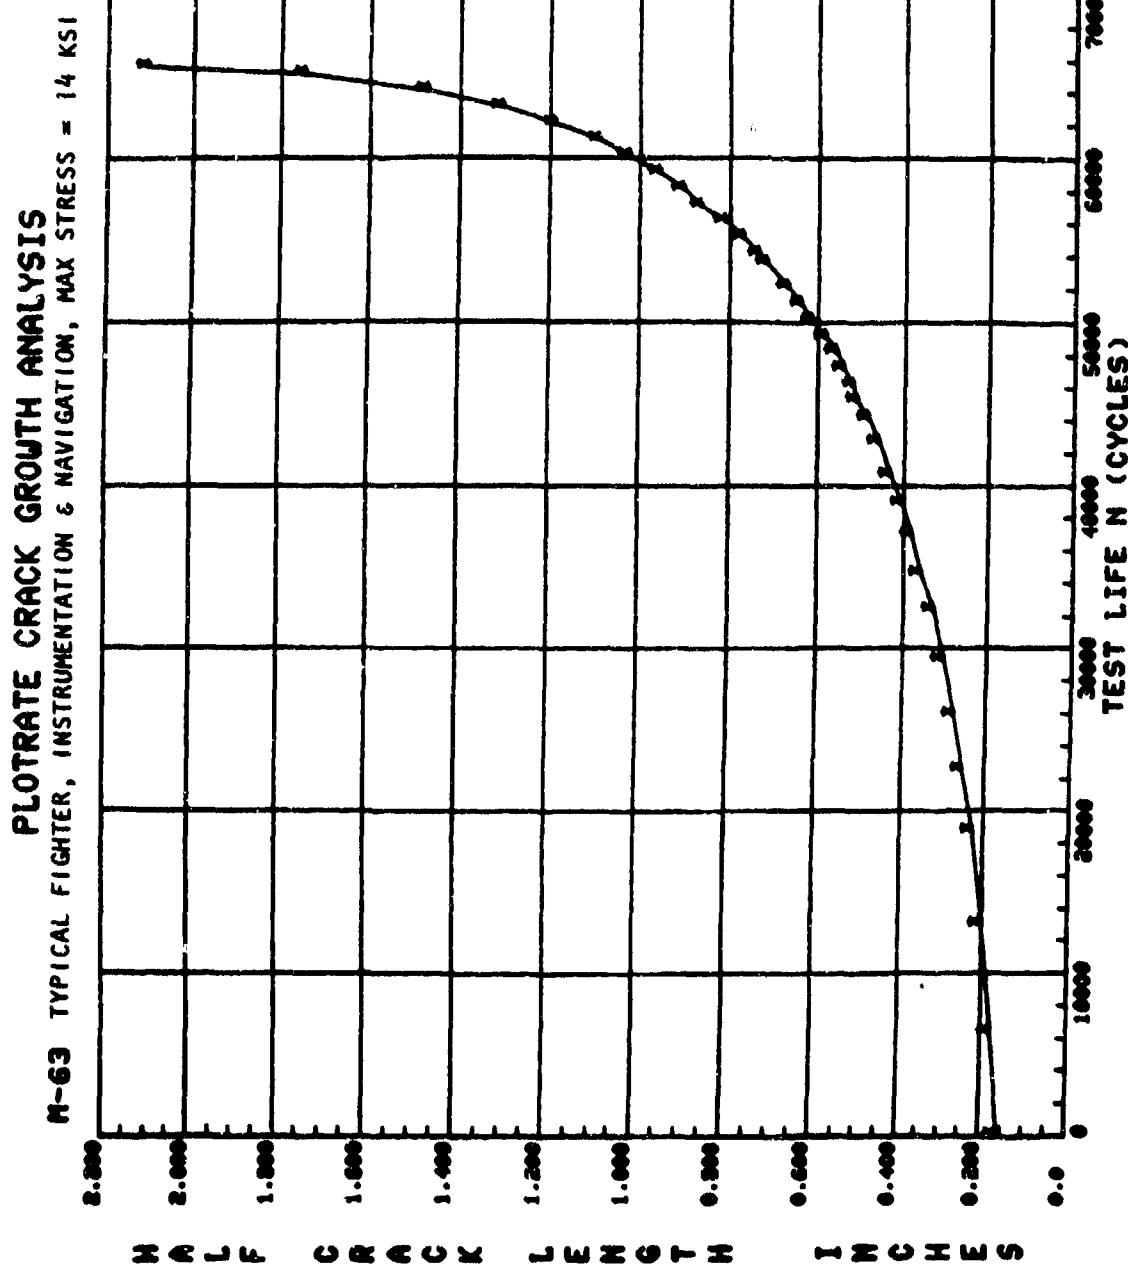


Figure 79. Crack growth curve for test M-63.

TABLE 79. DATA TABULATION FOR TEST M-63A

SPECIMEN NO.: M-63A TEST FREQUENCY: 6.00 Hz.

CCT SPECIMEN $\theta = 0.250$ IN. $H = 6.000$ IN. $A_{\text{Net}} = 0.0$ IN.
P_{MIN} =

TEST FREQUENCY: 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR
P_{MAX} =

NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR. COEFF.	R-MAX	DELTA K	DAWN
1	0	0.295	0.295	0.999878	6.52	8.18	1.114E-06
2	20000.	0.335	0.330	0.992748	7.21	8.66	8.786E-07
3	40000.	0.370	0.365	0.995344	7.59	9.11	9.425E-07
4	60000.	0.345	0.405	0.996665	8.00	9.59	1.020E-06
5	80000.	0.450	0.445	0.997538	8.39	10.06	1.132E-06
6	100000.	0.495	0.492	0.997254	8.83	10.52	1.323E-06
7	120000.	0.543	0.549	0.994295	9.34	11.20	1.621E-06
8	133700.	0.590	0.592	0.998134	9.70	11.64	1.943E-06
9	146522.	0.640	0.644	0.997076	10.13	12.15	2.164E-06
10	153000.	0.640	0.676	0.997470	10.38	12.46	2.219E-06
11	162400.	0.725	0.718	0.994629	10.71	12.96	2.450E-06
12	172360.	0.765	0.767	0.9925154	11.05	13.30	2.641E-06
13	185000.	0.826	0.833	0.996231	11.57	13.89	3.178E-06
14	192600.	0.890	0.894	0.994960	11.94	14.32	3.295E-06
15	201700.	0.945	0.952	0.991882	12.42	14.90	3.580E-06
16	208900.	1.015	1.000	0.9935240	12.74	15.29	4.100E-06
17	216060.	1.060	1.063	0.994401	13.17	15.80	4.748E-06
18	224000.	1.115	1.142	0.994624	12.69	16.42	5.598E-06
19	228000.	1.200	1.184	0.987462	13.96	16.75	6.028E-06
20	232000.	1.250	1.239	0.988194	14.31	17.18	6.319E-06
21	236000.	1.290	1.297	0.992630	14.69	17.62	6.766E-06
22	240000.	1.245	1.343	0.9999150	14.97	17.97	6.763E-06
23	244000.	1.395	1.398	0.999605	15.32	18.38	7.297E-06
24	248000.	1.460	1.457	0.998765	15.68	16.82	8.260E-06
25	252000.	1.536	1.531	0.995985	16.14	19.37	8.868E-06
26	258000.	1.635	1.644	0.996894	16.83	20.19	9.950E-06
27	264000.	1.790	1.767	0.996869	17.58	21.10	1.129E-05
28	268000.	1.840	1.858	0.996963	18.14	21.76	1.226E-05

TABLE 79. DATA TABULATION FOR TEST M-63A (CONCL)

SPECIMEN NO.:	B= 0.250 IN.	Y= 6.000 IN.	A= 0.0 IN.	TEST FREQ= 6.00 Hz.			
NO.	CYCLES	AI MEASURED	AI REGRESSION	MULT. COEFF	K-MAX	DELTA K	DA/DN
ENVIRONMENT CONDITION: AMBIENT AIR							
29	273000.	1.960	1.964	0.996578	16.91	22.69	1.608E-05
30	277000.	2.100	2.093	0.998973	19.58	23.50	1.615E-05
31	280500.	2.210	2.218	0.999616	20.36	24.44	1.627E-05
32	283450.	2.335	2.335	0.999799	21.11	25.33	2.045E-05
33	286191.	2.445	2.442	0.999863	21.81	26.17	2.250E-05
34	288429.	2.542	2.547	0.999866	22.51	27.01	2.439E-05
35	290164.	2.635	2.632	0.999504	23.08	27.70	2.654E-05
36	292053.	2.735	2.734	0.999455	23.79	28.55	2.952E-05
37	293828.	2.835	2.836	0.989513	24.67	29.61	2.766E-05
38	295336.	2.945	2.954	0.956753	25.40	30.48	2.986E-05
39	296568.	3.040	3.036	0.916203	26.03	31.23	3.398E-05
40	299919.	3.140	3.302	0.660135	26.41	33.85	4.837E-05
41	298993.	3.240	3.191	0.676046	27.27	32.73	5.426E-05
42	300017.	3.358	3.306	0.876150	28.25	33.89	6.799E-05
43	300628.	3.445	3.390	0.665521	28.99	34.78	7.412E-05
44	301325.	3.530	3.532	0.998721	30.31	36.37	7.350E-05
45	301876.	3.605	3.611	0.948765	31.09	37.31	8.192E-05
46	302462.	3.710	3.708	0.999157	32.09	36.50	9.636E-05
47	302891.	3.792	3.792	0.999460	33.01	39.61	1.093E-04
48	303459.	3.917	3.926	0.999296	34.50	41.47	1.312E-04
49	303832.	4.032	4.026	0.998022	35.81	42.97	1.574E-04
50	304163.	4.125	4.135	0.998159	37.28	44.73	1.865E-04
51	304361.	4.200	4.209	0.997642	38.34	46.01	2.153E-04
52	304529.	4.290	4.279	0.998412	39.39	47.27	2.486E-04
53	304751.	4.387	4.396	0.994934	41.32	49.56	3.257E-04
54	304889.	4.460	4.486	0.992388	42.94	51.52	4.195E-04
55	305064.	4.570	4.584	0.996416	44.64	53.81	5.298E-04
56	305118.	4.700	4.715	0.997262	47.73	57.27	7.010E-04

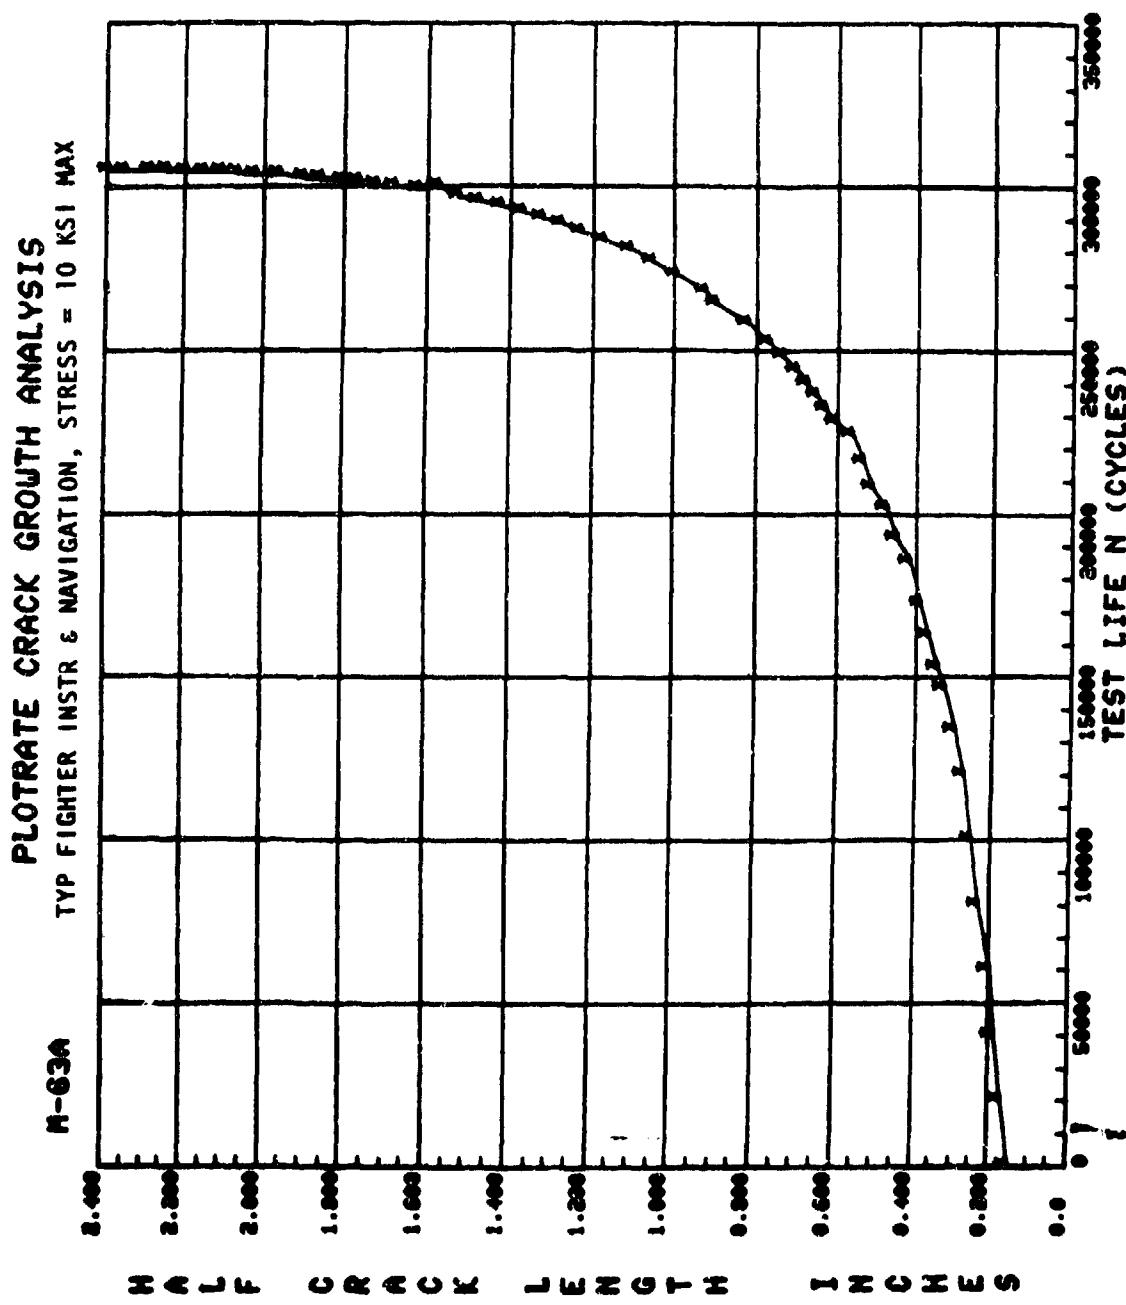


Figure 80. Crack growth curve for test M-63A.

TABLE 80. DATA TABULATION FOR TEST N-64

SPECIMEN NO.:	N-64	TYPICAL FIGHTER, COMPOSITE MISSION, MAX STRESS = 20 KSI		
CLL. SPECIMEN	R= 0.250 IN.	W= 6.000 IN.	A= 0.0 IN.	
PHIN=	PMAX=	TEST FREQ= 6.00 Hz.		
ENVIRONMENT CONDITION: AMBIENT AIR				
IND.	CYCLES	AM MEASURED)	AIRGRESSION)	MULT. CORR. COEFF
1	0.	0.313	0.312	0.997779
2	2000.	0.355	0.366	0.992110
3	4000.	0.435	0.428	0.993908
4	5000.	0.470	0.462	0.993320
5	6000.	0.490	0.501	0.991999
6	7000.	0.515	0.536	0.998065
7	8000.	0.550	0.566	0.995241
8	9000.	0.645	0.649	0.999683
9	10000.	0.720	0.717	0.998855
10	11000.	0.800	0.798	0.997270
11	11700.	0.855	0.865	0.997351
12	12400.	0.940	0.945	0.997470
13	12800.	1.005	1.000	0.999060
14	13200.	1.060	1.069	0.998897
15	13690.	1.150	1.146	0.998308
16	13800.	1.190	1.188	0.998567
17	14000.	1.230	1.238	0.998730
18	14200.	1.290	1.288	0.998626
19	14400.	1.345	1.342	0.998992
20	14600.	1.400	1.399	0.998965
21	14820.	1.460	1.463	0.999565
22	14990.	1.520	1.517	0.999651
23	15280.	1.625	1.626	0.994857
24	15510.	1.725	1.727	0.999650
25	15720.	1.835	1.832	0.999773
26	15907.	1.935	1.940	0.999422
27	16059.	2.040	2.040	0.999603
28	16186.	2.133	2.130	0.999717

TABLE 80. DATA TABULATION FOR TEST M-64 (CONCL.)

SPECIMEN NO.: M-64 TYPICAL FIGHTER, COMPOSITE MISSION, MAX STRESS = 20 KSI

CCT	SPECIMEN	B= 0.250 IN.	W= 6.000 IN.	A _N = 0.0	I _N =	TEST FREQ= 6.00 Hz.
P _{MIN} =	P _{MAX} =	ENVIRONMENT CONDITION: AMBIENT AIR				
NO.	CYCLES	AS MEASURED)	AI REGRESSION)	MULT. COEF. COEFF	K-MAX	DELTA K
29	16321.	2.250	2.243	0.999521	41.06	47.21
30	16445-	2.350	2.352	0.998312	42.44	48.81
31	16572-	2.475	2.484	0.997505	44.17	50.79
32	16643-	2.560	2.565	0.999576	45.26	52.06
33	16731-	2.690	2.693	0.999687	47.01	54.06
34	16774-	2.770	2.759	0.996047	47.24	52.13
35	16841-	2.885	2.896	0.997241	49.92	57.41
36	16887-	2.990	3.000	0.996841	51.50	59.23
37	16940-	3.176	3.160	0.983005	54.93	62.14
38	16987-	3.325	3.375	0.986554	57.71	66.37
39	17006-	3.450	3.488	0.989071	59.78	68.74
40	17035-	3.740	3.740	0.999904	64.86	74.59

M-64 TYPICAL FIGHTER, COMPOSITE MISSION, MAX STRESS = 20 KSI

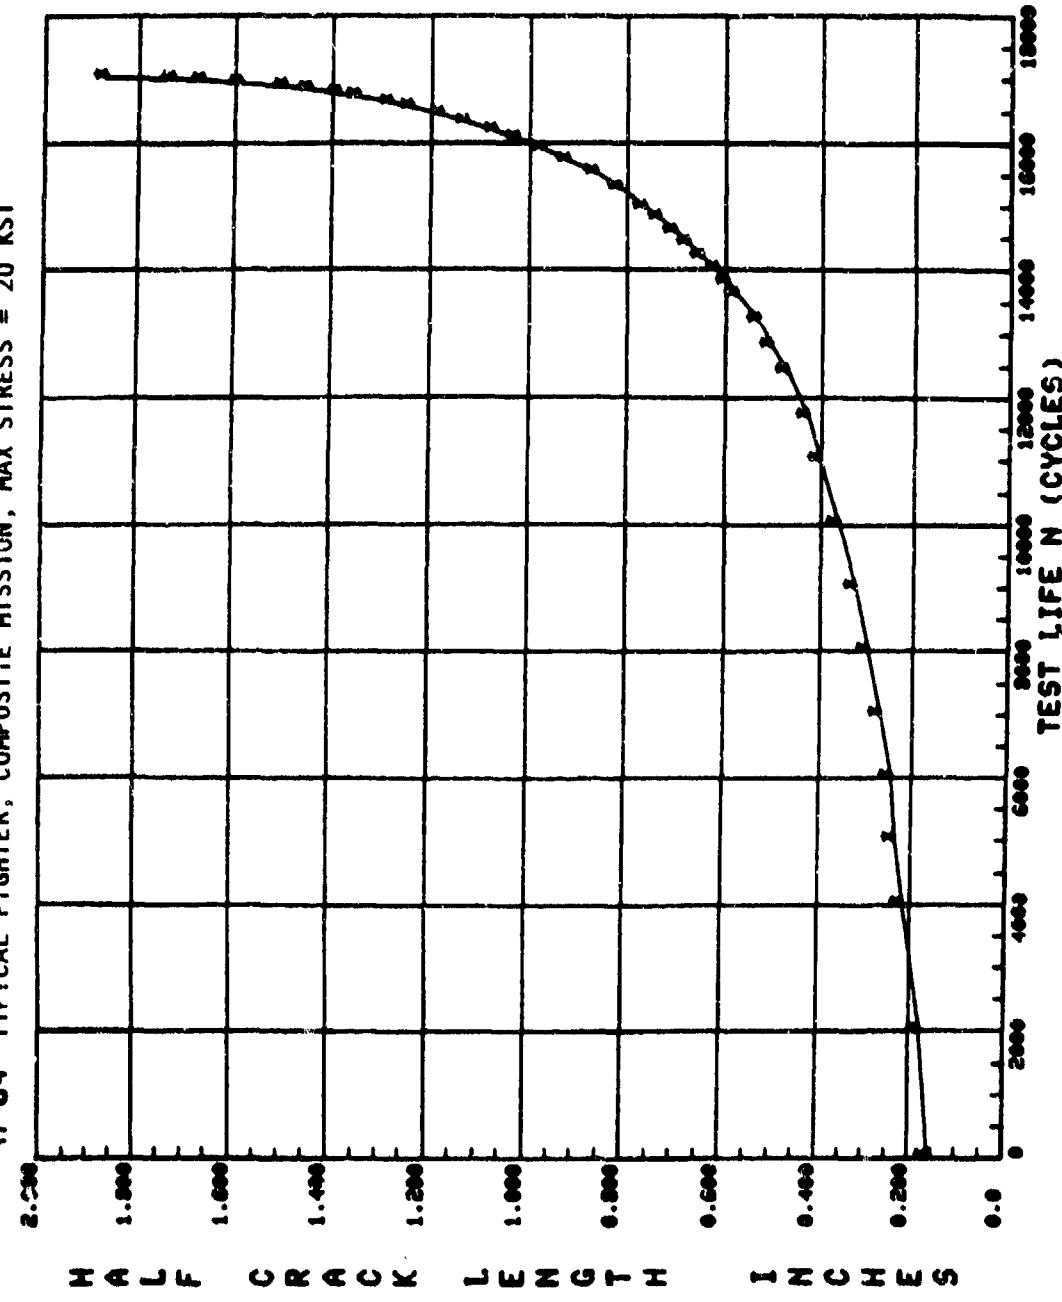


Figure 81. Crack growth curve for test M-64.

TABLE 81. DATA TABULATION FOR TEST M-54A

SPECIMEN NO.: M-54A TYP FIGHTER COMPOSITE MISS. STRESS = 15 KSI MAX

NO.	CCT	SPECIMEN	$\delta = 0.250$ IN.	$W = 6,000$ IN.	AMP= 0.0	IN.	TEST FREQ= 6.00 Hz.			
							PHIN=	PHAX=	A(MEASURD)	A(REGRESSION)
ENVIRONMENT CONDITIONS: AMBIENT AIR										
1	0-	0-	0.300	0.300	0.998883	10.41	12.47	8.899E-07		
2	5450-	0.325	0.321	0.999565	10.77	12.91	3.024E-06			
3	12000-	0.375	0.360	0.999007	11.72	14.92	5.428E-06			
4	17628-	0.455	0.454	0.999307	12.82	15.36	7.394E-06			
5	22700-	0.538	0.538	0.998240	13.90	16.75	9.382E-06			
6	26000-	0.600	0.602	0.998236	14.84	17.79	1.069E-05			
7	2E200-	0.644	0.652	0.998396	15.42	18.48	1.193E-05			
8	30400-	0.710	0.704	0.999280	16.04	19.22	1.356E-05			
9	32400-	0.760	0.763	0.998315	16.73	20.92	1.724E-05			
10	34000-	0.810	0.822	0.978650	17.39	20.84	1.743E-05			
11	35500-	0.865	0.877	0.977584	17.99	21.55	1.880E-05			
12	35600-	0.915	0.891	0.977624	18.04	21.61	2.002E-05			
13	38000-	0.965	0.960	0.977601	19.08	22.86	2.248E-05			
14	39000-	1.020	1.021	0.982207	19.51	23.37	2.343E-05			
15	40000-	1.060	1.069	0.993082	19.98	23.94	2.492E-05			
16	41000-	1.120	1.129	0.997156	20.58	24.66	2.813E-05			
17	42050-	1.180	1.187	0.997127	21.16	25.35	3.038E-05			
18	42750-	1.225	1.226	0.998770	21.26	25.83	3.6248E-05			
19	43300-	1.270	1.265	0.998641	21.91	26.26	3.421E-05			
20	43900-	1.310	1.310	0.999641	22.35	26.78	3.638E-05			
21	44600-	1.360	1.361	0.999261	22.63	27.35	3.893E-05			
22	45300-	1.415	1.413	0.999752	23.32	27.94	4.044E-05			
23	45900-	1.460	1.462	0.999718	23.78	28.49	4.389E-05			
24	46600-	1.525	1.525	0.999887	24.37	29.20	4.844E-05			
25	47533-	1.620	1.621	0.999976	25.26	30.26	5.565E-05			
26	48243-	1.705	1.703	0.999675	26.02	31.17	6.285E-05			
27	49021-	1.805	1.804	0.998569	26.95	32.29	7.378E-05			
28	49759-	1.916	1.917	0.999113	27.99	33.54	8.459E-05			

TABLE 81. DATA TABULATION FOR TEST M-64A (CONCL)

SPECIMEN NO. i. M-64A TYP. FIGHTER COMPOSITE MISS. STRESS = 15 KSI MAX

CCT. SPECIMEN	D= 0.250 IN.		ME 6,000 IN.		AHE 0.0 IN.	
	P MIN=	P MAX=				TEST FREQ= 6.00 Hz.
ENVIRONMENT CONDITION: AMBIENT AIR						
NO.	CYCLES	A(MEASURED)	A(BEFORESSION)	MULT. CORR. COEFF	K-MAX	DELTA A.
29	50283.	2.005	2.010	0.999618	26.85	34.57
30	56739.	2.110	2.102	0.999710	29.72	35.62
31	51221.	2.215	2.218	0.999759	30.83	36.94
32	51620.	2.315	2.315	0.999042	31.76	38.05
33	51962.	2.410	2.408	0.999464	32.67	39.15
34	52338.	2.520	2.527	0.998672	33.66	40.57
35	52601.	2.625	2.623	0.999329	34.84	41.74
36	52865.	2.730	2.738	0.998717	36.06	43.20
37	53064.	2.840	2.835	0.99366	37.10	44.46
38	53282.	2.960	2.950	0.998237	36.39	46.00
39	53483.	3.050	3.067	0.997231	39.76	47.64
40	53637.	3.170	3.165	0.997500	40.94	49.02
41	53765.	3.255	3.259	0.998055	42.14	50.45
42	53897.	3.375	3.363	0.998450	43.77	52.45
43	53987.	3.480	3.476	0.999644	45.07	54.00
44	54069.	3.560	3.581	0.996524	46.60	55.84
45	54151.	3.700	3.707	0.996819	48.56	58.16
46	54225.	3.825	3.825	0.990403	50.98	61.06
47	54271.	3.970	3.978	0.993632	53.27	63.83
48	54300.	4.050	4.037	0.996707	55.21	65.12
49	54336.	4.250	4.249	0.998907	58.92	70.60

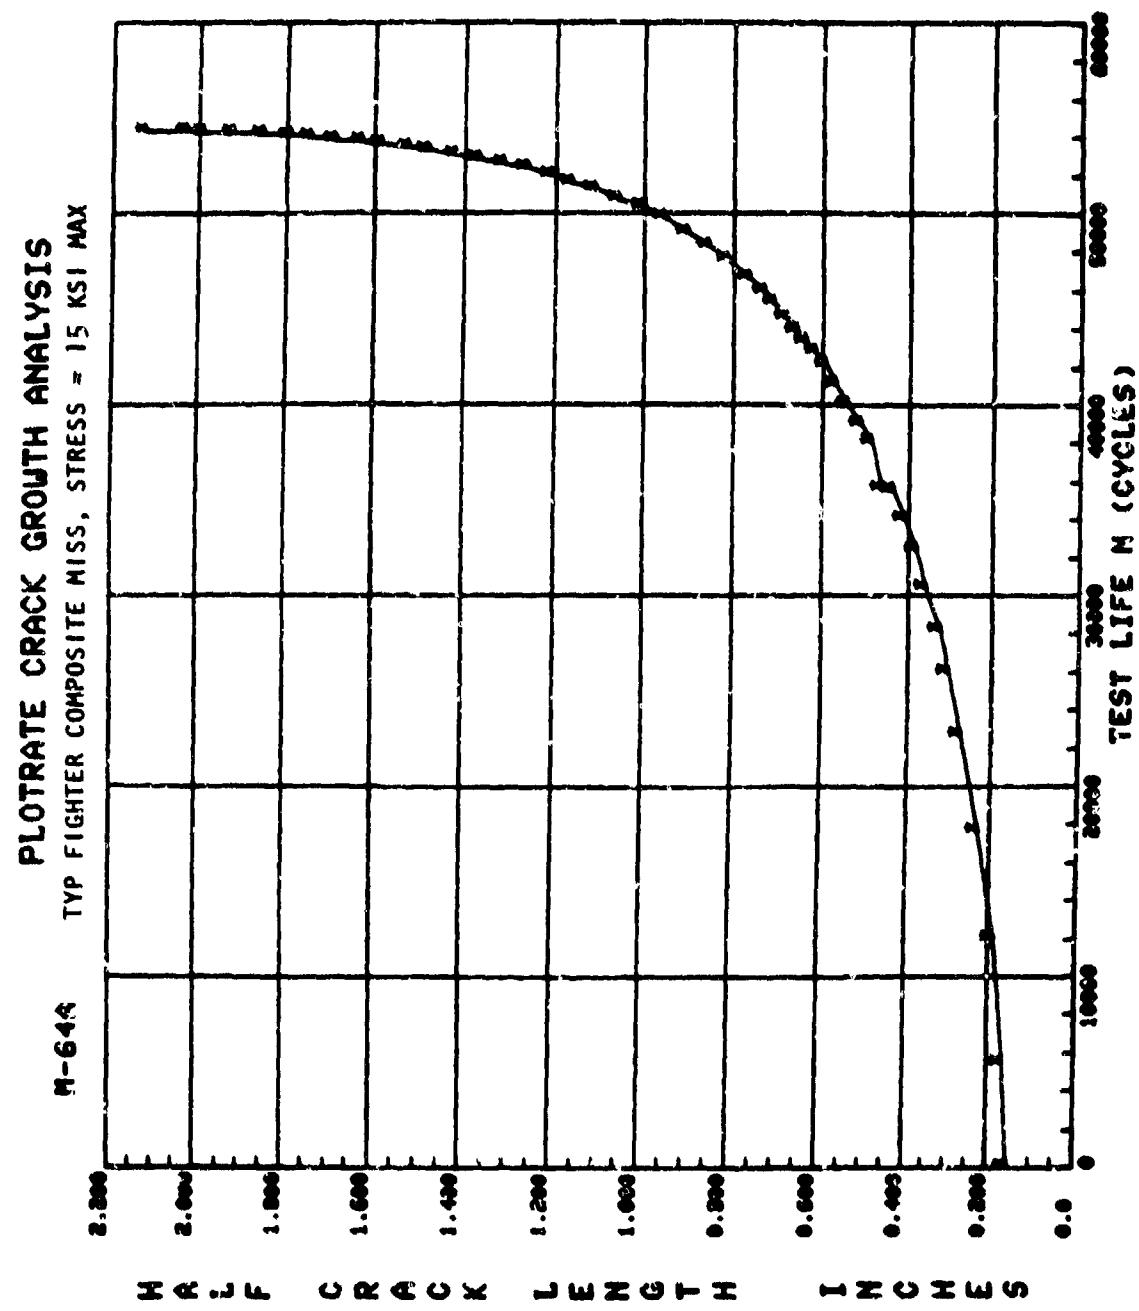


Figure 82. Crack growth curve for test N-64A.

TABLE 82. DATA TABULATION FOR TEST M-64B

SPECIMEN NO.: M-64B TYP FIGHTER COMPOSITE MISS. STRESS = 10 KSI MAX

E.C.T. SPECIMEN: S= 0.2250 IN. W= 6.000 IN.

A= 0.0 AN= 0.0 IN.

Pmax= TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

IN.	CYCLES	AS MEASURED)	REGRESSION)	MULT. COEF.	COEFF	K-MAX	DELTA K	DATA
1	0.	0.300	0.300	0.9963n2	6.67	6.93	1.579E-06	
2	8500.	0.320	0.319	0.982537	7.09	7.42	9.384E-07	
3	18000.	0.350	0.333	0.965673	7.25	7.42	7.61E-07	
4	59100.	0.390	0.390	0.946987	7.83	10.20	1.929E-07	
5	92450.	0.440	0.443	0.992995	9.37	10.82	1.044E-06	
6	112429.	0.482	0.486	0.929102	5.77	11.49	1.279E-06	
7	129500.	0.530	0.530	0.997787	9.17	11.92	1.538E-06	
8	149350.	0.597	0.594	0.997536	9.75	12.63	1.889E-06	
9	165200.	0.655	0.642	0.997271	10.21	13.35	2.134E-06	
10	175300.	0.720	0.707	0.996862	10.63	13.82	2.363E-06	
11	187000.	0.760	0.755	0.996294	11.07	14.39	2.734E-06	
12	192200.	0.800	0.808	0.991440	11.39	14.81	3.976E-06	
13	202400.	0.855	0.852	0.980646	11.71	15.22	3.356E-06	
14	209800.	0.910	0.908	0.999252	12.11	15.74	3.794E-06	
15	215537.	0.955	0.954	0.999310	12.43	16.15	4.102E-06	
16	222200.	1.005	1.009	0.999604	12.80	16.54	4.377E-06	
17	228500.	1.065	1.065	0.999704	13.18	17.14	4.675E-06	
18	233800.	1.120	1.116	0.999996	13.52	17.59	5.279E-06	
19	239000.	1.170	1.173	0.998910	13.89	18.86	5.576E-06	
20	243700.	1.225	1.230	0.998965	14.26	18.53	6.319E-06	
21	247600.	1.265	1.281	0.998908	14.56	18.92	6.752E-06	
22	251200.	1.325	1.334	0.999134	14.91	19.39	6.939E-06	
23	255000.	1.369	1.367	0.997742	15.25	19.83	7.331E-06	
24	257100.	1.430	1.425	0.999114	15.49	20.13	7.729E-06	
25	262100.	1.482	1.493	0.998955	15.90	20.63	8.705E-06	
26	264300.	1.535	1.533	0.998973	16.15	21.80	9.172E-06	
27	269200.	1.630	1.630	0.999193	16.74	21.77	9.941E-06	
28	273600.	1.730	1.726	0.999461	17.33	22.53	1.166E-05	

TABLE 82. DATA TABULATION FOR TEST M-64B (CONT.)

SPECIMEN NO.: M-64B TYP FIGHTER COMPOSITE MISS. STRESS = 16 KSI MAX

CCT SPECIMEN S= 0.250 IN. N= 6,000 IN. AM= 0.0 IN.

PHASE PHASE TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	AM MEASURED (DEGREES)	MULT. CORR. COEFF	N-MAX	DATA
29	278000.	1.830	0.999732	17.99	23.39
30	281400.	1.920	0.999743	18.53	24.69
31	284350.	2.010	0.999759	19.03	25.74
32	288200.	2.120	0.9999310	19.76	25.69
33	291300.	2.220	0.999367	20.39	26.51
34	293600.	2.302	0.999409	20.93	27.23
35	295100.	2.400	0.999495	21.54	28.03
36	298100.	2.525	0.999370	22.29	28.78
37	29950.	2.605	0.999396	22.92	29.57
38	301700.	2.710	0.998117	23.69	30.78
39	303100.	2.805	0.999771	24.33	31.62
40	304300.	2.910	0.999294	25.04	32.25
41	305398.	3.000	0.999433	25.77	33.31
42	306214.	3.055	0.998658	26.34	34.23
43	307270.	3.175	0.997764	27.15	35.23
44	308220.	3.270	0.998475	27.99	36.39
45	309294.	3.410	0.999742	29.21	37.97
46	297911.	3.290	0.999972	29.92	38.79
47	310450.	3.635	3.641	0.998348	31.40
48	311100.	3.723	3.730	0.997093	32.32
49	311659.	3.865	3.863	0.998615	32.91
50	312000.	3.960	3.950	0.997068	34.92
51	312400.	4.065	4.100	0.997612	36.79
52	312800.	4.265	4.275	0.999298	39.33
53	313100.	4.450	4.450	0.999929	42.26

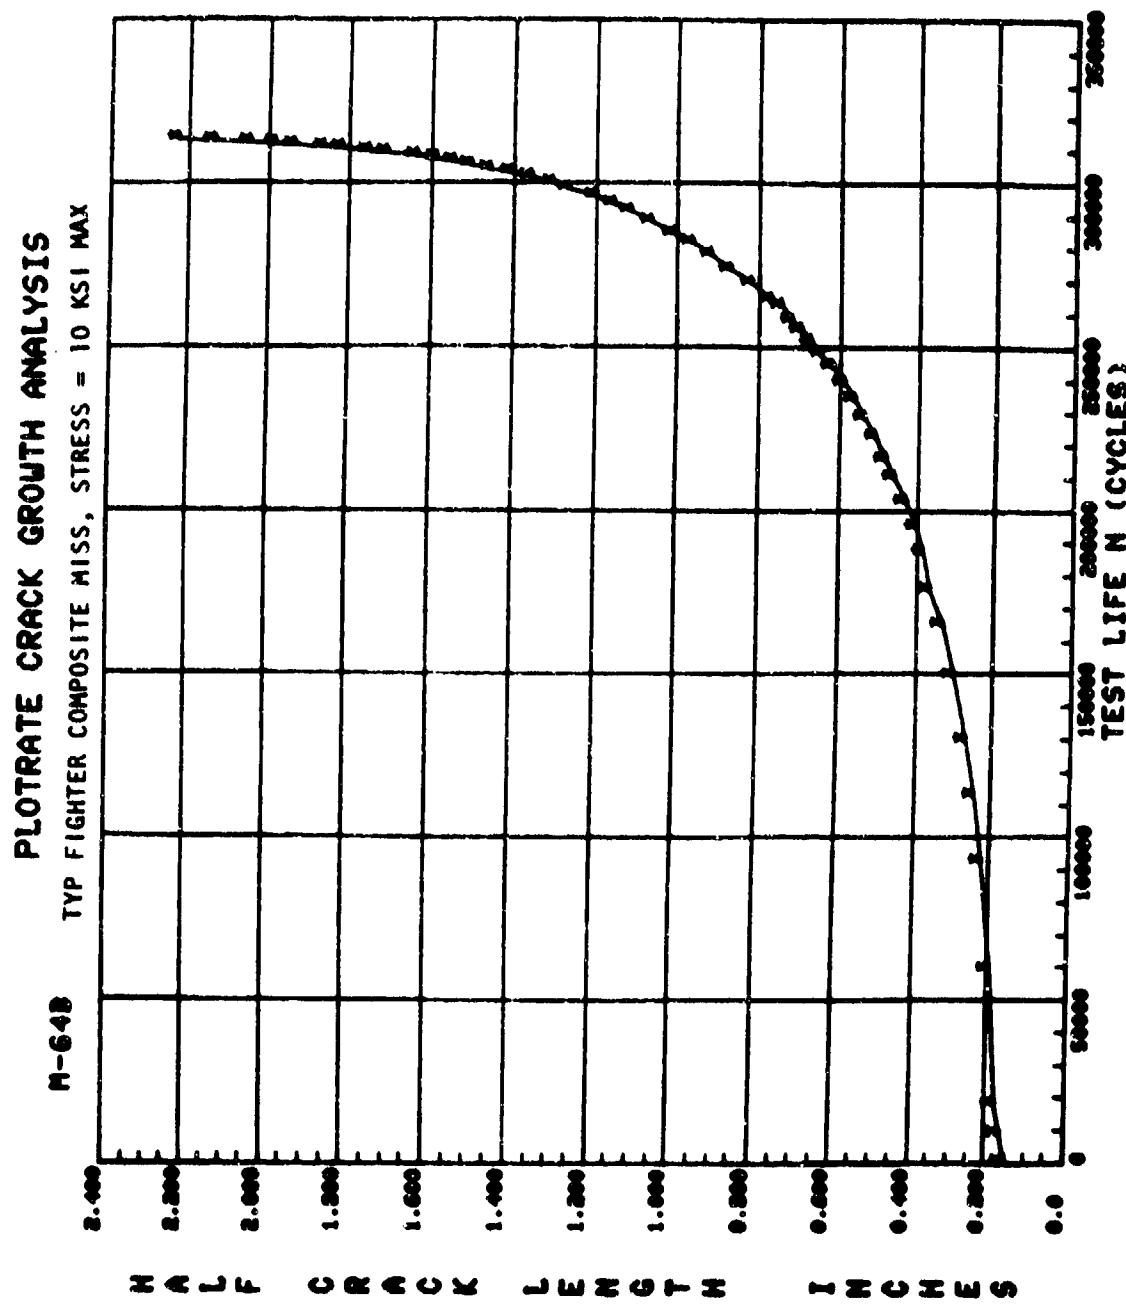


Figure 83. Crack growth curve for test M-64B.

TABLE 83. DATA TABULATION FOR TEST M-65

SPECIMEN NO.: M-65		TYPICAL TRANSPORT, MAX STRESS = 12 KSI			
LCT	SPECIMEN	A = 0.250 IN.	M = 6,000 IN.	A _N = 0.0	I _N
P _{MIN}	P _{MAX}				TEST FREC = 5.000 Hz
ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLFS	A(MEASURD)	A(PREDICTED)	MULT. COVR. COEFF	K-MAX
1	0.	0.750	0.750	6.991805	12.14
2	0.765	0.767	0.762	0.974202	12.20
3	0.765	0.770	0.770	0.974195	13.40
4	0.790	0.791	0.791	0.952491	12.71
5	0.800	0.812	0.812	0.975649	13.90
6	0.820	0.823	0.823	0.996799	13.66
7	0.820	0.830	0.830	0.996799	13.66
8	0.850	0.852	0.852	0.996927	14.03
9	0.860	0.863	0.863	0.997692	14.37
10	0.920	0.926	0.926	0.998852	14.66
11	0.940	0.943	0.943	0.997938	14.92
12	0.965	0.964	0.964	0.997796	15.16
		1.010	1.010	0.996773	15.28
		1.170000.	1.170000.	0.996773	24.99
		1.170000.	1.170000.	0.996773	24.99
					1.420E-07

PLOTRATE CRACK GROWTH DATA
 TYPICAL TRANSPORT, MAX STRESS = 12 KSI

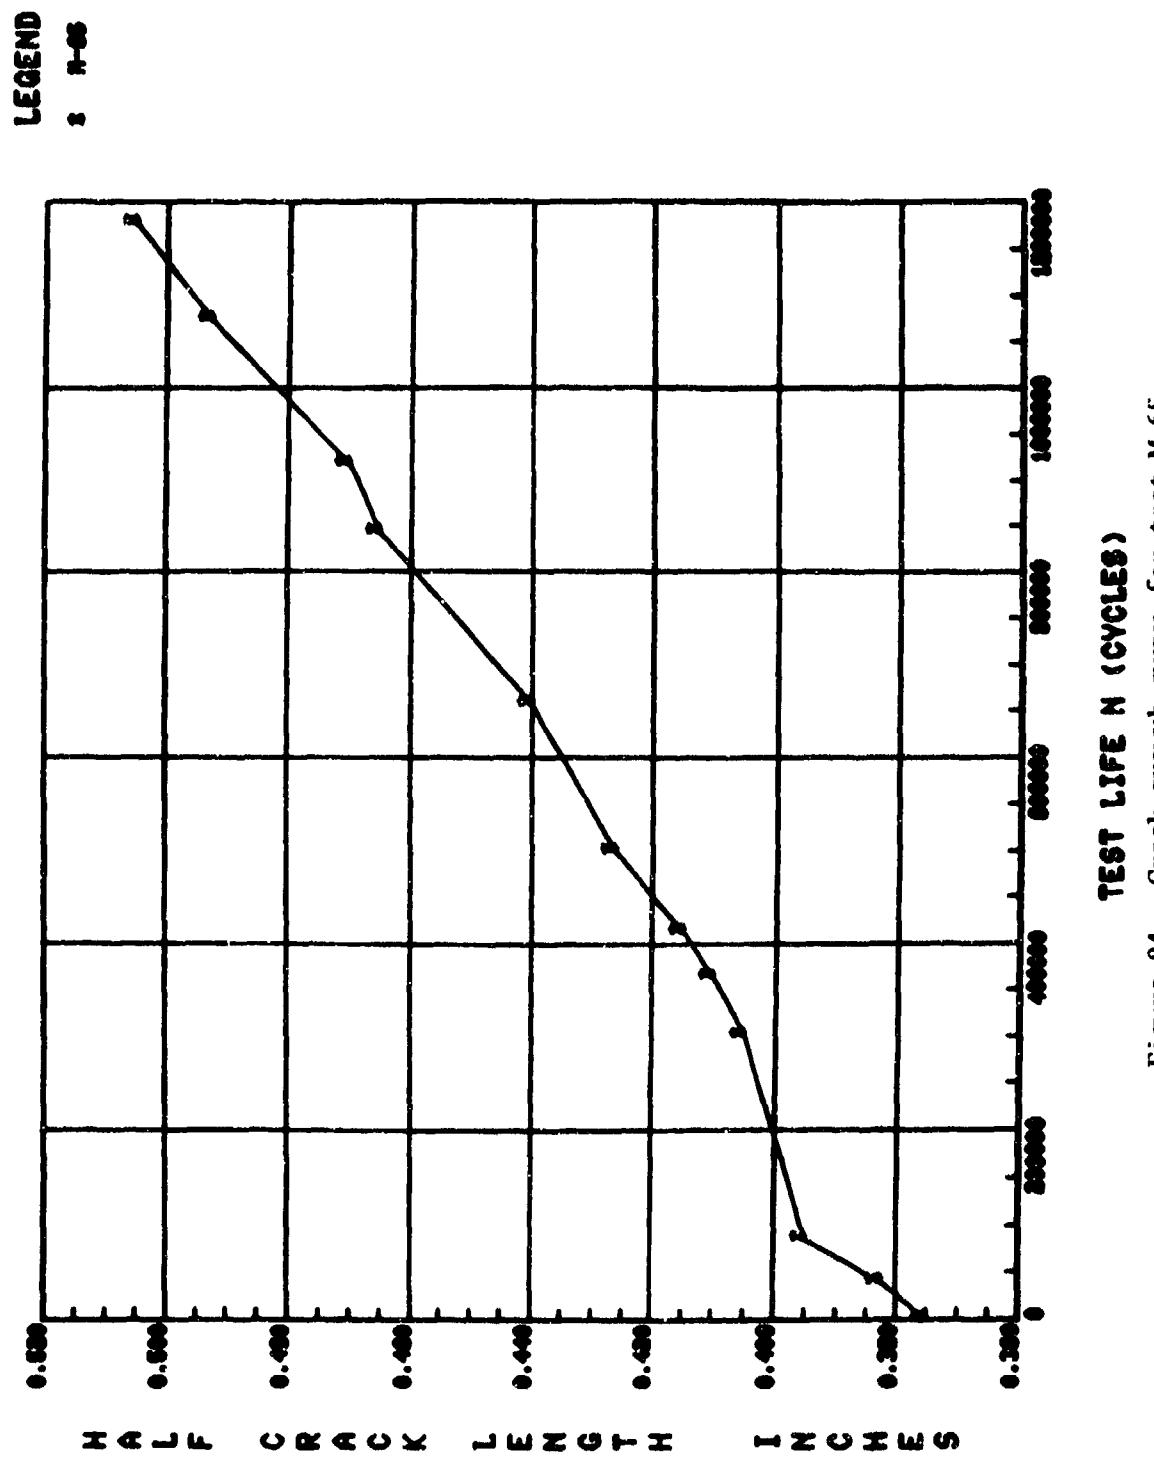


Figure 84. Crack growth curve for test M-65.

TABLE 84. DATA TABULATION FOR TEST M-66

SPECIMEN NO.:	M-66	TYPICAL TRANSPORT, MAX STRESS = 16.8 KSI			TEST FREQ = 6.00 Hz.	
		CYCLES	b = 0.250 IN.	b = 6.000 IN.		
CCT	SPECIMEN	PMIN =	PMAX =	ENVIRONMENT CONDITION: AMBIENT AIR		
1	0.	0.500	0.500	0.945275	K-MAX	24.29
2	71100-	0.510	0.516	0.967160	15.19	24.69
3	86200-	0.525	0.519	0.975568	15.24	24.76
4	161700-	0.535	0.535	0.951709	15.47	25.14
5	211300-	0.545	0.549	0.955739	15.67	25.47
6	250000-	0.555	0.559	0.965050	15.83	25.72
7	268100-	0.575	0.567	0.970582	15.93	25.89
8	335000-	0.587	0.588	0.971575	16.24	26.40
9	362000-	0.595	0.596	0.967614	16.35	26.57
10	396000-	0.605	0.607	0.989658	16.51	26.82
11	428500-	0.620	0.620	0.992555	16.68	27.11
12	447500-	0.630	0.627	0.993462	16.79	27.28
13	500000-	0.645	0.645	0.998611	17.03	27.67

PLOT RATE CRACK GROWTH DATA
M-66 TYPICAL TRANSPORT, MAX STRESS = 16.8 KSI

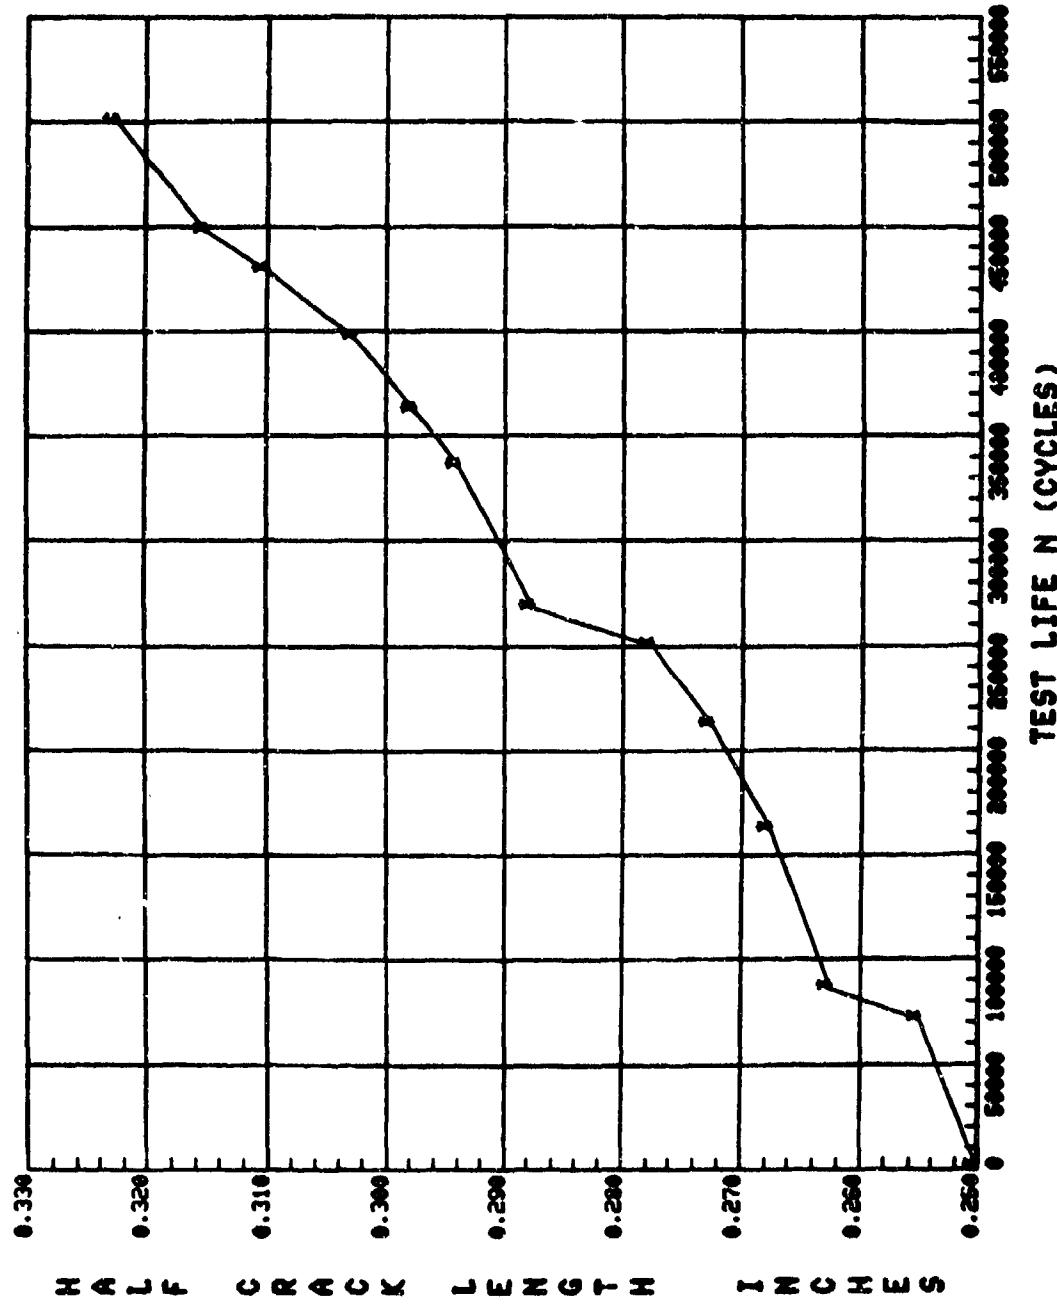


Figure 85. Crack growth curve for test M-66.

TABLE 85. DATA TABULATION FOR TEST M-69

SPECIMEN NO.: M-69		TYPICAL FIGHTER, AIR-TO-AIR, MAX STRESS = 20 KSI		TEST FREQ= 6.00 Hz.	
CCT	SPECIMEN	B= 0.250 IN.	M= 6.000 IN.	AM= 0.0	IN.
PHASE=		ENVIRONMENT CONDITION: AMBIENT AIR			
NU.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. COEF.	K-MAX
1	0.	0.310	0.310	0.999997	13.98
2	3500.	0.350	0.350	0.999998	16.59
3	6600.	0.400	0.400	0.999951	17.75
4	9050.	0.450	0.450	0.999163	16.87
5	11350.	0.505	0.507	0.999498	17.92
6	13100.	0.525	0.526	0.999701	16.82
7	14700.	0.615	0.612	0.999399	19.72
8	16250.	0.670	0.672	0.999278	20.71
9	17500.	0.725	0.729	0.999129	21.59
10	18300.	0.770	0.767	0.999716	22.16
11	19400.	0.830	0.827	0.998470	23.05
12	20500.	0.885	0.893	0.998313	24.90
13	21100.	0.935	0.933	0.998850	24.56
14	21800.	0.985	0.984	0.998836	25.26
15	22400.	1.035	1.032	0.996407	25.92
16	23050.	1.085	1.089	0.997991	26.69
17	23550.	1.135	1.140	0.998625	27.35
18	24900.	1.200	1.194	0.997092	28.06
19	24350.	1.240	1.242	0.998046	28.67
20	24700.	1.295	1.290	0.997857	29.28
21	25000.	1.325	1.330	0.998458	29.78
22	25300.	1.375	1.375	0.998447	30.35
23	25600.	1.425	1.424	0.999638	30.95
24	25900.	1.480	1.481	0.999797	31.57
25	26200.	1.545	1.546	0.999813	32.46
26	26500.	1.615	1.616	0.999854	33.32
27	26800.	1.690	1.690	0.999441	34.23
28	27200.	1.800	1.800	0.999049	35.56

TABLE 85. DATA TABULATION FOR TEST M-69 (CONCL)

SPECIMEN NO.: H-69	TYPICAL FIGHTER, AIR-TO-AIR, MAX STRESS = 20 KSI		TEST FREQ= 6.00 Hz.	MULT. CORR. COEFF	K-MAX	DELTA K
	P-MIN=	P-MAX=				
ENVIRONMENT CONDITION: AMBIENT AIR						
NO.	CYCLES	AM MEASURED1 - AIRREGRESSION1				
29	27516.	1.890	1.895	0.998819	36.73	41.01
30	27790.	1.995	1.997	0.999685	37.98	42.41
31	28915.	2.090	2.091	0.999597	39.14	43.71
32	28220.	2.195	2.193	0.998837	40.41	45.13
33	28420.	2.300	2.308	0.999236	41.88	46.77
34	28560.	2.400	2.402	0.999374	43.10	46.13
35	28680.	2.500	2.496	0.999607	44.32	49.50
36	28810.	2.610	2.614	0.999131	45.92	51.28
37	28930.	2.740	2.740	0.997362	47.67	53.24
38	29020.	2.845	2.855	0.997140	49.33	55.08
39	29095.	2.960	2.975	0.997612	51.11	57.08
40	29145.	3.070	3.070	0.999163	52.60	58.73
41	29180.	3.155	3.155	0.999629	53.95	60.24
42	29221.	3.265	3.272	0.995996	55.90	62.43
43	29251.	3.375	3.371	0.994792	57.63	64.36
44	29276.	3.455	3.460	0.996072	59.64	66.60
45	29291.	3.560	3.557	0.996730	61.10	68.23
46	29311.	3.690	3.691	0.997608	63.02	71.27

PLOT RATE CRACK GROWTH ANALYSIS
M-69 TYPICAL FIGHTER, AIR-TO-AIR, MAX STRESS = 20 KSI

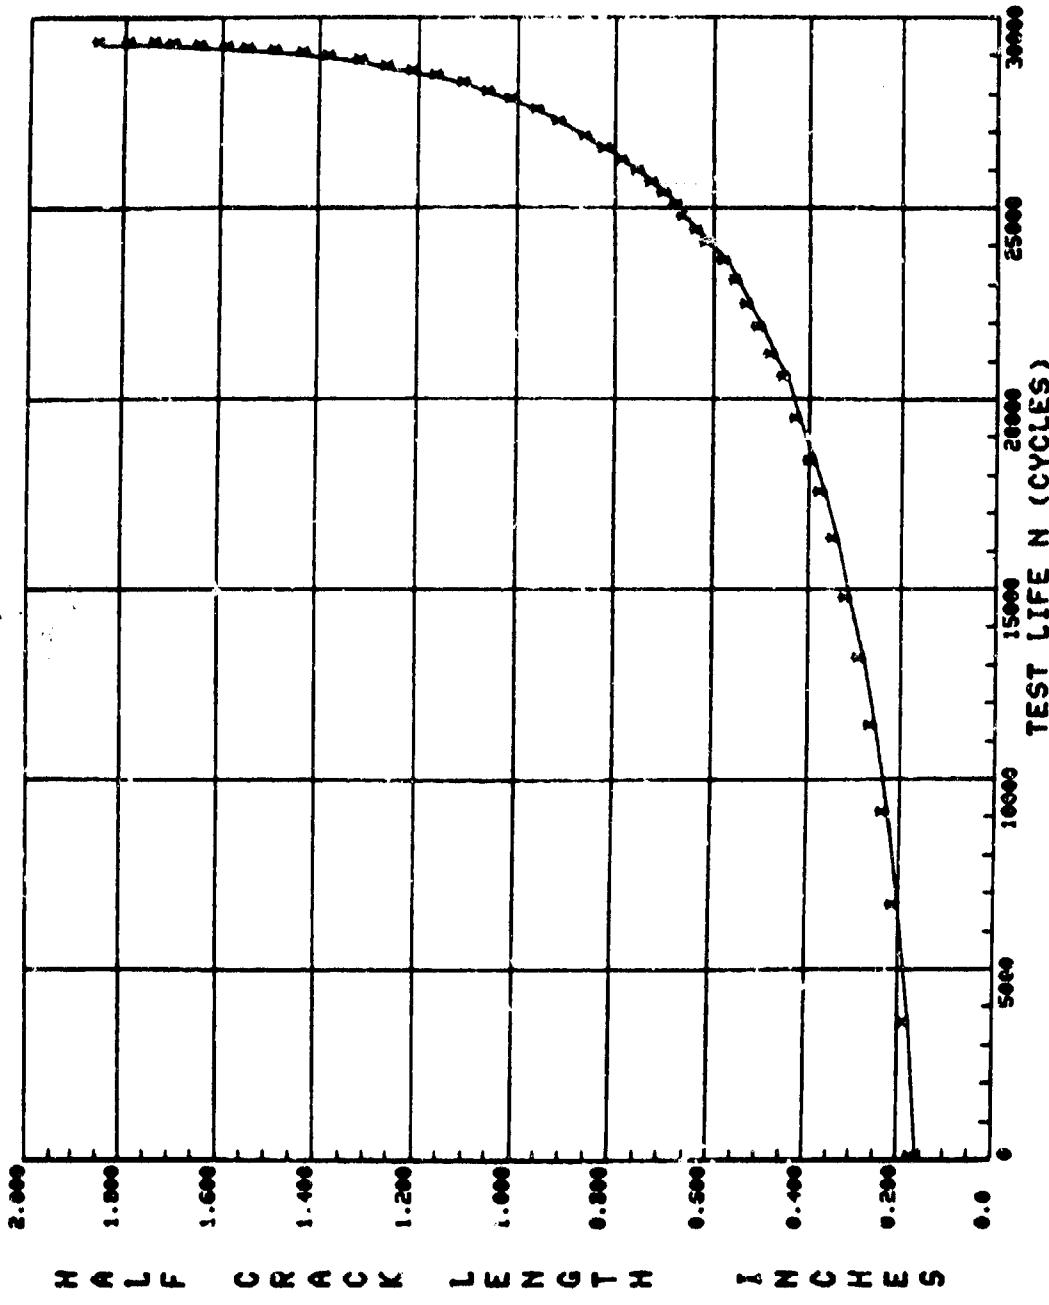


Figure 86. Crack growth curve for test M-69.

TABLE 86. DATA TABULATION FOR TEST M-69A

SPECIMEN NO.: M-69A SIMPLIFIED SPECTRUM, TYP FIGHTER-AIR TO AIR, MAX STRESS = 12 KSI

NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K	DA/DN
ENVIRONMENT CONDITIONS: AMBIENT AIR							
P <small>MAX</small>	TEST FREQU.						
1	0.	0.310	0.310	0.998348	5.59	6.52	1.670E-06
2	11600.	0.345	0.346	0.997398	5.91	6.89	1.629E-06
3	24350.	0.395	0.383	0.991477	6.22	7.25	2.014E-06
4	37460.	0.435	0.442	0.992365	6.69	7.20	2.774E-06
5	47700.	0.490	0.500	0.996100	7.12	8.31	3.543E-06
6	52000.	0.590	0.587	0.999601	7.73	9.01	4.819E-06
7	64050.	0.640	0.636	0.999573	8.06	9.41	5.416E-06
8	68900.	0.690	0.695	0.996584	8.42	9.83	5.829E-06
9	72500.	0.740	0.737	0.997784	8.69	10.13	6.443E-06
10	75600.	0.780	0.777	0.993468	8.93	10.42	7.064E-06
11	80300.	0.840	0.867	0.995652	9.34	10.89	8.671E-06
12	82800.	0.890	0.890	0.995561	9.59	11.16	9.225E-06
13	85500.	0.940	0.943	0.995804	9.88	11.53	1.019E-05
14	87100.	0.990	0.979	0.996456	10.08	11.76	1.096E-05
15	92750.	1.030	1.038	0.996417	10.40	12.14	1.142E-05
16	91600.	1.080	1.080	0.996138	10.63	12.40	1.205E-05
17	93800.	1.140	1.133	0.997830	10.90	12.72	1.277E-05
18	96100.	1.190	1.197	0.998925	11.24	13.41	1.304E-05
19	97600.	1.240	1.237	0.998470	11.44	13.35	1.466E-05
20	99500.	1.295	1.293	0.998693	11.73	13.68	1.596E-05
21	101500.	1.355	1.361	0.998917	12.07	14.06	1.773E-05
22	102500.	1.400	1.396	0.999546	12.24	14.26	1.862E-05
23	103900.	1.450	1.450	0.999615	12.51	14.66	2.031E-05
24	105100.	1.500	1.502	0.999631	12.77	14.99	2.176E-05
25	107200.	1.595	1.595	0.999723	13.22	15.43	2.391E-05
26	109200.	1.700	1.698	0.999531	13.73	16.02	2.600E-05
27	111900.	1.790	1.793	0.998066	14.19	16.56	2.684E-05
28	112700.	1.900	1.891	0.996923	14.67	17.11	3.263E-05

TABLE 86. DATA TABULATION FOR TEST M-69A (CONCL)

SPECIMEN NO. 2 M-69A SIMPLIFIED SPECTRUM, TYP FIGHTER-AIR TO AIR STRESS = 12 KSI MAX

CCT SPECIMEN $\theta = 0.250$ IN. $M = 6.000$ IN. $A_N = 0.0$ IN.
Pmax= TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	ALMEASIS(LD1)	ALREGRESSION(L)	MULT. CORR. COEFF	K-MAX	DELTA K	DATA
29	114888.	2.070	2.040	0.997690	15.40	17.97	3.867E-05
30	116000.	2.130	2.127	0.998190	15.84	18.48	4.234E-05
31	117120.	2.240	2.228	0.998353	16.34	19.07	4.829E-05
32	118200.	2.330	2.338	0.997831	16.90	19.72	5.468E-05
33	119250.	2.445	2.453	0.999074	17.50	20.42	6.224E-05
34	119940.	2.540	2.538	0.999825	17.96	20.95	6.997E-05
35	120540.	2.630	2.626	0.999506	18.43	21.51	7.873E-05
36	121210.	2.750	2.735	0.99445	19.04	22.22	8.944E-05
37	121792.	2.840	2.842	0.999546	19.65	22.93	1.024E-04
38	122298.	2.950	2.968	0.999885	20.28	23.67	1.162E-04
39	122754.	3.055	3.060	0.999872	20.87	24.47	1.292E-04
40	123126.	3.165	3.161	0.999627	21.62	25.23	1.435E-04
41	123498.	3.270	3.268	0.999020	22.34	26.06	1.629E-04
42	123797.	3.360	3.367	0.998550	23.03	26.87	1.463E-04
43	124080.	3.470	3.474	0.999519	23.80	27.77	2.176E-04
44	124284.	3.565	3.564	0.999693	24.50	26.53	2.482E-04
45	124490.	3.670	3.672	0.999775	25.37	29.60	2.857E-04
46	124685.	3.775	3.788	0.999831	26.37	30.76	3.286E-04
47	124800.	3.885	3.864	0.999373	27.06	31.57	3.684E-04
48	124921.	3.955	3.956	0.999310	27.94	32.59	4.172E-04
49	125050.	4.060	4.067	0.998442	29.06	33.92	5.058E-04
50	125120.	4.140	4.137	0.998513	29.84	34.51	5.465E-04
51	125200.	4.225	4.233	0.994369	30.95	36.11	5.476E-04
52	125268.	4.320	4.336	0.995346	32.24	37.61	9.375E-04
53	125325.	4.430	4.449	0.997297	33.79	39.43	1.201E-03
54	125363.	4.556	4.548	0.997243	35.30	41.19	1.505E-03

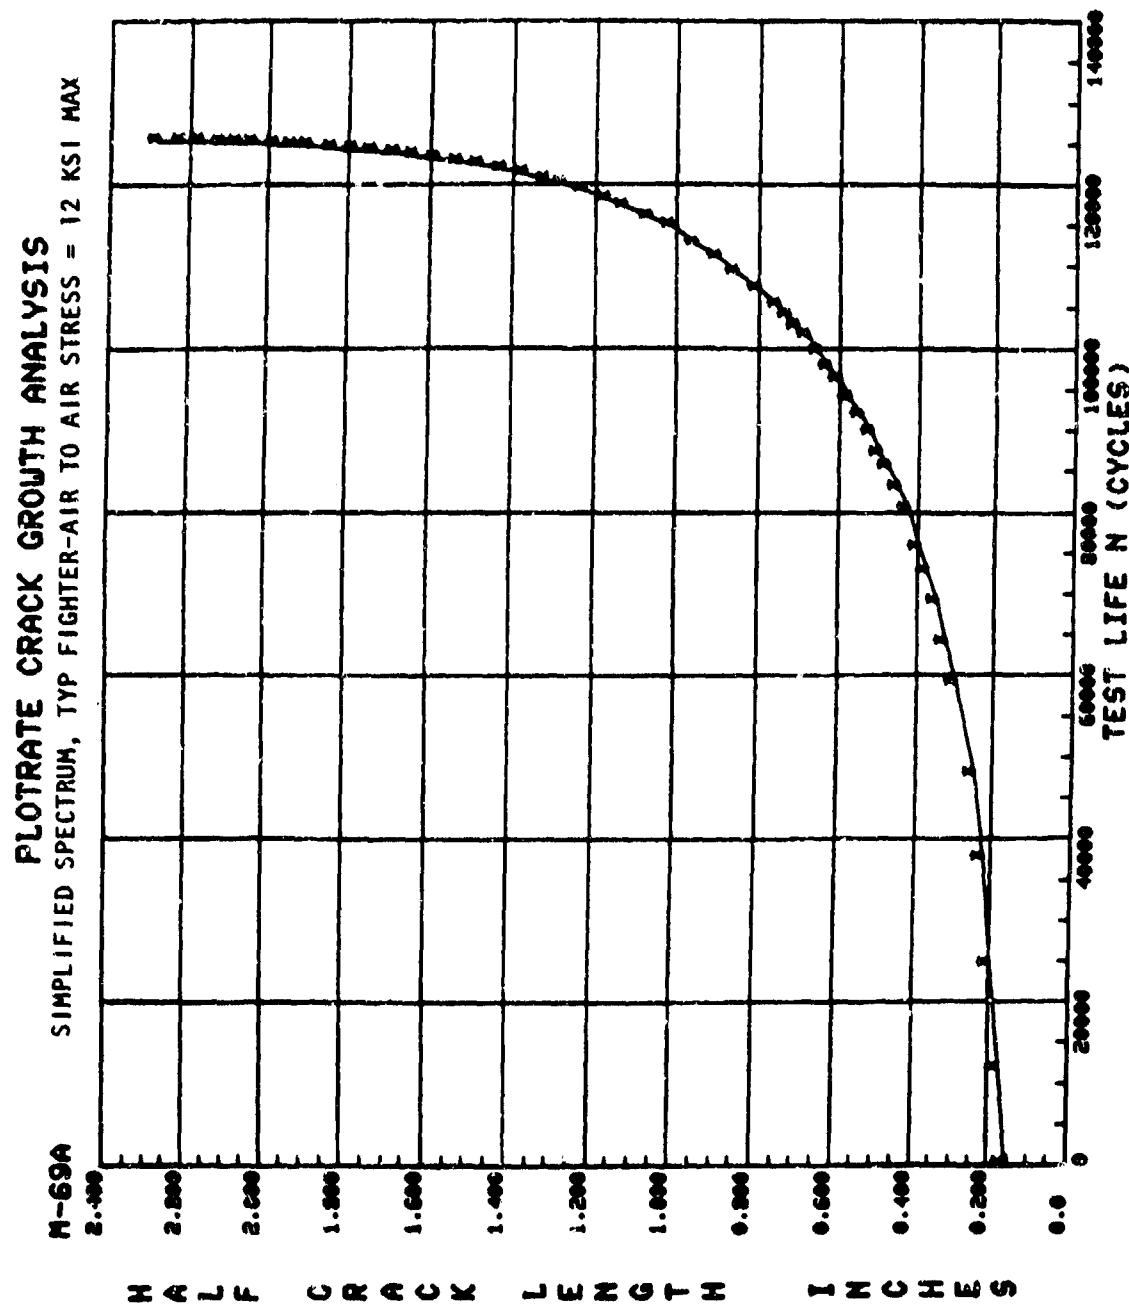


Figure 27. Crack growth curve for test M-69A.

TABLE 87. DATA TABULATION FOR TEST H-70

SPECIMEN NO.: H-70 TYPICAL FIGHTER, AIR-TO-GROUND, MAX STRESS = 18KSI

CCL SPECIMEN **B= 0.250 IN.** **H= 6.000 IN.** **AH= 0.0 IN.**

P_{MIN}= **P_{MAX}=** **TEST FREQ= 6.00 Hz.**

ENVIRONMENT CONDITION:		AMBIENT AIR		MULT. CORR. CEFF		K-MAX		DELTA K		DAW	
NO.	CYCLES	AIMED(S)	REGRESSION)								
1	0.	0.248	0.297	0.999844	12.32	15.06	7.604E-06				
2	2500.	0.330	0.325	0.989729	12.89	15.75	5.176E-06				
3	5000.	0.355	0.351	0.993178	13.39	16.36	4.825E-06				
4	8000.	0.370	0.373	0.994506	13.80	16.67	4.669E-06				
5	12000.	0.415	0.406	0.993243	14.41	17.62	5.202E-06				
6	16000.	0.440	0.450	0.996341	15.19	18.57	6.406E-06				
7	20000.	0.510	0.507	0.996896	16.14	19.72	7.953E-06				
8	24000.	0.580	0.576	0.997695	17.21	21.03	9.773E-06				
9	26000.	0.615	0.619	0.998327	17.86	21.83	1.090E-05				
10	28000.	0.640	0.661	0.994469	18.46	22.58	1.219E-05				
11	30000.	0.710	0.712	0.999074	19.19	23.46	1.329E-05				
12	32000.	0.770	0.770	0.999364	19.99	24.43	1.448E-05				
13	34000.	0.835	0.830	0.998187	20.79	25.41	1.608E-05				
14	35500.	0.875	0.879	0.997722	21.42	26.19	1.751E-05				
15	37000.	0.925	0.932	0.998087	22.09	27.00	1.965E-05				
16	38000.	0.975	0.970	0.999057	22.57	27.59	2.130E-05				
17	39000.	1.015	1.015	0.998020	23.12	28.25	2.443E-05				
18	40000.	1.065	1.066	0.997886	23.74	29.92	2.661E-05				
19	41000.	1.115	1.119	0.998447	24.37	29.78	2.973E-05				
20	42000.	1.190	1.183	0.998569	25.12	30.70	3.312E-05				
21	43000.	1.245	1.252	0.998636	25.92	31.48	3.677E-05				
22	44000.	1.335	1.329	0.997886	26.80	32.75	4.162E-05				
23	45000.	1.410	1.415	0.998853	27.76	33.92	4.744E-05				
24	45500.	1.460	1.463	0.998949	28.30	34.59	5.171E-05				
25	46000.	1.520	1.513	0.999655	28.85	35.26	5.483E-05				
26	47000.	1.630	1.628	0.998658	30.12	36.61	6.693E-05				
27	48000.	1.770	1.770	0.998512	31.64	38.71	8.982E-05				
28	48700.	1.895	1.894	0.999361	33.05	40.39	9.993E-05				

TABLE 87. DATA TABULATION FOR TEST M-70 (CONCL)

SPECIMEN NO.:	TEST	SPECIMEN	B= 0.250 IN.	W= 6.000 IN.	A= 0.0 IN.	P _{MAX} =	TEST FREQ= 6.00 Hz.					
							ENVIRONMENT CONDITION:	AIR MEASURED	AIR REGRESSION	MULT. CORR.	Coeff.	K-MAX
NO.												DELTA K
29		49400.	2-040	2-043		0.999577	34.69	42.40				1.211E-04
30		49900.	2-175	2-170		0.998579	36.11	44.13				1.484E-04
31		50100.	2-220	2-228		0.998771	36.77	44.92				1.589E-04
32		50500.	2-350	2-359		0.999001	38.28	46.79				1.796E-04
33		50900.	2-525	2-510		0.998547	40.07	48.97				2.158E-04
34		51100.	2-595	2-600		0.998104	41.16	50.21				2.428E-04
35		51300.	2-685	2-698		0.997006	42.38	51.00				2.787E-04
36		51500.	2-810	2-805		0.999763	43.74	53.46				3.241E-04
37		51700.	2-940	2-946		0.999756	45.61	55.75				3.482E-04
38		51825.	3-050	3-047		0.996787	47.00	57.45				4.579E-04
39		51965.	3-175	3-182		0.997346	48.96	59.84				5.402E-04
40		52066.	3-275	3-293		0.996790	50.64	61.90				6.812E-04
41		52125.	3-385	3-370		0.995676	51.86	63.34				8.040E-04
42		52225.	3-525	3-546		0.953099	54.80	66.98				1.123E-03
43		52276.	3-645	3-642		0.994066	56.20	69.55				1.598E-03
44		52308.	3-750	3-752		0.999774	58.61	71.63				1.724E-03
45		52341.	3-875			0.999969	61.11	74.70				2.080E-03

PLOTRATE CRACK GROWTH ANALYSIS
M-70 TYPICAL FIGHTER, AIR-TO-GROUND, MAX STRESS = 18 KSI

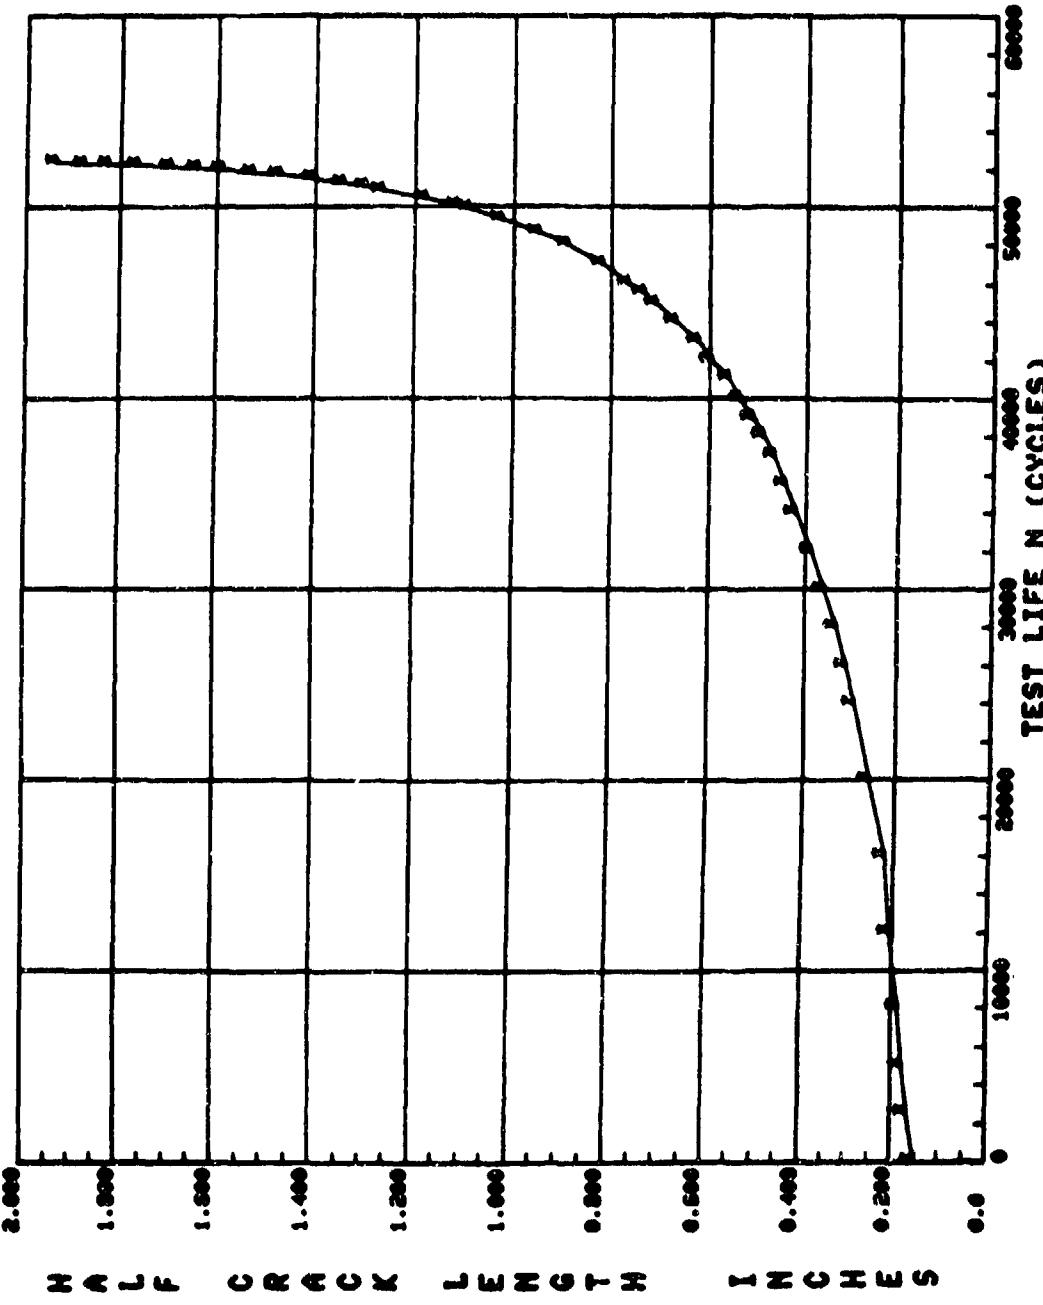


Figure 88. Crack growth curve for test M-70.

TABLE 88. DATA TABULATION FOR TEST M-70A

SPECIMEN NO.: M-70A SIMPLIFIED SPEC. TYP FIGHTER-AIR TO GROUND STRESS = 10 KSI MAX

CCY SPECIMEN B= 6.750 IN. H= 6.000 IN. AM= 0.0 PHM= FMAX= TEST FREQ= 6.00 Hz.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	AS MEASURED)	AS REGRESSION)	MULT. CORR. COEFF	R-MAX	DELTA K	DATA
1	0.	0.368	0.999912	4.64	6.50	2.478E-07	
2	33800.	0.335	0.998750	4.82	6.75	5.253E-07	
3	59000.	0.365	0.999283	5.84	7.81	7.123E-07	
4	66000.	0.410	0.999298	5.39	7.55	1.622E-06	
5	167400.	0.465	0.997330	5.69	7.97	1.278E-06	
6	126600.	0.515	0.995915	6.02	8.62	1.514E-06	
7	144800.	0.565	0.996170	6.36	8.99	1.779E-06	
8	157300.	0.620	0.999335	6.61	9.25	2.072E-06	
9	167300.	0.660	0.997267	6.84	9.57	2.451E-06	
10	175400.	0.760	0.997926	7.06	9.88	2.721E-06	
11	184100.	0.745	0.996646	7.30	10.22	3.035E-06	
12	199100.	0.745	0.993346	7.49	10.62	3.408E-06	
13	197700.	0.840	0.998025	7.76	10.87	3.695E-06	
14	203500.	0.885	0.997601	7.98	11.17	4.024E-06	
15	207500.	0.925	0.995341	8.12	11.37	4.133E-06	
16	214400.	0.975	0.996824	8.41	11.78	4.549E-06	
17	218800.	1.025	0.992265	8.59	12.02	4.858E-06	
18	224200.	1.075	1.073	8.62	12.35	5.244E-06	
19	229400.	1.125	1.131	9.05	12.71	5.682E-06	
20	235000.	1.200	1.197	9.36	13.11	6.548E-06	
21	239300.	1.255	1.252	9.41	13.54	7.452E-06	
22	242450.	1.300	1.304	9.82	13.75	7.979E-06	
23	244650.	1.340	1.339	9.96	13.95	8.532E-06	
24	247600.	1.295	1.324	9.99704	10.19	14.27	9.682E-06
25	250600.	1.445	1.449	0.998627	10.42	14.59	9.552E-06
26	252900.	1.500	1.491	0.998883	10.59	14.83	9.849E-06
27	258500.	1.600	1.606	0.999289	11.07	15.22	1.169E-05
28	261500.	1.675	1.673	0.999332	11.34	15.49	1.261E-05

TABLE 88. DATA TABULATION FOR TEST M-70A (CONCL)

SPECIMEN NO.:	CCT	SPECIMEN	$\theta = 0.250$ IN.	$H = 6,000$ IN.	$A = 0.0$ IN.	PHASE =	TEST FREQ= 6.00 Hz.						
							CYCLES	AM MEASURED	AM REGRESSION	MUL. COEF.	COEF F.	K-MAX	DELTA K
ENVIRONMENT CONDITION: AMBIENT AIR													
29	264750.		1.610	1.807			0.999735	11.88	16.63				1.377E-03
30	269660.		1.685	1.888			0.999702	12.22	17.10				1.595E-03
31	272500.		1.980	1.977			0.999792	12.28	17.61				1.636E-03
32	275200.		2.065	2.086			0.999756	12.94	18.12				1.786E-03
33	279800.		2.240	2.243			0.999766	13.68	19.15				2.113E-03
34	282100.		2.346	2.342			0.999771	14.10	19.75				2.316E-03
35	284000.		2.435	2.432			0.999546	14.50	20.29				2.552E-03
36	286000.		2.535	2.533			0.999925	14.94	26.92				2.966E-03
37	288500.		2.675	2.694			0.999422	15.63	21.88				3.326E-03
38	290000.		2.765	2.786			0.999995	16.10	22.54				3.738E-03
39	292000.		2.950	2.942			0.998504	16.87	23.62				4.432E-03
40	294000.		3.110	3.131			0.998461	17.86	25.80				5.332E-03
41	295000.		3.240	3.224			0.998331	18.45	25.84				6.183E-03
42	295700.		3.330	3.240			0.999749	19.53	27.24				7.926E-03
43	296400.		3.420	3.424			0.999077	20.21	28.30				9.120E-03
44	297100.		3.530	3.533			0.999666	21.10	29.54				1.116E-03
45	297800.		3.660	3.666			0.999613	22.13	30.98				1.322E-03
46	298400.		3.810	3.809			0.999913	22.53	31.54				1.424E-03
47	298600.		3.860	3.861			0.997500	23.77	33.27				1.759E-03
48	299100.		4.010	4.014			0.999769	24.32	34.06				2.028E-03
49	299300.		4.080	4.078			0.999527	25.10	35.13				2.346E-03
50	299500.		4.150	4.161			0.994606	26.22	36.71				3.079E-03
51	299750.		4.285	4.275			0.993741	27.62	38.67				4.051E-03
52	299950.		4.460	4.603			0.993942	29.86	41.60				5.349E-03
53	300150.		4.545	4.581			0.997463	32.45	45.43				7.317E-03
54	300300.		4.745	4.795			0.999924	33.82	47.35				9.119E-03
55	300350.		4.835	4.835									

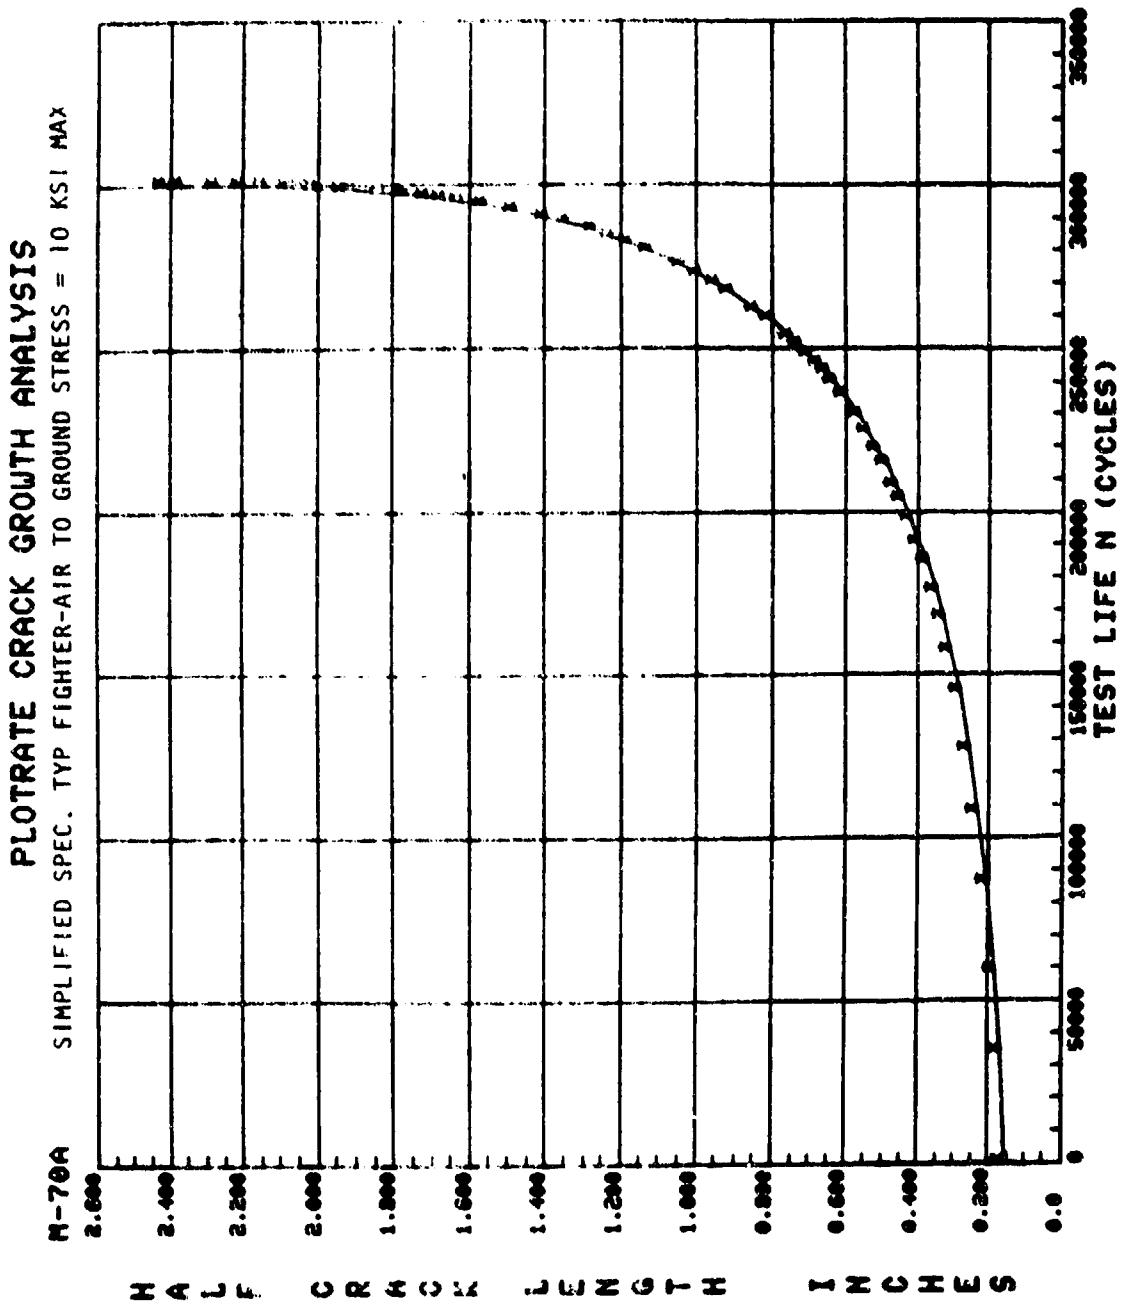


Figure 89. Crack growth curve for test M-70A.

TABLE 89. DATA TABULATION FOR TEST M-71

SPECIMEN NO.: M-71 TYPICAL FIGHTER, INSTRUMENTATION AND NAVIGATION, MAX STRESS = 14 KSI

NO.	CYCLES	A(MEASUR ED)		MULT.	CORR. COEFF	K-MAX	DELTA K	DA/DON
		(REGRESSION)	(ADDITION)					
1	0.	0.295	0.295	0.996324	9.55	11.14	2.873E-06	
2	5000.	0.325	0.320	0.996499	9.95	11.60	2.254E-06	
3	10000.	0.340	0.337	0.988854	10.20	11.90	1.783E-06	
4	20000.	0.370	0.365	0.962712	10.62	12.39	1.606E-06	
5	30000.	0.390	0.393	0.994271	11.03	12.87	1.744E-06	
6	40000.	0.425	0.420	0.996428	11.54	13.46	2.234E-06	
7	48000.	0.470	0.466	0.999276	12.03	14.03	2.697E-06	
8	54000.	0.500	0.503	0.999146	12.49	14.57	3.035E-06	
9	61000.	0.550	0.550	0.999337	13.07	15.25	3.308E-06	
10	68000.	0.600	0.596	0.997790	13.63	15.90	3.682E-06	
11	75000.	0.650	0.649	0.997050	14.23	16.60	4.211E-06	
12	82000.	0.700	0.702	0.996356	14.90	17.39	4.723E-06	
13	88000.	0.770	0.767	0.998425	15.52	18.11	5.465E-06	
14	93000.	0.830	0.825	0.998251	16.12	18.61	6.024E-06	
15	98600.	0.890	0.894	0.998544	16.85	19.66	6.738E-06	
16	101700.	0.945	0.939	0.998778	17.25	20.13	7.222E-06	
17	105700.	0.995	0.997	0.998863	17.82	20.76	8.053E-06	
18	1092100.	1.060	1.061	0.998707	18.42	21.49	9.040E-06	
19	1130000.	1.125	1.125	0.999912	19.01	22.13	1.029E-05	
20	1160000.	1.190	1.191	0.999902	19.61	22.48	1.157E-05	
21	1175000.	1.225	1.226	0.999926	19.92	23.24	1.211E-05	
22	1200000.	1.290	1.290	0.998626	20.50	23.91	1.265E-05	
23	1220000.	1.345	1.343	0.998509	20.96	24.45	1.335E-05	
24	1249900.	1.400	1.397	0.998267	21.43	25.00	1.411E-05	
25	1255000.	1.430	1.438	0.997986	21.79	25.42	1.503E-05	
26	1270000.	1.485	1.482	0.998624	22.18	25.87	1.604E-05	
27	1289000.	1.545	1.546	0.998582	22.72	26.01	1.781E-05	
28	1300000.	1.590	1.588	0.999332	23.09	26.93	1.894E-05	

TABLE 89. DATA TABULATION FOR TEST M-71 (CONT)

SPECIMEN NO.:	M-71	TYPICAL FIGHTER, INSTRUMENTATION AND NAVIGATION, MAX STRESS = 14 KSI		
ECC SPECIMEN	R= 0.250 IN.	H= 6.000 IN.	A= 0.0 IN.	TEST FREQ= 6.000HZ.
PHIN#				
ENVIRONMENT CONDITION: AMBIENT AIR				
NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR. COEFF
29	131000.	1.625	1.625	0.999549
30	132000.	1.665	1.667	0.999547
31	133000.	1.710	1.711	0.999267
32	134000.	1.760	1.759	0.999681
33	135000.	1.810	1.808	0.999837
34	136000.	1.855	1.856	0.999559
35	137800.	1.950	1.949	0.999642
36	139000.	2.015	2.018	0.999800
37	140000.	2.080	2.079	0.999476
38	141000.	2.150	2.146	0.999703
39	142000.	2.215	2.224	0.999384
40	143700.	2.365	2.361	0.999389
41	144700.	2.455	2.448	0.998674
42	145950.	2.560	2.571	0.998295
43	146990.	2.665	2.668	0.999406
44	147700.	2.770	2.768	0.99945
45	148420.	2.870	2.872	0.999775
46	149090.	2.965	2.965	0.999603
47	149570.	3.065	3.068	0.999874
48	150030.	3.160	3.162	0.999906
49	150430.	3.255	3.249	0.998657
50	150920.	3.370	3.372	0.997495
51	151335.	3.480	3.495	0.996565
52	151542.	3.575	3.575	0.998309
53	151804.	3.675	3.662	0.996886
54	151973.	3.775	3.773	0.994689
55	152185.	3.895	3.905	0.998503
56	152308.	3.990	3.995	0.995043

JAV/DK
2.019E-05
2.161E-05
2.250E-05
2.373E-05
2.467E-05
2.549E-05
2.864E-05
3.011E-05
3.317E-05
3.577E-05
3.648E-05
3.805E-05
3.976E-05
4.070E-05
5.322E-05
6.040E-05
6.878E-05
7.610E-05
8.779E-05
9.830E-05
1.078E-04
1.261E-04
2.578E-04
2.950E-04
3.651E-04
4.495E-04

TABLE 89. DATA TABULATION FOR TEST M-71 (CONCL)

SPECIMEN NO.: M-71 TYPICAL FIGHTER, INSTRUMENTATION AND NAVIGATION, MAX STRESS = 14 KSI

GCT	SPECIMEN	$\theta = 0.250$ IN.	$W = 6.000$ IN.	$A_N = 0.0$ IN.			
PRIME	PHMAX				TEST FREQ= 6.000HZ.		
ENVIRONMENT CONDITIONS: AMBIENT AIR							
NO.							
57	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR. COEFF.	K-MAX	DELTA K	DATA
57	152421.	4.085	4.096	0.968980	51.47	60.05	6.549E-04
58	152527.	4.205	4.234	0.976611	54.18	63.21	9.553E-04
59	152606.	4.335	4.397	0.982476	57.86	67.50	1.394E-03
60	152652.	4.560	4.545	0.988756	61.67	71.95	2.037E-03

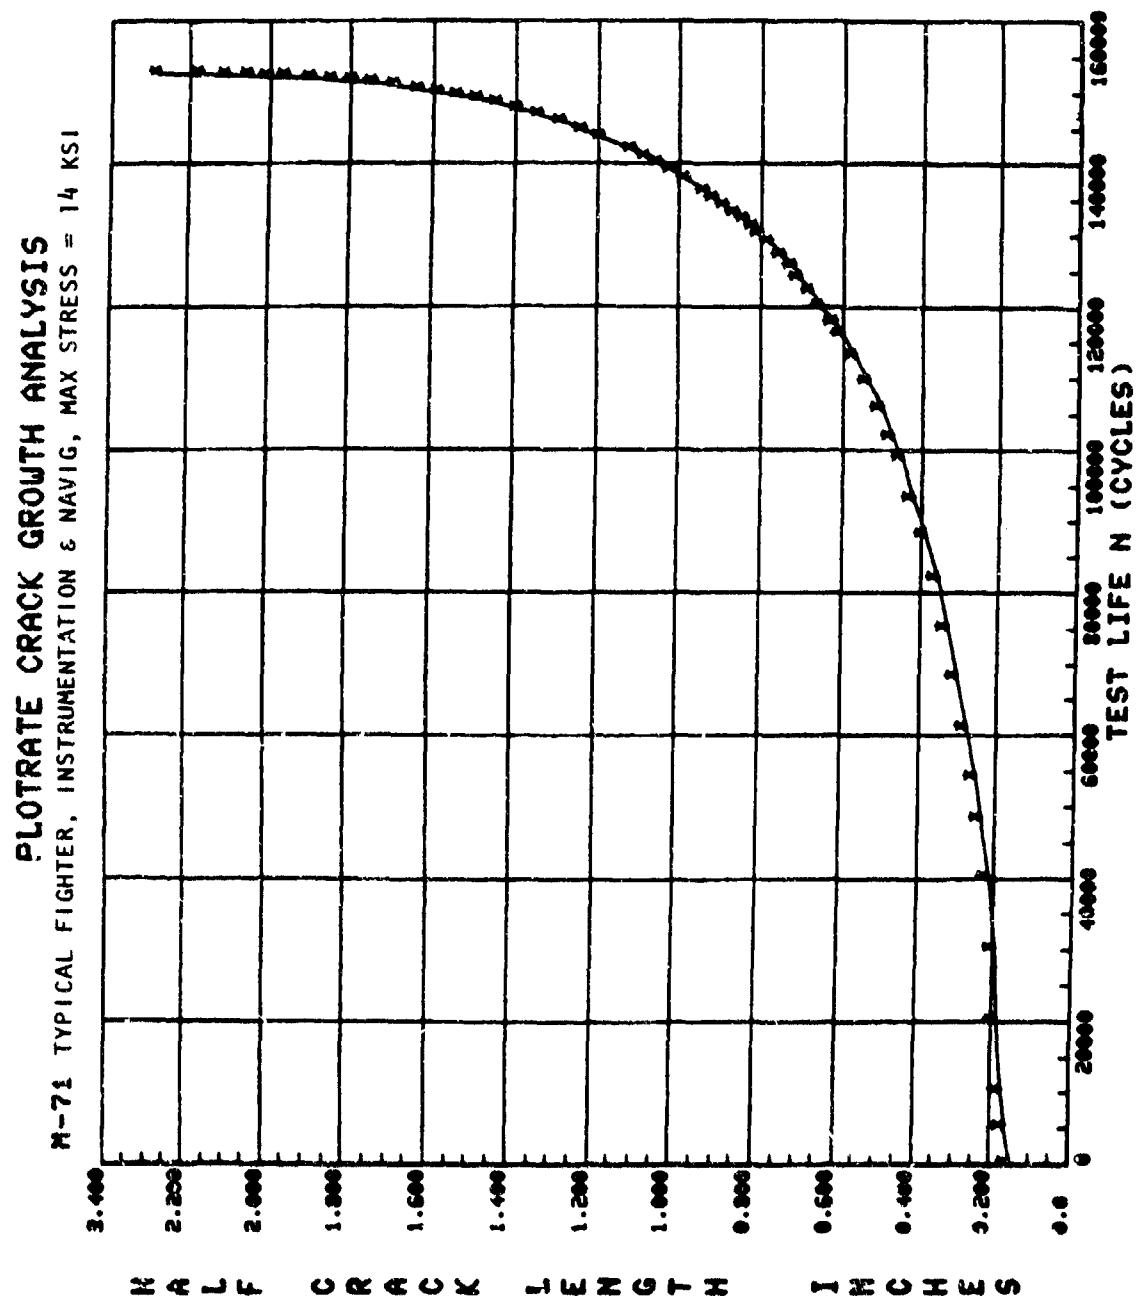


Figure 90. Crack growth curve for test M-71.

TABLE 90. DATA TABULATION FOR TEST M-72

SPECIMEN NO.: M-72 TYPICAL FIGHTER, COMPOSITE MISSION, MAX STRESS = 19 KSI

CLT	SPECIMEN	$\beta = 0.250$ IN.	$W = 6.000$ IN.	$AH = 0.0$ IN.	TEST FREQ = 6.000-HZ.
P MIN		PHMAX			
ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLES	AMEASURD1	AMREGESICN1	MULT. CORR. COEFF	K-MAX
1	U.	0.306	0.310	0.965737	15.39
2	1.000-	0.345	0.327	0.989414	15.00
3	6.000-	0.405	0.401	0.992576	15.13
4	9.750-	0.460	0.466	0.994756	16.32
5	12.700-	0.525	0.525	0.999620	17.34
6	14.750-	0.575	0.574	0.998445	18.14
7	16.600-	0.625	0.628	0.997739	18.99
8	18.250-	0.675	0.682	0.998464	19.82
9	19.000-	0.715	0.710	0.999193	20.24
10	20.350-	0.770	0.772	0.999209	21.13
11	21.350-	0.825	0.825	0.999251	21.88
12	22.250-	0.875	0.875	0.998776	22.56
13	23.000-	0.920	0.910	0.999566	23.14
14	23.600-	0.965	0.962	0.998969	23.72
15	25.000-	1.030	1.031	0.997537	24.62
16	25.800-	1.065	1.085	0.998974	25.29
17	26.600-	1.145	1.150	0.999535	26.11
18	27.570-	1.245	1.244	0.999563	27.26
19	28.300-	1.330	1.324	0.999025	28.23
20	29.070-	1.415	1.422	0.997004	29.39
21	29.500-	1.475	1.482	0.996610	30.09
22	29.800-	1.530	1.529	0.999500	30.64
23	30.300-	1.630	1.621	0.999108	31.72
24	30.800-	1.725	1.730	0.999317	32.98
25	31.300-	1.650	1.853	0.998771	34.41
26	31.700-	1.975	1.969	0.999324	35.75
27	32.100-	2.095	2.101	0.998661	37.38
28	32.400-	2.230	2.228	0.995092	38.62

TABLE 90. DATA TABULATION FOR TEST M-72 (CONCL)

SPECIMEN NO.:	CCT	SPECIMEN	$\theta = 0.250$ IN.	$W = 6.000$ IN.	$A_N = 0.0$ IN.	TEST FREQ= 6.000Hz.	ENVIRONMENT CONDITION: AMBIENT AIR		DAVID K
							PIN#	MAX=	
29	32500-		2-315	2-319	0-999596	39.92	46.22	2.549E-04	
30	32600-		2-420	2-426	0-999411	41.24	47.75	2.890E-04	
31	32000-		2-540	2-544	0-997751	42.72	49.47	3.250E-04	
32	33150-		2-645	2-642	0-998031	43.99	50.96	3.721E-04	
33	33400-		2-675	2-842	0-998532	46.68	54.06	4.735E-04	
34	33500-		2-975	2-938	0-996480	48.03	55.61	5.259E-04	
35	33600-		3-055	3-054	0-999055	49.73	57.58	6.702E-04	
36	33650-		3-115	3-120	0-995887	50.71	58.72	7.394E-04	
37	33700-		3-195	3-196	0-998953	51.90	60.10	6.337E-04	
38	33750-		3-285	3-275	0-997667	53.16	61.56	9.732E-04	
39	33800-		3-370	3-367	0-976321	54.68	63.32	1.352E-03	
40	33850-		3-490	3-506	0-976967	57.12	66.14	1.926E-03	
41	33900-		3-655	3-724	0-985069	61.29	70.97	2.980E-03	
42	33925-		3-690	3-890	0-989409	64.84	75.08	4.194E-03	
43	33430-		3-940	3-941	0-999792	66.01	76.44	5.902E-03	

PLOTRATE CRACK GROWTH ANALYSIS

M-72 TYPICAL FIGHTER, COMPOSITE MISSION, MAX STRESS = 19 KSI

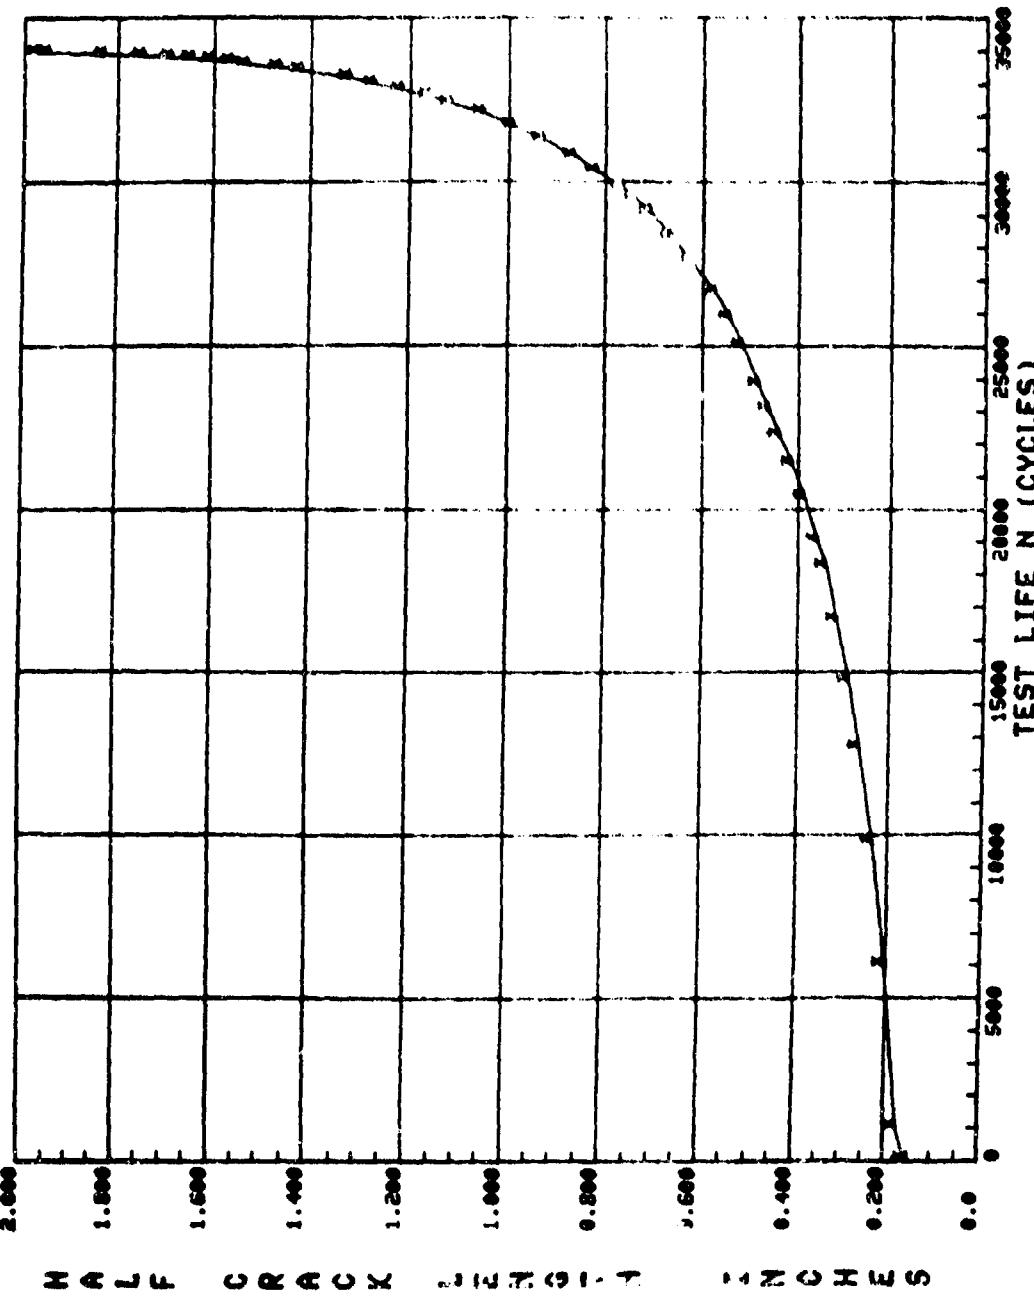


Figure 91. Crack growth curve for test M-72.

TABLE 91. DATA TABULATION FOR TEST M-72A

SPECIMEN NO.: M-72A SIMPLIFIED SPECTRUM, TYP FIGHTER-COMPOSITE MISSION, MAX STRESS = 14 KSI

LEN. - SPECIMEN b= 5.250 IN. W= 6.000 lb. AN= 0.0 IN.
 PHASE= TEST FREQ= 6.0000HZ.

ENVIRONMENT CONDITION: AMBIENT AIR

LEN. - NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. COEF	CUEFF	K-MAX	DA/DN	DELTA K
1	0.	0.330	0.330	0.999831	3.05	2.29	2.462E-06	
2	8800.	0.375	0.374	0.998645	4.10	5.63	2.790E-06	
3	14400.	0.410	0.404	0.994642	4.26	5.86	3.335E-06	
4	24000.	0.470	0.478	0.993743	4.64	6.38	4.609E-06	
5	29100.	0.520	0.527	0.996611	4.87	6.70	5.646E-06	
6	32800.	0.575	0.571	0.994530	5.08	6.98	5.992E-06	
7	36800.	0.625	0.626	0.996745	5.32	7.32	6.753E-06	
8	40800.	0.660	0.681	0.994305	5.56	7.64	7.514E-06	
9	44800.	0.720	0.729	0.996012	5.80	7.97	8.501E-06	
10	48400.	0.800	0.801	0.993448	6.05	8.31	1.046E-05	
11	50600.	0.852	0.850	0.996238	6.24	8.58	1.078E-05	
12	52500.	0.895	0.895	0.997326	6.41	8.81	1.175E-05	
13	54200.	0.942	0.935	0.996267	6.56	9.02	1.252E-05	
14	56700.	0.987	0.997	0.995999	6.78	9.33	1.434E-05	
15	58500.	1.050	1.049	0.997403	6.97	9.59	1.637E-05	
16	59900.	1.095	1.095	0.998256	7.14	9.81	1.774E-05	
17	61200.	1.150	1.148	0.999107	7.32	10.07	1.880E-05	
18	62400.	1.195	1.194	0.998926	7.48	10.29	1.954E-05	
19	63600.	1.245	1.243	0.999117	7.65	10.52	2.007E-05	
20	64800.	1.285	1.289	0.998515	7.80	10.73	2.097E-05	
21	66000.	1.342	1.339	0.994136	7.97	10.96	2.232E-05	
22	67200.	1.390	1.393	0.999578	8.15	11.21	2.427E-05	
23	68400.	1.455	1.454	0.999696	8.36	11.49	2.671E-05	
24	69600.	1.520	1.520	0.999869	8.57	11.79	2.938E-05	
25	71200.	1.620	1.618	0.999625	8.89	12.23	3.256E-05	
26	72700.	1.720	1.720	0.999731	9.22	12.68	3.707E-05	
27	74100.	1.825	1.828	0.994533	9.57	13.16	4.240E-05	
28	75245.	1.925	1.927	0.999717	9.90	13.61	4.537E-05	

TABLE 91. DATA TABULATION FOR TEST M-72A (CONCL)

SPECIMEN NO.:	ECC. SPECIMEN	$\theta = 0.250$ IN.		$W = 6.000$ IN.		$A_N = 0.0$ IN.		TEST FREQ = 6.000HZ.			
		P MIN =	P MAX =	ENVIRONMENT CONDITION =	AMBIENT AIR	A MEASURED	A REGRESSION	MULT. CORR. COEFF	K-MAX	DELTA K	DATA
29	76300-	2.030	2.032	0.999837	10.24	14.03	5.546E-05				
30	77034-	2.115	2.115	0.999344	10.52	14.46	6.169E-05				
31	77899-	2.225	2.227	0.999857	10.89	16.98	6.875E-05				
32	78587-	2.325	2.324	0.998506	11.22	15.43	7.924E-05				
33	79100-	2.410	2.406	0.998667	11.50	15.82	8.467E-05				
34	79655-	2.495	2.509	0.999052	11.67	16.32	9.098E-05				
35	80220-	2.630	2.623	0.999115	12.28	16.88	1.130E-04				
36	80755-	2.755	2.749	0.998369	12.75	17.23	1.327E-04				
37	81212-	2.865	2.879	0.997863	13.25	18.41	1.533E-04				
38	81549-	2.975	2.961	0.999235	13.66	18.78	1.710E-04				
39	81809-	3.060	3.072	0.998943	14.03	19.33	1.919E-04				
40	82017-	3.160	3.156	0.998232	14.39	19.79	2.133E-04				
41	82340-	3.265	3.295	0.996444	15.03	20.67	2.428E-04				
42	82500-	3.380	3.379	0.995024	15.41	21.19	3.046E-04				
43	82660-	3.475	3.480	0.999774	15.90	21.67	3.536E-04				
44	82800-	3.590	3.584	0.9999095	16.44	22.60	4.166E-04				
45	82920-	3.710	3.705	0.996680	17.11	23.53	5.556E-04				
46	83190-	3.855	3.867	0.995066	16.30	24.63	6.613E-04				
47	83200-	3.965	4.001	0.997663	16.92	26.02	8.163E-04				
48	83360-	4.165	4.177	0.991174	20.19	27.77	1.048E-03				
49	83350,	4.290	4.289	0.999747	21.10	29.01	1.267E-03				

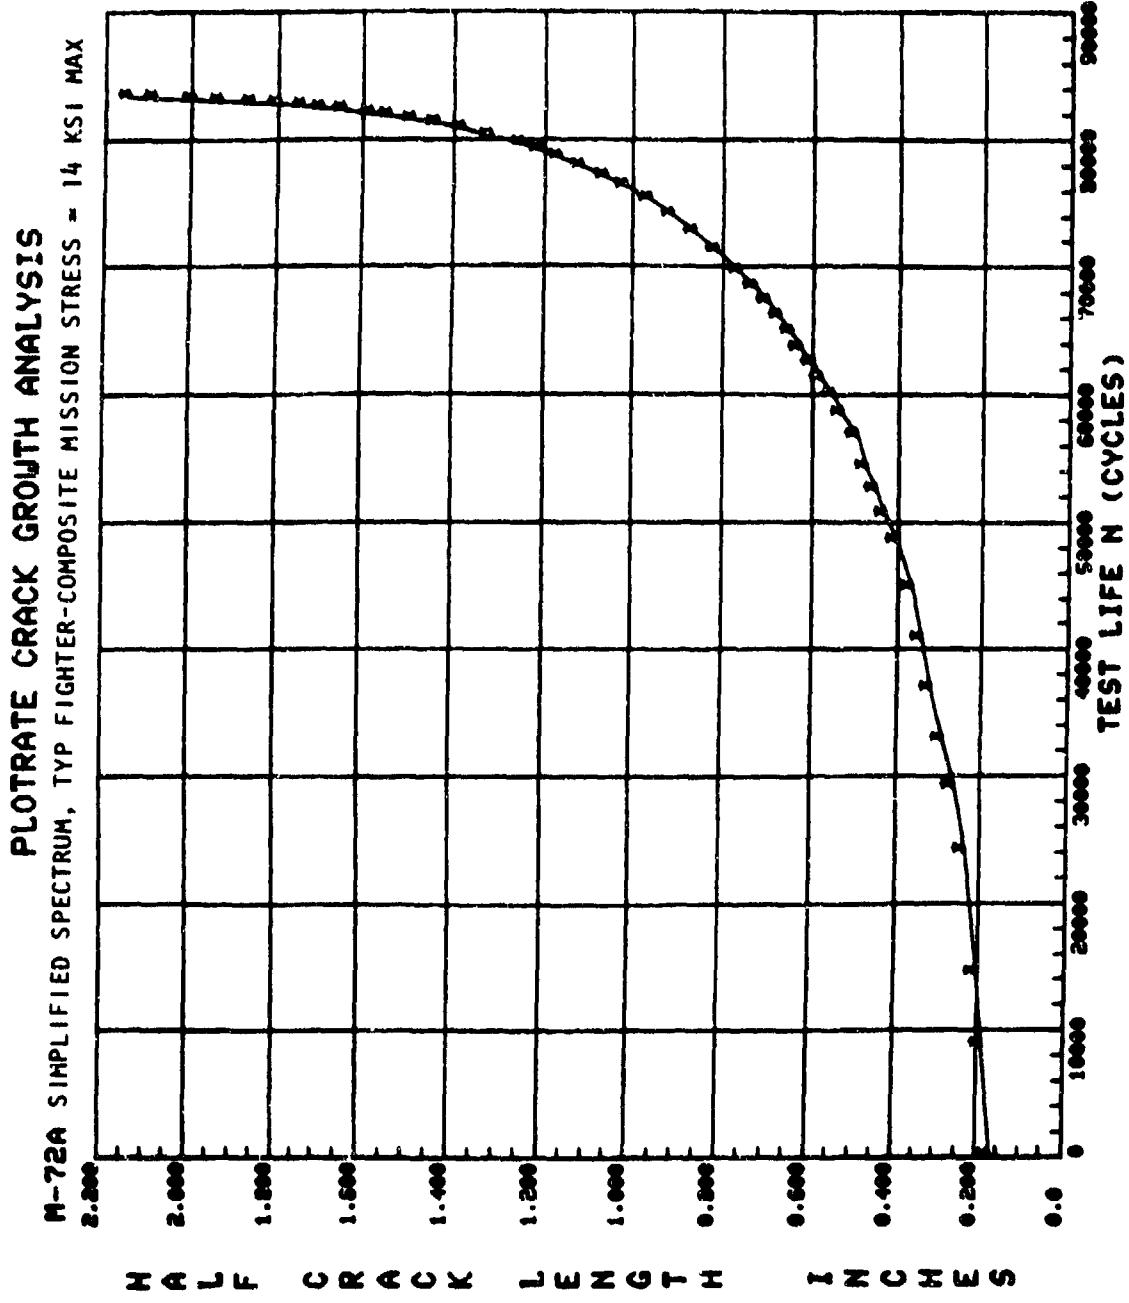


Figure 92. Crack growth curve for test M-72A.

TABLE 92. DATA TABULATION FOR TEST M-72B
 SPECIMEN NO.: M-72B SIMPLIFIED SPECTRUM, TYP FIGHTER-COMPOSITE STRESS = 8 KSI MAX
 CCT SPECIMEN B= 0.250 IN. W= 6.000 IN. AN= C.0 1W.
 PMAX=

ENVIRONMENT CONDITION: AMBIENT AIR		A1MEASURD) A(REGRESSION)		MULT. COEF. COEFF	K-MAX	DA/DN
No.	CYCLES	A1MEASURD)	A(REGRESSION)			
1	0.	0.305	0.305	0.993713	6.47	3.033E-07
2	52500.	0.335	0.342	0.995767	6.86	3.827E-07
3	93000.	0.350	0.374	0.997095	7.17	4.191E-07
4	139000.	0.415	0.414	0.997718	7.55	4.665E-07
5	179700.	0.450	0.456	0.997947	7.90	5.216E-07
6	222400.	0.500	0.496	0.997497	6.27	6.032E-07
7	254000.	0.535	0.534	0.995393	5.59	7.127E-07
8	312000.	0.615	0.626	0.995928	9.32	9.952E-07
9	339700.	0.680	0.682	0.997648	9.74	1.310E-06
10	354800.	0.725	0.722	0.996655	10.03	12.18
11	373900.	0.775	0.783	0.998770	10.46	12.70
12	385700.	0.830	0.825	0.998768	10.75	13.05
13	401700.	0.690	0.686	0.997955	11.17	13.56
14	415000.	0.945	0.950	0.997813	11.57	14.05
15	425300.	0.995	0.998	0.998195	11.88	14.43
16	432600.	1.045	1.036	0.998093	12.12	14.72
17	444900.	1.100	1.108	0.998077	12.53	15.26
18	451500.	1.150	1.143	0.998014	12.01	15.56
19	459400.	1.200	1.197	0.997327	13.11	15.92
20	466600.	1.250	1.250	0.996151	13.43	16.30
21	473400.	1.295	1.304	0.997043	13.75	16.69
22	477000.	1.340	1.336	0.997074	13.94	16.92
23	481900.	1.390	1.384	0.998020	14.22	17.26
24	487000.	1.430	1.433	0.998438	14.50	17.61
25	493000.	1.495	1.488	0.998933	14.82	17.94
26	505500.	1.620	1.627	0.998469	15.61	18.99
27	512000.	1.705	1.711	0.995931	16.09	19.26
28	518700.	1.805	1.762	0.993226	16.49	20.03

TABLE 92. DATA TABULATION FOR TEST M-72B (CONCL)

SPECIMEN No.: M-72B SIMPLIFIED SPECTRUM, TYP FIGHTER-COMPOSITE STRESS = 8 KSI MAX

ECC SPECIMEN δ= 0.210 IN. W= 6.000 IN. AN= 0.0 IN.

PHASE=

TEST FREQ= 6.000HZ.

ENVIRONMENT CONDITION: AMBIENT AIR

NU.	CYCLES	AI MEASURED	AI REGRESSION	MULT. COEFF	K-MAX	DELTA K	DATA
29	523500.	1.870	1.837	0.99401	16.81	20.41	6.468E-06
30	533700.	1.945	1.966	0.996671	17.54	21.30	7.433E-06
31	544000.	2.210	2.200	0.999469	18.90	22.95	1.049E-05
32	555000.	2.355	2.359	0.999534	19.85	24.10	1.253E-05
33	555500.	2.470	2.478	0.999409	20.58	24.99	1.399E-05
34	563600.	2.595	2.591	0.999863	21.23	25.85	1.553E-05
35	564000.	2.725	2.736	0.999785	22.22	26.98	1.752E-05
36	573800.	2.915	2.922	0.999612	23.48	28.51	2.039E-05
37	575000.	3.005	3.003	0.999816	24.06	29.21	2.164E-05
38	577600.	2.690	3.092	0.999675	24.70	30.00	2.345E-05
39	579000.	3.192	3.185	0.999475	25.43	30.85	2.548E-05
40	581000.	3.265	3.290	0.999577	26.23	31.86	2.795E-05
41	582900.	3.400	3.399	0.999599	27.13	32.95	3.193E-05
42	584330.	3.490	3.491	0.999653	27.92	33.91	3.554E-05
43	585940.	3.605	3.612	0.999622	29.03	35.25	3.981E-05
44	587060.	3.765	3.699	0.999655	29.86	36.26	4.296E-05
45	588160.	3.860	3.798	0.999576	30.86	37.47	4.689E-05
46	589260.	3.900	3.903	0.999477	32.00	38.85	5.225E-05
47	590150.	4.000	4.002	0.999462	33.14	40.24	5.901E-05
48	591000.	4.100	4.105	0.999139	34.40	41.77	6.908E-05
49	591650.	4.200	4.195	0.998653	35.59	43.22	8.097E-05
50	592300.	4.295	4.304	0.998416	37.14	45.69	9.767E-05
51	5942800.	4.400	4.402	0.997851	38.66	46.95	1.184E-04
52	593300.	4.510	4.526	0.997728	40.77	49.51	1.522E-04
53	5943630.	4.620	4.633	0.996246	42.75	51.91	1.931E-04
54	593900.	4.725	4.736	0.992445	45.05	54.71	2.627E-04
55	594080.	4.825	4.830	0.996104	47.23	57.35	3.403E-04
56	594235.	4.910	4.916	0.998049	50.07	60.80	4.151E-04

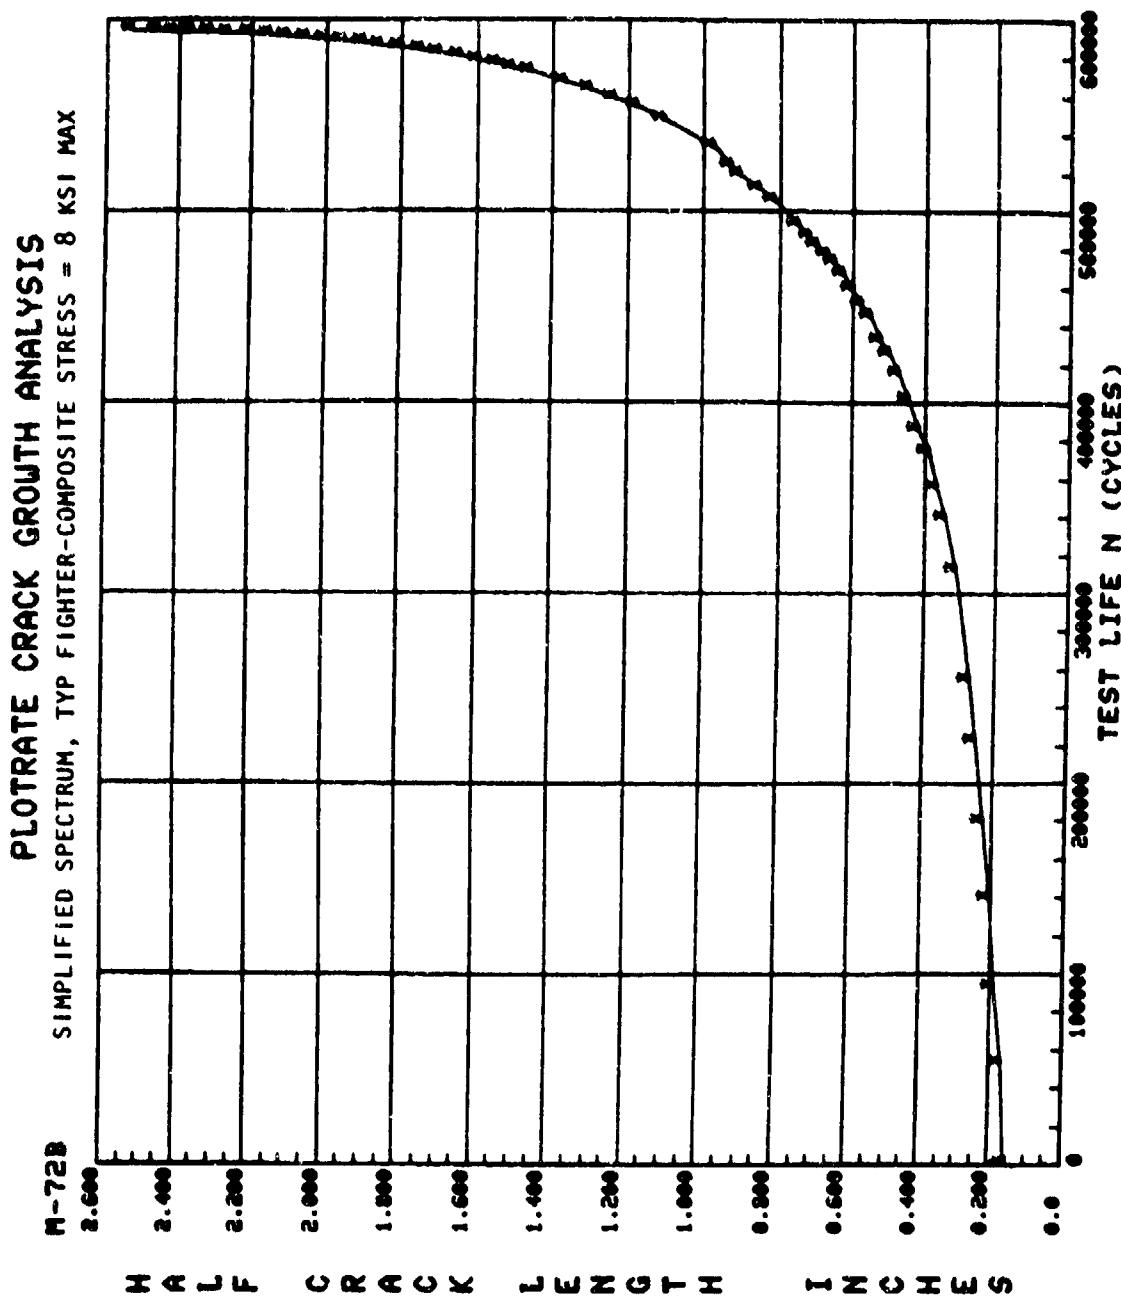


Figure 93. Crack growth curve for test M-72B.

TABLE 93. DATA TABULATION FOR TEST M-74

SPECIMEN NO.: M-74		SIMPLIFIED SPECTRUM. TYP. TRANSPORT, MAX STRESS = 16.8 KSI		TEST FREQ = 6.00 Hz.	
CCT	SPECIMEN	B = 0.250 IN.	b = 6.000 IN.	A _N = 0.0 IN.	
P _{MIN}	P _{MAX}	ENVIRONMENT CONDITION: AMBIENT AIR			
NO-	CYCLES	A(MEASURED)	A(REGRESSION)	MUL. CORR. COEFF	K-MAX
1	0.	0.460	0.440	0.999283	16.01
2	106712.	0.495	0.493	0.999312	14.84
3	284000.	0.555	0.557	0.994854	15.79
4	303000.	0.565	0.562	0.986208	15.87
5	415944.	0.590	0.602	0.980200	16.44
6	488720.	0.625	0.634	0.984567	16.08
7	500000.	0.645	0.643	0.984962	17.00
					27.63
					27.77
					24.11
					25.66
					1.734E-07
					1.855E-07
					25.79
					2.052E-07
					26.71
					27.42
					3.679E-07
					4.251E-07

M-74 PLOTRATE CRACK GROWTH DATA
 SIMPLIFIED SPECTRUM, TYP TRANSPORT, STRESS = 16.8 MAX

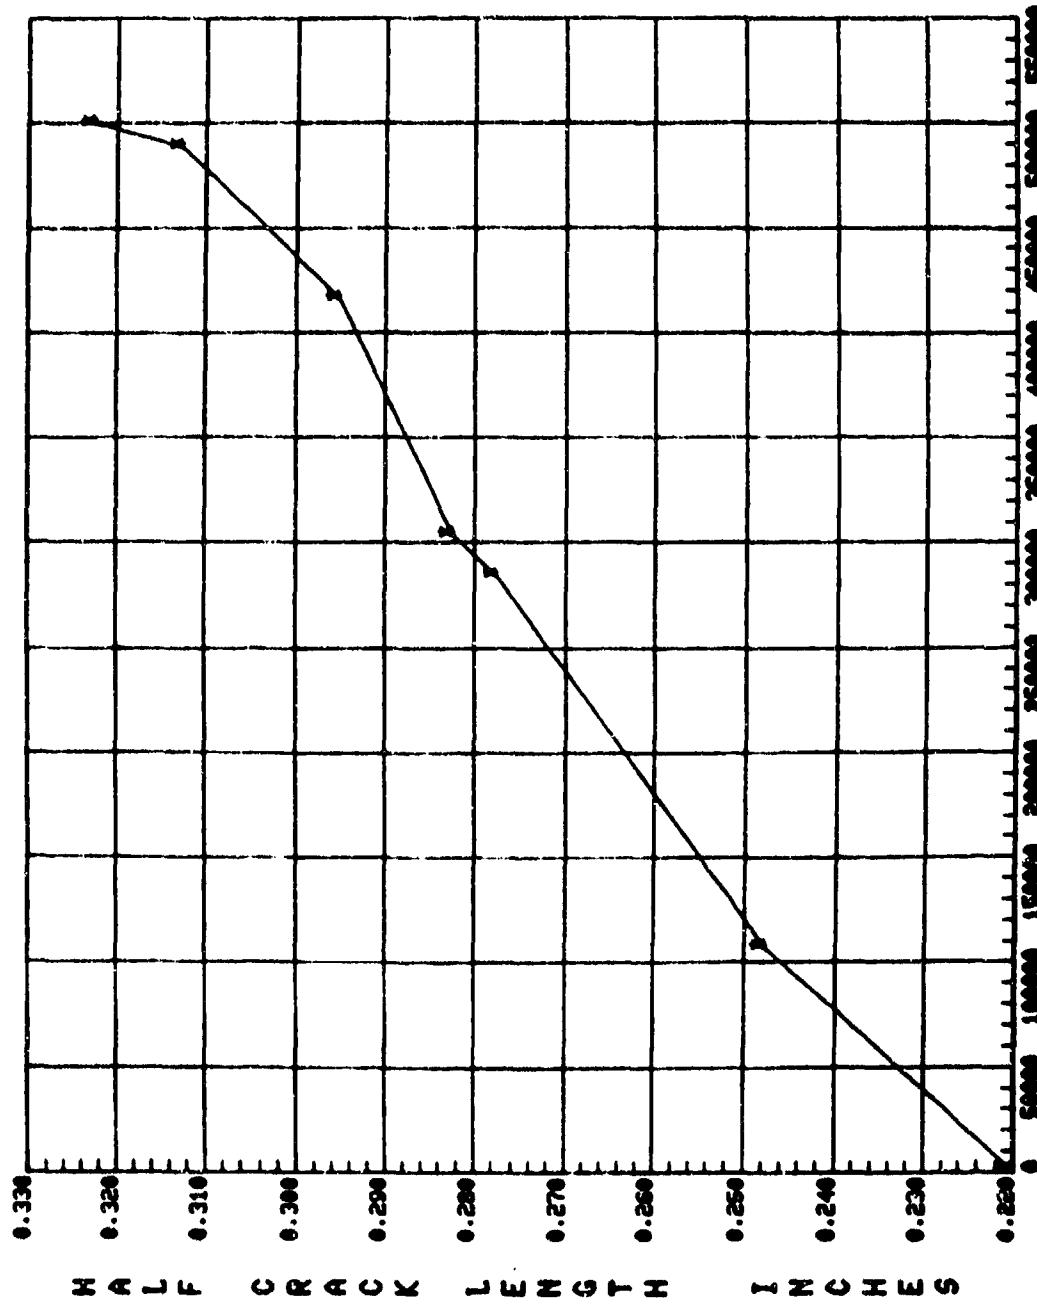


Figure 94. Crack growth curve for test M-74.

TABLE 94. DATA TABULATION FOR TEST M-77

SPECIMEN NO.: M-77 SIMPLIFIED FLIGHT SPECTRUM, TYPICAL FIGHTER, MAX STRESS ≈ 20 KSI

G= 9.250 IN. H= 6.000 IN. A= 0.0 IN.

P_{MIN}= P_{MAX}= TEST FREQ= 6000HZ.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	AS MEASURED)	A(REGRESSION)	MULT. CURR. COEFF	K-MAX	DELTA K	DA/DN
1	0.	0-300	0-301	0.98294E	13.79	15.85	2.794E-06
2	700.	0-315	0-309	0.99074E	13.96	16.06	6.446E-06
3	2900.	0-335	0-346	0.99424E	14.73	17.00	8.630E-06
4	4781.	0-385	0-378	0.99591E	15.45	17.77	9.806E-06
5	7500.	0-440	0-436	0.99677E	16.60	19.09	1.401E-05
6	10000.	0-495	0-503	0.99769E	17.83	20.53	1.394E-05
7	11500.	0-545	0-543	0.99805E	19.50	21.34	1.569E-05
8	13400.	0-610	0-604	0.99765E	19.60	22.54	1.864E-05
9	15450.	0-675	0-685	0.99806E	20.91	24.05	2.281E-05
10	16700.	0-745	0-742	0.99905E	21.79	25.06	2.600E-05
11	18260.	0-830	0-829	0.99876E	23.08	26.54	3.187E-05
12	19750.	0-925	0-931	0.99865E	24.23	28.21	3.807E-05
13	20520.	0-965	0-989	0.99938E	25.34	29.14	4.164E-05
14	21140.	1-050	1-042	0.99682E	26.06	29.97	4.659E-05
15	21790.	1-105	1-106	0.99576E	26.93	34.94	5.089E-05
16	22470.	1-170	1-177	0.99858E	27.63	32.01	5.655E-05
17	23100.	1-255	1-248	0.99864E	28.75	33.06	6.557E-05
18	23425.	1-315	1-320	0.99638E	29.66	34.11	7.652E-05
19	24010.	1-375	1-381	0.99268E	30.43	34.99	8.533E-05
20	24275.	1-425	1-425	0.99943E	30.97	35.62	9.200E-05
21	24615.	1-495	1-493	0.99967E	31.61	36.58	1.036E-04
22	25145.	1-605	1-607	0.99901E	33.21	38.20	1.222E-04
23	25575.	1-720	1-716	0.99949E	34.54	39.72	1.424E-04
24	25900.	1-820	1-828	0.99929E	35.90	41.29	1.669E-04
25	26225.	1-935	1-932	0.99924E	37.18	42.76	1.925E-04
26	26575.	2-055	2-060	0.99959E	36.75	44.57	2.279E-04
27	26810.	2-170	2-172	0.99953E	40.15	46.17	2.612E-04
28	27005.	2-275	2-274	0.99945E	41.45	47.67	3.000E-04

TABLE 94. DATA TABULATION FOR TEST M-77 (CONCL)

SPECIMEN NO.: M-77		SIMPLIFIED FLIGHT SPECTRUM, TYPICAL FIGHTER, MAX STRESS = 20 KSI			
CCT	SPECIMEN	B= 6.25G IN.	W= 6.000 IN.	AH= 0.0	IN.
PHIN=	PMAX=	TEST FREQ= 6.00HZ.			
ENVIRONMENT CONDITIONS:	AMBIENT AIR				
NO.	CYCLES	AI MEASURED	AI REGRESSION	MULT. CORR. COEFF	K-MAX
29	17200-	2.395	2.396	0.998922	43.02
30	27375-	2.515	2.523	0.999256	44.69
31	27507-	2.634	2.636	0.999300	46.23
32	27620-	2.750	2.751	0.999169	47.83
33	27715-	2.865	2.872	0.998622	49.58
34	27794-	2.975	2.978	0.996445	51.17
35	27857-	3.065	3.069	0.997415	52.91
36	27904-	3.180	3.183	0.993409	54.57
37	27956-	3.340	3.346	0.994593	57.18
38	27996-	3.475	3.509	0.994254	60.18
39	28012-	3.590	3.580	0.994765	61.56
40	28033-	3.710	3.726	0.995495	64.62
41	28045-	3.630	3.827	0.991942	66.30
					DELTA A
					59.47
					3.531E-04
					4.195E-04
					4.951E-04
					5.888E-04
					7.030E-04

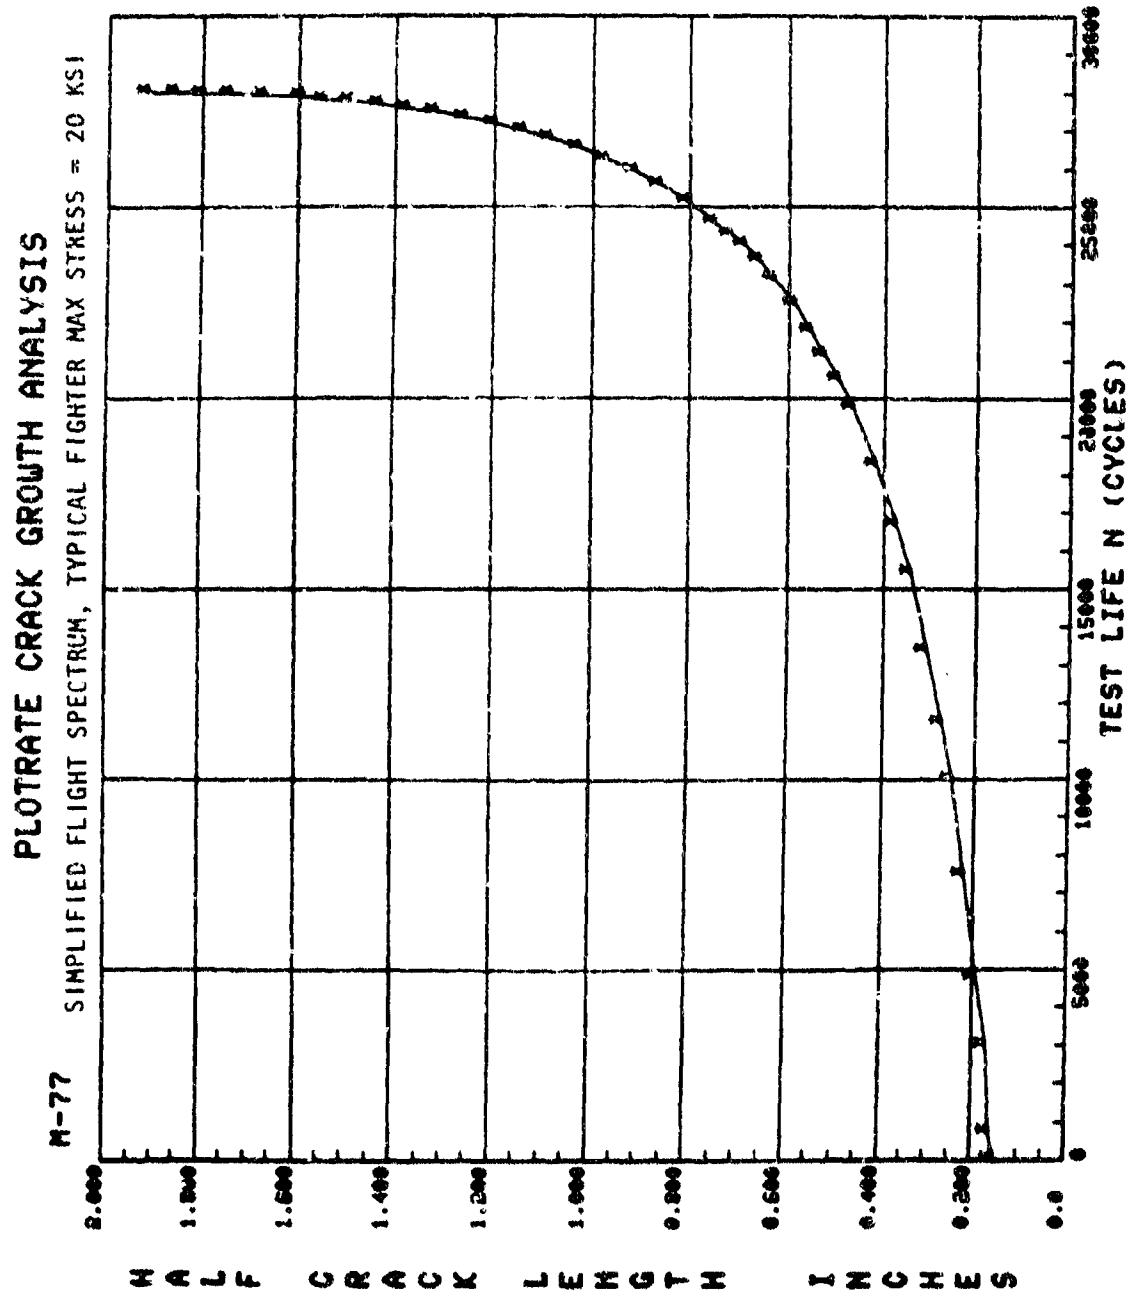


Figure 95. Crack growth curve for test M-77.

TABLE 95. DATA TABULATION FOR TEST M-77A

SPECIMEN NO.: H-77A	CCT	SPECIMEN	B = 0.250 IN.	W = 6.000 IN.	A _N = 0.0	IN.	SIMPLIFIED SPECTRUM, TYP FIGHTER STRESS = 14 KSI MAX		TEST FREQUENCY = 6.00HZ.				
							P _{MIN}	P _{MAX}		MULT.	CURR. CUTOFF	K-MAX	UTIL. K
ENVIRONMENT CONDITION: AMBIENT AIR													
NO.	CYCLES	A1 MEASURED(D)	A1 REGRESSION)	MULT.	CURR. CUTOFF	K-MAX	Util. K	UNKN					
1	0.	0.295	0.295	0.999561	6.36	9.09	1.005E-06						
2	21900.	0.370	0.371	0.999646	7.14	10.21	2.251E-06						
3	34400.	0.450	0.446	0.999559	7.54	11.20	3.244E-06						
4	43200.	0.510	0.516	0.998612	8.44	12.05	4.426E-06						
5	49000.	0.565	0.568	0.999059	8.85	12.66	5.169E-06						
6	54700.	0.625	0.626	0.999556	9.32	13.31	5.973E-06						
7	59900.	0.695	0.691	0.999291	9.50	14.00	6.989E-06						
8	65300.	0.765	0.764	0.999264	10.36	14.60	8.259E-06						
9	70300.	0.855	0.856	0.999295	10.52	15.62	9.509E-06						
10	75200.	0.955	0.957	0.999437	11.62	16.60	1.165E-05						
11	76000.	1.025	1.025	0.999680	12.05	17.22	1.266E-05						
12	81500.	1.120	1.119	0.999790	12.63	16.65	1.427E-05						
13	62710.	1.155	1.154	0.999695	12.85	16.36	1.488E-05						
14	84525.	1.205	1.209	0.999419	13.18	16.63	1.615E-05						
15	26062.	1.260	1.256	0.999532	13.47	19.23	1.788E-05						
16	57261.	1.366	1.362	0.999521	13.74	19.62	1.903E-05						
17	66466.	1.350	1.352	0.999277	14.03	20.64	2.063E-05						
18	89543.	1.400	1.395	0.999310	14.26	20.39	2.169E-05						
19	90823.	1.450	1.449	0.999038	14.59	20.84	2.473E-05						
20	92006.	1.500	1.502	0.999544	14.90	21.28	2.401E-05						
21	94057.	1.605	1.606	0.999417	15.49	22.13	2.755E-05						
22	95604.	1.705	1.697	0.999911	16.31	22.87	3.089E-05						
23	97355.	1.610	1.613	0.998797	16.62	23.79	3.617E-05						
24	98626.	1.900	1.904	0.999058	17.19	24.56	3.969E-05						
25	99936.	2.005	2.012	0.999302	17.81	25.44	4.434E-05						
26	100981.	2.120	2.108	0.999256	18.36	26.23	4.075E-05						
27	102190.	2.275	2.232	0.999227	19.09	27.27	5.423E-05						
28	103219.	2.245	2.346	0.995247	19.77	28.24	6.160E-05						

TABLE 95. DATA TABULATION FOR TEST M-77A (CONCL)

SCT.	SPECIMEN	B= 0.250 IN.	W= 6.000 IN.	AN= 0.0	IN.	TEST FREQ= 6.00HZ.	
						P MAX=	
ENVIRONMENT CONDITION: AMBIENT AIR							
-	NO.	CYCLES	A (MEASURED)	A (REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K DA/DN
-	29	104111-	2.415	2.455	0.995317	23.44	29.12 7.138E-05
30	104812-	2.550	2.559	0.999346	21.08	30.12 7.937E-05	
31	105617-	2.660	2.655	0.997240	21.69	30.99 9.404E-05	
32	106015-	2.775	2.771	0.997131	22.45	32.63 1.110E-04	
33	106420-	2.850	2.870	0.998057	23.13	33.64 1.457E-04	
-	34	106924-	3.005	2.994	0.998523	23.99	34.27 1.432E-04
-	35	107297-	3.110	3.107	0.998165	24.92	35.45 1.024E-04
36	107592-	3.205	3.210	0.995241	25.60	36.57 1.797E-04	
37	107838-	3.310	3.317	0.999354	26.45	37.79 2.047E-04	
38	108101-	3.405	3.400	0.999149	27.14	38.77 2.346E-04	
39	108361-	3.520	3.527	0.999322	28.24	40.34 2.701E-04	
-	40	108521-	3.615	3.616	0.996360	29.07	41.52 3.220E-04
-	41	108693-	3.720	3.730	0.999254	30.17	43.14 3.795E-04
42	108867-	3.860	3.871	0.998487	31.64	45.26 4.074E-04	
43	108950-	3.955	3.949	0.998973	32.52	46.45 5.280E-04	
44	109050-	4.050	4.059	0.999063	33.84	48.32 6.059E-04	
45	109150-	4.190	4.189	0.998349	35.51	50.73 6.942E-04	

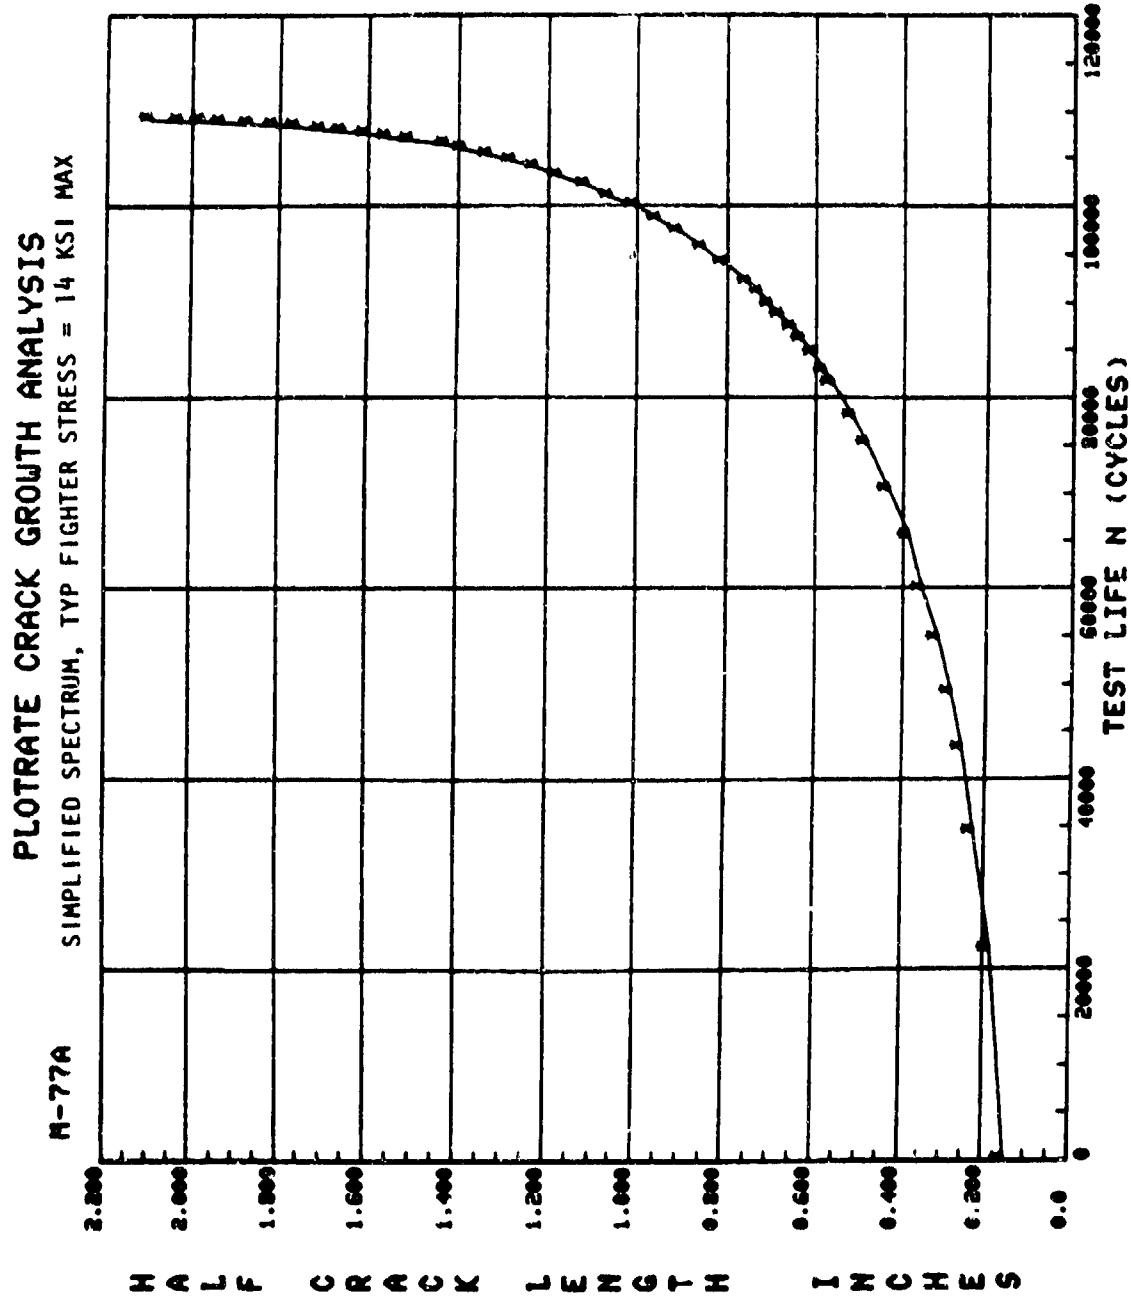


Figure 96. Crack growth curve for test M-77A.

TABLE 96. DATA TABULATION FOR TEST M-78

SPECIMEN NO.:	MATERIAL:	SPECIMEN	B= 0.250 IN.	H= 6.000 IN.	A= 0.0 IN.	TEST FREQ= 6.00HZ.	ENVIRONMENT CONDITION: AMBIENT AIR		TEST FREQ= 6.00HZ.	TEST FREQ= 6.00HZ.
							P MIN=	P MAX=		
NO.	CYCLES	A(MEASUR'D)	A(REGRESSION)	MULT.	CORR.	COEFF	K-MAX	DA/DK	DELTA K	DELTA K
1	C.	0.245	0.295	1.000000	1.000000	1.227	4.580E-06	4.391E-06	16.36	17.47
2	5000.	0.340	0.336	0.996418	0.996418	13.10	4.391E-06	5.203E-06	16.65	16.410E-06
3	10000.	0.385	0.382	0.997507	0.997507	13.98	5.203E-06	6.410E-06	19.97	7.298E-06
4	15000.	0.420	0.436	0.997154	0.997154	14.98	6.410E-06	7.298E-06	20.62	22.17
5	16000.	0.446	0.476	0.998720	0.998720	15.62	7.298E-06	9.235E-06	23.39	1.161E-05
6	22000.	0.575	0.528	0.996416	0.996416	16.63	1.161E-05	1.341E-05	24.31	24.66
7	25000.	0.592	0.598	0.994334	0.994334	17.54	1.341E-05	1.341E-05	24.66	25.35
8	27000.	0.615	0.644	0.996776	0.996776	18.23	1.470E-05	1.616E-05	26.32	27.68
9	220000.	0.675	0.673	0.995495	0.995495	18.64	1.797E-05	1.797E-05	28.91	2.112E-05
10	140000.	0.710	0.701	0.995923	0.995923	19.04	2.112E-05	2.112E-05	29.72	2.260E-05
11	207000.	0.752	0.751	0.995499	0.995499	19.74	2.442E-05	2.442E-05	30.90	2.520E-05
12	330000.	0.670	0.820	0.997915	0.997915	20.76	2.839E-05	3.182E-05	31.95	3.260E-05
13	350000.	0.905	0.903	0.998603	0.998603	21.73	3.182E-05	3.501E-05	33.91	3.647E-05
14	360000.	0.925	0.947	0.998415	0.998415	22.29	3.501E-05	3.983E-05	34.56	3.983E-05
15	375000.	1.010	1.020	0.996299	0.996299	23.13	4.506E-05	4.506E-05	35.40	4.506E-05
16	388000.	1.040	1.064	0.998163	0.998163	23.96	4.839E-05	4.839E-05	36.00	4.842E-05
17	398000.	1.140	1.142	0.998789	0.998789	24.64	32.85	3.647E-05	37.22	3.647E-05
18	408000.	1.205	1.216	0.998126	0.998126	25.44	33.91	3.983E-05	38.08	3.983E-05
19	41397.	1.255	1.252	0.999627	0.999627	25.92	39.85	7.092E-05	39.91	7.092E-05
20	42055.	1.305	1.309	0.999355	0.999355	26.55	41.45	6.246E-05	41.51	6.246E-05
21	42491.	1.350	1.347	0.999505	0.999505	27.03	42.73	9.276E-05	44.38	1.071E-04
22	43292.	1.475	1.429	0.999760	0.999760	27.92	44.38	1.191E-04	45.76	1.191E-04
23	42463.	1.490	1.467	0.999673	0.999673	28.56	46.04	6.041E-05	46.04	6.041E-05
24	44752.	1.610	1.609	0.999798	0.999798	29.91	47.44	6.246E-05	48.73	6.246E-05
25	45483.	1.715	1.716	0.999348	0.999348	31.11	49.73	9.276E-05	51.32	9.276E-05
26	45993.	1.8C5	1.804	0.999473	0.999473	32.05	52.05	1.191E-04	53.32	1.191E-04
27	46572.	1.910	1.916	0.999640	0.999640	33.26	54.38	1.071E-04	55.76	1.071E-04
28	470000.	2.010	2.010	0.999757	0.999757	34.32	56.32	1.191E-04	57.76	1.191E-04

TABLE 96. DATA TABULATION FOR TEST M-78 (CONCL)

SPECIMEN NO.: M-76 TYPICAL FIGHTER, MAX STRESS = 18 KSI

P= 5.05G IN. W= 6.000 IN. AN= 0.0 I_n.P_{MIN}= P_{MAX}=

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A(MEASURD)	A(REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K	DA/DK
29	47363.	2.105	2.104	0.999406	35.37	47.16	1.343E-04
30	47737.	2.205	2.203	0.999383	36.49	46.46	1.501E-04
31	46047.	2.290	2.297	0.999227	37.57	50.09	1.684E-04
32	46329.	2.400	2.394	0.998925	38.69	51.56	1.921E-04
33	46637.	2.510	2.517	0.998566	40.14	53.53	2.329E-04
34	46852.	2.615	2.621	0.996631	41.41	55.21	2.669E-04
35	49001.	2.700	2.701	0.999811	42.41	56.54	3.015E-04
36	49165.	2.610	2.805	0.999807	43.74	58.33	3.406E-04
37	49326.	2.915	2.919	0.996426	45.25	60.33	3.487E-04
38	49464.	3.030	3.030	0.999539	46.77	62.37	4.283E-04
39	49587.	3.125	3.132	0.997413	48.31	64.42	4.994E-04
40	49683.	3.240	3.236	0.992652	49.76	66.35	6.986E-04
41	49780.	3.340	3.348	0.995192	51.83	69.11	7.755E-04
42	49830.	3.420	3.429	0.996474	52.82	70.43	8.913E-04
43	49885.	3.545	3.527	0.992453	54.48	72.63	1.149E-03
44	49949.	3.665	3.689	0.991497	57.40	76.53	1.515E-03
45	49976.	3.755	3.774	0.994160	59.05	78.73	1.819E-03
46	50017.	3.935	3.935	0.999810	62.39	63.19	2.576E-03

PLOT RATE CRACK GROWTH ANALYSIS
N-78 N-78 TYPICAL FIGHTER, MAX STRESS = 18 KSI

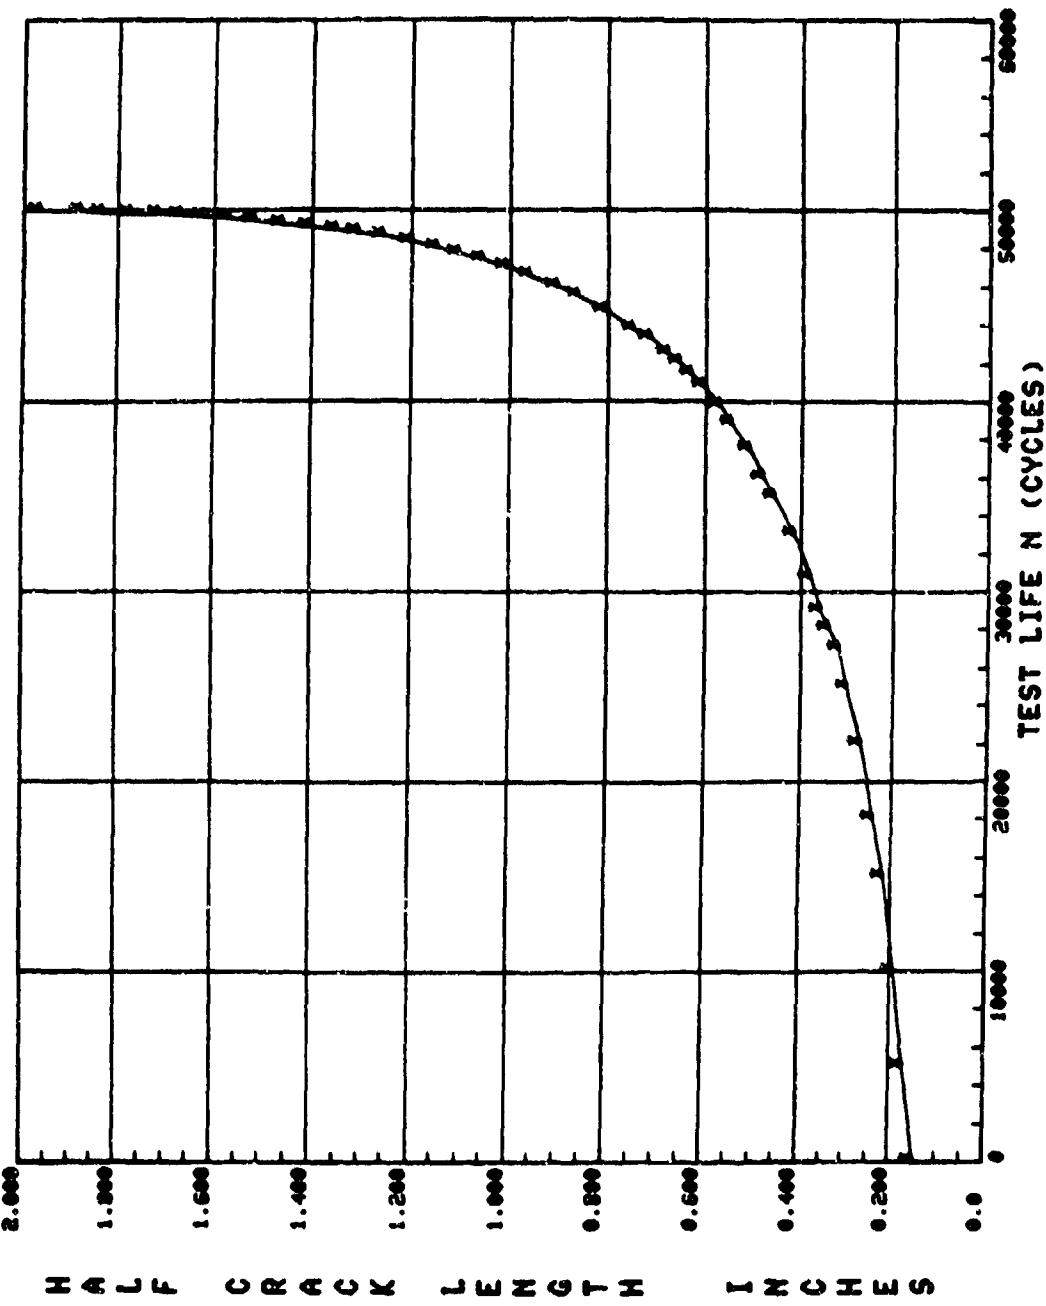


Figure 97. Crack growth curve for test N-78.

TABLE 97. DATA TABULATION FOR TEST M-79

SPECIMEN NO.: M-79		SIMPLIFIED SPECTRUM. TYP. TRANSPORT. MAX STRESS = 12 KSI			
CYCLES	TEST FREQ = 6.00 Hz.	TEST FREQ = 6.00 Hz.	TEST FREQ = 6.00 Hz.	TEST FREQ = 6.00 Hz.	TEST FREQ = 6.00 Hz.
PMIN =					
ENVIRONMENT CONDITION: AMBIENT AIR					
NO. CYCLES					
1	0.	0.815	0.817	0.903832	13.74
2	42000.	0.870	0.852	0.979546	14.05
3	128567.	0.905	0.901	0.979792	14.47
4	213000.	0.935	0.940	0.982489	14.80
5	291000.	0.970	0.969	0.995944	15.04
6	361447.	1.005	1.004	0.997278	15.33
7	431746.	1.040	1.047	0.997231	15.68
8	500000.	1.100	1.100	0.997915	16.09
					26.15
					4.542E-07
					5.350E-07
					3.656E-07
					2.716E-07
					2.385E-07
					2.444E-07
					2.897E-07
					3.488E-07

PLOT RATE CRACK GROWTH DATA
M-79 SIMPLIFIED SPECTRUM, TYP TRANSPORT, MAX STRESS = 12 KSI

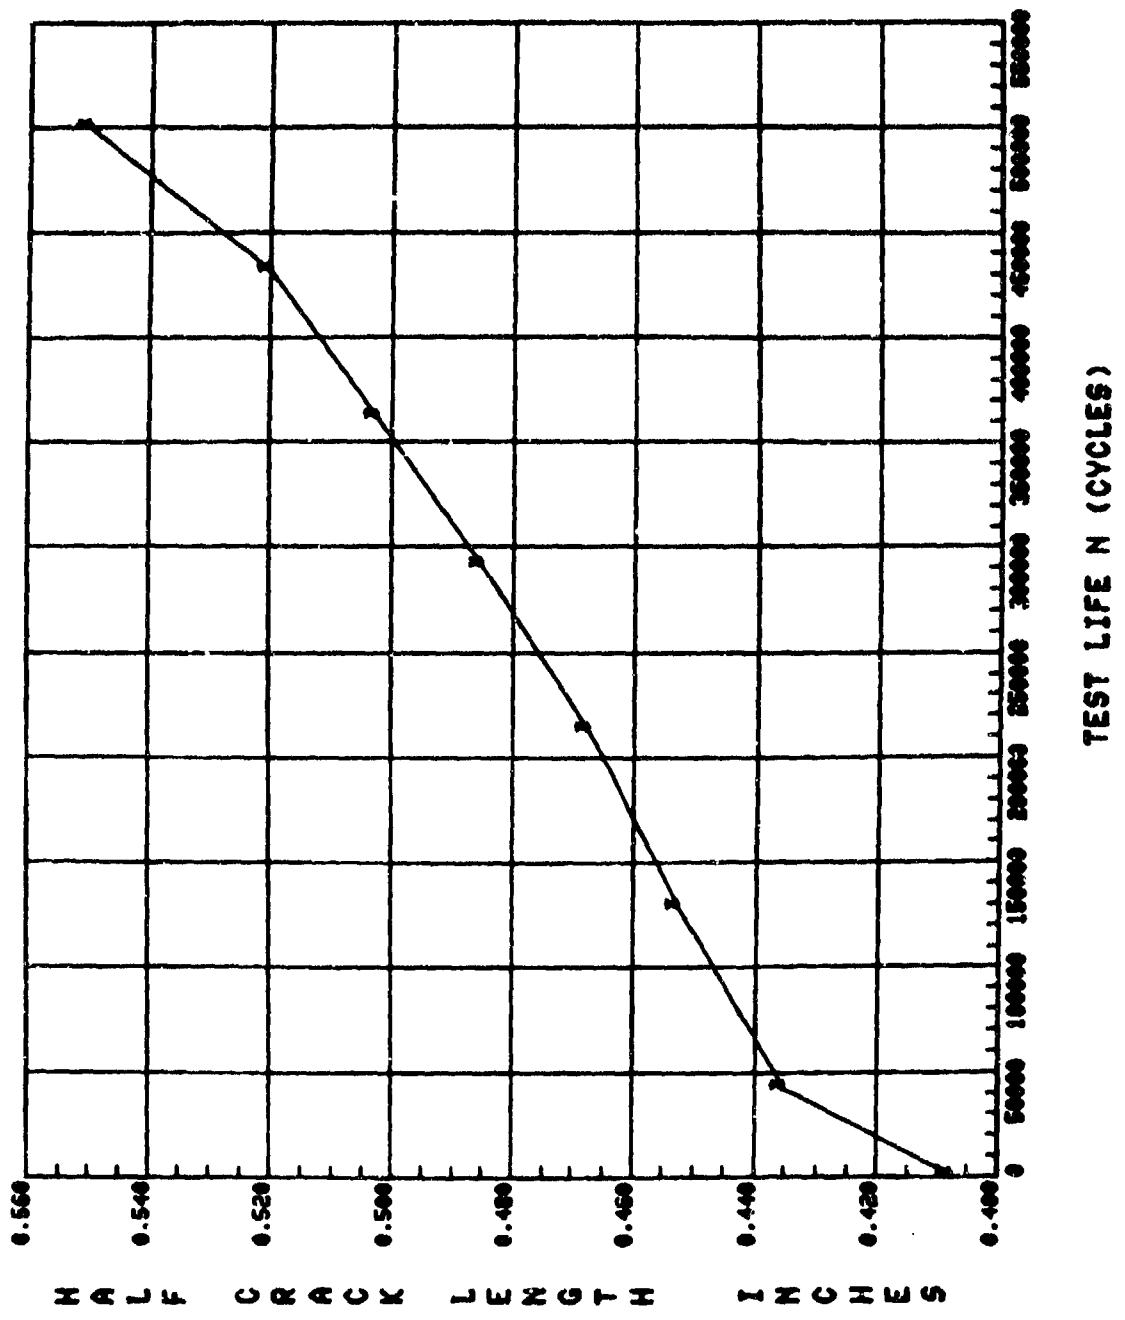


Figure 98. Crack growth curve for test M-79.

TABLE 98. DATA TABULATION FOR TEST M-80

SPECIMEN NO.: M-80		SIMPLIFIED SPECTRUM. TYP. TRANSPORT. MAX STRESS = 16.8 KSI		
CCT	SPECIMEN	B = 0.250 IN.	b = 6.000 IN.	A _N = 0.0 IN.
P _{MIN}	P _{MAX}	TEST FREQ = 6.00 Hz.		
ENVIRONMENT CONDITIONS: AMBIENT AIR				
NO.	CYCLES	AS MEASURED)	(REGRESSION)	MULT. CORR. COEFF
1	0.	0.500	0.500	0.996806
2	40000.	0.510	0.514	0.977437
3	71000.	0.520	0.527	0.986788
4	112000.	0.550	0.543	0.990907
5	194600.	0.575	0.575	0.992579
6	294000.	0.605	0.608	0.987650
7	342000.	0.620	0.622	0.995796
8	395000.	0.640	0.644	0.991012
9	416000.	0.655	0.653	0.995051
10	462000.	0.680	0.684	0.994376
11	476000.	0.700	0.695	0.991942
12	500000.	0.715	0.715	0.986881
				14.95
				15.16
				15.36
				15.60
				16.05
				16.51
				16.71
				17.02
				17.14
				17.55
				17.70
				17.96
				17.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15
				27.66
				27.86
				28.52
				28.76
				29.18
				24.30
				24.63
				24.96
				25.35
				26.08
				26.83
				27.15

M-80 PLOTRATE CRACK GROWTH DATA
 SIMPLIFIED SPECTRUM, TYP TRANSPORT, MAX STRESS = 16.8 KSI

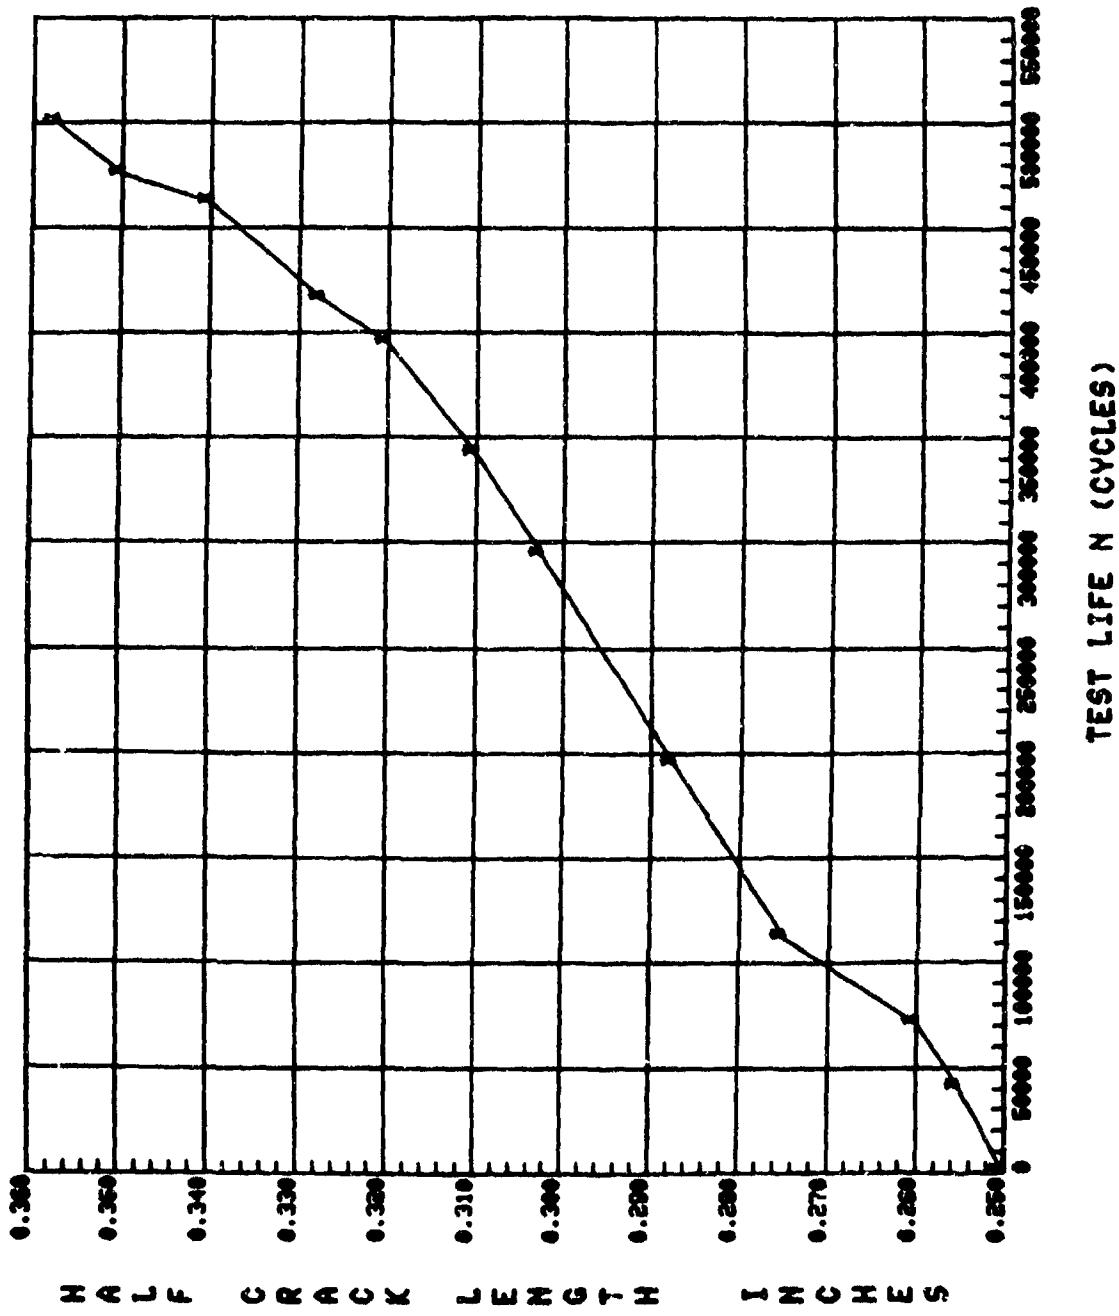


Figure 99. Crack growth curve for test M-80.

TABLE 99. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, AIR-TO-AIR MISSION, A TYPICAL FIGHTER

Test M-81 $\sigma_{lim} = 20$ ksi, M-82 $\sigma_{lim} = 30$ ksi, M-83 $\sigma_{lim} = 40$ ksi

HEADIN T=00000 IS UN LIU 04

HEADIN	C....	MATERIAL	A-A	($\tau=1500$)								
0001	-5.00*	10.0	16.1	54.1	20.1	45.5	25.0	52.3	36.0	50.7		
0002	28.4	44.5	14.6	48.6	24.5	41.9	8.6	29.4	17.6	52.4		
0003	17.5	24.5	10.2	74.9	16.8	50.6	52.5	53.7	17.3	65.7		
0004	50.0	63.5	3.1	67.5	10.4	60.6	44.0	54.9	16.2	45.1		
0005	14.7	34.0	20.4	58.4	31.2	45.6	27.9	63.5	9.4	69.7		
0006	34.1	58.2	-5.0	19.4	27.0	42.4	27.9	41.0	9.4	33.5		
0007	16.0	40.2	5.2	39.1	19.5	51.9	9.3	31.4	19.1	46.6		
0008	0.4	27.6	16.9	56.2	11.0	28.7	9.3	33.2	1.8	13.2		
0009	1.4	50.2	18.6	31.8	19.1	46.6	34.0	63.7	29.9	86.8		
0010	22.5	42.7	12.2	40.8	22.0	41.9	21.2	42.2	16.3	26.6		
0011	-3.0	27.3	11.9	45.3	-5.0	46.8	14.7	40.6	23.6	57.2		
0012	30.4	58.3	32.7	48.1	27.1	41.5	29.7	61.1	29.3	60.7		
0013	19.8	43.5	28.5	74.9	19.2	46.5	22.4	38.3	5.1	52.6		
0014	34.0	45.0	14.7	46.4	3.0	34.8	19.8	48.7	33.4	54.2		
0015	25.4	38.7	18.3	36.0	18.5	63.7	17.7	50.1	11.7	29.3		
0016	-7.5	41.4	15.3	33.8	9.7	36.1	-5.0	61.7	16.3	50.9		
0017	30.1	47.9	25.4	52.1	24.9	65.2	-10.3	50.7	12.6	44.6		
0018	32.1	47.0	24.3	36.4	19.6	46.2	23.4	42.3	3.5	52.9		
0019	35.8	64.4	16.9	30.6	19.1	47.2	6.4	74.1	12.2	50.2		
0020	28.8	45.6	12.7	46.2	15.3	39.2	20.2	46.4	36.3	58.6		
0021	5.0	60.0	11.9	44.6	29.5	41.3	11.5	40.4	-5.0	47.4		
0022	0.9	44.3	32.4	58.2	19.3	55.1	-4.6	83.3	0.6	37.5		
0023	24.1	57.1	16.2	34.8	22.2	65.7	24.8	47.5	13.4	55.9		
0024	42.5	64.5	24.9	38.5	-22.0	61.8	36.2	66.4	39.4	60.9		
0025	35.4	50.8	25.5	51.2	34.5	54.9	26.8	39.5	-3.7	61.0		
0026	-1.8	47.0	12.5	59.6	8.3	55.9	7.7	45.3	29.7	66.4		
0027	-5.0	49.2	5.5	33.5	15.0	36.1	2.7	58.5	2.0	40.9		
0028	13.0	58.1	15.2	51.7	4.0	33.3	9.4	29.3	11.6	68.5		
0029	14.0	45.4	30.9	45.9	13.5	48.1	21.1	57.3	13.9	35.2		
0030	18.7	37.3	19.3	40.6	1.1	25.6	8.3	67.1	32.8	71.0		
0031	21.5	51.4	12.5	42.8	11.3	41.4	22.8	47.5	17.9	48.9		
0032	17.5	55.1	-5.0	41.4	12.2	79.3	15.1	50.4	28.7	45.8		
0033	34.3	59.1	28.3	45.5	29.1	52.9	12.0	45.1	30.9	48.0		
0034	4.2	66.6	47.6	61.6	15.0	31.1	14.3	50.6	7.7	53.2		
0035	34.1	68.1	6.8	20.5	6.2	56.5	9.3	75.7	12.6	52.7		
0036	51.3	55.7	17.4	57.7	22.3	61.7	29.0	51.7	39.8	59.5		
0037	12.2	42.6	8.1	25.8	-5.0	60.0	13.5	56.0	14.8	63.7		
0038	21.6	52.6	20.3	43.4	9.7	48.1	33.5	45.2	-7.3	67.1		
0039	0.4	77.4	45.4	58.8	10.3	71.8	10.6	38.2	23.3	46.2		
0040	-4.8	40.3	4.9	41.1	17.9	42.7	5.1	41.8	27.2	58.7		
0041	24.8	42.4	13.3	46.0	1.2	26.5	-4.5	51.3	5.4	26.6		
0042	15.4	50.5	8.6	39.0	5.1	60.3	-5.0	42.2	13.0	34.4		
0043	15.8	55.6	12.7	40.8	23.6	49.4	36.7	53.9	25.7	41.0		
0044	16.2	53.3	22.5	46.5	3.0	44.7	6.4	39.8	22.5	64.3		
0045	24.5	57.0	26.3	53.4	9.8	33.3	0.9	46.4	0.3	68.9		
0046	24.5	47.4	22.3	47.2	6.3	77.4	25.9	74.7	18.7	64.1		
0047	22.7	58.6	4.7	72.1	7.6	72.3	17.5	53.0	-5.0	59.3		
0048	15.0	42.4	27.6	41.0	17.3	70.0	12.9	47.9	25.4	66.3		
0049	50.3	89.4	-0.2	69.5	47.1	60.2	13.1	66.1	11.6	71.4		
0050	18.7	53.3	18.2	35.5	10.7	42.3	5.6	61.0	23.5	49.3		
0051	19.1	51.0	1.3	45.7	15.9	32.5	20.9	43.4	20.4	47.3		
0052	22.5	46.1	21.0	52.4	36.4	61.3	8.7	57.5	38.5	54.9		
0053	-5.0	39.9	28.4	50.2	8.9	31.0	13.8	55.9	42.8	75.9		
0054	10.6	50.3	34.6	46.2	11.4	66.4	11.7	55.5	-6.0	50.9		
0055	37.6	51.0	22.5	37.5	14.6	24.7	1.2	33.1	6.7	26.8		
0056	1.5	42.0	0.5	41.0	11.2	47.8	19.5	37.6	9.6	49.7		
0057	-0.4	40.1	29.0	44.2	23.4	60.8	14.2	40.4	23.3	45.3		
0058	24.3	56.4	-5.0	67.6	22.8	60.6	32.9	52.2	29.9	56.5		

* % of σ_{lim}

TABLE 99. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, AIR-TO-AIR MISSION, A TYPICAL FIGHTER (CONT)

Test M-81 $\sigma_{lim} = 20$ ksi, M-82 $\sigma_{lim} = 30$ ksi, M-83 $\sigma_{lim} = 40$ ksi

0060	24.3	58.5	25.0	55.4	38.0	60.4	23.8	68.7	24.0	61.6
0061	18.6	65.3	21.5	49.1	6.0	50.4	1.0	54.5	17.4	29.3
0062	6.0	42.3	31.0	49.6	34.0	48.4	25.7	46.8	16.8	41.3
0063	-0.7	61.2	6.6	42.7	5.1	44.4	16.0	59.0	-0.7	64.7
0064	21.5	55.4	17.6	36.6	-5.0	36.9	7.5	55.0	29.6	51.4
0065	2.2	72.7	1.3	32.2	-3.8	70.1	8.8	73.8	21.9	49.6
0066	38.6	54.0	41.3	56.3	27.5	38.1	25.3	49.5	9.6	60.9
0067	13.9	53.4	14.9	36.7	15.9	41.0	15.3	38.3	19.8	58.7
0068	28.7	46.8	19.0	55.2	0.9	49.2	5.9	49.6	19.9	59.6
0069	-0.1	21.5	-8.9	27.4	12.2	51.4	-5.0	59.9	16.8	78.8
0070	-2.5	40.2	3.7	80.9	7.5	62.3	31.2	60.0	37.3	54.7
0071	48.2	42.3	30.5	57.2	13.4	26.6	9.6	29.9	12.5	25.8
0072	-0.7	55.7	-4.2	37.7	16.1	56.9	36.3	56.8	27.5	41.8
0073	-0.6	47.0	23.3	62.3	10.0	50.8	30.6	50.0	15.0	37.6
0074	20.2	37.0	21.7	53.2	37.1	65.4	18.7	57.7	-5.0	37.8
0075	26.6	42.7	1.6	40.1	13.4	62.1	4.4	52.7	2.6	68.3
0076	6.2	34.7	-0.9	38.9	24.2	59.2	2.4	47.6	12.3	36.2
0077	9.1	52.4	2.4	16.6	-5.1	56.3	35.8	53.2	1.7	52.1
0078	35.6	70.2	28.3	40.0	25.2	49.2	20.9	35.2	17.6	37.4
0079	26.4	53.7	20.7	34.3	8.1	45.5	34.6	46.7	23.9	88.7
0080	-5.0	82.4	21.1	54.4	30.2	60.1	5.0	35.7	14.5	60.4
0081	43.2	48.4	19.9	44.7	5.5	68.3	42.8	54.4	24.5	48.8
0082	23.6	42.7	5.8	43.6	26.00	74.2	12.6	34.2	23.3	37.5
0083	24.9	36.9	26.5	55.5	22.5	66.8	52.5	65.0	23.9	56.2
0084	12.7	61.0	27.4	53.4	13.3	37.9	20.5	33.2	22.3	40.3
0085	25.7	62.8	-5.0	53.4	21.5	67.9	24.8	48.5	6.9	31.1
0086	18.1	41.4	14.8	27.1	10.4	61.2	8.5	53.4	3.1	27.7
0087	15.0	44.5	14.9	66.4	35.8	59.1	30.2	71.3	24.0	76.1
0088	28.3	52.1	14.8	64.1	40.5	73.0	8.4	56.3	22.4	37.6
0089	17.2	60.1	6.2	36.5	16.9	57.2	10.1	42.2	21.2	67.9
0090	5.3	63.4	34.3	47.4	-5.0	52.9	21.4	57.5	17.5	38.7
0091	10.0	56.2	26.1	45.5	27.9	60.4	25.5	41.8	19.7	56.5
0092	24.4	37.0	24.6	47.5	17.2	92.5	5.3	44.1	5.4	20.5
0093	-0.3	37.7	26.0	39.8	3.3	23.9	3.2	42.6	-1.9	57.6
0094	42.5	62.9	19.4	74.2	13.4	46.8	23.2	52.5	26.4	37.2
0095	4.1	35.9	22.0	69.2	32.4	54.8	-5.0	54.0	14.5	53.6
0096	12.8	38.9	21.4	53.7	28.6	49.5	39.2	60.8	20.1	52.9
0097	6.7	61.4	21.5	43.1	19.7	31.6	4.8	24.1	11.9	47.8
0098	14.6	34.3	10.4	55.8	10.2	21.6	9.0	41.6	12.7	51.6
0099	10.1	36.5	16.7	54.3	35.0	73.8	34.4	71.1	38.3	52.0
0100	20.4	58.5	28.7	48.7	24.9	44.6	28.0	48.0	-5.0	62.3
0101	45.4	74.7	33.8	46.3	21.4	53.4	8.9	45.9	-3.5	48.8
0102	15.6	58.4	32.2	48.8	9.0	48.7	15.3	26.4	3.0	57.5
0103	15.4	51.7	15.3	41.5	7.4	27.7	14.7	71.6	6.4	24.7
0104	3.0	54.2	-0.8	46.7	11.5	34.2	-2.9	32.1	-0.3	47.4
0105	3.1	31.1	9.6	55.2	5.7	50.7	27.8	38.6	9.6	63.1
0106	-5.0	44.0	31.0	61.7	43.5	65.7	6.3	47.8	23.1	71.9
0107	10.0	76.6	22.7	58.0	5.2	31.1	17.5	70.8	35.3	61.6
0108	26.8	56.5	7.2	54.9	17.4	30.1	9.2	19.9	5.9	17.9
0109	6.2	65.2	-1.4	76.0	5.9	55.4	13.8	63.4	37.4	59.9
0110	33.4	45.6	23.8	50.1	21.7	54.7	12.2	46.3	32.0	44.1
0111	6.6	70.8	-5.0	48.4	23.4	45.7	20.3	52.5	6.2	35.3
0112	20.3	61.4	8.1	47.5	20.7	41.5	16.8	34.2	6.3	64.1
0113	25.8	47.9	30.3	59.6	20.5	64.6	38.3	55.0	27.8	43.2
0114	26.0	62.8	17.1	40.1	17.0	30.6	12.8	65.8	9.5	59.6
0115	34.4	67.6	-4.2	60.6	0.9	63.5	12.8	37.9	7.7	69.5
0116	10.7	42.4	25.9	42.3	-5.0	54.1	24.7	66.4	23.2	49.9
0117	12.4	34.5	23.5	50.5	25.5	44.1	22.4	45.7	26.1	74.2
0118	39.4	61.1	28.2	45.7	18.3	53.7	20.6	54.1	32.1	67.6
0119	23.4	62.3	28.4	80.2	19.1	48.7	29.4	55.4	19.7	79.2
0120	11.2	43.8	21.7	48.2	20.9	71.9	33.9	63.3	34.9	52.7
0121	24.8	60.6	10.7	65.8	17.5	64.4	-5.0	41.7	11.5	34.0
0122	-22.0	26.3	11.0	30.1	19.0	40.1	49.5	47.3	2.7	60.1
0123	26.0	59.6	28.2	64.4	21.4	52.8	34.7	45.6	27.3	51.8

TABLE 99. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, AIR-TO-AIR MISSION, A TYPICAL FIGHTER (CONT)

Test M-81 σ_{lim} = 20 ksi, M-82 σ_{lim} = 30 ksi, M-83 σ_{lim} = 40 ksi

0124	30.2	57.5	23.3	62.3	3.2	46.9	11.1	55.2	16.7	35.3
0125	7.1	45.4	15.4	46.9	22.0	50.0	24.0	36.6	13.8	52.0
0126	4.1	17.7	-4.2	36.9	6.0	36.1	5.3	59.4	-5.0	67.1
0127	19.0	48.0	14.8	78.5	21.8	45.9	21.9	45.8	9.5	67.8
0128	17.8	37.8	18.5	85.2	24.5	35.3	20.3	56.2	31.6	62.8
0129	8.7	50.2	10.5	65.9	20.0	42.2	5.2	34.2	11.9	52.6
0130	21.4	64.7	-0.1	10.4	-3.7	62.3	6.6	44.1	9.8	41.6
0131	24.3	39.6	19.4	31.1	15.6	32.8	-0.2	48.3	15.5	45.0
0132	-5.0	41.0	16.2	45.2	34.1	58.6	26.5	48.3	10.5	59.9
0133	9.8	61.8	5.4	53.0	26.9	44.4	2.1	57.4	26.3	49.5
0134	18.3	56.5	-2.9	49.3	36.9	68.0	49.3	74.5	34.2	44.8
0135	21.6	54.1	12.5	52.3	12.8	46.1	29.1	71.4	34.0	69.0
0136	30.4	42.4	14.7	39.9	6.6	27.4	11.9	77.7	27.1	53.9
0137	16.3	70.1	-5.0	67.1	43.0	63.1	7.7	27.8	8.7	46.0
0138	8.8	54.7	25.8	53.5	22.6	48.9	33.4	47.8	35.2	74.6
0139	43.2	53.3	21.5	69.1	21.7	83.9	10.9	43.6	18.9	34.3
0140	7.6	45.9	32.7	54.3	9.3	50.3	2.6	35.7	16.2	43.8
0141	29.4	52.5	13.8	58.6	16.2	63.3	29.5	49.1	9.2	38.3
0142	16.4	57.4	-0.1	65.3	-5.0	65.0	32.1	53.7	27.4	45.1
0143	33.1	65.3	15.4	31.0	5.3	22.3	7.6	45.0	-3.7	25.6
0144	2.1	68.4	7.4	63.3	10.5	22.3	2.6	58.8	13.3	45.6
0145	8.0	56.9	7.5	38.5	-1.1	41.8	12.6	61.7	3.3	36.2
0146	25.1	51.8	20.6	58.3	42.7	63.7	25.9	49.2	11.7	46.3
0147	28.4	54.7	23.2	46.2	14.7	46.7	-5.0	18.7	-10.0	48.0
0148	-5.8	39.7	-2.7	64.8	1.0	41.2	29.8	49.8	20.4	39.5
0149	9.1	40.2	4.5	51.5	20.8	54.8	22.4	59.8	2.3	25.2
0150	5.6	24.8	13.5	38.4	28.2	43.7	12.3	29.3	12.3	63.5
0151	30.4	45.0	22.7	75.1	30.8	49.9	23.8	43.8	2.1	70.7
0152	3.5	36.2	10.4	48.9	25.1	41.5	28.6	44.1	-5.0	66.4
0153	21.8	49.5	28.1	56.1	6.9	44.9	20.3	65.4	44.0	71.0
0154	11.6	51.9	6.3	58.1	22.0	41.8	24.6	53.5	14.2	63.4
0155	11.1	41.1	13.7	32.6	11.4	75.6	2.5	64.5	10.0	43.3
0156	28.8	57.7	-4.2	73.5	12.7	41.9	18.6	46.0	24.6	36.9
0157	14.6	41.7	30.7	67.3	28.5	71.2	15.4	49.9	21.4	59.2
0158	-5.0	47.9	22.9	66.1	15.4	47.0	31.7	43.6	20.8	34.2
0159	8.5	20.4	0.0	42.3	-14.3	48.6	21.2	43.3	7.2	80.1
0160	27.6	55.3	32.2	66.5	2.1	43.4	9.2	62.8	22.8	51.9
0161	0.4	43.6	19.7	56.8	8.7	20.8	3.0	45.7	13.3	36.2
0162	15.9	41.4	9.1	47.9	18.6	29.4	12.8	66.6	7.5	45.6
0163	29.6	61.3	-5.0	46.3	19.5	35.3	11.4	55.4	2.4	22.3
0164	7.2	48.1	35.6	50.1	23.3	49.8	19.3	42.2	25.2	57.0
0165	43.11	58.5	15.9	52.5	29.0	58.1	23.5	40.2	23.0	70.8
0166	27.9	52.1	14.5	44.6	16.6	44.7	28.1	66.9	10.2	43.4
0167	21.1	41.8	2.0	62.5	9.6	36.1	3.5	60.9	21.4	46.7
0168	33.7	47.5	14.4	54.5	-5.0	60.0	16.4	32.1	17.3	60.2
0169	8.8	26.9	9.9	55.7	13.5	65.1	41.6	53.3	20.7	39.4
0170	24.2	40.6	8.6	63.2	23.0	45.3	22.3	36.1	21.0	65.7
0171	27.6	40.2	22.5	43.0	31.8	77.5	-0.2	74.3	24.8	53.4
0172	28.1	45.1	31.2	67.5	21.2	35.4	4.1	25.5	14.0	36.3
0173	10.3	56.6	7.7	31.4	7.3	47.6	-5.0	15.1	1.1	36.7
0174	7.4	49.4	16.9	45.9	10.4	22.4	10.6	23.1	6.4	20.8
0175	6.4	50.6	1.5	34.4	-6.0	58.3	3.1	43.3	26.1	38.2
0176	21.9	42.9	27.1	48.3	11.2	34.4	21.0	69.4	14.2	79.2
0177	-10.1	67.3	11.1	44.8	8.9	51.4	18.2	52.6	15.8	61.3
0178	30.8	40.6	19.3	56.3	19.2	49.6	22.6	48.5	-5.0	51.8
0179	11.8	50.0	14.9	43.0	31.9	43.1	23.1	39.9	8.1	53.9
0180	5.4	55.0	21.7	49.9	18.2	46.0	6.7	47.9	27.4	43.8
0181	11.1	46.1	34.6	77.4	-8.6	64.6	4.6	70.9	19.1	48.6

TABLE 99. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, AIR-TO-AIR MISSION, A TYPICAL FIGHTER (CONT)

Test M-81 σ_{lim} = 20 ksi, M-82 σ_{lim} = 30 ksi, M-83 σ_{lim} = 40 ksi

0182	32.0	55.4	41.5	64.2	32.6	54.4	10.5	34.1	3.0	37.7
0183	27.3	58.1	44.3	50.3	29.5	45.4	4.1	42.8	19.6	57.9
0184	-5.0	50.8	37.0	47.6	3.3	57.6	28.1	44.6	36.7	51.1
0185	0.0	49.8	32.6	64.5	11.3	50.7	10.6	23.4	11.1	56.2
0186	38.8	54.4	14.5	27.6	7.9	30.8	20.4	45.0	14.3	54.4
0187	18.2	34.0	8.0	56.3	15.7	48.5	14.5	56.7	44.3	62.6
0188	13.3	49.0	22.7	42.1	16.1	38.2	8.0	49.6	7.1	24.9
0189	6.5	45.2	-5.0	67.7	15.7	37.8	9.3	57.4	19.5	61.6
0190	29.1	48.6	17.7	49.8	3.6	66.9	14.6	26.9	-0.5	35.5
0191	13.6	25.7	15.2	60.6	1.1	35.8	14.5	41.0	30.4	46.5
0192	4.8	19.9	7.2	44.2	22.7	33.6	11.6	40.9	4.8	67.1
0193	16.2	74.6	10.0	23.2	1.6	21.3	1.9	73.4	1.6	42.2
0194	30.1	61.0	13.6	34.7	-5.0	50.3	32.4	70.4	20.6	66.0
0195	25.8	56.5	42.0	55.6	10.4	48.5	17.1	37.8	3.4	32.5
0196	4.2	41.9	16.4	46.4	11.8	46.7	20.5	52.1	1.7	52.4
0197	35.4	49.1	24.7	70.4	18.8	64.8	-1.8	44.5	9.3	23.9
0198	12.0	48.2	22.9	37.3	10.8	31.5	16.8	40.2	20.3	48.5
0199	26.7	59.9	21.7	52.3	11.1	35.8	-5.0	49.2	5.4	25.2
0200	12.6	47.9	25.5	41.9	3.4	57.8	28.0	39.6	-0.2	31.0
0201	7.8	37.0	8.3	37.0	13.0	67.2	5.6	45.6	8.9	33.7
0202	4.4	67.4	15.9	46.6	36.1	46.6	18.3	59.3	38.2	64.7
0203	13.5	39.2	16.4	49.9	12.1	54.3	20.9	42.1	17.3	43.1
0204	11.5	51.2	19.2	39.1	12.0	44.9	23.4	34.3	-5.0	61.3
0205	4.0	48.7	8.8	39.1	24.4	42.4	15.5	45.6	21.5	35.9
0206	24.8	38.5	13.4	47.2	20.6	52.2	17.6	53.4	35.2	53.7
0207	19.0	38.5	22.5	67.3	8.2	38.0	25.5	44.1	30.3	42.3
0208	23.4	46.6	35.0	68.8	40.8	52.6	13.5	32.7	12.0	60.7
0209	32.0	49.7	33.7	46.6	27.7	49.5	38.1	55.1	-2.3	44.9
0210	-5.0	41.7	22.2	47.1	33.8	55.4	10.8	49.0	38.4	49.8
0211	4.8	56.9	27.4	53.7	31.9	60.6	8.0	51.0	26.1	61.8
0212	39.7	77.7	34.8	53.2	22.8	34.4	9.2	35.0	20.2	42.3
0213	15.6	41.5	18.8	45.7	34.1	45.0	26.0	47.5	26.0	44.1
0214	34.0	33.2	26.2	37.6	13.5	39.3	23.0	48.7	7.5	33.7
0215	22.6	43.5	-5.0	44.7	16.3	64.5	7.8	55.6	8.2	30.6
0216	20.2	44.8	34.1	54.0	20.7	41.1	26.6	72.3	25.5	55.5
0217	30.0	72.5	7.3	38.1	25.1	39.0	17.6	62.8	8.2	35.2
0218	-4.4	19.3	0.8	53.2	8.3	50.2	5.7	63.9	5.0	49.7
0219	27.7	38.3	-1.0	27.3	2.3	55.9	16.5	59.5	26.0	50.6
0220	4.5	41.5	2.8	39.0	-5.0	52.2	16.0	50.9	35.2	56.7
0221	-2.4	52.7	8.3	26.1	12.8	32.6	15.1	60.6	6.6	62.7
0222	-1.8	43.9	14.7	50.2	33.8	56.7	24.2	56.4	3.3	53.8
0223	41.4	69.1	31.5	41.7	23.0	48.9	38.5	78.3	10.6	37.5
0224	23.0	55.0	31.9	48.0	9.9	35.6	15.7	55.1	35.2	51.4
0225	11.2	45.0	33.1	46.8	23.9	53.5	-5.0	58.2	-3.1	62.8
0226	13.1	72.2	19.8	76.3	36.8	68.3	17.9	68.6	0.7	64.9
0227	35.0	67.2	17.1	35.1	6.8	29.4	12.4	45.8	15.1	43.2
0228	2.7	46.8	9.7	50.0	20.4	46.0	23.2	50.5	15.4	63.0
0229	17.4	30.2	19.6	38.4	26.5	77.5	19.8	52.2	10.0	63.5
0230	6.3	79.2	16.0	29.4	4.1	48.5	31.2	50.6	-5.0	52.4
0231	4.4	40.1	10.5	24.4	13.1	39.5	23.7	53.5	7.6	74.8
0232	16.7	68.6	4.8	49.5	28.1	45.7	25.9	47.0	13.1	54.6
0233	24.4	56.8	27.4	49.7	34.2	65.5	17.2	69.9	-8.2	30.7
0234	11.8	51.1	31.7	48.1	19.2	29.3	18.8	65.6	23.8	68.8
0235	56.2	74.6	38.4	56.8	28.1	54.3	31.5	59.4	45.9	61.3
0236	-5.0	57.0	36.9	71.7	34.1	67.1	43.7	61.0	28.7	47.3
0237	33.4	66.3	30.3	43.7	21.8	47.6	14.4	43.6	-6.8	55.2
0238	2.5	37.8	19.4	46.3	9.8	63.4	-12.7	5.0	-5.2	39.6
0239	12.1	30.3	17.4	53.8	21.6	55.5	17.7	45.1	16.8	54.3
0240	3.8	53.0	12.7	38.0	21.5	50.1	33.6	66.7	17.5	35.4
0241	25.0	44.8	-5.0	40.6	29.8	47.3	11.3	40.7	23.7	60.7
0242	3.4	43.8	19.9	50.6	5.7	51.8	-1.5	55.1	17.0	62.5

TABLE 99. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, AIR-TO-AIR MISSION, A TYPICAL FIGHTER (CONCL)

Test M-81 σ_{lim} = 20 ksi, M-82 σ_{lim} = 30 ksi, M-83 σ_{lim} = 40 ksi

0243	54.2	61.0	40.6	54.5	14.1	60.4	14.2	50.4	19.4	62.3
0244	2.9	74.2	41.4	53.4	11.0	28.1	15.2	26.4	8.2	50.0
0245	7.4	64.3	40.5	14.4	-10.2	43.7	29.5	40.3	13.6	41.3
0246	15.3	47.4	12.3	71.0	-5.0	50.0	24.0	51.6	32.4	44.4
0247	17.2	55.1	13.3	37.0	15.0	34.3	1.3	27.7	7.3	36.7
0248	7.6	41.3	30.3	47.2	26.2	41.0	4.7	61.4	18.3	35.5
0249	23.3	53.4	10.2	43.5	27.0	51.8	16.3	26.9	11.7	69.1
0250	0.6	59.4	-2.9	50.6	-1.1	45.4	34.8	53.7	22.4	40.4
0251	23.4	55.2	44.5	60.2	21.0	70.2	-5.0	56.3	18.4	61.0
0252	26.2	41.1	20.6	58.0	37.0	49.1	13.4	45.5	-0.6	59.0
0253	7.5	64.4	17.6	53.6	34.1	63.7	14.1	51.0	-0.6	39.2
0254	15.4	61.8	16.8	60.2	24.8	52.2	26.5	57.3	9.5	21.4
0255	4.3	55.0	2.9	49.6	16.5	41.8	10.1	47.6	33.7	67.7
0256	4.4	55.3	32.4	47.5	13.9	74.1	25.2	59.0	-5.0	54.6
0257	18.7	52.7	12.7	28.1	17.1	41.8	8.5	44.7	30.1	69.6
0258	0.5	48.1	24.0	40.5	21.4	35.5	15.4	38.2	10.0	57.7
0259	16.6	35.8	23.9	42.0	26.4	52.8	23.8	36.5	-5.6	54.1
0260	14.3	43.4	30.1	49.8	25.4	56.1	18.4	44.6	7.8	51.0
0261	35.9	59.7	37.2	51.7	33.6	47.7	57.0	59.2	32.5	54.9

TABLE 100. DATA TABULATION FOR TEST M-81

SPECIMEN NO.: H-61 RANDOM SPECTRUM, TYPICAL FLYER, AIR-TO-AIR MISSION, LIMIT STRESS = 20 KSI

CCT SPECIMEN b= 0.750 IN. W= 6.000 IN.
 PHIRE PMAX= TEST FREQ = 6.00HZ.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR-CLEFF	K-MAX	DAV/DN	DELTA K
1	0.	0.550	0.321	0.995870	6.41	1.417E-06	1.0.49
2	15099.	0.370	0.358	0.990507	6.89	1.1.09	1.264E-06
3	36500.	0.420	0.424	0.992570	9.68	12.68	1.916E-06
4	50001.	0.470	0.481	0.993155	10.32	12.66	2.481E-06
5	56102.	0.515	0.509	0.998289	10.62	13.25	2.728E-06
6	65750.	0.565	0.568	0.999669	11.23	14.02	3.142E-06
7	74300.	0.630	0.627	0.999416	11.82	14.75	3.501E-06
8	84475.	0.700	0.696	0.994452	12.47	15.26	4.023E-06
9	97640.	0.865	0.810	0.994846	13.49	16.83	5.064E-06
10	105150.	0.870	0.387	0.996126	14.15	17.05	5.934E-06
11	109500.	0.955	0.934	0.995198	14.77	18.19	6.616E-06
12	115700.	1.026	1.026	0.990369	15.26	19.07	7.405E-06

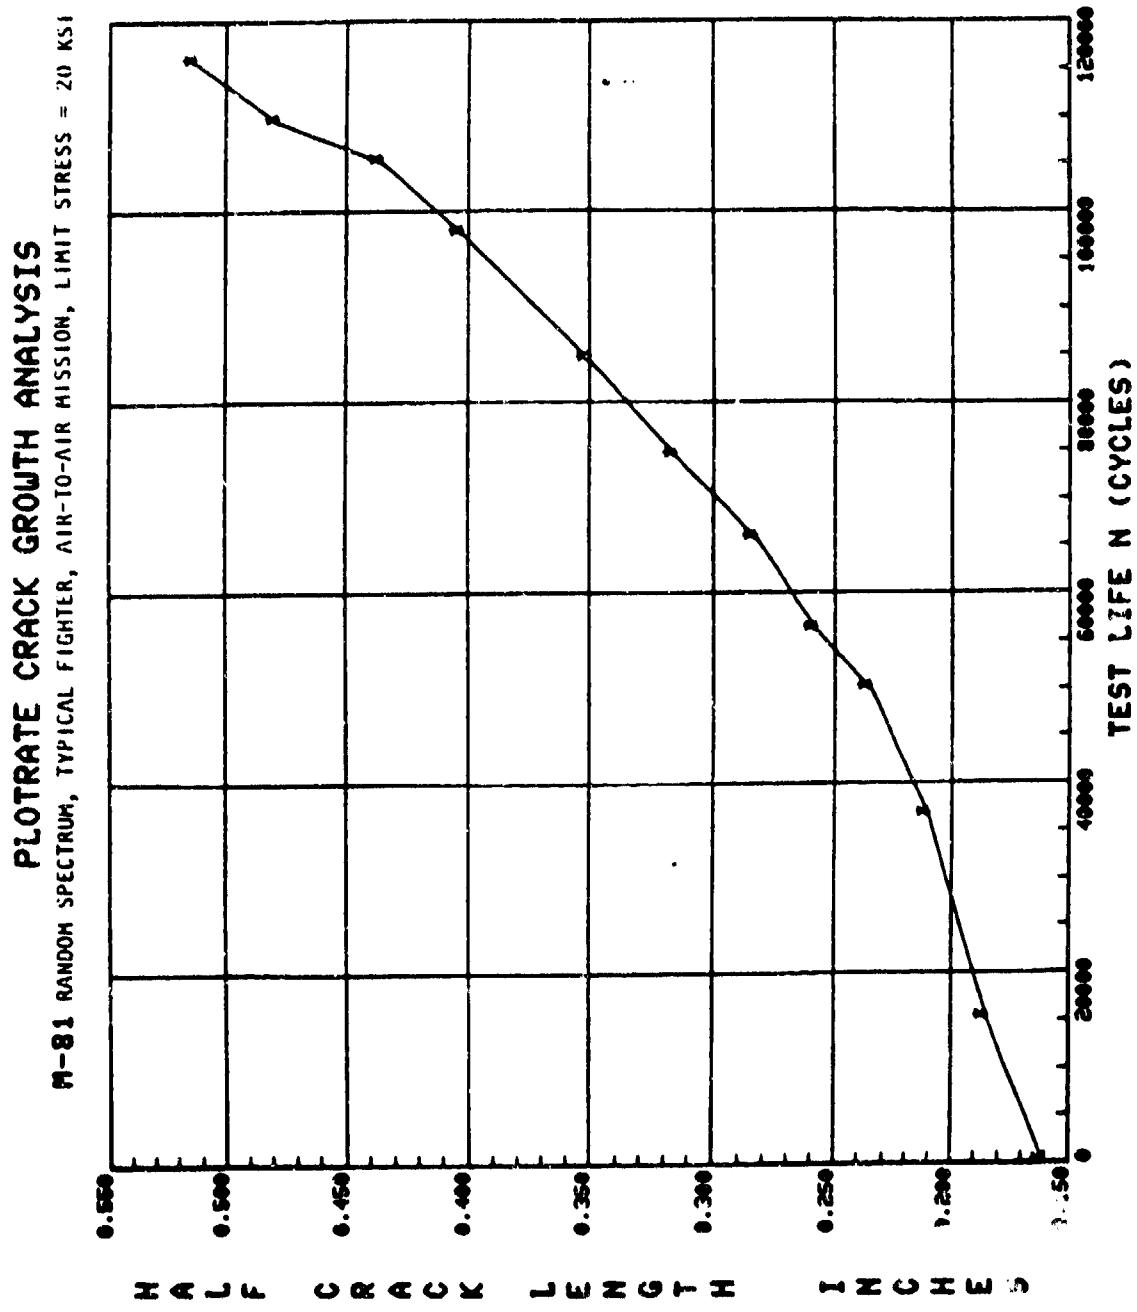


Figure 100. Crack growth curve for test M-81.

TABLE 101. DATA TABULATION FOR TEST M-82

SPECIMEN NO.: M-82 CCT SPECIMEN b = 0.250 IN.
 PMIN= W = 0.000 IN. AN= 0.0 IN.
 PMAX= TEST FREQ = 6.00HZ.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A(MEAS)(D)	A(REGRESSION)	MULT. COVR. COEFF	K-MAX	DELTA K	DAVON
1	6.	0.300	0.300	0.996825	12.20	15.23	4.31E-06
2	2335.	0.327	0.327	0.997643	12.73	15.69	5.615E-06
3	5487.	0.355	0.356	0.991722	13.36	16.59	4.999E-06
4	8463.	0.395	0.385	0.993429	13.83	17.26	5.020E-06
5	17421.	0.405	0.477	0.994547	15.41	19.24	5.925E-06
6	21249.	0.530	0.524	0.995326	16.16	20.17	6.784E-06
7	23312.	0.550	0.550	0.997644	16.57	20.68	7.530E-06
8	26221.	0.595	0.596	0.994926	17.26	21.55	8.942E-06
9	28327.	0.630	0.632	0.956622	13.75	22.20	9.425E-06
10	31542.	0.645	0.700	0.999065	13.75	23.40	1.141E-05
11	34471.	0.720	0.771	0.998933	19.72	24.61	1.321E-05
12	37520.	0.815	0.862	0.994346	20.90	26.09	1.355E-05
13	39957.	0.930	0.930	0.993607	21.75	27.15	1.449E-05
14	41792.	1.000	0.982	0.990469	22.38	27.94	1.564E-05
15	44209.	1.075	1.056	0.987477	23.30	29.08	1.843E-05
16	46012.	1.120	1.121	0.992476	24.05	30.01	2.166E-05
17	47151.	1.175	1.169	0.956462	24.59	30.69	2.453E-05
18	48547.	1.250	1.249	0.999451	25.51	31.83	2.828E-05
19	49706.	1.310	1.315	0.999709	26.25	32.76	3.055E-05
20	50644.	1.375	1.372	0.996C99	26.86	33.55	3.462E-05
21	51584.	1.440	1.436	0.998612	27.59	34.44	3.914E-05
22	52991.	1.545	1.556	0.999217	28.40	36.07	4.755E-05
23	53884.	1.650	1.640	0.956565	24.62	37.21	5.654E-05
24	55038.	1.780	1.782	0.997376	31.35	39.12	6.965E-05
25	55953.	1.845	1.916	0.995233	32.81	46.54	6.573E-05
26	56477.	2.020	2.008	0.994746	33.61	42.20	1.094E-04
27	57005.	2.105	2.125	0.955790	35.10	43.60	1.373E-04
28	57481.	2.250	2.263	0.996291	36.63	45.32	1.675E-04

TABLE 101. DATA TABULATION FOR TEST M-82 (CONCL)

SPECIMEN NO.=		M-82	RANDOM SPECTRUM, TYPICAL FIGHTER, AIR-TO-AIR, LIMIT STRESS = 30 KSI		
CCT	SPECIMEN	B= 0.250 IN.	M= 6.000 IN.	AH= 0.0	IN.
$P_{MIN}= P_{MAX}=$					TEST FREQ= 6.00HZ.
ENVIRONMENT CONDITIONS: AMBIENT AIR					
NO.	CYCLES	A (MEASURED)	A (REGRESSION)	MULT. CURR. COEFF	K-MAX
29	57715.	2.350	2.338	0.998272	37.49
30	57998.	2.460	2.455	0.993116	38.84
31	58194.	2.535	2.543	0.991209	39.88
32	58444.	2.650	2.582	0.992267	41.56
33	58565.	2.790	2.788	0.995264	42.89
					53.53
					4.763E-04

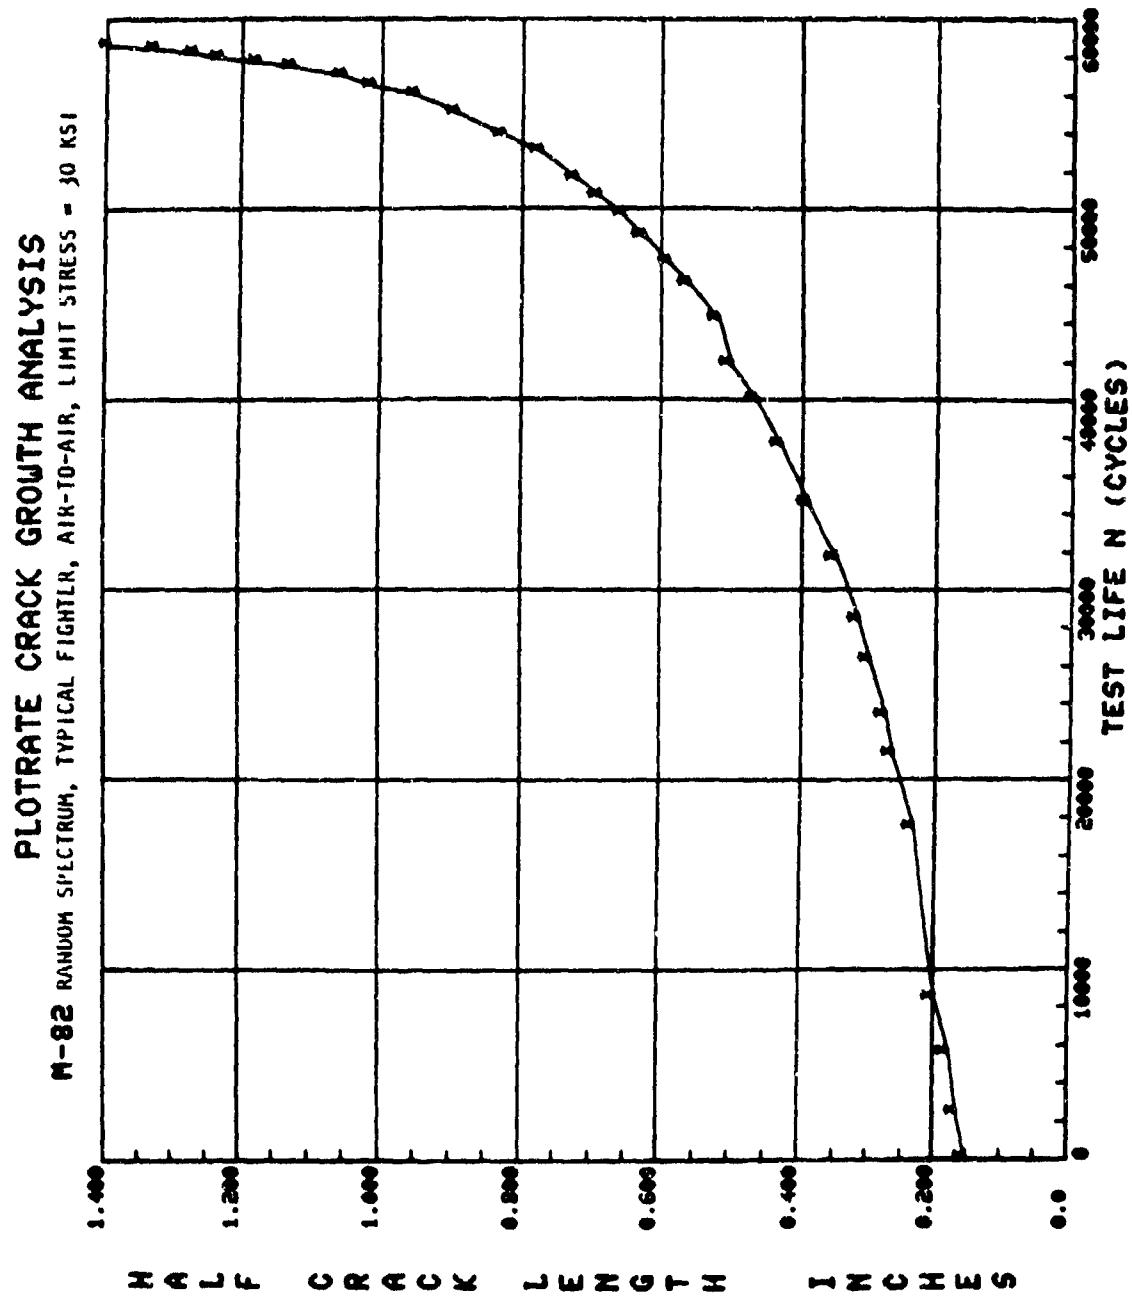


Figure 101. Crack growth curve for test M-82.

TABLE 102. DATA TABULATION FOR TEST M-83
 SPECIMEN NO.: M-83 RANDOM SPECTRUM, TYPICAL FIGHTER, AIR-TO-AIR, LIMIT STRESS = 40 KSI
 CCT SPECIMEN B= 0.750 IN.
 PRIME PPI/XZ
 ENVIRONMENT CONDITIONS: AMBIENT AIR
 NO. CYCLES A(MEASUR'D) A(REGRESSION)
 1 0. 0.300 C-301
 2 411. 0.320 0.315
 3 2167. 0.370 0.365
 4 4183. 0.475 0.425
 5 5270. 0.450 0.453
 6 6919. 0.500 0.492
 7 9399. 0.550 0.562
 8 10265. 0.585 0.591
 9 11129. 0.675 0.627
 10 11935. 0.665 0.674
 11 12075. 0.725 0.720
 12 13428. 0.775 0.774
 13 14096. 0.825 0.829
 14 14738. 0.850 0.884
 15 15250. 0.925 0.945
 16 15764. 1.005 1.012
 17 16202. 1.100 1.073
 18 16693. 1.140 1.157
 19 17148. 1.235 1.249
 20 17446. 1.325 1.317
 21 17689. 1.405 1.390
 22 17807. 1.430 1.420
 23 17983. 1.455 1.459
 24 18434. 1.610 1.651
 25 18569. 1.745 1.772
 26 18612. 1.835 1.831

TEST FREQ= 6.00HZ.

NO.	CYCLES	A(MEASUR'D)	A(REGRESSION)	MULT. COEF.	COEFF	K-MAX	DELTA K	DAWNS
1	0.	0.300	C-301	0.996104	16.28	26.32	1.745E-05	
2	411.	0.320	0.315	0.995903	16.66	20.61	1.701E-05	
3	2167.	0.370	0.365	0.998205	18.01	22.48	1.459E-05	
4	4183.	0.475	0.425	0.996641	19.40	24.21	1.347E-05	
5	5270.	0.450	0.453	0.997672	20.01	24.96	1.315E-05	
6	6919.	0.500	0.492	0.966546	20.86	26.06	1.394E-05	
7	9399.	0.550	0.562	0.949039	22.53	27.87	1.745E-05	
8	10265.	0.585	0.591	0.959405	22.92	26.61	2.166E-05	
9	11129.	0.675	0.627	0.967417	23.63	29.44	2.627E-05	
10	11935.	0.665	0.674	0.997636	24.52	30.61	3.015E-05	
11	12075.	0.725	0.720	0.997556	25.57	31.67	3.445E-05	
12	13428.	0.775	0.774	0.998121	20.34	22.64	3.661E-05	
13	14096.	0.825	0.829	0.997614	27.30	34.08	4.475E-05	
14	14738.	0.850	0.884	0.994215	26.24	35.22	5.592E-05	
15	15250.	0.925	0.945	0.991477	29.26	36.51	6.576E-05	
16	15764.	1.005	1.012	0.942591	30.34	37.66	6.920E-05	
17	16202.	1.100	1.073	0.990365	31.31	39.08	6.064E-05	
18	16693.	1.140	1.157	0.958207	32.62	40.71	9.932E-05	
19	17148.	1.235	1.249	0.996066	34.01	42.45	1.205E-04	
20	17446.	1.325	1.317	0.967937	35.03	43.71	1.316E-04	
21	17689.	1.405	1.390	0.946676	36.11	45.06	1.381E-04	
22	17807.	1.430	1.420	0.975641	35.55	45.62	1.283E-04	
23	17983.	1.455	1.459	0.962452	37.13	46.33	1.741E-04	
24	18434.	1.610	1.651	0.978116	39.91	49.61	3.941E-04	
25	18569.	1.745	1.772	0.964747	41.65	51.98	5.773E-04	
26	18612.	1.835	1.831	0.995449	42.21	53.05	7.752E-04	

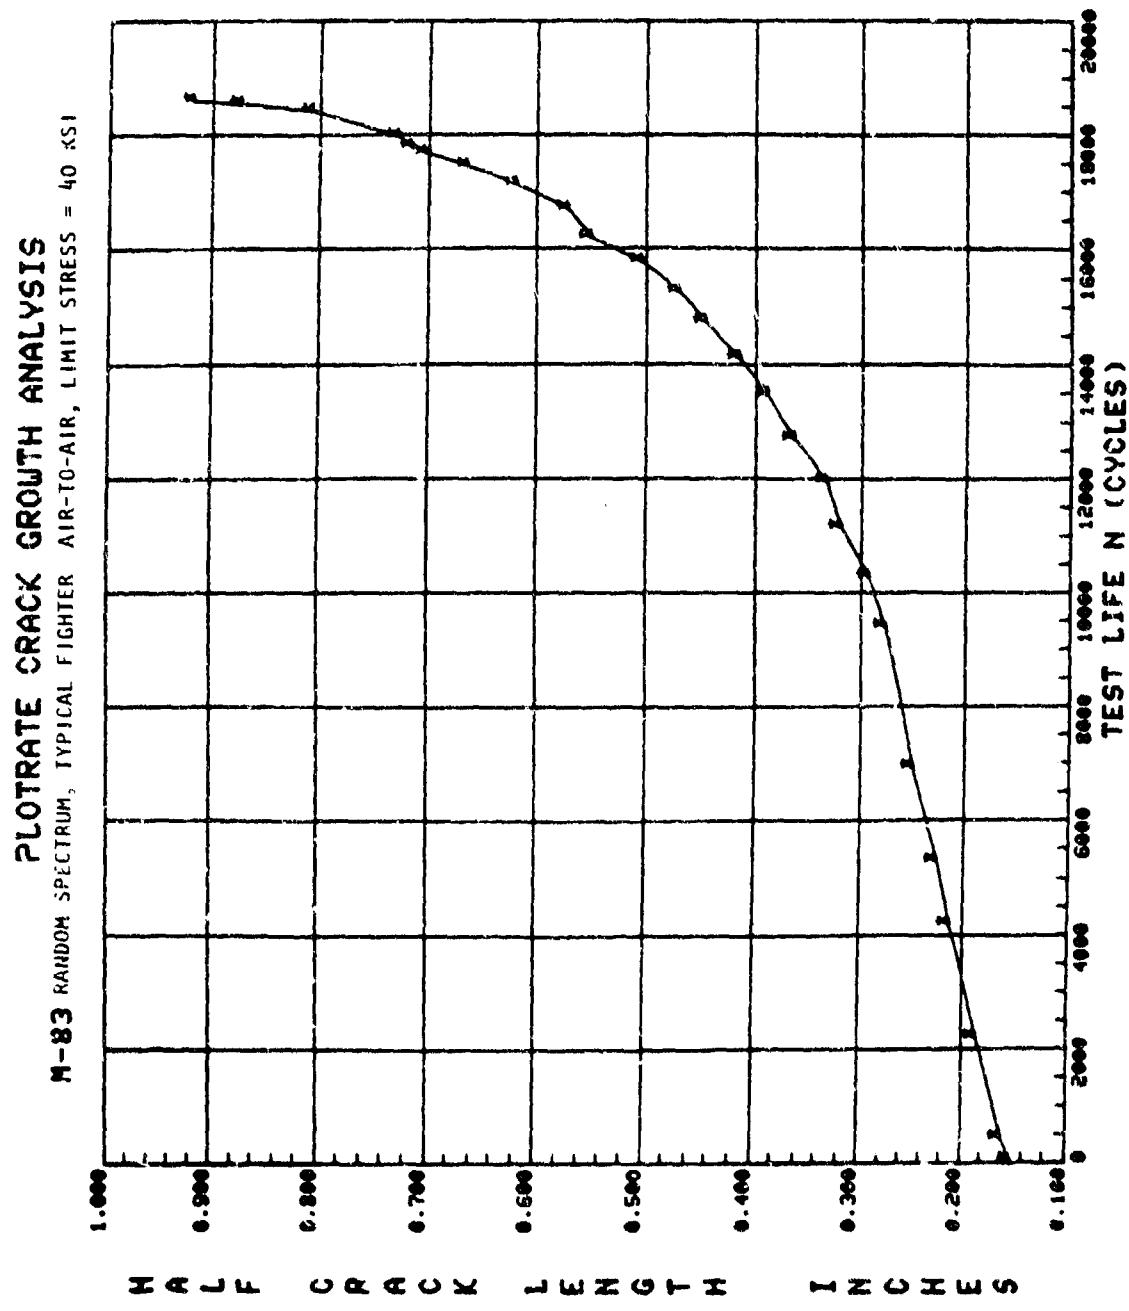


Figure 102. Crack growth curve for test M-83.

TABLE 103. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, AIR-TO-GROUND MISSION, A TYPICAL FIGHTER

Test M-84 $\sigma_{lim} = 30$ ksi, M-85 $\sigma_{lim} = 30$ ksi, M-86 $\sigma_{lim} = 40$ ksi

HEADR 1=00000 IS ON LU 05

0001	C.... HANUUM A-6 (N=450)	0.0	24.6	41.4	4.2	20.1	7.8	48.9	6.3	37.1
0002	-10.0*	70.0	24.6	41.4	4.2	20.1	7.8	48.9	6.3	37.1
0003	11.4	37.8	16.4	28.6	17.8	49.5	13.8	20.9	4.0	42.9
0004	11.4	74.1	20.3	34.5	1.5	21.0	7.8	39.5	11.4	23.8
0005	2.1	71.5	11.3	43.6	6.5	33.1	10.9	56.3	-10.0	51.4
0006	0.4	18.4	7.0	55.9	31.7	48.6	3.0	17.3	6.4	44.1
0007	30.6	42.4	25.3	44.3	2.9	31.2	4.9	28.6	8.6	29.7
0008	18.0	28.4	14.4	44.2	16.4	35.2	8.0	51.8	8.1	23.3
0009	2.8	21.7	8.7	59.5	12.3	47.3	-10.0	67.1	42.2	57.2
0010	14.5	35.4	11.8	27.8	5.5	19.6	3.7	27.7	8.9	31.1
0011	0.6	28.6	9.2	22.6	12.5	41.6	0.5	26.4	10.3	39.3
0012	-0.1	19.5	5.1	26.7	5.7	31.4	4.3	22.3	10.7	24.5
0013	1.6	12.0	0.0	48.2	-10.0	31.1	7.1	23.7	6.6	35.2
0014	12.1	49.2	11.0	78.4	4.4	29.2	5.2	29.5	6.7	30.6
0015	16.1	26.3	11.0	37.8	5.8	17.2	-1.2	23.6	3.2	42.5
0016	22.8	40.3	6.5	33.6	8.5	49.9	21.0	43.2	22.5	45.2
0017	13.1	53.0	-10.0	25.1	8.4	78.6	11.3	42.4	5.5	34.6
0018	10.6	71.7	5.1	35.1	11.2	32.1	1.4	46.3	15.4	37.3
0019	5.4	46.9	0.1	24.1	8.5	40.8	21.2	42.7	9.4	23.3
0020	3.0	28.4	5.1	48.1	26.2	38.5	8.4	40.0	3.8	28.0
0021	-10.0	19.0	7.0	35.6	5.2	31.1	4.0	28.6	-0.0	53.1
0022	7.2	36.8	11.1	55.7	11.3	40.1	9.0	29.8	16.0	51.5
0023	-5.0	25.4	14.3	36.9	6.5	30.1	17.0	38.5	14.5	32.3
0024	6.4	38.1	8.6	35.2	-0.0	37.7	16.1	37.0	-10.0	50.3
0025	8.5	23.8	5.7	37.7	3.0	30.6	10.3	62.8	1.9	36.7
0026	10.6	39.3	3.6	38.0	4.0	32.3	7.2	35.1	19.6	53.2
0027	-0.0	47.4	3.0	58.1	14.6	32.0	7.5	21.2	2.7	29.6
0028	12.2	37.9	0.3	33.8	15.3	45.0	-10.0	32.5	8.6	46.5
0029	-0.4	75.6	-0.3	33.5	10.6	27.1	14.8	48.9	17.0	35.1
0030	2.6	57.0	10.8	38.9	2.2	48.3	26.3	64.1	12.6	34.4
0031	-14.7	53.0	17.1	62.1	27.3	39.1	8.7	38.5	6.6	45.3
0032	23.4	47.8	10.3	33.8	-10.0	70.0	-0.5	35.3	1.7	50.0
0033	3.1	41.4	0.8	25.8	13.9	30.7	15.9	53.5	1.3	38.9
0034	0.2	28.1	10.0	25.0	2.2	58.8	1.6	36.8	4.5	30.2
0035	3.3	48.7	0.3	26.9	2.5	18.9	2.5	58.5	17.3	27.6
0036	4.5	33.0	-10.0	32.8	3.0	35.7	7.5	41.9	27.8	39.7
0037	6.2	19.5	8.2	32.1	11.4	31.7	-0.4	18.6	2.5	60.7
0038	13.5	64.0	5.0	29.6	16.9	41.6	1.8	36.2	3.9	28.9
0039	4.2	34.1	7.4	32.0	14.8	37.9	13.5	26.1	6.0	25.7
0040	-10.0	46.1	22.5	38.5	3.2	33.0	13.9	25.0	15.3	30.9
0041	2.5	69.4	5.2	34.4	17.5	30.2	10.0	36.3	16.1	45.6
0042	11.8	36.6	11.6	35.7	12.0	24.8	5.8	21.0	7.0	54.0
0043	11.6	42.4	1.5	59.3	24.6	47.9	6.2	25.6	-10.0	38.6
0044	3.7	40.9	6.3	47.2	18.9	63.4	1.1	15.5	0.8	48.6
0045	3.6	68.2	0.7	46.1	16.9	43.4	12.6	28.2	3.7	45.9
0046	5.0	49.5	10.8	35.5	16.7	44.8	3.4	34.2	1.0	16.6
0047	5.1	53.6	3.8	45.8	4.6	34.8	-10.0	60.2	8.6	19.7
0048	6.2	33.9	2.9	44.4	19.5	40.1	-1.2	37.2	0.8	40.0
0049	22.3	58.4	23.3	46.6	1.7	54.0	3.0	28.2	11.0	38.3
0050	-1.7	12.3	0.8	33.7	-10.0	30.6	5.0	27.0	0.4	39.0
0051	12.2	45.2	10.1	29.5	2.4	38.9	16.8	31.7	-0.0	18.7
0052	6.5	19.8	-0.0	53.7	0.9	25.0	10.8	28.7	2.2	32.1
0053	0.1	49.5	-4.5	29.5	5.8	21.5	5.2	21.5	5.4	46.0
0054	4.6	28.3	9.3	41.0	19.3	44.9	8.9	33.0	5.9	24.7
0055	12.3	58.7	-10.0	28.5	15.0	35.7	1.2	27.9	8.6	50.4
0056	21.5	31.6	7.7	46.9	14.3	46.1	3.4	32.2	0.3	37.9
0057	-0.8	24.9	14.0	43.8	10.2	37.5	7.9	36.1	0.9	67.2
0058	13.9	51.4	4.0	45.9	15.2	54.6	7.7	54.2	0.5	69.2
0059	-10.0	68.4	2.5	35.4	13.6	42.3	15.1	27.0	6.1	30.1
0060	11.4	53.4	7.0	58.4	7.5	24.5	11.9	54.4	8.4	54.6
0061	25.4	74.1	-0.5	60.3	21.8	44.7	7.6	45.0	2.5	36.1
0062	20.4	60.9	0.0	34.3	19.3	41.3	27.0	57.	-10.0	24.5

* % of σ_{lim}

TABLE 103. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT
SPECTRUM LOADING TEST, AIR-TO-GROUND MISSION, A TYPICAL FIGHTER (CONT)

Test M-84 σ_{lim} = 20 ksi, M-85 σ_{lim} = 30 ksi, M-86 σ_{lim} = 40 ksi

0063	2.0	31.5	0.2	57.5	4.4	41.5	7.9	46.4	5.1	19.0
0064	0.4	37.8	27.0	40.1	6.0	21.4	6.4	28.4	11.2	34.7
0065	4.3	42.2	8.2	40.7	17.5	44.7	0.3	41.1	19.1	49.3
0066	11.4	24.8	12.3	42.9	0.7	23.8	-10.0	45.0	18.3	62.5
0067	2.2	40.2	14.0	34.1	3.2	52.1	4.0	24.4	11.9	46.6
0068	-3.8	34.7	23.2	38.9	9.5	25.3	10.1	25.0	7.4	21.2
0069	-0.1	31.6	0.9	18.4	1.4	36.4	-0.0	32.5	4.9	35.9
0070	7.1	33.5	2.0	39.9	-10.0	28.4	13.1	36.3	10.8	55.1
0071	34.6	49.6	1.9	20.3	7.3	35.7	8.3	50.6	13.3	57.1
0072	8.3	54.5	14.2	36.6	14.2	39.5	21.6	41.5	10.5	46.9
0073	9.5	41.6	19.7	47.7	11.3	54.6	6.1	51.4	10.7	28.5
0074	3.7	57.1	-10.0	30.4	11.7	41.0	8.3	23.2	0.7	24.9
0075	-0.1	49.3	8.4	24.5	0.5	30.6	12.4	33.0	16.2	40.0
0076	14.4	42.4	5.8	31.4	0.1	49.6	2.2	29.4	0.8	44.6
0077	3.7	46.6	0.2	58.4	9.1	44.5	5.4	25.8	10.5	31.7
0078	-10.0	20.5	8.3	44.4	22.2	34.1	16.6	38.9	0.0	78.9
0079	-0.7	25.1	-2.0	63.6	3.5	62.1	15.4	27.9	12.2	31.0
0080	18.7	40.8	20.4	41.0	11.2	28.5	12.7	23.8	12.2	35.6
0081	2.4	49.9	5.3	46.9	5.4	29.2	7.8	35.1	-10.0	26.7
0082	5.0	89.3	15.3	41.5	5.0	46.0	1.6	43.3	0.5	45.7
0083	5.0	47.8	12.0	26.2	-0.4	18.9	-2.3	31.1	10.4	38.6
0084	5.0	47.0	4.0	70.0	-1.7	35.5	0.2	27.0	16.4	70.0
0085	0.0	34.9	18.4	52.3	9.1	49.6	-10.0	40.3	8.4	30.4
0086	12.5	47.7	6.0	27.2	4.3	17.7	4.2	19.6	4.2	22.5
0087	-0.1	51.6	5.3	19.1	-1.0	23.0	6.4	24.1	13.3	50.7
0088	18.3	46.0	11.8	30.9	-1.5	37.6	7.4	50.7	2.9	34.1
0089	21.3	36.1	13.5	35.7	-10.0	28.0	4.4	25.2	14.2	25.3
0090	10.2	45.1	20.0	58.0	15.3	30.9	6.2	53.2	0.5	33.2
0091	12.5	38.3	-0.9	35.1	4.8	62.4	-0.8	26.0	11.3	47.7
0092	24.8	41.6	0.0	60.3	0.6	22.5	-1.8	31.9	14.7	44.9
0093	0.7	37.9	-10.0	24.8	2.3	29.9	5.1	46.6	0.3	14.5
0094	+1.5	16.9	2.0	45.5	20.0	50.8	-0.5	17.8	5.4	39.6
0095	22.4	67.4	9.6	25.2	6.4	36.2	8.0	27.6	9.5	47.3
0096	11.3	27.7	0.4	28.4	18.5	39.5	8.6	75.1	7.4	21.2
0097	-10.0	64.0	8.1	35.0	14.4	52.9	0.8	26.2	4.1	28.0
0098	14.2	53.4	10.1	35.6	4.3	38.1	-0.9	56.0	23.9	45.6
0099	7.1	57.1	8.3	31.2	1.5	22.9	7.9	32.1	10.9	65.9
0100	4.4	24.4	12.5	31.6	14.9	27.7	14.1	41.1	-10.0	50.8
0101	52.4	55.2	7.6	40.4	1.5	54.3	11.0	40.8	20.5	36.5
0102	4.6	35.7	14.7	25.6	7.7	24.0	9.1	33.3	11.2	48.6
0103	18.1	37.1	5.5	49.5	11.9	35.8	0.2	21.1	8.1	31.8
0104	0.0	17.4	6.5	18.4	2.4	33.8	-10.0	52.3	0.7	36.0
0105	0.1	24.6	7.5	17.1	5.1	56.4	21.0	33.7	19.5	39.3
0106	24.1	40.1	8.6	60.3	4.2	68.0	23.7	37.9	18.1	38.4
0107	4.9	21.3	6.7	54.9	21.4	58.2	8.2	23.5	0.9	44.3
0108	11.7	29.6	5.4	26.2	-10.0	54.0	1.8	29.8	5.8	48.9
0109	3.6	30.5	5.8	54.9	0.8	40.7	27.2	38.8	22.9	52.3
0110	13.6	39.8	7.9	32.5	7.4	49.2	6.3	27.7	1.8	49.1
0111	8.9	36.0	16.0	47.7	11.1	30.0	6.0	45.9	15.8	28.9
0112	10.4	28.4	-10.0	35.4	3.0	70.0	25.2	46.6	0.0	19.5
0113	8.3	20.4	12.4	34.8	2.1	18.5	0.2	35.0	12.5	29.8
0114	2.8	26.8	2.8	17.3	9.7	39.5	0.2	44.0	21.5	49.0
0115	9.3	56.5	15.8	30.6	5.4	42.6	9.1	39.2	12.9	32.2
0116	-10.0	25.4	8.4	57.0	14.0	39.9	13.9	45.7	6.0	48.8
0117	0.1	24.7	7.9	35.7	14.4	41.2	21.9	56.4	10.7	40.2
0118	2.7	40.3	34.3	48.0	8.0	26.1	8.8	24.9	3.6	15.8
0119	-5.5	38.4	11.0	28.7	6.7	28.7	1.7	24.9	-10.0	15.1
0120	4.4	35.9	21.0	34.3	5.7	47.2	2.6	25.9	4.9	42.8
0121	21.7	32.0	15.0	64.2	11.4	53.0	15.5	38.1	5.1	50.6
0122	13.2	37.0	10.7	33.0	M.0	53.4	15.2	46.3	22.9	72.0
0123	14.6	35.3	5.6	43.2	3.0	22.0	-10.0	54.2	0.0	12.5
0124	1.1	39.4	11.0	25.7	6.9	27.6	14.5	42.6	12.2	48.5
0125	3.7	44.8	4.1	21.1	0.6	47.3	8.6	21.0	3.0	29.4
0126	2.0	24.0	5.1	65.6	0.7	21.5	0.1	46.8	0.1	37.1
0127	3.4	30.7	1.0	27.1	-10.4	19.6	-0.0	35.4	18.7	37.2
0128	-0.0	25.1	1.4	45.5	2.0	37.2	10.2	27.7	3.4	44.6
0129	32.8	45.9	4.9	35.1	15.4	51.3	23.2	54.1	0.2	40.2

TABLE 103. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, AIR-TO-GROUND MISSION, A TYPICAL FIGHTER (CONCL)

Test M-84 $\sigma_{lim} = 20$ ksi, M-85 $\sigma_{lim} = 30$ ksi, M-86 $\sigma_{lim} = 40$ ksi

0130	8.9	61.9	1.6	57.0	43.9	65.0	6.5	31.6	0.3	26.9
0131	3.8	57.9	-10.0	40.8	30.1	49.7	9.7	40.5	17.4	31.0
0132	0.8	47.4	10.4	24.1	2.1	13.9	1.2	17.1	3.9	52.1
0133	36.8	53.2	-0.2	65.2	13.3	30.8	3.7	39.2	4.3	47.5
0134	15.8	40.3	15.3	33.4	4.2	43.1	6.4	49.6	5.6	33.3
0135	-10.0	31.4	0.2	24.1	13.4	42.0	23.1	66.0	-2.5	13.3
0136	1.4	34.3	11.2	45.2	9.6	40.2	0.9	30.7	10.2	47.7
0137	1.1	40.6	13.2	30.6	6.0	30.2	0.4	67.9	10.4	37.5
0138	14.1	40.3	7.4	29.1	17.6	54.0	21.6	40.2	-10.0	20.1
0139	8.5	55.8	27.1	48.0	2.9	31.0	8.0	22.0	3.6	63.9
0140	6.1	50.7	11.4	60.4	-0.7	46.1	5.7	20.5	0.3	46.6
0141	3.3	25.5	-0.2	70.2	4.0	32.4	19.8	31.5	12.0	34.3
0142	1.3	53.5	19.1	44.1	9.7	55.8	-10.0	40.0	4.6	5.5
0143	8.3	45.3	10.4	35.4	9.3	32.7	6.0	64.3	18.7	47.0
0144	13.4	37.0	8.6	42.4	6.3	45.4	16.5	30.2	15.8	58.0
0145	7.1	49.5	11.5	74.8	8.5	34.8	11.9	48.8	5.2	71.6
0146	20.4	50.1	3.6	28.8	-10.0	44.1	10.1	58.0	11.3	52.7
0147	20.4	33.3	17.6	40.8	11.2	45.2	18.0	31.4	1.8	50.0
0148	6.4	20.3	6.3	48.5	2.9	35.9	4.3	27.5	13.0	23.8
0149	-10.2	20.2	3.0	24.5	12.3	28.0	13.0	29.5	14.1	36.1
0150	0.3	49.4	-10.0	53.1	10.7	50.9	6.4	41.6	15.0	29.9
0151	4.7	47.0	14.6	41.4	21.7	35.9	7.3	52.3	0.7	45.0
0152	2.7	26.0	7.0	29.6	2.5	34.6	6.8	40.4	6.8	36.3
0153	9.0	29.4	4.2	38.4	1.3	16.4	-1.4	15.8	4.4	29.2
0154	-10.0	21.4	2.0	32.3	0.2	50.4	5.9	55.7	7.2	20.8
0155	6.5	40.2	17.1	35.5	9.1	22.5	11.5	77.7	5.5	32.4
0156	10.3	41.3	1.7	59.7	5.2	25.4	5.8	23.3	0.7	76.7
0157	7.5	23.4	6.1	38.6	11.5	63.2	2.2	18.1	-10.0	35.0
0158	1.4	40.8	35.1	63.2	4.2	28.4	-0.1	21.6	1.9	48.6
0159	12.7	56.1	14.4	35.1	-2.3	60.0	10.8	25.4	3.0	39.5
0160	1.3	25.7	12.2	32.4	8.9	19.4	5.4	29.0	0.0	41.3
0161	7.8	24.0	10.4	37.0	-0.0	25.7	-10.0	33.5	18.2	58.0
0162	11.5	32.5	2.3	45.4	16.5	29.8	0.3	48.9	2.1	39.7
0163	6.2	30.4	0.3	44.1	8.7	37.5	17.9	34.5	7.5	47.2
0164	24.7	37.9	-3.1	32.4	14.9	60.1	28.6	68.0	14.3	27.7
0165	7.6	39.5	3.4	53.3	-10.0	31.5	11.9	63.8	15.4	66.5
0166	15.6	34.7	2.5	28.3	1.2	14.0	4.0	67.3	11.1	34.9
0167	4.6	27.3	15.6	64.5	20.4	32.3	6.0	32.6	21.5	55.6
0168	24.5	54.4	0.6	24.2	2.5	20.8	6.8	41.4	2.4	41.7
0169	11.9	44.4	-10.0	24.6	14.3	34.5	17.0	35.1	14.4	62.1
0170	23.5	43.5	6.5	54.4	9.6	71.3	2.3	36.5	9.9	26.7
0171	1.7	50.4	16.4	34.2	1.0	38.0	24.6	37.2	0.0	20.5
0172	7.3	27.4	15.5	35.2	14.5	38.9	3.3	44.8	2.6	51.0
0173	-10.0	37.2	9.5	27.1	3.3	26.1	6.5	26.0	10.6	24.1
0174	13.7	49.1	-0.5	51.4	26.2	53.0	9.9	38.4	6.7	25.3
0175	13.8	59.9	7.4	20.8	0.0	16.7	4.3	35.0	-1.2	23.2
0176	0.4	14.2	3.7	56.0	1.2	52.7	29.8	42.2	-10.0	15.7
0177	0.3	63.3	16.5	30.5	3.2	34.5	1.9	62.0	1.4	24.0
0178	-1.7	34.0	5.7	56.3	33.3	47.5	0.7	25.5	12.3	42.1
0179	4.9	21.3	10.9	42.6	10.5	49.1	26.2	40.4	12.0	39.5
0180	4.4	43.3	12.0	44.5	7.4	33.8	-10.0	36.2	0.5	19.6
0181	-0.9	40.4	-0.6	28.6	3.9	17.0	0.1	52.9	-1.1	29.4
0182	11.1	41.5	4.2	32.6	3.7	30.0	-0.0	43.7	6.6	36.3
0183	5.5	50.0	1.7	17.1	0.3	20.2	4.5	39.3	20.3	34.3
0184	4.4	17.1	3.0	56.4	-10.0	35.3	6.8	73.5	16.2	46.3
0185	7.4	34.0	0.4	64.6	1.6	36.0	2.1	36.5	15.5	35.4
0186	15.5	34.4	6.9	56.3	4.7	39.5	14.6	40.5	0.7	27.8
0187	17.0	56.6	6.7	58.4	21.6	54.5	1.8	43.1	-0.4	43.4
0188	22.6	33.8	-10.0	26.6	4.4	40.2	2.1	56.5	2.2	40.2
0189	3.5	22.5	10.7	21.3	4.6	70.5	26.5	45.3	0.1	22.5
0190	9.2	57.0	7.0	24.0	8.6	45.1	-0.4	69.8	4.7	37.5
0191	6.0	37.7	27.3	40.4	11.5	25.1	6.5	28.1	11.5	57.0

TABLE 104. DATA TABULATION FOR TEST M-84

SPECIMEN NO.: M-R4 RANDOM SPECTRUM TYPICAL FIGHTER, AIR TO GROUND LIMIT STRESS = 20 KSI

$\Delta t = 0.250$ IN. $b = 6.000$ IN. $\Delta t = 0.0$ IN.

$P_{MAX} =$ TEST FREQ = 6.000HZ.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	ALMEASIZED	A(REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K	DA/DN
1	0.	0.315	0.316	0.996543	7.24	8.56	1.062E-06
2	1.9551.	0.365	0.356	0.997048	7.70	9.10	1.139E-06
3	4.4550.	0.415	0.419	0.997485	8.35	9.87	1.472E-06
4	5.9995.	0.465	0.467	0.998215	8.83	10.43	1.709E-06
5	7.4901.	0.520	0.519	0.999055	9.31	11.01	1.975E-06
6	8.8400.	0.580	0.577	0.996636	9.83	11.62	2.388E-06
7	1.52117.	0.640	0.646	0.996494	10.42	12.31	2.645E-06
8	10.7597.	0.670	0.675	0.996235	10.66	12.59	2.851E-06
9	11.3754.	0.725	0.715	0.992219	10.97	12.96	2.915E-06
10	12.8683.	0.810	0.809	0.994200	11.70	13.82	3.126E-06
11	13.6642.	0.870	0.956	0.993259	12.05	14.24	3.280E-06
12	14.4520.	0.855	0.906	0.995361	12.42	14.67	3.447E-06
13	15.3199.	0.565	0.967	0.995216	12.86	15.19	3.712E-06
14	16.0152.	1.025	1.017	0.997689	13.21	15.61	4.150E-06
15	16.7203.	1.080	1.082	0.997807	13.65	16.13	4.838E-06
16	17.4275.	1.145	1.151	0.998027	14.12	16.68	5.276E-06
17	18.1860.	1.235	1.235	0.997481	14.67	17.34	5.811E-06
18	18.5016.	1.285	1.274	0.997388	14.92	17.64	6.156E-06
19	18.9002.	1.320	1.325	0.996138	15.26	18.03	6.704E-06
20	19.2241.	1.380	1.369	0.994310	15.54	18.37	6.669E-06
21	1.96250.	1.425	1.423	0.995847	15.88	18.77	6.852E-06
22	1.99407.	1.480	1.467	0.997359	16.17	19.11	7.375E-06
23	2.04442.	1.525	1.542	0.998145	16.64	19.66	7.718E-06
24	2.10701.	1.625	1.639	0.999154	17.25	20.38	8.227E-06
25	2.16224.	1.740	1.732	0.999488	17.83	21.07	9.000E-06
26	2.23022.	1.860	1.865	0.999652	18.67	22.06	9.911E-06
27	2.28275.	1.970	1.971	0.999161	19.33	22.95	1.070E-05
28	2.33679.	2.057	2.087	0.998590	20.06	23.71	1.180E-05

TABLE 104. DATA TABULATION FOR TEST M-84 (CONCL)

SP E C I M E N N O . : 4-84 RANDOM SPECTRUM, TYPICAL FIGHTER. AIR TO GROUND. LIMIT STRESS = 20 KSI

TEST FREU = 6.0000HZ
P MIN = P MAX = 1N.

ENVIRONMENT CONDITION: AMBIENT AIR

NO.	CYCLES	A(MEASLRED)	A(REGRESSION)	MULT. COEFF	CORK. COEFF	K-MAX	DELTA K	DA/DN
29	241285.	2.2t0	2.277	0.998498	21.29	25.16	1.356E-05	1.545E-05
30	244515.	2.365	2.366	0.9988894	21.88	25.86	1.545E-05	1.545E-05
31	247962.	2.480	2.474	0.999613	22.60	26.71	1.736E-05	1.966E-05
32	251404.	2.555	2.601	0.999340	23.48	27.75	1.966E-05	1.966E-05
33	253917.	2.7t0	2.700	0.999580	24.18	28.58	2.153E-05	2.546E-05
34	256205.	2.8C0	2.800	0.998510	24.91	29.44	2.546E-05	2.854E-05
35	258253.	2.9C5	2.907	0.998712	25.72	30.39	2.854E-05	3.272E-05
36	260624.	3.040	3.049	0.998734	26.83	31.71	4.086E-05	4.086E-05
37	262291.	3.180	3.167	0.992592	27.80	32.85	4.725E-05	5.176E-05
38	263018.	3.215	3.225	0.991925	28.29	33.43	5.597E-05	5.597E-05
39	263963.	3.2t5	3.316	0.991036	29.09	34.37	6.724E-05	6.724E-05
40	264527.	3.3C5	3.371	0.991393	29.59	34.96	7.751E-05	7.751E-05
41	265584.	3.515	3.505	0.993686	30.85	36.46	8.845E-05	8.845E-05
42	266341.	3.5C0	3.612	0.991726	31.93	37.73	1.115E-04	1.367E-04
43	266834.	3.685	3.682	0.997801	32.67	38.61	2.068E-04	2.068E-04
44	267449.	3.750	3.794	0.998322	33.91	40.07	3.038E-04	3.837E-04
45	267791.	3.875	3.872	0.992124	34.82	41.16	5.664E-04	5.664E-04
46	268229.	3.984	3.997	0.976954	36.39	43.00	1.000000	1.000000
47	268561.	4.1C0	4.137	0.986097	38.30	45.26	1.000000	1.000000
48	268701.	4.2C0	4.217	0.994667	39.48	46.66	1.000000	1.000000
49	268908.	4.4C0	4.400	1.000000	42.49	50.21	1.000000	1.000000

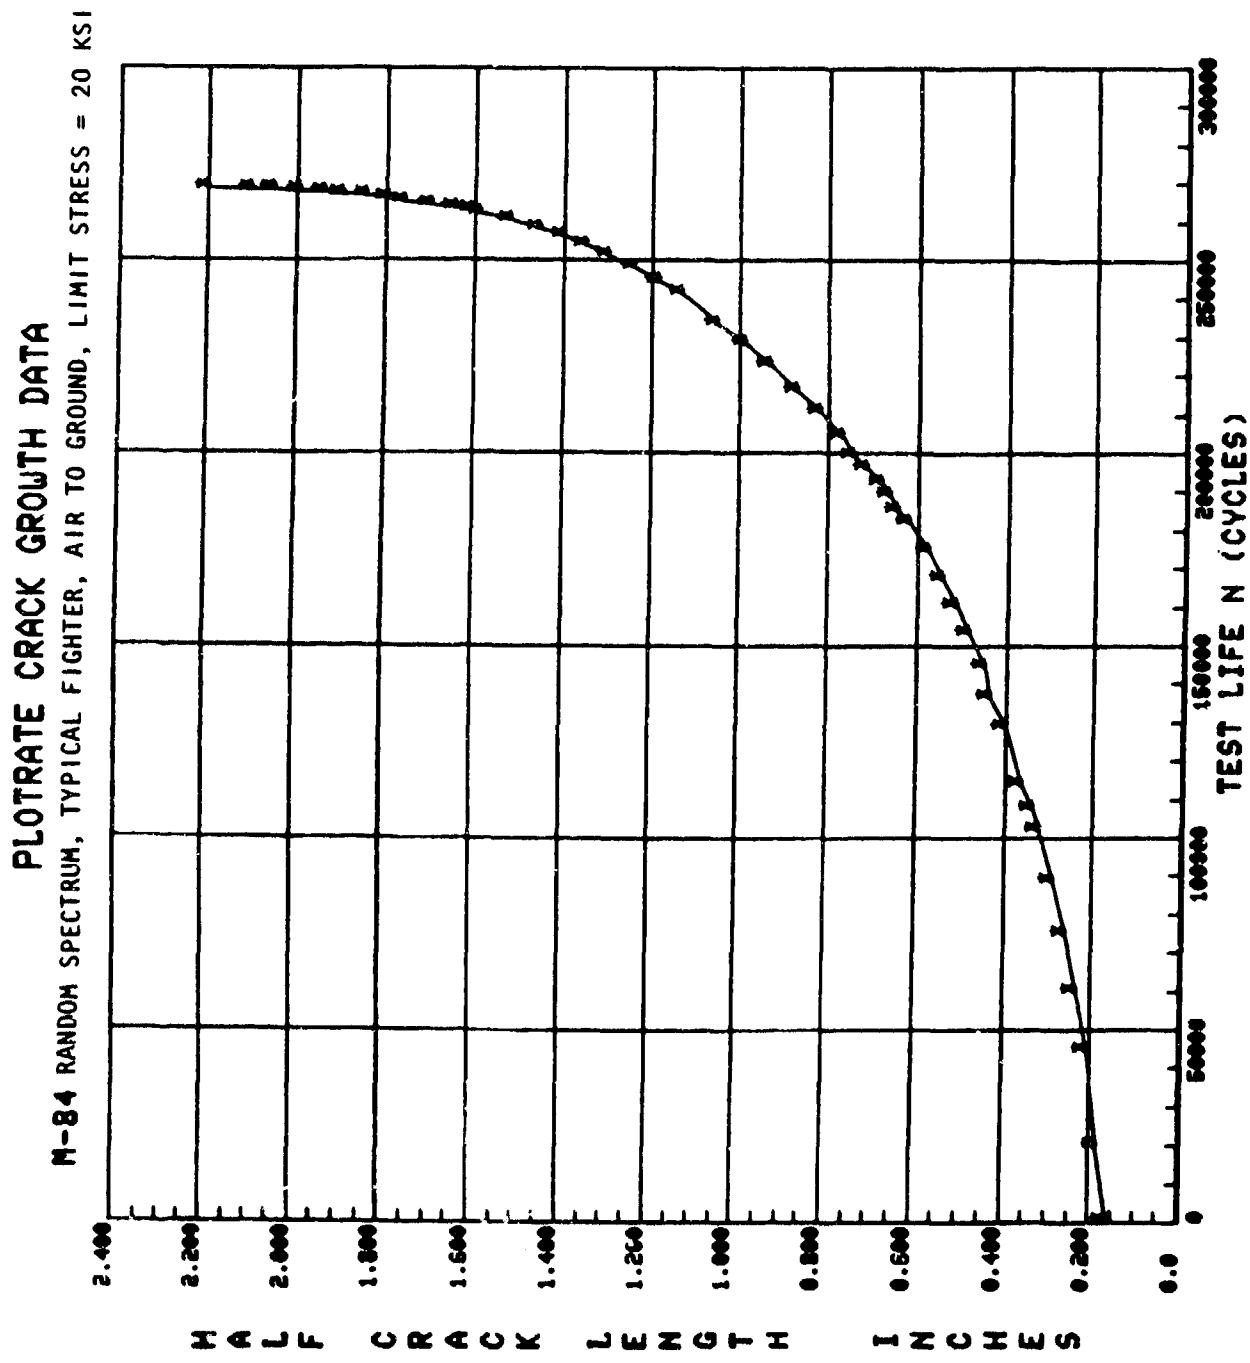


Figure 103. Crack growth curve for test M-84.

TABLE 105. DATA TABULATION FOR TEST M-85

SPECIMEN NO.: M-85 RANDOM SPECTRUM, TYPICAL FIGHTER, AIR TO GROUND, LIMIT STRESS = 30 KSI

NO.	CYCLES	AIMEASURED)	AIRREGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA K	DA/DN
ENVIRONMENT CONDITION: AMBIENT AIR							
1	0.	0.288	0.288	0.995998	10.37	12.25	1.261E-06
2	1.6532.	0.360	0.364	0.997163	11.35	13.41	2.928E-06
3	2.2575.	0.410	0.401	0.998073	12.26	14.48	3.971E-06
4	3.2606.	0.485	0.494	0.998440	13.62	16.09	5.231E-06
5	3.9198.	0.575	0.569	0.998530	14.64	17.30	6.059E-06
6	4.5203.	0.665	0.645	0.998743	15.60	18.44	7.012E-06
7	4.9820.	0.710	0.714	0.997826	16.44	19.43	8.008E-06
8	5.3902.	0.775	0.777	0.999324	17.19	20.31	9.405E-06
9	5.6717.	0.830	0.832	0.999251	17.81	21.05	1.018E-05
10	6.0148.	0.905	0.908	0.998874	18.65	22.04	1.113E-05
11	6.3495.	0.995	0.989	0.999489	19.51	23.05	1.199E-05
12	6.7197.	1.080	1.080	0.999036	20.45	24.17	1.285E-05
13	7.0438.	1.160	1.164	0.998852	21.31	25.18	1.373E-05
14	7.2811.	1.225	1.228	0.999031	21.94	25.92	1.551E-05
15	7.4730.	1.290	1.288	0.998893	22.53	26.53	1.656E-05
16	7.6233.	1.335	1.340	0.998951	23.03	27.22	1.763E-05
17	7.8055.	1.415	1.405	0.997961	23.66	27.96	1.963E-05
18	7.9908.	1.475	1.479	0.998620	24.36	28.79	2.164E-05
19	8.1621.	1.550	1.555	0.997792	25.08	29.64	2.477E-05
20	8.3473.	1.655	1.649	0.998979	25.97	30.69	2.815E-05
21	8.5271.	1.750	1.759	0.999305	27.00	31.90	3.259E-05
22	8.6280.	1.835	1.825	0.999155	27.62	32.64	3.542E-05
23	8.7763.	1.930	1.931	0.999183	28.62	33.82	3.978E-05
24	9.0113.	2.130	2.134	0.998598	30.55	36.11	5.094E-05
25	9.1299.	2.255	2.257	0.999733	31.75	37.52	5.950E-05
26	9.2178.	2.360	2.367	0.996353	32.83	38.80	7.140E-05
27	9.3096.	2.495	2.500	0.995676	34.17	40.39	8.990E-05
28	9.3747.	2.595	2.618	0.996082	35.41	41.86	1.139E-04

TABLE 105. DATA TABULATION FOR TEST M-85. (CONCL.)

SPECIMEN NO.: M-85		RANDOM SPECTRUM, TYPICAL FIGHTER, AIR TO GROUND, LIMIT STRESS = 30 KSI			
CCT	SPECIMEN	B = 0.250 IN.	b = 6.000 IN.	A _N = 0.0 IN.	
P _{MIN}	P _{MAX}	TEST FREQ = 6.00 Hz.			
ENVIRONMENT CONDITION: AMBIENT AIR					
NO.	CYCLES	A _I MEASURED ¹	A _I (REGRESSION)	MULT. CORR. COEFF	K-MAX
29	94174.	2.720	2.718	0.994132	36.47
30	94510.	2.810	2.813	0.997103	37.52
31	94862.	2.925	2.948	0.991402	39.04
32	95084.	3.060	3.047	0.989070	40.22
33	95313.	3.155	3.196	0.990265	42.06
34	95413.	3.275	3.273	0.987142	43.05
35	95507.	3.390	3.349	0.979993	44.07
36	95642.	3.470	3.471	0.998006	45.78
					DA/DW
					1.465E-04
					44.34
					1.759E-04
					2.304E-04
					46.14
					3.062E-04
					47.53
					49.71
					3.776E-04
					50.88
					4.080E-04
					4.445E-04
					54.10
					2.233E-04

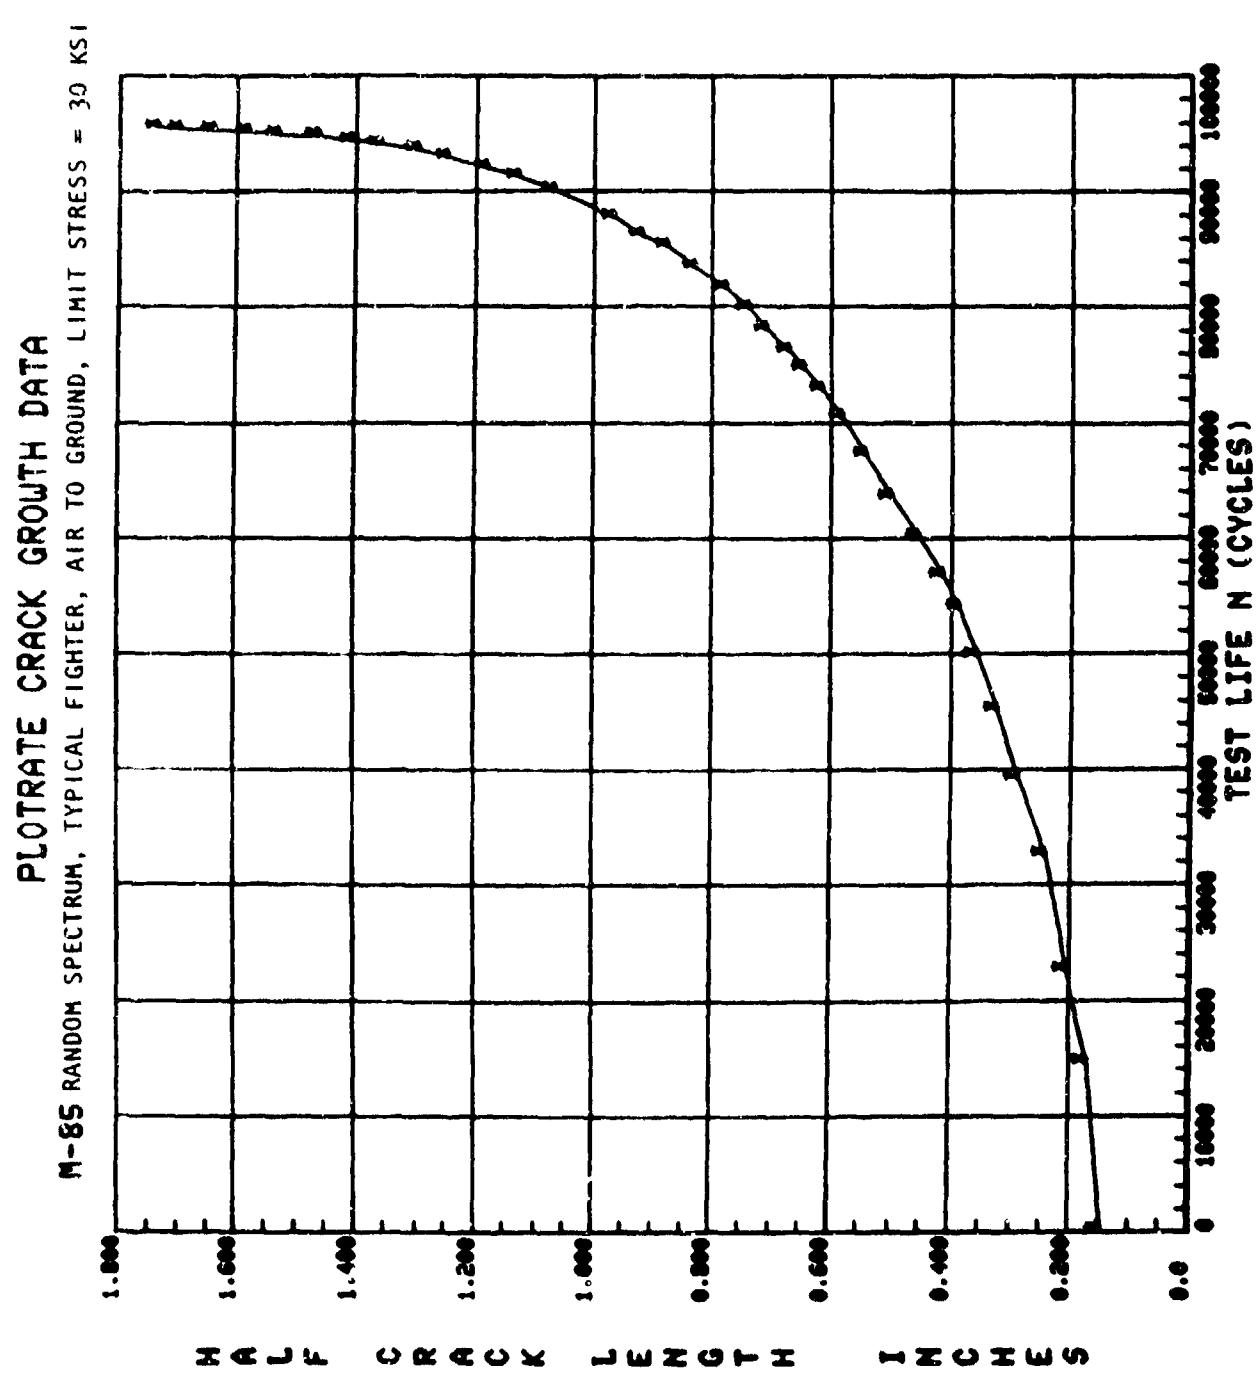


Figure 104. Crack growth curve for test M-85.

TABLE 106. DATA TABULATION FOR TEST M-86

SPECIMEN NO.: A-26 RANDOM SPECTRUM, TYPICAL FIGHTER, AIR-TO-GROUND, LIMIT STRESS = 40 KSI

CCT	SPECIMEN	D= 0.250 IN.	W= 0.00 IN.	A= 0.0 IN.	TEST FREQ= 6.000HZ.	ENVIRONMENT CONDITION: AMBIENT AIR		MULT. CLR, COEFF	K-MAX	DELTA K	DAWN
						P MIN	P MAX				
1	0.	0.205	0.305	0.305	0.944709	14.49	14.49	0.944709	14.49	14.49	2.444E-06
2	5149-	0.245	0.352	0.352	0.997512	15.58	15.58	0.997512	15.58	15.58	5.721E-06
3	10072-	0.470	0.417	0.417	0.945451	16.97	16.97	0.945451	16.97	16.97	8.249E-06
4	13301-	0.480	0.476	0.476	0.946220	18.14	18.14	0.946220	18.14	18.14	1.00E-05
5	16461-	0.530	0.546	0.546	0.945121	19.43	19.43	0.945121	19.43	19.43	1.444E-05
6	17786-	0.560	0.570	0.570	0.996146	19.69	19.69	0.996146	19.69	19.69	1.342E-05
7	20023-	0.635	0.639	0.639	0.996735	21.53	21.53	0.996735	21.53	21.53	2.612E-05
8	21632-	0.695	0.694	0.694	0.995715	22.60	22.60	0.995715	22.60	22.60	1.678E-05
9	23395-	0.760	0.762	0.762	0.996962	23.09	23.09	0.996962	23.09	23.09	2.149E-05
10	24394-	0.805	0.809	0.809	0.958780	43.63	43.63	0.958780	43.63	43.63	2.554E-05
11	25242-	0.855	0.847	0.847	0.996162	24.40	24.40	0.996162	24.40	24.40	2.443E-05
12	26840-	0.940	0.927	0.927	0.997612	25.59	25.59	0.997612	25.59	25.59	2.751E-05
13	28215-	0.995	1.004	1.004	0.996296	46.10	46.10	0.996296	46.10	46.10	3.109E-05
14	29457-	1.045	1.048	1.048	0.999192	27.51	27.51	0.999192	27.51	27.51	3.090E-05
15	30371-	1.155	1.152	1.152	0.999262	26.76	26.76	0.999262	26.76	26.76	3.415E-05
16	31098-	1.210	1.217	1.217	0.949242	49.63	49.63	0.949242	49.63	49.63	4.469E-05
17	31865-	1.290	1.290	1.290	0.999696	30.61	30.61	0.999696	30.61	30.61	5.241E-05
18	32426-	1.355	1.349	1.349	0.998906	31.39	31.39	0.998906	31.39	31.39	5.482E-05
19	33133-	1.425	1.434	1.434	0.997536	32.49	32.49	0.997536	32.49	32.49	6.079E-05
20	33906-	1.535	1.536	1.536	0.956557	33.63	33.63	0.956557	33.63	33.63	6.950E-05
21	34448-	1.635	1.634	1.634	0.951277	25.06	25.06	0.951277	25.06	25.06	1.162E-04
22	35003-	1.755	1.767	1.767	0.992050	36.75	36.75	0.992050	36.75	36.75	1.575E-04
23	35681-	1.970	2.016	2.016	0.965116	39.94	39.94	0.965116	39.94	39.94	2.043E-04
24	35946-	2.130	2.161	2.161	0.9E6579	41.82	41.82	0.9E6579	41.82	41.82	3.571E-04
25	36117-	2.250	2.288	2.288	0.994652	43.51	43.51	0.994652	43.51	43.51	4.705E-04
26	36163-	2.355	2.326	2.326	0.992203	32.33	32.33	0.992203	32.33	32.33	4.939E-04
27	36242-	2.430	2.415	2.415	0.968692	45.22	45.22	0.968692	45.22	45.22	5.232E-04
28	36397-	2.580	2.580	2.580	0.943966	47.51	47.51	0.943966	47.51	47.51	5.926E-04

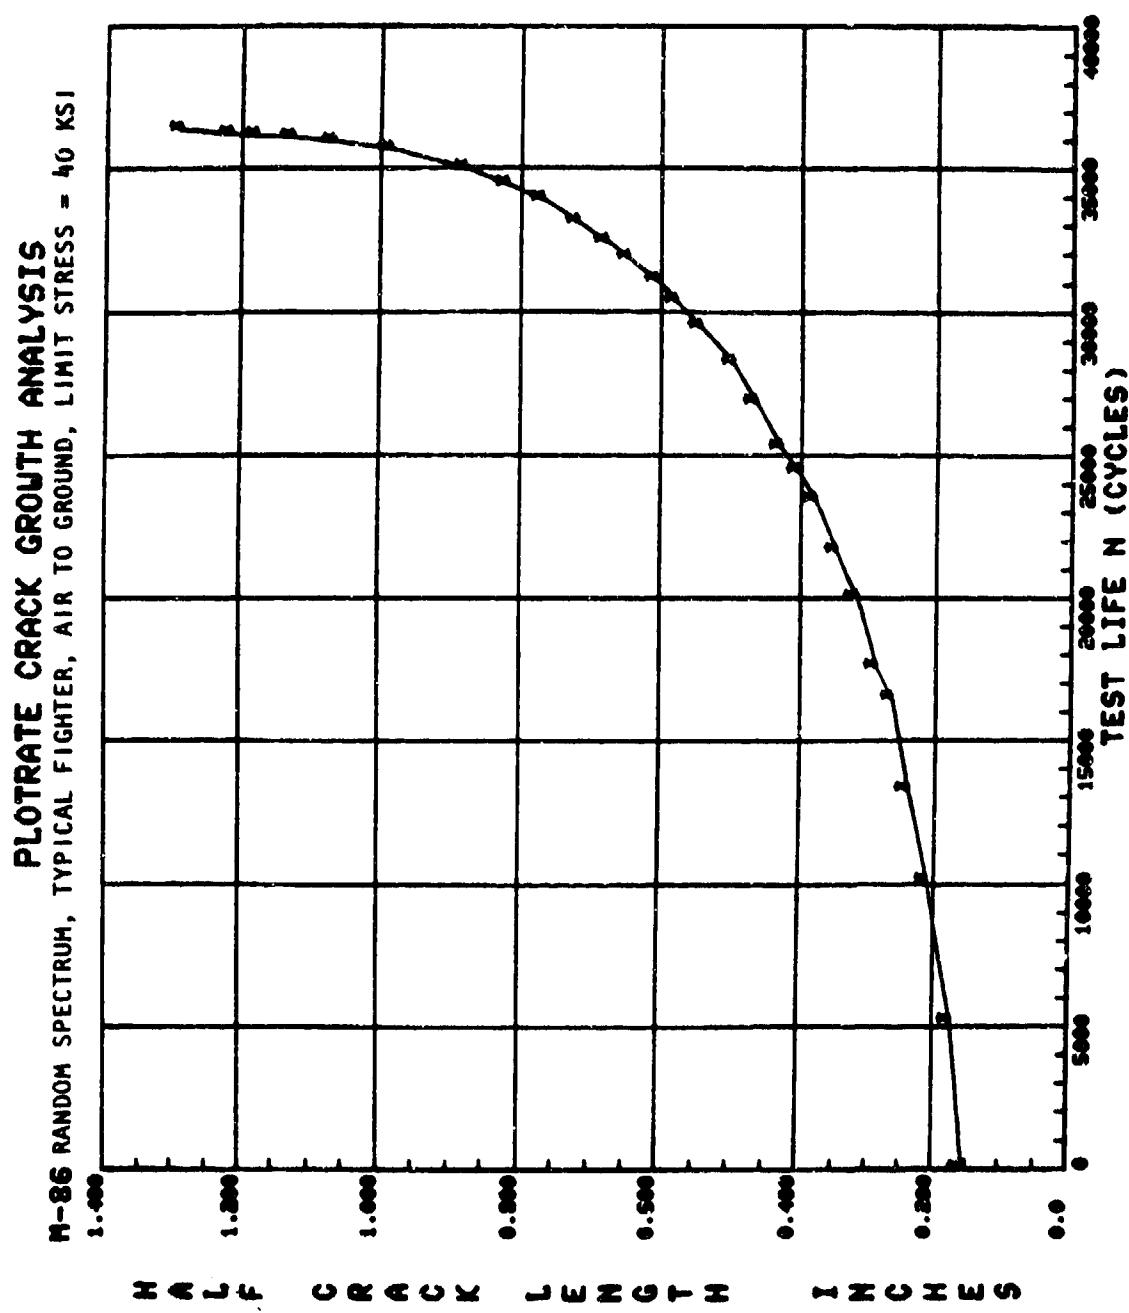


Figure 105. Crack growth curve for test M-86.

TABLE 107. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, INSTRUMENTATION AND NAVIGATION MISSION, A TYPICAL FIGHTER

Test M-88 $\sigma_{lim} = 30$ ksi, M-89 $\sigma_{lim} = 40$ ksi

MEADM 1200000 IS UN LI 05

0001	C...	HANUM I-N (N=300)									
0002	-5.0*	70.0	16.4	28.9	16.2	31.7	13.9	33.1	13.4	26.6	
0003	16.0	41.0	-5.0	29.4	14.4	31.3	16.3	31.7	13.7	29.2	
0004	9.0	33.2	13.9	26.3	-5.0	33.0	14.6	26.7	7.3	31.4	
0005	10.9	30.3	13.0	27.8	14.7	32.3	-5.0	23.4	10.2	27.4	
0006	14.7	32.4	17.9	28.0	11.7	23.8	7.1	29.8	-5.0	34.1	
0007	15.3	44.5	11.8	35.8	8.2	25.8	6.3	24.5	13.2	26.6	
0008	-5.0	24.6	11.5	26.1	8.8	30.0	14.4	26.2	15.3	29.7	
0009	14.7	28.8	-5.0	34.1	7.4	29.7	17.1	29.3	11.3	25.8	
0010	13.6	31.5	13.7	28.1	-5.0	34.1	16.8	31.6	12.0	32.1	
0011	19.2	34.1	9.4	25.0	7.4	27.8	-5.0	24.4	12.1	23.4	
0012	12.3	22.7	10.9	31.0	19.2	30.7	16.1	29.2	-5.0	36.3	
0013	10.8	23.0	13.0	28.3	10.2	33.4	14.3	32.4	11.5	27.0	
0014	-5.0	23.0	9.4	26.1	11.6	30.8	10.4	30.0	16.6	26.4	
0015	15.9	29.3	-5.0	31.7	13.3	30.4	11.9	32.2	13.3	23.5	
0016	8.6	35.8	16.9	30.5	-5.0	40.8	16.2	27.6	13.7	32.6	
0017	15.6	27.5	14.5	27.4	5.8	33.9	-5.0	35.1	14.7	28.2	
0018	17.2	28.9	17.1	28.7	10.4	37.2	7.1	25.9	-5.0	32.1	
0019	16.4	28.4	13.5	30.7	18.6	39.1	16.2	27.2	10.5	22.1	
0020	-5.0	40.1	11.7	24.2	11.5	31.1	16.7	38.7	10.1	29.3	
0021	17.6	28.4	-5.0	33.0	10.0	36.7	14.5	28.9	12.4	30.7	
0022	17.8	37.3	13.8	27.4	-5.0	27.7	15.6	25.7	15.2	26.7	
0023	13.0	34.0	16.1	26.3	13.6	29.8	-5.0	36.8	16.9	27.6	
0024	12.7	28.2	9.4	29.0	15.2	28.8	6.3	34.3	-5.0	30.6	
0025	11.9	35.7	10.7	26.7	14.9	34.0	15.1	35.7	16.4	32.6	
0026	-5.0	39.6	10.5	26.5	7.8	25.8	9.1	35.7	9.3	29.6	
0027	14.6	29.6	-5.0	25.9	15.7	40.4	15.1	28.4	17.2	30.4	
0028	15.2	30.8	14.6	25.9	-5.0	34.1	18.0	31.8	14.2	27.2	
0029	16.0	29.7	10.2	24.4	10.0	34.4	-5.0	31.5	11.5	25.5	
0030	15.0	31.6	15.9	36.9	16.9	38.6	11.1	29.5	-5.0	31.3	
0031	14.3	30.6	9.8	33.2	16.7	29.5	12.7	34.3	15.6	26.7	
0032	-5.0	27.3	13.0	28.6	3.7	30.1	17.1	35.2	11.3	39.1	
0033	14.2	24.6	-5.0	24.1	13.3	31.3	19.5	29.8	10.9	21.6	
0034	9.1	32.3	11.5	45.4	-5.0	32.9	14.2	37.7	16.1	36.9	
0035	16.8	43.4	13.5	24.6	13.4	24.7	-5.0	41.2	6.8	30.9	
0036	20.1	37.0	16.1	34.8	14.0	27.7	12.5	32.6	-5.0	29.1	
0037	10.5	27.1	12.0	36.0	14.1	28.5	17.6	34.8	17.0	31.4	
0038	-5.0	27.1	10.2	35.9	17.8	31.1	6.0	35.7	18.7	38.6	
0039	15.8	36.5	-5.0	27.1	14.7	39.9	10.9	29.9	14.3	34.1	
0040	12.7	37.6	15.3	32.0	-5.0	34.3	16.0	33.7	13.8	26.5	
0041	15.2	32.4	18.5	29.0	8.8	35.1	-5.0	31.2	11.7	29.5	
0042	14.4	26.4	9.6	29.7	9.1	28.9	12.3	23.9	-5.0	29.9	
0043	13.1	33.0	9.0	28.0	9.9	35.6	19.2	34.0	12.5	26.6	
0044	-5.0	24.8	12.1	41.3	20.9	32.6	20.3	34.6	12.7	29.0	
0045	12.4	26.7	-5.0	25.5	12.9	33.4	11.2	35.3	12.3	26.7	
0046	10.6	24.9	14.2	30.5	-5.0	27.8	16.4	30.9	8.2	29.1	
0047	12.3	32.3	14.2	35.8	10.5	35.4	-5.0	26.8	11.6	27.0	
0048	15.1	28.0	16.0	28.7	12.8	23.9	8.5	32.9	-5.0	34.1	
0049	13.8	31.5	16.5	42.7	18.3	28.3	6.2	35.2	14.1	31.7	
0050	-5.0	29.8	16.5	32.6	12.8	27.8	13.8	34.3	10.8	27.2	
0051	9.7	38.0	-5.0	27.5	7.4	30.7	13.8	32.7	16.6	39.4	
0052	6.2	39.1	14.5	35.5	-5.0	27.3	14.7	37.9	30.9	42.1	
0053	17.5	26.4	9.7	27.2	20.4	36.3	-5.0	29.9	4.1	52.7	
0054	13.1	26.5	14.4	35.8	17.4	39.0	8.9	52.3	-5.0	23.7	
0055	9.4	34.2	23.7	39.7	9.8	19.9	13.0	19.0	8.9	23.2	
0056	-5.0	46.4	17.7	31.0	11.2	23.2	10.8	18.1	8.3	39.0	
0057	25.2	42.5	-9.0	23.5	8.4	32.9	11.4	21.3	12.0	33.2	
0058	15.1	31.8	9.0	37.0	-5.0	38.5	13.3	29.3	10.6	37.7	
0059	14.0	43.2	4.0	37.2	22.3	37.8	-5.0	38.0	14.1	29.3	
0060	14.2	35.6	16.7	30.4	37.9	47.1	11.2	18.4	-5.0	48.0	
0061	18.9	30.5	17.4	25.3	12.5	21.6	7.9	17.0	2.6	27.2	

* % of σ_{lim}

TABLE 108. DATA TABULATION FOR TEST M-88

SPECIMEN NO.:	H-F-0	RANDOM SPECTRUM, TYPICAL FIGHTER, INSTRUMENTATION AND NAVIGATION, LIMIT STRESS = 30 KSI		W= 6.000 IN.	A= 0.0 IN.	P _{MAX} = TEST FREQ= 6.000HZ.
		CCT	SPECIMEN	B= 0.75C IN.		
ENVIRONMENT CONDITION: AMBIENT AIR						
NO.	CYCLES	A1MEAS(D)	A1REGRESSION	MULT. CURR. L _{EFF}	X-MAX	DAWN
1	0.	0.760	0.501	0.954750	9.64	6.739E-07
2	21035.	0.335	0.315	0.960855	9.86	3.005E-07
3	85492.	0.360	0.401	0.974422	11.14	1.04E-06
4	92358.	0.470	0.413	0.982441	11.51	1.163E-06
5	110797.	0.465	0.457	0.954752	11.91	1.476E-06
6	127691.	0.510	0.512	0.996132	12.60	1.716E-06
7	143558.	0.570	0.574	0.996511	13.36	1.790E-06
8	165107.	0.670	0.657	0.996823	14.32	2.026E-06
9	184205.	0.715	0.741	0.997059	15.24	2.186E-06
10	198731.	0.742	0.805	0.996400	15.92	17.05
11	206346.	0.860	0.847	0.996437	16.34	17.51
12	219281.	0.966	0.900	0.947731	16.67	2.512E-06
13	228174.	0.940	0.944	0.934605	17.30	1.54
14	233992.	0.960	0.974	0.991254	17.59	18.82
15	239522.	1.020	1.009	0.991346	17.62	3.390E-06
16	245847.	1.060	1.059	0.991646	18.40	3.672E-06
17	254683.	1.115	1.126	0.993864	19.03	3.838E-06
18	259370.	1.170	1.157	0.995713	19.30	20.60
19	267413.	1.220	1.225	0.995519	19.91	21.34
20	271544.	1.260	1.257	0.993475	20.20	21.65
21	277677.	1.310	1.312	0.999073	20.69	22.47
22	282803.	1.365	1.371	0.997512	21.21	22.72
23	287893.	1.435	1.431	0.996463	21.73	23.28
24	292414.	1.490	1.485	0.999279	22.20	23.79
25	296480.	1.530	1.528	0.997769	22.57	24.18
26	305816.	1.670	1.625	0.996663	23.46	25.08
27	315094.	1.725	1.733	0.999454	24.32	26.06
28	321987.	1.820	1.819	0.999572	25.06	26.85

TABLE 108. DATA TABULATION FOR TEST M-38 (CONCL)

SPECIMEN NO.:	GCI	SPECIMEN	D= 0.250 IN.	W= 6.000 IN.	A N= 0.0	I N.	TEST FREQ= 6.000HZ.	
							P MIN=	P MAX=
ENVIRONMENT CONDITION: AMBIENT AIR								
NO.		CYCLES	A(MEASURED)	A(REGRESSION)	MULT.	CORR. COEFF	K-MAX	DELTA K DA/DN
29		328954.	1.920	1.914	0.999582	25.87	27.72 7.017E-06	
30		336739.	2.025	2.030	0.999794	26.87	28.79 7.266E-06	
31		342931.	2.125	2.124	0.999870	27.69	29.67 7.937E-06	
32		3449757.	2.235	2.234	0.999801	29.66	30.73 8.564E-06	
33		354381.	2.315	2.313	0.999645	29.36	31.40 9.074E-06	
34		359161.	2.400	2.404	0.999008	30.16	32.34 1.142E-05	
35		364506.	2.510	2.529	0.996745	31.34	33.56 1.457E-05	
36		366884.	2.605	2.599	0.998657	32.00	34.48 1.647E-05	
37		370162.	2.715	2.714	0.996408	33.12	35.46 2.051E-05	
38		372331.	2.615	2.605	0.993279	34.02	36.45 2.470E-05	
39		374623.	2.695	2.917	0.993441	35.17	37.68 3.176E-05	
40		376796.	3.050	3.059	0.993364	36.69	39.31 4.525E-05	
41		378199.	3.175	3.195	0.980435	36.18	40.91 6.554E-05	
42		379698.	3.345	3.419	0.977569	40.96	43.63 9.647E-05	
43		380131.	3.450	3.505	0.982105	42.07	45.06 1.375E-04	
44		380443.	3.610	3.610	0.999919	43.51	46.61 2.195E-04	

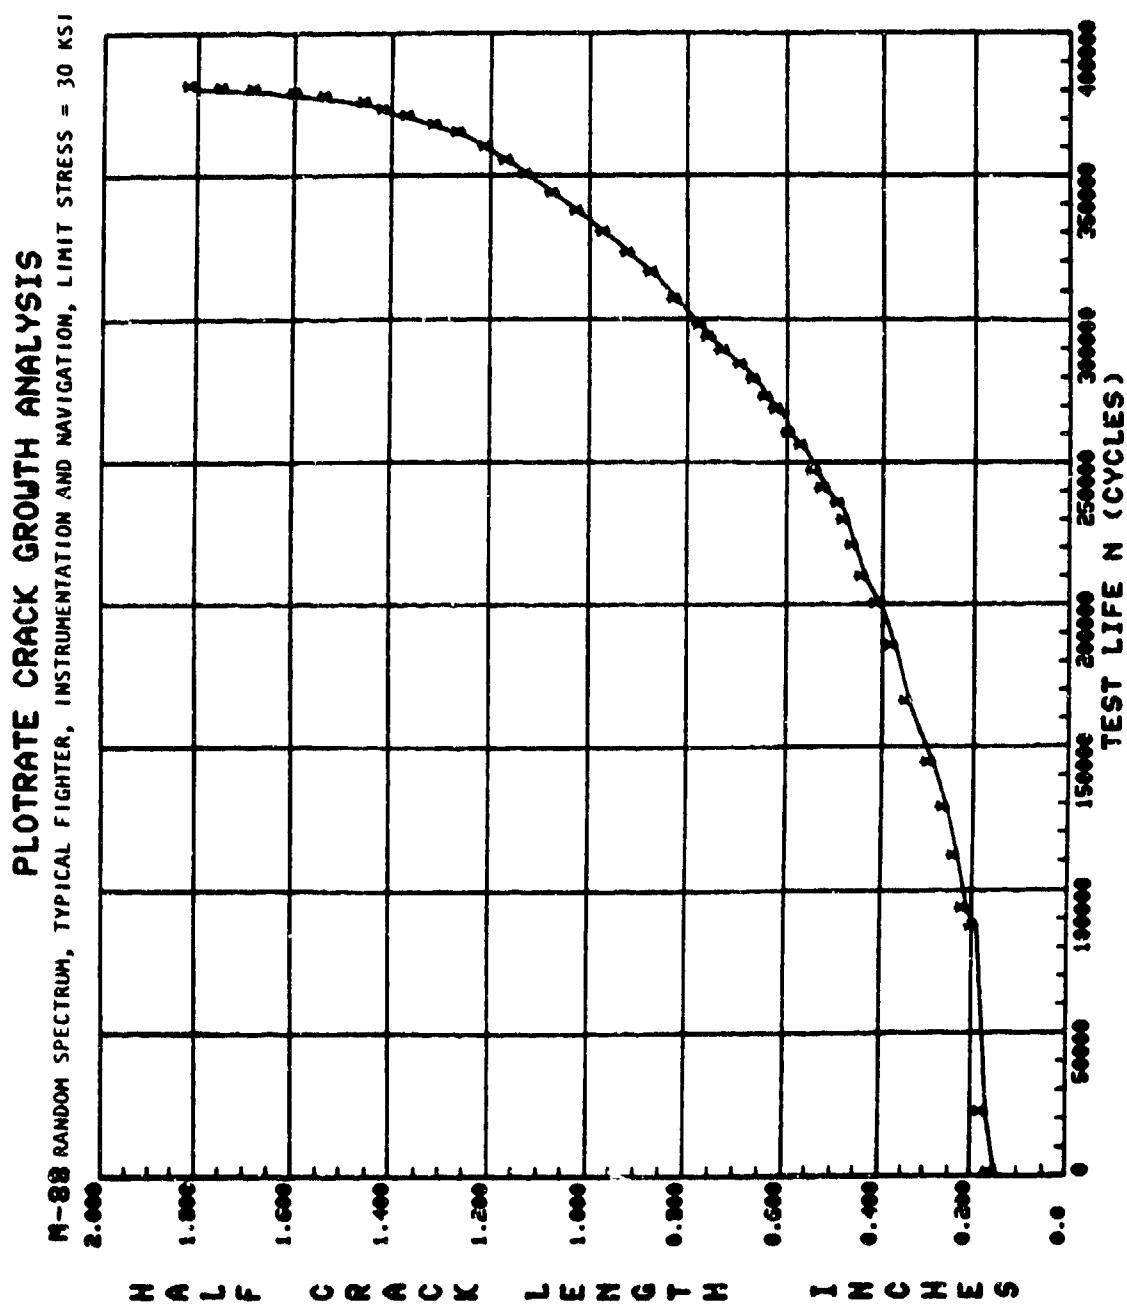


Figure 106. Crack growth curve for test M-88.

TABLE 109. DATA TABULATION FOR TEST M-89

SPECIMEN NO.:	H-59	RANDOM SPECTRUM, TYPICAL FIGHTER, INSTRUMENTATION AND NAVIGATION, LIMIT STRESS = 40 KSI					
		CCT	SPECIMEN	G= 0.25G IN.	W= 0.000 IN.	A= 0.0 IN.	TEST FREQ= 6.000HZ.
P MIN=	P MAX=	ENVIRONMENT CONDITIONS: AMBIENT AIR					
NU.	CYCLES	A MEASURED (1)	A REGRESSION (1)	MULT. CKA8. COEFF	K-MAX	DELTA K	DATA NO.
1	0.	C-200	0.300	0.996664	12.84	13.76	7.333E-07
2	25075.	0-365	0.353	0.997923	13.92	14.92	1.426E-06
3	48450.	0-420	0.434	0.996397	15.53	16.64	2.310E-06
4	60470.	0-495	0.496	0.996981	16.54	17.72	2.750E-06
5	72439.	0-560	0.566	0.997247	17.70	18.96	3.508E-06
6	76324.	0-605	0.595	0.997006	18.20	19.50	3.712E-06
7	86460.	0-665	0.674	0.994946	19.35	20.73	4.023E-06
8	90737.	0-720	0.712	0.994324	19.90	21.32	4.262E-06
9	98224.	0-780	0.776	0.994845	20.61	22.30	4.353E-06
10	107382.	0-805	0.814	0.992946	21.34	22.67	4.689E-06
11	106339.	0-855	0.847	0.995143	21.79	23.35	5.012E-06
12	112725.	0-905	0.915	0.995759	22.69	24.31	5.720E-06
13	115969.	0-955	0.954	0.995139	23.20	24.86	6.479E-06
14	116576.	0-995	0.950	0.991425	23.66	25.35	6.453E-06
15	124360.	1-065	1-073	0.993264	24.71	26.45	7.334E-06
16	126751.	1-120	1-108	0.993543	25.13	26.93	7.340E-06
17	131171.	1-160	1-173	0.992876	25.93	27.78	7.926E-06
18	133849.	1-225	1-214	0.940639	26.43	28.32	8.673E-06
19	137455.	1-270	1-277	0.994541	27.17	29.11	9.687E-06
20	129607.	1-375	1-326	0.995122	27.78	29.76	1.065E-05
21	141305.	1-365	1-358	0.997332	28.12	30.13	1.107E-05
22	143650.	1-415	1-414	0.998633	28.76	30.83	1.263E-05
23	145773.	1-465	1-467	0.999593	29.39	31.49	1.364E-05
24	147915.	1-525	1-525	0.999970	30.06	32.21	1.469E-05
25	151873.	1-655	1-649	0.998324	31.48	33.72	1.861E-05
26	155096.	1-775	1-775	0.996746	32.91	35.26	2.400E-05
27	157614.	1-855	1-904	0.994992	34.36	36.83	3.089E-05
28	159477.	2.016	2.016	0.996686	35.67	38.22	3.960E-05

TABLE 109. DATA TABULATION FOR TEST M-89 (CONCL)

SPECIMEN NO.: M-89 RANDOM SPECTRUM, TYPICAL FIGHTER, INSTRUMENTATION AND NAVIGATION, LIMIT STRESS = 40 KSI

CCT	SPECIMEN	$t = 0.750$ IN.	$W = 6.000$ IN.	$A_N = 0.6$	TEST FREQ = 6.000HZ.	PHINE = MAX =		ENVIRONMENT CONDITION: AMBIENT AIR		NO. CYCLES		A (MEASURED) AIRAGRESSION		MULT. COHR. COEFF		K-MAX		DELTA K		DA/DN	
						MAX =	TEST FREQ = 6.000HZ.	A (MEASURED)	AIRAGRESSION	NO.	CYCLES	A (MEASURED)	AIRAGRESSION	MULT. COHR. COEFF	K-MAX	DELTA K	DA/DN				
29	161303-	2-155	2-170					0.9942E2	37.45	40.13	5.507E-05										
30	162402-	2-200	2-295					0.984203	39.93	41.71	7.940E-05										
31	1632P2-	2-400	2-446					0.957974	40.76	43.67	1.304E-04										
32	162861-	2-515	2-552					0.973269	42.45	45.48	1.288E-04										
33	164432-	2-740	2-819					0.985255	45.55	48.80	2.695E-04										
34	164736-	2-075	3.013					0.950911	48.33	51.79	4.256E-04										

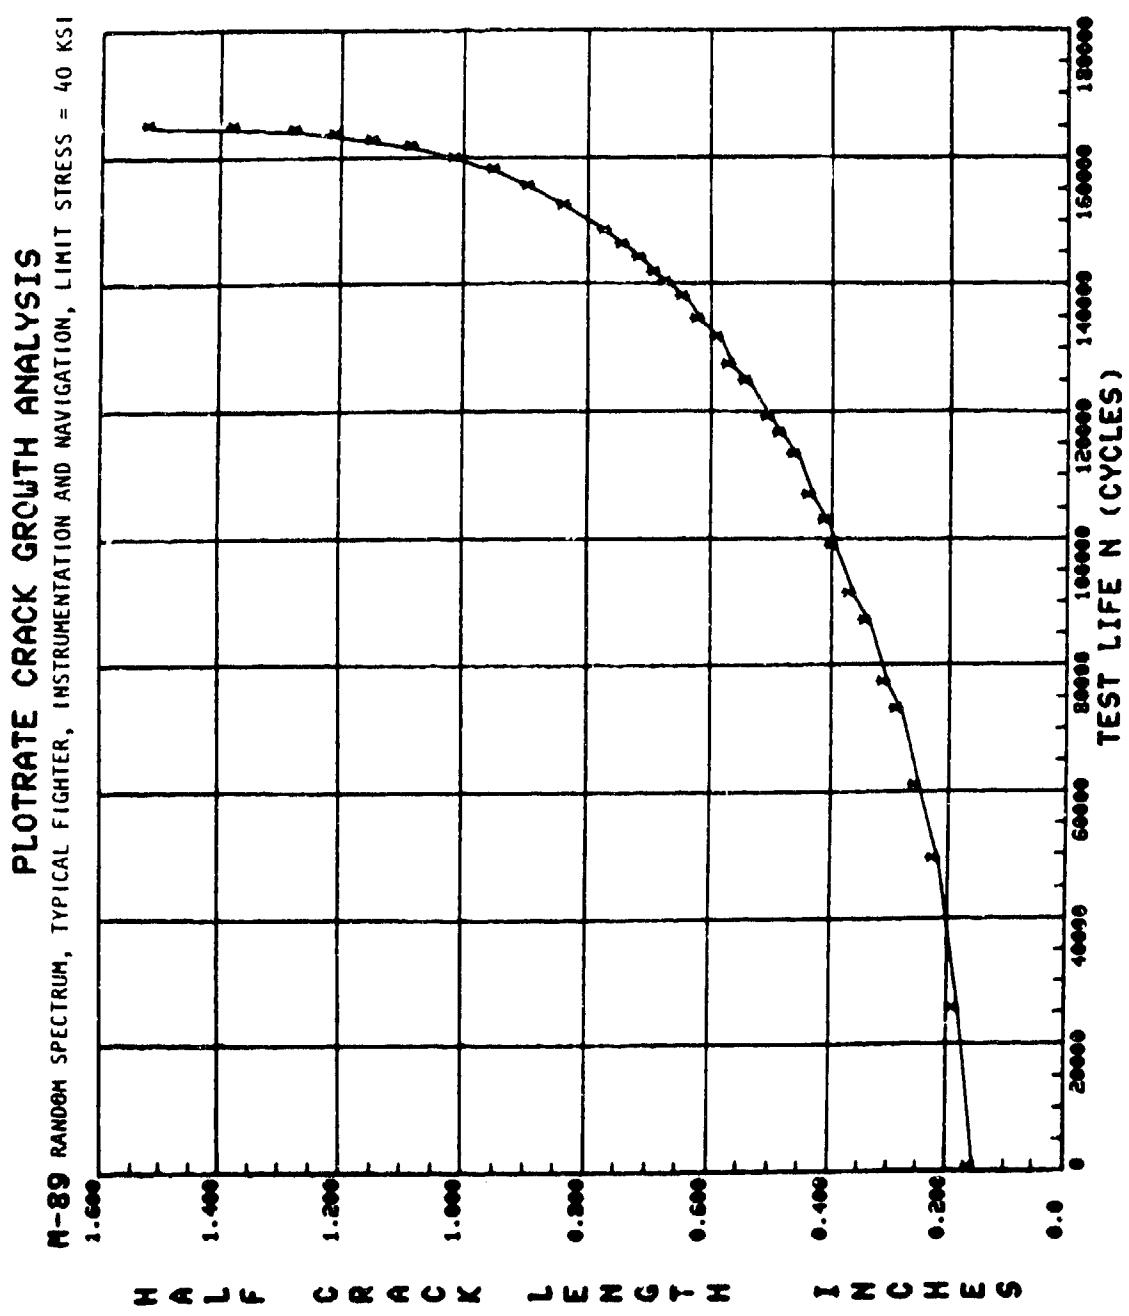


Figure 107. Crack growth curve for test M-89.

TABLE 110. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, COMPOSITE MISSION, A TYPICAL FIGHTER

Test M-90 $\sigma_{lim} = 20$ ksi, M-91 $\sigma_{lim} = 30$ ksi, M-92 $\sigma_{lim} = 40$ ksi

MEAUN TAOUHOU IS ON LU OH

C.... HANULUM COMPOSISIT (NAT1055)										
0002	-05.0*	70.0	16.1	34.1	20.1	45.5	25.0	52.3	36.4	50.1
0003	26.2	44.5	16.6	48.6	24.5	61.4	8.8	29.4	17.8	52.0
0004	17.5	29.5	10.2	74.4	18.8	30.6	32.5	53.7	17.3	65.1
0005	50.6	63.5	3.1	67.5	10.9	60.6	44.0	56.9	16.2	45.1
0006	14.7	34.0	20.4	58.4	31.2	45.6	27.8	63.5	9.4	69.1
0007	36.1	58.2	-5.0	74.4	27.6	42.9	27.4	41.0	9.4	30.9
0008	16.0	40.2	5.2	39.1	19.5	51.9	9.3	31.4	19.1	40.1
0009	0.4	27.6	16.9	36.2	11.8	28.7	9.3	33.2	1.8	13.3
0010	1.4	50.2	18.6	31.8	19.1	48.8	34.0	63.7	24.9	66.1
0011	22.5	42.7	12.2	40.8	22.0	41.9	21.2	42.2	16.3	26.0
0012	-3.6	27.3	11.9	45.3	-5.0	48.8	14.7	48.6	23.6	57.1
0013	36.4	58.3	32.1	48.7	27.1	41.5	29.7	61.1	29.3	60.1
0014	19.8	43.5	28.5	74.9	19.2	48.5	22.4	38.3	5.1	52.1
0015	34.0	45.0	14.7	46.4	3.0	34.8	19.8	48.7	33.4	54.0
0016	25.4	38.7	18.3	36.0	18.5	63.7	17.7	56.1	11.7	29.1
0017	-7.5	41.4	15.3	33.8	9.7	36.1	-5.0	61.7	16.3	50.1
0018	30.1	47.9	25.4	52.1	24.4	65.2	-10.1	50.7	12.6	44.6
0019	32.1	47.0	24.3	38.4	19.6	46.2	23.4	42.3	3.5	52.5
0020	39.8	64.4	16.9	30.6	19.1	47.2	6.4	74.1	12.2	50.2
0021	28.8	45.6	12.7	46.2	15.3	39.2	20.2	46.4	36.5	50.4
0022	3.8	60.0	11.9	44.6	29.5	41.3	11.5	40.4	-5.0	47.4
0023	6.4	44.3	32.4	58.2	16.3	55.1	-4.6	83.1	0.6	37.3
0024	24.1	57.7	16.2	34.8	22.2	65.7	24.8	47.5	13.4	55.9
0025	42.5	64.5	24.9	38.5	-22.0	61.8	36.2	66.4	39.4	60.9
0026	35.4	56.8	25.5	51.2	34.5	54.9	26.8	39.5	-3.7	81.0
0027	-1.8	47.0	12.5	59.6	8.3	53.9	7.7	45.3	29.7	66.4
0028	-5.0	44.2	5.5	33.5	15.0	36.1	2.7	58.5	2.8	40.9
0029	13.8	38.1	13.2	51.7	4.0	33.3	9.4	29.3	11.6	60.9
0030	14.0	45.4	30.9	45.9	13.5	48.1	21.1	57.3	13.9	35.2
0031	18.7	37.3	19.3	40.6	1.1	25.6	8.3	67.1	32.8	71.0
0032	21.5	51.4	12.5	42.8	11.3	41.4	22.8	47.5	17.9	48.9
0033	17.5	55.1	-5.0	41.4	12.2	79.3	15.1	50.4	28.7	45.8
0034	34.3	59.1	28.3	45.3	29.1	52.9	12.0	65.1	30.9	40.0
0035	9.2	64.8	47.6	61.6	15.0	31.1	14.3	50.6	7.7	53.2
0036	34.7	68.1	6.8	20.5	6.2	56.5	9.3	75.7	12.6	52.7
0037	31.3	55.7	17.4	57.7	22.3	61.7	29.0	51.7	39.8	55.5
0038	12.2	42.6	8.1	25.8	-5.0	60.0	13.5	56.0	14.8	63.7
0039	21.6	32.0	20.3	43.4	9.7	48.1	33.5	45.2	-7.3	47.1
0040	8.4	77.9	45.9	58.8	10.3	71.8	10.6	38.2	23.3	40.2
0041	-4.8	40.3	4.9	41.1	17.9	42.7	5.1	61.8	27.2	50.7
0042	24.8	42.9	13.3	46.0	1.2	26.5	-4.5	51.3	5.4	26.6
0043	15.4	38.3	8.6	39.0	5.3	60.3	-5.0	42.2	13.0	34.4
0044	15.5	55.6	12.7	40.8	23.6	49.4	36.7	53.9	25.7	41.0
0045	18.2	33.3	22.5	46.5	3.0	44.7	6.4	39.8	22.5	64.3
0046	24.5	57.0	26.3	53.4	9.8	33.3	0.9	46.4	0.3	46.9
0047	24.5	47.4	22.3	47.2	6.3	77.9	25.4	74.7	18.7	64.1
0048	22.7	53.6	4.7	72.1	7.6	72.3	17.5	53.0	-5.0	59.3
0049	15.0	42.4	27.8	41.6	17.3	70.0	12.9	47.5	25.4	66.3
0050	50.3	69.4	-6.2	69.5	47.1	60.2	13.1	66.1	11.6	71.4
0051	18.7	53.3	16.2	35.5	10.7	42.3	5.6	61.4	23.5	49.3
0052	19.1	51.0	1.3	45.7	15.9	32.5	20.9	43.4	28.9	47.3
0053	22.5	46.1	21.8	52.4	38.4	61.3	8.7	57.3	38.5	54.9
0054	-5.0	34.9	28.4	50.2	8.9	31.0	13.8	55.9	42.8	75.9
0055	16.6	50.3	34.6	46.2	11.4	66.4	11.7	55.5	-6.0	50.9
0056	37.6	51.0	22.5	37.5	14.6	24.7	1.2	33.1	0.7	26.8
0057	1.5	42.0	0.5	41.0	11.2	47.8	19.5	37.6	9.6	49.7
0058	-0.4	40.1	29.0	44.2	23.4	60.8	14.2	40.4	23.3	45.3
0059	-10.0	70.0	29.6	41.9	4.2	20.1	7.8	48.9	6.3	37.1

*% of σ_{lim}

TABLE 110. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT
SPECTRUM LOADING TEST, COMPOSITE MISSION, A TYPICAL FIGHTER (CONT)

Test M-90 $\sigma_{lim} = 20$ ksi, M-91 $\sigma_{lim} = 30$ ksi, M-92 $\sigma_{lim} = 40$ ksi

0040	8.4	37.8	16.4	20.6	17.8	49.5	13.8	26.9	4.0	42.9
0061	11.4	74.1	20.3	34.5	1.5	21.0	7.8	34.5	11.9	23.8
0062	2.1	71.5	11.3	43.6	8.5	33.1	10.4	56.3	-10.0	51.4
0063	0.6	18.9	7.0	55.9	31.7	48.6	3.0	17.3	6.9	44.1
0064	30.6	42.4	25.3	44.3	2.4	31.4	4.4	24.6	8.6	29.7
0065	18.0	28.4	14.4	44.2	16.4	35.2	8.0	51.8	8.1	23.3
0066	2.8	21.7	8.7	59.5	12.3	47.3	-10.0	67.1	42.2	57.2
0067	14.5	35.4	11.0	27.8	5.5	19.6	3.7	27.7	8.9	31.1
0068	0.6	28.8	9.2	22.6	12.5	41.6	0.5	26.4	10.3	34.3
0069	-0.1	19.5	5.1	26.7	5.7	31.4	4.3	22.3	10.7	24.5
0070	1.6	12.0	0.0	48.2	-10.0	31.1	7.1	23.7	6.6	35.2
0071	12.1	49.2	11.0	78.4	4.4	24.2	5.2	29.5	6.7	30.6
0072	16.1	26.3	11.0	37.8	5.6	17.2	-1.2	23.6	3.2	42.5
0073	22.8	40.3	6.5	33.6	8.5	49.9	21.0	43.2	22.5	45.2
0074	13.1	33.6	-10.0	25.1	8.4	78.6	11.3	42.4	9.5	34.6
0075	10.6	71.7	5.1	35.1	11.2	32.1	1.4	46.3	15.4	37.3
0076	5.4	46.9	0.1	24.1	8.5	40.8	21.2	42.7	9.4	23.3
0077	3.8	28.4	5.1	48.1	26.2	38.5	4.4	40.0	3.8	28.0
0078	-10.0	19.0	7.0	35.6	5.2	31.1	4.0	28.6	-0.0	53.1
0079	7.2	36.8	11.1	35.7	11.3	40.1	9.0	29.8	16.0	51.5
0080	-5.6	25.4	14.3	36.9	6.5	30.1	17.0	38.5	14.5	32.3
0081	6.9	38.1	6.6	35.2	-0.0	37.7	18.1	37.0	-10.0	50.5
0082	8.5	23.8	5.7	37.7	3.0	30.6	18.3	62.8	1.9	36.7
0083	10.6	39.3	3.6	38.0	4.0	32.3	7.2	35.1	19.6	55.2
0084	-0.0	47.4	3.0	38.1	14.6	32.0	7.5	21.2	2.7	29.6
0085	12.2	37.9	0.3	33.8	15.3	45.0	-10.0	32.5	8.6	46.5
0086	-0.4	75.6	-0.3	33.5	10.8	27.1	14.8	48.9	17.9	35.1
0087	2.8	57.0	10.8	38.4	2.2	48.3	26.3	64.1	12.0	34.4
0088	-14.7	53.9	17.3	62.1	27.3	39.1	4.7	38.5	6.6	45.3
0089	23.4	47.8	10.3	33.8	-10.0	70.0	-0.5	35.3	1.7	50.0
0090	3.1	41.4	0.8	25.8	13.9	30.7	15.9	53.5	1.3	38.9
0091	0.2	28.1	10.0	25.0	2.2	58.8	1.6	36.8	4.5	30.2
0092	3.3	48.7	0.3	26.9	2.5	18.9	2.5	58.5	17.3	27.6
0093	4.5	33.0	-10.0	32.6	3.0	39.7	7.5	41.9	27.6	39.7
0094	6.2	19.5	8.2	32.1	11.4	31.7	-9.4	18.6	2.5	60.7
0095	13.5	64.0	5.0	29.6	10.9	41.6	1.8	38.2	3.9	28.9
0096	9.2	34.1	7.4	32.0	18.8	37.9	13.5	26.1	6.8	25.7
0097	-10.0	46.1	22.5	38.5	3.2	33.0	13.9	25.0	15.3	30.9
0098	2.5	69.4	5.2	34.4	17.5	30.2	10.0	36.3	16.1	45.6
0099	11.8	36.0	11.8	35.7	12.0	24.8	5.8	21.0	7.0	54.0
0100	11.8	42.4	1.9	59.3	24.6	47.9	6.2	25.6	-10.0	38.6
0101	-5.0	70.0	16.8	28.9	16.2	31.7	13.9	33.1	13.4	28.4
0102	16.0	41.0	-5.0	29.4	14.4	31.3	16.3	31.7	13.7	29.2
0103	9.0	33.2	13.9	26.3	-5.0	33.0	14.6	26.7	7.3	31.4
0104	10.9	30.3	15.0	27.8	14.7	32.3	-5.0	24.4	10.2	27.4
0105	24.3	56.8	-5.0	67.6	22.8	66.6	32.4	52.2	29.9	56.5
0106	28.3	58.5	25.0	55.9	38.0	40.4	23.6	68.7	24.0	61.6
0107	18.6	65.3	21.5	44.1	6.0	30.4	1.0	58.5	17.4	29.3
0108	8.8	42.3	31.6	44.6	34.8	48.4	25.7	46.8	16.8	41.3
0109	-0.7	61.2	8.6	42.7	5.1	44.9	16.0	59.0	-0.7	64.7
0110	21.5	55.4	17.6	36.6	-5.0	36.9	7.5	55.0	29.8	51.4
0111	2.2	72.7	1.3	32.2	-3.0	70.1	6.8	73.8	21.9	49.6
0112	38.6	54.0	41.3	56.3	27.5	38.1	25.3	49.5	9.6	60.9
0113	13.9	53.4	14.9	36.7	15.4	41.8	15.3	38.3	19.8	58.7
0114	28.7	46.8	19.0	55.2	8.9	49.2	9.9	49.6	19.9	55.6
0115	-0.1	21.5	-8.9	27.4	12.2	51.4	-5.0	59.9	16.8	78.8
0116	-2.9	40.2	3.7	80.9	7.5	62.3	31.2	60.0	37.3	54.7
0117	28.2	42.3	30.5	57.2	13.4	28.6	9.6	29.9	12.5	23.8
0118	-0.7	55.7	-4.2	37.7	18.1	56.9	36.3	56.8	27.5	41.8
0119	-0.6	47.0	23.3	62.3	10.0	50.6	30.6	50.0	15.0	37.6
0120	20.2	37.6	21.7	53.2	37.1	65.4	18.7	57.7	-5.0	37.8

TABLE 110. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, COMPOSITE MISSION, A TYPICAL FIGHTER (CONT)

Test M-90 $\sigma_{lim} = 20$ ksi, M-91 $\sigma_{lim} = 30$ ksi, M-92 $\sigma_{lim} = 40$ ksi

0121	24.6	42.7	1.6	40.1	13.4	62.1	4.4	52.7	2.6	68.3
0122	6.2	34.7	-0.9	38.9	24.2	59.2	2.4	47.6	12.3	36.2
0123	9.1	52.4	2.4	16.6	-5.1	56.3	35.8	53.2	1.7	52.1
0124	35.6	70.2	28.3	40.0	25.2	44.2	20.9	35.2	17.6	37.4
0125	26.4	53.7	20.7	34.3	8.1	45.5	34.6	48.7	23.4	84.7
0126	-5.0	62.4	21.1	54.4	30.2	60.1	5.8	35.7	14.5	60.4
0127	23.2	48.4	14.9	49.7	5.5	68.3	42.8	54.4	24.5	48.8
0128	23.6	42.7	5.8	43.6	26.00	74.2	12.6	34.2	23.3	37.5
0129	24.4	36.4	26.5	55.5	22.5	66.8	52.5	65.0	23.9	56.2
0130	12.7	61.0	27.4	53.4	13.3	37.9	20.5	33.2	22.8	40.3
0131	25.7	62.8	-5.0	53.4	21.5	67.4	24.8	48.5	6.9	31.1
0132	18.1	41.4	14.8	27.1	10.4	61.2	8.5	53.4	3.1	27.7
0133	15.0	44.5	14.9	66.4	35.8	59.1	30.2	71.3	24.0	76.1
0134	28.3	52.1	14.8	69.1	40.5	73.0	8.4	56.3	22.9	37.6
0135	17.2	60.1	6.2	36.5	16.9	57.2	10.1	42.2	21.2	67.9
0136	5.3	63.4	34.3	47.4	-5.0	52.4	21.4	57.5	17.5	38.7
0137	10.0	56.2	26.1	45.5	27.4	60.4	25.5	41.8	19.7	56.9
0138	24.4	37.0	24.6	47.5	17.2	92.5	5.3	44.1	5.4	20.5
0139	-0.3	57.7	26.0	39.8	5.5	23.4	3.2	42.6	-1.9	57.6
0140	42.5	62.9	19.4	74.2	13.4	46.8	23.2	52.5	26.4	37.2
0141	9.1	35.4	22.0	69.2	32.4	54.8	-5.0	54.0	14.5	53.6
0142	12.8	38.4	21.4	53.7	28.6	49.5	39.2	60.6	26.1	52.9
0143	6.7	61.4	21.5	43.1	19.7	31.6	4.8	24.1	-11.9	47.8
0144	14.6	34.3	10.4	35.8	10.2	21.6	9.0	41.6	12.7	51.6
0145	10.1	36.5	16.7	54.3	35.0	73.8	34.4	71.1	38.3	52.0
0146	20.9	58.5	28.7	40.7	24.4	44.6	28.0	48.0	-5.0	62.3
0147	45.4	74.7	33.0	46.3	21.4	53.4	8.9	45.9	-3.5	48.8
0148	15.6	58.4	32.2	40.8	9.6	48.7	15.3	26.4	3.0	57.5
0149	15.4	31.7	15.3	41.5	7.9	27.7	14.7	71.6	6.4	24.7
0150	3.0	54.2	-0.8	46.7	11.5	34.2	-2.9	32.1	-0.3	47.9
0151	3.1	31.1	9.6	55.2	5.7	50.7	27.8	38.6	9.6	63.1
0152	-5.0	49.0	31.0	61.7	43.5	65.7	6.3	47.8	23.1	71.9
0153	10.0	76.6	22.7	38.0	5.2	31.1	17.5	70.8	35.3	61.6
0154	26.8	56.5	7.2	54.9	17.4	30.1	9.2	19.9	5.9	17.9
0155	6.2	65.2	-1.9	76.0	5.9	55.9	13.8	63.4	37.4	59.9
0156	33.4	45.6	23.8	50.1	21.7	54.7	12.2	46.3	32.0	44.1
0157	6.6	70.8	-5.0	46.4	23.9	45.7	20.3	52.5	6.2	35.3
0158	20.3	61.0	8.1	47.5	20.7	41.5	16.8	34.2	6.3	84.1
0159	25.8	47.9	30.3	59.6	20.5	64.6	38.3	55.0	27.8	43.2
0160	26.0	62.8	17.1	40.1	17.0	30.6	12.8	65.8	9.5	54.6
0161	34.4	67.6	-4.2	60.6	0.9	63.5	12.8	37.9	7.7	69.5
0162	10.7	42.4	25.9	42.1	-5.0	54.1	24.7	66.4	23.2	49.9
0163	12.4	34.5	23.5	50.5	25.5	44.1	22.4	45.7	26.1	74.2
0164	39.4	61.1	28.2	45.7	18.3	53.7	20.6	54.1	32.1	67.6
0165	23.4	62.3	28.4	80.2	19.1	48.7	29.4	55.9	19.7	79.2
0166	11.2	63.8	21.7	48.2	20.9	71.9	33.9	63.3	34.9	52.7
0167	29.8	60.6	10.7	65.8	17.5	64.9	-5.0	41.7	11.3	34.0
0168	3.7	49.4	6.3	47.2	18.4	63.4	1.1	15.5	9.0	46.6
0169	3.6	68.2	0.7	66.1	16.9	43.4	12.6	28.2	3.7	45.9
0170	5.8	49.5	10.8	35.5	16.7	44.8	3.4	34.2	1.0	16.6
0171	5.1	53.0	3.8	49.8	4.6	34.8	-10.0	60.2	8.6	19.7
0172	6.2	33.4	2.9	44.4	19.5	40.1	-1.2	37.2	0.8	40.0
0173	22.3	58.4	23.3	46.6	1.7	34.0	3.0	28.2	11.0	38.3
0174	-1.7	12.3	0.8	33.7	-10.0	30.6	5.0	27.0	0.4	39.0
0175	12.2	45.2	10.1	29.5	2.4	38.9	16.8	31.7	-0.0	16.9
0176	6.5	19.8	-0.0	53.7	0.9	25.0	10.8	28.7	2.2	32.1
0177	0.1	44.5	-4.5	29.5	5.8	21.5	5.2	21.5	5.4	46.0
0178	4.6	28.3	9.3	61.0	19.3	44.9	8.9	33.0	9.4	24.7
0179	12.3	38.7	-10.0	28.5	15.8	35.7	1.2	27.9	8.8	50.4
0180	21.5	31.8	7.7	46.4	14.3	46.1	3.4	32.2	0.3	37.9
0181	-0.8	24.9	14.0	43.8	10.2	37.5	7.9	36.1	0.9	67.2

TABLE 110. METHODOLOGY DEVELOPMENT TEST PROGRAM GROUP V - RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST, COMPOSITE MISSION, A TYPICAL FIGHTER (CONCL)

Test M-90 σ_{lim} = 20 ksi, M-91 σ_{lim} = 30 ksi, M-92 σ_{lim} = 40 ksi

0182	13.9	51.4	4.0	25.9	15.2	54.6	7.7	54.2	0.5	64.2
0183	-10.0	68.4	2.5	35.4	13.6	42.3	15.1	27.0	6.1	30.1
0184	11.9	33.9	7.6	38.4	7.3	24.5	11.9	39.9	8.4	54.6
0185	25.4	74.1	-0.3	60.3	21.8	44.7	7.6	43.6	2.5	36.1
0186	20.4	60.9	0.0	34.3	19.3	41.3	27.0	37.	-10.0	24.5
0187	2.0	31.5	0.2	57.5	9.4	41.5	7.9	46.4	5.1	19.0
0188	0.4	37.8	27.0	40.1	6.0	21.9	6.4	28.4	11.2	34.7
0189	0.3	42.2	8.2	40.7	17.5	40.7	0.3	41.1	19.1	49.3
0190	11.9	24.8	12.3	42.9	0.7	23.8	-10.0	45.0	18.3	62.5
0191	2.2	40.2	14.0	34.1	3.2	52.3	4.0	24.4	11.9	48.6
0192	-3.0	34.7	23.2	38.9	4.5	25.3	10.1	25.0	7.4	21.2
0193	-0.1	31.6	0.9	18.9	1.4	36.4	-0.0	32.5	4.9	35.9
0194	7.1	33.5	2.0	34.9	-10.0	28.4	13.1	36.3	10.8	58.1
0195	34.6	49.6	1.9	28.3	7.3	35.7	8.3	50.6	13.3	57.1
0196	8.3	54.5	14.2	36.6	14.2	39.5	21.6	41.5	10.5	48.9
0197	9.5	41.6	19.7	47.7	11.3	59.0	6.1	51.4	10.7	28.5
0198	3.7	57.1	-10.0	30.4	11.7	41.0	8.3	23.2	0.7	24.9
0199	-0.1	49.3	8.4	24.5	0.5	30.6	12.4	33.0	16.2	40.0
0200	14.4	62.4	3.6	31.9	0.1	49.6	2.2	29.4	0.8	44.6
0201	3.7	46.6	0.2	58.4	9.1	44.5	9.4	25.8	10.5	31.7
0202	-10.0	20.5	8.3	44.4	22.2	34.1	16.6	38.9	0.0	78.4
0203	-0.7	25.1	-2.0	63.6	3.5	62.1	15.4	27.9	12.2	31.0
0204	16.7	40.8	20.9	41.0	11.2	20.5	12.7	23.8	12.2	35.6
0205	2.4	49.4	5.3	46.9	5.4	29.2	7.8	35.1	-10.0	26.7
0206	9.0	49.3	15.3	41.5	5.0	46.0	1.6	43.3	0.5	45.7
0207	5.0	47.8	12.0	26.2	-0.4	16.9	-2.3	31.1	10.4	38.6
0208	5.6	47.6	4.0	70.0	-1.7	35.5	0.2	27.0	16.4	70.0
0209	0.0	34.9	18.4	52.3	9.1	49.6	-10.0	40.3	8.4	30.4
0210	14.7	32.4	17.9	29.0	11.7	23.8	7.1	29.0	-5.0	34.1
0211	15.3	44.5	11.8	35.8	8.2	25.8	6.3	24.5	13.2	28.6
0212	-5.0	24.6	11.5	20.1	8.8	30.0	14.4	26.2	15.3	29.7

TABLE III. DATA TABULATION FOR TEST M-90

SPE CIMEN NO.:	CCT	SPECIMEN	B= 0.250 IN.	W = 6.000 IN.	AN = 0.0 IN.	P MIN	PHMAX	ENVIRONMENT CONDITION: AMBIENT AIR								
								NU.	CYCLES	AIM MEASURED	AIR FGRESSIGNAL	MULT.	CORR.	COEFF	K-MAX	DFLIAK
TEST FREQ= 6.000MHz.																
1	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16
22618.	0.305	0.345	0.385	0.425	0.470	0.515	0.565	0.595	0.635	0.675	0.750	0.795	0.845	0.910	0.975	1.055
41134.	0.341	0.390	0.423	0.469	0.519	0.558	0.603	0.632	0.670	0.693	0.760	0.784	0.849	0.912	0.972	1.050
51136.	0.390	0.423	0.469	0.519	0.558	0.603	0.632	0.670	0.693	0.760	0.784	0.849	0.912	0.972	1.050	1.123
63116.	0.423	0.469	0.519	0.558	0.603	0.632	0.670	0.708	0.736	0.795	0.845	0.904	0.963	1.022	1.081	1.140
73981.	0.469	0.519	0.558	0.603	0.632	0.670	0.708	0.736	0.765	0.824	0.873	0.932	0.991	1.050	1.109	1.168
82165.	0.519	0.558	0.603	0.632	0.670	0.708	0.736	0.765	0.794	0.853	0.902	0.961	1.020	1.079	1.138	1.197
90240.	0.558	0.603	0.632	0.670	0.708	0.736	0.765	0.794	0.823	0.882	0.931	0.989	1.048	1.107	1.166	1.225
95490.	0.595	0.632	0.670	0.708	0.736	0.765	0.794	0.823	0.852	0.911	0.960	1.019	1.078	1.137	1.196	1.255
104687.	0.632	0.670	0.708	0.736	0.765	0.794	0.823	0.852	0.881	0.940	0.989	1.048	1.107	1.166	1.225	1.284
113091.	0.670	0.708	0.736	0.765	0.794	0.823	0.852	0.881	0.910	0.969	1.018	1.077	1.136	1.195	1.254	1.313
116050.	0.708	0.736	0.765	0.794	0.823	0.852	0.881	0.910	0.939	0.988	1.037	1.096	1.155	1.214	1.273	1.332
123106.	0.736	0.765	0.794	0.823	0.852	0.881	0.910	0.939	0.968	1.017	1.066	1.125	1.184	1.243	1.302	1.361
128997.	0.765	0.823	0.852	0.881	0.910	0.939	0.968	0.997	1.026	1.075	1.124	1.183	1.242	1.301	1.360	1.419
135098.	0.794	0.852	0.881	0.910	0.939	0.968	0.997	1.026	1.055	1.104	1.153	1.212	1.271	1.330	1.389	1.448
141450.	0.823	0.852	0.881	0.910	0.939	0.968	0.997	1.026	1.055	1.104	1.153	1.212	1.271	1.330	1.389	1.448
147371.	0.852	0.881	0.910	0.939	0.968	0.997	1.026	1.055	1.084	1.133	1.182	1.241	1.300	1.359	1.418	1.477
152591.	0.881	0.910	0.939	0.968	0.997	1.026	1.055	1.084	1.113	1.162	1.211	1.270	1.329	1.388	1.447	1.506
157346.	0.910	0.939	0.968	0.997	1.026	1.055	1.084	1.113	1.142	1.191	1.240	1.299	1.358	1.417	1.476	1.535
163955.	0.939	0.968	0.997	1.026	1.055	1.084	1.113	1.142	1.171	1.220	1.269	1.328	1.387	1.446	1.505	1.564
168015.	0.968	0.997	1.026	1.055	1.084	1.113	1.142	1.171	1.200	1.249	1.288	1.347	1.406	1.465	1.524	1.583
173273.	0.997	1.026	1.055	1.084	1.113	1.142	1.171	1.200	1.229	1.268	1.307	1.366	1.425	1.484	1.543	1.602
177311.	1.025	1.055	1.084	1.113	1.142	1.171	1.200	1.229	1.258	1.297	1.336	1.395	1.454	1.513	1.572	1.631
182356.	1.055	1.084	1.113	1.142	1.171	1.200	1.229	1.258	1.287	1.326	1.365	1.424	1.483	1.542	1.601	1.660
186635.	1.084	1.113	1.142	1.171	1.200	1.229	1.258	1.287	1.316	1.355	1.394	1.453	1.512	1.571	1.630	1.689
190676.	1.113	1.142	1.171	1.200	1.229	1.258	1.287	1.316	1.345	1.384	1.423	1.482	1.541	1.600	1.659	1.718
193932.	1.142	1.171	1.200	1.229	1.258	1.287	1.316	1.345	1.374	1.413	1.452	1.511	1.570	1.629	1.688	1.747
196674.	1.171	1.200	1.229	1.258	1.287	1.316	1.345	1.374	1.403	1.442	1.481	1.540	1.6	1.669	1.728	1.787

TABLE III. DATA TABULATION FOR TEST M-90 (CONCL)

SPECIMEN NO.: M-90 RANDOM SPECTRUM, TYPICAL FIGHTER COMPOSITE MISSION, LIMIT STRESS = 20 KSI

CCT SPECIMEN B= 0.250 IN. W= 6.000 IN. AN= 0.0 IN.
 ρ_{MAX}
 ρ_{MIN}

TEST FREQ= 6.000HZ.

ENVIRONMENT CONDITION: AMBIENT AIR

NO-	CYCLES	AI(MEASURED)	AIRREGRESSION(1)	MULT. CORR. COEFF	K-MAX	DATA/DN
29	199493.	2.225	2.223	0.998575	22.37	1.891F-05
30	201859.	2.305	2.312	0.999333	23.51	28.87
31	204342.	2.415	2.417	0.999649	24.27	79.67
32	206624.	2.535	2.528	0.999626	25.13	30.64
33	208293.	2.615	2.617	0.998680	25.77	2.317F-05
34	210233.	2.710	2.726	0.998561	26.64	2.556E-05
35	211948.	2.830	2.838	0.998495	27.57	32.52
36	213598.	2.973	2.977	0.997011	28.63	34.73
37	214531.	3.050	3.060	0.997454	29.60	36.14
38	215428.	3.160	3.172	0.997893	30.47	4.80AF-05
39	215979.	3.250	3.249	0.999997	31.13	5.931F-05
40	216555.	3.355	3.353	0.996515	32.14	3.215E-05
41	214980.	3.440	3.440	0.994172	33.32	34.73
42	217477.	3.545	3.579	0.956589	34.51	36.14
43	217700.	3.645	3.655	0.955049	35.41	44.70
44	217982.	3.755	3.854	0.965366	37.83	3.023F-04
45	218068.	3.945	3.930	0.973865	38.81	47.71
46	216151.	4.060	4.064	0.987464	40.71	48.98
					51.39	6.892F-04
						1.064F-03

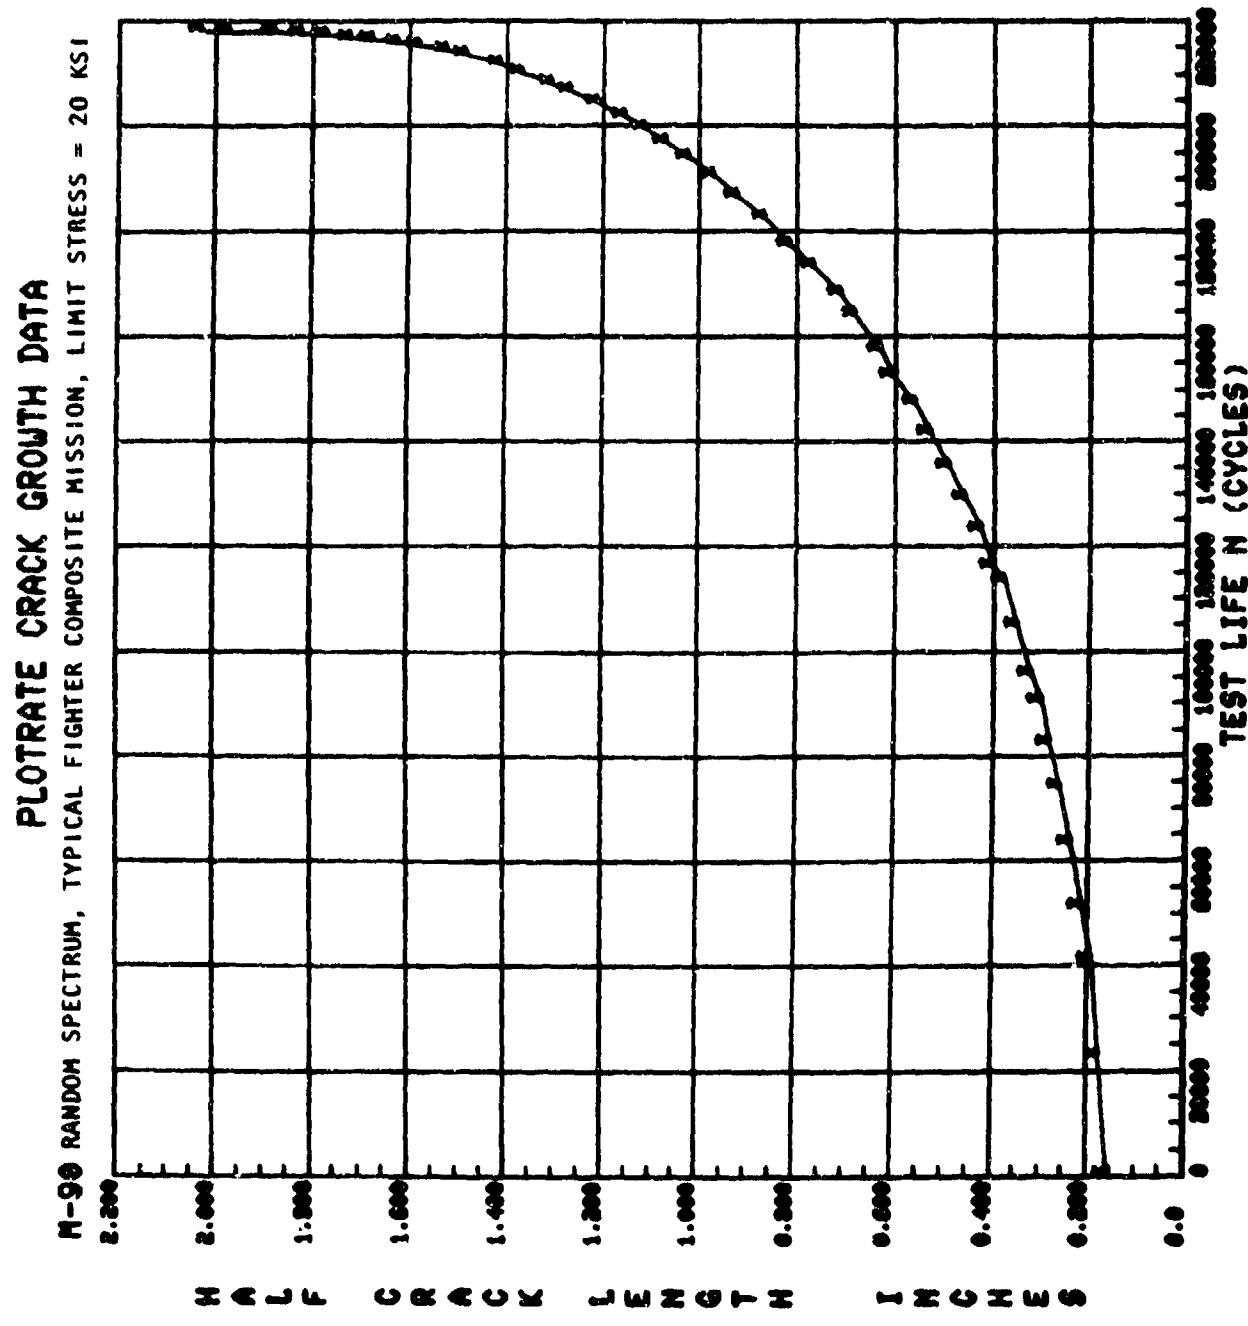


Figure 108. Crack growth curve for test M-90.

TABLE 112. DATA TABULATION FOR TEST M-91
 RANDOM SPECTRUM, TYPICAL FIGHTER COMPOSITE MISSION, LIMIT STRESS = 30 KSI

SPECIMEN NO.: M-91	CCT SPECIMEN	B= 0.25G IN.	A= 6.000 IN.	AN= 0.0	IN.	PHASE	TEST FREQU= 6.000HZ.	X-MAX	DELTIA X	Y/A/UN
ENVIRONMENT CONDITION: AMBIENT AIR	NO.	CYCLES	(MEASURD)	AIREGRESSION)	MULT.	CORR.	COEFF	X-MAX	DELTIA X	Y/A/UN
	1	0.	0.300	0.300	0.999497	1.1.26	1.4.22	2.532E-06		
	2	6647.	0.350	0.348	0.997970	1.2.46	15.72	3.203E-06		
	3	14667.	0.400	0.395	0.997967	13.26	16.75	4.656E-06		
	4	20724.	0.450	0.459	0.998263	14.33	15.06	6.061E-06		
	5	26304.	0.500	0.531	0.998890	15.44	19.48	7.245E-06		
	6	30212.	0.550	0.591	0.999031	16.31	20.57	8.165E-06		
	7	73612.	0.655	0.653	0.999765	17.15	21.66	9.002E-06		
	8	38981.	0.750	0.753	0.998507	18.67	23.30	1.051E-05		
	9	42146.	0.870	0.820	0.998348	19.30	24.35	1.222E-05		
	10	44881.	0.880	0.868	0.999212	20.13	25.40	1.393E-05		
	11	46642.	0.941	0.943	0.998754	20.78	26.21	1.577E-05		
	12	48773.	1.010	1.006	0.996963	21.50	27.13	1.753E-05		
	13	51086.	1.085	1.093	0.999021	22.49	29.57	2.069E-05		
	14	52549.	1.160	1.155	0.999154	23.17	29.23	2.143E-05		
	15	54191.	1.225	1.226	0.998759	23.94	30.20	2.371E-05		
	16	55656.	1.300	1.299	0.998624	24.72	31.19	2.510E-05		
	17	56764.	1.350	1.356	0.998499	25.32	31.54	2.671E-05		
	18	57388.	1.395	1.391	0.998963	26.69	32.42	3.182E-05		
	19	58368.	1.450	1.456	0.997918	26.37	33.26	3.541E-05		
	20	59144.	1.510	1.513	0.997546	26.96	34.02	4.020E-05		
	21	594416.	1.545	1.533	0.996534	27.37	34.27	4.143E-05		
	22	60817.	1.655	1.661	0.998158	28.46	35.93	5.337E-05		
	23	61615.	1.750	1.746	0.996952	29.36	37.64	6.340E-05		
	24	62452.	1.855	1.860	0.997325	30.53	36.51	6.950E-05		
	25	63089.	1.960	1.966	0.996145	31.61	39.28	9.414E-05		
	26	63662.	2.070	2.078	0.996565	32.78	41.35	1.114E-04		
	27	64133.	2.205	2.189	0.985446	33.94	42.62	1.402E-04		
	28	64365.	2.290	2.317	0.977759	35.32	46.56	1.553E-04		

TABLE 112. DATA TABULATION FOR TEST M-91 (CONCL)

RANDOM SPECTRUM. TYPICAL FIGHTER COMPOSITE MISSION. LIMIT STRESS = 30 MSI

SPECIMEN NO. : M-51

PHINE = PHMAX TEST FREQU = 6.0000Hz.

ENVIRONMENTAL MONITORING: A PRACTICAL APPROACH

NO.	CYCLES	A(MEASURED)	A(REFLECTION)	MULT. CORR. COEFF	K-MAX	DELTA K	DABIN
24	65000.	2.435	2.490	0.979210	37.21	46.95	2.366E-04
30	65097.	2.550	2.530	0.980642	37.64	47.52	2.561E-04
31	65173.	2.625	2.578	0.979273	38.21	48.20	2.710E-04
32	65479.	2.725	2.777	0.976385	40.54	51.14	2.344E-04
33	65627.	2.845	2.843	0.985645	41.34	52.15	3.299E-04

304

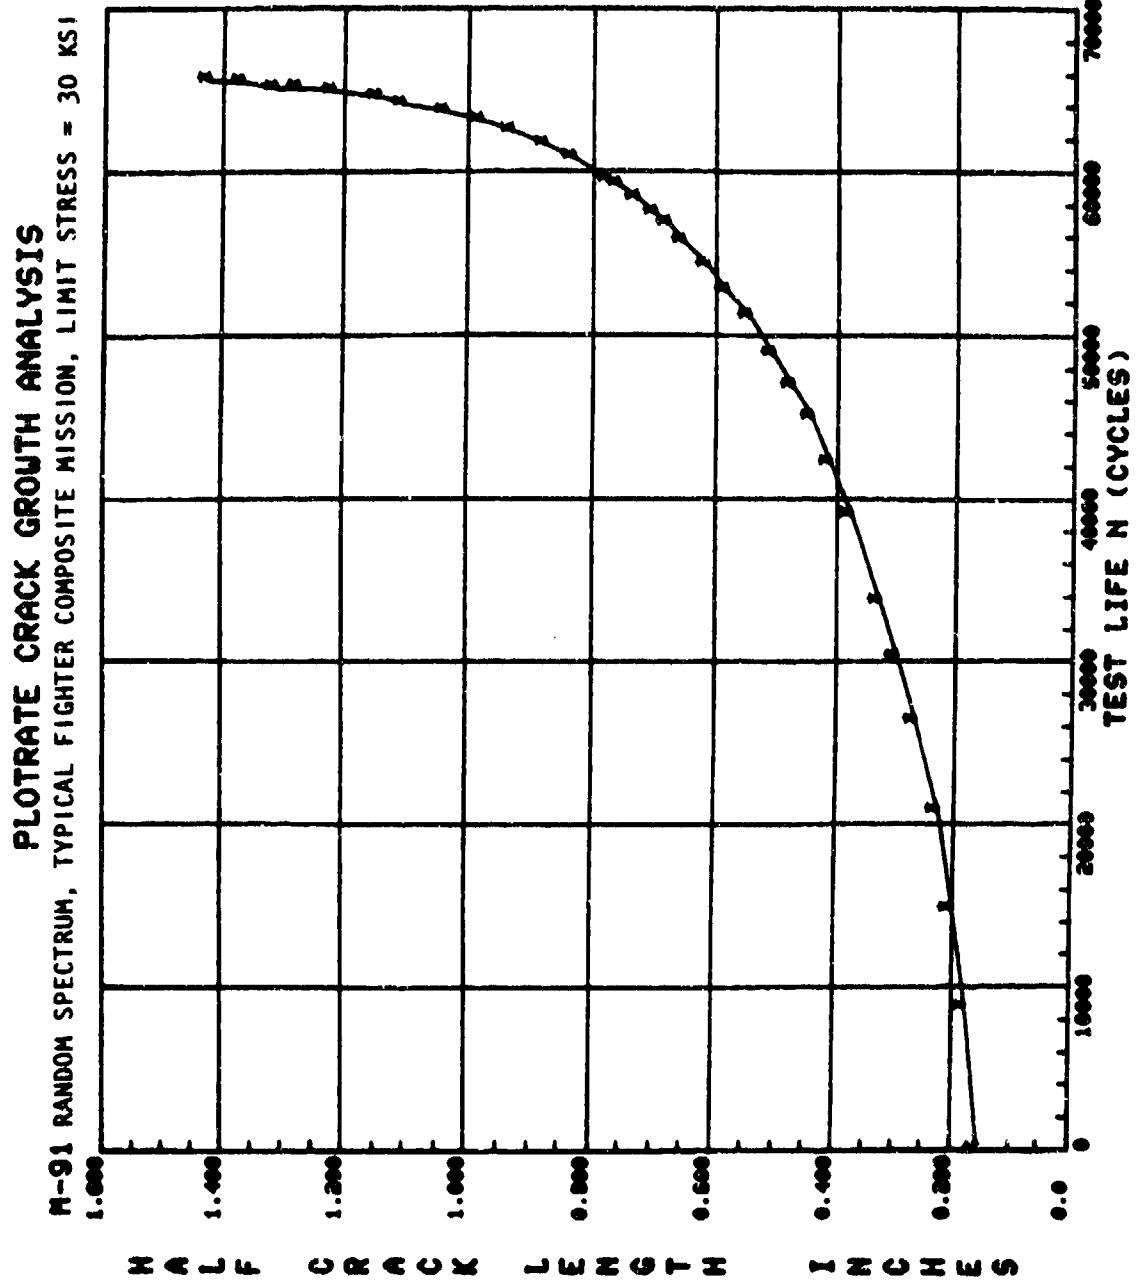


Figure 109. Crack growth curve for test M-91.

TABLE 113. DATA TABULATION FOR TEST M-92
 SPECIMEN NO.: M-92 RANDOM SPECTRUM, TYPICAL FIGHTER COMPOSITE MISSION, LIMIT STRESS = 40 KSI

CCT	SPECIMEN	B = 0.250 IN.	b = 6.000 IN.	A _N = 0.0 IN.	TEST FREQ = 6.00 Hz.
P <small>MIN</small>	P <small>MAX</small>	ENVIRONMENT CONDITION: AMBIENT AIR			
NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR. COEFF	K-MAX
1	0.	0.300	0.300	0.999148	15.42
2	4116.	0.360	0.362	0.999393	16.95
3	6043.	0.405	0.402	0.999562	17.86
4	7931.	0.445	0.447	0.999554	18.86
5	9115.	0.480	0.479	0.999436	19.53
6	10839.	0.530	0.528	0.999498	20.52
7	12486.	0.580	0.582	0.992164	21.56
8	13381.	0.615	0.619	0.992699	22.25
9	14463.	0.660	0.665	0.985360	23.15
10	15244.	0.725	0.714	0.985110	23.94
11	16387.	0.765	0.785	0.982067	25.16
12	16576.	0.815	0.797	0.981602	25.36
13	17734.	0.870	0.884	0.985312	26.77
14	17973.	0.915	0.907	0.985044	27.14
15	18662.	0.975	0.973	0.993635	28.17
16	18974.	1.015	1.013	0.993987	31.74
17	19421.	1.060	1.067	0.998459	31.99
18	19687.	1.110	1.107	0.997491	33.77
19	20003.	1.155	1.154	0.992929	34.23
20	20306.	1.210	1.207	0.985605	35.54
21	20653.	1.260	1.281	0.987375	36.30
22	20800.	1.320	1.317	0.987021	37.34
23	20902.	1.365	1.344	0.986520	38.08
24	21151.	1.410	1.420	0.990810	38.94
25	21269.	1.455	1.436	0.917912	39.92
26	21425.	1.510	1.497	0.938292	41.26
27	21733.	1.635	1.750	0.946027	45.07
28	21826.	1.915	1.857	0.955927	51.46

TABLE 113. DATA TABULATION FOR TEST M-92 (CONCL.)

SPECIMEN NO.: M-92 RANDOM SPECTRUM, TYP. FIGHTER COMPOSITE MISSION, LIMIT STRESS = 40 KSI

CCT SPECIMEN B = 0.250 IN. b = 6.000 IN. AN = 0.0 IN.

P_{MIN} = P_{MAX} =

ENVIRONMENT CONDITION: AMBIENT AIR TEST FREQ = 6.00 Hz.

NO.	CYCLES	A(MEASURED)	A(REGRESSION)	MULT. CORR. COEFF	K-MAX	DELTA X	DA/DN
29	21897.	2.035	1.946	0.953953	41.88	52.84	6.041E-04
30	22043.	2.110	2.194	0.967804	45.33	57.19	5.588E-04
31	22182.	2.325	2.323	0.982004	47.17	59.51	7.398E-04

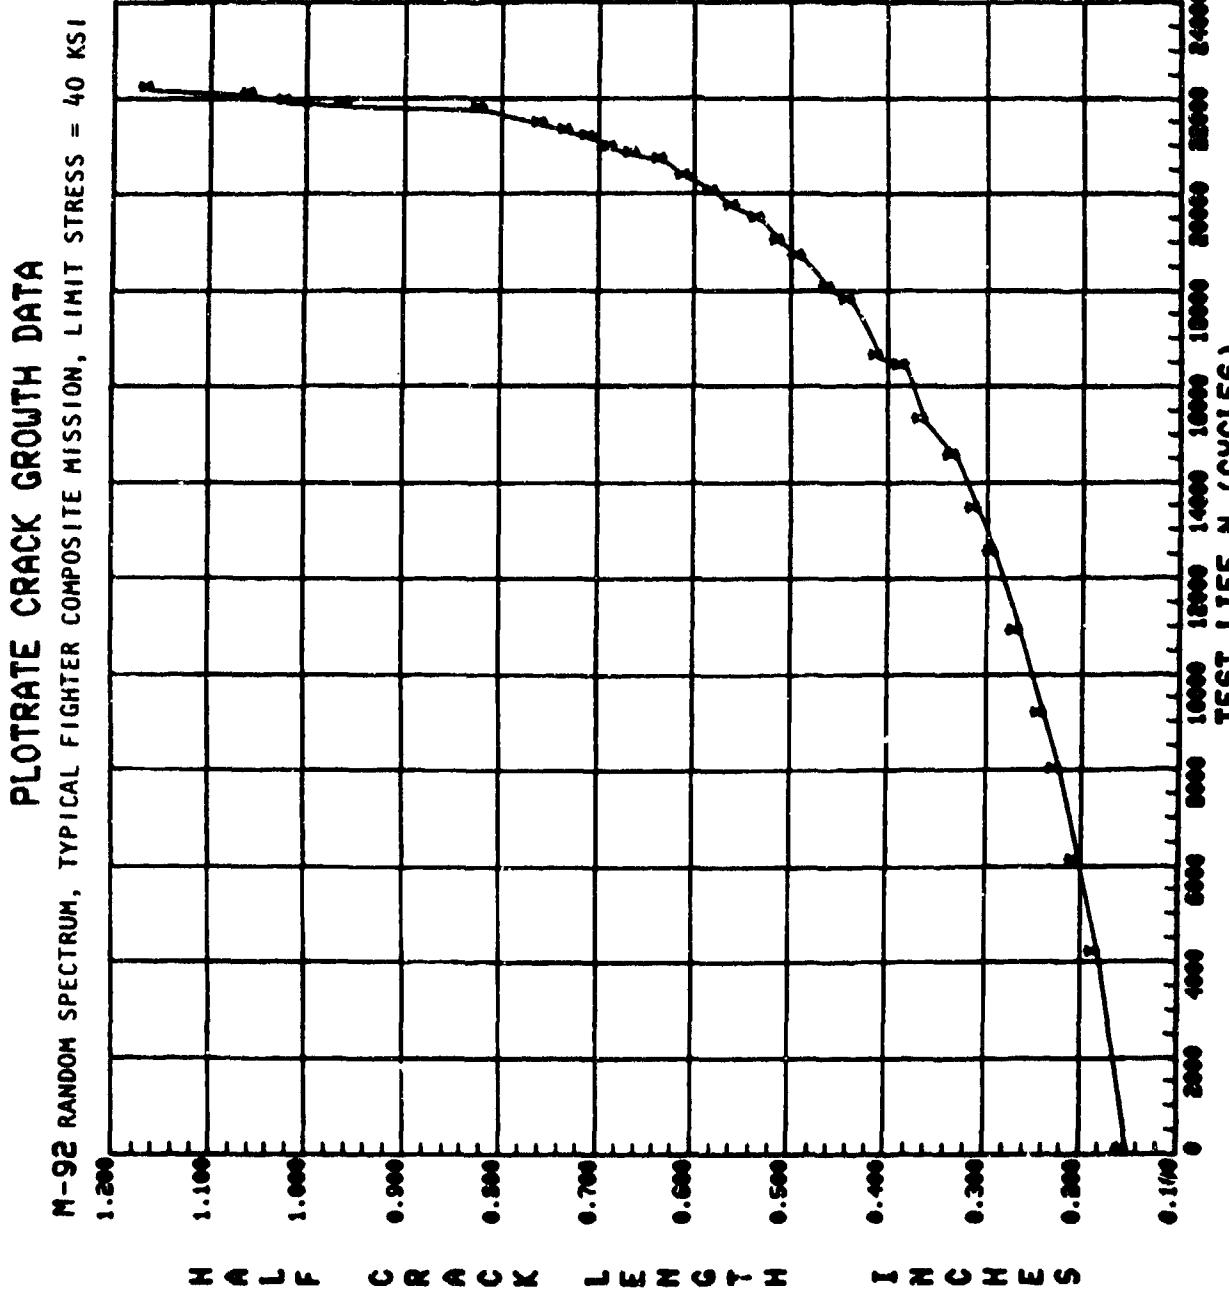


Figure 110. Crack growth curve for test M-92.

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
COMPOSITE MISSION, TYPICAL TRANSPORT

Test M-93: This table as shown
M-94: 1.4 factor on this table

Line	Stresses in KSI										
001	6.0	-6.4	10.8	10.7	10.9	10.8	10.8	10.3	12.5	8.4	
	12.0	9.8	11.3	10.3	11.1	10.7	10.8	10.7	10.8	10.8	
	10.8	10.7	11.2	9.3	12.2	10.2	10.9	10.5	11.4	10.5	
	11.5	9.6	11.3	10.3	11.5	9.9	11.2	10.7	11.0	10.0	
	11.4	10.7	10.7	10.7	11.1	10.7	10.8	10.7	10.8	10.7	
	10.9	10.7	10.9	10.4	11.3	10.5	10.9	10.5	11.3	10.4	
	11.0	10.1	12.5	8.6	12.3	10.1	11.0	10.6	10.8	10.6	
	11.0	10.7	10.8	10.8	11.0	10.5	11.1	10.8	10.8	10.7	
	11.3	10.0	11.2	10.6	11.3	9.8	11.7	9.9	11.9	10.1	
010	10.8	10.8	11.0	10.2	11.5	10.3	11.1	10.8	10.8	10.8	
	10.8	10.8	10.8	10.4	12.2	9.2	11.6	10.7	10.8	10.7	
	11.0	10.6	11.0	10.7	10.8	10.8	10.9	10.7	10.8	10.7	
	11.4	9.2	12.2	10.3	10.9	10.6	11.1	10.4	11.5	9.1	
	9.8	9.0	9.1	9.0	9.2	9.1	9.1	8.7	10.7	8.8	
	10.8	8.2	9.6	8.7	9.4	9.0	9.1	9.0	9.1	9.0	
	9.1	9.0	9.4	7.7	10.4	8.5	9.2	8.9	9.6	8.8	
	9.5	9.0	9.0	9.0	9.0	9.0	9.0	8.8	10.2	7.2	
	10.4	8.4	9.3	8.7	9.2	8.9	9.0	9.0	9.0	9.0	
	9.0	9.0	9.2	8.0	10.0	8.6	9.0	8.9	9.4	8.9	
020	9.4	8.2	9.4	8.8	9.4	8.4	9.2	9.0	9.1	8.5	
	9.4	9.0	9.0	9.0	9.1	9.0	9.0	9.0	9.0	9.0	
	11.4	10.6	10.6	10.5	10.7	10.6	10.6	10.2	12.3	8.3	
	12.5	9.7	11.2	10.2	10.9	10.5	10.7	10.8	10.7	10.6	
	10.6	10.6	11.0	9.2	12.0	10.0	10.7	10.4	11.2	10.4	
	11.3	9.5	11.3	10.2	11.3	9.7	11.0	10.6	10.8	9.8	
	11.2	10.5	10.6	10.5	10.9	10.5	10.7	10.6	10.6	10.5	
	10.7	10.6	10.7	10.3	11.1	10.4	10.7	10.4	11.1	10.2	
	10.9	9.9	12.3	8.5	12.1	10.0	10.8	10.6	10.6	10.5	
030	10.9	10.6	10.6	10.6	10.9	10.3	10.9	10.5	10.6	10.5	
	11.1	9.8	11.0	10.4	11.1	9.7	11.5	9.8	11.7	-6.4	
	12.9	9.1	11.5	10.6	10.8	10.7	10.8	10.8	10.8	10.7	
	11.2	9.8	12.4	9.5	11.2	10.6	11.1	10.4	10.9	10.2	
	11.2	10.7	10.8	10.7	11.3	10.1	11.2	10.6	10.9	10.7	
	11.2	10.2	11.2	10.5	11.0	10.6	11.3	9.4	12.7	9.1	
	11.3	10.9	11.0	10.6	11.0	10.6	10.9	10.7	10.6	10.6	
	11.1	10.7	10.8	10.7	11.4	10.1	11.0	10.2	12.1	9.5	
	11.6	10.2	11.6	9.9	11.4	9.8	12.1	10.1	10.8	10.8	
	11.0	9.8	12.0	8.5	12.3	10.1	11.8	10.4	11.2	10.8	
040	11.1	10.8	11.1	10.5	11.0	10.7	10.8	10.8	11.0	10.1	
	11.0	9.9	11.1	10.7	10.9	10.6	11.5	9.9	11.7	9.3	
	11.0	10.6	11.0	10.6	11.1	10.2	11.4	10.4	10.9	10.8	
	10.8	10.6	11.2	10.3	11.2	10.5	10.9	10.8	10.8	10.6	

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
 RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
 COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
 M-94: 1.4 factor on this table

Line	Stresses in KSI									
	9.7	9.0	9.7	9.7	9.7	9.3	9.5	9.0	9.3	9.3
	9.6	9.0	9.0	9.0	9.3	9.0	9.1	9.0	9.1	9.0
	9.1	9.0	9.2	8.8	9.5	8.8	9.2	8.9	9.5	8.7
	9.0	9.0	9.1	8.8	9.3	8.9	9.0	8.9	9.3	8.8
050	9.1	8.6	10.2	7.3	10.0	8.6	9.1	9.0	9.0	8.9
	9.1	9.0	9.0	9.0	9.1	8.8	9.2	8.9	9.0	9.0
	9.3	8.5	9.2	8.9	9.3	8.4	9.6	8.5	9.7	8.6
	9.0	9.0	9.1	8.8	9.4	8.7	9.1	9.0	9.0	9.0
060	10.7	10.6	10.8	10.0	11.3	10.1	10.9	10.6	10.6	10.6
	10.7	10.6	10.6	10.3	12.0	9.1	11.4	10.5	10.6	10.6
	10.8	10.4	10.8	10.8	10.8	10.6	10.7	10.5	10.6	10.6
	11.2	9.1	12.0	10.2	10.7	10.4	11.0	10.3	11.3	9.0
	12.7	9.0	11.3	10.4	10.7	10.6	10.7	10.6	10.6	10.6
	11.0	9.4	12.2	9.5	11.0	10.4	11.0	10.3	10.8	10.1
	11.0	10.5	10.6	10.5	11.1	10.0	11.0	10.4	10.7	10.5
	11.0	10.1	11.0	10.4	10.8	10.4	11.1	9.3	12.5	9.0
	11.3	10.3	10.8	10.9	10.8	10.5	10.7	10.6	10.7	-8.4
	11.3	10.3	11.0	10.8	10.8	10.7	10.9	10.7	10.8	10.4
070	11.8	9.8	11.3	10.7	10.9	10.5	11.6	9.2	12.4	10.1
	11.0	10.8	11.2	10.8	10.8	10.7	11.7	9.4	11.3	10.1
	12.0	10.3	10.9	10.6	11.4	10.2	11.0	10.7	11.0	10.4
	11.0	10.7	10.9	10.7	11.0	10.6	10.9	10.6	10.9	10.7
	11.0	10.3	11.8	10.0	11.1	10.6	11.0	10.5	10.8	10.7
	10.9	10.7	10.9	10.5	11.6	9.9	11.0	10.9	11.0	9.9
	11.6	10.6	10.9	10.3	11.4	10.6	11.3	10.3	11.2	10.5
	10.8	10.8	10.8	10.7	11.8	10.8	10.9	10.1	11.8	10.0
	11.0	10.6	11.6	9.5	11.8	10.5	10.8	10.7	11.2	10.3
	11.1	10.7	10.8	10.8	10.9	10.5	11.2	10.3	10.9	10.7
080	11.1	10.5	10.8	10.8	10.8	10.5	10.6	10.8	10.9	9.8
	12.7	9.1	11.6	10.1	12.2	9.2	11.5	10.8	10.8	9.5
	9.3	8.4	10.7	7.0	10.5	8.5	9.2	9.1	9.1	8.9
	9.3	9.0	9.1	9.1	9.3	8.8	9.4	8.9	9.1	9.0
	9.6	8.3	9.4	8.9	9.5	8.2	9.9	8.3	10.1	8.5
	9.0	9.0	9.0	8.8	9.9	7.9	9.5	9.0	9.0	9.0
	9.1	8.9	9.1	9.0	9.0	9.0	9.0	9.0	9.0	9.0
	9.3	7.9	10.0	8.7	9.0	8.9	9.2	8.8	9.4	7.8
	10.6	7.8	9.4	8.9	9.0	9.0	9.0	9.0	9.0	9.0
	9.2	8.2	10.1	8.2	9.2	8.9	9.2	8.8	9.1	8.7
	10.9	10.5	10.6	10.6	11.2	10.0	10.8	10.0	11.9	9.3
	11.4	10.0	11.4	9.8	11.3	9.6	11.9	10.0	10.6	10.6
	11.8	9.6	12.5	8.4	12.1	10.0	11.0	10.2	11.1	10.2
	10.9	10.3	10.9	10.3	10.8	10.5	10.6	10.6	10.8	10.0
	11.6	9.8	11.0	10.5	10.7	10.4	11.3	9.8	11.5	9.2

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
 RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
 COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown

M-94: 1.4 factor on this table

Line	Stresses in KSI										
	11.7	10.4	10.8	10.4	10.9	10.3	10.8	10.6	10.6	10.5	
	10.9	10.4	10.8	10.5	10.9	10.1	11.2	10.2	10.7	10.6	
	10.7	10.4	11.0	10.1	11.1	10.3	10.8	10.6	10.6	10.5	
090	11.1	10.2	10.8	10.6	10.6	10.5	10.8	10.6	10.7	10.7	-8.9
	7.2	6.5	6.6	6.5	6.6	6.6	6.6	6.2	7.8	4.9	
	7.9	5.9	7.0	6.2	6.8	6.5	6.6	6.5	6.6	6.5	
	6.6	6.5	6.9	5.5	7.6	6.1	6.7	6.4	7.0	6.3	
	7.1	5.7	7.1	6.2	7.1	5.9	6.9	6.5	6.7	5.9	
	7.0	6.5	6.5	6.5	6.8	6.5	6.6	6.5	6.6	6.5	
	6.6	6.5	6.7	6.3	6.9	6.4	6.6	6.4	6.9	6.3	
	8.8	8.0	7.6	5.0	7.6	8.1	6.7	6.6	6.6	6.4	
	6.6	6.5	6.6	6.5	6.7	6.3	6.8	6.4	6.6	6.5	
	6.7	6.1	6.2	6.1	6.2	6.2	6.2	5.9	7.2	4.7	
100	7.4	5.5	6.5	5.9	6.4	6.1	6.2	6.1	6.2	6.1	
	9.2	8.9	9.0	9.0	9.3	8.6	9.2	8.9	9.0	9.0	
	9.2	8.7	9.2	8.9	9.1	8.9	9.3	8.1	10.4	7.8	
	9.4	8.8	9.1	8.9	9.1	8.9	9.0	9.0	9.0	8.9	
	9.1	9.0	9.0	9.0	9.3	8.6	9.1	8.6	9.9	8.1	
	9.5	8.7	9.5	8.4	9.4	8.4	9.9	8.6	9.0	9.0	
	9.1	8.3	10.4	7.3	10.0	8.6	9.2	8.8	9.3	8.8	
	9.2	8.9	9.2	8.8	9.1	9.0	9.0	9.0	9.1	8.6	
	9.6	8.5	9.2	9.0	9.0	8.9	9.4	8.5	9.6	8.0	
	9.7	8.9	9.1	8.9	9.2	8.8	9.1	9.0	9.0	9.0	
110	9.3	8.6	8.7	8.6	8.7	8.6	8.7	8.3	10.1	6.5	
	10.4	7.8	9.1	8.3	8.9	8.5	8.7	8.6	8.7	8.6	
	8.7	8.8	8.9	7.4	10.0	8.1	8.7	8.5	9.2	8.4	
	9.3	7.6	9.2	8.3	9.3	7.8	9.0	8.6	8.8	-8.9	
	7.0	5.9	6.9	6.4	6.9	5.8	7.3	5.9	7.4	6.0	
	5.6	6.6	6.7	6.1	7.1	6.2	6.8	6.5	6.5	6.5	
	6.6	6.6	6.6	6.3	7.6	5.4	7.2	6.5	6.6	6.5	
	6.7	6.4	6.7	6.5	6.6	6.6	6.6	6.5	6.6	6.5	
	7.0	5.4	7.6	6.2	6.7	6.4	6.8	6.3	7.1	5.3	
120	8.1	5.3	7.1	6.4	6.6	6.5	6.6	6.6	6.6	6.5	
	6.9	5.7	7.7	5.7	6.9	6.4	6.8	6.3	6.7	6.1	
	6.9	6.5	6.6	6.5	6.9	6.1	6.9	6.4	6.6	6.5	
	6.2	6.1	6.4	5.2	7.2	5.7	6.2	6.0	6.6	5.9	
	6.7	5.4	6.6	5.9	6.7	5.5	6.4	6.1	6.4	5.6	
	9.1	8.9	9.1	8.9	9.2	8.7	9.3	8.8	9.0	9.0	
	9.0	8.9	9.2	8.7	9.3	8.8	9.1	9.0	9.0	8.9	
	9.3	8.7	9.1	9.0	9.0	9.0	9.1	9.0	9.0	8.8	
	9.7	8.4	9.3	8.9	9.0	8.9	9.5	7.9	10.1	8.6	
	9.1	8.9	9.2	8.9	9.0	9.0	9.6	8.0	9.3	8.6	
	9.8	8.7	9.0	8.9	9.4	8.6	9.1	9.0	9.1	8.8	

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
 RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
 COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
 M-94: 1.4 factor on this table

Line	Stresses in KSI										
	9.1	9.9	9.0	9.0	9.1	9.9	9.0	9.9	9.1	9.0	9.0
130	9.1	9.7	9.6	8.5	9.2	8.9	9.1	8.8	9.1	9.1	9.0
	9.0	9.0	9.0	8.9	9.5	8.4	9.1	9.1	9.1	9.1	9.0
	9.2	8.6	8.6	8.6	8.6	8.6	8.7	8.6	8.7	8.7	8.6
	8.7	8.6	8.5	8.3	9.0	8.5	8.7	8.4	9.0	9.0	8.4
	8.9	7.9	10.3	8.8	9.8	8.2	8.8	8.6	8.7	8.7	8.6
	8.8	8.6	8.6	8.6	8.6	8.4	8.9	8.5	8.7	8.7	-6.4
	11.6	10.7	10.8	10.7	10.9	10.8	10.8	10.3	12.5	8.6	
	12.7	9.8	11.3	10.3	11.1	10.7	10.8	10.7	10.8	10.8	
	10.8	10.7	11.2	9.3	12.2	10.2	10.9	10.5	11.4	10.5	
140	11.5	9.6	11.5	10.3	11.5	9.9	11.2	10.7	11.0	10.0	
	11.4	10.7	10.7	10.7	11.1	10.7	10.8	10.7	10.8	10.7	
	10.9	10.7	10.9	10.4	11.3	10.5	10.9	10.5	11.3	10.4	
	11.0	10.1	12.5	8.6	12.3	10.1	11.0	10.8	10.8	10.8	10.6
	11.0	10.7	10.8	10.8	11.0	10.5	11.1	10.6	10.8	10.7	
	11.3	10.0	11.2	10.6	11.3	9.8	11.7	9.9	11.9	10.1	
	12.6	10.8	11.0	10.2	11.5	10.3	11.1	10.8	10.8	10.8	
	12.8	10.8	10.8	10.4	12.2	9.2	11.6	10.7	10.8	10.7	
	11.0	10.6	11.0	10.7	10.8	10.8	10.9	10.7	10.8	10.7	
	11.4	9.2	12.2	10.3	10.9	10.6	11.1	10.4	11.5	9.1	
150	9.8	9.0	9.1	9.0	9.2	9.1	9.1	8.7	10.7	6.8	
	10.8	8.2	9.6	8.7	9.4	9.0	9.1	9.0	9.1	9.0	
	9.1	9.0	9.4	7.7	10.4	8.5	9.2	8.9	9.6	8.6	
	9.5	9.0	9.0	9.0	9.0	9.0	9.0	8.8	10.2	7.2	
	10.4	8.4	9.3	8.7	9.2	8.9	9.0	9.0	9.0	9.0	
	9.0	9.0	9.2	8.0	10.0	8.6	9.0	8.9	9.6	8.9	
	9.4	8.2	9.4	8.8	9.4	8.4	9.2	9.0	9.1	8.5	
	9.4	9.0	9.0	9.0	9.1	9.0	9.0	9.0	9.0	9.0	
	11.4	10.6	10.6	10.5	10.7	10.6	10.6	10.2	12.3	8.3	
160	12.5	9.7	11.2	10.2	10.9	10.5	10.7	10.6	10.7	10.6	
	10.6	10.6	11.0	9.2	12.0	10.0	10.7	10.4	11.2	10.4	
	11.3	9.5	11.3	10.2	11.3	9.7	11.0	10.6	10.8	9.8	
	11.2	10.4	10.6	10.6	10.9	10.5	10.7	10.6	10.6	10.6	
	10.7	10.6	10.7	10.3	11.1	10.4	10.7	10.4	11.1	10.2	
	10.9	9.9	12.3	8.5	12.1	10.0	10.8	10.6	10.6	10.5	
	10.9	10.6	10.6	10.6	10.9	10.3	10.9	10.5	10.6	10.5	
	11.1	9.8	11.0	10.4	11.1	9.7	11.5	9.8	11.7	-6.4	
	12.9	9.1	11.5	10.6	10.6	10.7	10.6	10.6	10.8	10.7	
	11.2	9.6	12.4	9.6	11.2	10.6	11.1	10.4	10.9	10.2	
	11.2	10.7	10.8	10.7	11.3	10.1	11.2	10.6	10.9	10.7	
170	11.2	10.2	11.2	10.5	11.0	10.6	11.3	9.4	12.7	9.1	
	11.5	10.5	11.0	10.6	11.0	10.6	10.9	10.7	10.8	10.6	
	11.1	10.7	10.8	10.7	11.4	10.1	11.0	10.2	12.1	9.5	

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
 RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
 COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
 M-94: 1.4 factor on this table

Line	Stresses in KSI											
	11.6	10.2	11.6	9.9	11.4	9.8	12.1	10.1	10.8	10.8	10.8	10.8
	11.0	9.8	12.8	8.5	12.3	10.1	11.2	10.4	11.2	10.4	10.4	10.4
	11.1	10.5	11.1	10.5	11.0	10.7	10.8	10.8	11.0	10.1	10.1	10.1
	11.8	9.9	11.1	10.7	10.9	10.6	11.5	9.9	11.7	9.3	9.3	9.3
	11.9	10.6	11.0	10.5	11.1	10.5	11.0	10.8	10.8	10.7	10.7	10.7
	11.0	10.5	11.0	10.6	11.1	10.2	11.4	10.4	10.9	10.8	10.8	10.8
	10.8	10.6	11.2	10.3	11.2	10.5	10.9	10.8	10.8	10.6	10.6	10.6
180	9.7	8.0	9.7	8.7	9.7	8.3	9.5	9.0	9.3	8.3	8.3	8.3
	9.6	9.0	9.0	9.0	9.3	9.0	9.1	9.0	9.1	9.0	9.0	9.0
	9.1	9.0	9.2	8.8	9.5	8.8	9.2	8.9	9.5	8.7	8.7	8.7
	9.0	9.0	9.1	8.8	9.3	8.9	9.0	8.9	9.3	8.8	8.8	8.8
	9.1	8.6	10.2	7.3	10.0	8.6	9.1	9.0	9.0	8.9	8.9	8.9
	9.1	9.0	9.0	9.0	9.1	8.8	9.2	8.9	9.0	9.0	9.0	9.0
	9.3	8.5	9.2	8.9	9.3	8.4	9.6	8.5	9.7	8.6	8.6	8.6
	9.0	9.0	9.1	8.6	9.4	8.7	9.1	9.0	9.0	9.0	9.0	9.0
	10.7	10.6	10.8	10.0	11.3	10.1	10.9	10.6	10.6	10.6	10.6	10.6
190	10.7	10.6	10.6	10.3	12.0	9.1	11.4	10.5	10.6	10.6	10.6	10.6
	10.8	10.4	10.8	10.6	10.6	10.6	10.7	10.5	10.6	10.6	10.6	10.6
	11.2	9.1	12.0	10.2	10.7	10.4	11.0	10.3	11.3	9.0	9.0	9.0
	12.7	9.0	11.3	10.4	10.7	10.6	10.7	10.5	10.6	10.5	10.5	10.5
	11.0	9.4	12.2	9.5	11.0	10.4	11.0	10.3	10.8	10.1	10.1	10.1
	11.0	10.5	10.6	10.5	11.1	10.0	11.0	10.4	10.7	10.5	10.5	10.5
	11.0	10.1	11.0	10.6	10.6	10.6	11.1	9.3	12.9	9.0	9.0	9.0
	11.3	10.3	10.8	10.5	10.8	10.5	10.7	10.6	10.7	10.7	10.7	10.7
	11.3	10.3	11.0	10.8	10.8	10.7	10.9	10.7	10.8	10.4	10.4	10.4
200	11.0	9.8	11.3	10.7	10.9	10.5	11.6	9.2	12.4	10.1	10.1	10.1
	11.0	10.6	11.2	10.6	10.8	10.7	11.7	9.4	11.3	10.4	10.4	10.4
	12.0	10.3	10.9	10.6	11.4	10.2	11.0	10.7	11.0	10.4	10.4	10.4
	11.0	10.7	10.9	10.7	11.0	10.6	10.9	10.5	10.9	10.7	10.7	10.7
	11.0	10.3	11.8	10.0	11.1	10.6	11.0	10.5	10.9	10.7	10.7	10.7
	10.9	10.7	10.9	10.5	11.6	9.9	11.0	10.9	11.0	9.9	9.9	9.9
	11.0	10.8	10.9	10.3	11.4	10.6	11.3	10.3	11.2	10.3	10.3	10.3
	10.8	10.8	10.8	10.7	10.8	10.8	10.9	10.1	11.3	10.0	10.0	10.0
	11.0	10.6	11.6	9.5	11.8	10.5	10.8	10.7	11.2	10.3	10.3	10.3
	11.1	10.7	10.8	10.8	10.9	10.5	11.2	10.3	10.9	10.7	10.7	10.7
	11.1	10.5	10.8	10.8	10.8	10.6	10.8	10.8	10.8	10.4	10.4	10.4
	12.7	9.1	11.6	10.1	12.2	9.2	11.9	10.6	10.6	10.6	10.6	10.6
210	9.3	8.4	10.7	7.0	10.5	8.5	9.2	9.1	9.1	8.7	8.7	8.7
	9.3	9.0	9.1	9.1	9.3	8.8	9.4	8.9	9.1	9.0	9.0	9.0
	9.6	8.3	9.4	8.9	9.5	8.2	9.9	8.3	10.1	8.5	8.5	8.5
	9.0	9.0	9.0	8.8	9.9	7.9	9.9	9.0	9.0	9.0	9.0	9.0
	9.1	8.9	9.1	9.0	9.0	9.0	9.0	9.0	9.0	9.0	9.0	9.0
	9.3	7.9	10.0	8.7	9.0	8.9	9.2	8.8	9.4	7.8	7.8	7.8

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
 RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
 COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
 M-94: 1.4 factor on this table

Line	Stresses in KSI											
	10.6	7.8	9.4	8.9	9.0	9.0	9.0	9.0	9.0	9.0	9.0	9.0
	9.2	6.2	10.1	8.2	9.2	8.8	9.2	8.8	9.1	9.1	8.7	
	10.9	10.8	10.6	10.6	11.2	10.0	10.8	10.0	11.9	9.3		
	11.4	10.0	11.4	9.8	11.3	9.8	11.9	10.0	10.6	10.6	10.6	
220	10.6	9.6	12.5	9.4	12.1	10.0	11.0	10.2	11.1	10.2		
	10.9	10.3	10.9	10.3	10.8	10.5	10.6	10.6	10.8	10.8	10.5	
	11.6	9.8	11.0	10.5	10.7	10.4	11.3	9.8	11.5	9.2		
	11.7	10.4	10.8	10.4	10.4	10.3	10.8	10.8	10.8	10.8	10.7	
	10.9	10.4	10.8	10.5	10.9	10.1	11.2	10.2	10.7	10.6		
	10.7	10.4	11.0	10.1	11.1	10.3	10.8	10.6	10.6	10.6	10.5	
	11.1	10.2	10.8	10.0	10.6	10.5	10.8	10.6	10.7	10.2		
	11.1	10.2	10.8	10.0	10.6	10.5	10.8	10.6	10.7	10.7	-8.9	
	7.2	6.5	6.6	6.5	6.6	6.6	6.6	6.2	7.6	4.9		
230	7.9	5.9	7.0	6.2	6.8	6.5	6.8	6.7	6.8	6.8	6.5	
	6.6	6.5	6.9	5.5	7.6	6.1	6.7	6.4	7.0	6.3		
	7.1	5.7	7.1	6.2	7.1	5.9	6.9	6.5	6.7	5.9		
	7.6	6.5	6.5	6.5	6.8	6.5	6.6	6.5	6.6	6.5		
	6.6	6.5	6.7	6.3	6.9	6.4	6.6	6.4	6.9	6.3		
	6.8	6.0	7.8	5.0	7.6	6.1	6.7	6.6	6.6	6.6	6.4	
	6.8	6.5	6.8	6.3	6.7	6.3	6.8	6.4	6.6	6.5		
	6.7	6.1	6.2	6.1	6.2	6.2	6.2	5.9	7.2	4.7		
	7.4	5.5	6.5	5.9	6.4	6.1	6.2	6.1	6.2	6.1		
240	9.2	8.9	9.0	9.0	9.3	8.6	9.1	8.9	9.0	9.0	9.0	
	9.2	8.7	9.2	9.9	9.1	8.9	9.3	9.1	10.4	7.8		
	9.4	8.8	9.1	9.9	9.1	8.9	9.0	9.0	9.0	9.0	8.9	
	9.1	9.0	9.0	9.0	9.3	9.0	9.1	9.0	9.0	9.0	9.0	
	9.5	8.7	9.5	8.4	9.4	8.4	9.9	8.6	9.0	9.0		
	9.1	8.3	10.4	7.3	10.0	8.6	9.2	8.8	9.3	8.8		
	9.2	8.9	9.2	8.8	9.1	9.0	9.0	9.0	9.1	9.0		
	9.6	8.5	9.2	9.0	9.0	8.9	9.4	8.5	9.6	8.0		
	9.7	8.9	9.1	8.9	9.2	8.8	9.1	9.0	9.0	9.0	9.0	
	9.3	8.8	8.7	8.8	8.7	8.8	8.7	8.5	10.1	8.5		
	10.4	7.8	9.1	8.3	8.9	8.5	8.7	8.4	8.7	8.6		
	8.7	8.6	8.0	7.4	10.0	8.1	8.7	8.5	9.2	8.4		
250	9.3	7.5	9.2	8.3	9.3	7.8	9.0	8.6	8.8	-8.9		
	7.0	5.9	6.9	6.4	6.9	5.8	7.3	5.9	7.4	6.0		
	6.6	6.6	6.7	6.1	7.1	6.2	6.8	6.5	6.5	6.5		
	6.6	6.6	6.6	6.3	7.0	6.4	7.2	6.5	6.5	6.5		
	6.7	6.4	6.7	6.5	6.6	6.6	6.6	6.5	6.6	6.6	6.6	
	7.0	5.4	7.6	6.2	6.7	6.1	6.8	6.3	7.1	5.3		
	8.1	5.3	7.1	6.4	8.0	6.5	6.6	6.6	6.6	6.6	6.5	
	6.9	5.7	7.7	5.7	6.9	6.4	6.8	6.3	6.7	6.1		
	6.9	6.5	6.6	6.5	6.9	6.1	6.9	6.4	6.6	6.5		

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
M-94: 1.4 factor on this table

Line	Stresses in KSI									
	8.8	8.1	8.4	8.2	7.8	8.7	8.2	8.0	8.6	8.9
260	8.7	8.4	8.5	8.9	8.7	8.5	8.6	8.1	8.8	8.8
	8.1	8.9	9.1	8.9	9.2	8.7	9.3	8.8	9.0	9.0
	8.0	8.9	9.2	8.7	9.3	8.8	9.1	8.0	9.0	8.9
	8.3	8.7	8.1	8.0	8.0	8.0	8.1	8.0	8.0	8.5
	8.7	8.4	9.3	8.9	8.0	8.9	8.5	7.9	10.1	8.4
	8.1	8.9	9.2	8.9	9.0	9.0	9.6	8.0	9.3	8.6
	8.6	8.7	9.0	8.9	9.4	8.8	8.1	8.0	8.1	8.6
	8.1	8.9	9.0	9.0	9.1	8.9	9.0	8.9	9.1	9.0
	8.1	8.7	9.6	8.5	9.2	8.9	9.1	8.8	9.1	9.0
	8.0	8.0	8.0	8.0	9.5	8.4	8.1	8.1	8.1	8.4
270	8.2	8.6	8.6	8.6	8.8	8.6	8.7	8.6	8.7	8.6
	8.7	8.6	8.8	8.3	9.0	8.5	8.7	8.4	9.0	8.4
	8.9	7.8	10.3	8.8	9.8	8.2	8.8	8.6	8.7	8.6
	8.8	8.6	8.6	8.6	8.8	8.4	8.9	8.5	8.7	8.4
	11.6	10.7	10.8	10.7	10.9	10.8	10.8	10.3	12.5	8.4
	12.7	9.8	11.3	10.3	11.1	10.7	10.8	10.7	10.8	10.8
	10.8	10.7	11.2	9.3	12.2	10.2	10.9	10.5	11.4	10.5
	11.5	9.6	11.5	10.3	11.5	9.9	11.2	10.7	11.0	10.0
	11.4	10.7	10.7	10.7	11.1	10.7	10.8	10.7	10.8	10.7
280	10.9	10.7	10.9	10.4	11.3	10.5	10.9	10.5	11.3	10.4
	11.0	10.1	12.5	8.6	12.3	10.1	11.0	10.8	10.8	10.6
	11.0	10.7	10.8	10.8	11.0	10.5	11.1	10.8	10.8	10.7
	11.3	10.0	11.2	10.6	11.3	9.8	11.7	9.9	11.9	10.1
	10.8	10.8	11.0	10.2	11.5	10.3	11.1	10.8	10.8	10.8
	10.8	10.8	10.8	10.8	12.2	9.2	11.6	10.7	10.8	10.7
	11.0	10.6	11.0	10.7	10.8	10.8	10.9	10.7	10.8	10.7
	11.4	9.2	12.2	10.3	10.9	10.6	11.1	10.4	11.5	9.1
	8.8	9.0	9.1	9.0	9.2	9.1	9.1	8.7	10.7	8.8
	10.8	8.2	9.6	8.7	9.4	9.0	9.1	9.0	9.1	8.0
	9.1	9.0	9.4	7.7	10.4	8.5	9.2	8.9	9.6	8.8
290	9.5	9.0	9.0	9.0	9.0	9.0	9.0	8.8	10.2	7.2
	10.4	8.4	9.3	8.7	9.2	8.9	9.0	9.0	9.0	8.0
	9.0	9.0	9.2	8.0	10.0	8.6	9.0	8.9	9.4	8.9
	9.4	8.2	9.4	8.8	9.8	8.4	9.2	9.0	9.1	8.5
	9.4	9.0	9.0	9.0	9.1	9.0	9.0	9.0	9.0	9.0
	11.4	10.6	10.6	10.5	10.7	10.6	10.6	10.2	12.3	8.3
	12.0	9.7	11.2	10.2	10.9	10.5	10.7	10.6	10.7	10.6
	10.6	10.6	11.0	9.2	12.0	10.0	10.7	10.4	11.2	10.4
	11.3	9.9	11.3	10.2	11.3	9.7	11.0	10.6	10.8	9.8
	11.2	10.9	10.6	10.6	10.9	10.5	10.7	10.6	10.6	10.6
300	10.7	10.6	10.7	10.3	11.1	10.4	10.7	10.4	11.1	10.2
	10.9	9.9	12.3	8.5	12.1	10.6	10.8	10.6	10.6	10.5

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
 RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
 COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown

M-94: 1.4 factor on this table

Line	Stresses in KSI									
	10.9	10.6	10.4	10.6	10.9	10.3	10.9	10.9	10.6	10.8
	11.1	9.8	11.0	10.4	11.1	9.7	11.5	9.8	11.7	-9.4
	12.9	9.1	11.9	10.6	10.8	10.7	10.8	10.8	10.8	10.7
	11.2	9.4	12.4	9.6	11.2	10.6	11.1	10.4	10.9	10.2
	11.2	10.7	10.8	10.7	11.3	10.1	11.2	10.6	10.9	10.7
	11.2	10.2	11.2	10.5	11.0	10.6	11.3	9.4	12.7	9.1
	11.5	10.5	11.0	10.6	11.0	10.6	10.9	10.7	10.8	10.6
310	11.1	10.7	10.8	10.7	11.4	10.1	11.0	10.2	12.1	9.5
	11.6	10.2	11.6	9.9	11.4	9.8	12.1	10.1	10.8	10.8
	11.0	9.8	12.8	8.5	12.3	10.1	11.2	10.4	11.2	10.4
	11.1	10.5	11.1	10.5	11.0	10.7	10.8	10.8	11.0	10.1
	11.8	9.9	11.1	10.7	10.9	10.6	11.5	9.9	11.7	9.3
	11.9	10.6	11.0	10.5	11.1	10.5	11.0	10.8	10.8	10.7
	11.0	10.5	11.0	10.6	11.1	10.2	11.4	10.4	10.9	10.8
	10.8	10.6	11.2	10.3	11.2	10.5	10.9	10.8	10.8	10.6
	9.7	8.0	9.7	8.7	9.7	8.3	9.5	9.0	9.3	8.3
	9.6	9.0	9.0	9.0	9.3	9.0	9.1	9.0	9.1	9.0
320	9.1	9.0	9.2	8.8	9.5	8.8	9.2	8.9	9.5	8.7
	9.0	9.0	9.1	8.8	9.3	8.9	9.0	8.9	9.3	8.8
	9.1	8.6	10.2	7.3	10.0	8.8	9.1	9.0	9.0	8.9
	9.1	9.0	9.0	9.0	9.1	8.8	9.2	8.9	9.0	9.0
	9.3	8.5	9.2	8.9	9.3	8.4	9.6	8.5	9.7	8.6
	9.0	9.0	9.1	8.8	9.3	8.9	9.0	8.9	9.3	8.8
	10.7	10.6	10.8	10.0	11.3	10.1	10.9	10.6	10.6	9.0
	10.7	10.6	10.6	10.3	12.0	9.1	11.4	10.5	10.6	10.6
	10.8	10.4	10.8	10.6	10.8	10.6	10.7	10.5	10.6	10.6
	11.2	9.1	12.0	10.2	10.7	10.4	11.0	10.3	11.3	9.0
	12.7	9.0	11.3	10.4	10.7	10.6	10.7	10.6	10.6	10.6
330	11.0	9.4	12.2	9.5	11.0	10.4	11.0	10.3	10.8	10.1
	11.0	10.5	10.6	10.5	11.1	10.0	11.0	10.4	10.7	10.5
	11.0	10.1	11.0	10.4	10.8	10.4	11.1	9.3	12.5	9.0
	11.3	10.3	10.8	10.5	10.8	10.5	10.7	10.6	10.7	-8.4
	11.8	9.8	11.3	10.7	10.9	10.5	11.6	9.2	12.4	10.4
	11.0	10.6	11.2	10.6	10.8	10.7	11.7	9.4	11.3	10.1
	12.0	10.3	10.9	10.6	11.4	10.2	11.0	10.7	11.0	10.1
	11.0	10.7	10.8	10.7	11.0	10.6	10.9	10.6	10.9	10.4
340	11.0	10.3	11.8	10.0	11.7	10.6	11.0	10.3	10.9	10.7
	10.9	10.7	10.9	10.5	11.6	9.9	11.0	10.9	11.0	9.9
	11.0	10.6	10.9	10.3	11.4	10.6	11.3	10.3	11.2	10.5
	10.8	10.8	10.8	10.7	10.8	10.8	10.9	10.1	11.8	10.0
	11.0	10.6	11.6	9.5	11.8	10.5	10.8	10.7	11.2	10.3
	11.1	10.7	10.8	10.8	10.9	10.5	11.2	10.3	10.9	10.7

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
M-94: 1.4 factor on this table

Line	Stresses in KSI									
	10.1	10.2	10.3	10.4	10.5	10.6	10.7	10.8	10.9	10.0
	10.1	9.1	11.6	10.1	12.2	9.2	11.8	10.8	10.8	9.1
	10.2	8.4	10.7	7.0	10.5	8.5	9.2	9.1	9.1	8.9
	10.3	9.0	9.1	9.1	9.3	8.8	9.4	9.9	9.1	9.0
350	9.4	8.3	9.4	8.9	9.8	8.2	9.5	8.3	10.1	8.5
	9.0	9.0	9.0	8.8	9.9	7.9	9.5	9.0	9.0	9.0
	9.1	8.9	9.1	9.0	9.0	9.0	9.0	9.0	9.0	9.0
	9.3	7.9	10.0	8.7	9.0	8.9	9.2	8.8	9.4	7.8
	10.6	7.8	9.4	8.9	9.0	9.0	9.0	9.0	9.0	9.0
360	9.2	8.2	10.1	8.2	9.2	8.9	9.2	8.8	9.1	8.7
	10.0	10.5	10.6	10.6	11.2	10.0	10.8	10.0	11.9	9.3
	11.4	10.0	11.4	9.8	11.3	9.6	11.9	10.0	10.6	10.6
	10.8	9.8	12.5	8.4	12.1	10.0	11.0	10.2	11.1	10.2
	10.9	10.3	10.9	10.3	10.8	10.5	10.6	10.6	10.8	10.6
370	11.6	9.8	11.0	10.5	10.7	10.4	11.3	9.8	11.5	9.2
	11.7	10.4	10.8	10.4	10.9	10.3	10.8	10.6	10.6	10.5
	10.9	10.4	10.6	10.5	10.9	10.1	11.2	10.2	10.7	10.6
	10.7	10.4	11.0	10.1	11.1	10.3	10.8	10.6	10.6	10.5
	11.1	10.2	10.8	10.6	10.6	10.5	10.8	10.6	10.7	-8.9
380	7.2	6.5	6.6	6.5	6.6	6.6	6.5	6.2	7.0	6.9
	7.9	8.9	7.0	6.2	6.8	6.5	6.6	6.5	6.6	6.5
	6.6	6.5	6.9	5.5	7.6	6.1	6.7	6.4	7.0	6.3
	7.1	5.7	7.1	6.2	7.1	5.9	5.9	6.5	6.7	5.9
	7.0	6.5	6.5	6.5	6.8	6.5	6.6	6.5	6.6	6.5
	6.6	6.5	6.7	6.3	6.9	6.4	6.6	6.4	6.9	6.3
	6.8	6.0	7.8	5.0	7.6	6.1	6.7	6.5	6.6	6.4
	6.8	6.5	6.6	6.5	6.7	6.3	6.8	6.4	6.6	6.5
	6.7	6.1	6.2	6.1	6.2	6.2	6.2	5.9	7.2	4.7
	7.4	5.5	6.5	5.9	6.4	6.1	6.2	6.1	6.2	6.1
	9.2	8.9	9.0	9.0	9.3	8.6	9.2	8.9	9.0	9.0
	9.2	8.7	9.2	8.9	9.1	8.9	9.3	8.1	10.4	7.8
	9.4	8.8	9.1	8.9	9.1	8.9	9.0	9.0	9.0	8.9
	9.1	9.0	9.0	9.0	9.3	8.6	9.1	8.6	9.9	8.1
	9.5	8.7	9.5	8.4	9.4	8.4	9.9	8.6	9.0	9.0
	9.1	8.3	10.4	7.3	10.0	8.6	9.2	8.8	9.3	8.8
	9.2	8.9	9.2	8.8	9.1	9.0	9.0	9.0	9.1	8.6
	9.6	8.9	9.2	9.0	9.0	8.9	9.4	8.5	9.6	8.0
	9.7	8.9	9.1	8.9	9.2	8.8	9.1	9.0	9.0	8.0
	9.3	8.6	8.7	8.6	8.7	8.6	8.7	8.3	10.1	6.5
	10.4	7.8	9.1	8.3	8.9	8.5	8.7	8.6	8.7	8.6
	8.7	8.6	8.9	7.4	10.0	8.1	8.7	8.5	9.2	8.4
	9.3	7.6	9.2	8.3	9.3	7.6	9.0	8.6	8.6	-8.9
	7.0	5.9	6.9	6.4	6.9	5.8	7.3	5.9	7.4	6.0

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
M-94: 1.4 factor on this table

Line	Stresses in KSI										
	6.6	6.6	6.7	6.1	7.1	6.2	6.6	6.5	6.5	6.5	6.5
	6.6	6.6	6.6	6.3	7.6	6.4	7.2	6.5	6.6	6.6	6.6
390	6.7	6.6	6.7	6.3	6.6	6.6	6.6	6.6	6.6	6.6	6.6
	7.0	6.4	7.6	6.2	6.7	6.4	6.6	6.3	7.1	6.3	6.3
	6.1	6.3	7.1	6.4	6.6	6.3	6.6	6.6	6.6	6.6	6.6
	6.9	6.7	7.7	5.7	6.9	6.4	6.8	6.3	6.7	6.1	6.1
	6.9	6.5	6.6	6.5	6.9	6.1	6.9	6.4	6.6	6.5	6.5
	6.2	6.1	6.4	5.2	7.2	5.7	6.2	6.0	6.6	5.9	5.9
	6.7	5.4	6.6	5.9	6.7	5.5	6.4	6.1	6.4	5.6	5.6
	9.1	8.9	9.1	8.9	9.2	8.7	9.3	8.8	9.0	9.0	9.0
	9.0	8.9	9.2	8.7	9.3	8.8	9.1	9.0	9.0	8.9	8.9
400	9.3	8.7	9.1	9.0	9.0	9.0	9.0	9.1	9.0	9.0	8.8
	9.7	8.4	9.3	8.9	9.0	8.9	9.5	7.9	10.1	8.6	8.6
	9.1	8.9	9.2	8.9	9.0	9.0	9.0	9.0	9.3	8.6	8.6
	9.8	8.7	9.0	8.9	9.4	8.6	9.1	9.0	9.1	8.8	8.8
	9.1	8.9	9.0	9.0	9.1	8.9	9.0	8.9	9.1	9.0	9.0
	9.1	8.7	9.6	8.5	9.2	8.9	9.1	8.8	9.1	9.0	9.0
	9.0	9.0	9.0	8.9	9.5	8.4	9.1	9.1	9.1	8.4	8.4
	9.2	8.6	8.6	8.6	8.8	8.6	8.7	8.6	8.7	8.6	8.6
	8.7	8.6	8.8	8.3	9.0	8.5	8.7	8.6	9.0	8.6	8.6
	8.9	7.9	10.3	8.8	9.8	8.2	8.8	8.6	8.7	8.6	8.6
	8.8	8.6	8.6	8.6	8.8	8.4	8.9	8.5	8.7	-6.4	-6.4
410	11.6	10.7	10.8	10.7	10.9	10.8	10.8	10.3	12.5	8.4	8.4
	12.7	9.8	11.3	10.3	11.1	10.7	10.8	10.7	10.8	10.8	10.8
	10.8	10.7	11.2	9.3	12.2	10.2	10.9	10.5	11.4	10.5	10.5
	11.5	9.6	11.5	10.3	11.5	9.9	11.2	10.7	11.0	10.6	10.6
	11.4	10.7	10.7	10.7	11.1	10.7	10.8	10.7	10.8	10.7	10.7
	10.9	10.7	10.9	10.4	11.3	10.5	10.9	10.9	11.3	10.4	10.4
	11.0	10.1	12.5	8.6	12.3	10.1	11.0	10.8	10.8	10.6	10.6
	11.0	10.7	10.8	10.8	11.0	10.5	11.1	10.6	10.6	10.7	10.7
	11.3	10.0	11.2	10.6	11.3	9.8	11.7	9.9	11.9	10.1	10.1
	10.8	10.8	11.0	10.2	11.3	10.3	11.1	10.8	10.8	10.8	10.8
420	10.8	10.8	10.8	10.4	12.2	9.2	11.6	10.7	10.8	10.7	10.7
	11.0	10.6	11.0	10.7	10.8	10.8	10.9	10.7	10.8	10.7	10.7
	11.4	9.2	12.2	10.3	10.9	10.6	11.1	10.4	11.5	9.1	9.1
	9.8	9.0	9.1	9.0	9.2	9.1	9.1	8.7	10.7	6.8	6.8
	10.8	8.2	9.6	8.7	9.4	9.0	9.1	9.0	9.1	9.0	9.0
	9.1	9.0	9.6	7.7	10.4	8.5	9.2	9.9	9.6	8.8	8.8
	9.5	9.0	9.0	9.0	9.0	9.0	9.0	8.8	10.2	7.2	7.2
	10.4	8.4	9.3	8.7	9.2	8.9	9.0	9.0	9.0	9.0	9.0
	9.0	9.0	9.2	8.0	10.0	8.6	9.0	8.9	9.4	8.9	8.9
430	9.4	8.2	9.4	8.8	9.4	8.4	9.2	9.0	9.1	8.5	8.5
	9.4	9.0	9.0	9.0	9.1	9.0	9.0	9.0	9.0	9.0	9.0

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
 RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
 COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
 M-94: 1.4 factor on this table

Line	Stresses in KSI										
	11.4	10.6	10.6	10.5	10.7	10.6	10.6	10.6	12.3	8.3	
	12.5	9.7	11.2	10.2	10.9	10.5	10.7	10.6	10.7	10.6	
	10.6	10.6	11.0	9.2	12.0	10.0	10.7	10.4	11.2	10.4	
	11.3	9.5	11.3	10.2	11.3	9.7	11.0	10.6	10.8	9.8	
	11.2	10.5	10.6	10.6	10.9	10.5	10.7	10.6	10.6	10.6	
	10.7	10.6	10.7	10.3	11.1	10.4	10.7	10.4	11.1	10.2	
	10.9	9.9	12.3	8.5	12.1	10.0	10.8	10.6	10.6	10.5	
	10.9	10.6	10.6	10.6	10.9	10.3	10.9	10.5	10.6	10.5	
440	11.1	9.8	11.0	10.4	11.1	9.7	11.5	9.8	11.7	-6.4	
	12.9	9.1	11.5	10.6	10.8	10.7	10.8	10.8	10.8	10.7	
	11.2	9.6	12.4	9.6	11.2	10.6	11.1	10.4	10.9	10.2	
	11.2	10.7	10.8	10.7	11.3	10.1	11.2	10.6	10.9	10.7	
	11.2	10.2	11.2	10.5	11.0	10.6	11.3	9.4	12.7	9.1	
	11.5	10.5	11.0	10.6	11.0	10.6	10.9	10.7	10.8	10.6	
	11.1	10.5	11.1	10.5	11.0	10.7	10.8	10.8	11.0	10.1	
	11.6	10.2	11.6	9.9	11.4	9.8	12.1	10.1	10.8	10.8	
	11.0	9.4	12.6	8.5	12.3	10.1	11.2	10.4	11.2	10.4	
	11.1	10.7	10.8	10.7	11.4	10.1	11.0	10.2	12.1	9.5	
	11.8	9.9	11.1	10.7	10.9	10.6	11.5	9.9	11.7	9.3	
450	11.9	10.6	11.0	10.5	11.1	10.5	11.0	10.6	10.8	10.7	
	11.0	10.5	11.0	10.6	11.1	10.2	11.4	10.4	10.9	10.8	
	10.8	10.6	11.2	10.3	11.2	10.5	10.9	10.8	10.8	10.6	
	9.7	8.0	9.7	8.7	9.7	8.3	9.5	9.0	9.3	8.3	
	9.6	9.0	9.0	9.0	9.3	9.0	9.1	9.0	9.1	9.0	
	9.1	9.0	9.2	8.8	9.3	8.8	9.2	8.9	9.5	8.7	
	9.0	9.0	9.1	8.8	9.3	8.9	9.0	8.9	9.3	8.8	
	9.1	8.6	10.2	7.3	10.0	8.6	9.1	9.0	9.0	8.9	
	9.1	9.0	9.0	9.0	9.1	8.8	9.2	8.9	9.0	9.0	
460	9.3	8.5	9.2	8.9	9.3	8.4	9.6	8.5	9.7	8.8	
	9.0	9.0	9.1	8.6	9.4	8.7	9.1	9.0	9.0	9.0	
	10.7	10.6	10.6	10.0	11.3	10.1	10.9	10.6	10.6	10.6	
	10.7	10.6	10.6	10.3	12.0	9.1	11.4	10.5	10.6	10.6	
	10.8	10.4	10.8	10.6	10.6	10.6	10.7	10.5	10.6	10.6	
	11.2	9.1	12.0	10.2	10.7	10.4	11.0	10.3	11.3	9.0	
	12.7	9.0	11.3	10.4	10.7	10.6	10.7	10.6	10.6	10.6	
	11.0	9.4	12.2	9.5	11.0	10.4	11.0	10.3	10.8	10.1	
	11.0	10.5	10.6	10.5	11.1	10.0	11.0	10.4	10.7	10.5	
470	11.0	10.1	11.0	10.4	10.9	10.4	11.1	9.3	12.0	9.6	
	11.3	10.3	10.8	10.5	10.8	10.5	10.7	10.6	10.7	10.4	
	11.3	10.3	11.0	10.8	10.8	10.7	10.9	10.7	10.8	-6.4	
	11.8	9.8	11.3	10.7	10.9	10.5	11.0	9.2	12.4	10.1	
	11.0	10.6	11.2	10.6	10.8	10.7	11.7	9.4	11.3	10.1	
	12.0	10.3	10.9	10.6	11.4	10.2	11.0	10.7	11.0	10.4	

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
 RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
 COMPOSITE MISSION, TYPICAL TRANSPORT (CONT)

Test M-93: This table as shown
 M-94: 1.4 factor on this table

Line	Stresses in KSI										
	11.0	10.7	10.9	10.7	11.0	10.6	10.9	10.6	10.8	10.7	
	11.0	10.3	11.8	10.0	11.1	10.6	11.0	10.5	10.9	10.7	
	10.9	10.7	10.9	10.5	11.6	9.9	11.0	10.9	11.0	9.9	
	11.0	10.6	10.9	10.3	11.4	10.6	11.3	10.3	11.2	10.5	
	10.8	10.8	10.8	10.7	10.8	10.8	10.9	10.1	11.8	10.0	
	11.0	10.6	11.6	9.5	11.8	10.5	10.8	10.7	11.2	10.3	
480	11.1	10.7	10.8	10.8	10.9	10.5	11.2	10.3	10.9	10.7	
	11.1	10.5	10.8	10.8	10.8	10.6	10.8	10.8	10.9	9.8	
	12.7	9.1	11.6	10.1	12.2	9.2	11.5	10.8	10.8	9.5	
	9.3	8.4	10.7	7.0	10.5	8.5	9.2	9.1	9.1	8.9	
	9.3	9.0	9.1	9.1	9.3	8.8	9.4	8.9	9.1	9.0	
	9.6	8.3	9.4	8.9	9.5	8.2	9.9	8.3	10.1	8.5	
	9.0	9.0	9.0	8.8	9.9	7.9	9.5	9.0	9.0	9.0	
	9.1	8.4	9.1	9.0	9.0	9.0	9.0	9.0	9.0	9.0	
	9.3	7.9	10.0	8.7	9.0	8.9	9.2	8.8	9.4	7.8	
	10.6	7.8	9.4	8.9	9.0	9.0	9.0	9.0	9.0	9.0	
490	9.2	8.2	10.1	8.2	9.2	8.9	9.2	8.8	9.1	8.7	
	10.9	10.5	10.6	10.6	11.2	10.0	10.8	10.0	11.9	9.3	
	11.4	10.0	11.4	9.8	11.3	9.6	11.9	10.0	10.6	10.6	
	10.8	9.6	12.5	8.4	12.1	10.0	11.0	10.2	11.1	10.2	
	10.9	10.3	10.9	10.3	10.8	10.5	10.6	10.6	10.8	10.0	
	11.6	9.8	11.0	10.5	10.7	10.4	11.3	9.8	11.5	9.2	
	11.7	10.4	10.8	10.4	10.9	10.3	10.8	10.6	10.6	10.5	
	10.9	10.4	10.8	10.5	10.9	10.1	11.2	10.2	10.7	10.6	
	10.7	10.4	11.0	10.1	11.1	10.3	10.8	10.6	10.6	10.5	
	11.1	10.2	10.8	10.8	10.8	10.5	10.8	10.6	10.7	8.9	
500	7.2	6.5	6.6	6.5	6.6	6.6	6.6	6.2	7.8	4.9	
	7.9	5.9	7.0	6.2	6.8	6.5	6.6	6.5	6.6	6.5	
	6.6	6.5	6.9	5.5	7.6	6.1	6.7	6.4	7.0	6.3	
	7.1	5.7	7.1	6.2	7.1	5.9	6.9	6.5	6.7	5.9	
	7.0	6.5	6.5	6.5	6.8	6.5	6.6	6.5	6.6	6.5	
	6.8	6.5	6.7	6.3	6.9	6.4	6.6	6.4	6.9	6.3	
	6.8	6.0	7.8	5.0	7.6	6.1	6.7	6.6	6.6	6.4	
	6.8	6.5	6.6	6.5	6.7	6.3	6.8	6.4	6.6	6.5	
	6.7	6.1	6.2	6.1	6.2	6.2	6.2	5.9	7.2	4.7	
510	7.4	5.5	6.5	5.9	6.4	6.1	6.2	6.1	6.2	6.1	
	9.2	6.9	9.0	9.0	9.3	8.6	9.2	8.9	9.0	9.0	
	9.2	8.7	9.2	8.9	9.1	8.9	9.3	8.1	10.4	7.8	
	9.4	8.8	9.1	8.9	9.1	8.9	9.0	9.0	9.0	8.9	
	9.1	9.0	9.0	9.0	9.3	8.6	9.1	8.6	9.9	8.1	
	9.5	8.7	9.5	8.4	9.4	8.4	9.9	8.6	9.0	9.0	
	9.1	8.3	10.4	7.3	10.0	8.6	9.2	8.8	9.3	8.8	
	9.2	8.9	9.2	8.8	9.1	9.0	9.0	9.0	9.1	8.6	

TABLE 114. METHODOLOGY DEVELOPMENT TEST PROGRAM, GROUP V,
RANDOM FLIGHT-BY-FLIGHT SPECTRUM LOADING TEST
COMPOSITE MISSION, TYPICAL TRANSPORT (CONCL)

Test M-93: This table as shown
M-94: 1.4 factor on this table

Line	Stresses in KSI										
	9.6	8.5	9.2	9.0	9.0	8.9	9.4	8.5	9.6	8.0	
	9.7	8.9	9.1	8.9	9.2	8.8	9.1	9.0	9.0	9.0	
	9.3	8.6	8.7	8.6	8.7	8.6	8.7	8.3	10.1	6.5	
520	10.4	7.8	9.1	8.3	8.9	8.5	8.7	8.6	8.7	8.6	
	8.7	8.6	8.9	7.6	10.0	8.1	8.7	8.5	9.2	8.4	
	9.3	7.6	9.2	8.3	9.3	7.8	9.0	8.6	8.8	-8.7	
	7.0	5.9	6.9	6.4	6.9	5.8	7.3	5.9	7.4	6.0	
	6.6	6.6	6.7	6.1	7.1	6.2	6.8	6.5	6.5	6.5	
	6.6	6.6	6.6	6.3	7.6	5.4	7.2	6.5	6.6	6.5	
	6.7	6.4	6.7	6.5	6.6	6.6	6.6	6.5	6.6	6.5	
	7.0	5.4	7.6	6.2	6.7	6.4	6.8	6.3	7.1	5.3	
	8.1	5.3	7.1	6.4	6.6	6.5	6.6	6.6	6.6	6.5	
	6.9	5.7	7.7	5.7	6.9	6.4	6.8	6.3	6.7	6.1	
530	6.9	6.5	6.6	6.5	6.9	6.1	6.9	6.4	6.6	6.5	
	6.2	6.1	6.4	5.2	7.2	5.7	6.2	6.0	6.6	5.9	
	6.7	5.4	6.6	5.9	6.7	5.5	6.4	6.1	6.4	5.6	
	9.1	8.9	9.1	8.9	9.2	8.7	9.3	8.8	9.0	9.0	
	9.0	8.9	9.2	8.7	9.3	8.8	9.1	9.0	9.0	8.9	
	9.3	8.7	9.1	9.0	9.0	9.0	9.1	9.0	9.0	8.8	
	9.7	8.4	9.3	8.9	9.0	8.9	9.3	7.9	10.1	8.8	
	9.1	8.9	9.2	8.9	9.0	9.0	9.6	8.0	9.3	8.6	
	9.8	8.7	9.0	8.9	9.4	8.6	9.1	9.0	9.1	8.8	
	7.1	6.9	9.0	9.0	9.1	8.9	9.0	8.9	9.1	9.0	
540	9.1	8.7	9.6	8.5	9.2	8.9	9.1	8.8	9.1	9.0	
	9.0	9.0	9.0	8.9	9.5	8.4	9.1	9.1	9.1	8.4	
	7.2	6.6	8.6	8.6	8.8	8.6	8.7	8.5	8.7	8.6	
	8.7	8.6	8.8	8.3	9.0	8.5	8.7	8.4	9.0	8.4	
	9.9	7.9	10.3	6.8	9.8	8.2	8.8	8.6	8.7	-11.5	
	11.9	8.6	9.5	8.5	10.2	9.4	9.6	7.5	13.0	9.0	
	13.2	6.6	11.4	7.4	10.9	8.4	9.9	8.7	9.9	8.9	
	9.5	6.8	7.6	6.8	8.2	7.5	7.7	5.9	10.4	4.0	
	9.3	8.9	9.1	8.7	9.4	8.9	9.3	8.7	9.2	8.9	
	9.0	9.0	9.0	9.0	9.0	9.0	9.1	8.6	9.7	8.5	
550	9.1	8.9	9.5	8.2	9.6	8.9	9.0	9.0	9.2	8.7	
	9.1	9.0	9.0	9.0	9.0	8.9	9.2	8.8	9.1	8.9	
	9.2	8.9	9.0	9.0	9.0	8.9	9.0	9.0	9.0	8.4	
	10.4	7.8	9.5	8.6	9.9	7.9	9.4	9.0	9.0	8.2	
	11.2	7.2	9.8	8.8	9.4	9.3	9.1	8.5	9.3	9.0	
	9.0	8.9	9.6	7.6	10.7	7.8	9.7	8.7	9.0	8.6	
	9.8	8.9	9.2	8.9	9.1	9.0	9.0	8.8	—	—	
	12.0	9.9	10.4	9.4	11.2	10.3	10.6	8.4	13.0	6.1	
	14.0	7.6	12.3	8.4	11.9	9.3	10.9	9.6	10.8	9.8	

TABLE 115. DATA TABULATION FOR TEST M-93
 SPECIMEN NO.: M-93 RANDOM SPECTRUM, TYPICAL TRANSPORT, MAX SPECTRUM STRESS = 14 KSI
 CCI SPECIMEN b = 0.250 IN. h = 6.000 IN.
 PMIN = AN = 0.0 IN.
 PMAX = TEST FREQ = 6.00 Hz.
 ENVIRONMENT CONDITION: AMBIENT AIR

NU.	CYCLES	AI MEASURED	AIRREGRESSION	MULTI. CORR. COEFF	K-MAX	DELTA K	DA/DN
1	0.	0.500	0.500	0.999865	8.31	13.59	1.244E-07
2	173380.	0.550	0.550	0.998907	8.71	14.26	1.788E-07
3	198193.	0.560	0.564	0.990058	8.83	14.44	1.634E-07
4	281790.	0.590	0.592	0.989765	9.05	14.80	1.579E-07
5	335088.	0.620	0.608	0.988674	9.18	15.01	1.657E-07
6	491969.	0.655	0.657	0.990822	9.55	15.67	1.588E-07
7	558000.	0.670	0.675	0.993863	9.68	15.83	1.625E-07
8	682690.	0.720	0.715	0.999036	9.98	16.32	1.854E-07
9	775550.	0.750	0.752	0.999031	10.24	16.75	2.134E-07
10	860629.	0.790	0.791	0.999175	10.51	17.19	2.375F-07
11	980335.	0.850	0.850	0.998301	10.92	17.86	2.622E-07
12	1037066.	0.885	0.883	0.999143	11.13	18.21	2.712E-07
13	1108137.	0.925	0.922	0.998565	11.39	18.64	2.703E-07
14	1146757.	0.940	0.941	0.992619	11.52	18.84	2.993F-07
15	1208901.	0.980	0.979	0.991254	11.76	19.24	3.074F-07
16	1246536.	0.995	1.002	0.988626	11.91	19.48	3.165E-07
17	1313740.	1.060	1.048	0.986884	12.19	19.95	3.241F-07
18	1359024.	1.075	1.076	0.979614	12.37	20.24	2.508E-07

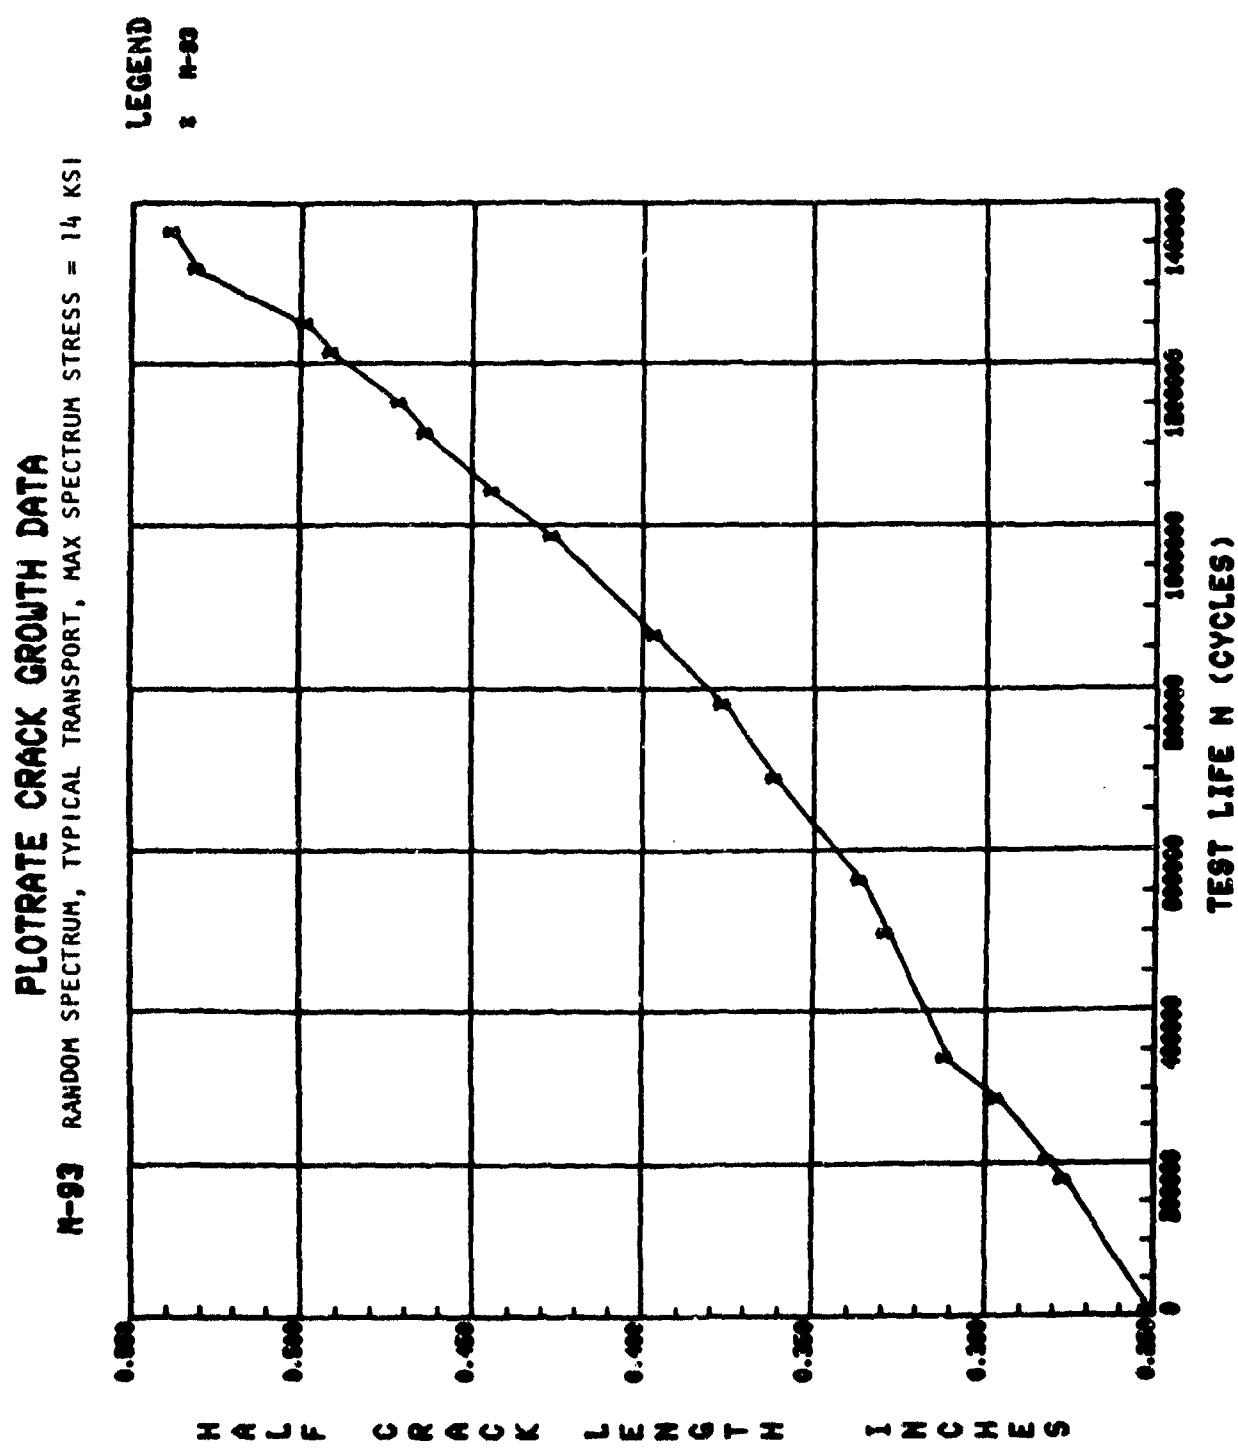


Figure 111. Crack growth curve for test M-93.

TABLE 116. DATA TABULATION FOR TEST M-94

SPECIMEN NO.: M-94 RANDOM SPECTRUM, TYPICAL TRANSPORT, MAX SPECTRUM STRESS = 19.6 KSI

CCF SPECIMEN	B = 0.250 IN.	b = 6.000 IN.	A _N = 0.0 IN.	TEST FREQ = 6.00 Hz.
P _{MIN}	P _{MAX}	ENVIRONMENT CONDITION: AMBIENT AIR		
No.	CYCLES	AI(MEASURED)	AI(REGRESSION)	MULR. CORR. COEFF
1	0.	0.515	0.516	0.996742
2	52467.	0.565	0.556	0.996051
3	122275.	0.605	0.603	0.992595
4	186640.	0.650	0.656	0.992480
5	244690.	0.700	0.708	0.997491
6	279000.	0.750	0.749	0.998112
				K-MAX
				0.437E-07
				21.98
				22.84
				3.730E-07
				23.82
				3.877E-07
				4.424E-07
				24.85
				25.85
				5.586E-07
				26.63
				7.001E-07
				DELTA K

M-94 TRANSPORT, RANDOM SPECTRUM, MAX STRESS = 19.6 KSI

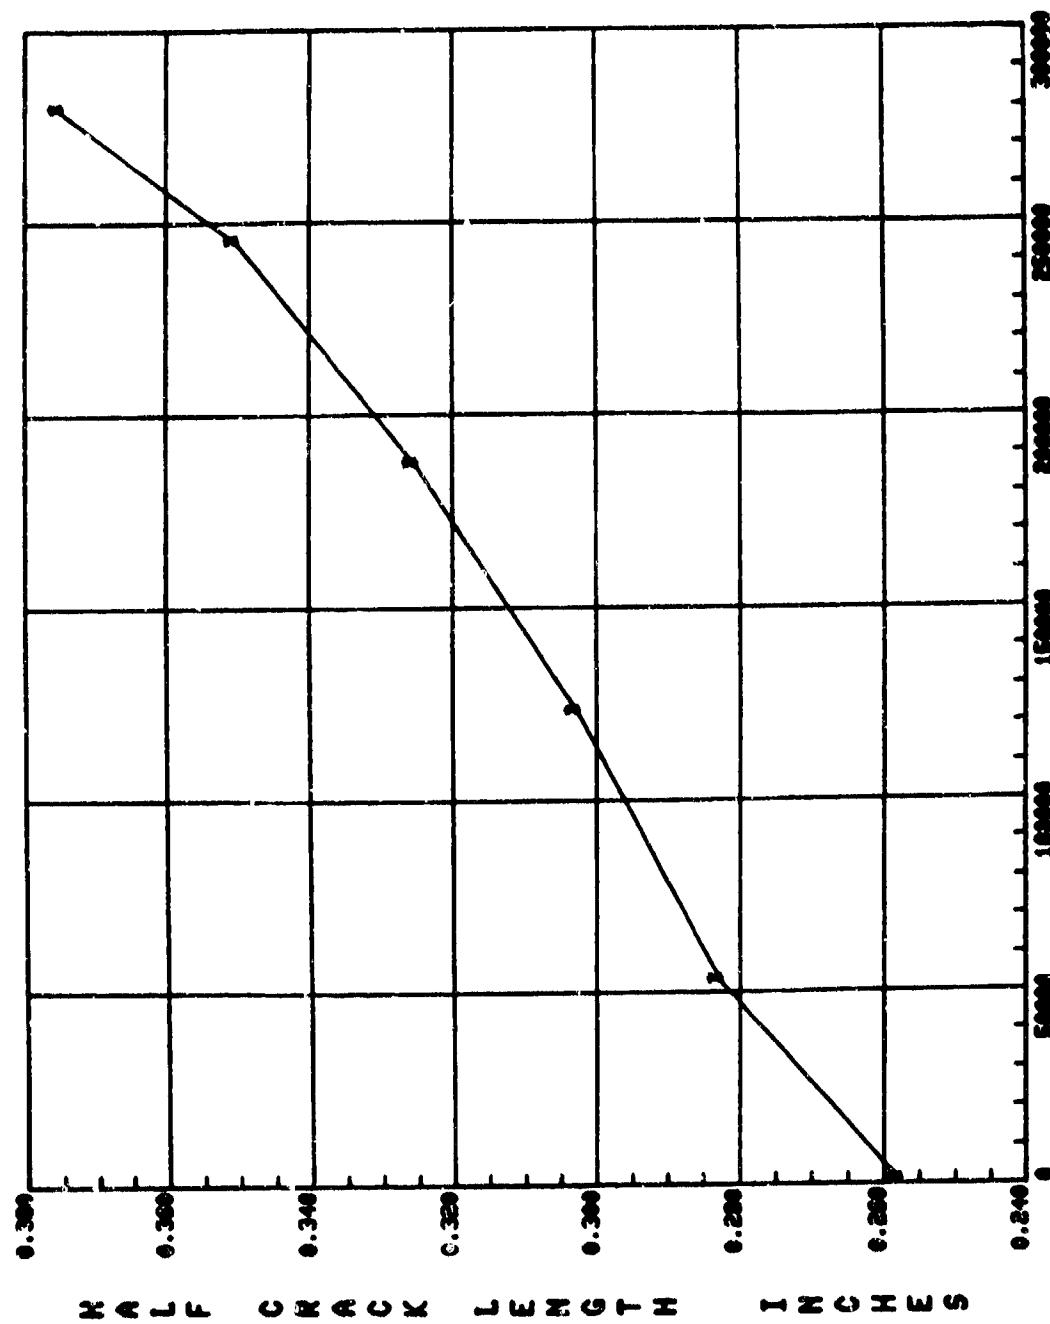


Figure 112. Crack growth curve for test M-94.