

TWR- 50087

DEVELOPMENT OF INSPECTION TECHNIQUES
FOR QUANTITATIVELY MEASURING
SURFACE CONTAMINATION ON SRM HARDWARE
INTERIM REPORT

October 13, 1989

Prepared for:

NATIONAL AERONAUTICS AND SPACE ADMINISTRATION
GEORGE C. MARSHALL SPACE FLIGHT CENTER
MARSHALL SPACE FLIGHT CENTER, ALABAMA 35812

Contract No. NAS8-30490

DR. No. 3-5

WBS.No. HQ301 18 02

MORTON THIOKOL, INC.

Aerospace Group

Space Operations

P.O. Box 707, Brigham City, Utah 84302-0707 (801) 863-3511

FORM TC 4677 (REV 1-88)

(NASA-CR-183902) DEVELOPMENT OF INSPECTION
TECHNIQUES FOR QUANTITATIVELY MEASURING
SURFACE CONTAMINATION ON SRM HARDWARE
Interim Report (Morton Thiokol) 247 p

N90-19605

Unclass
0274812

CSCL 140 63/38

DOC NO. TWR-50087
TITLE LSDI-90-08

VOL REV

DEVELOPMENT OF INSPECTION TECHNIQUES
FOR QUANTITATIVELY MEASURING
SURFACE CONTAMINATION ON SRM HARDWARE
INTERIM REPORT
October 13, 1989
PREPARED BY:

R. D. Law
R. D. Law
Spectrochemical Analysis

APPROVED BY:

J. M. Dietz
J. M. Dietz, Supervisor
Spectrochemical Analysis

R. Furrows
R. Furrows
Project Engineer

V. W. Fitch 12-19-89
V. W. Fitch
Design

J. R. Braithwaite
J. R. Braithwaite
Flight Certification

R. D. Larson 12/20/89
R. D. Larson
System Safety

D. B. Davis
D. B. Davis, Manager
Laboratory Services Department

E. L. Gray
E. L. Gray
Program Manager

S. M. West
S. M. West
Reliability

I. N. Black
I. N. Black
Test Plans and Reports

P. C. Tydeek 3-6-90
P. C. Tydeek
Release ECS SS 1638

MORTON THIOKOL, INC.

Wasatch Operations

P.O. Box 707, Brigham City, Utah 84302 (801)863-3511
RESEARCH AND DEVELOPMENT LABORATORIES

Laboratory Services Department

PRELIMINARY

TABLE OF CONTENTS

Section	Title	Page
1.0	INTRODUCTION	1
2.0	OBJECTIVES	1
3.0	EXPERIMENTAL METHOD	1
4.0	CONCLUSIONS (PHASES I AND III ONLY)	3
5.0	RECOMMENDATIONS	4
6.0	DISCUSSION	5
	NVR Blank Extractions, Tables IV-XXIII	7
	Extraction of Contaminants From Wipers, Tables XXIV-XXXI	30
	Comparison of Soxhlet Extraction Versus Boiling-Shaking Extraction, Table XXXII	38
	FTIR Spectra of NVR Blank Extractions, Figures 1-36	39
	FTIR Reference Spectra of Contaminants, Figures 37-44	75
	FTIR Spectra of HD-2 Grease Extracts, Figures 45-69	83
	FTIR Spectra of Fluorocarbon Grease Extracts, Figures 70-92	108
	FTIR Spectra of Hydraulic Oil Extracts, Figures 93-115	131
	FTIR Spectra of Silicone Oil Extracts, Figures 116-134	154
	FTIR Spectra of Mineral Oil Extracts, Figures 135-152	173
	FTIR Spectra of DOP Extracts, Figures 153-170	191
	FTIR Spectra of Vinyl Tape Adhesive Extracts, Figures 171-188	209
	FTIR Spectra of Teflon Tape Adhesive Extracts, Figures 189-206	226
	DISTRIBUTION	244

DEVELOPMENT OF INSPECTION TECHNIQUES FOR QUANTITATIVELY
MEASURING SURFACE CONTAMINATION ON SRM HARDWARE
INTERIM REPORT

R. D. Law

1.0 INTRODUCTION

A contaminant is any material or substance which is potentially undesirable or which may adversely affect any part, component, or assembly. Contamination control of SRM hardware surfaces is a serious concern, for both Thiokol and NASA, with particular concern for contaminants which may adversely affect bonding surfaces. The purpose of this study is to develop laboratory analytical techniques which will make it possible to certify the cleanliness of any designated surface, with special focus on particulates (dust, dirt, lint, etc.), oils (hydrocarbons, silicones, plasticizers, etc.), and greases (HD-2, fluorocarbon grease, etc.). The hardware surfaces of concern will include D6AC steel, aluminum alloys, anodized aluminum alloys, glass/phenolic, carbon/phenolic, NBR/asbestos-silica, and EPDM rubber.

This interim report covers work performed in completion of Phases I and III, outlined in ETP-0491. Phases II, IV, and V of ETP-0491 will be completed in future work and will be reported in a final report (TWR-19555).

2.0 OBJECTIVES

- A. To identify and select wiper cloth materials which are suitable for determination of non-volatile residues and particulates.
- B. To determine the compatibility of selected cleaning solvents with selected wiper cloth materials and with hardware surfaces.
- C. To determine the analytical efficiency of selected wiper/solvent combinations for removal of selected contaminants from each hardware surface.
- D. To develop analytical methods for the isolation and identification of insoluble particulates and of soluble non-volatile residues.
- E. Finalization of each of the foregoing into a complete inspection technique suitable for all SRM hardware.

3.0 EXPERIMENTAL METHOD

This study is being pursued in five phases, as follows:

3.1 Phase I, Wiper Cloth/Solvent Compatibility

The wiper cloth materials evaluated included polyester, nylon, polyurethane, polypropylene, cotton, cotton/polyester, and cotton/polypropylene. A list of commercially available wiper materials which were evaluated is given in Table I.

Solvents evaluated included 1,1,1-trichloroethane (methyl chloroform), 1,1,2-trichloro-1,2,2-trifluoroethane (Freon TF), and methyl ethyl ketone (MEK). Methyl chloroform and Freon TF were selected because of non-flammability, comparatively low toxicity, and widespread use in contamination control. MEK is included because of its widespread use in cleaning rubber surfaces and because chlorinated solvents frequently swell and/or degrade rubber. Although Freons are reportedly compatible with aluminum surfaces, it is possible that MEK will be needed here also. High purity clean room grade solvents were employed.

The compatibility of each wiper cloth with each solvent was determined by making repeated extractions followed by determination of the amount and nature of the material extracted.

3.2 Phase II, Hardware/Solvent Compatibility

Wiper cloth/solvent combinations which appear most acceptable from Phases I and III will be applied repeatedly by hand to clean experimental test panels of the following materials:

D6AC steel	Carbon fiber-filled phenolic
Aluminum alloy	NBR/asbestos-silica
Phosphoric acid anodized aluminum alloy	EPDM rubber
Fiberglas-filled phenolic	

After air drying, the surface of the test panels will be examined microscopically for any evidence of corrosion or degradation. The wiper cloths will also be extracted and the amount and nature of any material extracted will be determined. This work has not been completed and is not reported herein.

3.3 Phase III, Cloth Extraction Study

Wiper cloth/solvent combinations which appear most acceptable will be employed to develop suitable cloth extraction techniques.

Wiper cloth samples were doped with known amounts of the following contaminants:

HD-2 grease	Fluorocarbon grease
Hydraulic oil	Mineral oil
Silicone oil	Vinyl tape adhesive
Diocetyl phthalate (DOP)	Teflon tape adhesive

Suitability of wiper/solvent combinations selected from Phase I was determined for each contaminant from a combination of Fourier transform infrared (FTIR) identifiability plus percent recovery.

3.4 Phase IV, Cleaning Efficiency Study

Clean test panels of the below-listed materials will be doped with known amounts of the below-listed contaminants:

Hardware Surface

D6AC steel
Aluminum alloy
Phosphoric acid anodized aluminum alloy
Glass/phenolic
Carbon/phenolic
NBR/asbestos-silica
EPDM/rubber

Contaminant

HD-2 grease
Hydraulic fluid
Silicone oil
DOA
Fluorocarbon grease
Dust (soil)
Mineral oil

Using the appropriate wiper cloth/solvent combinations selected during Phases I through III, repeated wiping operations will be conducted using fresh solvent and a fresh cloth each time. Using cloth extraction techniques developed in Phase III, the best wiping techniques and number of wipes needed for recovery of contaminant will be determined. This work has not been completed and is not reported herein.

3.5 Phase V Final Method Verification

Using test methods formulated during Phases I through IV, the final inspection technique will be verified by application in the field for each hardware surface. Parameters to be evaluated and optimized will include size of surface, number of surfaces, location of representative surfaces, number of wiping operations, and overall precision (repeatability) of the total technique. This work has not been completed and is not reported herein.

4.0 CONCLUSIONS (PHASES I AND III ONLY)

4.1 The wiper/solvent combinations of greatest potential interest for HD-2 grease were:

Miraclewipe/methyl chloroform
Fabwipe/methyl chloroform
Alphawipe/methyl chloroform
Polx 1200/methyl chloroform

4.2 The wiper/solvent combinations of greatest potential interest for a fluorocarbon grease such as Krytox 240AZ were:

Miraclewipe/Freon TF
Polx 1200/Freon TF or methyl chloroform
Fabwipe/Freon TF

4.3 The wiper/solvent combinations of greatest potential interest for hydraulic oil were:

Fabwipe/methyl chloroform or MEK
Alphawipe/ Freon TF
Q-Tips/Freon TF

4.4 The wiper/solvent combinations of greatest potential interest for silicone oil were:

Anticon/methyl chloroform or Freon TF or MEK
Miraclewipe/Freon TF or MEK
Fabwipe/methyl chloroform or MEK
Alphawipe/methyl chloroform or Freon TF or MEK
Polx 1200/methyl chloroform or Freon TF or MEK

- 4.5 The wiper/solvent combinations of greatest potential interest for mineral oil were:

Miraclewipe/methyl chloroform or Freon TF or MEK
Fabwipe/methyl chloroform or Freon TF or MEK
Alphawipe/Freon TF
Polx 1200/methyl chloroform
Q-Tips/methyl chloroform or Freon TF or MEK

- 4.6 All wiper/solvent systems were found to be suitable for DOP. Those chosen for further study may be any which are also of interest for other contaminants.
- 4.7 All wiper/solvent systems were found to be suitable for vinyl tape adhesive, except Q-Tips/methyl chloroform and Miraclewipe/Freon TF. Those chosen for further study may be any others which are also of interest for other contaminants.
- 4.8 All wiper/solvent systems were found to be suitable for Teflon tape adhesive, except Fabwipe/Freon TF. Those chosen for further study may be any others which are also of interest for other contaminants.
- 4.9 No one solvent was found to be suitable for all contaminants, e.g., only methyl chloroform was suitable for HD-2 grease, and only Freon TF was suitable for fluorocarbon grease. Since MEK may be the only solvent compatible with NBR and EPDM rubber (to be determined in the next phase of testing) all three solvents will be carried over for further study.
- 4.10 No one wiper material was ideal for all the contaminants tested, but Fabwipe (a cotton/polypropylene blend) came closest, it being of potential interest for use with all eight contaminants, but not always with the same solvent. Runners-up for most universal wiper were Miraclewipe (a nylon), Alphawipe (a polyester), and Polx 1200 (a polyester), all of potential interest for seven of the eight contaminants. Anticon 100 (a polyester) and Q-Tips (cotton) were unsuitable for half of the contaminants and will be considered for further study only as a back-up.

5.0 RECOMMENDATIONS

1. The remaining phases of ETP-0491 should be pursued using suitable combinations of methyl chloroform, Freon TF, and MEK with Fabwipe, Miraclewipe, Alphawipe, and Polx 1200, in which known contaminants are removed from test surfaces in a controlled laboratory situation, as outlined in ETP-0491.

2. The FTIR scans generated in the first phases of ETP-0491 will serve as a useful library of background spectra, and should be used as an aid in the interpretation of future wipe spectra.

6.0 DISCUSSION

All 13 of the wipers listed in Table I were subjected to repeated 1-hour Soxhlet extractions using each of the solvents of interest—TCE, Freon TF, and MEK. The solutions were filtered to isolate particulates, and the non-volatile residue (NVR) and total particulates were determined by drying and weighing. This was a preliminary screening operation to determine which wipers appeared to be most stable toward the solvents. The wipers selected for further study are given in Table II. Analytical data are summarized in Tables IV through XXIII. This completed Phase I of ETP-0491.

In the next step, samples of the six wipers chosen for further study (Alphawipe, Anticon 100, Fabwipe, Miraclewipe, Polx 1200, and Q-Tips) were first extracted for four hours using a Soxhlet extractor to remove most of the background NVR, and were then re-extracted a second time for four hours. Both the first and second extracts were subjected to FTIR analysis, thus providing background FTIR spectra for each wiper with each solvent. These background spectra are given in Figures 1 through 36. These background spectra illustrate the need to pre-wash any and all wipers prior to analytical use, and also indicate that background spectra from the wiper cloth itself can seriously impact FTIR identification of unknown surface contaminants.

Stock solutions of the eight contaminants of interest were next prepared, such that 1.00 cubic centimeter contained 10 milligrams of contaminant. Using pre-washed wipers (one 4-hour Soxhlet) in glass vials, 1.00 milliliter of each contaminant stock solution was added to individual 1-gram samples of cloth, yielding specimens with 10-milligram contaminant per gram of wiper. These samples were dried overnight in a hood to remove solvent and were then quantitatively transferred to the Soxhlet extractor, using a wash bottle to transfer any residual contaminant adhering to the glass vial. After 4-hour reflux with the solvent being used, and filtration to remove particulates, the NVR was isolated, weighed, and subjected to FTIR analysis. Results are summarized in Table III, and analytical data are given in Tables XXIV through XXXI. FTIR spectra of the original contaminants prior to contact with wiper cloth are given in Figures 37 through 44. FTIR spectra of the contaminant extracts are given in Figures 45 through 205.

Even though all wipers were pre-washed in hopes of eliminating FTIR background arising from the wiper cloth itself, some wiper background is evident in almost all of the spectra, and, in some cases, the wiper background obscures the FTIR scan sufficiently as to render identification almost impossible. The ease of FTIR identification for each extract was rated as either good (easy, for a novice), fair (some skill required), poor (impossible without considerable skill, experience, and access to background spectra), and very poor (almost impossible). As seen from the data in Tables XXIV through XXXI, the contaminants which pose the greatest

challenge are HD-2 grease, Krytox fluorocarbon grease, and hydraulic oil. For HD-2 grease, only methyl chloroform was a suitable solvent, whereas for Krytox, only Freon TF gave satisfactory results. The results for hydraulic oil (Table XXVI) were entirely unexpected, especially the low recovery. The effect of boiling followed by physical agitation was explored to a limited extent, as compared to Soxhlet extraction (repeated reflux). Results are seen in Table XXXII, and recoveries for hydraulic oil were even lower for boiling-shaking than for Soxhlet extraction. Some improvement in FTIR scans for HD-2 and Krytox was seen for boiling-shaking versus Soxhlet. These data illustrate the importance of verifying the suitability of test conditions for each contaminant. Once wiper/solvent choices are finalized for each contaminant/surface combination, extraction details may be optimized as outlined in ETP-0491.

TABLE I
CANDIDATE WIPER MATERIALS

Trade Name	Type	Manufacturer
Absorbond TM	Polyester	Texwipe Company Upper Saddle River, New Jersey 07458
Alphawipe TM	Polyester	Texwipe Company
Anticon 100 TM	Polyester	Thomas West Company P.O. Box 592 Belmont, California 94002
Clean-Pal TM	Nylon	Clean Room Products, Incorporated 1800 Ocean Avenue Ronkonkoma, New York 11779
Crew-3330 TM	Polypropylene	Kimberly-Clark Corporation Roswell, Georgia 30076
Fabwipes TM	Cotton/Polypropylene	Texwipe Company
Foamwipes TM	Polyurethane	Texwipe Company
Miraclewipe TM	Nylon	Texwipe Company
One-Ups TM	Cotton/polyester	Berkshire Corporation Great Barrington, Massachusetts 01230
Polx 1200 TM	Polyester	Berkshire Corporation
Q-Tips	Cotton, glueless	Puritan Company Guilford, Maine 04443
Westwipe TM	Polyester, sealed edge	Thomas West Company
Wonderwipe TM	Nylon tricot	Clean Room Products, Incorporated

TABLE II

ETP-0491 WIPER CLOTH CANDIDATES
 OVERALL SUMMARY OF WIPER EXTRACTION STUDIES

Trade Name	111-TCE	Freon TF	MEK
Fabwipes ¹	A	A	A
Miraclewipe ²	A	A	A
Alphawipe ³	A	A	A
Polx 1200 ³	A	A	A
Anticon 100 ³	B	B	B
Q-Tips, glueless ⁴	B	B	B
Westwipes ³	B	B	B
Absorbond ³	C	C	C
Wonderwipe ²	C	C	C
One-Ups ⁵	C	C	C
Clean-Pal ²	C	C	C
Foamwipes ⁶	C	C	C
Crew-3330 ⁷	C	C	C

Codes: A. Carryover into final phases
 B. Borderline. Retain for possible future study
 in case initial selections do not hold up.
 C. Cancel from further consideration.

¹Cotton/polypropylene

²Nylon

³Polyester

⁴Cotton

⁵Cotton/polyester

⁶Polyurethane

⁷Polypropylene

TABLE III

ETP-0491

EXTRACTION EFFICIENCY STUDY SUMMARY

1. **HD-2 Grease.**
Adequate recovery for all systems except Freon/Anticon, Freon/Miraclewipe, Freon/Alphawipe, Freon/Polx 1200, and MEK/Q-Tips. Good FTIR only for methyl chloroform with Miraclewipe, Fabwipe, Alphawipe, and Polx 1200.
2. **Fluorocarbon Grease.**
Suitable recovery only for Freon. Good FTIR only for Freon/Miraclewipe and Freon/Polx 1200.
3. **Hydraulic Oil.**
Adequate recovery only for Freon/Alphawipe, Freon/Q-Tips, and Freon/Polx 1200. Fair recovery for methyl chloroform/Fabwipe and MEK/Q-Tips. No really good FTIRs. Fair FTIR for methyl chloroform/Fabwipe, Freon/Alphawipe, and Freon/Q-Tips.
4. **Silicone Oil.**
Good recovery for all systems except methyl chloroform/Miraclewipe, Freon/Fabwipe, and Freon/Q-Tips. Good FTIR for all systems except Freon/Q-Tips.
5. **Mineral Oil.**
Good recovery for all systems except MEK/Alphawipe. Good FTIR for all systems except methyl chloroform/Anticon, methyl chloroform/Alphawipe, Freon/Anticon, Freon/Polx 1200, MEK/Anticon, and MEK/Polx 1200.
6. **DOP.**
Good recovery and FTIR for all systems.
7. **Vinyl Tape Adhesive.**
Good recovery for all systems except methyl chloroform/Q-Tips and Freon/Miraclewipe. Good FTIR on all systems.
8. **Teflon Tape Adhesive.**
Good recovery for all systems except Freon/Fabwipe. Good FTIR for all systems.

TABLE IV
NVR BLANK EXTRACTION WITH 111-TCE

Trade Name	Description	Total Extractables ¹	No. of Extractions for Acceptable Level ²
Westwipe	Polyester, sealed edge	0.7	1 (0.1) ³
Air Weave Bleeder Cloth	Polyester	1.3	1 (0.1)
Alphawipe	Polyester	1.3	1 (0.1)
Westwipe Anticon 100	Polyester (aka Polywipe)	1.4	1 (0.2)
Polx 1200	Polyester	1.6	1 (0.1)
Q-Tips, Glueless	Cotton	2.2	1 (0.2)
Miraclewipe	Nylon	1.5	2 (0.2)
Absorbond	Polyester	1.8	2 (0.2)
Wonderwipe	Nylon	8.3	1 (0.2)
One-Ups	Cotton/polyester	11.4	1 (0.6)
Fabwipe	Cotton/polypropylene	18.2	2 (0.4)
Foamwipe	Polyurethane	39.9	2 (0.5)
Clean-Pal	Nylon	31.9	3 (0.4)
Crew 33330	Polypropylene	35.9	2 (0.2)

¹Total four-hour Soxhlet. Mg/gram of cloth.

²Consecutive one-hour Soxhlets on same sample.

³Level of residual extractables after indicated number of extractions, in mg/gram of cloth.

TABLE V
NVR BLANK EXTRACTION WITH FREON TF

Trade Name	Description	Total Extractables ¹	No. of Extractions ² for Acceptable Level ³
Air Weave Bleeder Cloth	Polyester	0.8	1 (0.0) ³
Alphawipe	Polyester	0.5	1 (0.1)
Westwipe	Polyester, sealed edge	0.6	1 (0.1)
Polx 1200	Polyester	0.8	1 (0.1)
Miraclewipe	Nylon	0.6	1 (0.1)
Absorbond	Polyester	0.7	2 (0.0)
Westwipe Anticon 100	Polyester	0.9	1 (0.3)
Q-Tips, Glueless	Cotton	1.9	1 (0.2)
One-Ups	Cotton/polyester	3.3	1 (0.4)
Wonderwipe	Nylon	3.8	1 (0.2)
Clean-Pal	Nylon	10.9	1 (0.3)
Fabwipe	Cotton/polypropylene	10.8	2 (0.5)
Foamwipe	Polyurethane	29.3	2 (0.6)
Crew 33330	Polypropylene	27.1	3 (0.5)

¹Total four-hour Soxhlet; mg/gram of cloth.

²Consecutive one-hour Soxhlets on same sample.

³Level of residual extractables after indicated number of extractions, in mg/gram of cloth.

TABLE VI
NVR BLANK EXTRACTION WITH MEK

Trade Name	Description	Total Extractables ¹	No. of Extractions ² for Acceptable Level ³
Air Weave Bleeder Cloth	Polyester	2.1	1 (0.2) ³
Miraclewipe	Nylon	2.3	1 (0.3)
Westwipe	Polyester, sealed edge	2.6	1 (0.3)
Polx 1200	Polyester	2.9	1 (0.2)
Alphawipe	Polyester	2.6	1 (0.4)
Westwipe Anticon 100	Polyester	2.9	1 (0.4)
Wonderwipe	Nylon	8.8	1 (0.4)
Fabwipe	Cotton/polypropylene	9.1	1 (0.4)
Q-Tips, Glueless	Cotton	4.0	2 (0.5)
Absorbond	Polyester	7.3	2 (0.6)
One-Ups	Cotton/Polyester	13.2	2 (0.2)
Crew-3330	Polypropylene	16.0	3 (0.2)
Foamwipe	Polyurethane	49.9	3 (0.8)
Clean-Pal	Nylon	51.0	4 (0.7)

¹Total four-hour Soxhlet; mg/gram of cloth.

²Consecutive one-hour Soxhlets on same sample.

³Level of residual extractables after indicated number of extractions, in mg/gram of cloth.

TABLE VII
PARTICULATES FROM BLANK EXTRACTION WITH 111-TCE

Trade Name	Description	Total Particulates ¹	No. of Extractions ² for Acceptable Level ³
Polx 1200	Polyester	0.01	0 (.01) ³
Westwipe Anticon 100	Polyester	0.05	0 (.03)
Miraclewipe	Nylon	0.04	1 (.04)
Alphawipe	Polyester	0.05	1 (0.00)
Air Weave Bleeder Cloth	Polyester	0.06	1 (0.00)
Q-Tips, Glueless	Cotton	0.08	1 (.04)
Westwipe	Polyester, sealed edge	0.09	1 (0.00)
Crew 3330	Polypropylene	0.14	1 (.03)
Wonderwipe	Nylon	0.25	1 (.01)
Fabwipe	Cotton/polypropylene	0.26	1 (0.00)
One-Ups	Cotton/polyester	0.28	1 (.02)
Clean-Pal	Nylon	0.34	1 (.06)
Absorbond	Polyester	0.40	2 (0.00)
Foamwipe	Polyurethane	0.42	2 (0.08)

¹Total four-hour Soxhlet; mg/gram of cloth.

²Consecutive one-hour Soxhlets on same sample.

³Level of residual particulates after indicated number of extractions, in mg/gram of cloth.

TABLE VIII
PARTICULATES FROM BLANK EXTRACTION WITH FREON TF

Trade Name	Description	Total Particulates ¹	No. of Extractions ² for Acceptable Level ³
Miraclewipe	Nylon	0.02	0 (.02) ³
Polx 1200	Polyester	0.05	0 (.03)
Westwipe Anticon 100	Polyester	0.10	0 (.07)
Crew 33330	Polypropylene	0.11	1 (.05)
Alphawipe	Polyester	0.13	1 (.03)
Westwipe	Polyester, sealed edge	0.17	1 (.03)
Clean-Pal	Nylon	0.22	1 (0.00)
Air Weave Bleeder Cloth	Polyester	0.24	1 (.06)
Absorbond	Polyester	0.29	2 (0.00)
Fabwipe	Cotton/polypropylene	0.47	2 (.08)
Q-Tips, Glueless	Cotton	0.51	3 (0.00)
Foamwipe	Polyurethane	0.54	3 (.03)
Wonderwipe	Nylon	0.87	3 (.05)
One-Ups	Cotton/polyester	0.74	4 (.45)

¹Total four-hour Soxhlet; mg/gram of cloth.

²Consecutive one-hour Soxhlets on same sample.

³Level of residual particulates after indicated number of extractions, in mg/gram of cloth.

TABLE IX
PARTICULATES FROM BLANK EXTRACTION WITH MEK

Trade Name	Description	Total Particulates ¹	No. of Extractions ² for Acceptable Level ³
Polx 1200	Polyester	0.03	0 (.03) ³
Westwipe	Polyester, sealed edge	0.03	0 (.03)
Westwipe Anticon 100	Polyester	0.04	0 (.02)
Air Weave Bleeder Cloth	Polyester	0.12	0 (.08)
Alphawipe	Polyester	0.03	0 (.03)
Foamwipe	Polyurethane	0.24	1 (0.00)
Wondervipe	Nylon	0.44	1 (.01)
Clean-Pal	Nylon	0.53	1 (0.00)
Miraclewipe	Nylon	0.05	2 (0.00)
Absorbond	Polyester	0.41	2 (0.00)
Q-Tips, Glueless	Cotton	0.15	3 (0.00)
One-Ups	Cotton/polyester	0.41	4 (0.12)
Fabwipe	Cotton/polypropylene	3.01	4 (0.26)
Crew 33330	Polypropylene	6.81	4 (0.19)

¹Total four-hour Soxhlet; mg/gram of cloth.

²Consecutive one-hour Soxhlets on same sample.

³Level of residual particulates after indicated number of extractions, in mg/gram of cloth.

TABLE X

ABSORBOND™ (POLYESTER)
CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	NVR	111-TCE Particulates	NVR	Freon TF Particulates	NVR	MEK Particulates
First Hour	0.9	0.09	Nil	Nil	4.5	0.06
Second Hour	0.7	0.22	0.5	0.29	1.7	0.35
Third Hour	Nil	Nil	Nil	Nil	0.6	Nil
Fourth Hour	<u>0.2</u>	<u>0.09</u>	<u>0.2</u>	<u>Nil</u>	<u>0.5</u>	<u>Nil</u>
Total	1.8	0.40	0.7	0.29	7.3	0.41

Note: Results expressed as mg/gram of wiper.

TM: Texwipe Company
Upper Saddle River, New Jersey 07458

TABLE XI
AIR WEAVE BLEEDER CLOTH™ (POLYESTER)
CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	NVR	111-TCE Particulates	NVR	Freon TF Particulates	NVR	MEK Particulates
First Hour	1.2	0.05	0.8	0.15	1.5	0.08
Second Hour	0.1	Nil	Nil	0.06	0.2	0.03
Third Hour	Nil	Nil	Nil	Nil	0.2	Nil
Fourth Hour	<u>Nil</u>	<u>0.01</u>	<u>Nil</u>	<u>0.03</u>	<u>0.2</u>	<u>0.01</u>
Total	1.3	0.06	0.8	0.24	2.1	0.12

Note: Results expressed as mg/gram of cloth.

TM: Richmond Corporation
Santa Fe Springs, California

TABLE XII

ALPHAWIPE™ (POLYESTER)
CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	NVR	111-TCE Particulates	NVR	Freon TF Particulates	NVR	MEK Particulates
First Hour	1.2	0.04	0.3	0.04	1.9	Nil
Second Hour	0.1	Nil	0.1	Nil	0.4	Nil
Third Hour	Nil	Nil	0.1	0.03	0.2	0.03
Fourth Hour	<u>Nil</u>	<u>0.01</u>	<u>0.1</u>	<u>0.06</u>	<u>0.1</u>	<u>Nil</u>
Total	1.3	0.05	0.6	0.13	2.6	0.03

Note: Results expressed as mg/gram of wiper.

TM: Texwipe Company
Upper Saddle River, New Jersey 07458

TABLE XIII

CLEAN-PAL™ (NYLON)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	NVR	111-TCE Particulates	NVR	Freon TF Particulates	NVR	MEK Particulates
First Hour	27.9	0.17	10.0	0.11	43.0	0.49
Second Hour	2.5	0.06	0.3	Nil	3.6	Nil
Third Hour	1.0	0.11	0.3	0.11	2.9	0.04
Fourth Hour	<u>0.4</u>	<u>Nil</u>	<u>0.3</u>	<u>Nil</u>	<u>1.5</u>	<u>Nil</u>
Total	31.8	0.34	10.9	0.22	51.0	0.53

Note: Results expressed as mg/gram of wiper.

TM: Clean Room Products, Incorporated
 1800 Ocean Avenue
 Ronkonkoma, New York 11779-9990

TABLE XIV

CREWTM (POLYPROPYLENE)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	33.5	0.09	20.9	0.06	14.7	5.92
Second Hour	1.9	0.03	5.2	0.05	0.4	0.51
Third Hour	0.3	0.03	0.5	Nil	0.7	0.19
Fourth Hour	<u>0.2</u>	<u>Nil</u>	<u>0.5</u>	<u>Nil</u>	<u>0.2</u>	<u>0.19</u>
Total	35.9	0.14	27.1	0.11	16.0	6.81

Note: Results expressed as mg/gram of wiper.

TM: Kimberly-Clark Corporation
 Roswell, Georgia 30076

TABLE XV

FABWIPE™ (COTTON/POLYPROPYLENE)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	16.2	0.22	9.3	0.26	8.3	1.94
Second Hour	1.4	Nil	0.8	0.13	0.4	0.30
Third Hour	0.4	0.04	0.5	0.08	0.3	0.51
Fourth Hour	<u>0.2</u>	<u>Nil</u>	<u>0.2</u>	<u>Nil</u>	<u>0.1</u>	<u>0.26</u>
Total	18.2	0.26	10.8	0.47	9.1	3.02

Note: Results expressed as mg/gram of wiper.

TM: Texwipe Company
 Upper Saddle River, New Jersey 07458

TABLE XVI

FOAMWIPE™ (POLYURETHANE)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	38.0	0.28	27.2	0.24	46.2	0.24
Second Hour	1.1	Nil	1.4	0.09	1.6	Nil
Third Hour	0.5	0.08	0.6	0.18	1.3	Nil
Fourth Hour	<u>0.3</u>	<u>0.06</u>	<u>0.1</u>	<u>0.03</u>	<u>0.8</u>	<u>Nil</u>
Total	39.9	0.42	29.3	0.54	49.9	0.24

Note: Results expressed as mg/gram of wiper.

TM: Texwipe Company
 Upper Saddle River, New Jersey 07458

TABLE XVII

GLUELESS™ Q-TIPS (COTTON)
CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	1.7	0.04	1.6	Nil	2.5	Nil
Second Hour	0.1	Nil	Nil	Nil	0.5	Nil
Third Hour	0.3	0.04	0.1	0.51	0.5	0.15
Fourth Hour	<u>0.1</u>	<u>Nil</u>	<u>0.2</u>	<u>Nil</u>	<u>0.5</u>	<u>Nil</u>
Total	2.2	0.08	1.9	0.51	4.0	0.15

Note: Results expressed as mg/gram of Q-Tip ends.

TM: Puritan Company
Guilford, Maine 04443

TABLE XVIII

MIRACLEWIPE™ (NYLON)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	1.1	Nil	0.4	Nil	1.6	Nil
Second Hour	0.1	0.04	0.1	0.01	0.3	0.05
Third Hour	0.2	Nil	0.1	Nil	0.2	Nil
Fourth Hour	<u>0.1</u>	<u>Nil</u>	<u>0.1</u>	<u>0.01</u>	<u>0.1</u>	<u>Nil</u>
Total	1.5	0.04	0.7	0.02	2.2	0.05

Note: Results expressed as mg/gram of wiper.

TM: Texwipe Company
 Upper Saddle River, New Jersey 07458

TABLE XIX

ONE/UPSTM (COTTON/POLYESTER)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	9.9	0.07	2.9	0.14	12.3	0.19
Second Hour	0.6	0.02	0.4	0.05	0.5	Nil
Third Hour	0.6	0.12	Nil	0.10	0.2	0.10
Fourth Hour	<u>0.3</u>	<u>0.07</u>	<u>Nil</u>	<u>0.45</u>	<u>0.2</u>	<u>0.12</u>
Total	11.4	0.28	3.3	0.74	13.2	0.41

Note: Results expressed as mg/gram of wiper.

TM: Berkshire Corporation
 Great Barrington, Massachusetts 01230

TABLE XX

POLYL200™ (POLYESTER)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	1.3	0.01	0.4	0.03	2.2	Nil
Second Hour	0.1	Nil	0.1	0.02	0.2	0.03
Third Hour	0.1	Nil	0.1	Nil	0.3	Nil
Fourth Hour	<u>0.1</u>	<u>Nil</u>	<u>0.2</u>	<u>Nil</u>	<u>0.2</u>	<u>Nil</u>
Total	1.6	0.01	0.8	0.05	2.9	0.03

Note: Results expressed as mg/gam of wiper.

TM: Berkshire Corporation
 Great Barrington, Massachusetts 01230

TABLE XXI

WESTWIPESTM (ANTICON 100) (POLYESTER)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	1.0	Nil	0.4	Nil	1.9	0.02
Second Hour	0.2	0.03	0.3	0.07	0.4	Nil
Third Hour	Nil	0.02	0.1	0.03	0.3	0.02
Fourth Hour	<u>0.2</u>	<u>Nil</u>	<u>0.1</u>	<u>Nil</u>	<u>0.3</u>	<u>Nil</u>
Total	1.4	0.05	0.9	0.10	2.9	0.04

Note: Results expressed as mg/gram of wiper.

TM: Thomas E. West Company
 P.O. Box 592
 Belmont, California 94002

TABLE XXII

WESTWIPESTM (SEALED EDGES) (POLYESTER)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	0.6	0.09	0.30	0.14	1.7	0.03
Second Hour	0.1	Nil	0.10	0.03	0.3	Nil
Third Hour	Nil	Nil	0.10	Nil	0.4	Nil
Fourth Hour	<u>Nil</u>	<u>Nil</u>	<u>0.05</u>	<u>Nil</u>	<u>0.2</u>	<u>Nil</u>
Total	0.7	0.09	0.60	0.17	2.6	0.03

Note: Results expressed as mg/gram of wiper.

TM: Thomas E. West Company
 P.O. Box 592
 Belmont, California 94002

TABLE XXIII

WONDER-WIPETM (NYLON)
 CONSECUTIVE SOXHLET EXTRACTIONS ON THE SAME SAMPLE

	111-TCE		Freon TF		MEK	
	NVR	Particulates	NVR	Particulates	NVR	Particulates
First Hour	8.0	0.22	3.4	0.47	8.0	0.54
Second Hour	0.2	0.01	0.2	0.20	0.4	0.01
Third Hour	0.1	0.01	0.2	0.15	0.2	Nil
Fourth Hour	<u>0.0</u>	<u>0.01</u>	<u>0.0</u>	<u>0.05</u>	<u>0.2</u>	<u>0.44</u>
Total	8.3	0.25	3.8	0.87	8.8	0.99

Note: Results expressed as mg/gram of wiper.

TM: Clean Room Products, Incorporated
 1800 Ocean Avenue
 Ronkonkoma, New York 11779-9990

TABLE XXIV

SOHXLLET EXTRACTION¹ OF HD-2 GREASE FROM VARIOUS WIPER MATERIALS^{2,3}

Wiper	111-TCE ⁴		Freon TF		MEK	
	% Recovery	FTIR ID	% Recovery	FTIR ID	% Recovery	FTIR ID
Anticon 100 Polyester	89.9	Fair	78.9	Poor	92.9	Very poor
Miraclewipe Nylon	105.9	Good	76.9	Very poor	98.9	Poor
Fabwipe Cotton/polypropylene	104.9	Good	90.9	Very poor	91.9	Poor
Alphawipe Polyester	89.9	Good	71.9	Poor	86.9	Very Poor
Q-Tips, Glueless Cotton	95.8	Poor	103.8	Very poor	72.0	Very poor
Polx 1200 Polyester	93.9	Good	70.9	Poor	87.0	Poor

¹Four-hour reflux.

²Wiper material prewashed with solvent used in extraction.

³About 10 mg of HD-2 added per gram of wiper.

⁴Methyl chloroform.

TABLE XXV

SOHXLLET EXTRACTION¹ OF KRYTOX FLUOROCARBON GREASE FROM VARIOUS WIPER MATERIALS^{2,3}

Wiper	111-TCE ⁴		Freon TF		MEK	
	% Recovery	FTIR ID	% Recovery	FTIR ID	% Recovery	FTIR ID
Anticon 100 Polyester	64.8	Fair	94.2	Fair	20.8	Poor
Miraclewiper Nylon	69.5	Fair	104.8	Good	16.8	Poor
Fabwiper Cotton/polypropylene	37.9	Fair	104.8	Fair	18.8	Poor
Alphawiper Polyester	68.3	Poor	66.5	Fair	12.9	Fair
Q-Tips, Glueless Cotton	61.2	Poor	110.7	Fair	10.0	Poor
Polx 1200 Polyester	66.0	Good	104.8	Good	15.8	Fair

¹Four-hour reflux.

²Wiper material prewashed with solvent used in extraction.

³About 10 mg of Krytox added per gram of wiper.

⁴Methyl chloroform.

TABLE XXVI

SOXHLET EXTRACTION¹ OF HYDRAULIC OIL FROM VARIOUS WIPER MATERIALS^{2,3}

Wiper	111-TCE ⁴		Freon TF		MEK	
	% Recovery	FTIR ID	% Recovery	FTIR ID	% Recovery	FTIR ID
Anticon 100 Polyester	61.7	Very poor	31.9	Very poor	78.7	Very poor
Miraclewiper Nylon	42.6	Poor	46.8	Fair	48.9	Fair
Fabwiper Cotton/polypropylene	72.3	Fair	34.0	Fair	61.7	Fair
Alphawiper Polyester	31.9	Very poor	85.1	Poor	34.0	Fair
Q-Tips, Glueless Cotton	68.1	Fair	85.1	Fair	76.6	Poor
Polx 1200 Polyester	25.5	Very poor	87.2	Very poor	53.2	Poor

¹Four-hour reflux.

²Wiper materials prewashed with solvent used in extraction.

³About 10 mg of hydraulic oil added per gram of wiper.

⁴Methyl chloroform.

TABLE XXVII

SOXHLET EXTRACTION¹ OF SILICONE OIL FROM VARIOUS WIPER MATERIALS^{2,3}

Wiper	111-TCE ⁴		Freon TF		MEK	
	% Recovery	FTIR ID	% Recovery	FTIR ID	% Recovery	FTIR ID
Anticon 100 Polyester	104.5	Good	87.6	Good	106.5	Good
Miraclewipe Nylon	79.6	Good	102.5	Good	105.5	Good
Fabwipe Cotton/polypropylene	115.4	Good	47.8	Good	109.5	Good
Alphawipe Polyester	94.5	Good	113.4	Good	104.5	Good
Q-Tips, Glueless Cotton	107.4	Good	49.8	Fair	111.0	Good
Polx 1200 Polyester	103.5	Good	107.5	Good	95.5	Good

¹Four-hour reflux.

²Wiper materials prewashed with solvent used in extraction.

³About 10 mg of silicone oil applied per gram of wiper.

⁴Methyl chloroform.

TABLE XXVIII

SOXHLET EXTRACTION¹ OF MINERAL OIL FROM VARIOUS WIPER MATERIALS^{2,3}

Wiper	111-TCE ⁴		Freon TF		MEK	
	% Recovery	FTIR ID	% Recovery	FTIR ID	% Recovery	FTIR ID
Anticon 100 Polyester	103.5	Fair	84.6	Fair	105.5	Fair
Miraclewiper Nylon	96.5	Good	89.6	Good	106.5	Good
Fabwipe Cotton/polypropylene	111.4	Good	101.5	Good	97.5	Good
Alphawipe Polyester	86.6	Fair	89.6	Good	68.7	Good
Q-Tips, Glueless Cotton	97.4	Good	83.7	Good	111.6	Good
Polx 1200 Polyester	97.5	Good	113.4	Fair	102.5	Fair

¹Four-hour reflux.

²wiper materials prewashed with solvent used in extraction.

³About 10 mg of mineral oil applied per gram of wiper.

⁴Methyl chloroform.

TABLE XXIX

SOHXLLET EXTRACTION¹ OF DOP FROM VARIOUS WIPER MATERIALS^{2,3}

Wiper	111-TCE ⁴		Freon TF		MEK	
	% Recovery	FTIR ID	% Recovery	FTIR ID	% Recovery	FTIR ID
Anticon 100 Polyester	119.6	Good	106.7	Good	118.6	Good
Miraclewiper Nylon	103.6	Good	110.7	Good	108.6	Good
Fabwiper Cotton/polypropylene	118.6	Good	108.7	Good	106.7	Good
Alphawiper Polyester	113.6	Good	119.6	Good	96.7	Good
Q-Tips, Glueless Cotton	105.8	Good	119.7	Good	113.8	Good
Polx 1200 Polyester	118.6	Good	121.6	Good	106.9	Good

¹Four-hour reflux.

²Wiper materials prewashed with solvent used in extraction.

³About 10 mg of DOP applied per gram of wiper.

⁴Methyl chloroform.

TABLE XXX

SOHXLLET EXTRACTION¹ OF YELLOW VINYL TAPE ADHESIVE* FROM VARIOUS WIPER MATERIALS^{2,3}

Wiper	111-TCE ⁴		Freon TF		MEK	
	% Recovery	FTIR ID	% Recovery	FTIR ID	% Recovery	FTIR ID
Anticon 100 Polyester	93.0	Good	80.3	Good	110.5	Good
Miraclewipe Nylon	101.9	Good	50.9	Good	107.7	Good
Fabwipe Cotton/polypropylene	118.5	Good	93.0	Good	107.7	Good
Alphawipe Polyester	111.6	Good	97.9	Good	105.8	Good
Q-Tips, Glueless Cotton	76.4	Good	90.2	Good	109.6	Good
Polx 1200 Polyester	105.8	Good	94.0	Good	109.7	Good

¹Four-hour reflux.

²Wiper materials prewashed with solvent used in extraction.

³About 10 mg of vinyl tape extract applied per gram of wiper.

⁴Methyl chloroform.

*Permacel, New Brunswick, New Jersey 08903

TABLE XXXI

SOXHLET EXTRACTION¹ OF TEFLON TAPE ADHESIVE* FROM VARIOUS WIPER MATERIALS^{2,3}

Wiper	111-TCE ⁴		Freon TF		MEK	
	% Recovery	FTIR ID	% Recovery	FTIR ID	% Recovery	FTIR ID
Anticon 100 Polyester	97.0	Good	105.9	Good	113.9	Good
Miraclewipe Nylon	111.9	Good	103.0	Good	105.0	Good
Fabwipe Cotton/polypropylene	117.7	Good	71.3	Good	113.8	Good
Alphawipe Polyester	108.7	Good	117.0	Good	105.0	Good
Q-Tips, Glueless Cotton	116.8	Good	112.9	Good	103.0	Good
Polx 1200 Polyester	101.0	Good	111.9	Good	105.9	Good

¹Four-hour reflux.

²Wiper materials prewashed with solvent used in extraction.

³About 10 mg of Teflon tape extract applied per gram of wiper.

⁴Methyl chloroform.


*"Fluoroglas"TM, Dodge Company.

TABLE XXXII

COMPARISON OF SOXHLET EXTRACTION
VERSUS BOILING-SHAKING EXTRACTION


System	Soxhlet		Boiling-Shaking	
	% Recovery	FTIR ID	% Recovery	FTIR ID
HD-2/Anticon/TCE	89.9	Fair	100.9	Fair
HD-2/Anticon/Freon TF	78.9	Poor	77.9	Very poor
HD-2/Miraclewipes/Freon TF	76.9	Very poor	80.9	Poor
HD-2/Fabwipes/Freon TF	90.9	Very poor	85.9	Poor
HD-2/Miraclewipes/MEK	98.9	Poor	85.9	Good
HD-2/Fabwipes/MEK	91.9	Poor	104.9	Good
HD-2/Polx 1200/MEK	87.0	Poor	88.9	Good
Krytox/Miraclewipes/TCE	69.5	Fair	68.2	Good
Krytox/Polx 1200/TCE	66.0	Good	62.3	Good
Krytox/Anticon/Freon TF	94.2	Fair	87.0	Good
Krytox/Fabwipes/Freon TF	104.8	Fair	93.0	Good
Krytox/Alphawipes/Freon TF	66.5	Fair	88.0	Good
Hydraulic oil/Alphawipes/Freon TF	85.1	Poor	35.1	Very poor
Hydraulic oil/Q-Tips/Freon TF	85.1	Fair	26.2	Fair
Hydraulic oil/Anticon/MEK	78.7	Very poor	32.1	Poor
Hydraulic oil/Fabwipes/MEK	61.7	Fair	32.1	Fair
Hydraulic oil/Fabwipes/TCE	72.3	Fair	37.1	Fair
Hydraulic oil/Q-Tips/TCE	68.1	Fair	30.2	Poor

Figure 1.

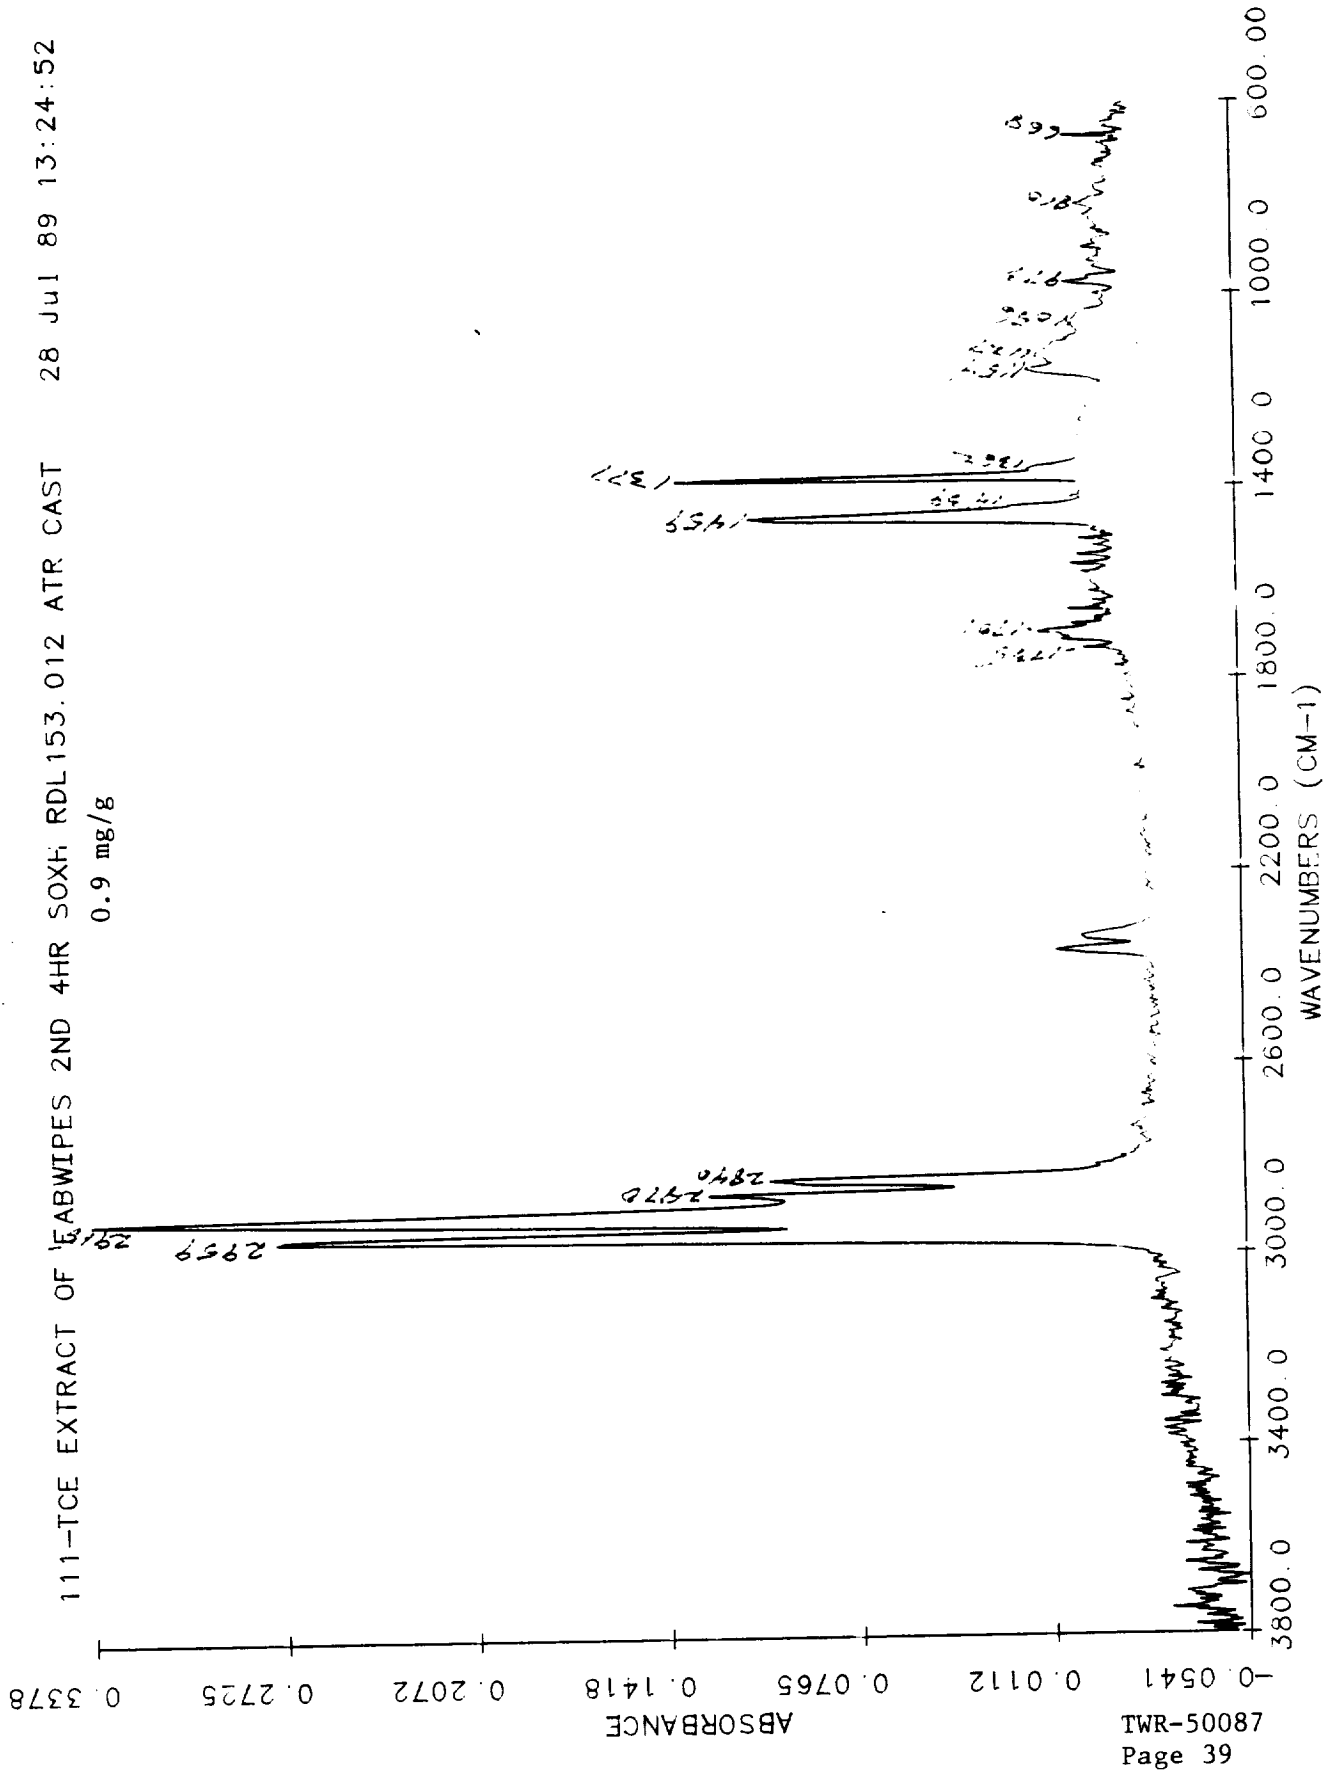


ORIGINAL PAGE IS
OF POOR QUALITY

Figure 2.

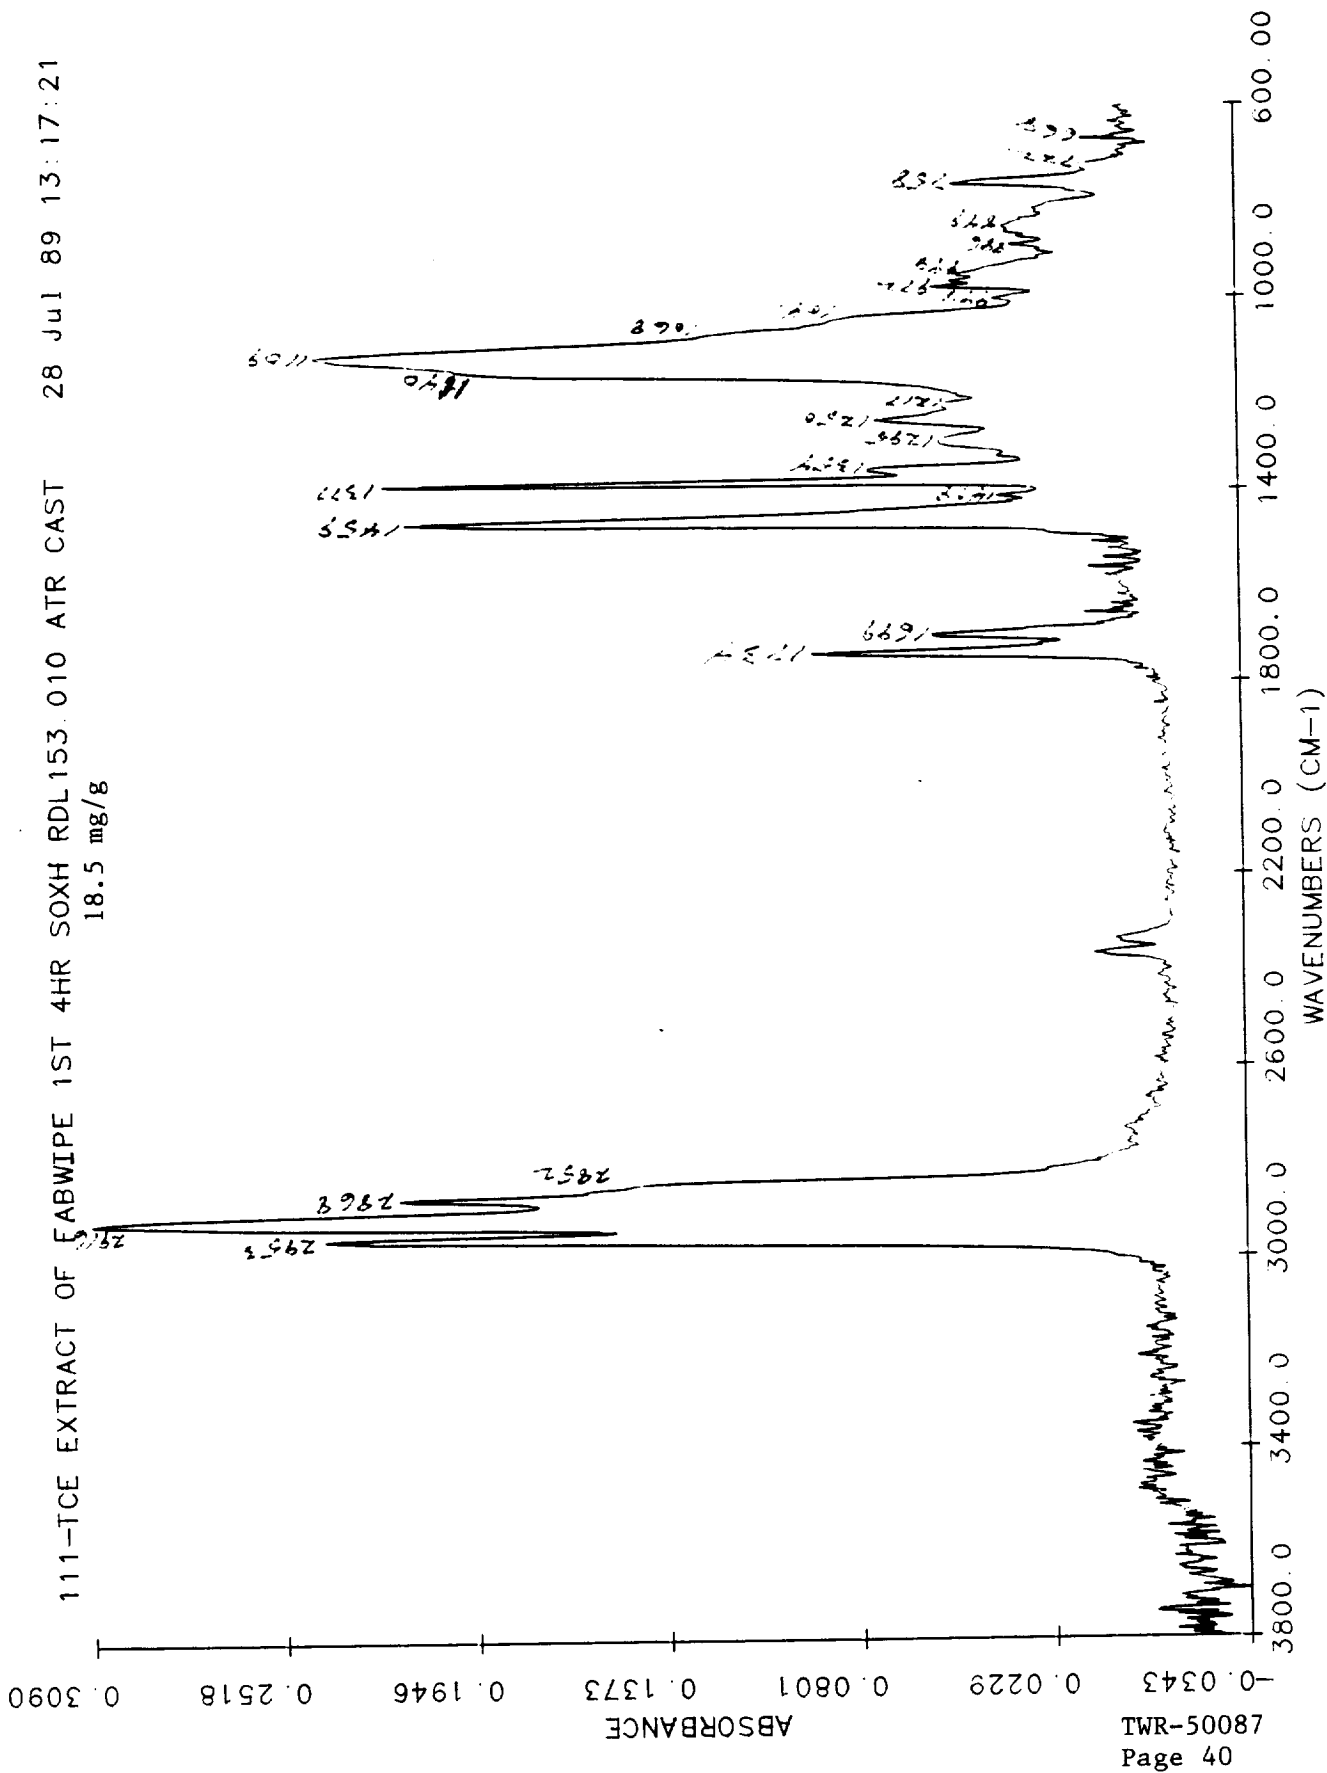

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 3.

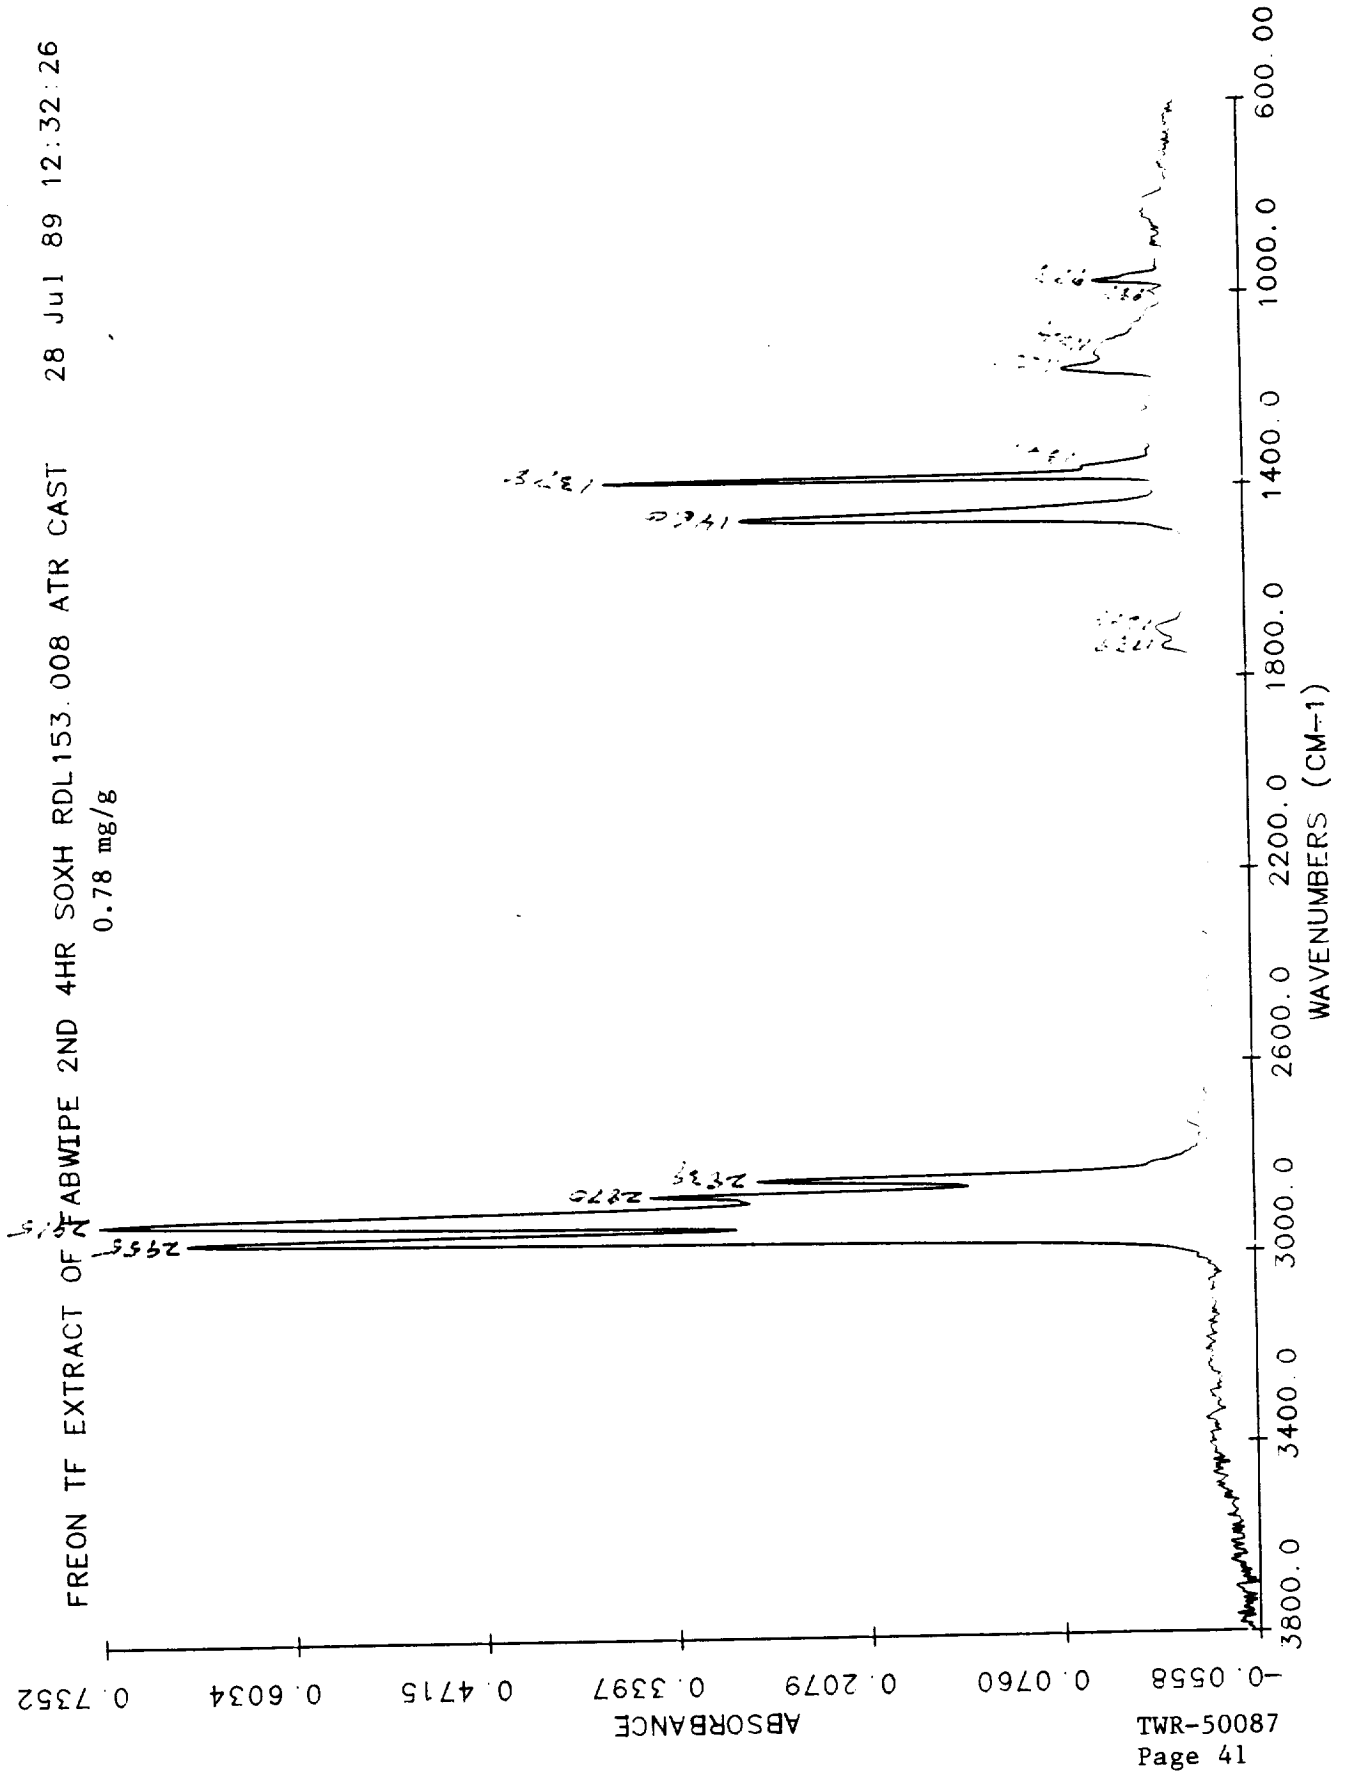

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 4.

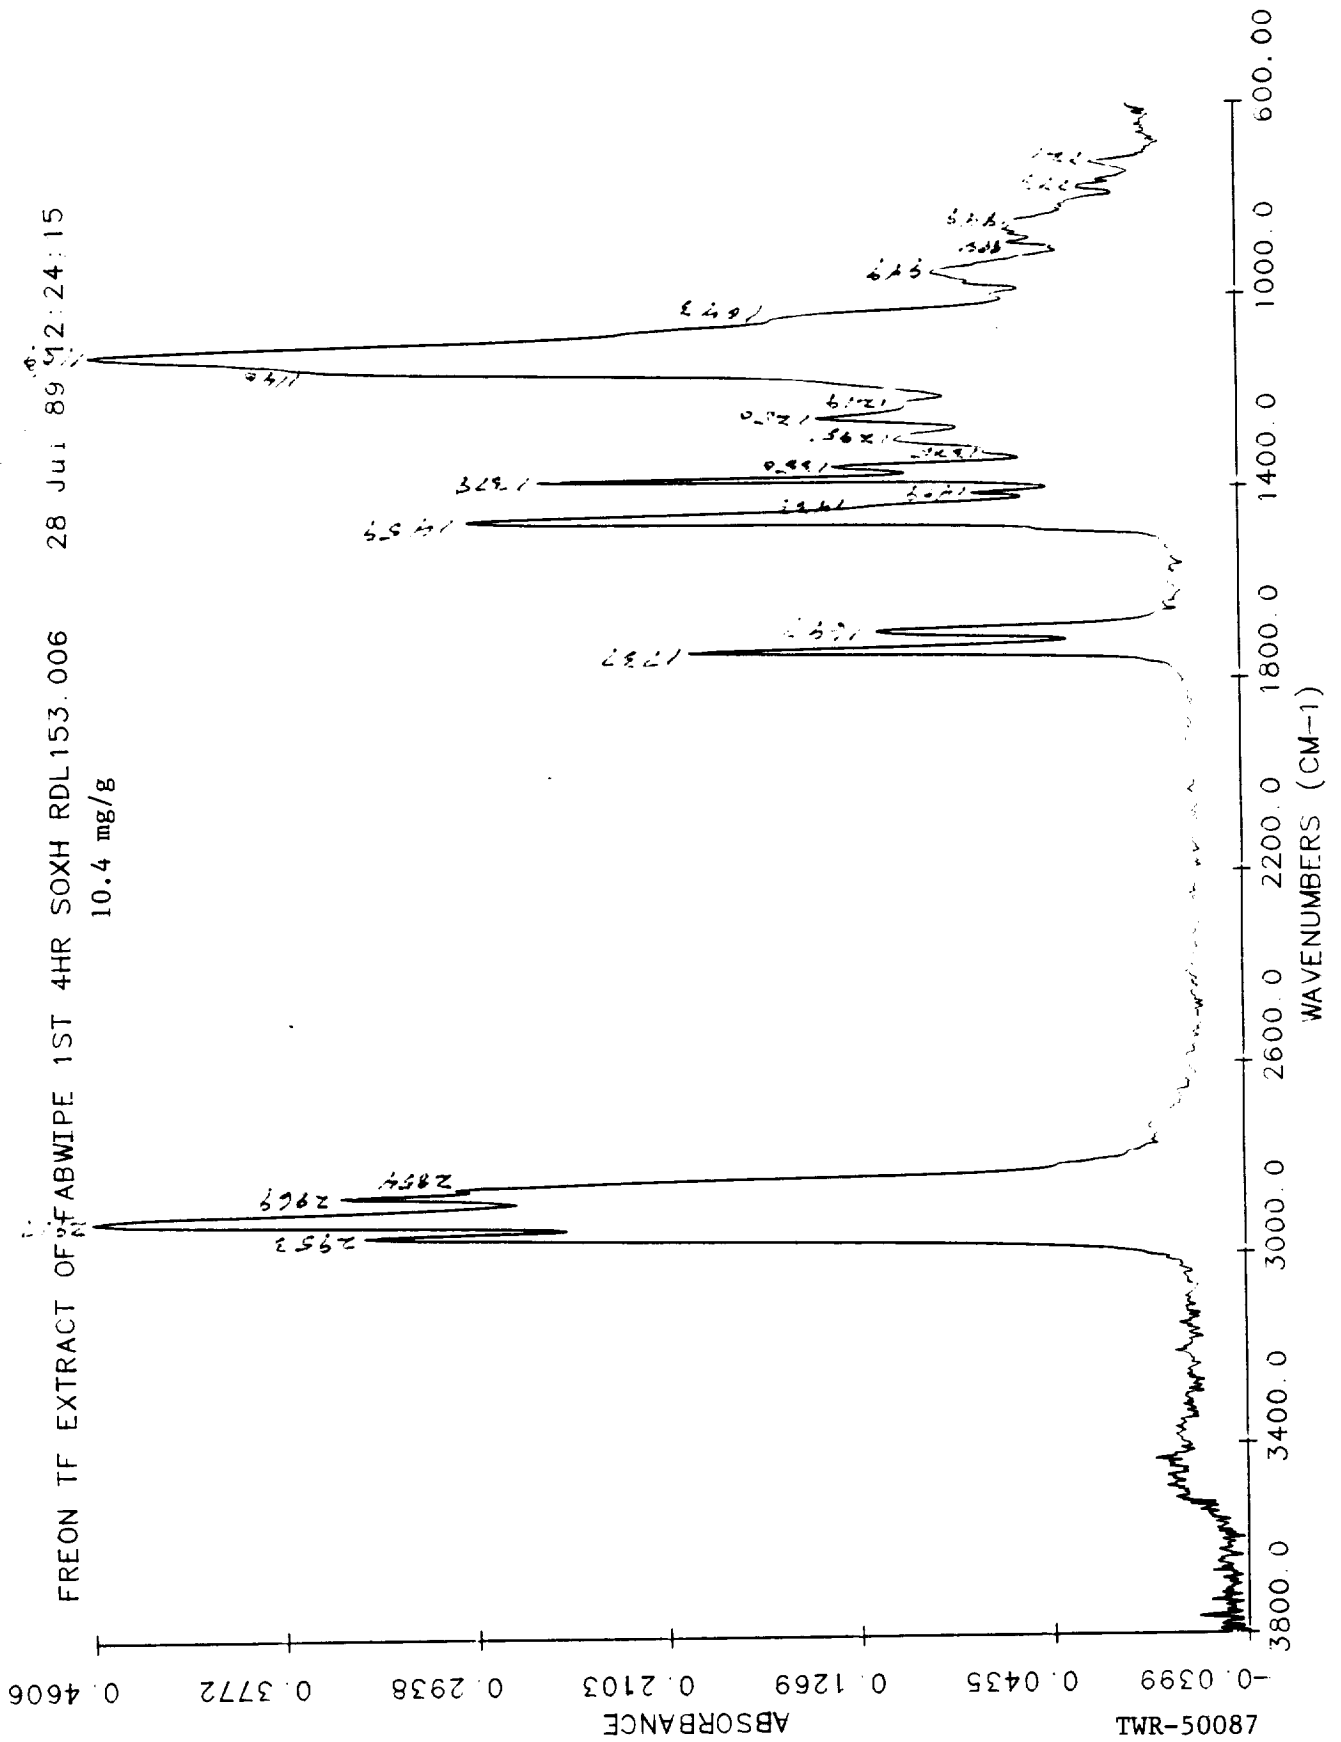


Figure 5.



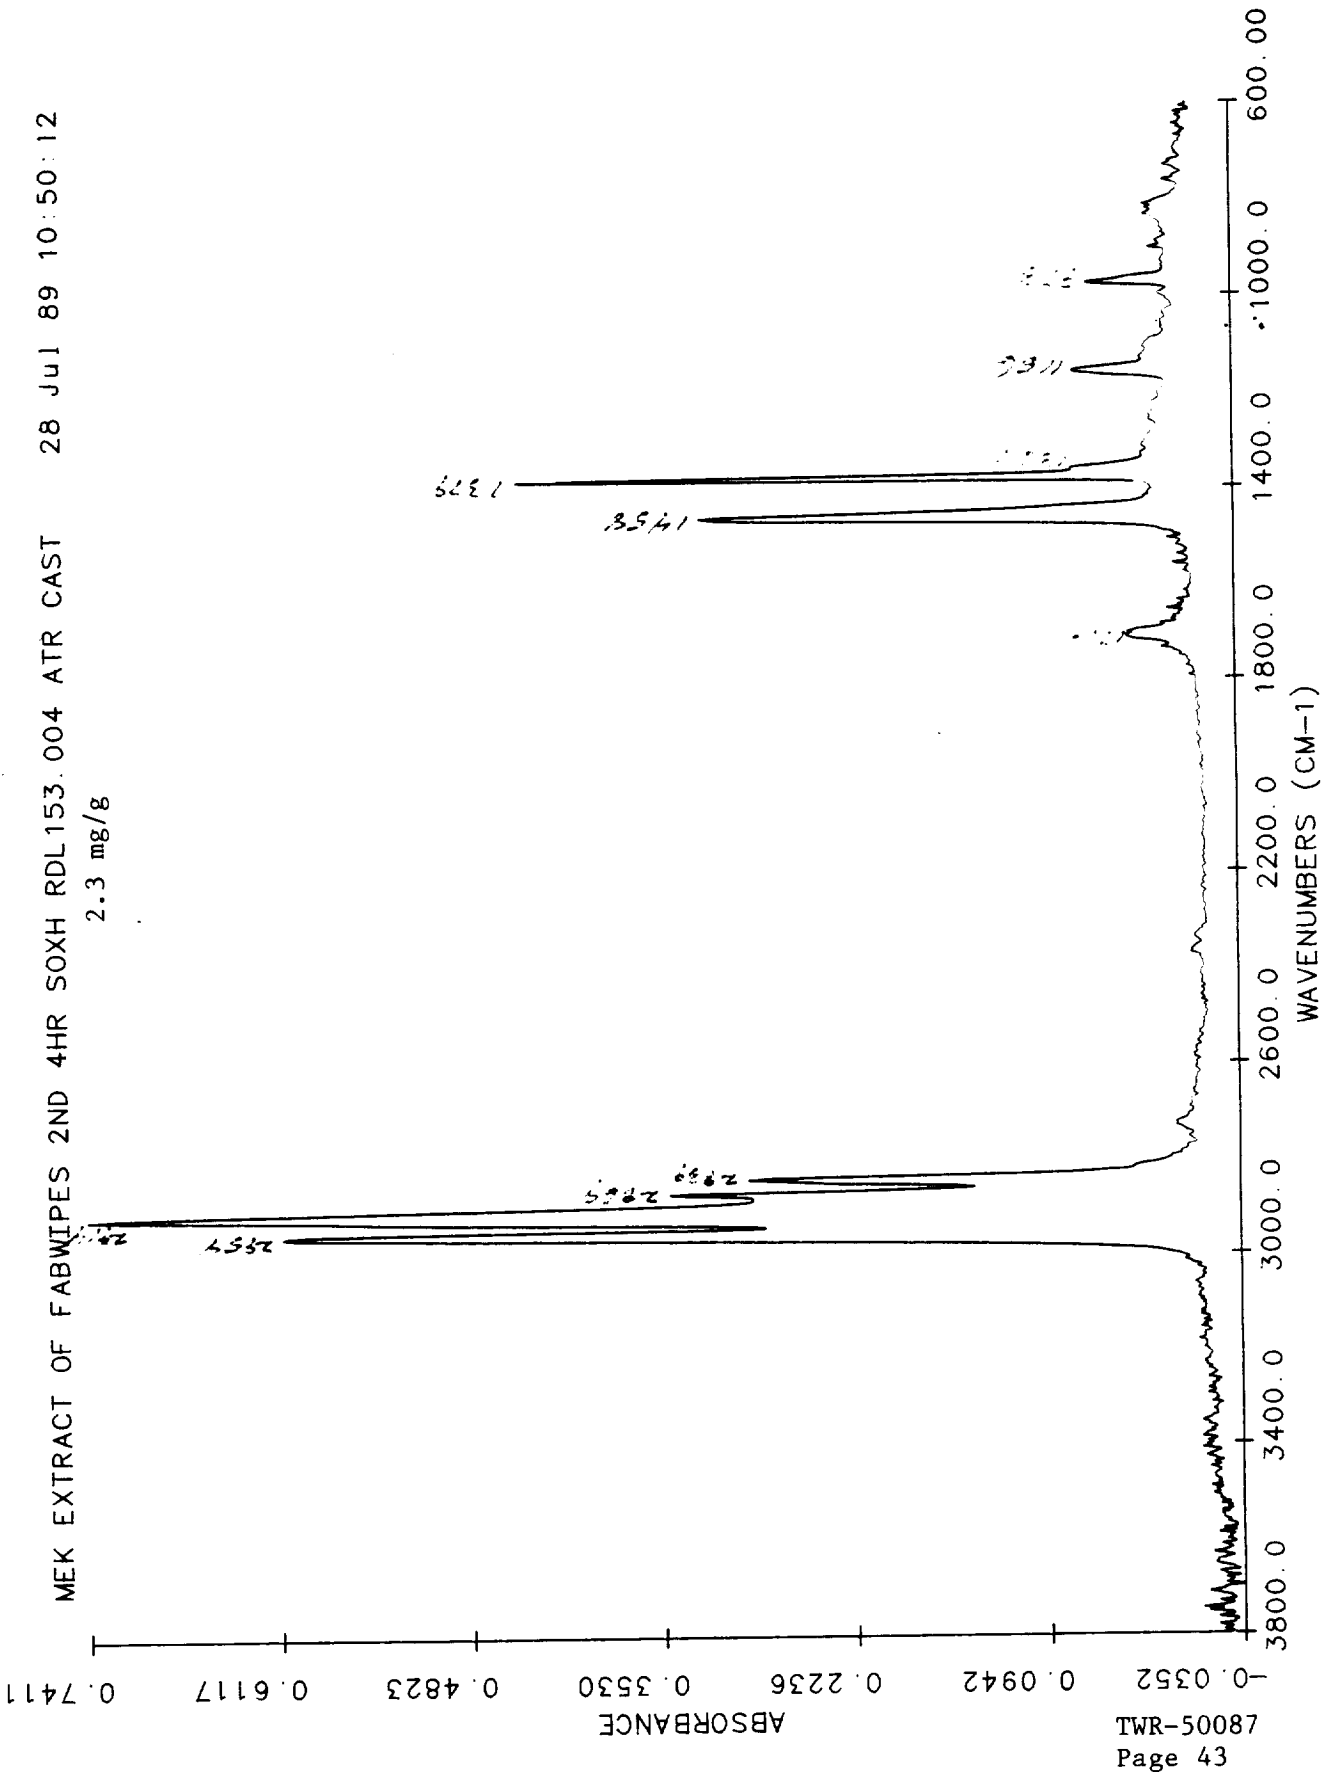


Figure 6.

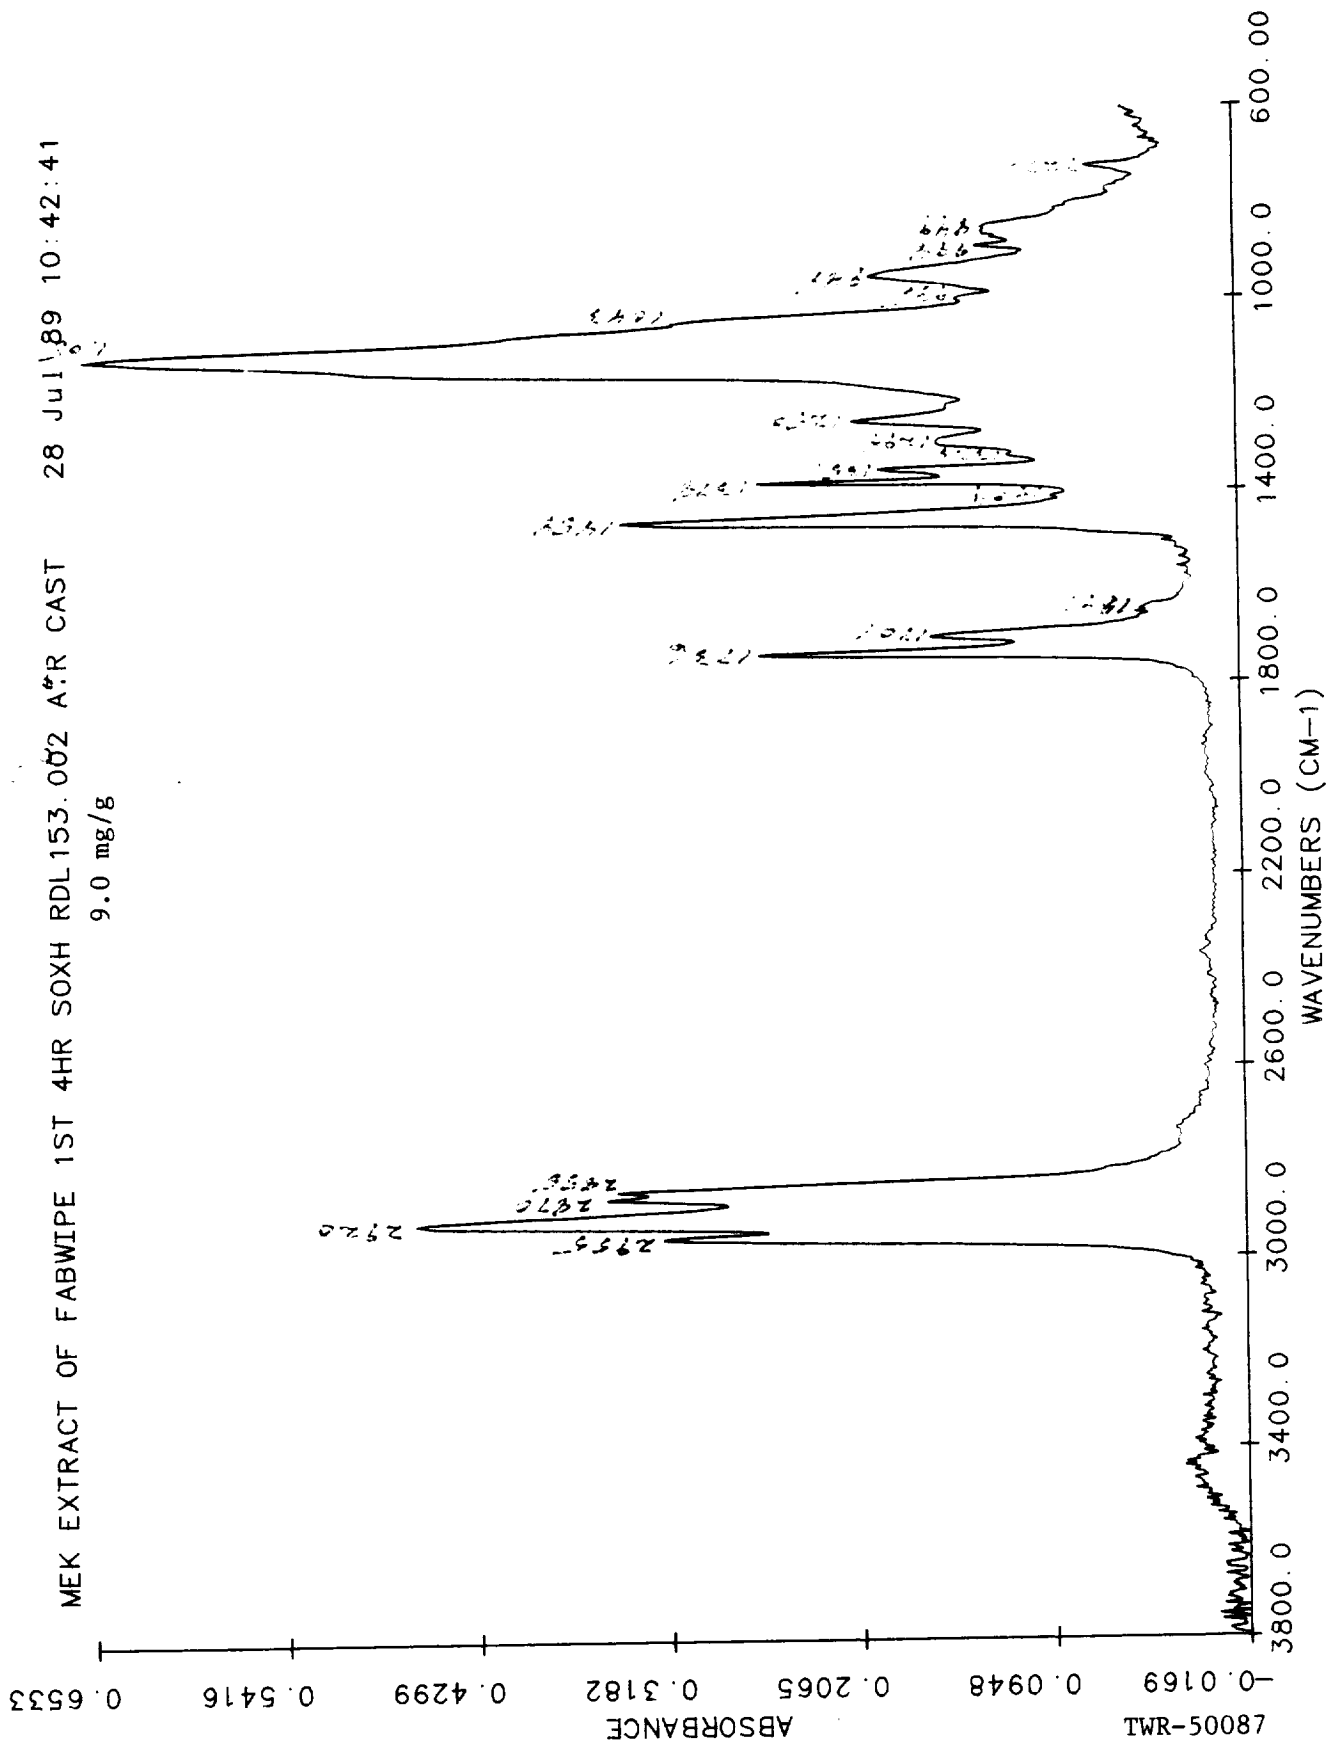


MECHCL3 EXTRACT OF MIRACLEWIPE 2ND 4-HR SOXH RDL2149.005 ATR CAST 14 Jul 89 15:09:30
 0.1 mg/g

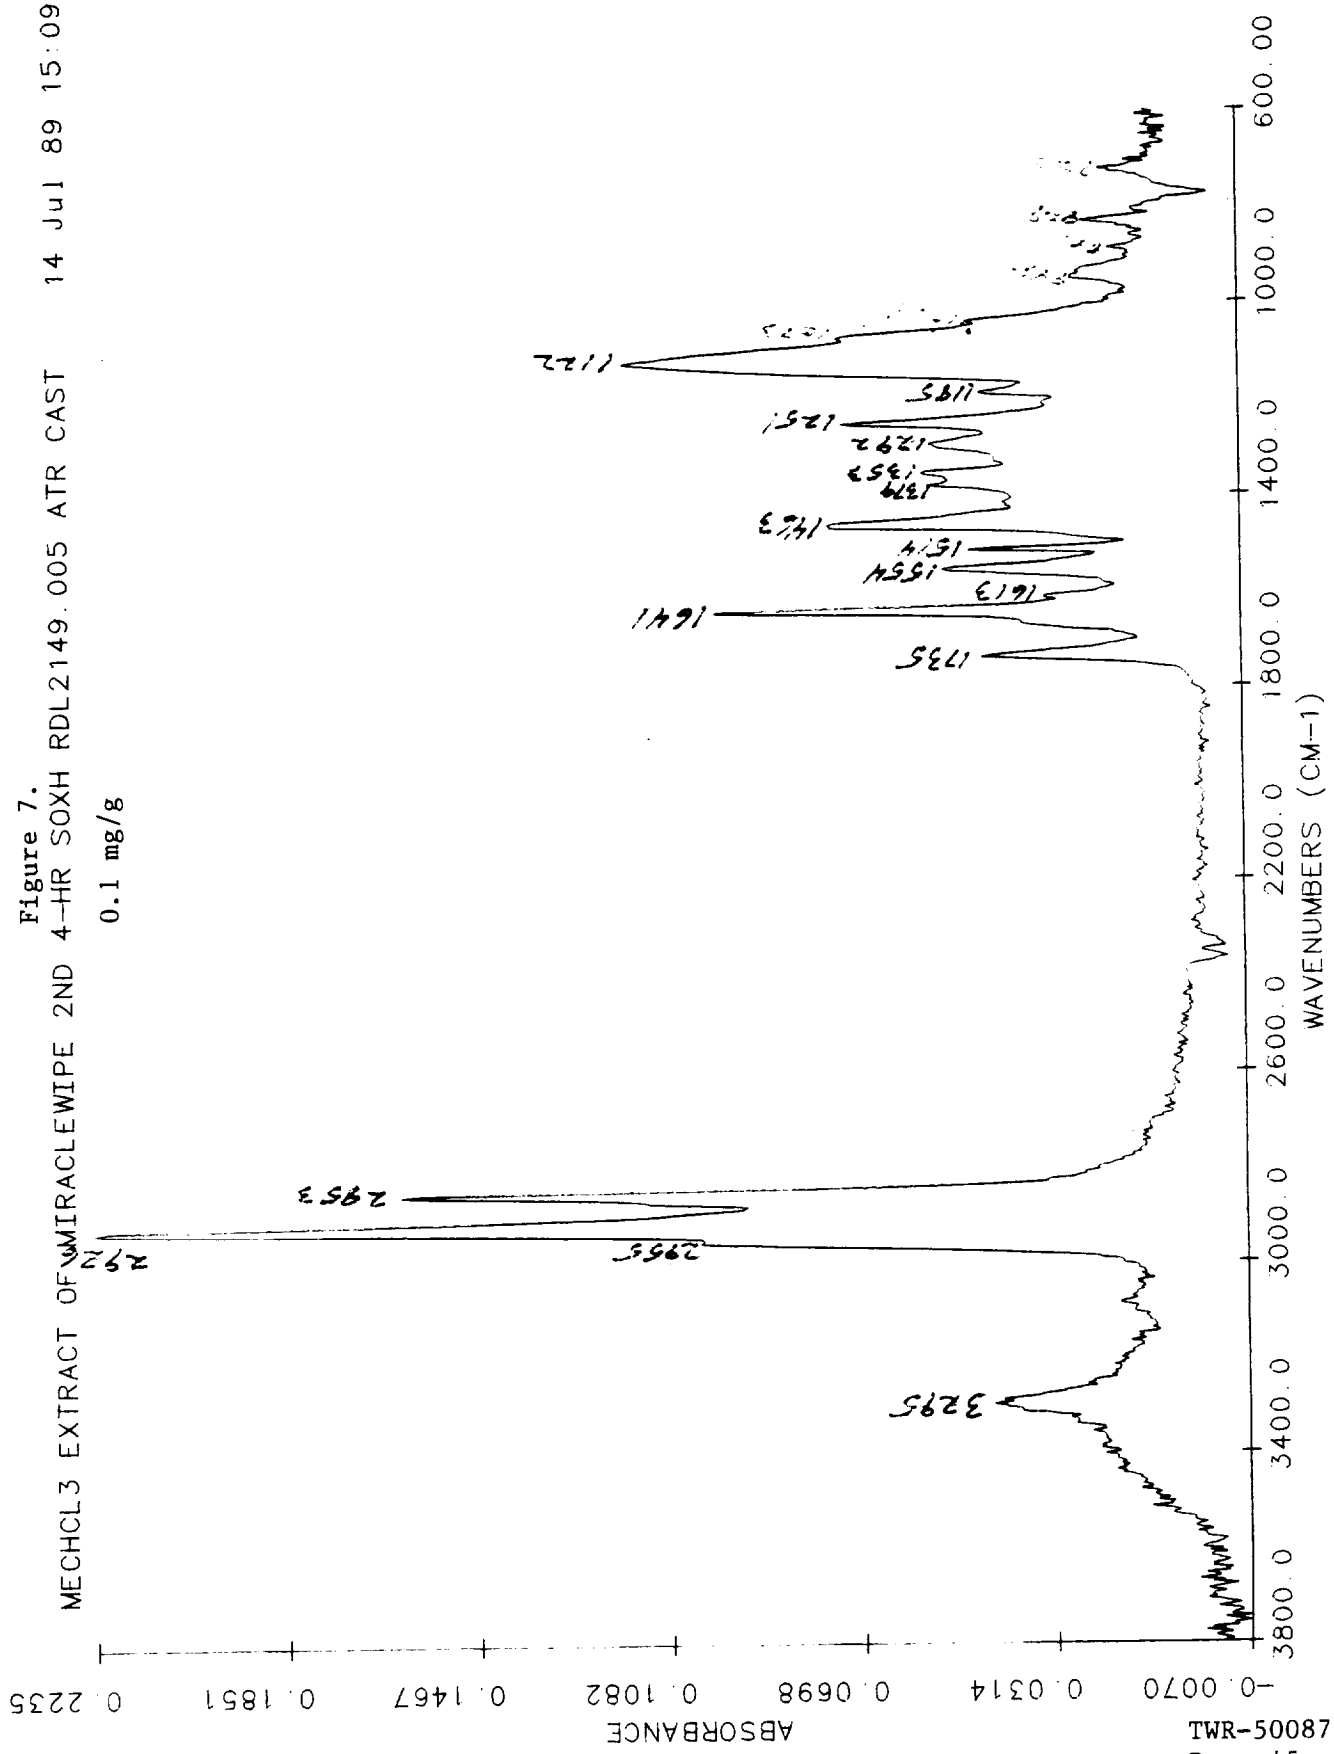


MECHCL3 EXTRACT OF MIRACLEWIPE 1ST 4-HR SOXH RDL149.005 ATR CAST 1.1 mg/g

14 Jul 89 14:29:10

Figure 8.

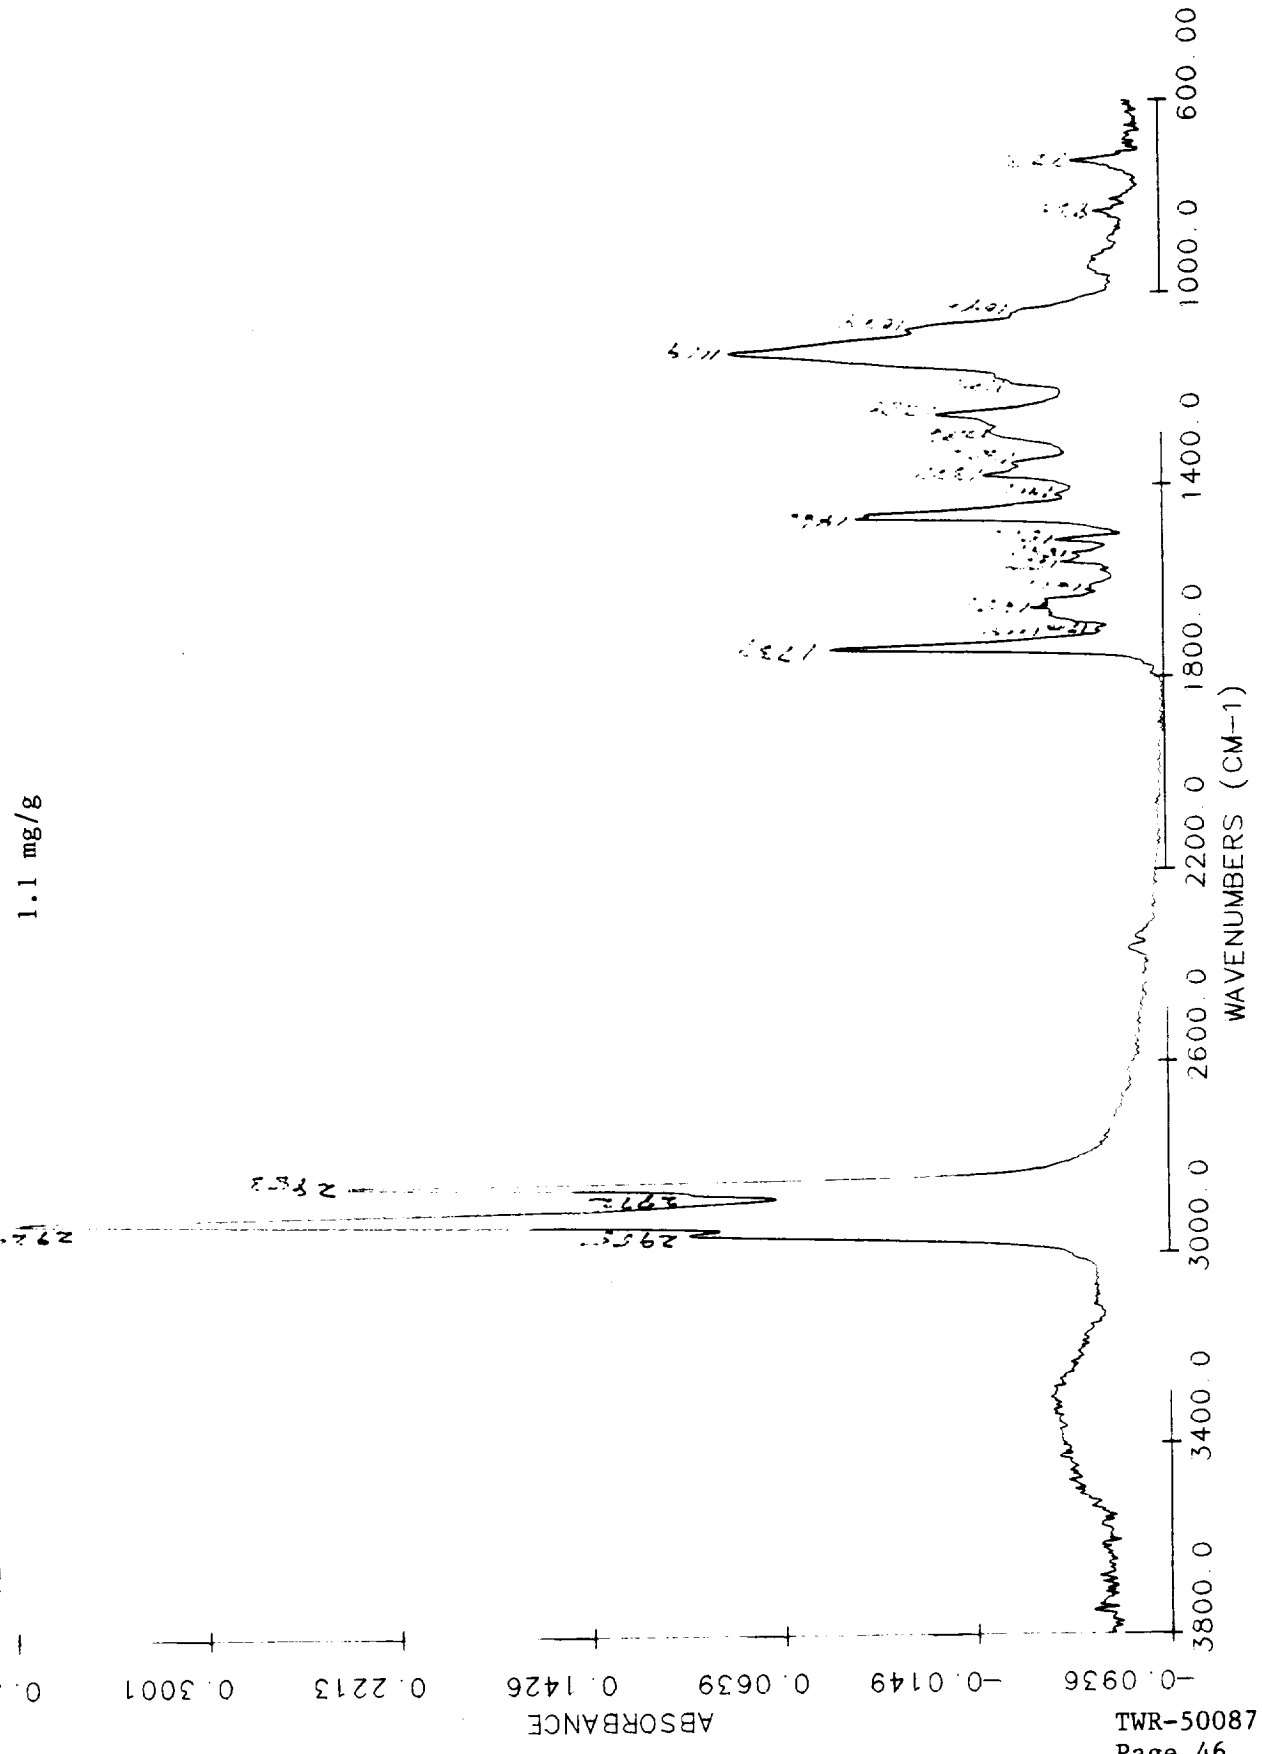


FREON TF EXTRACT OF MIRACLEWIPE 2ND 4-HR SOXH RDL2148.005 14 Jul 89 13:30:19
0.1 mg/g

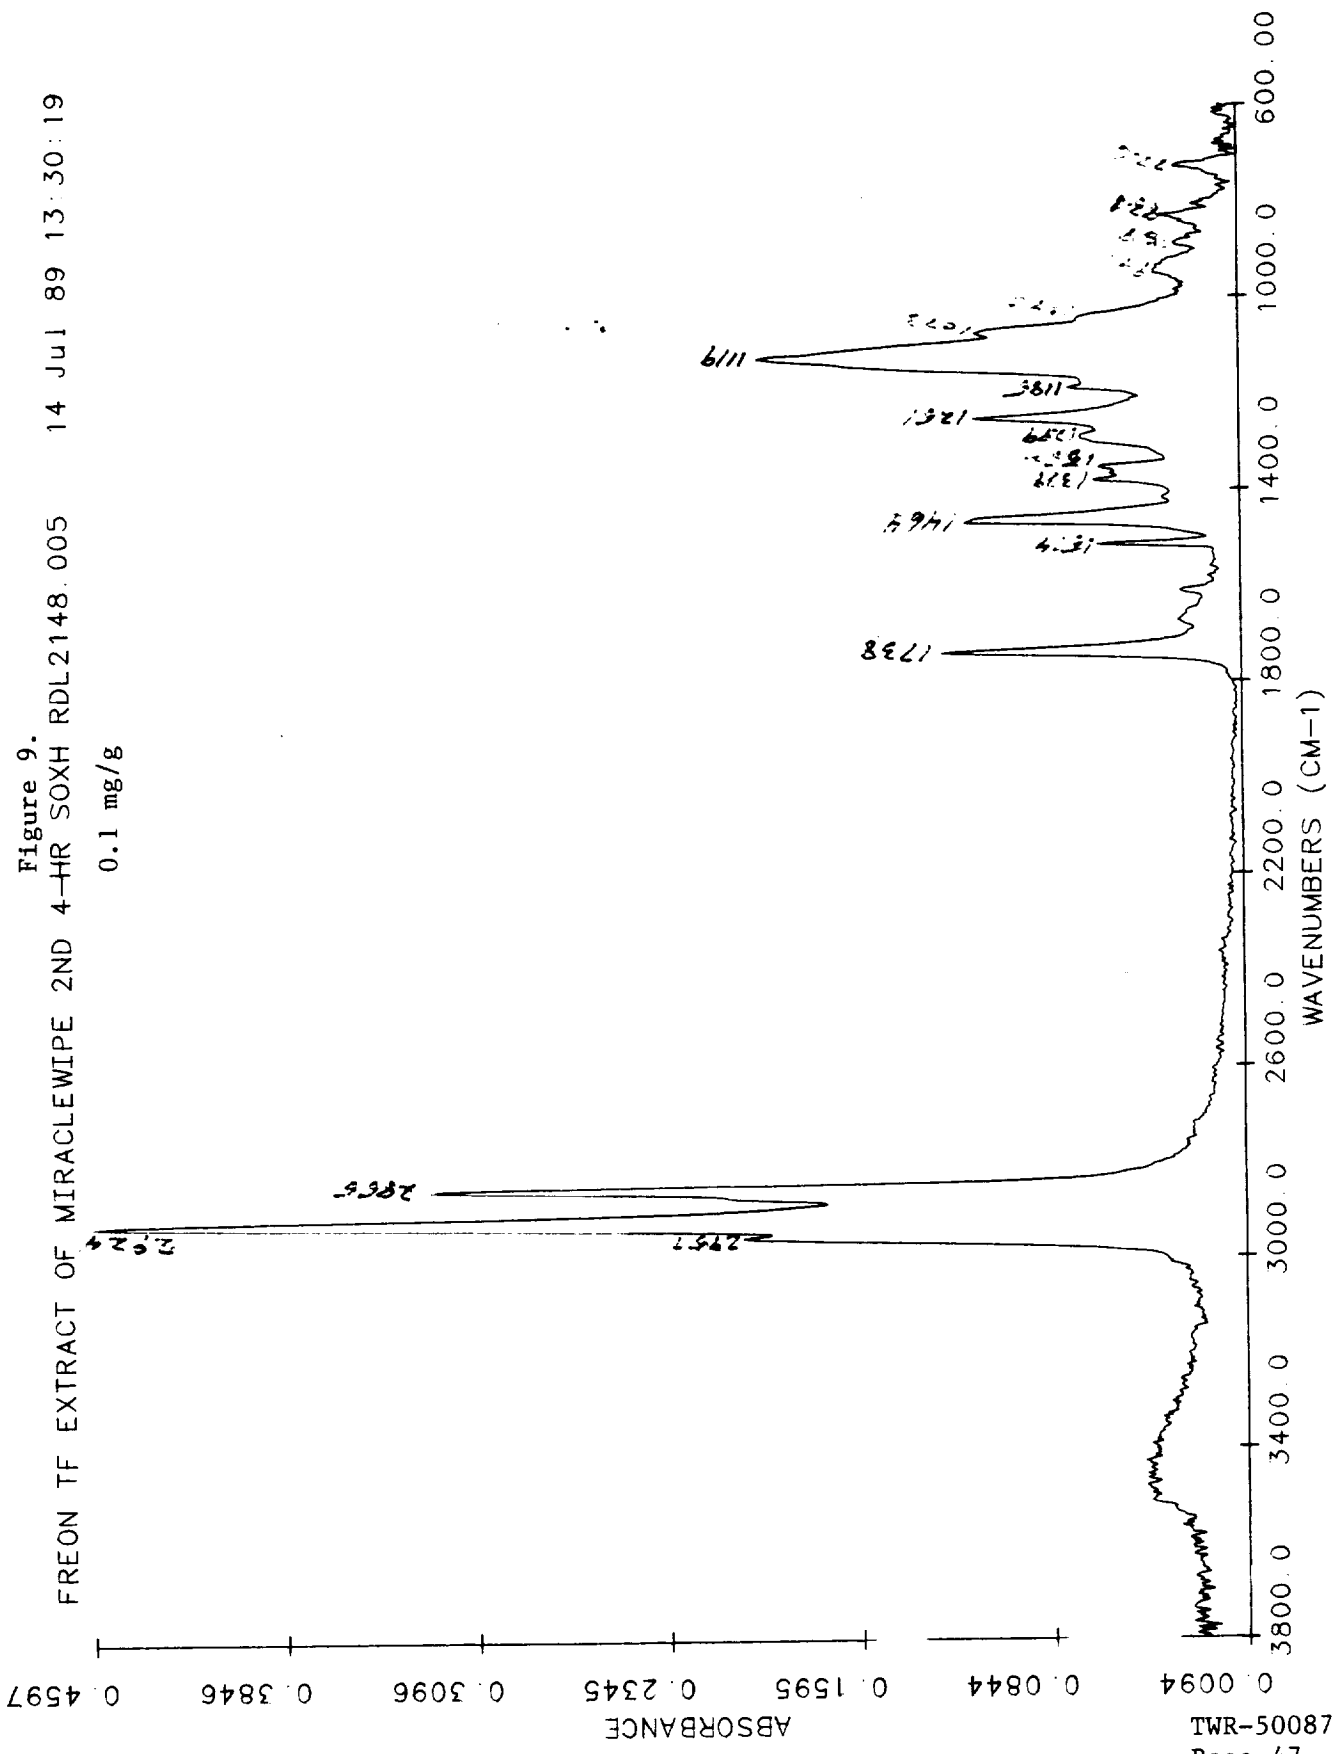


FREON TF EXTRACT OF MIRACLEWIPE 1ST 4-HR SOXH RDL148.005 ATR CAST 14 Jul 89 12:38:25

Figure 10.

0.5 mg/g

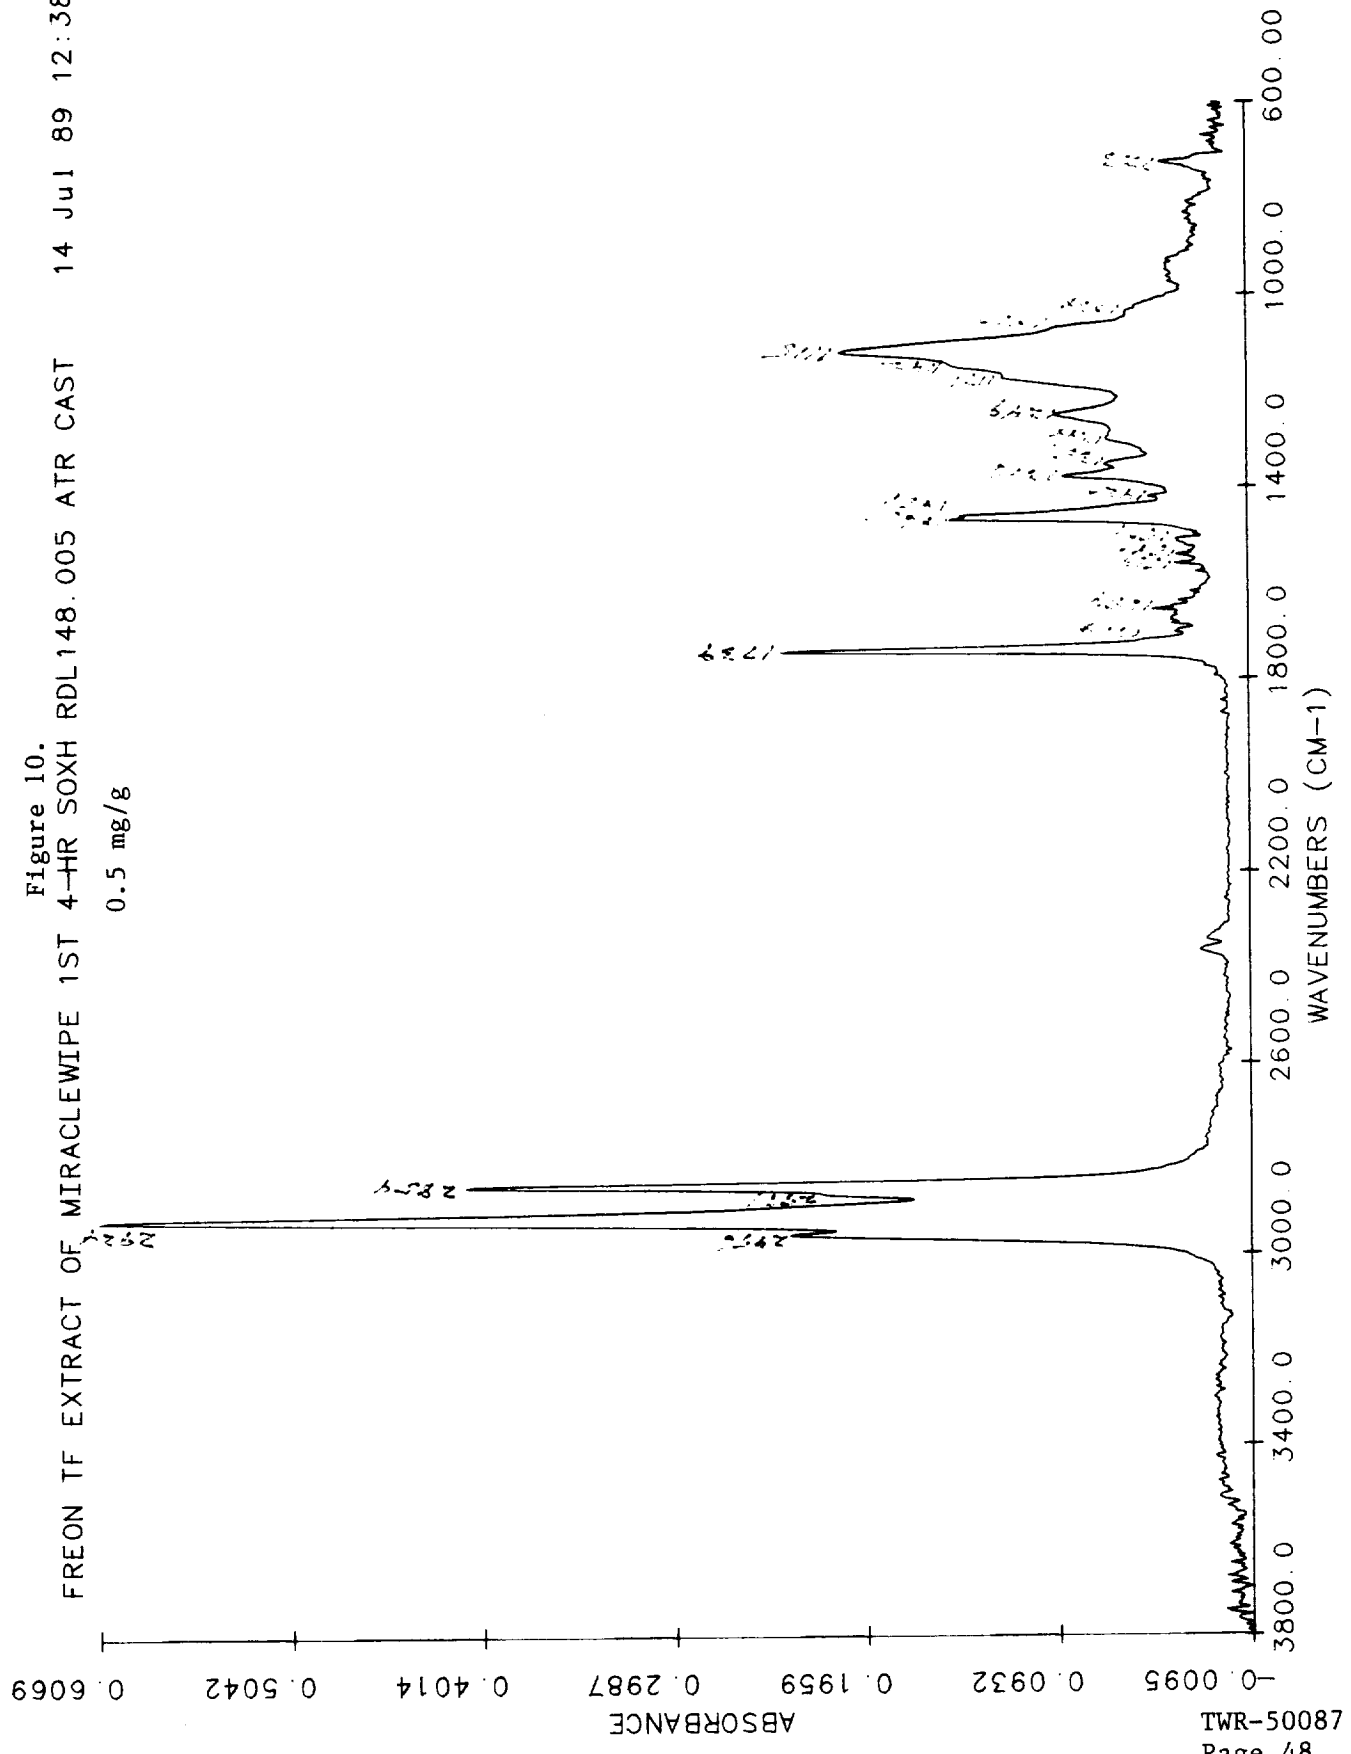


MEK EXTRACT OF MIRACLEWIPE 2ND 4-HR SOXHLET RDL2147.005 ATR CAST
0.2 mg/g
14 Jul 89 10:22:27

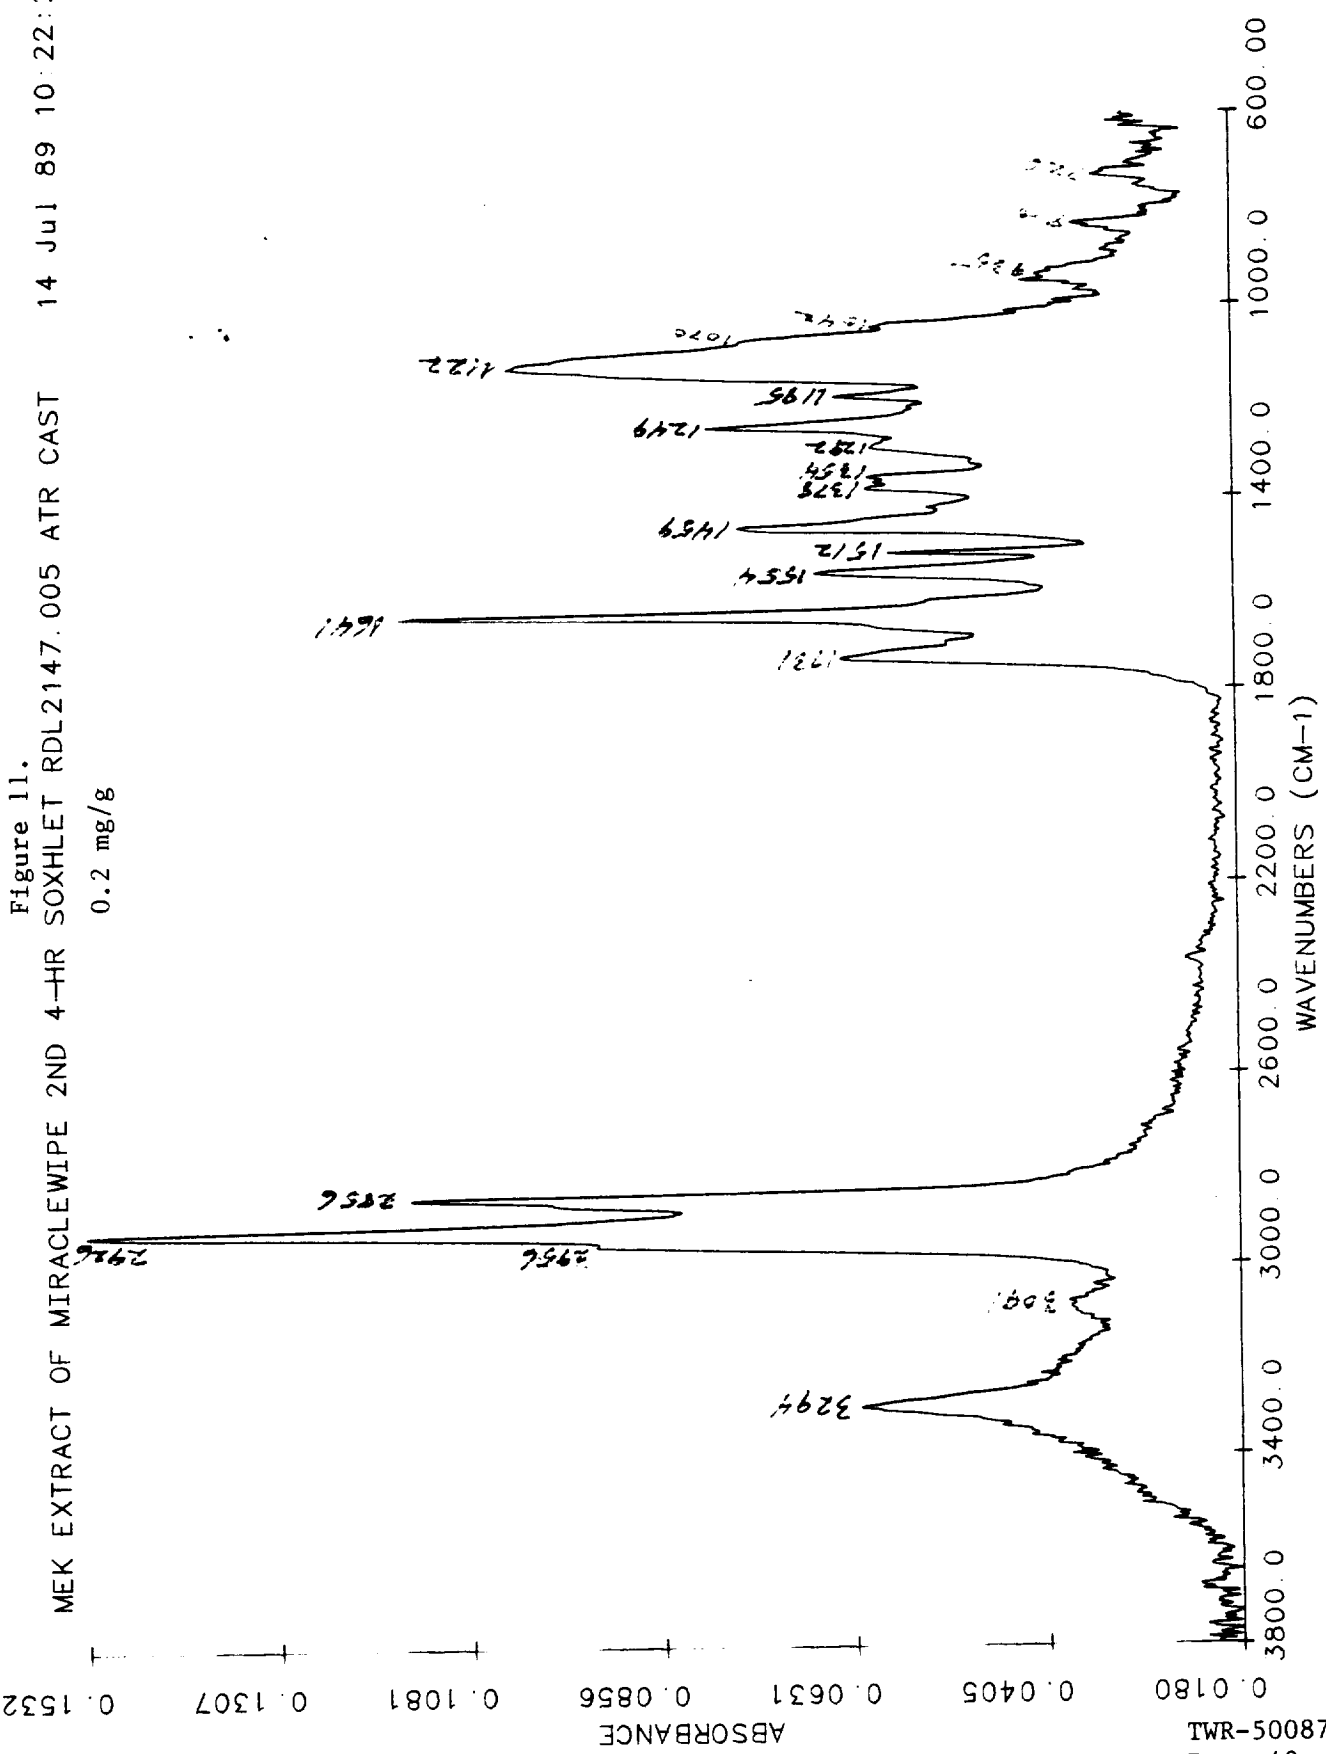

MEK EXTRACT OF MIRACLEWIPE FIRST 4-HOUR SOXHLET RDL147.005 ATR CAST 1.9 mg/g


Figure 12.

14 Jul 89 9:27:23

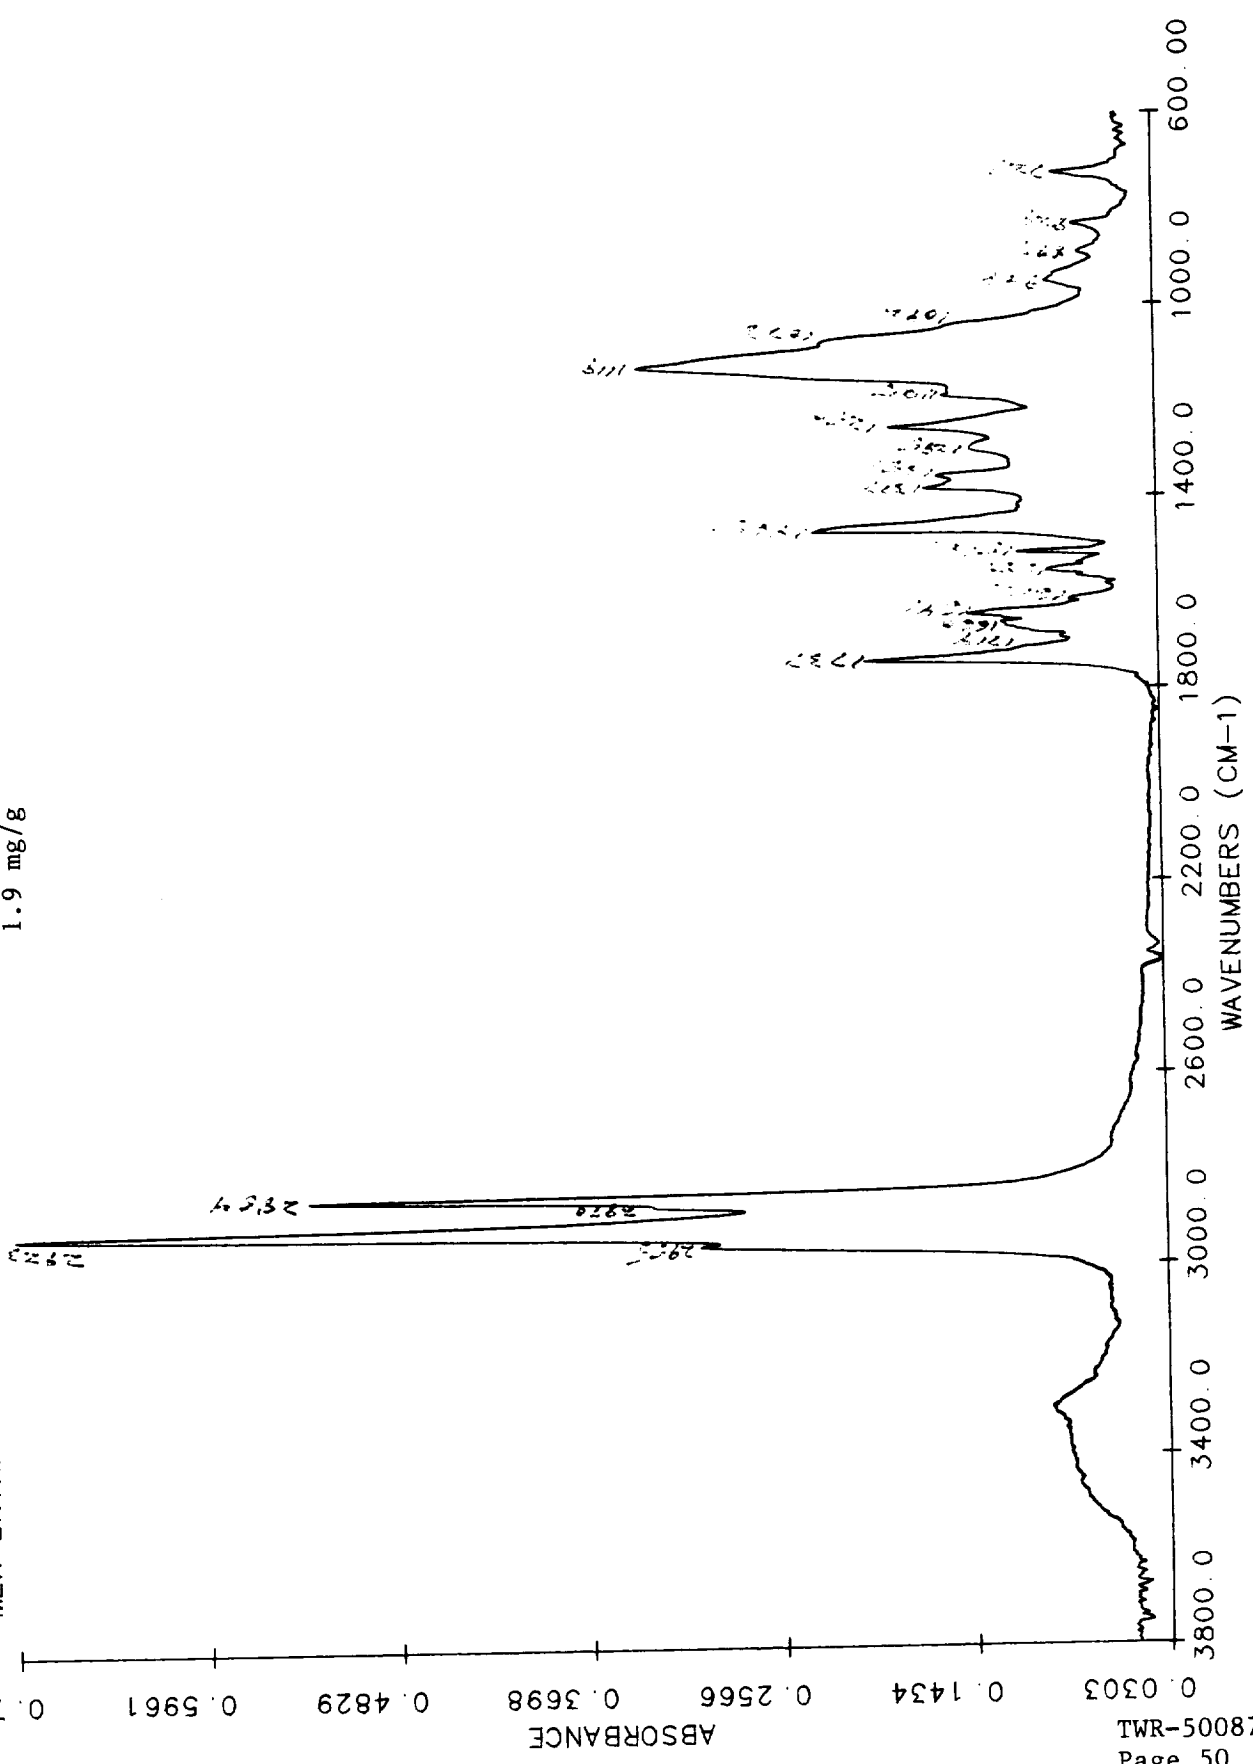

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 13.

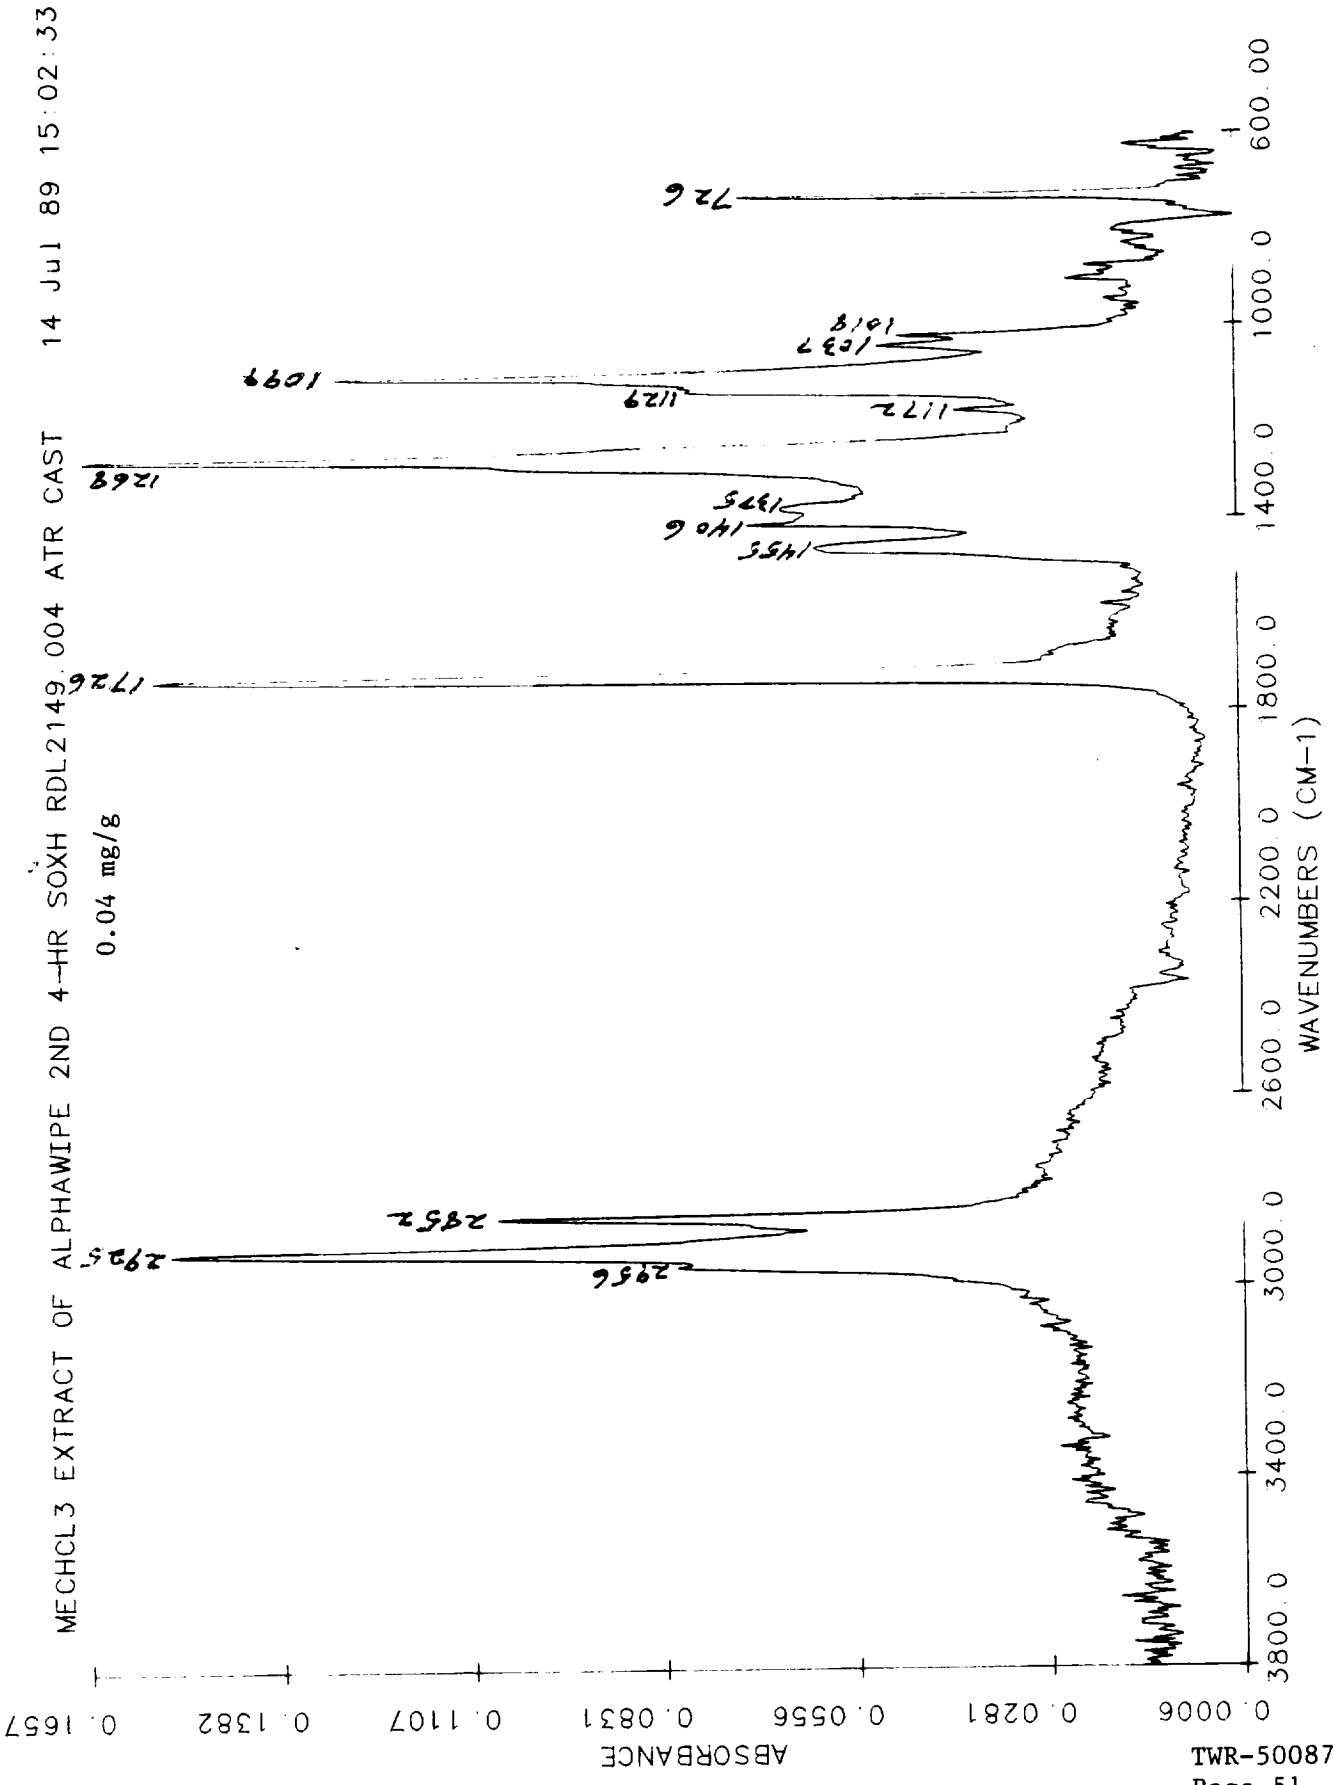


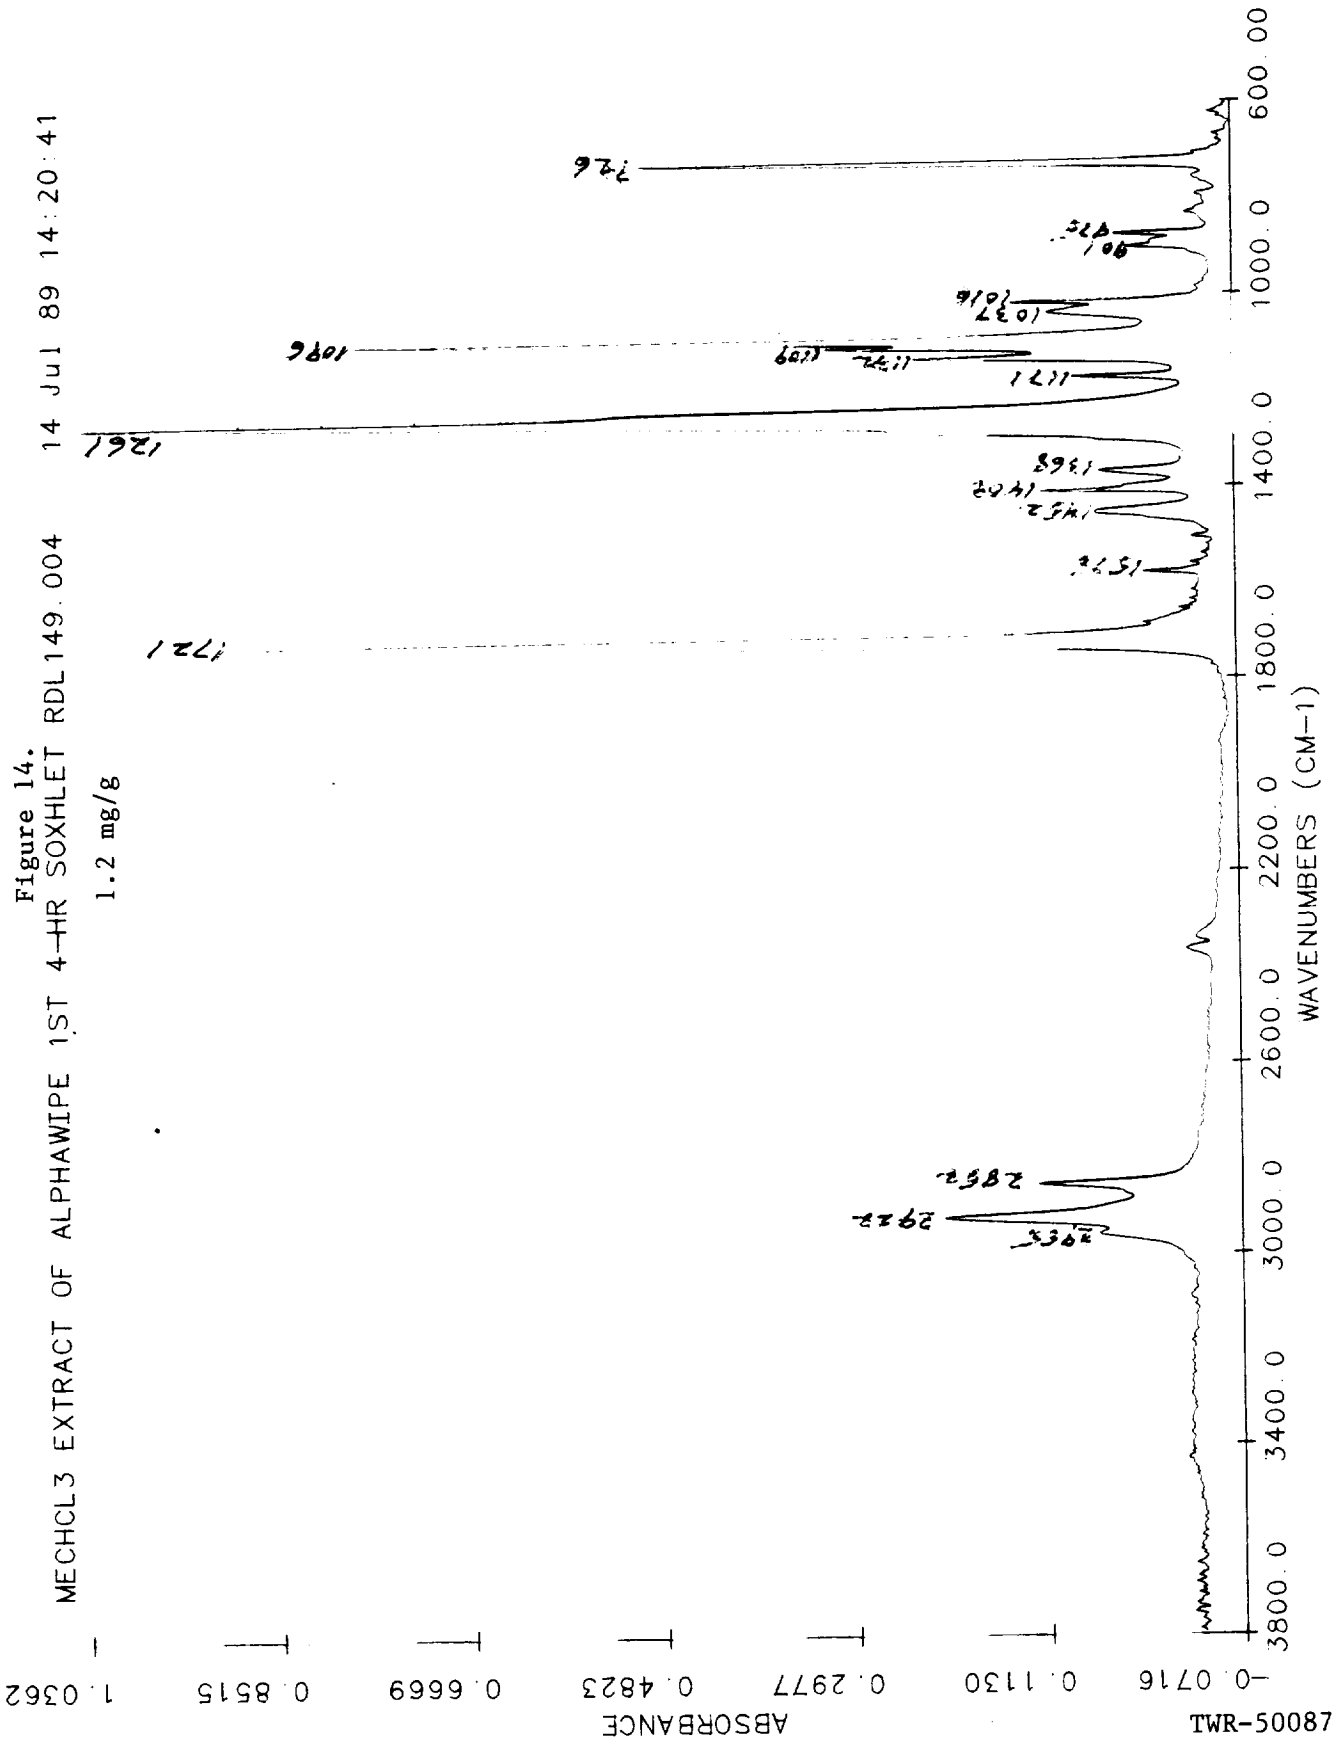


Figure 14.


FREON TF EXTRACT OF ALPHAWIPE 2ND 4-HR SOXHLET RDL2148.004 ATR CAST 14 Jul 89 13:19:36
0.09 mg/g

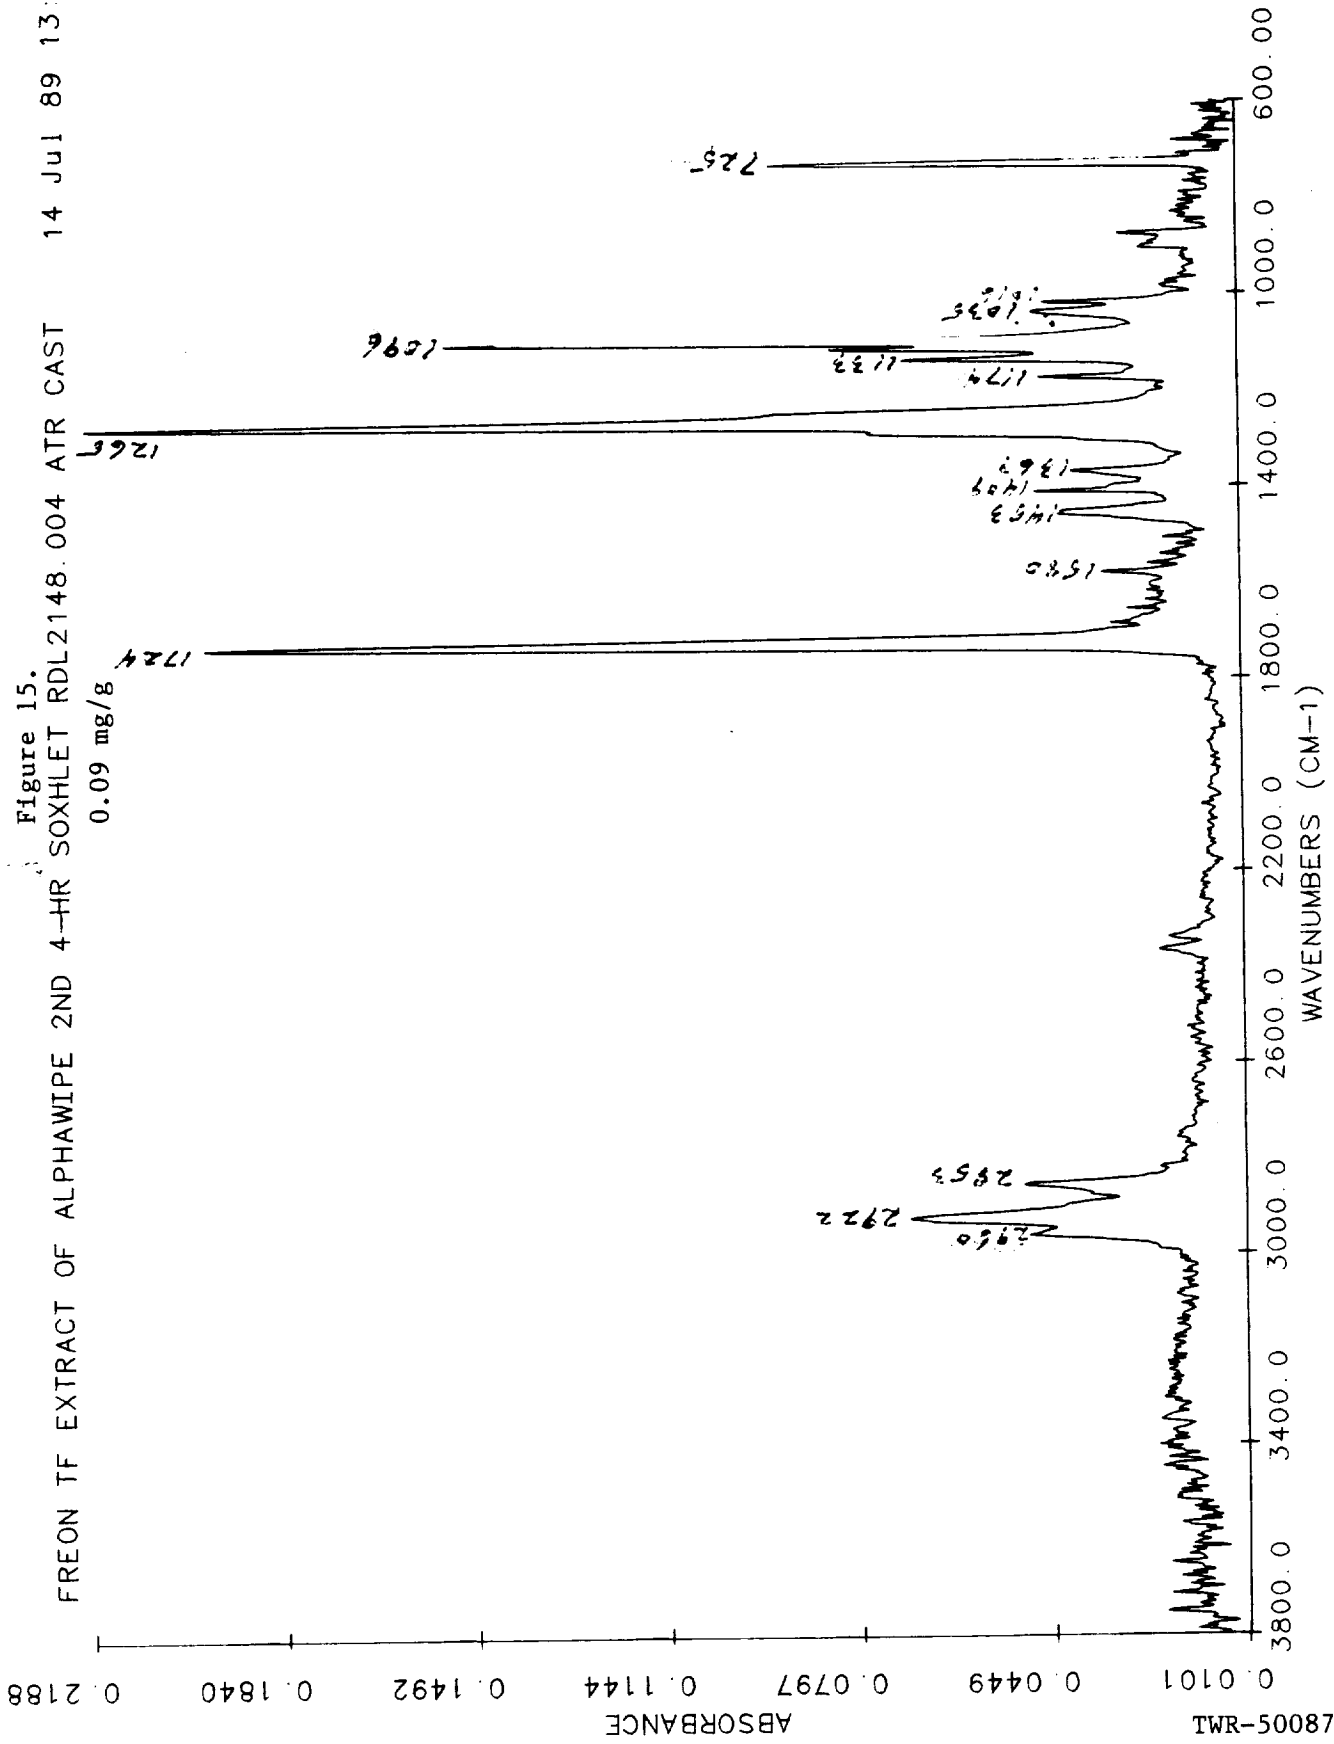

FREON TF EXTRACT OF ALPHAWIPE 1ST 4-HR SOXH RDL148.004 ATR CAST 14 Jul 89 12:30:59

Figure 16.

0.3 mg/g

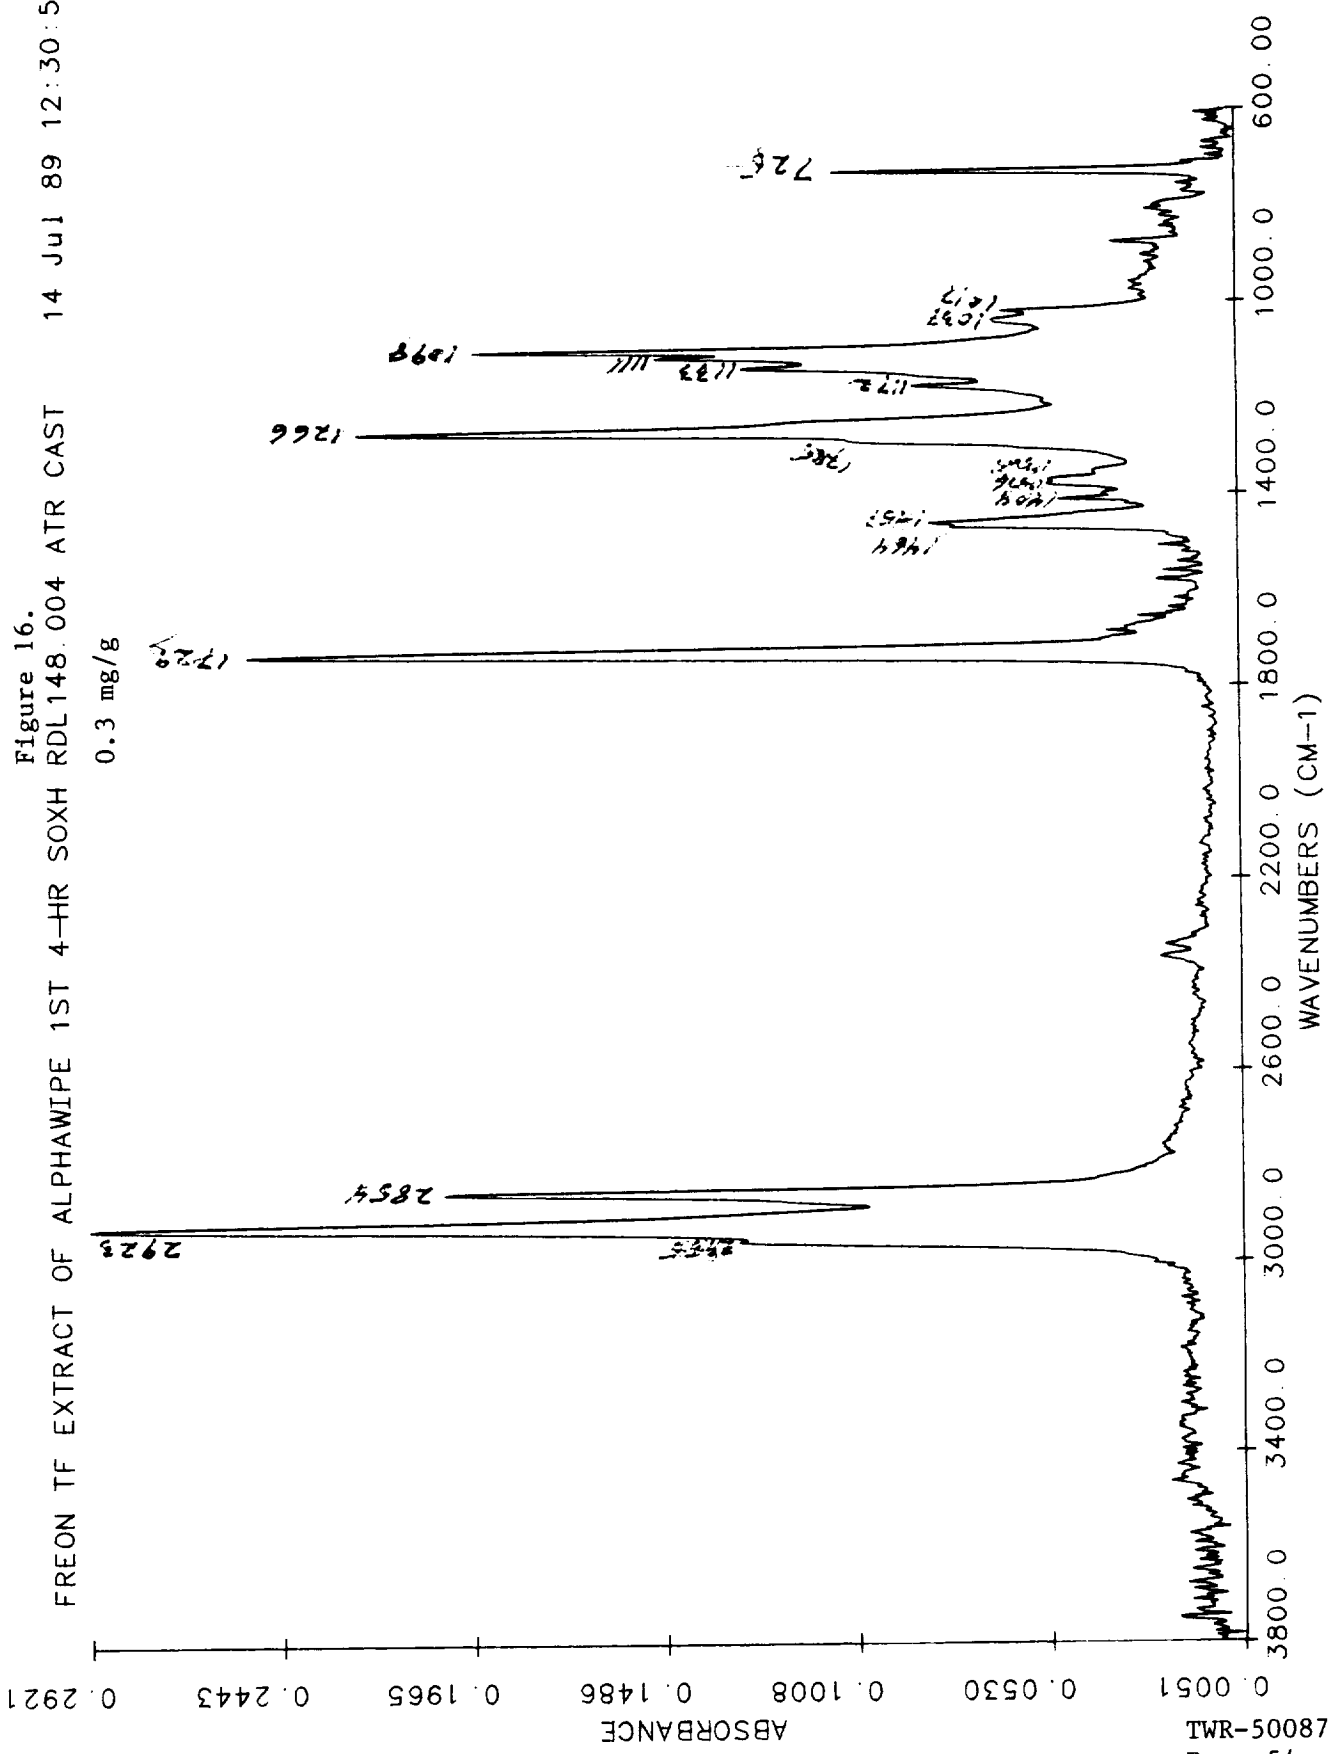


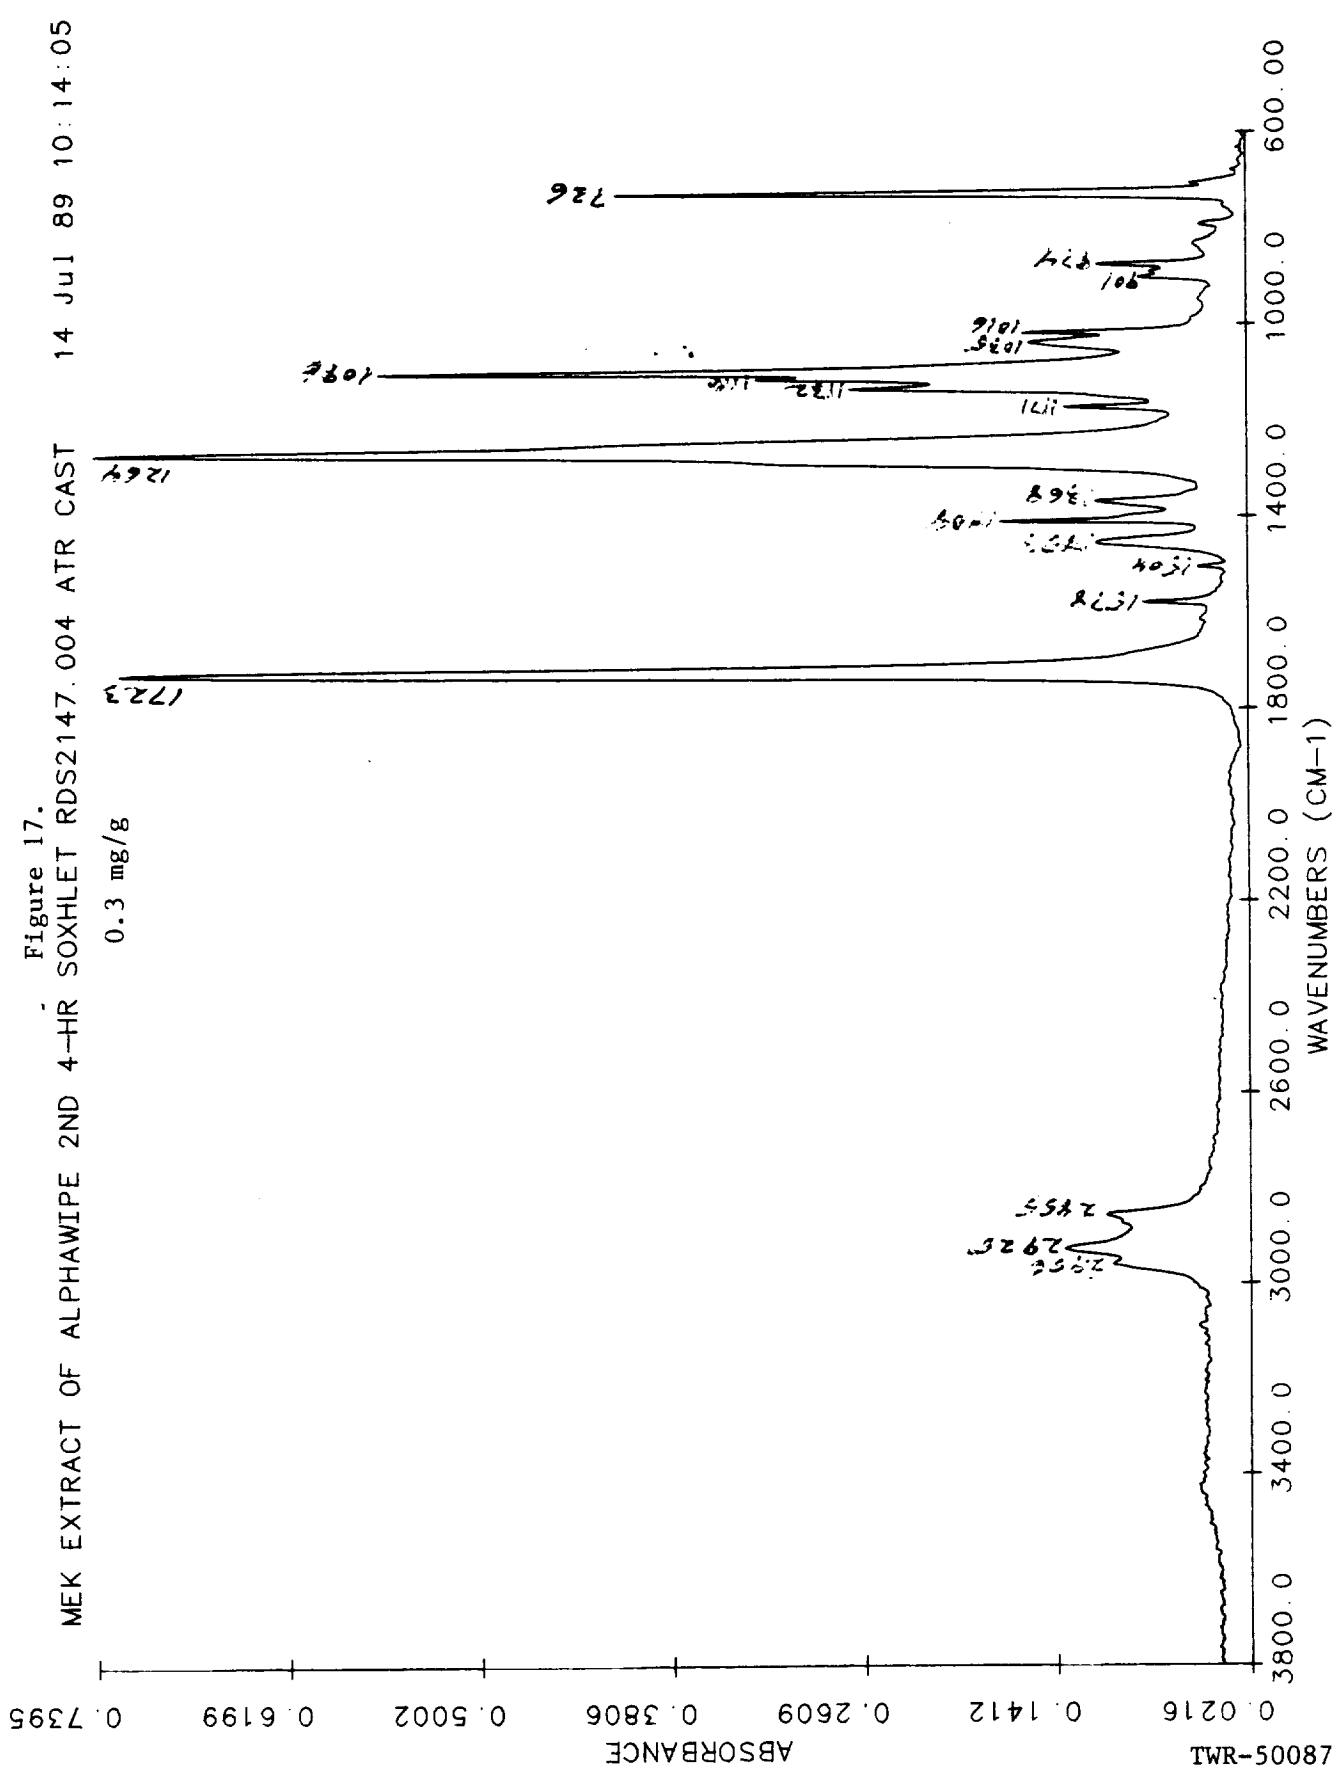


Figure 17.


MEK EXTRACT OF ALPHAWIPE FIRST 4-HOUR SOXHLET RDL147.004 ATR CAST 14 Jul 89 9:03:28

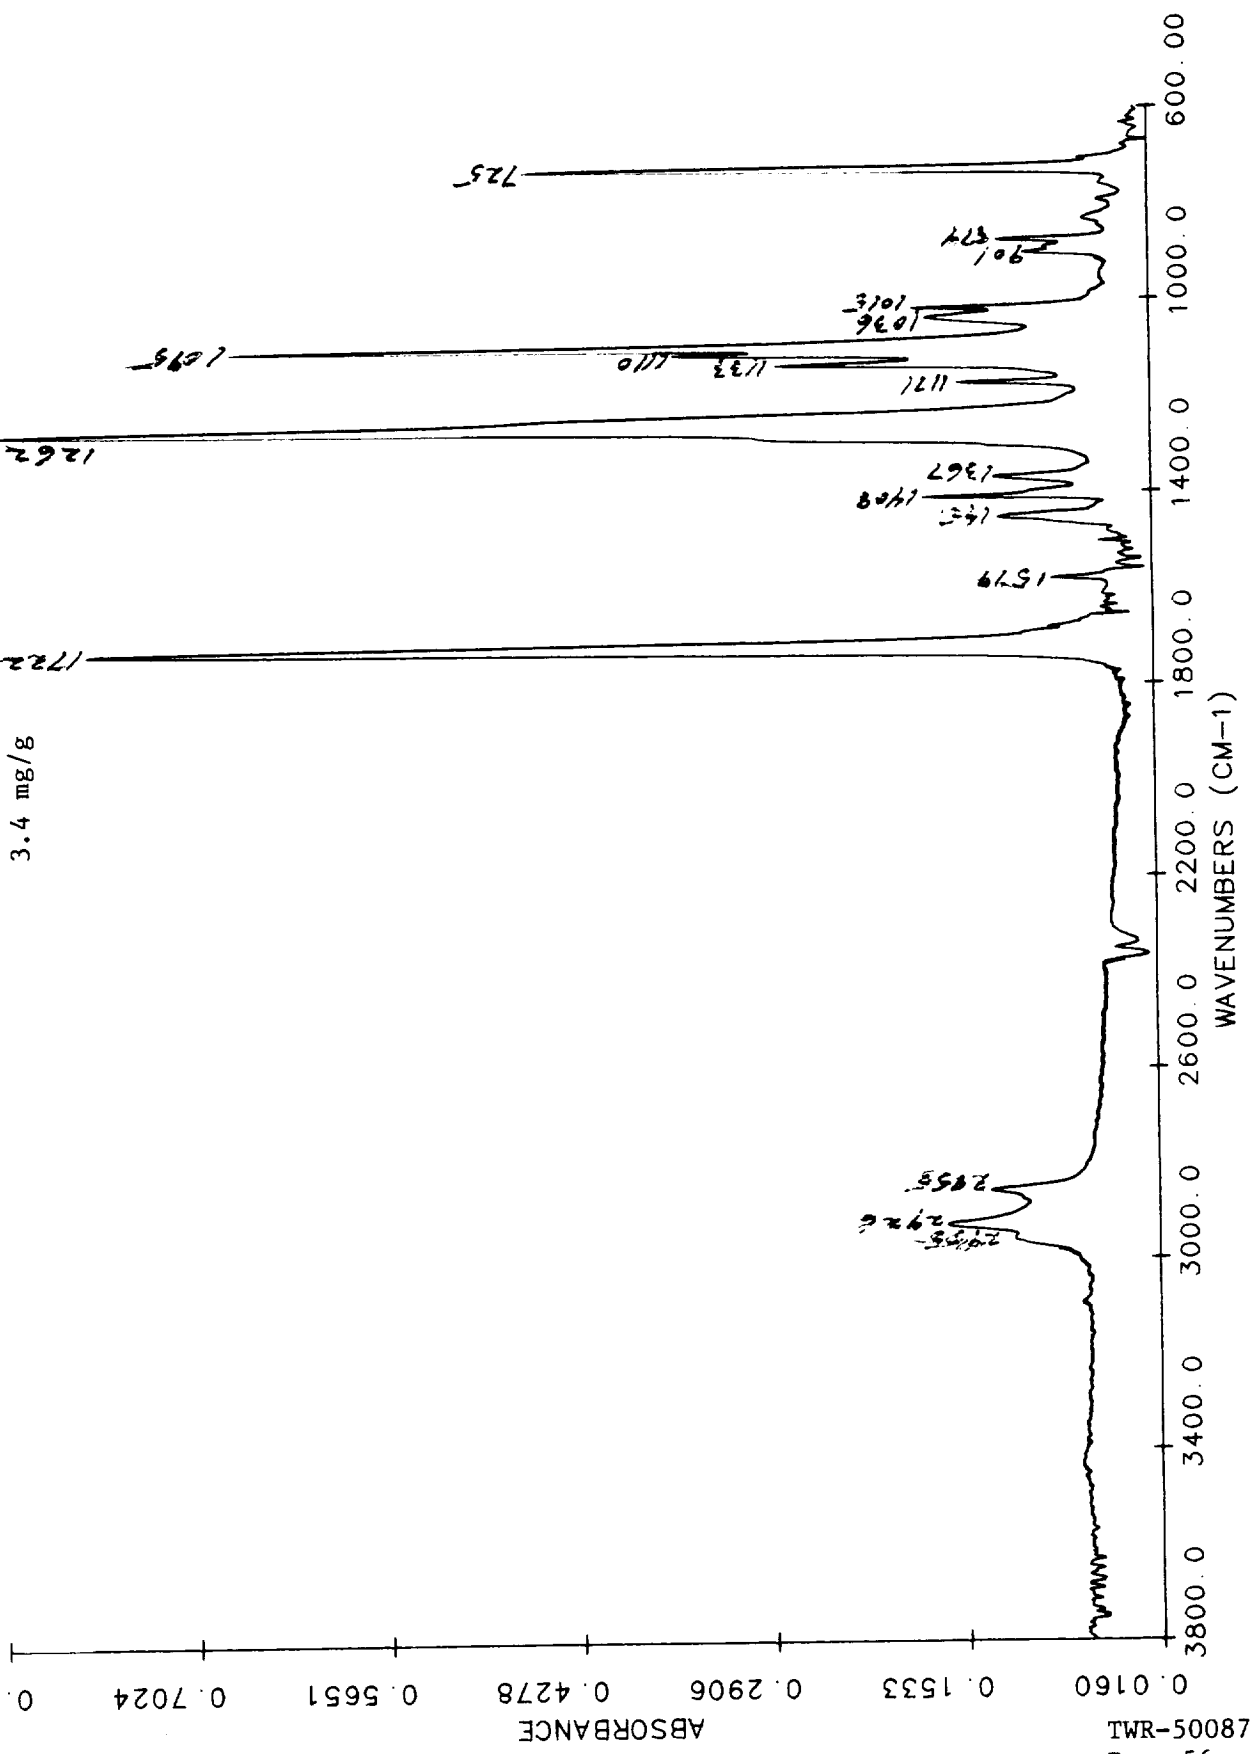


3.4 mg/g

ORIGINAL PAGE IS
OF POOR QUALITY

MECHCL3 EXTRACT OF POLX 1200 2ND 4-HR SOXH RDL2149.001 ATR CAST
0.1 mg/g
14 Jul 89 14:37:21

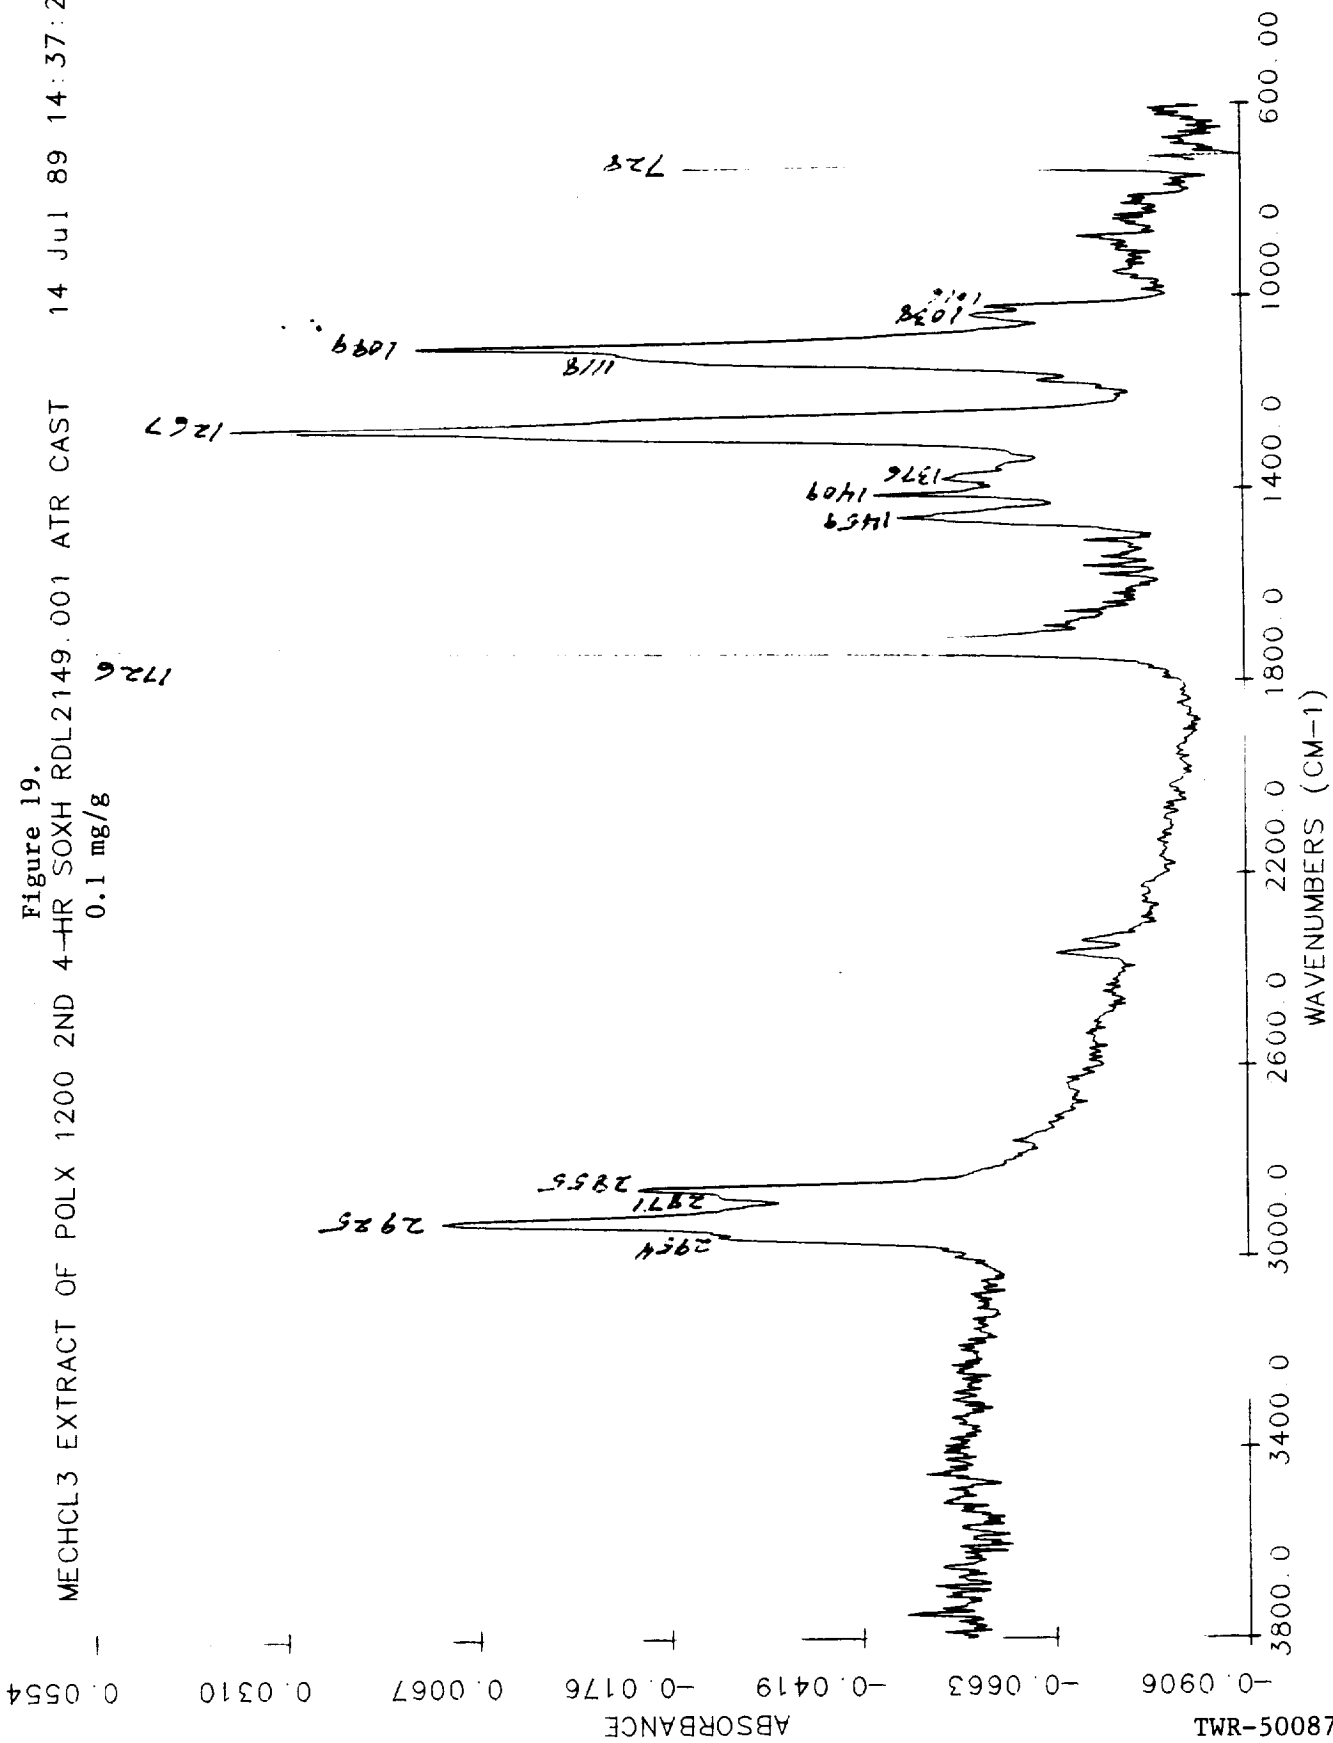

ORIGINAL PAGE IS
OF POOR QUALITY

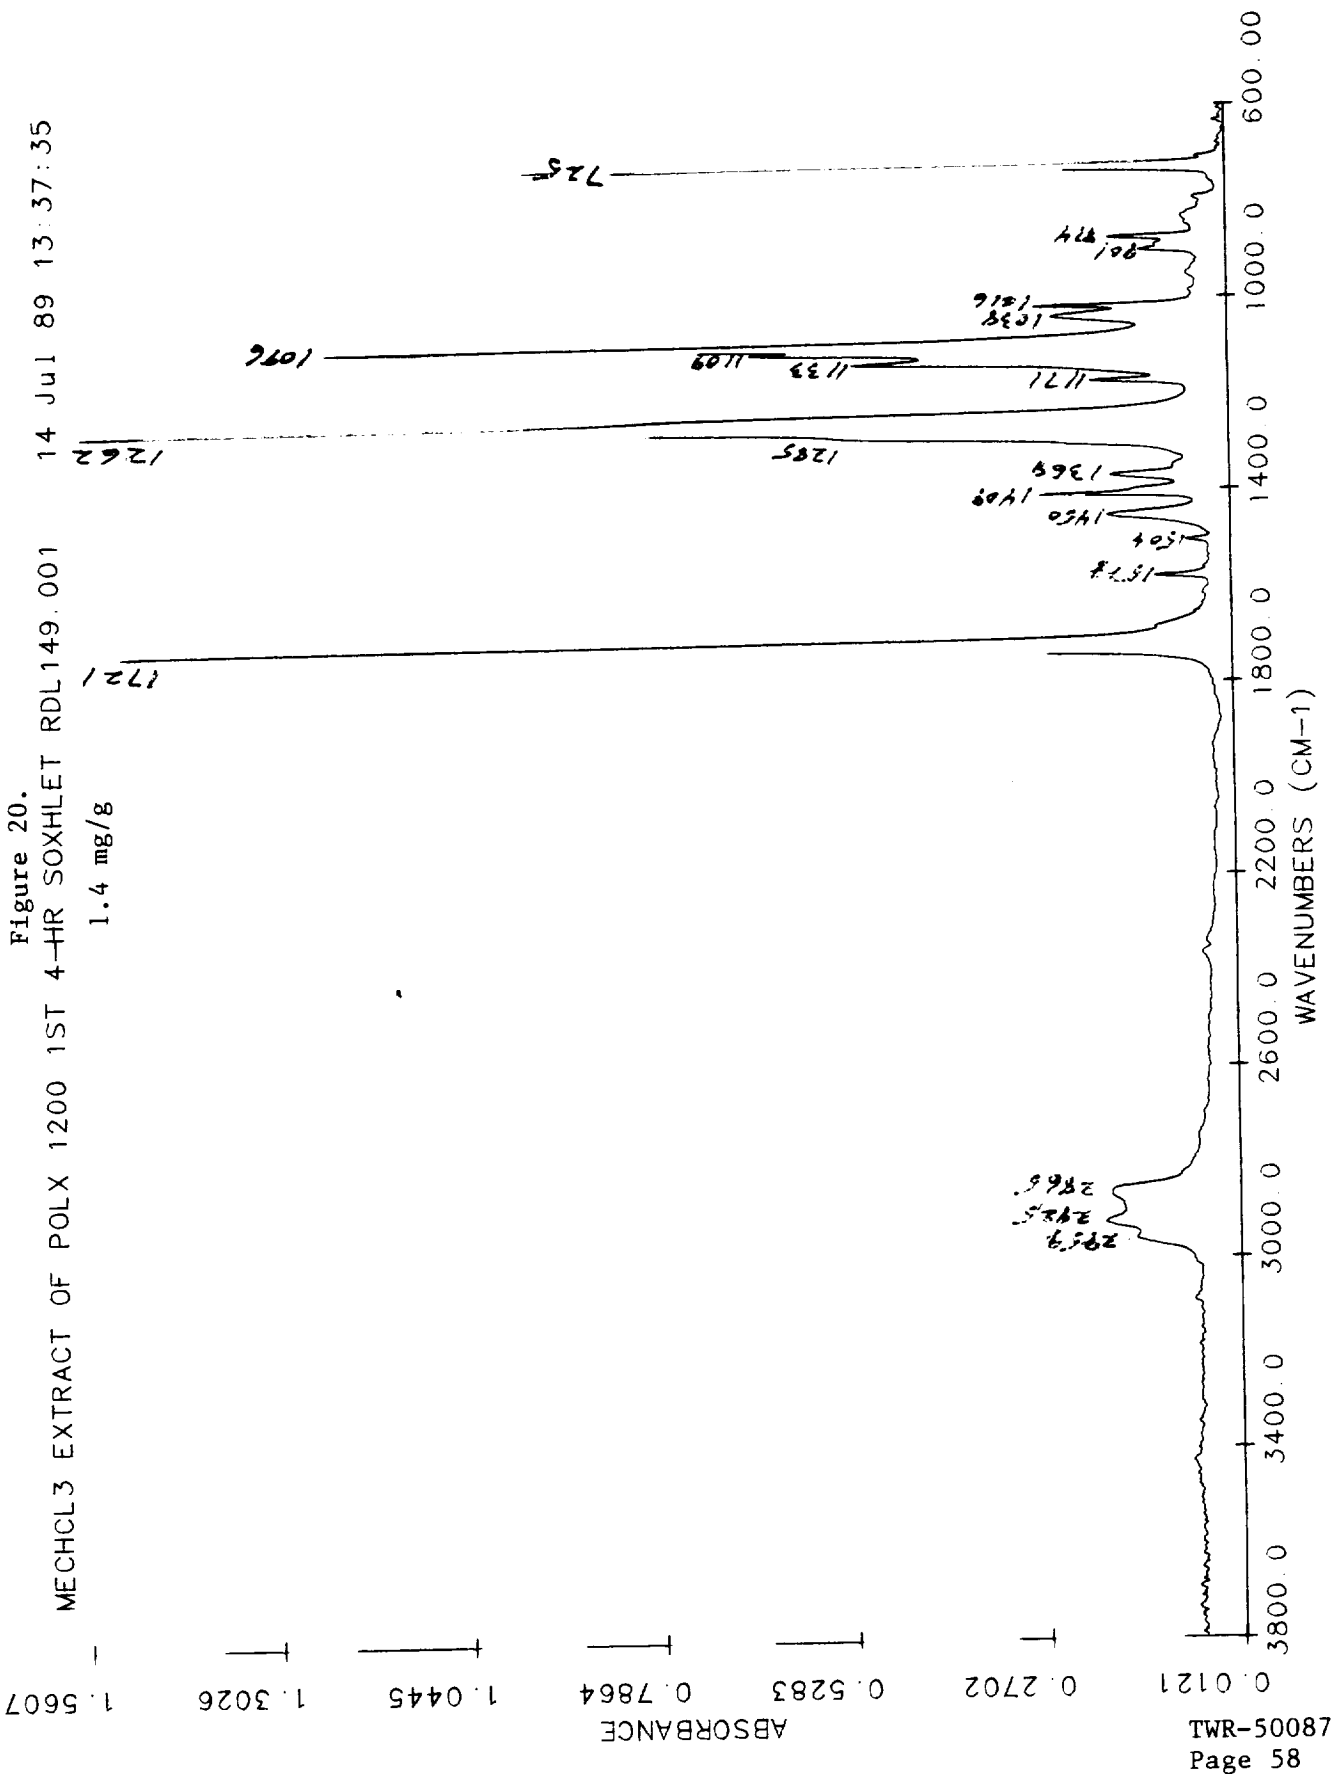

ORIGINAL PAGE IS
OF POOR QUALITY



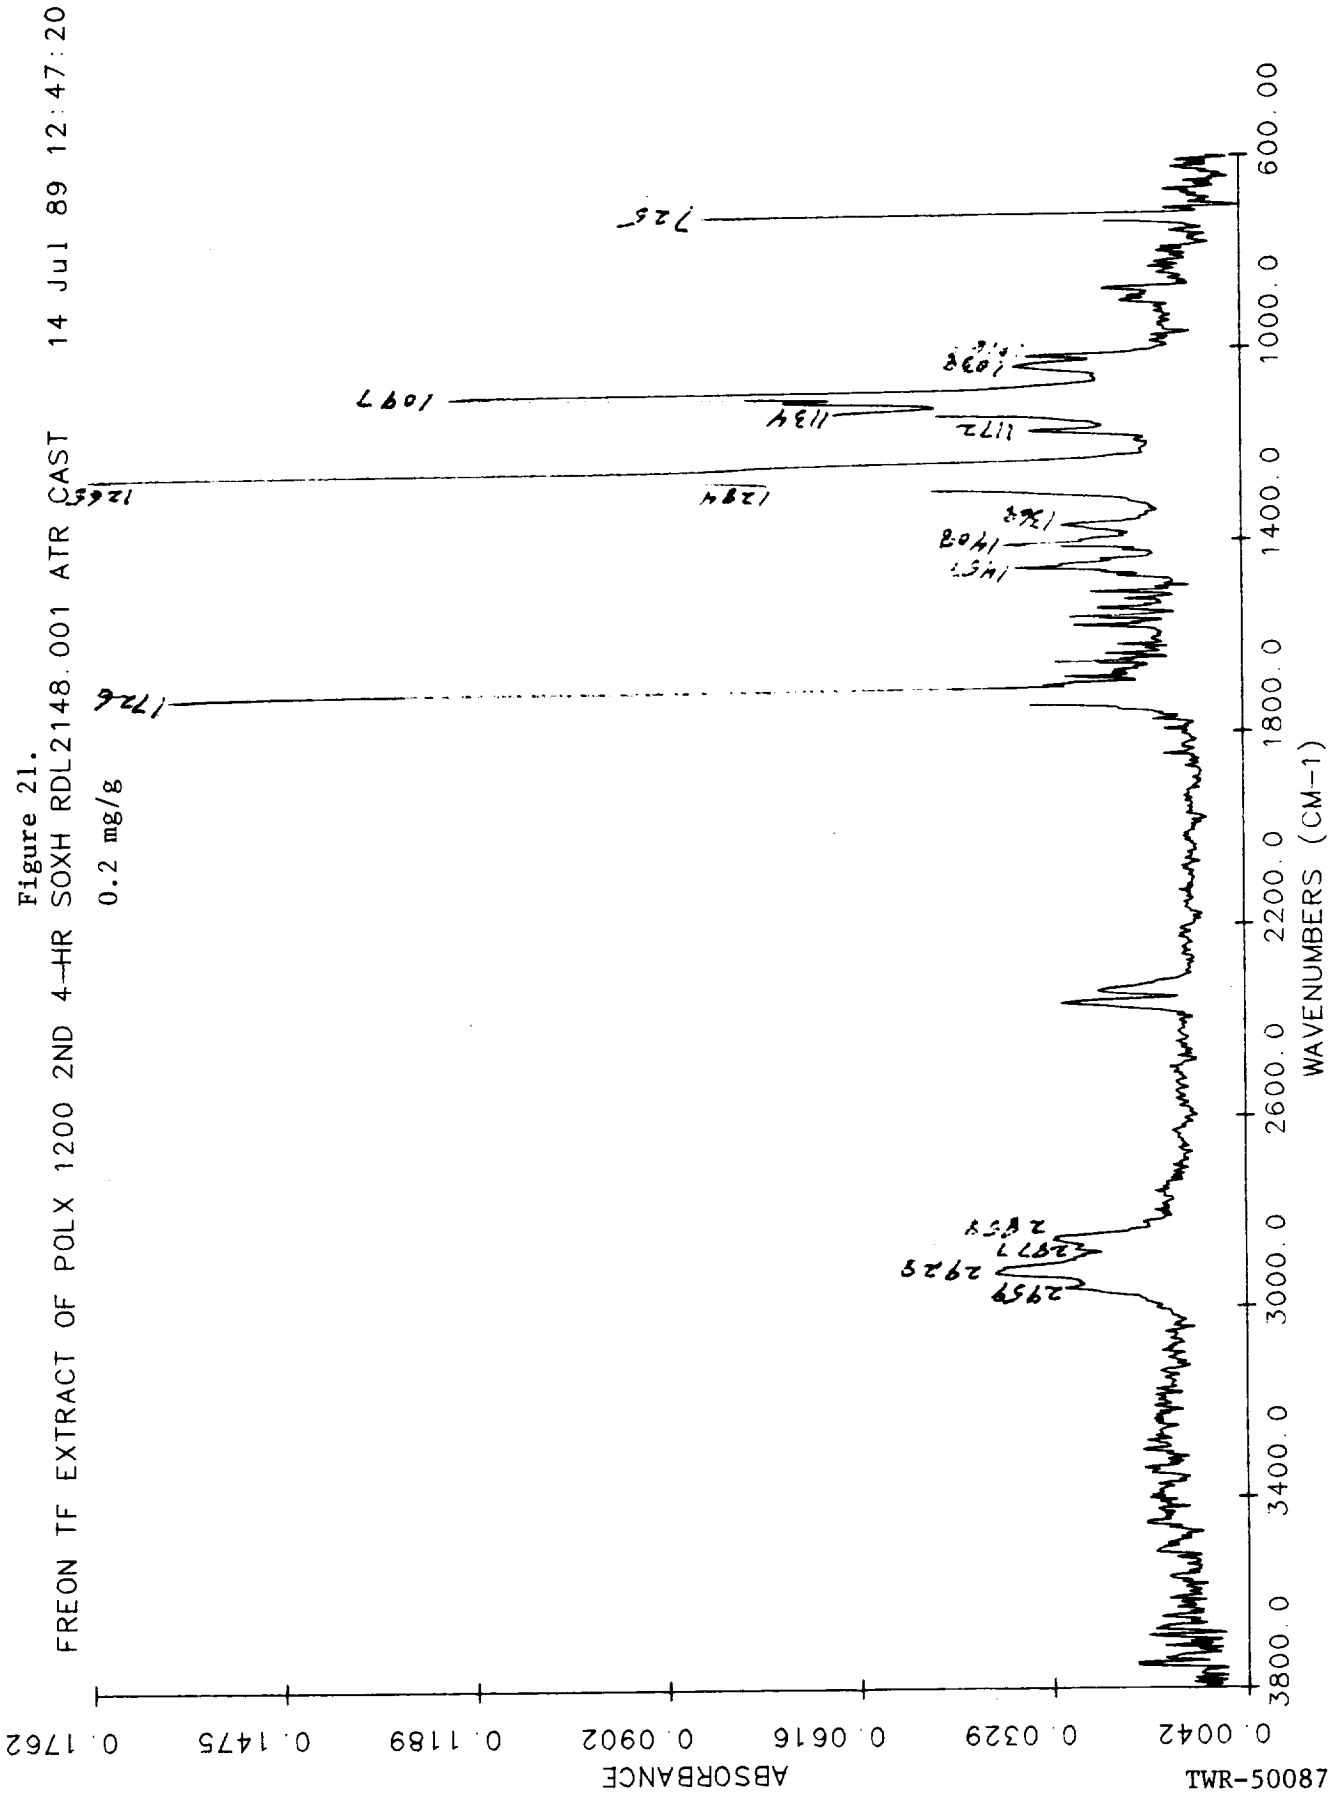



Figure 21.

ORIGINAL PAGE IS
OF POOR QUALITY

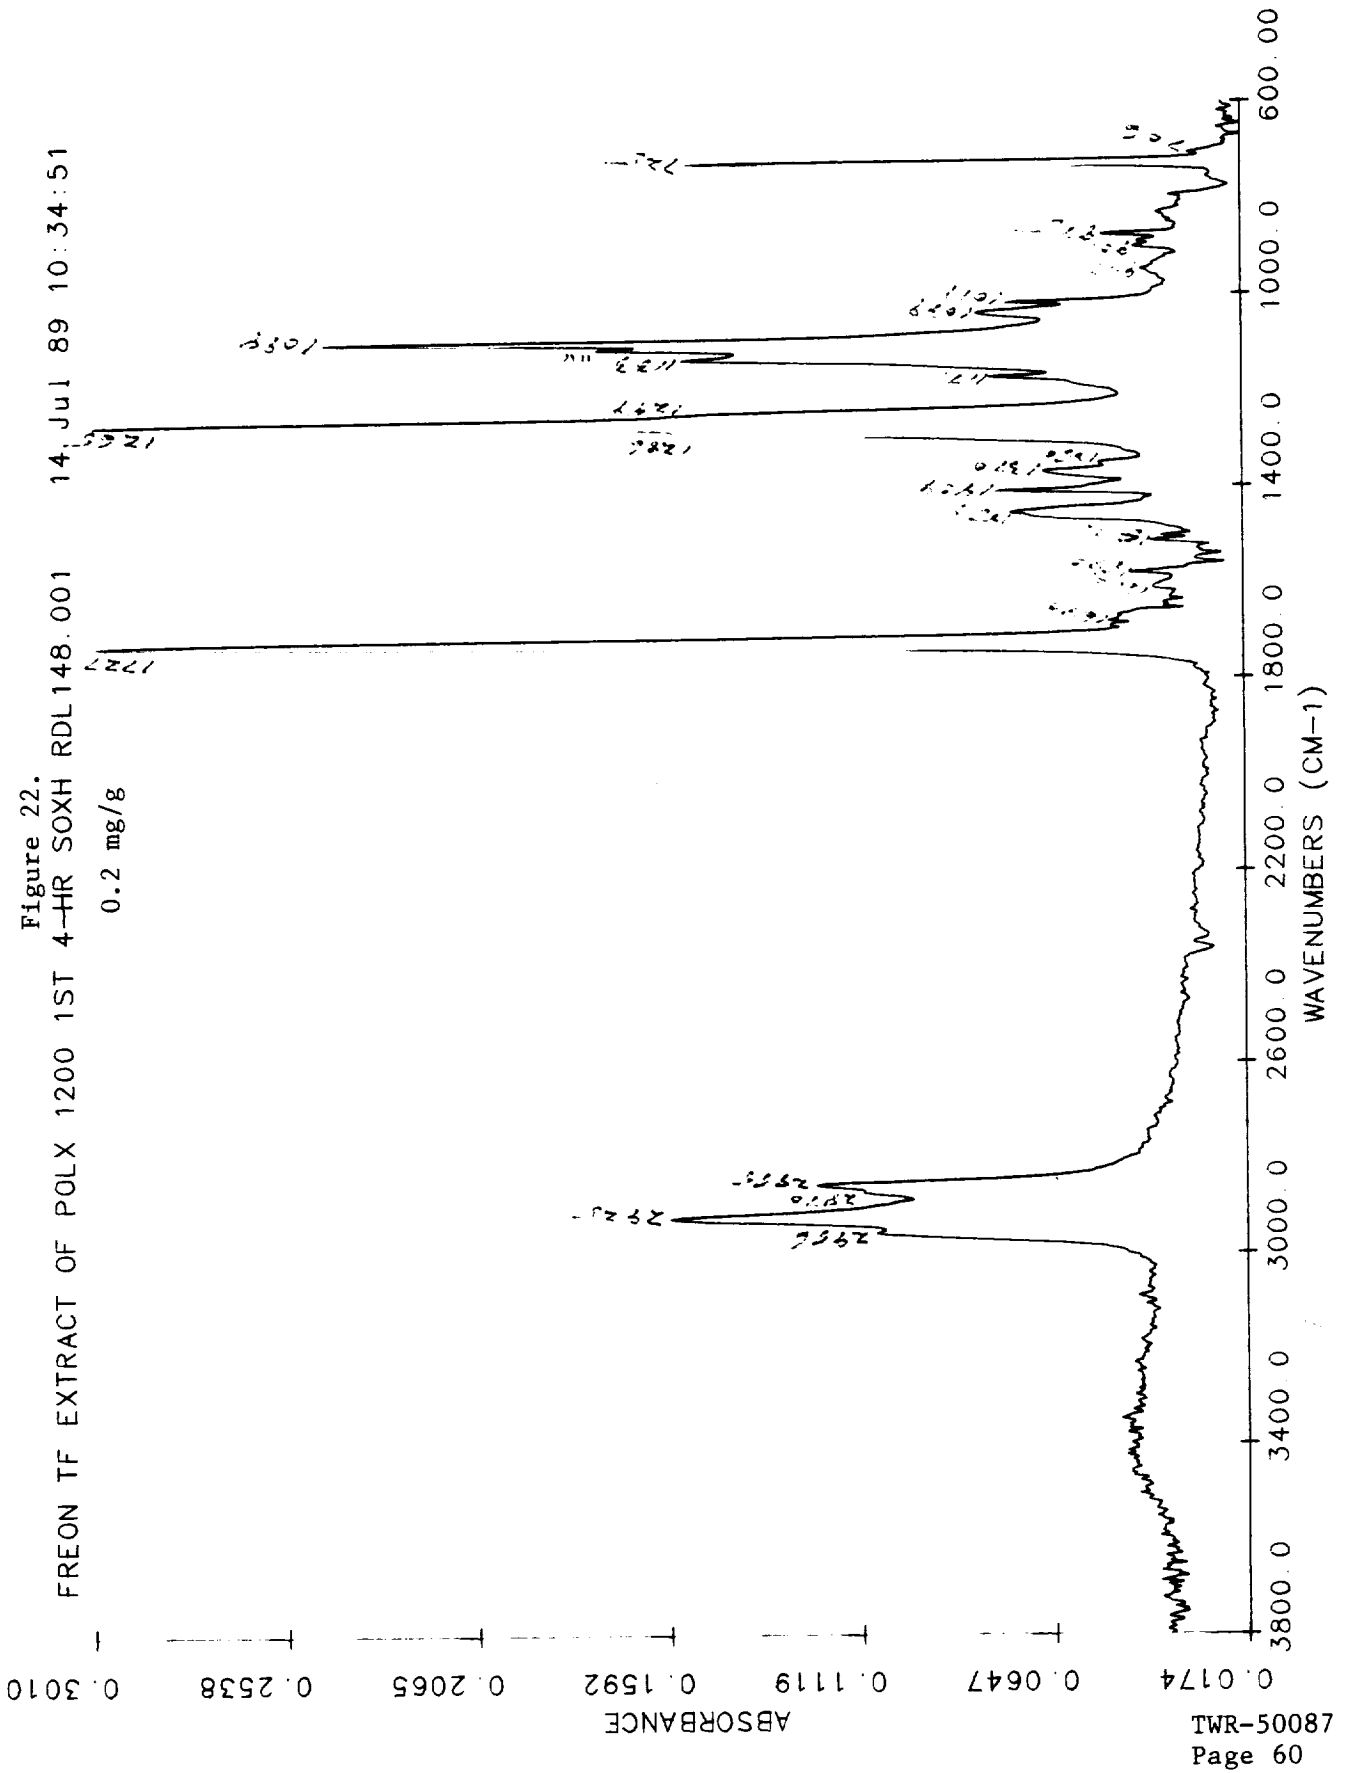


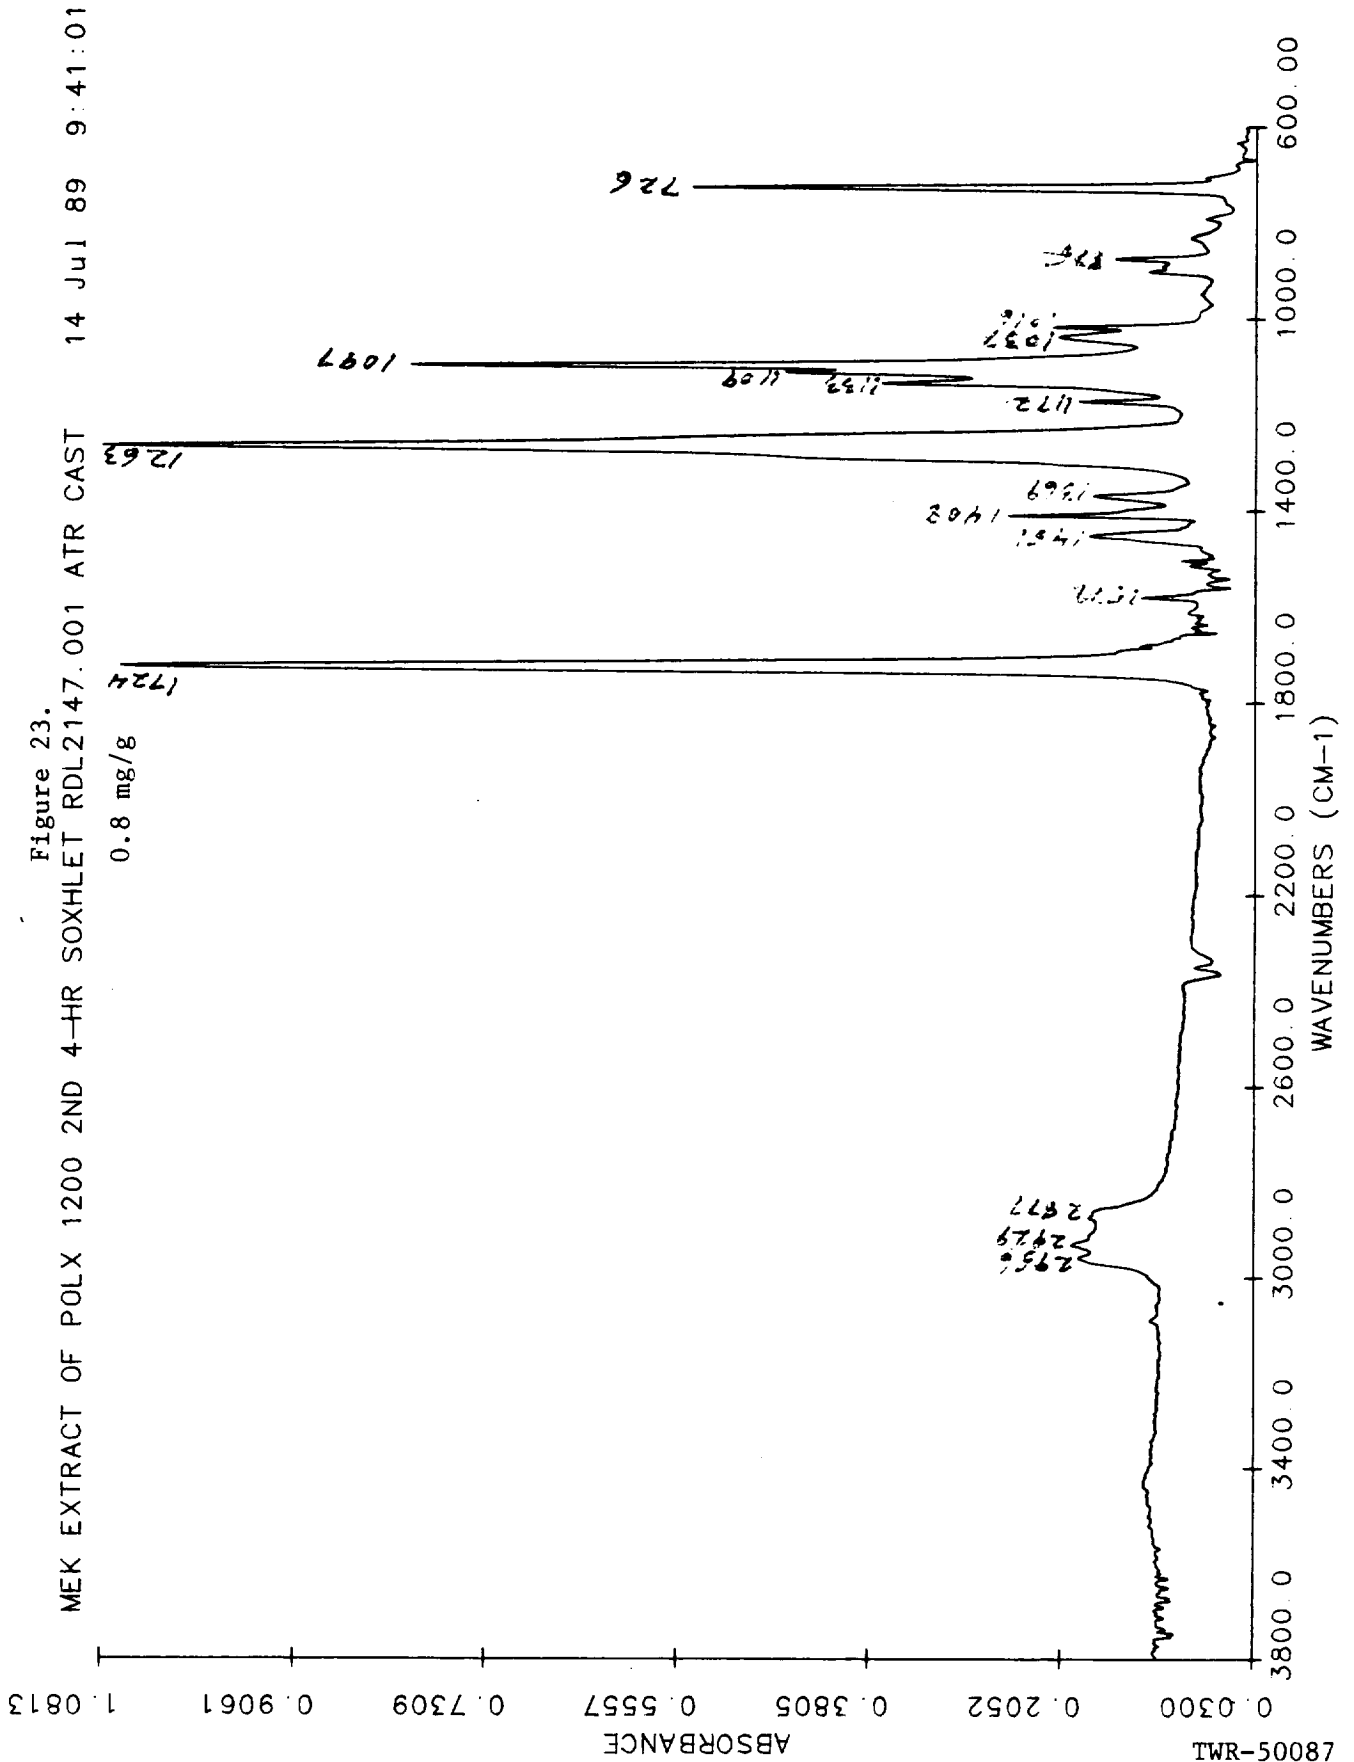

ORIGINAL PAGE IS
OF POOR QUALITY

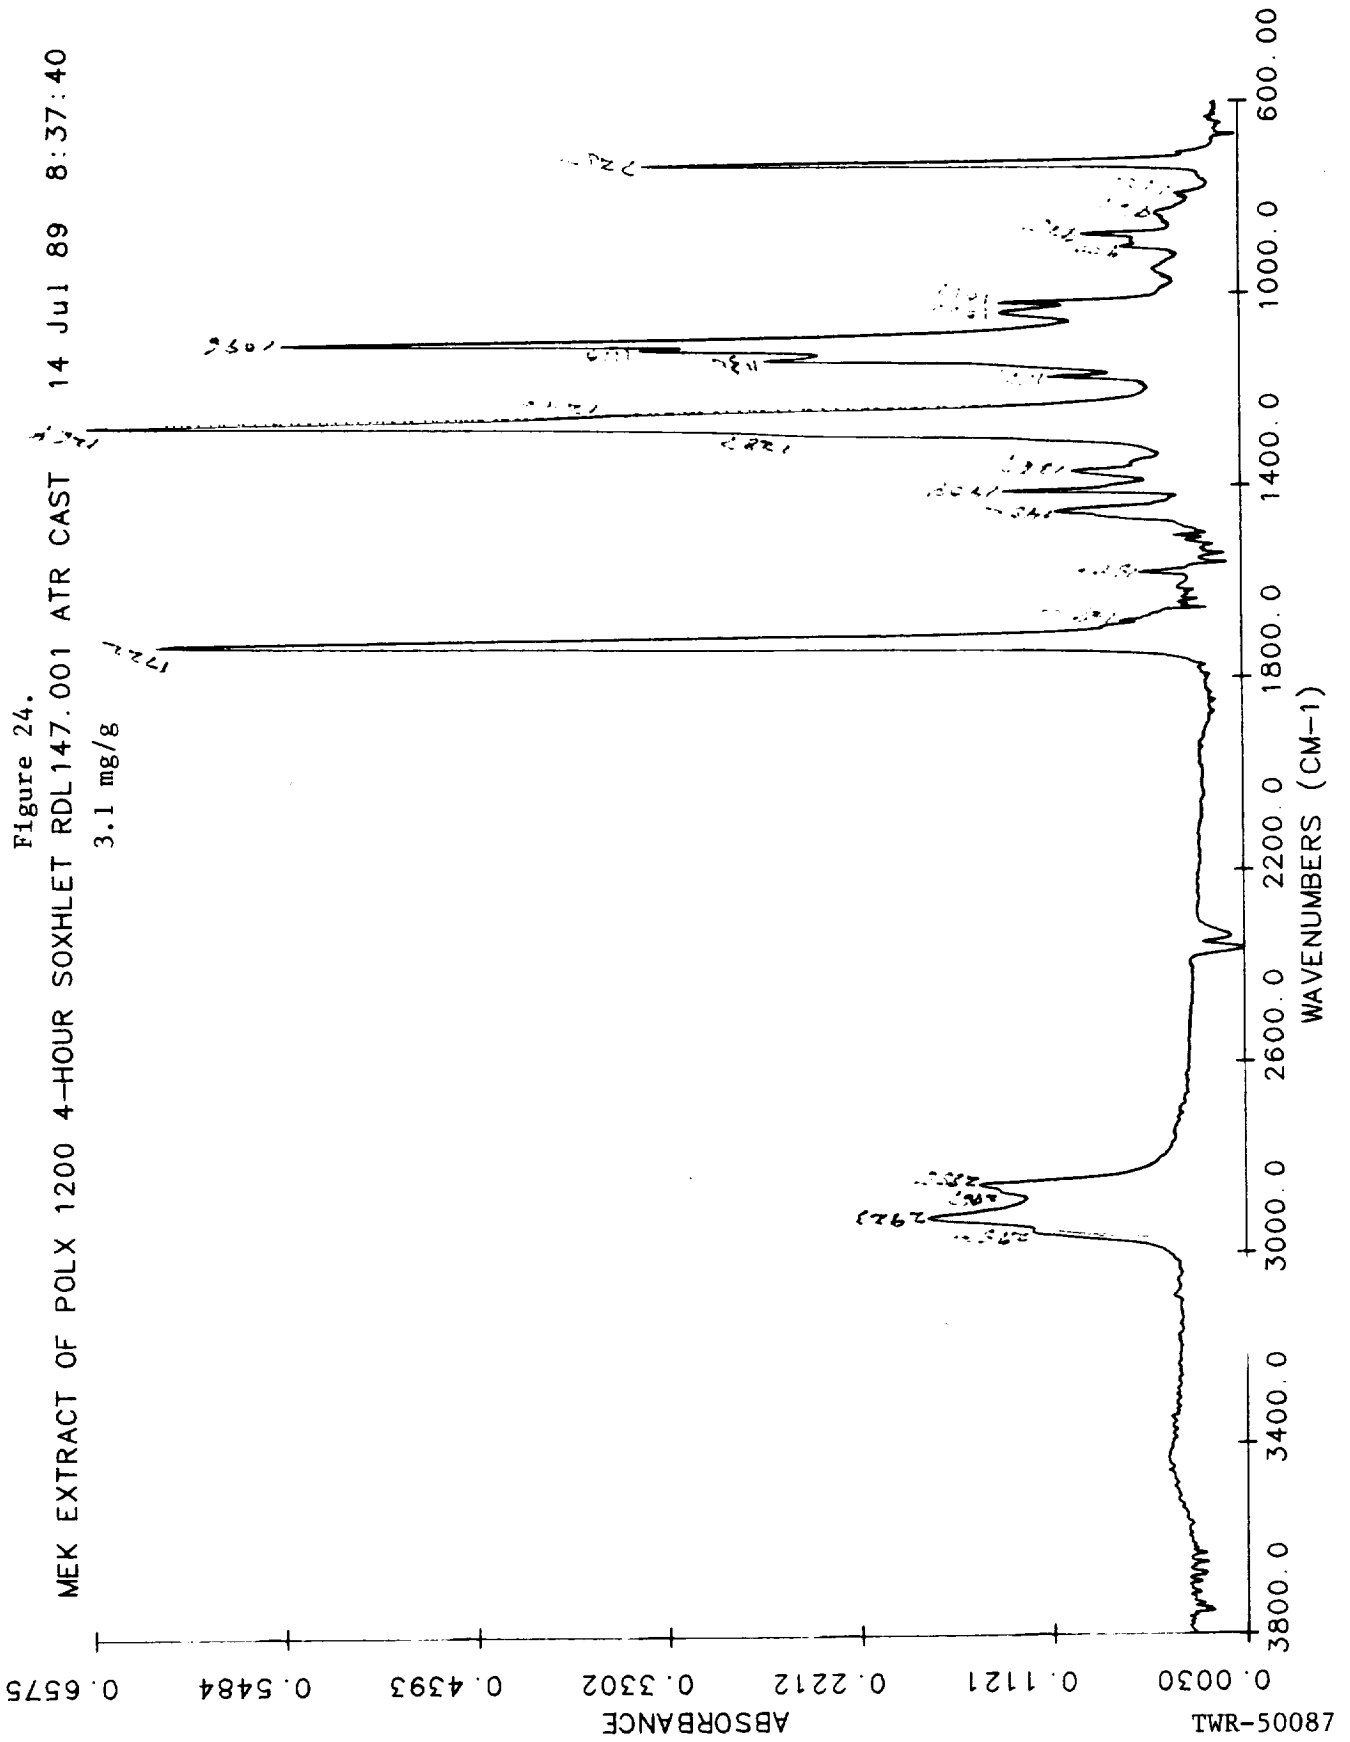

ORIGINAL PAGE IS
OF POOR QUALITY

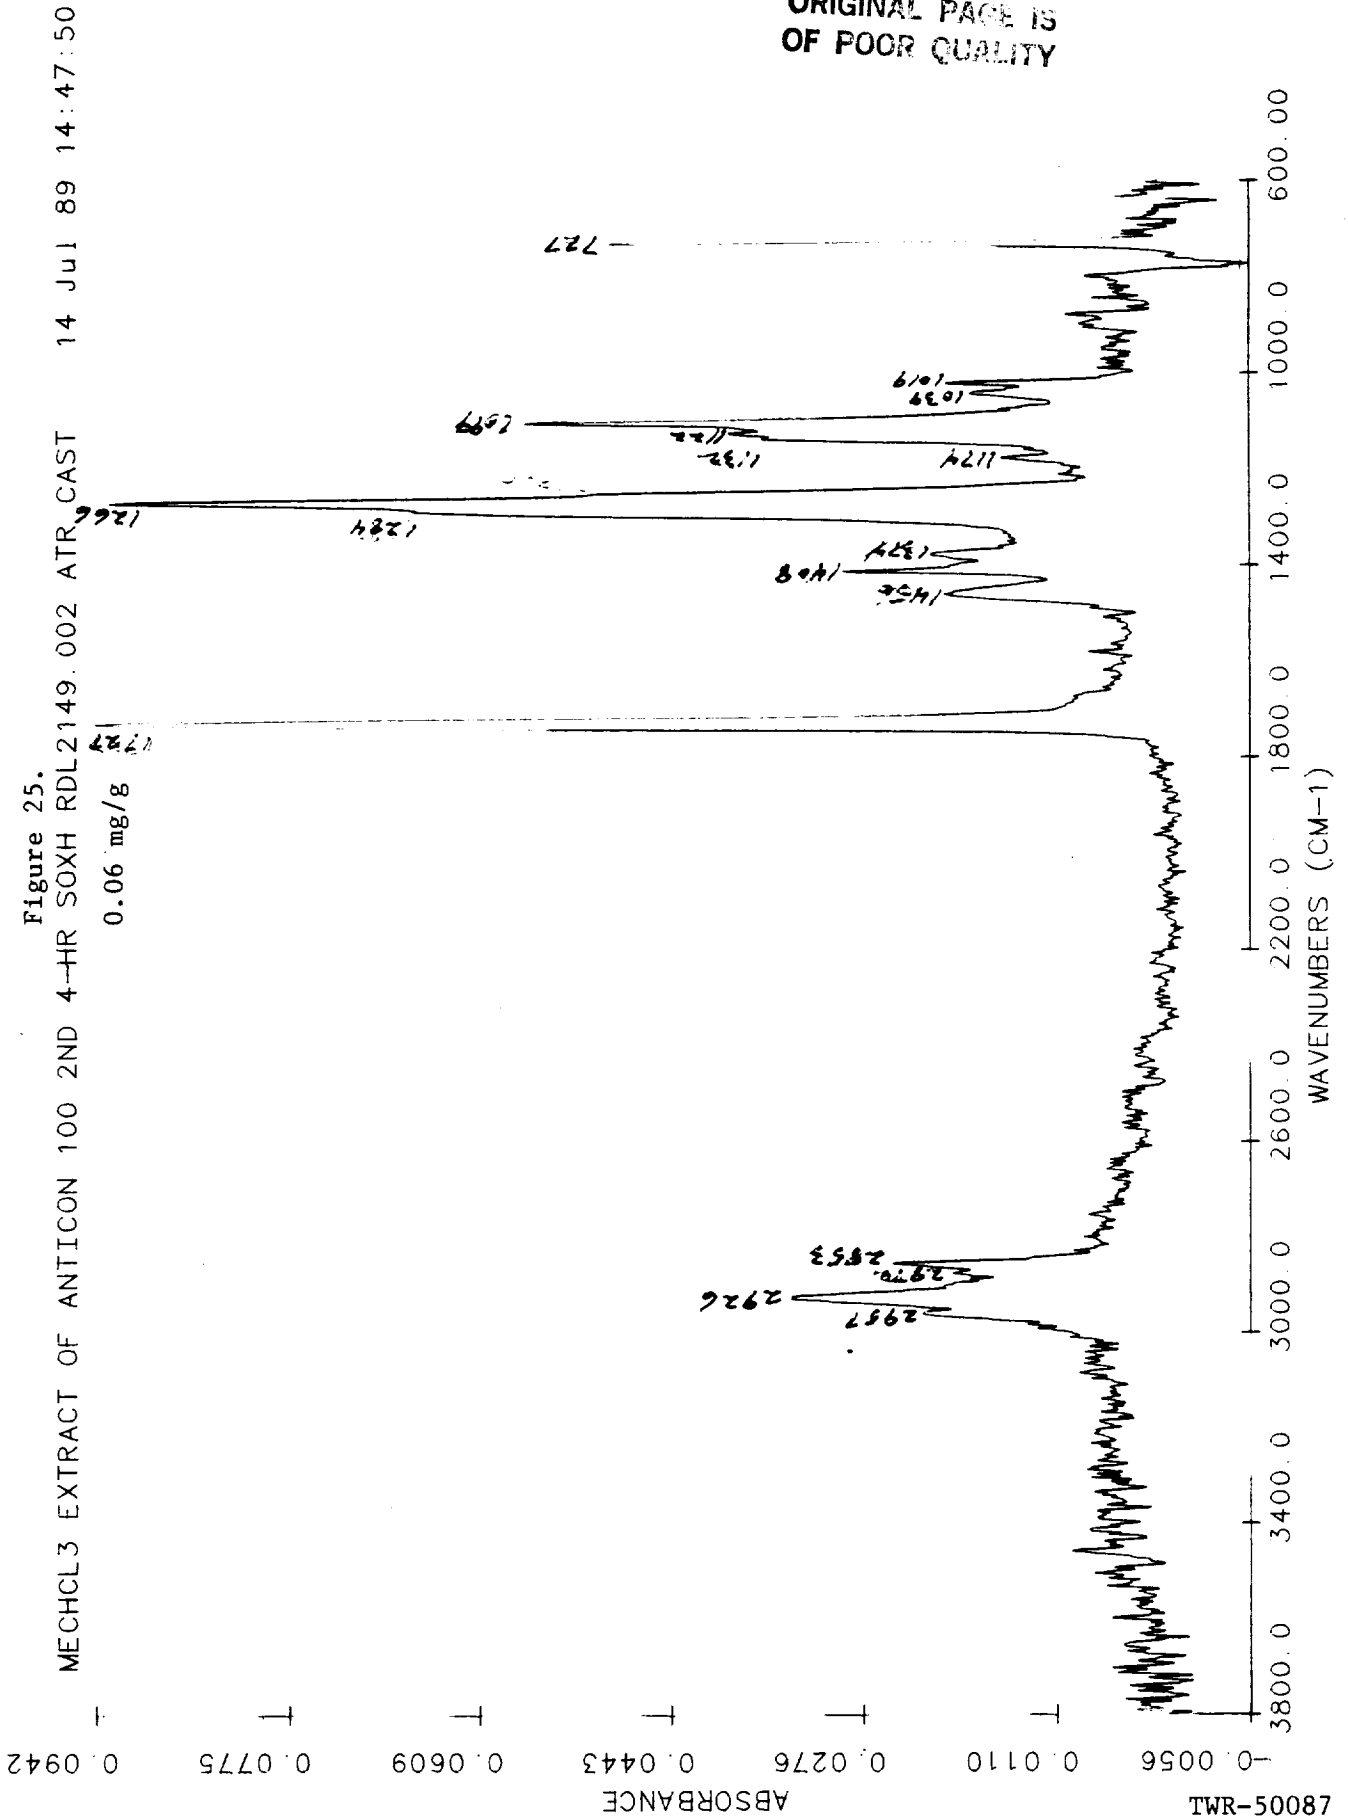

ORIGINAL PAGE IS
OF POOR QUALITY

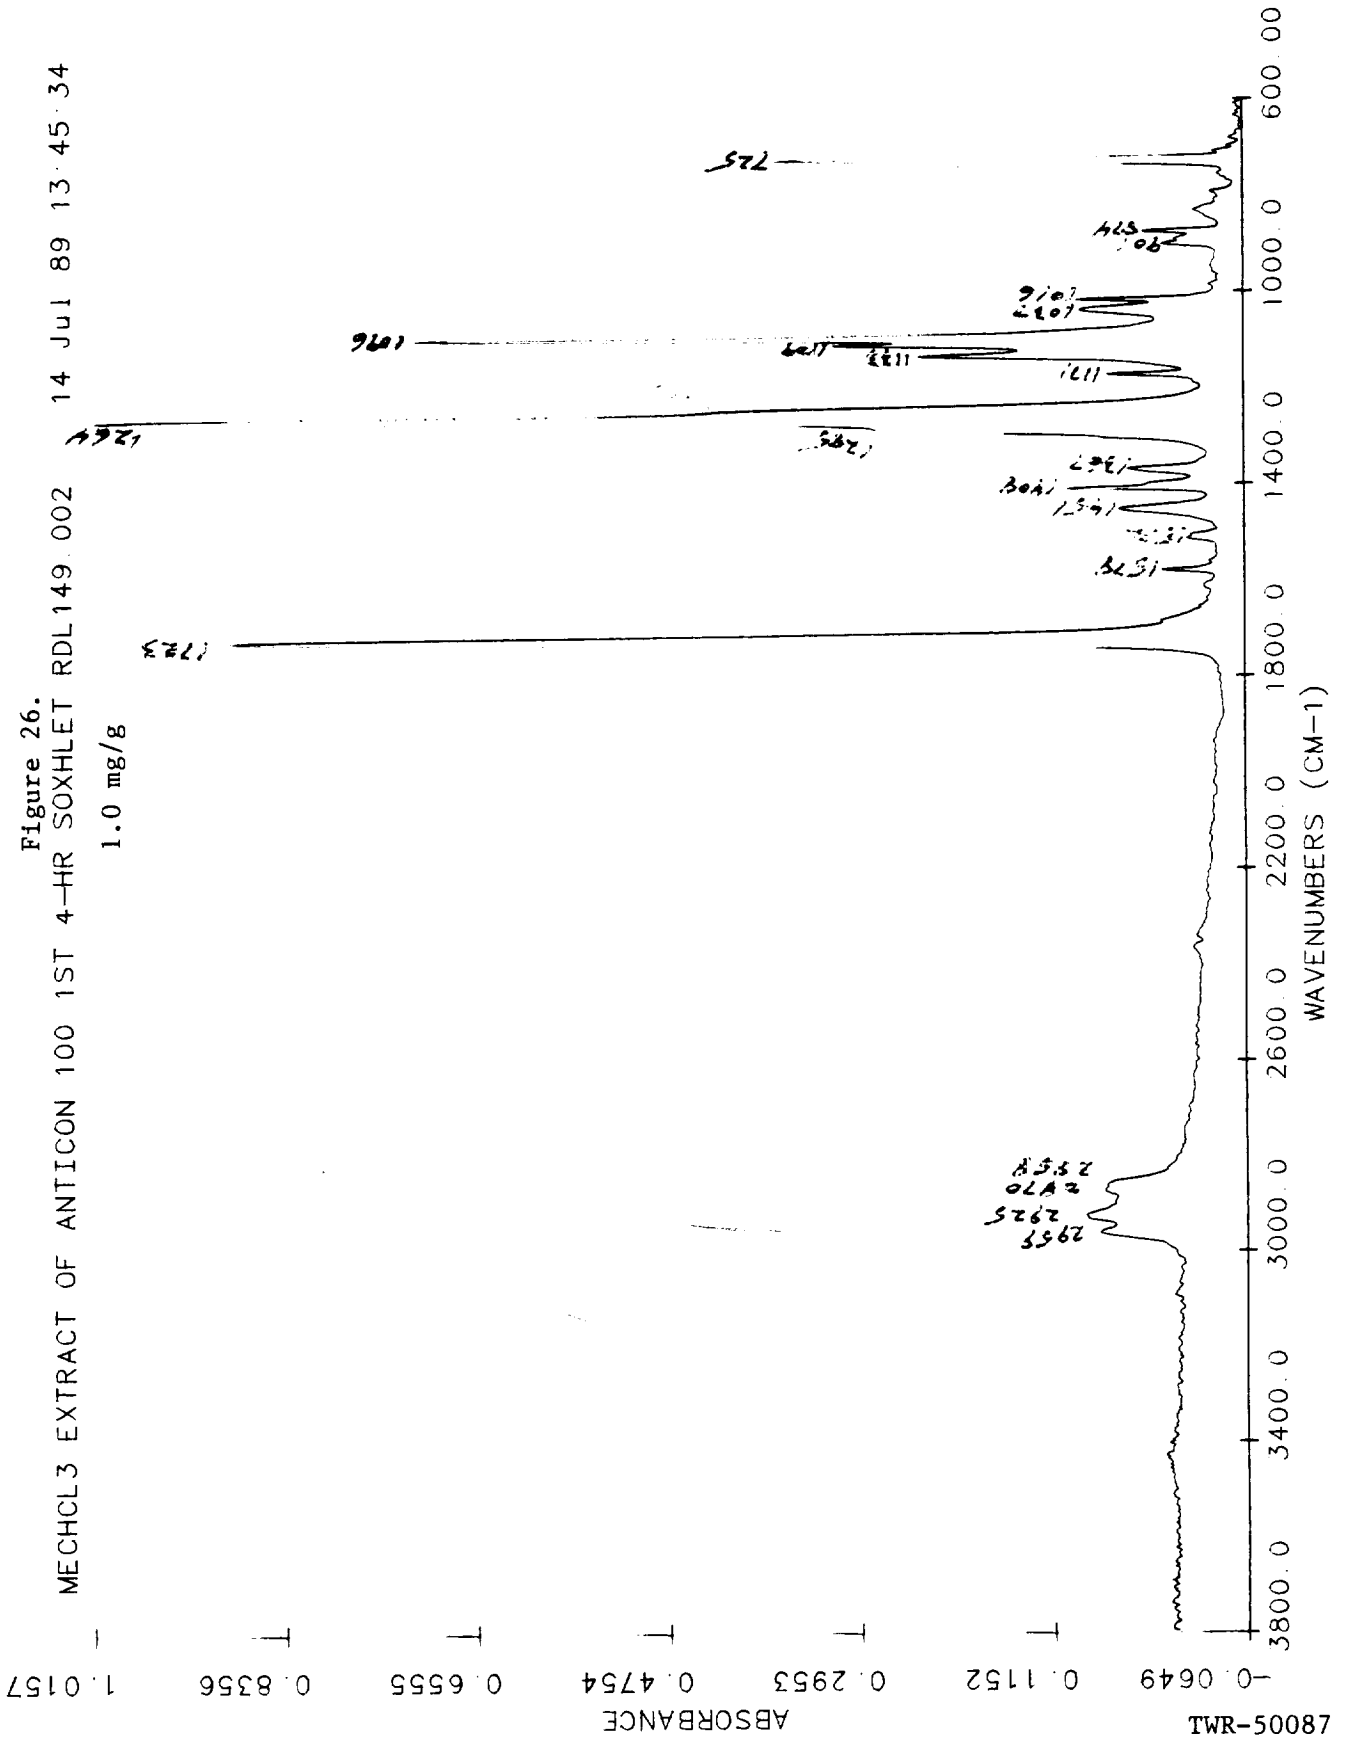


Figure 26.

ORIGINAL PAGE IS
OF POOR QUALITY

14 Jul 89 13:02:34

FREON TF EXTRACT OF ANTICON 100 2ND 4-HR SOXH RDL2148.002 ATR CAST

0.1 mg/g

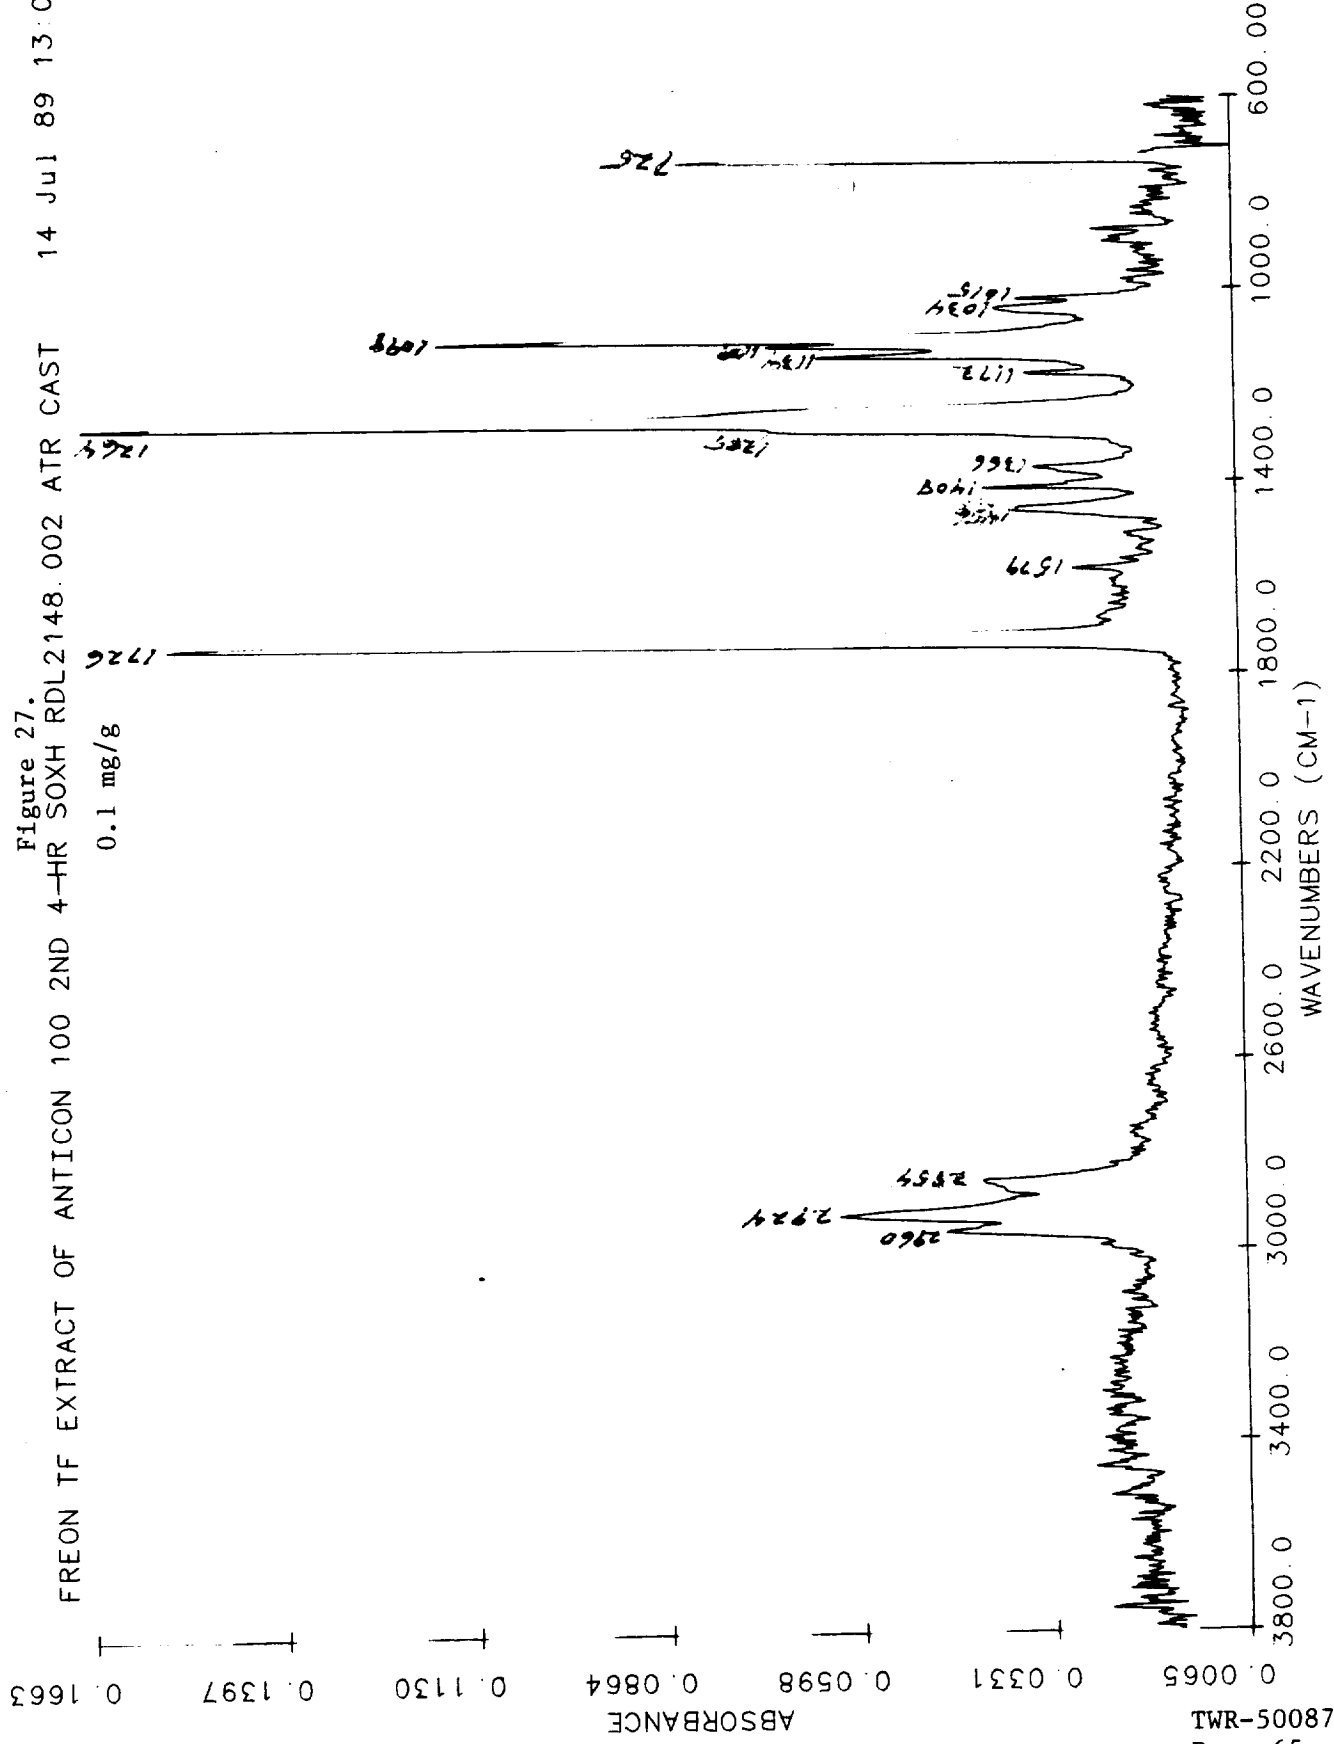



Figure 27.

ORIGINAL PAGE IS
OF POOR QUALITY


14 Jul 89 10:42:02

FREON TF EXTRACT OF ANTICON 100 1ST 4-HR SOXH RDL148.002 ATR CASTS

0.3 mg/g

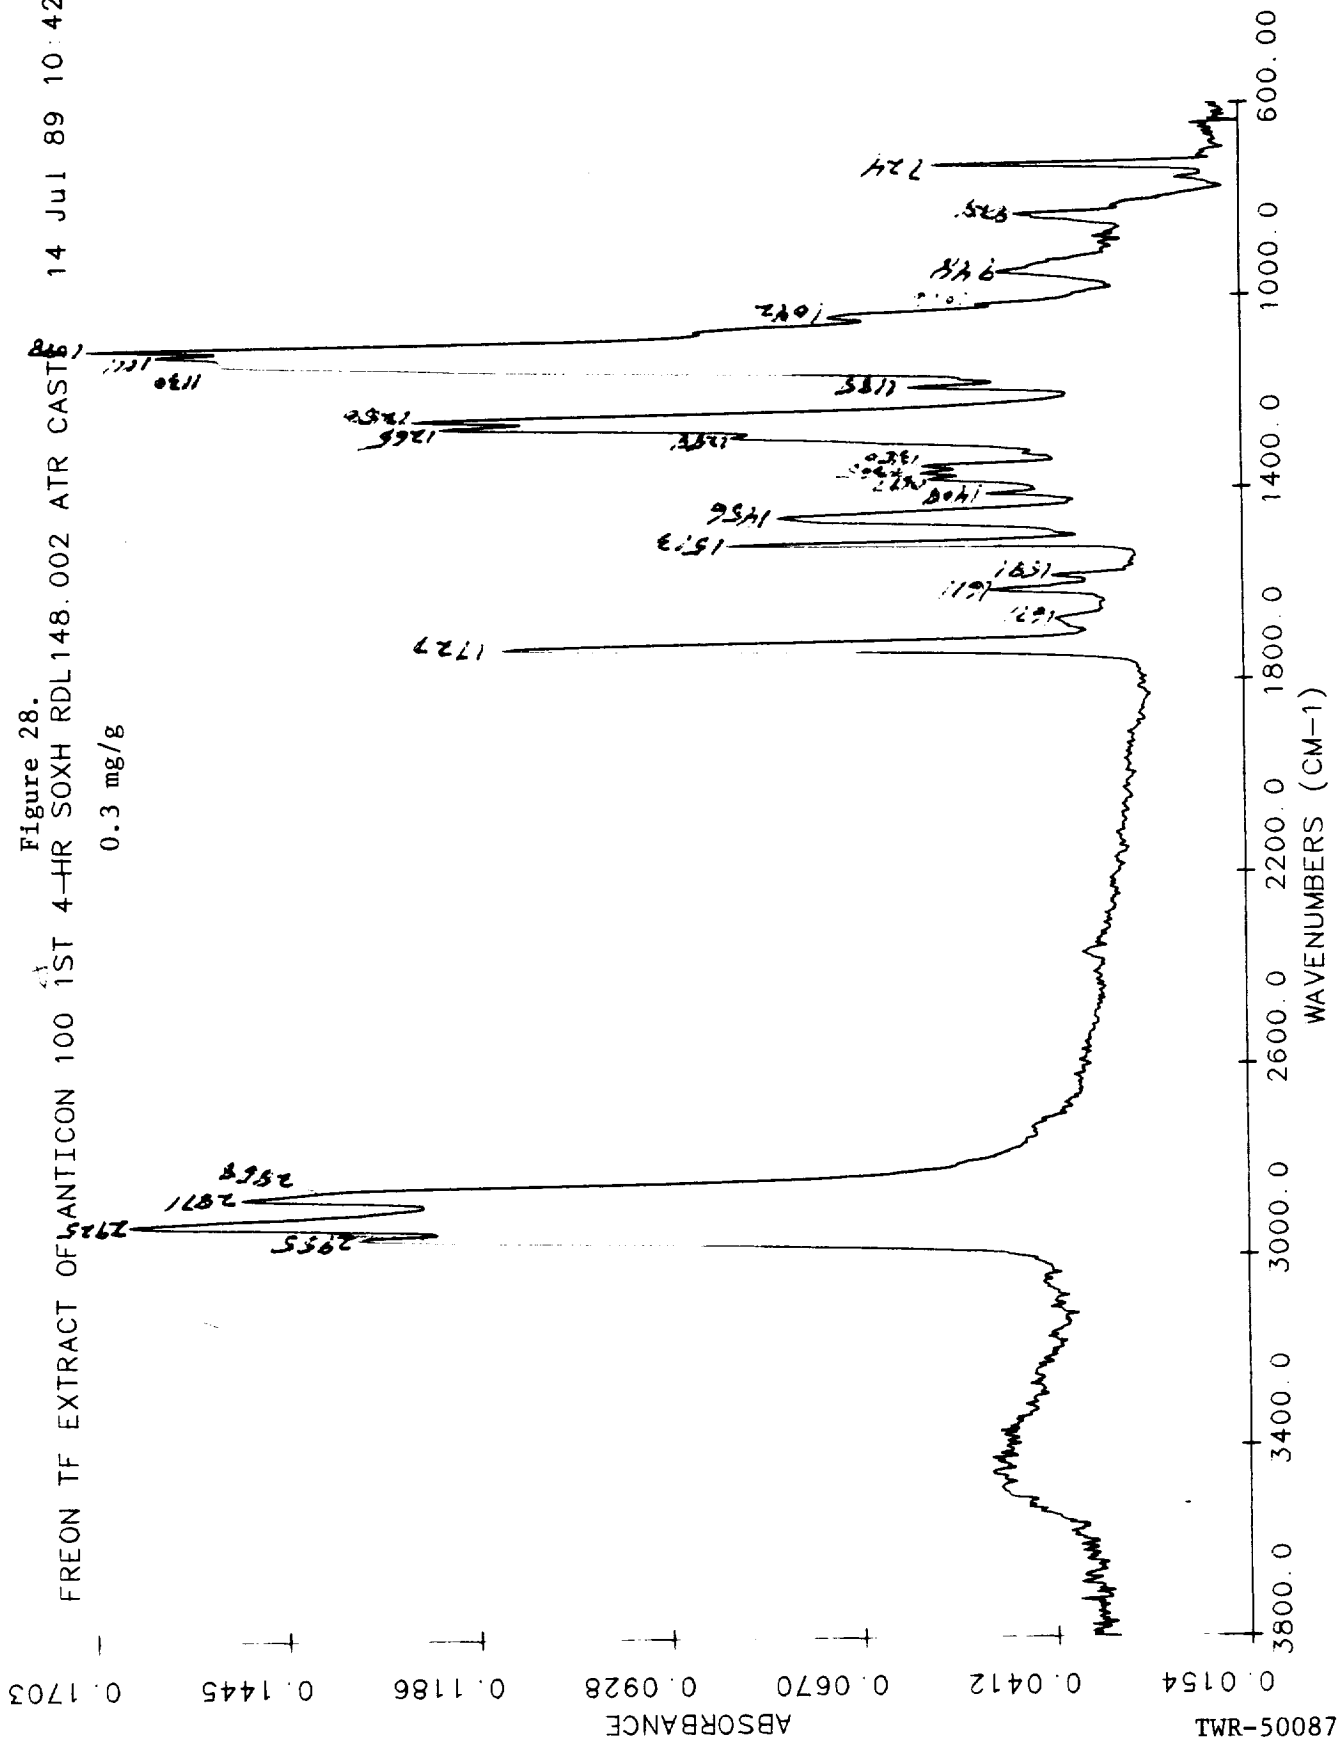

ORIGINAL PAGE IS
OF POOR QUALITY

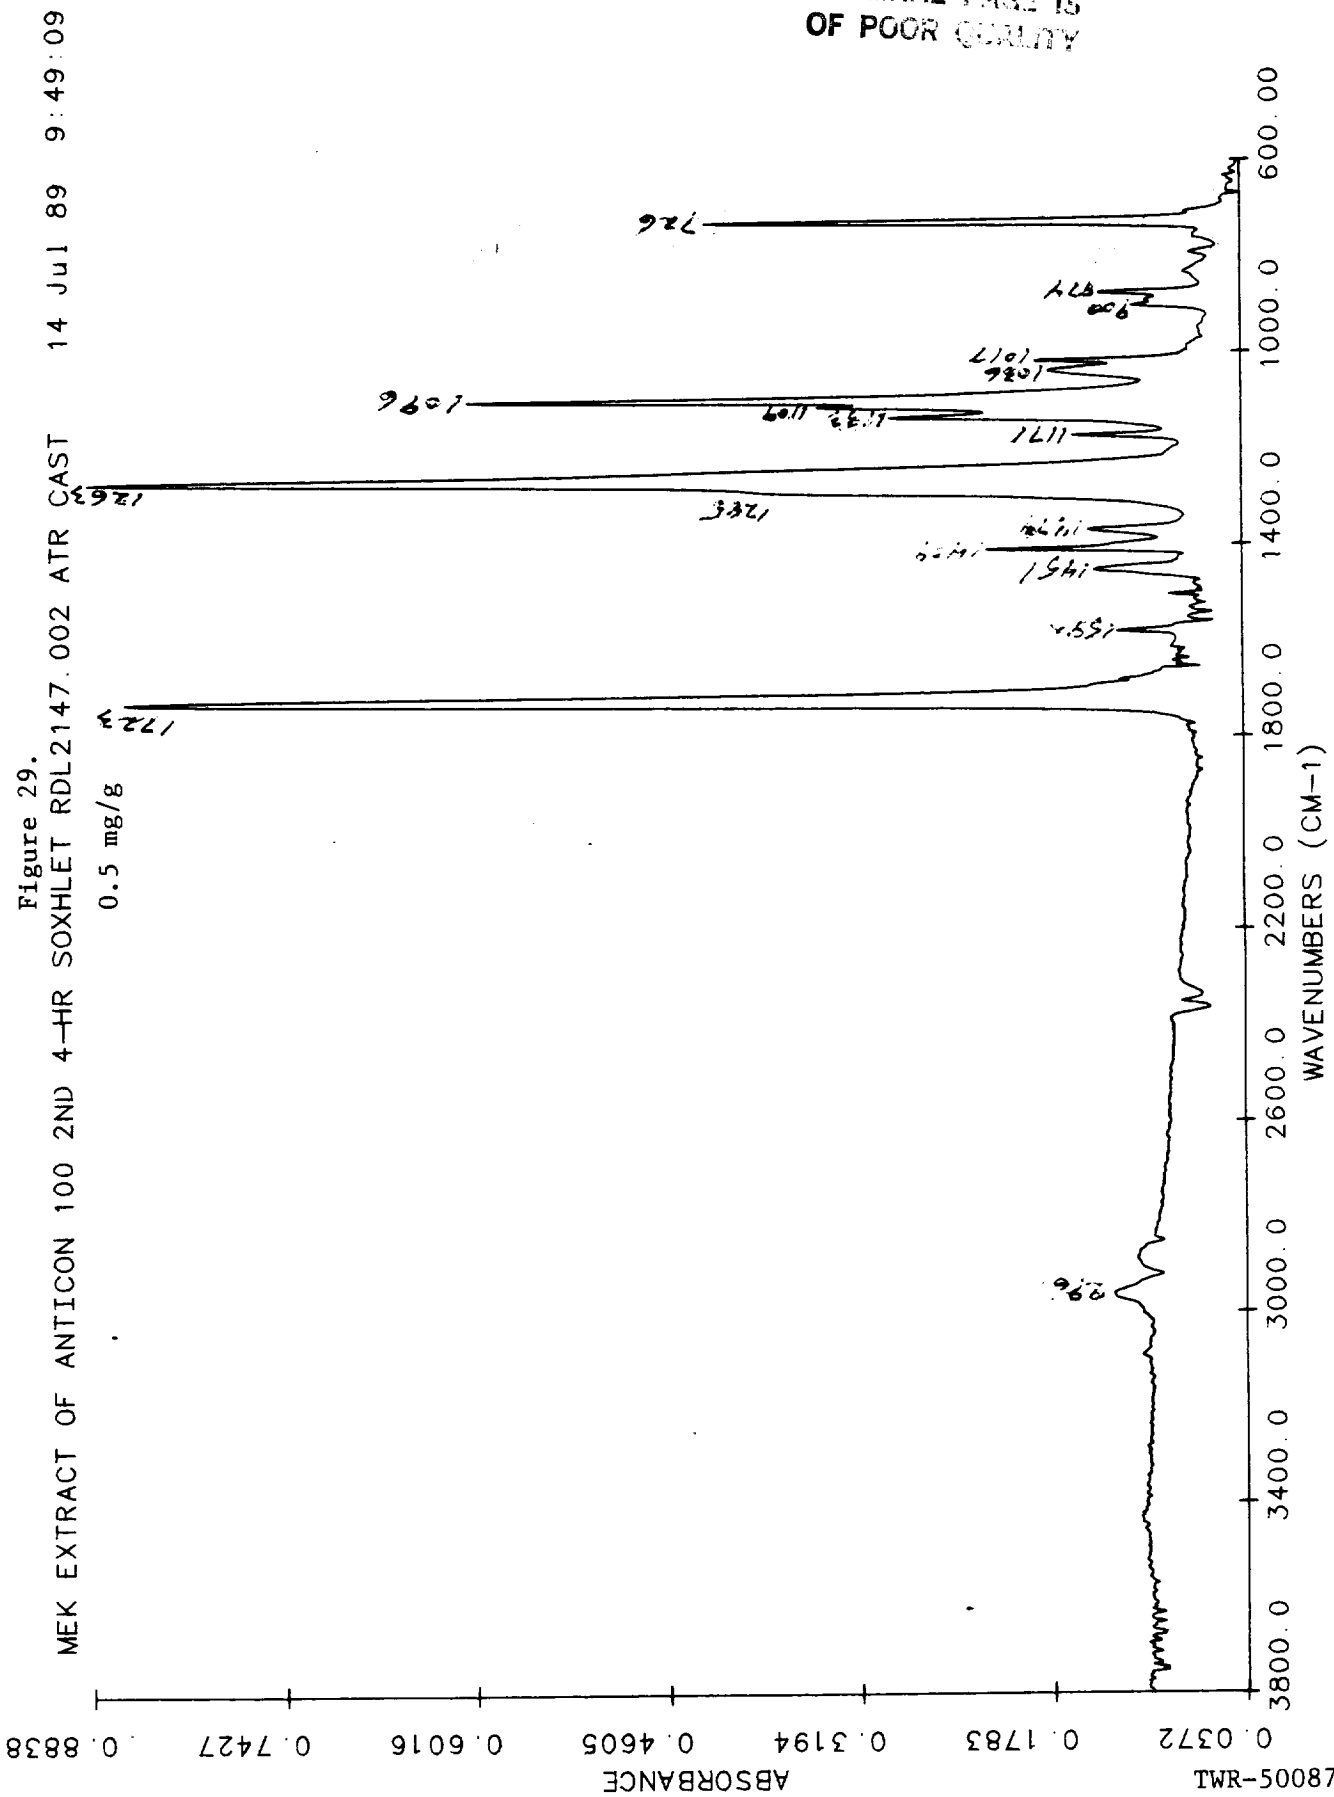

ORIGINAL PAGE IS
OF POOR QUALITY

14 Jul 89 8:47:13

MEK EXTRACT OF ANTICON 100 FIRST 4-HOUR SOXHLET RDL147.002 ATR CAST

2.58 mg/g

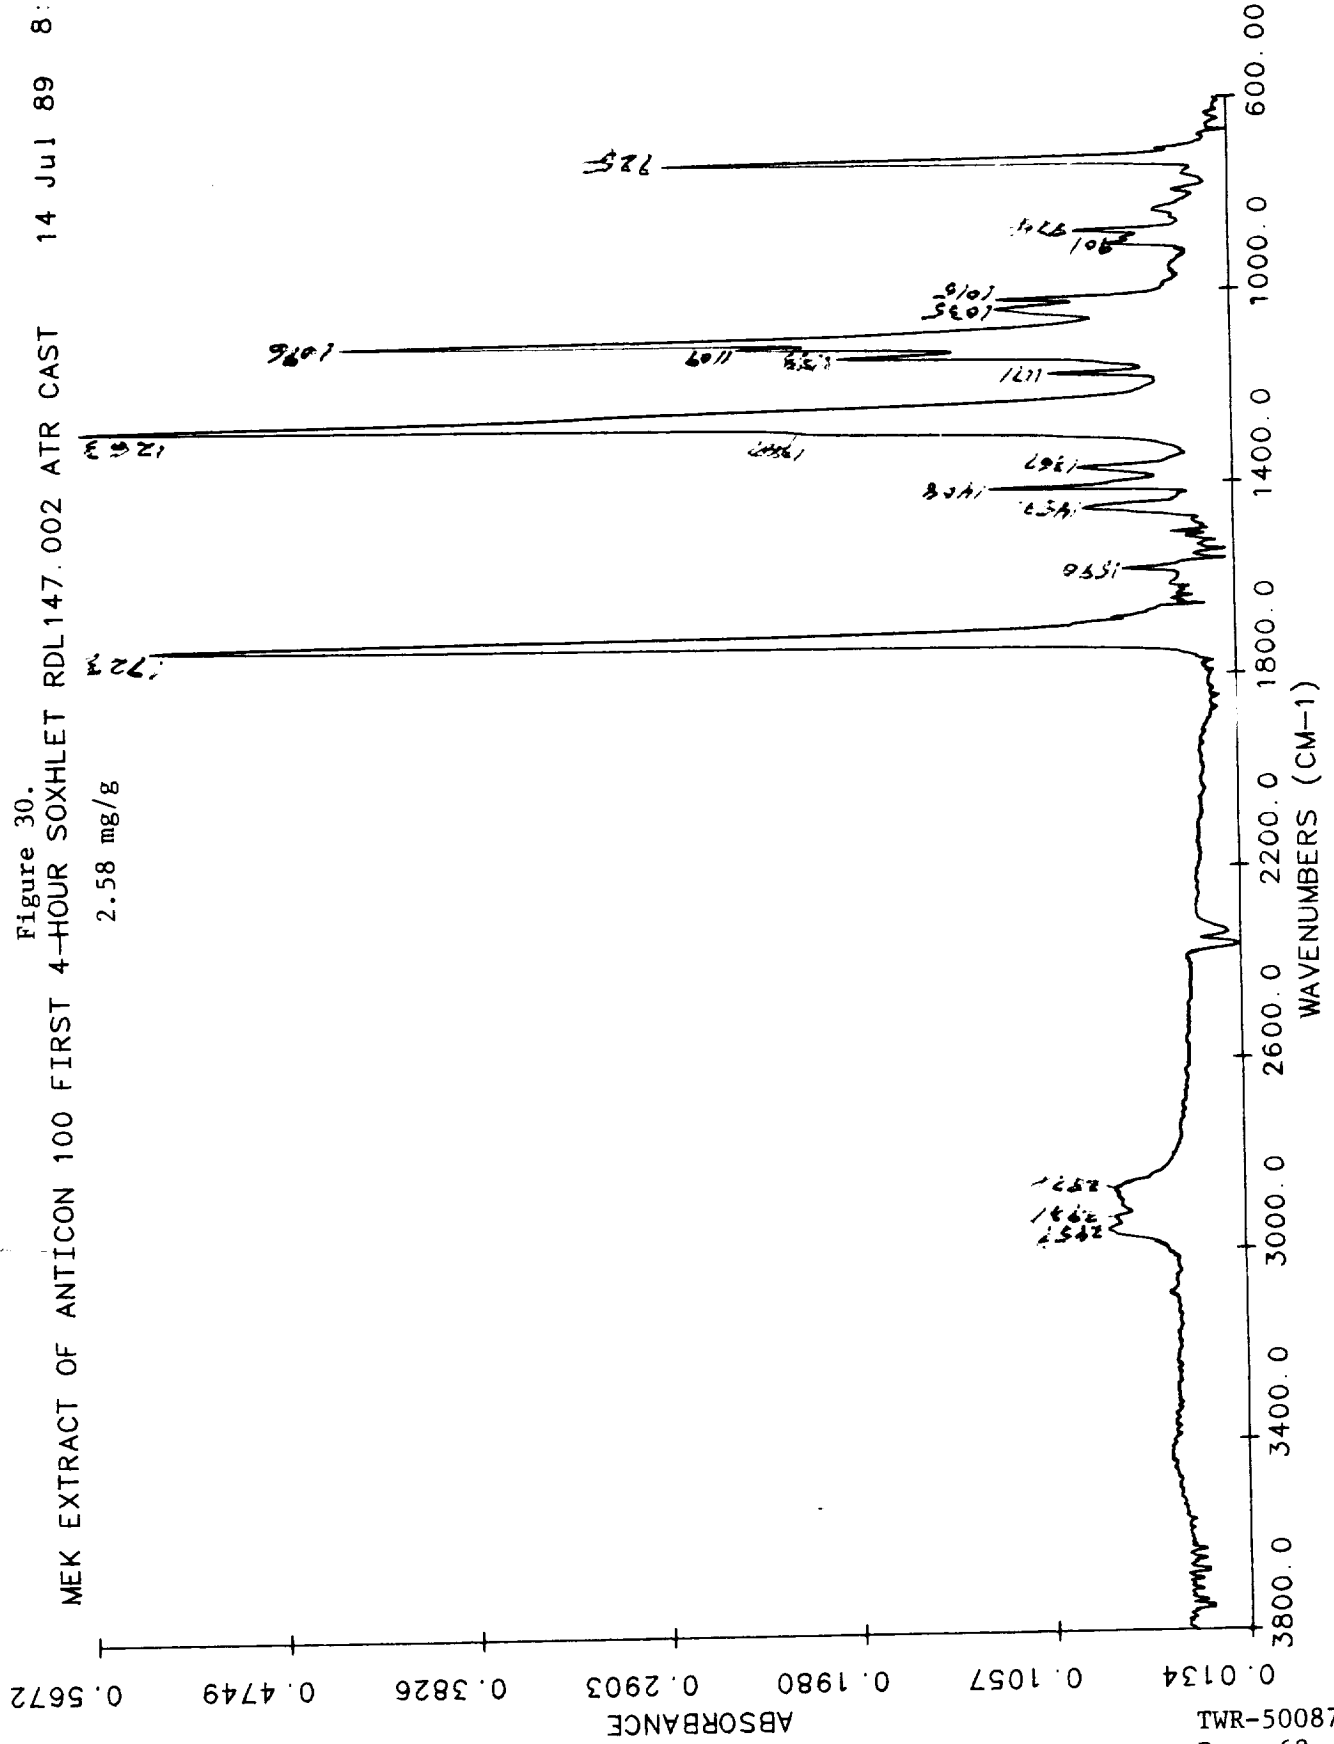


Figure 31.



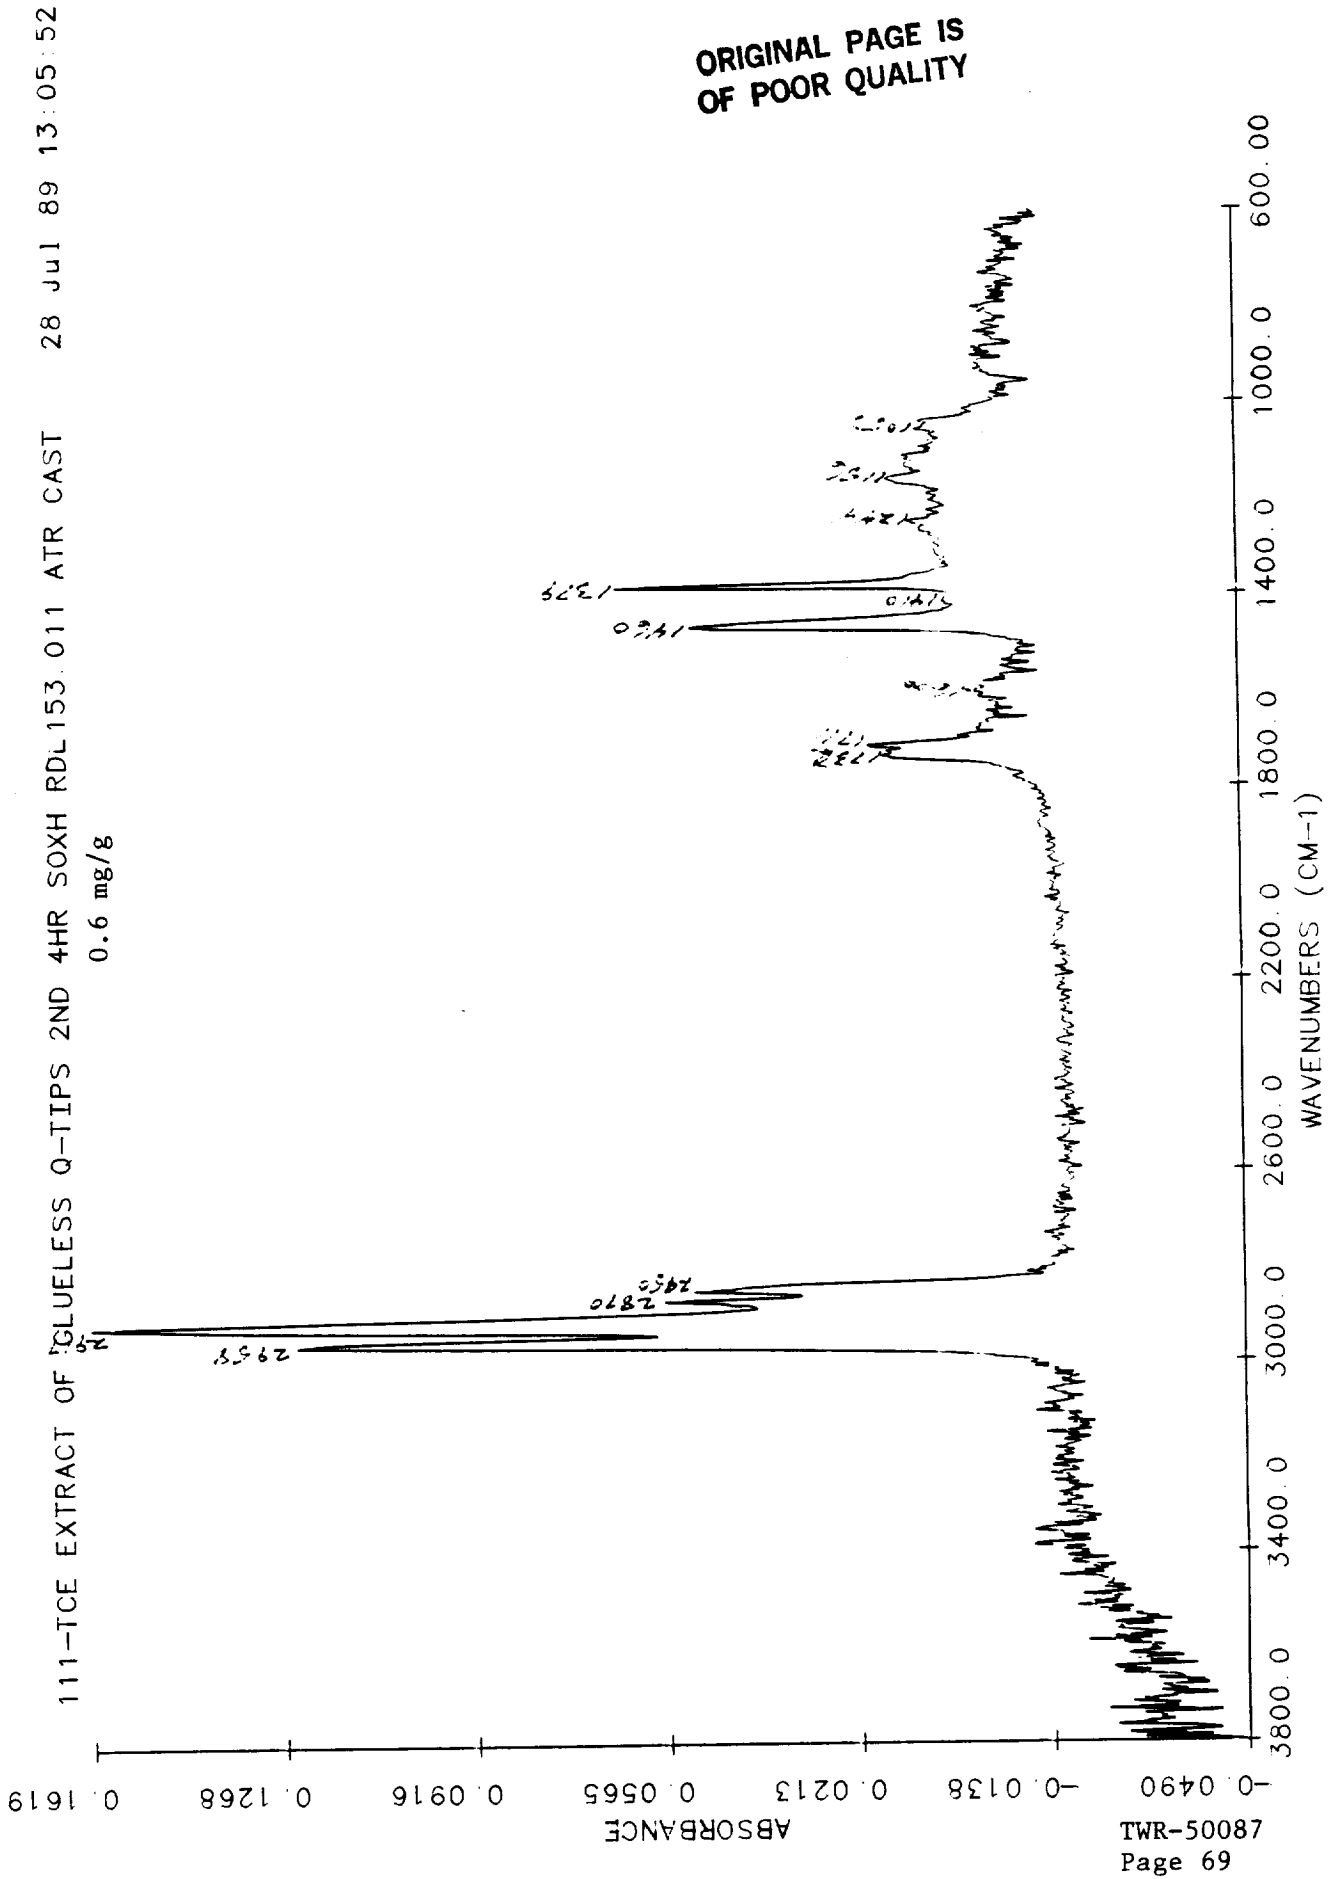


Figure 32.

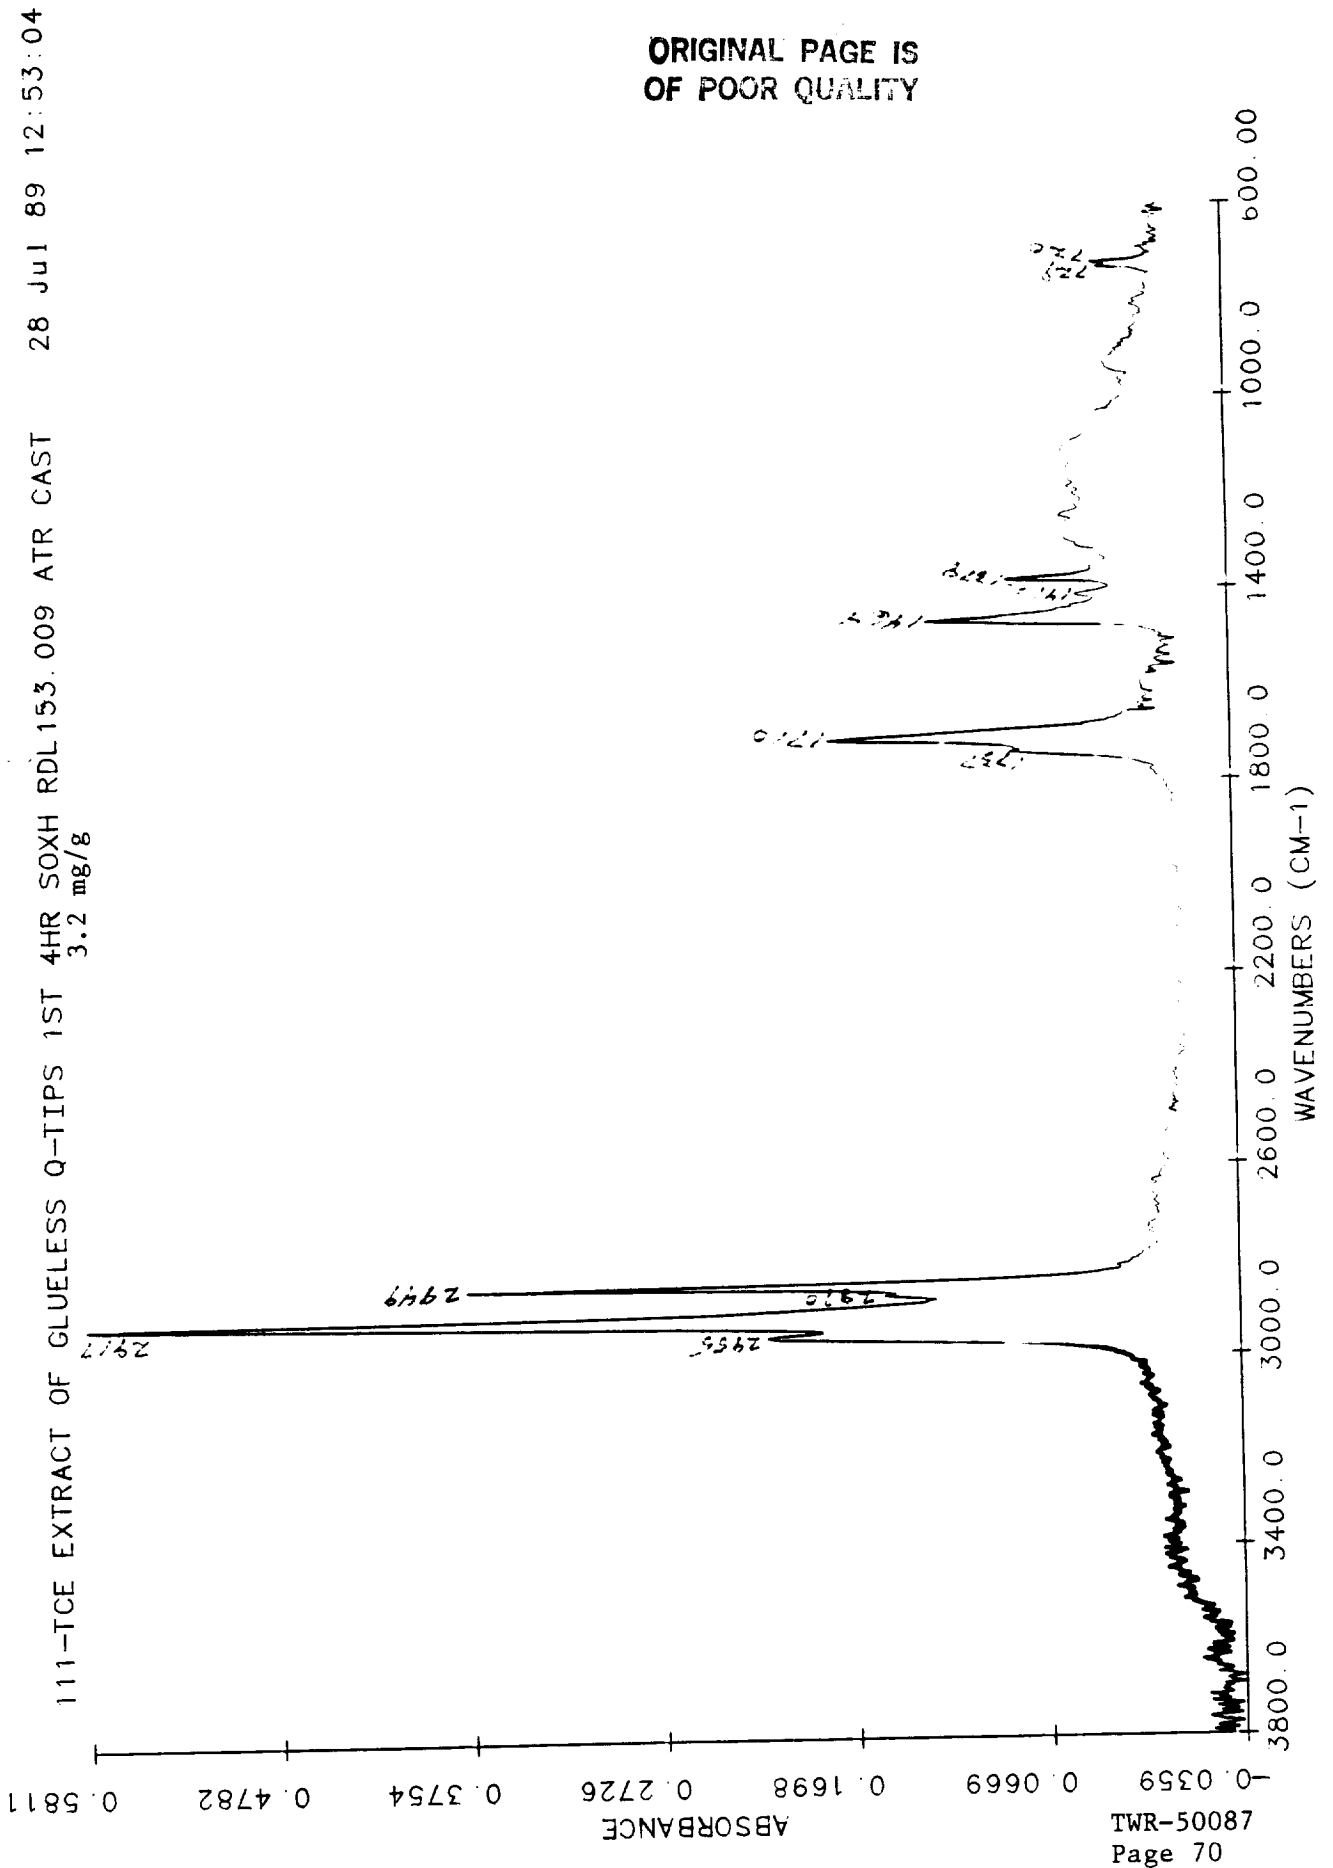


ORIGINAL PAGE IS
OF POOR QUALITY

Figure 33.

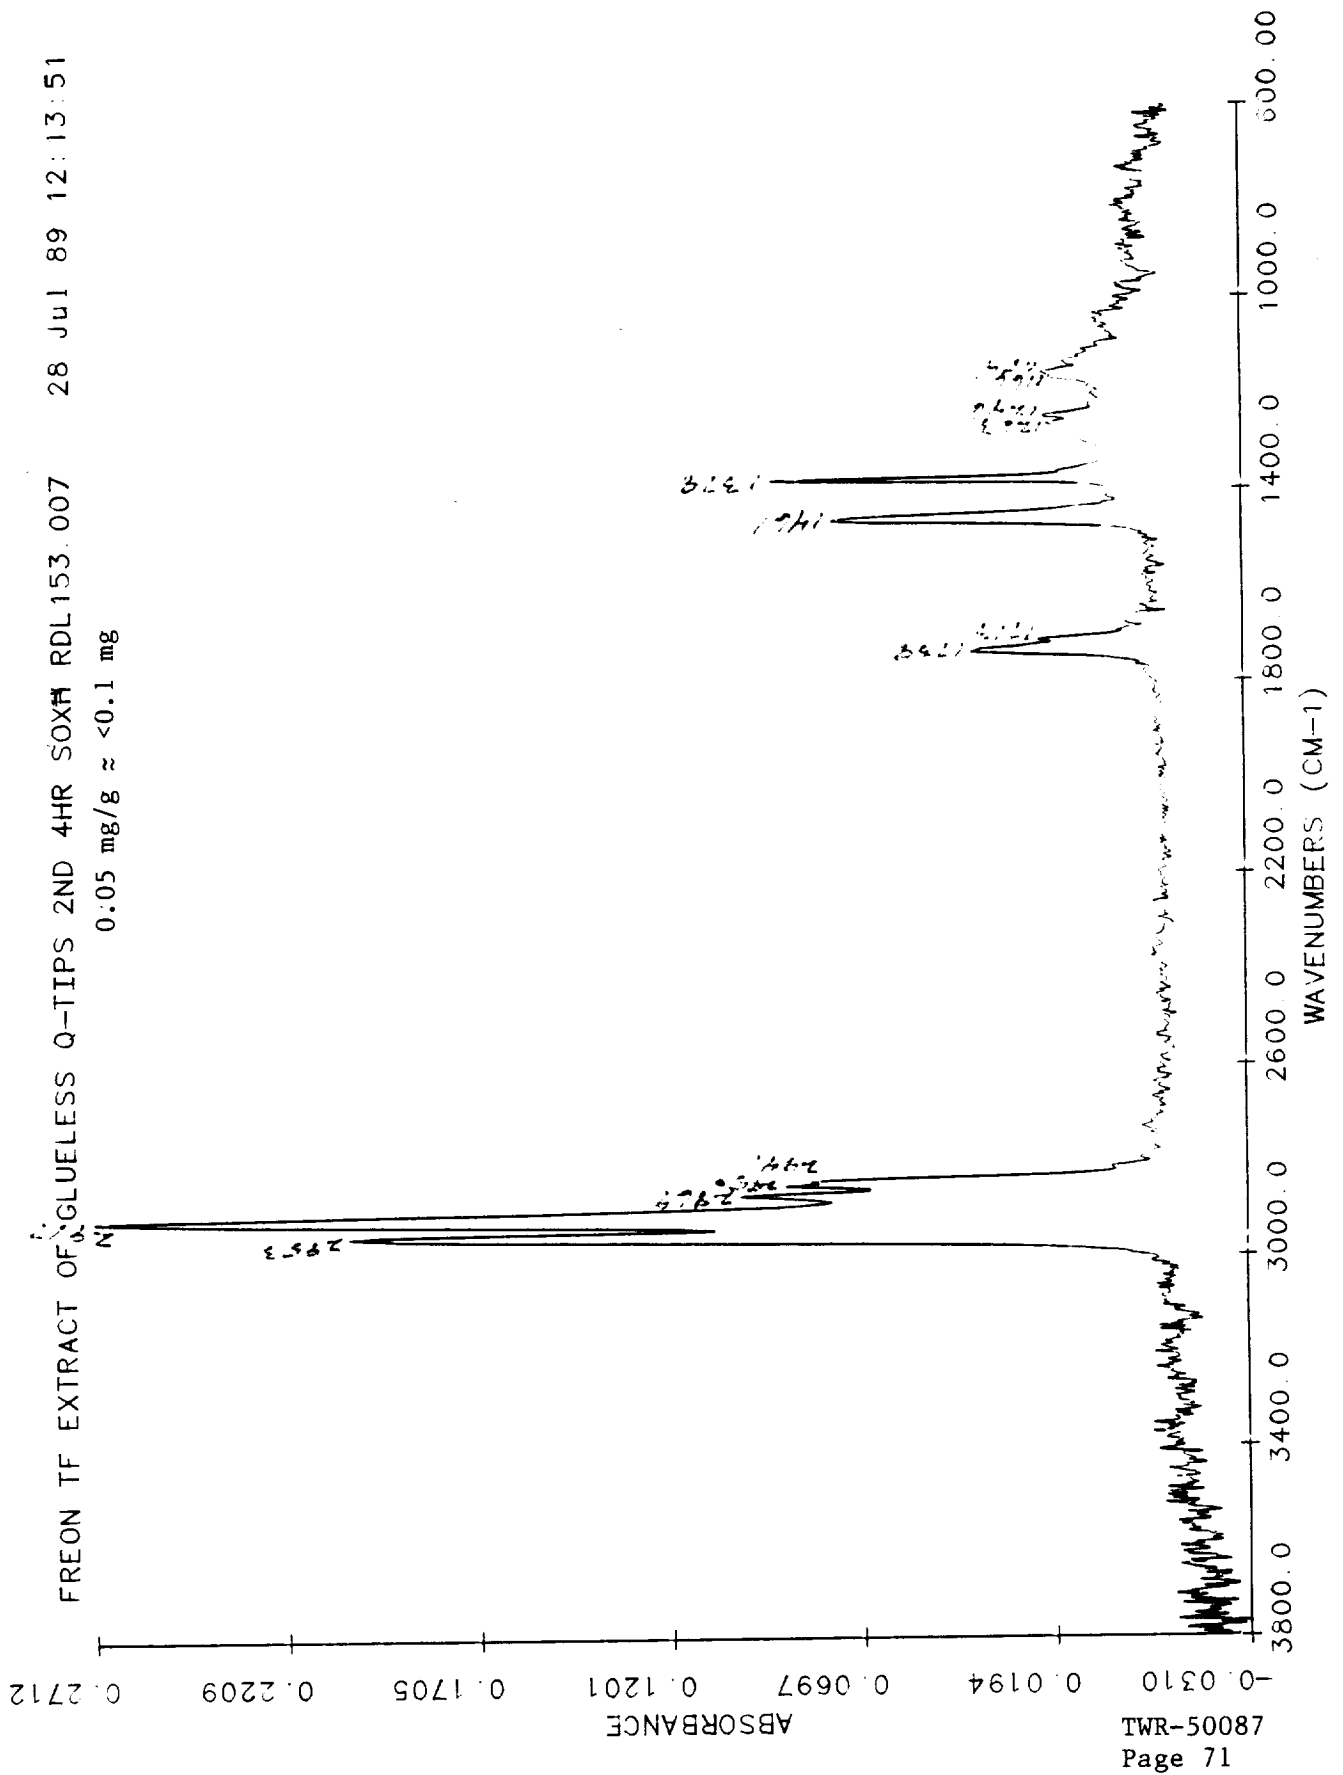

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 34.

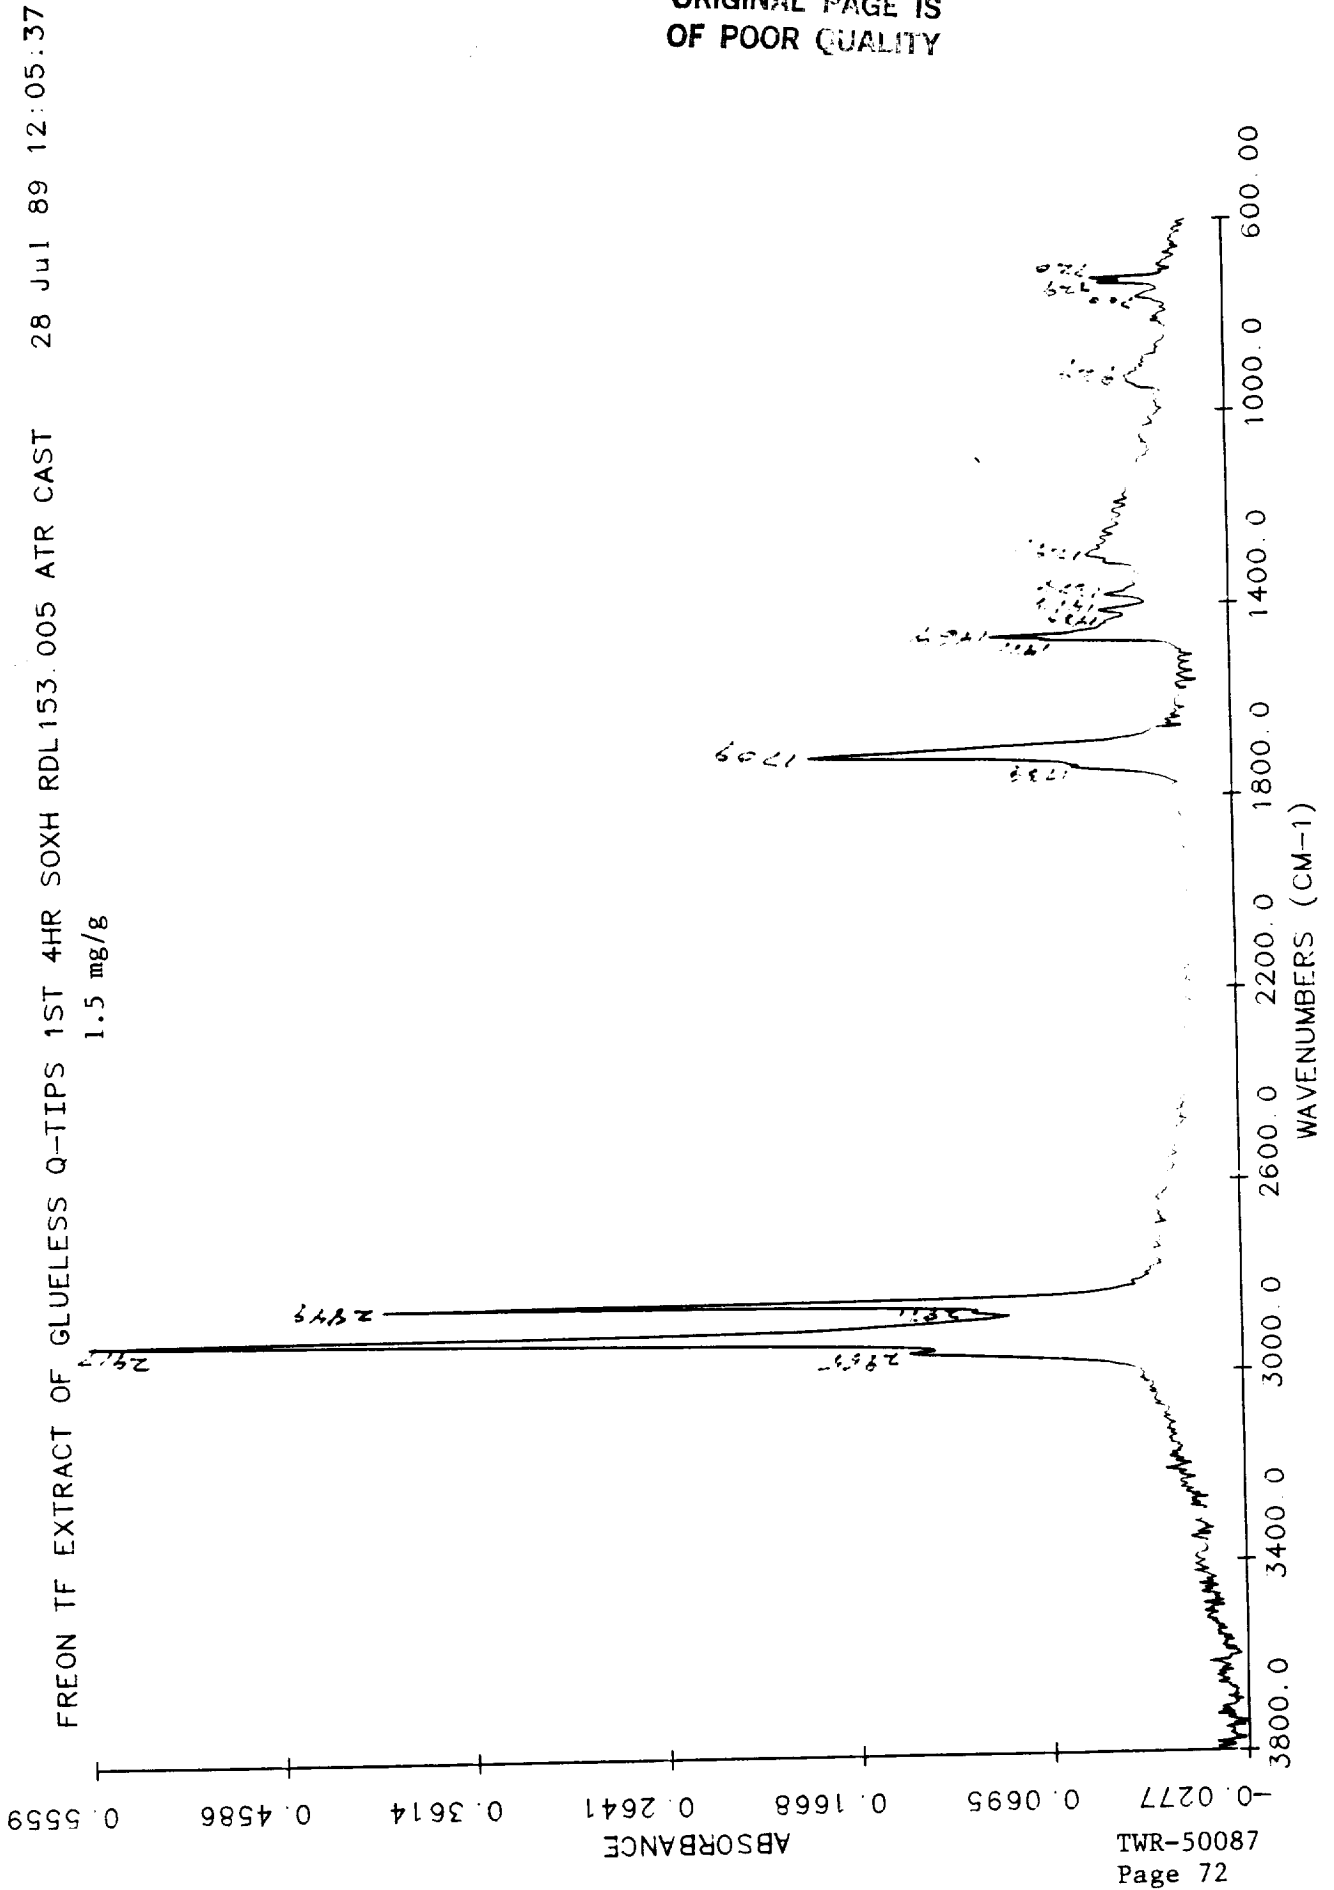

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 35.


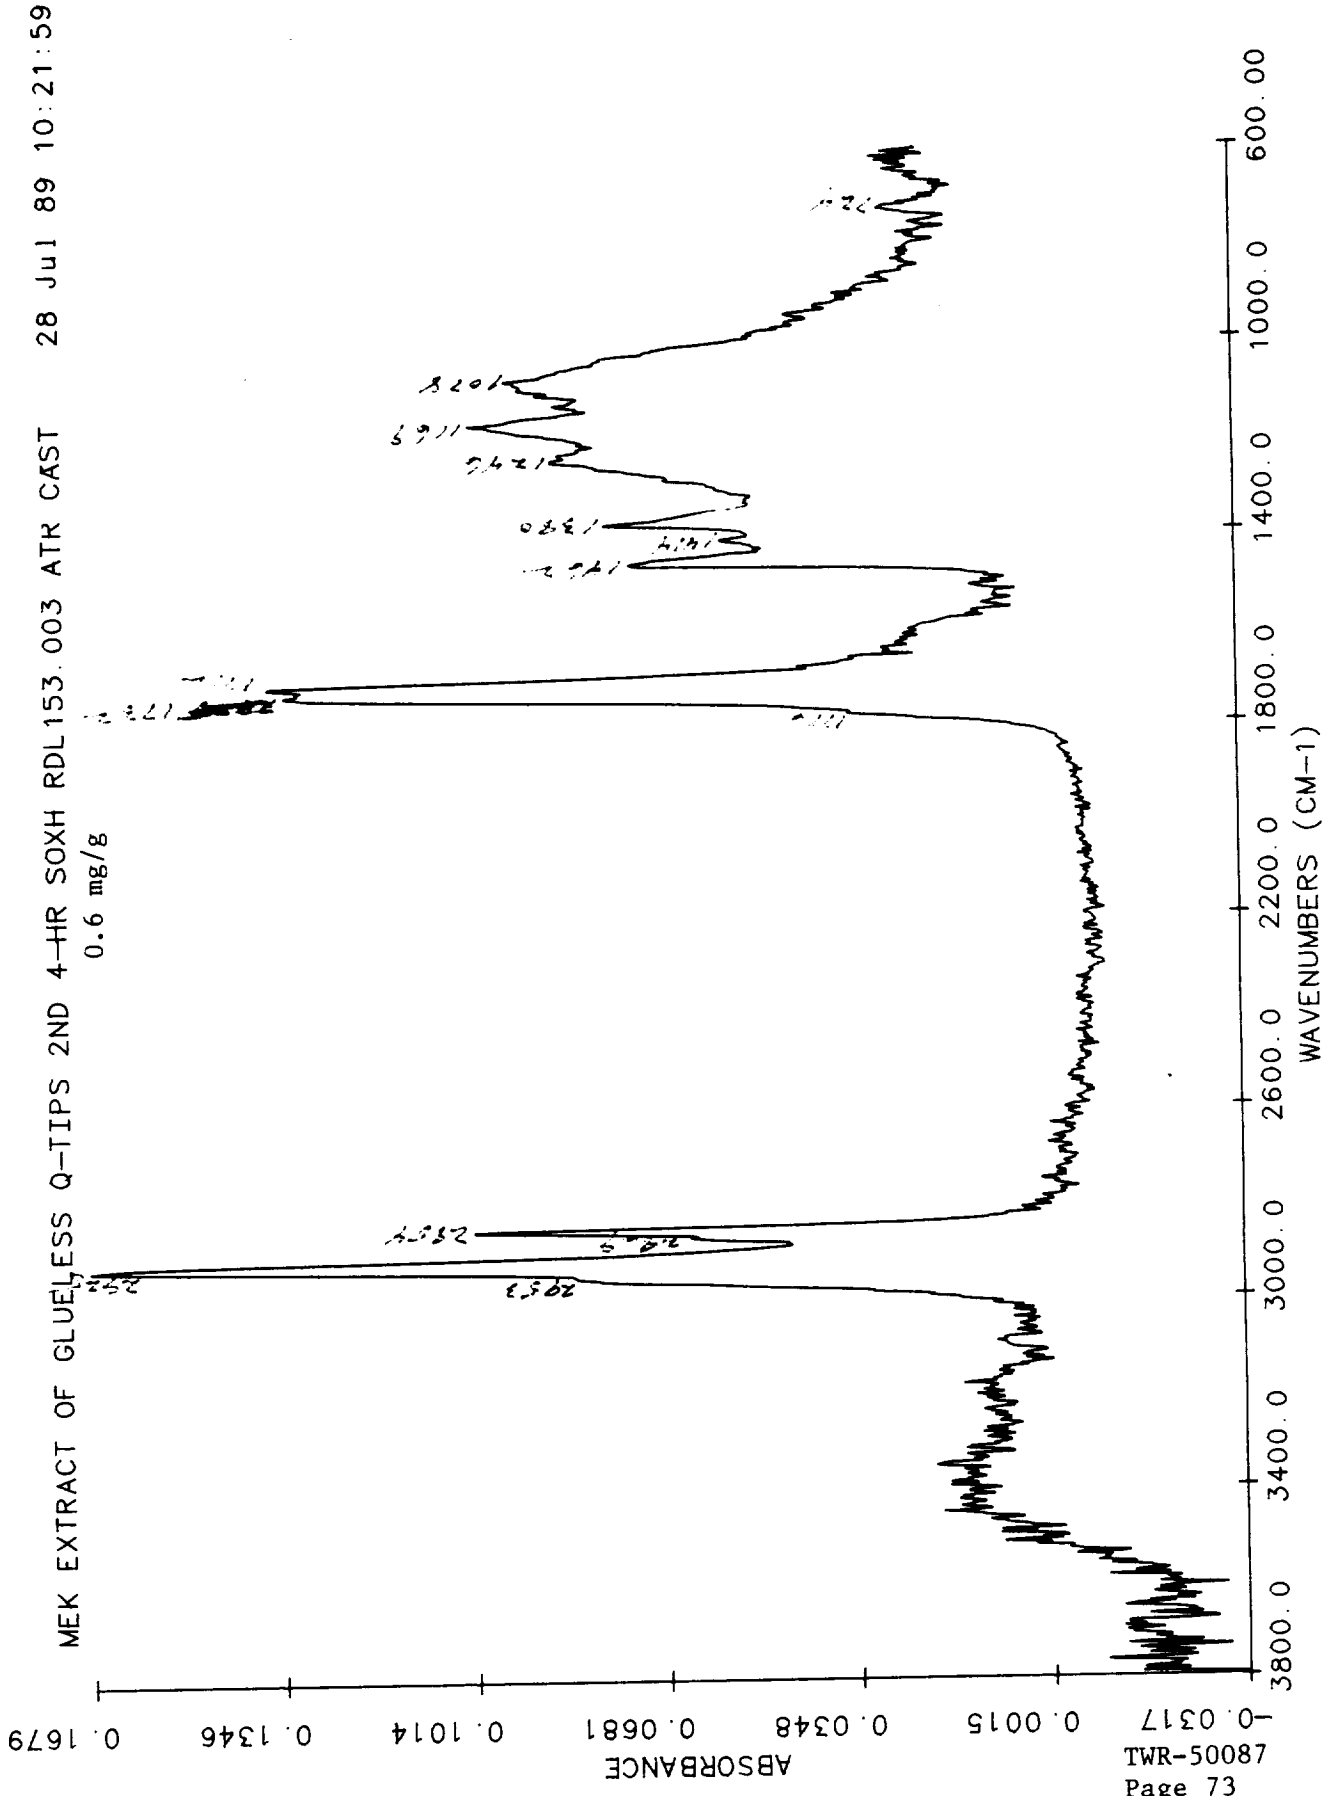


Figure 36.

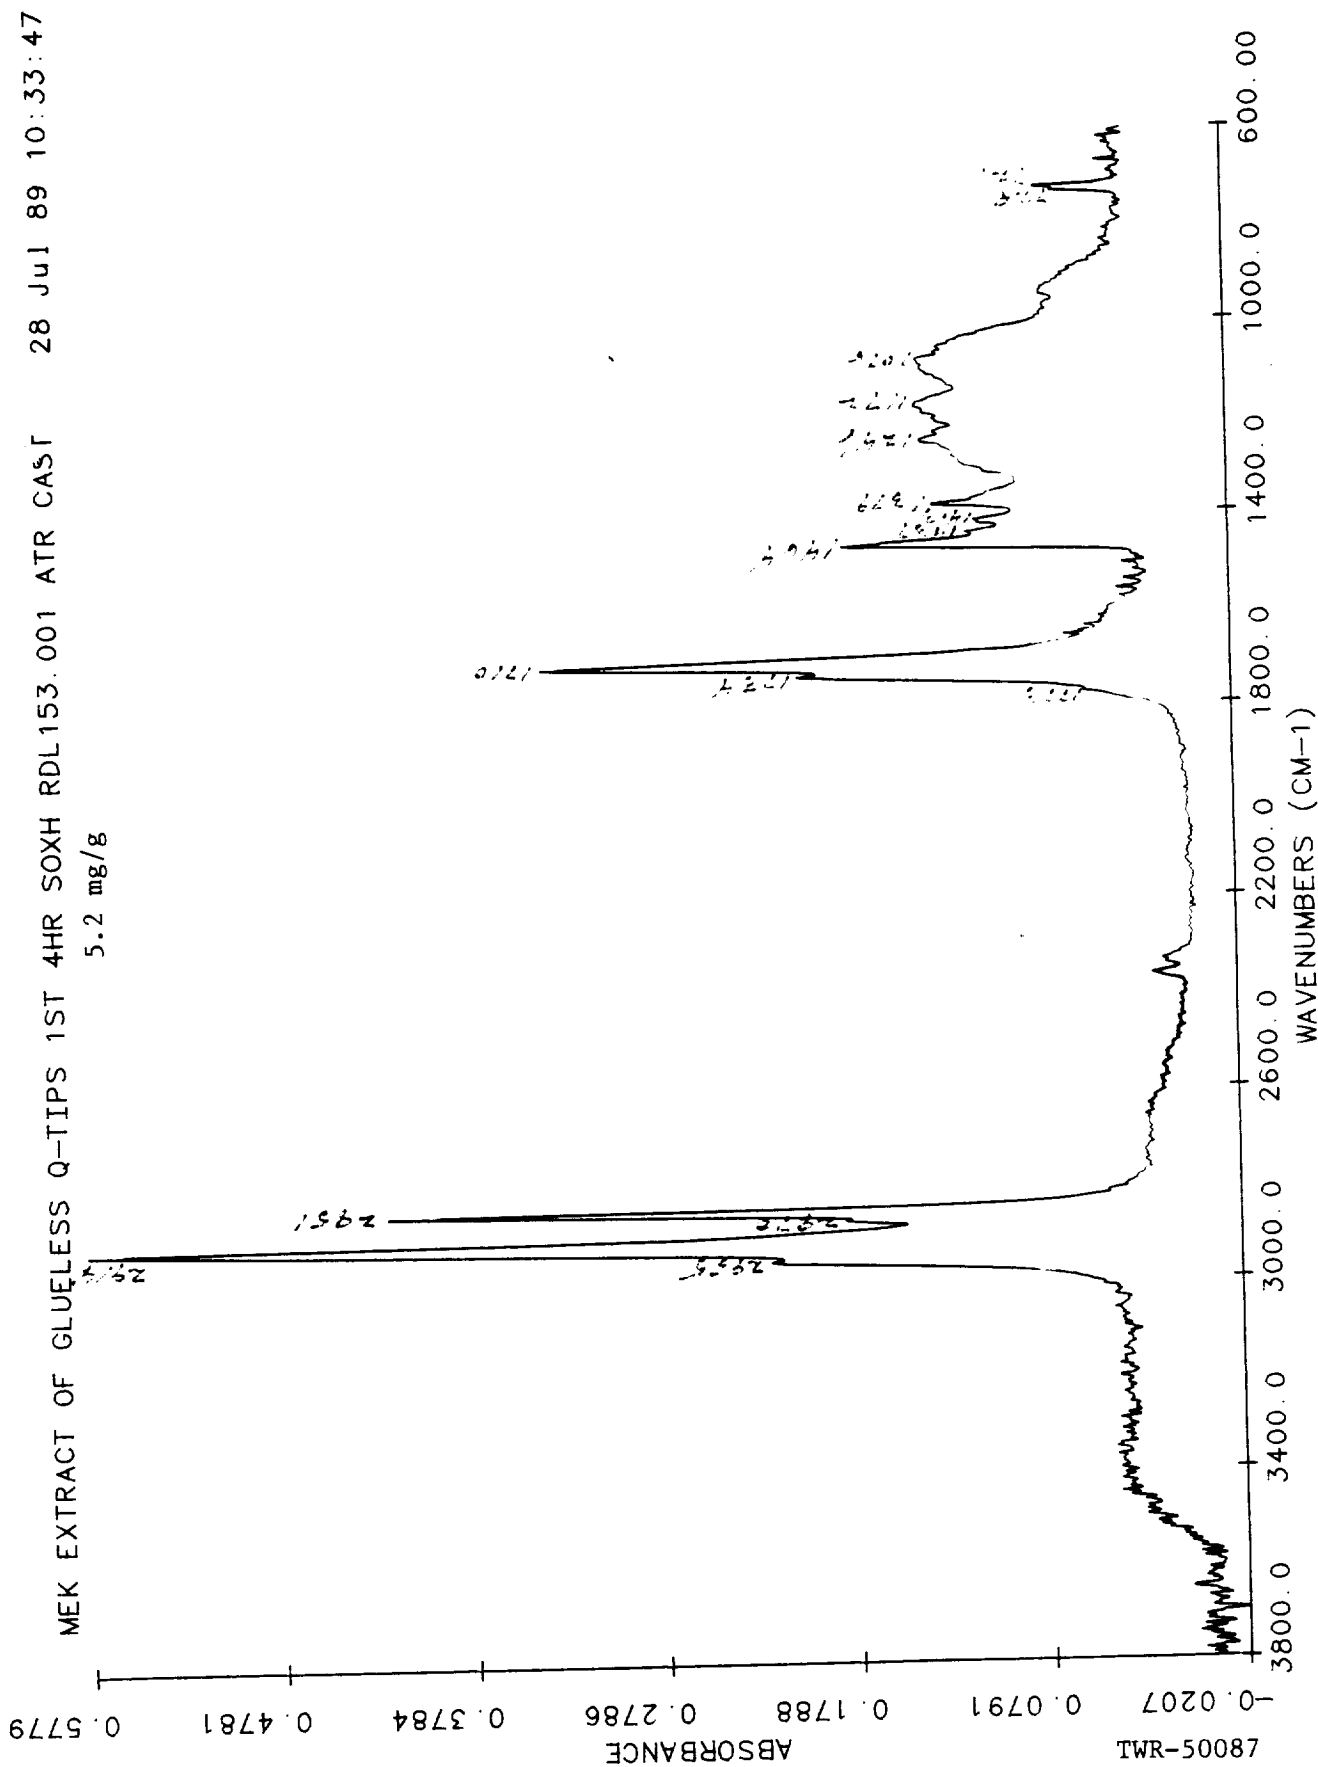

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 37.



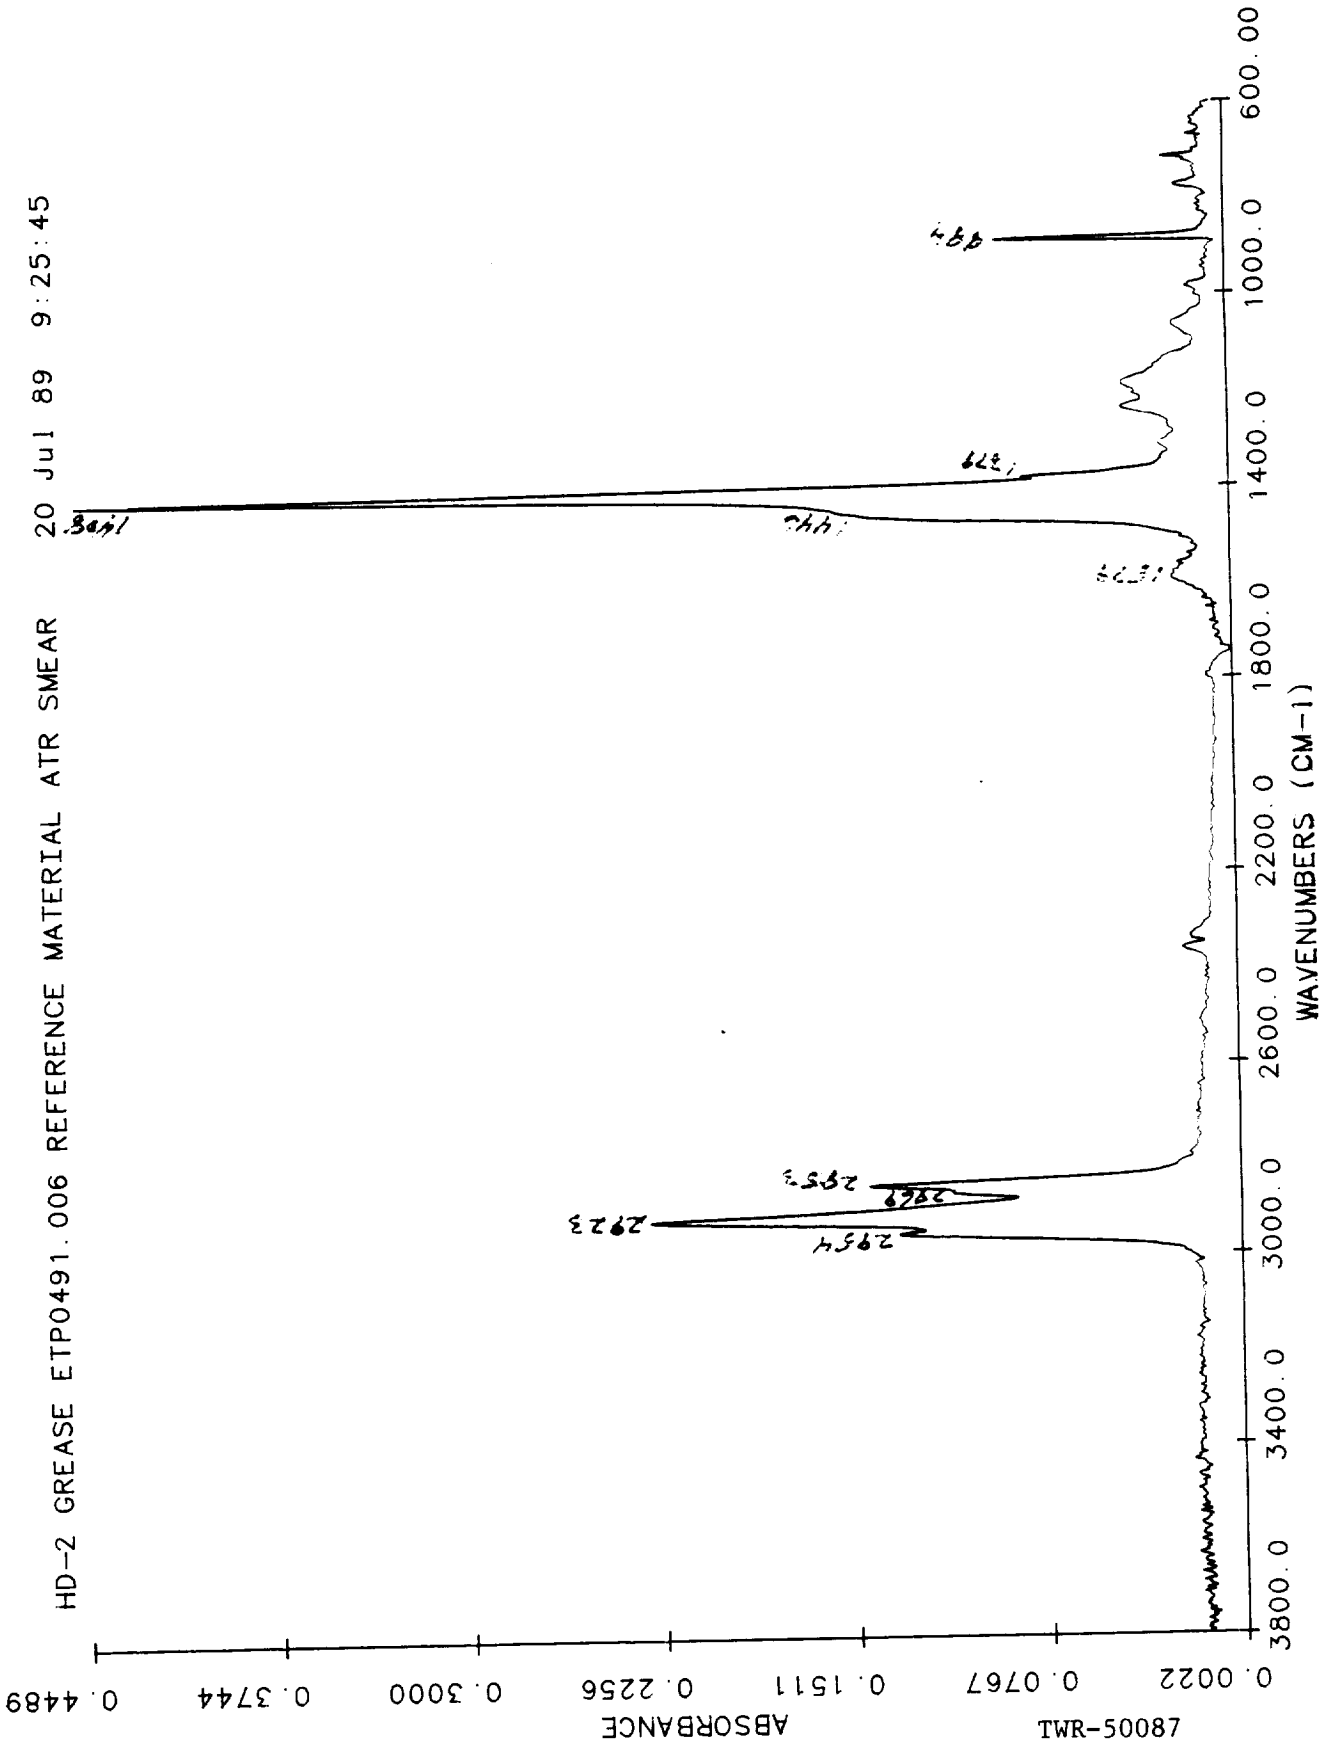


Figure 38.

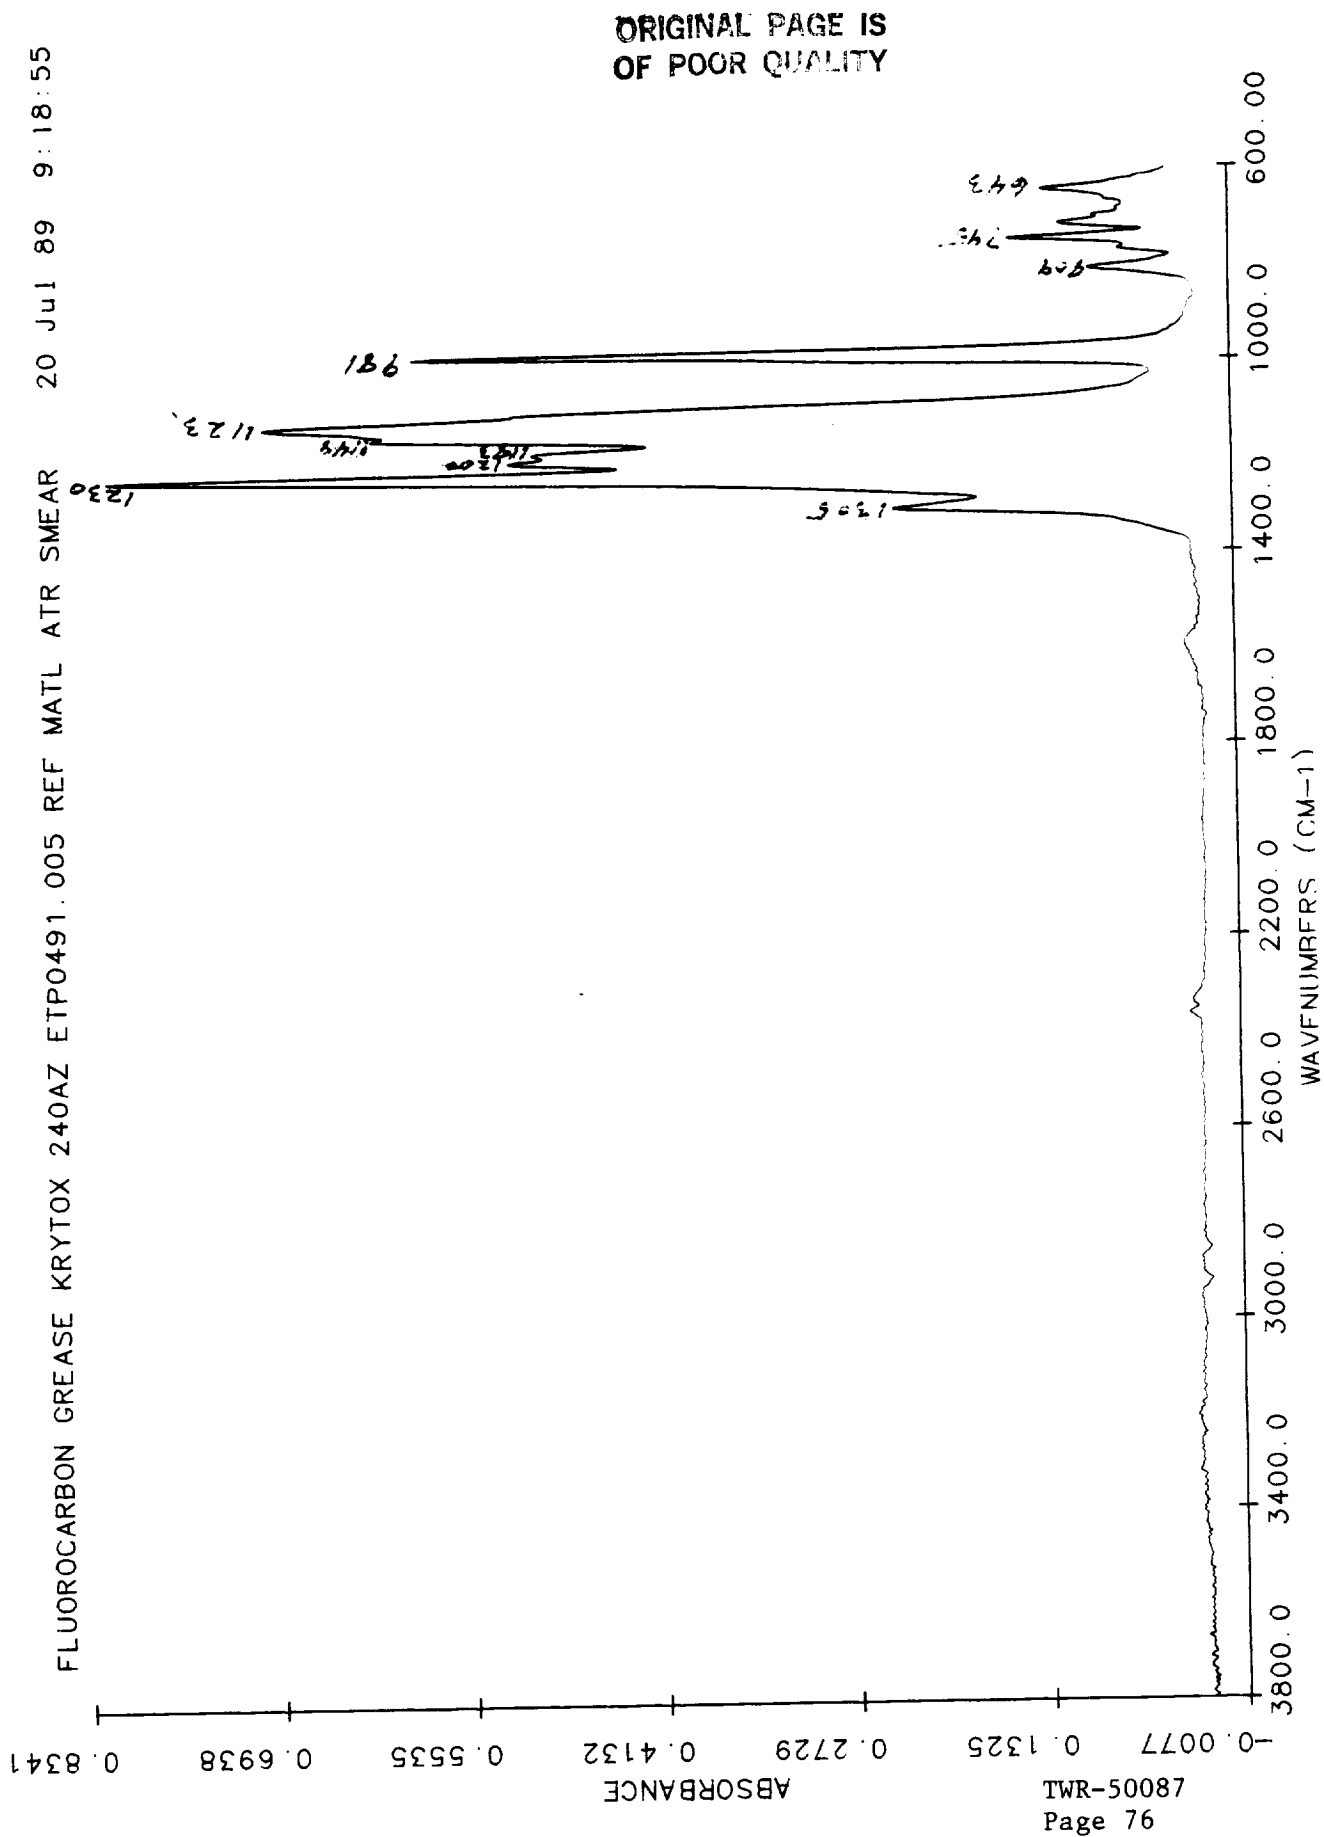


ORIGINAL PAGE IS
OF POOR QUALITY

Figure 39.

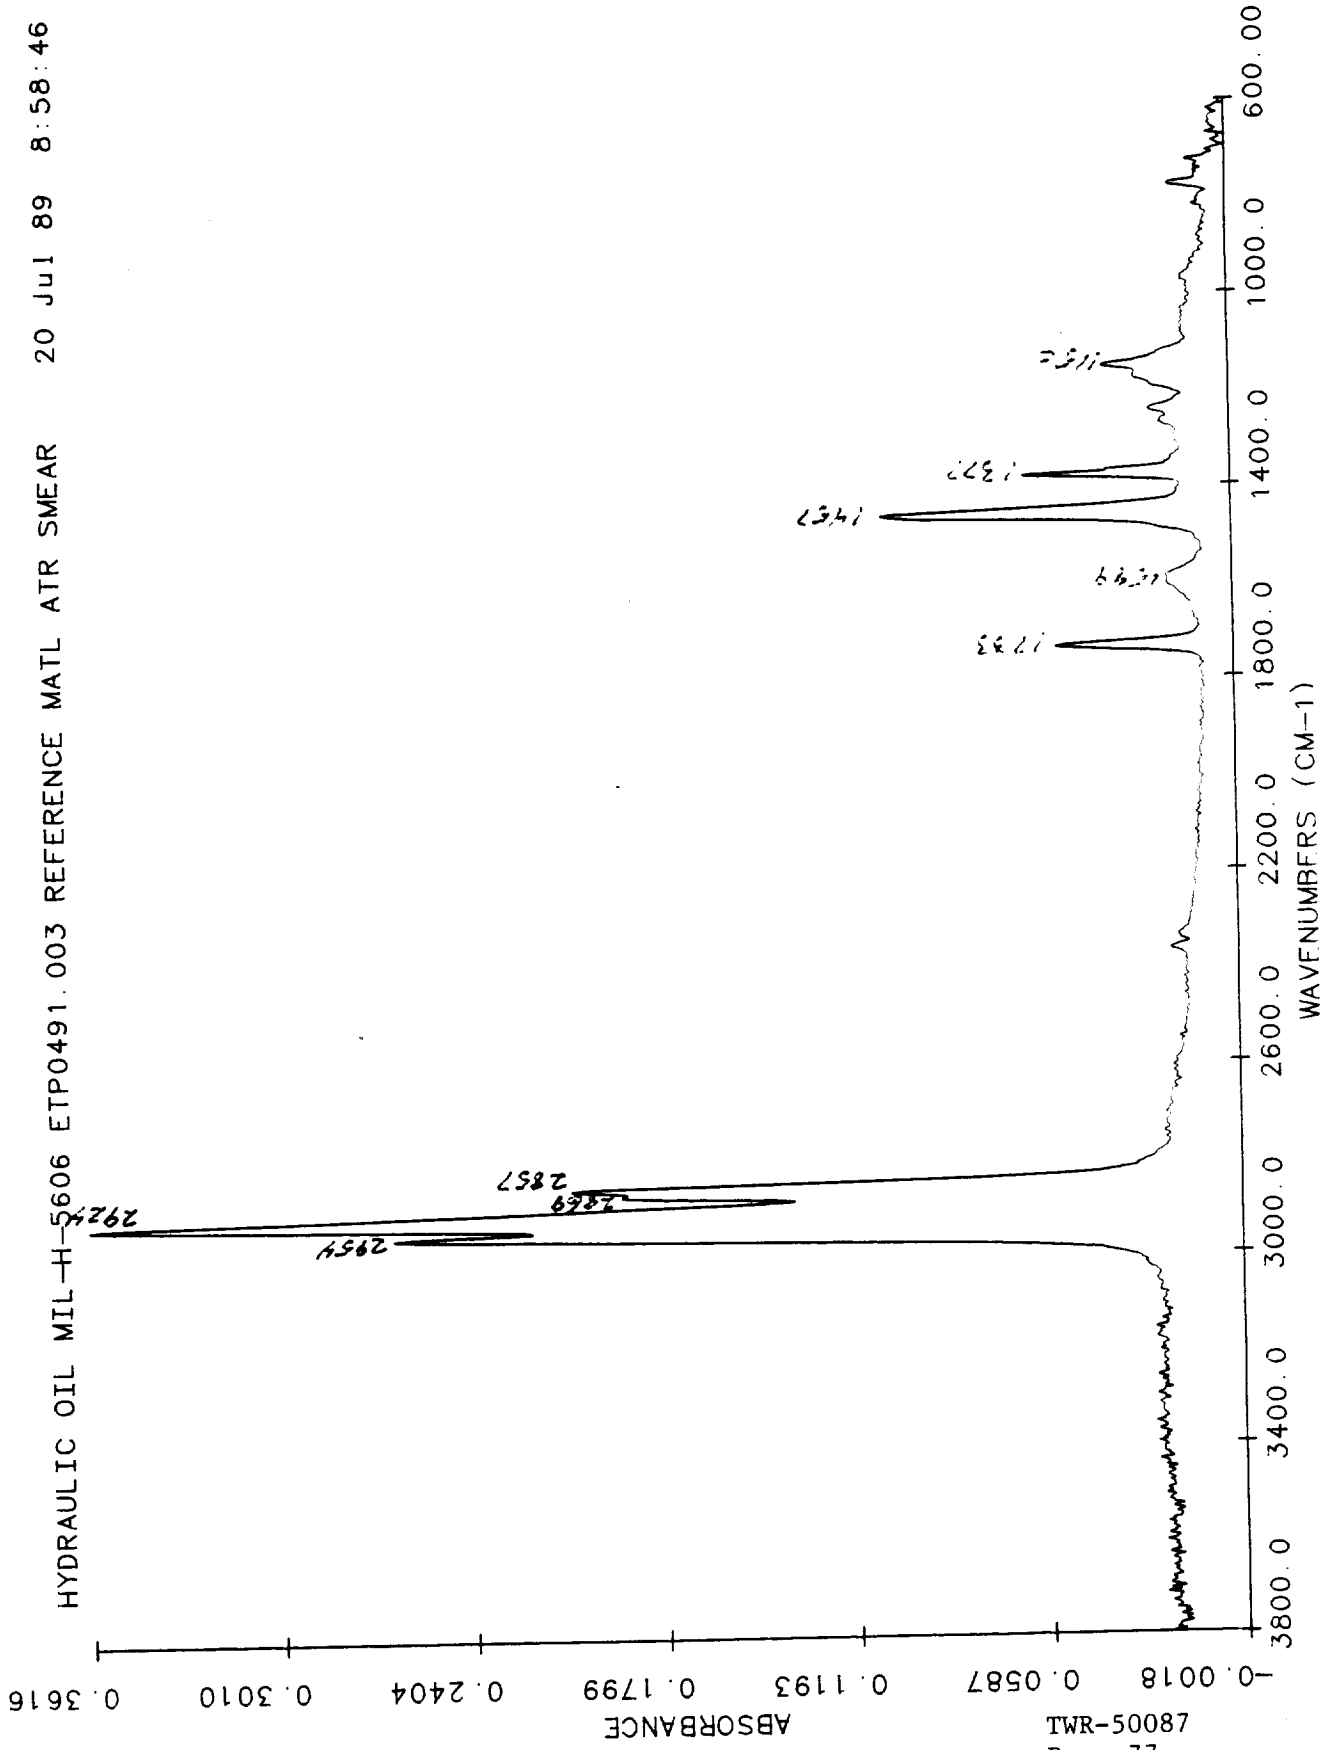

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 40.

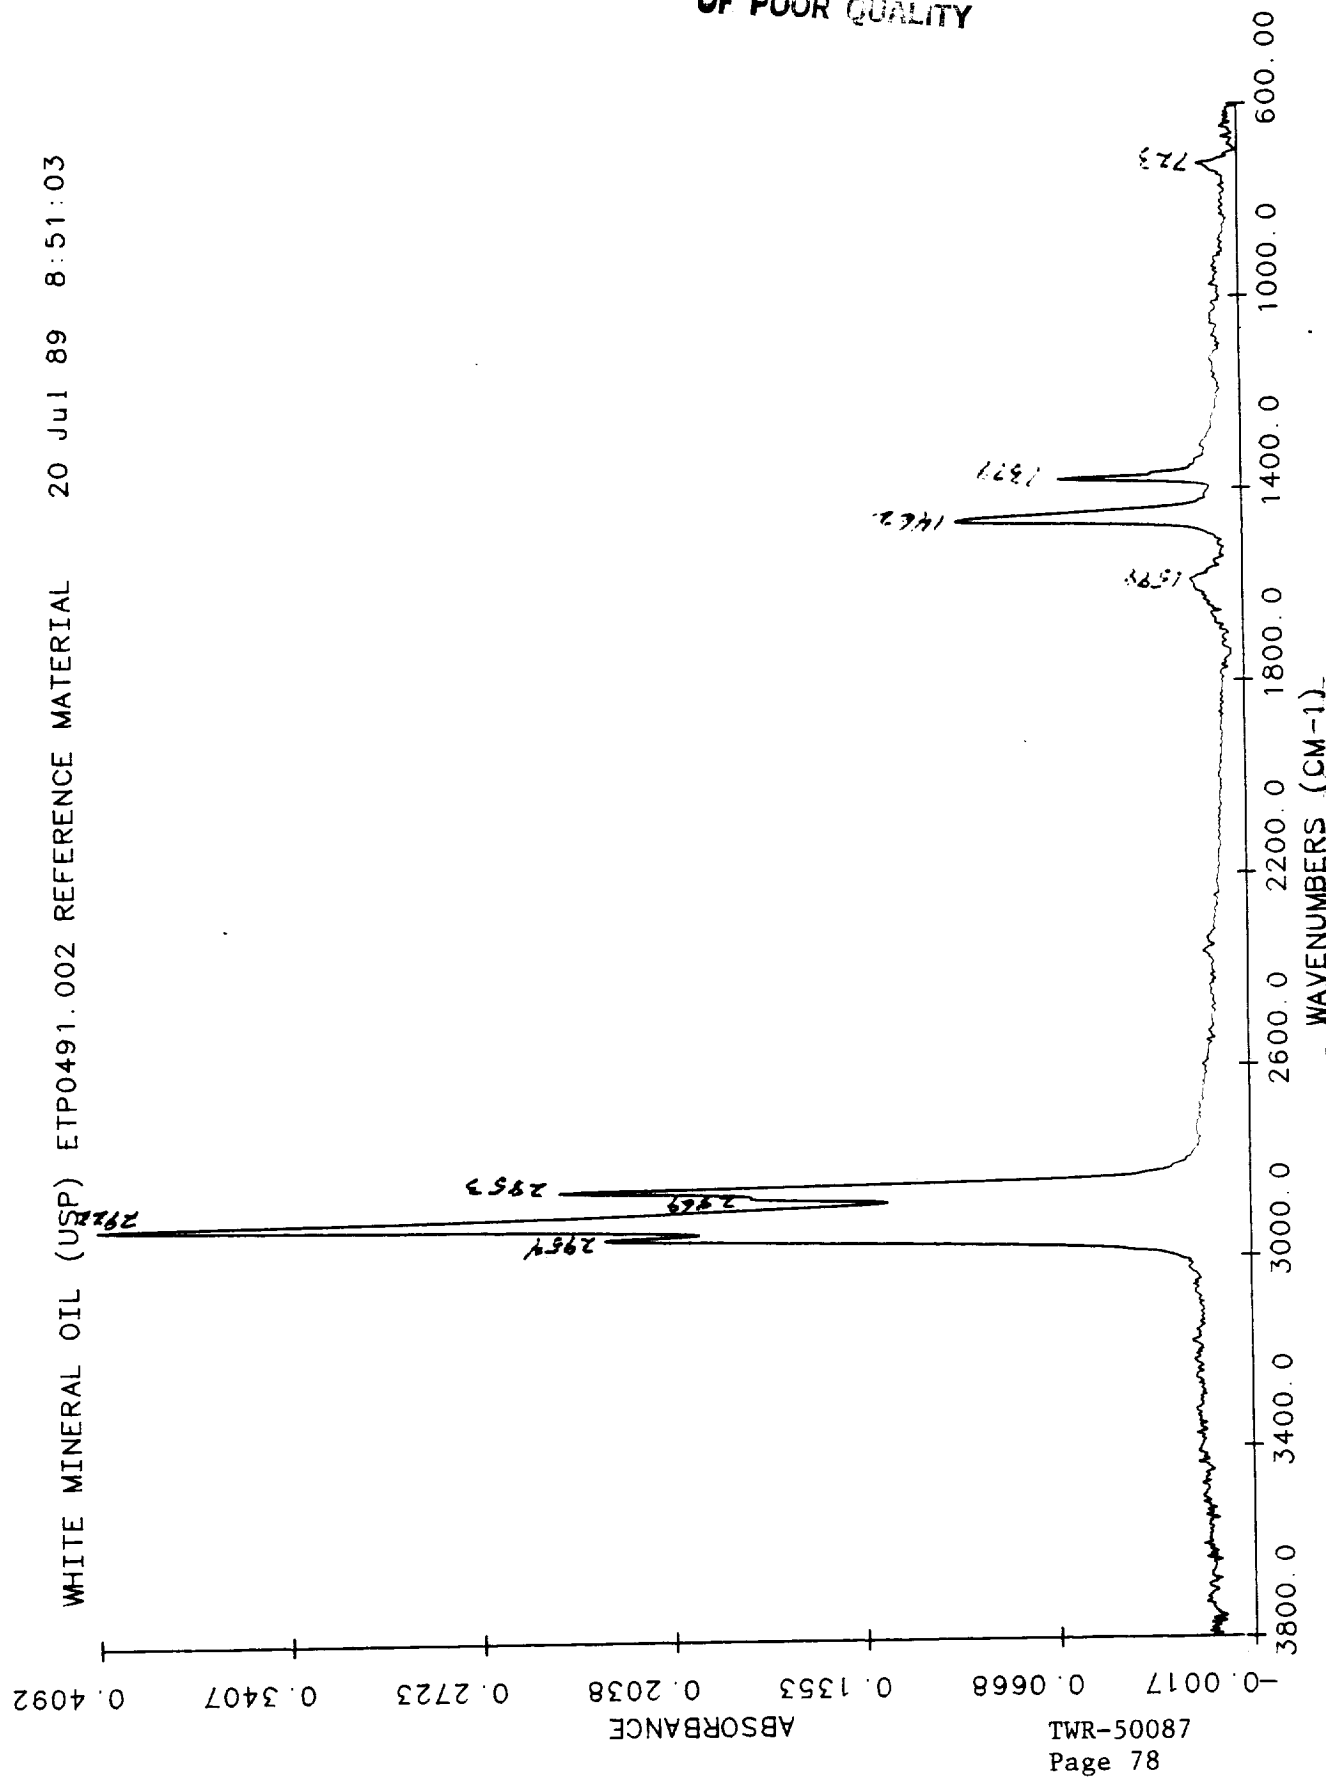

ORIGINAL PAGE IS
OF POOR QUALITY

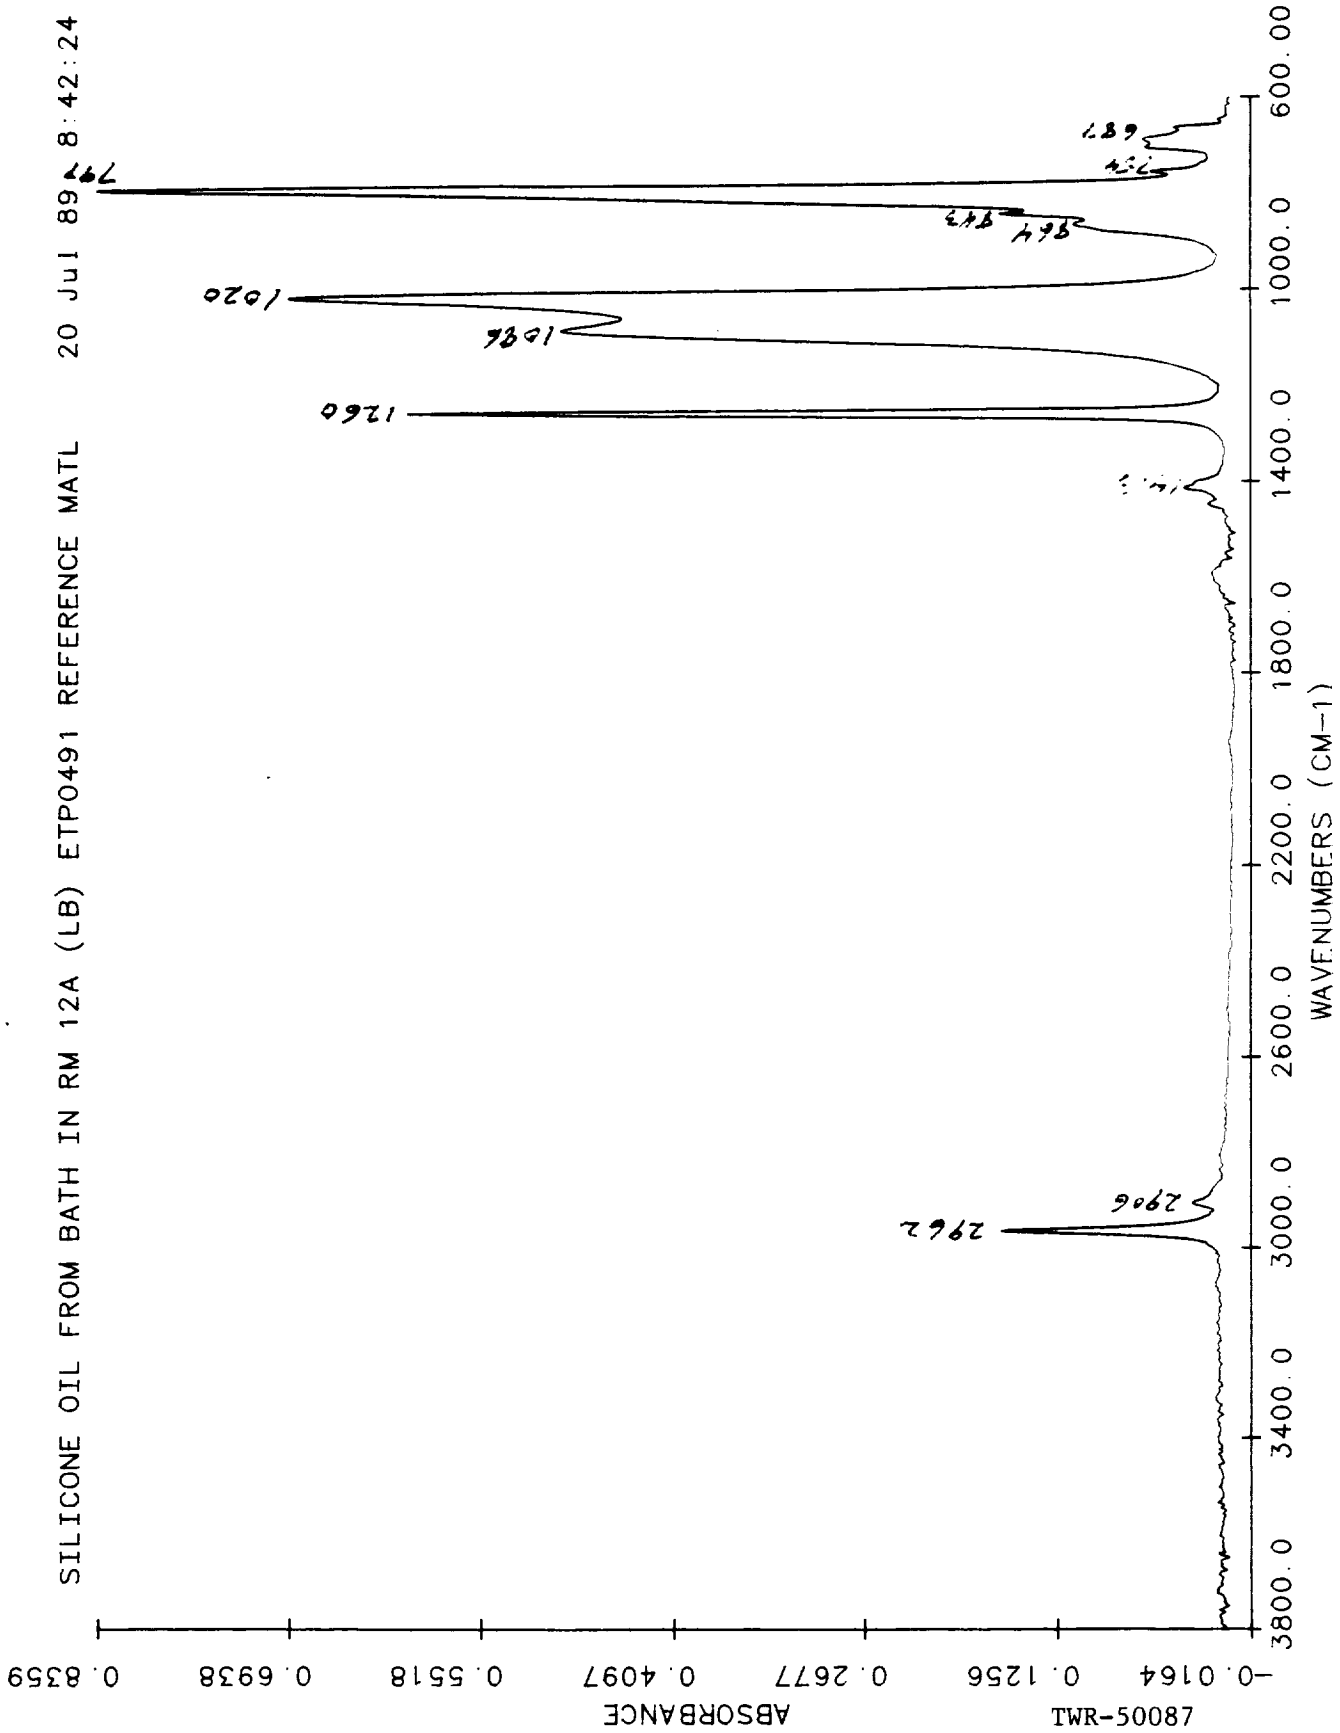


Figure 41.

ORIGINAL PAGE IS
OF POOR QUALITY


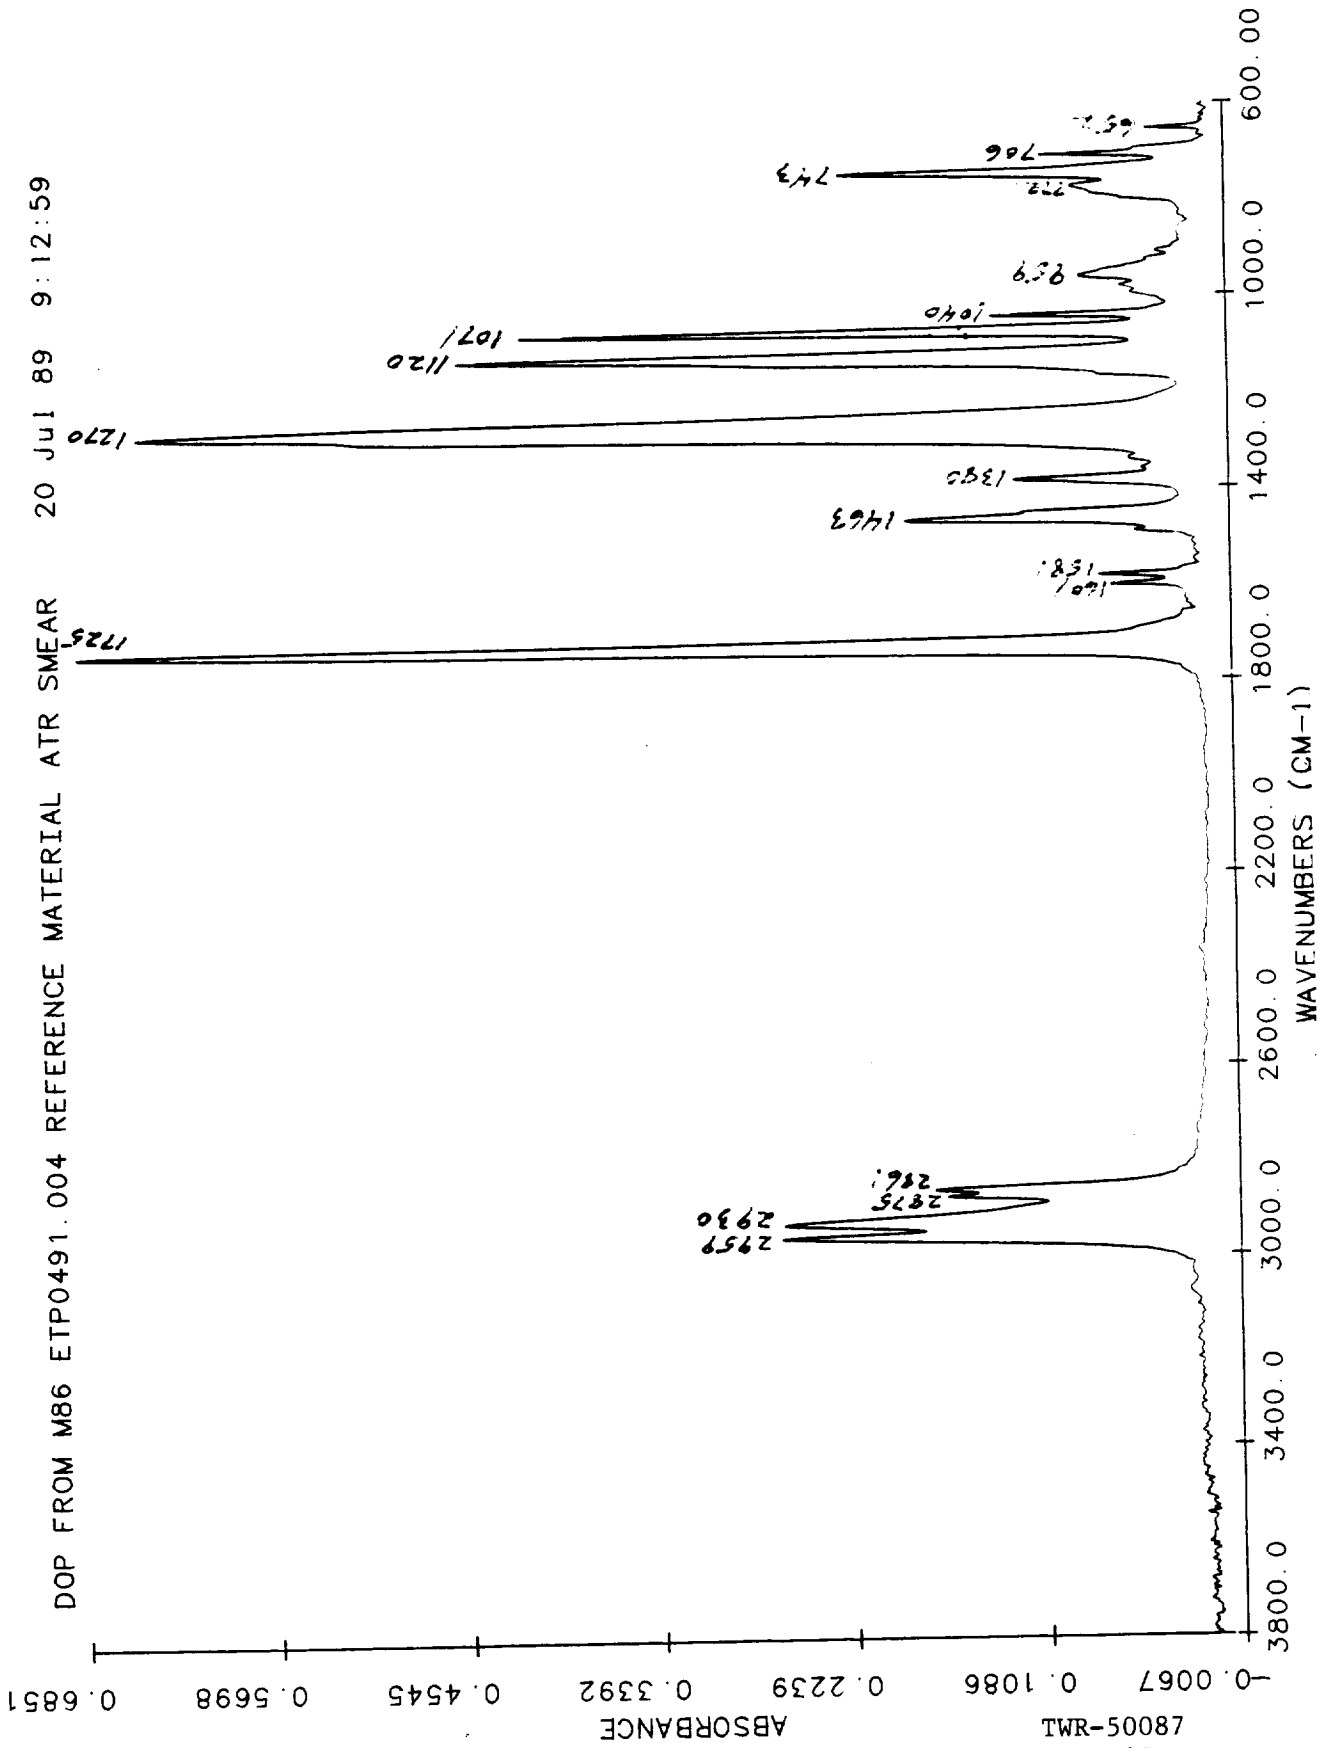


Figure 42.

Figure 43.

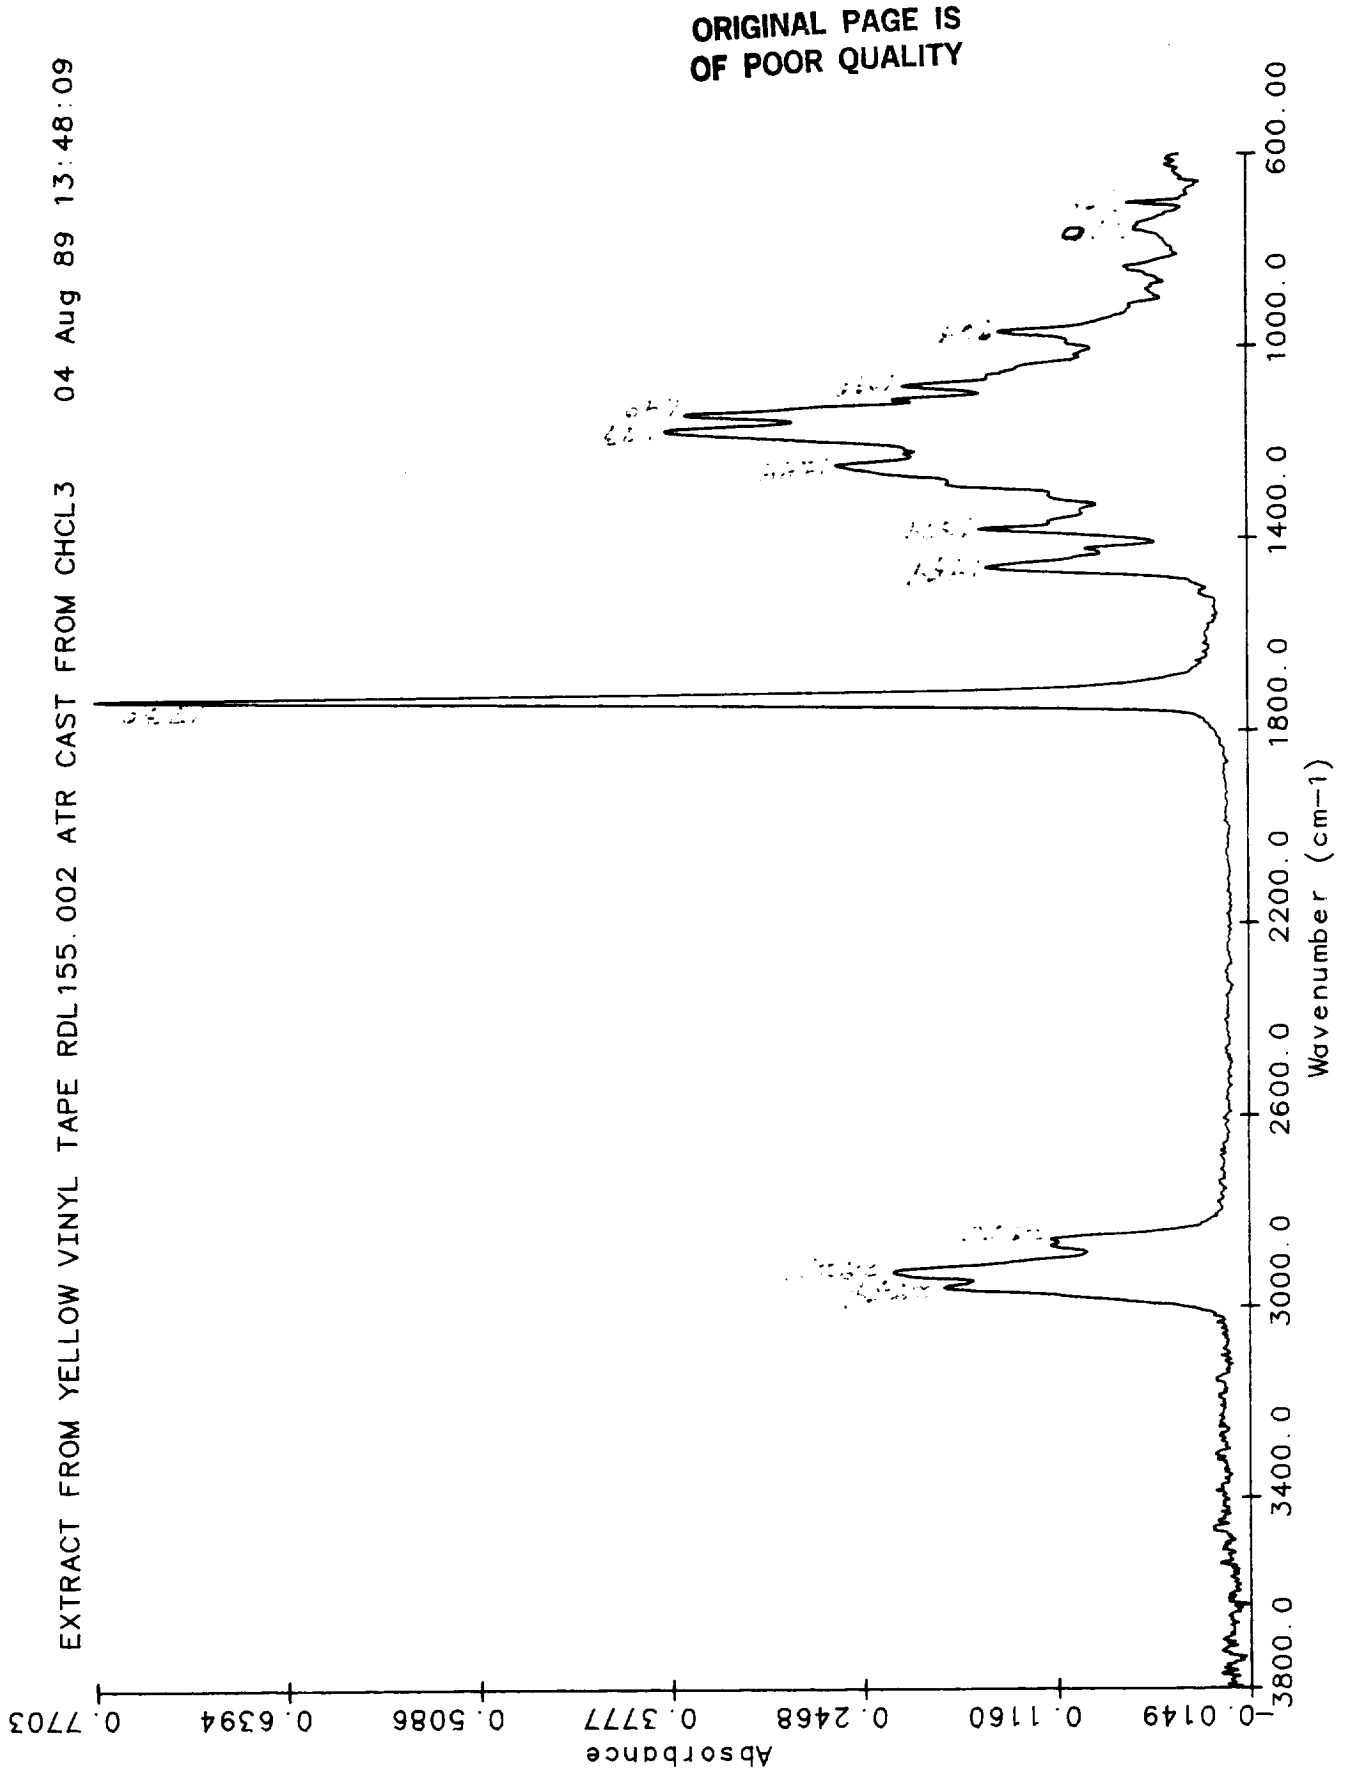

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 44.

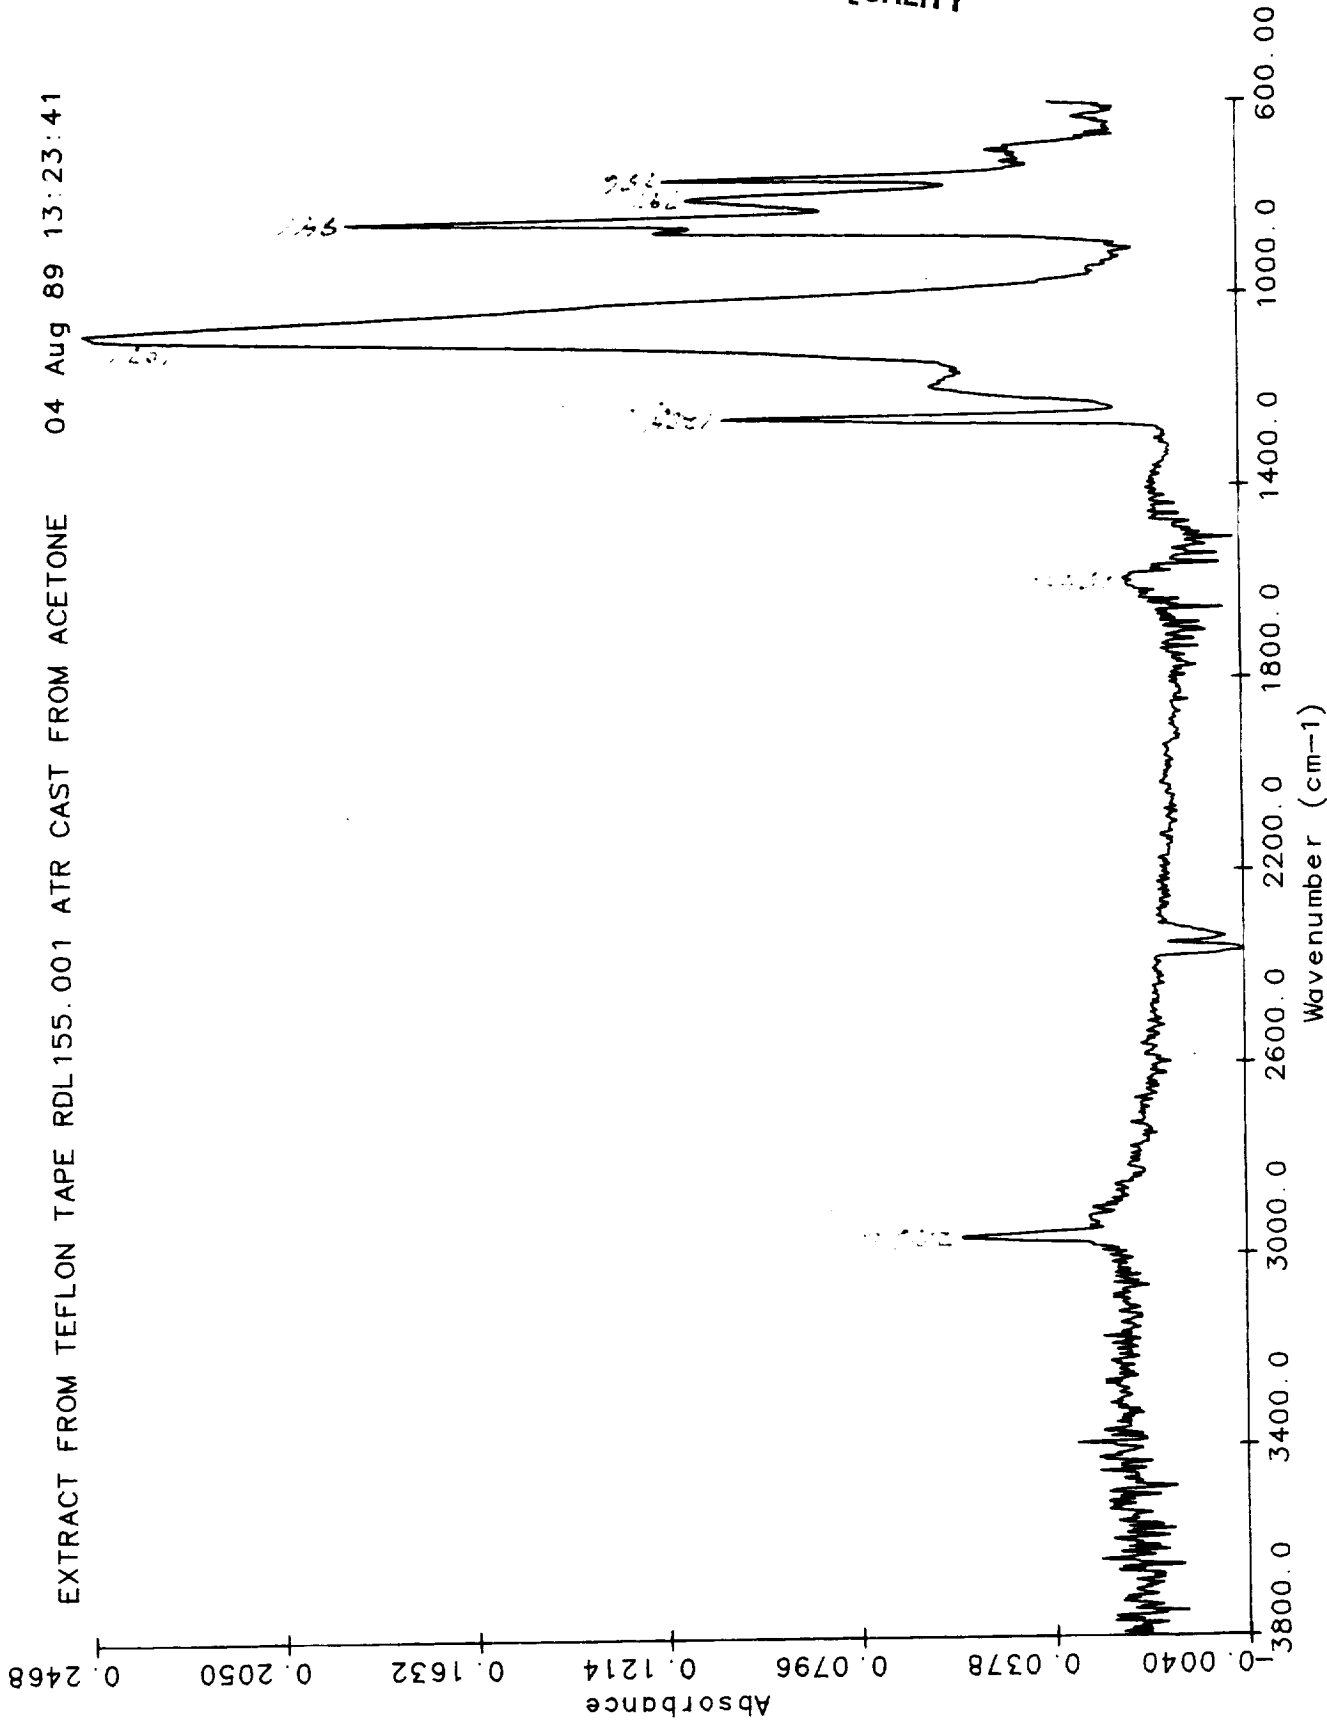


Figure 45.


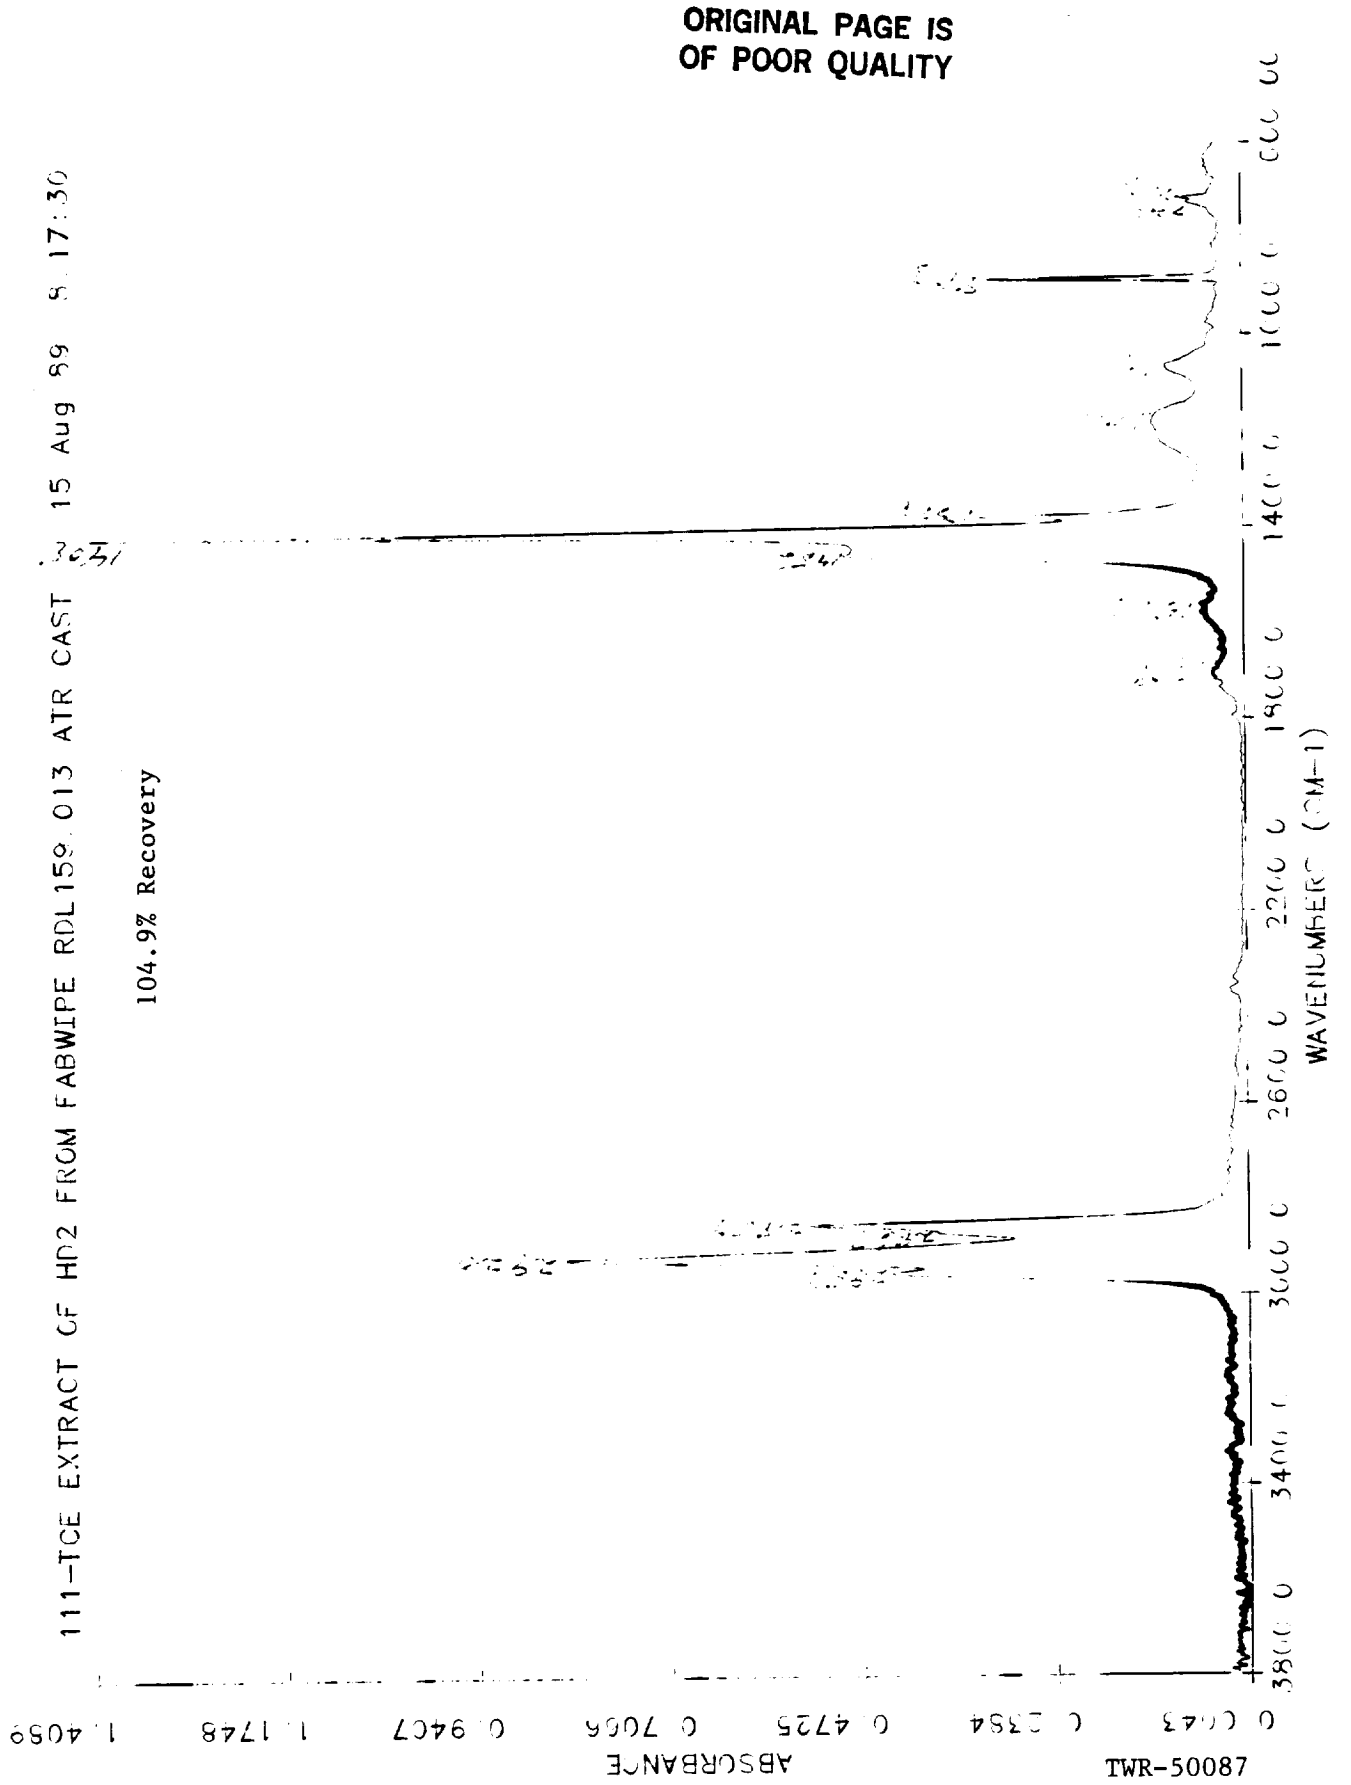


Figure 46.

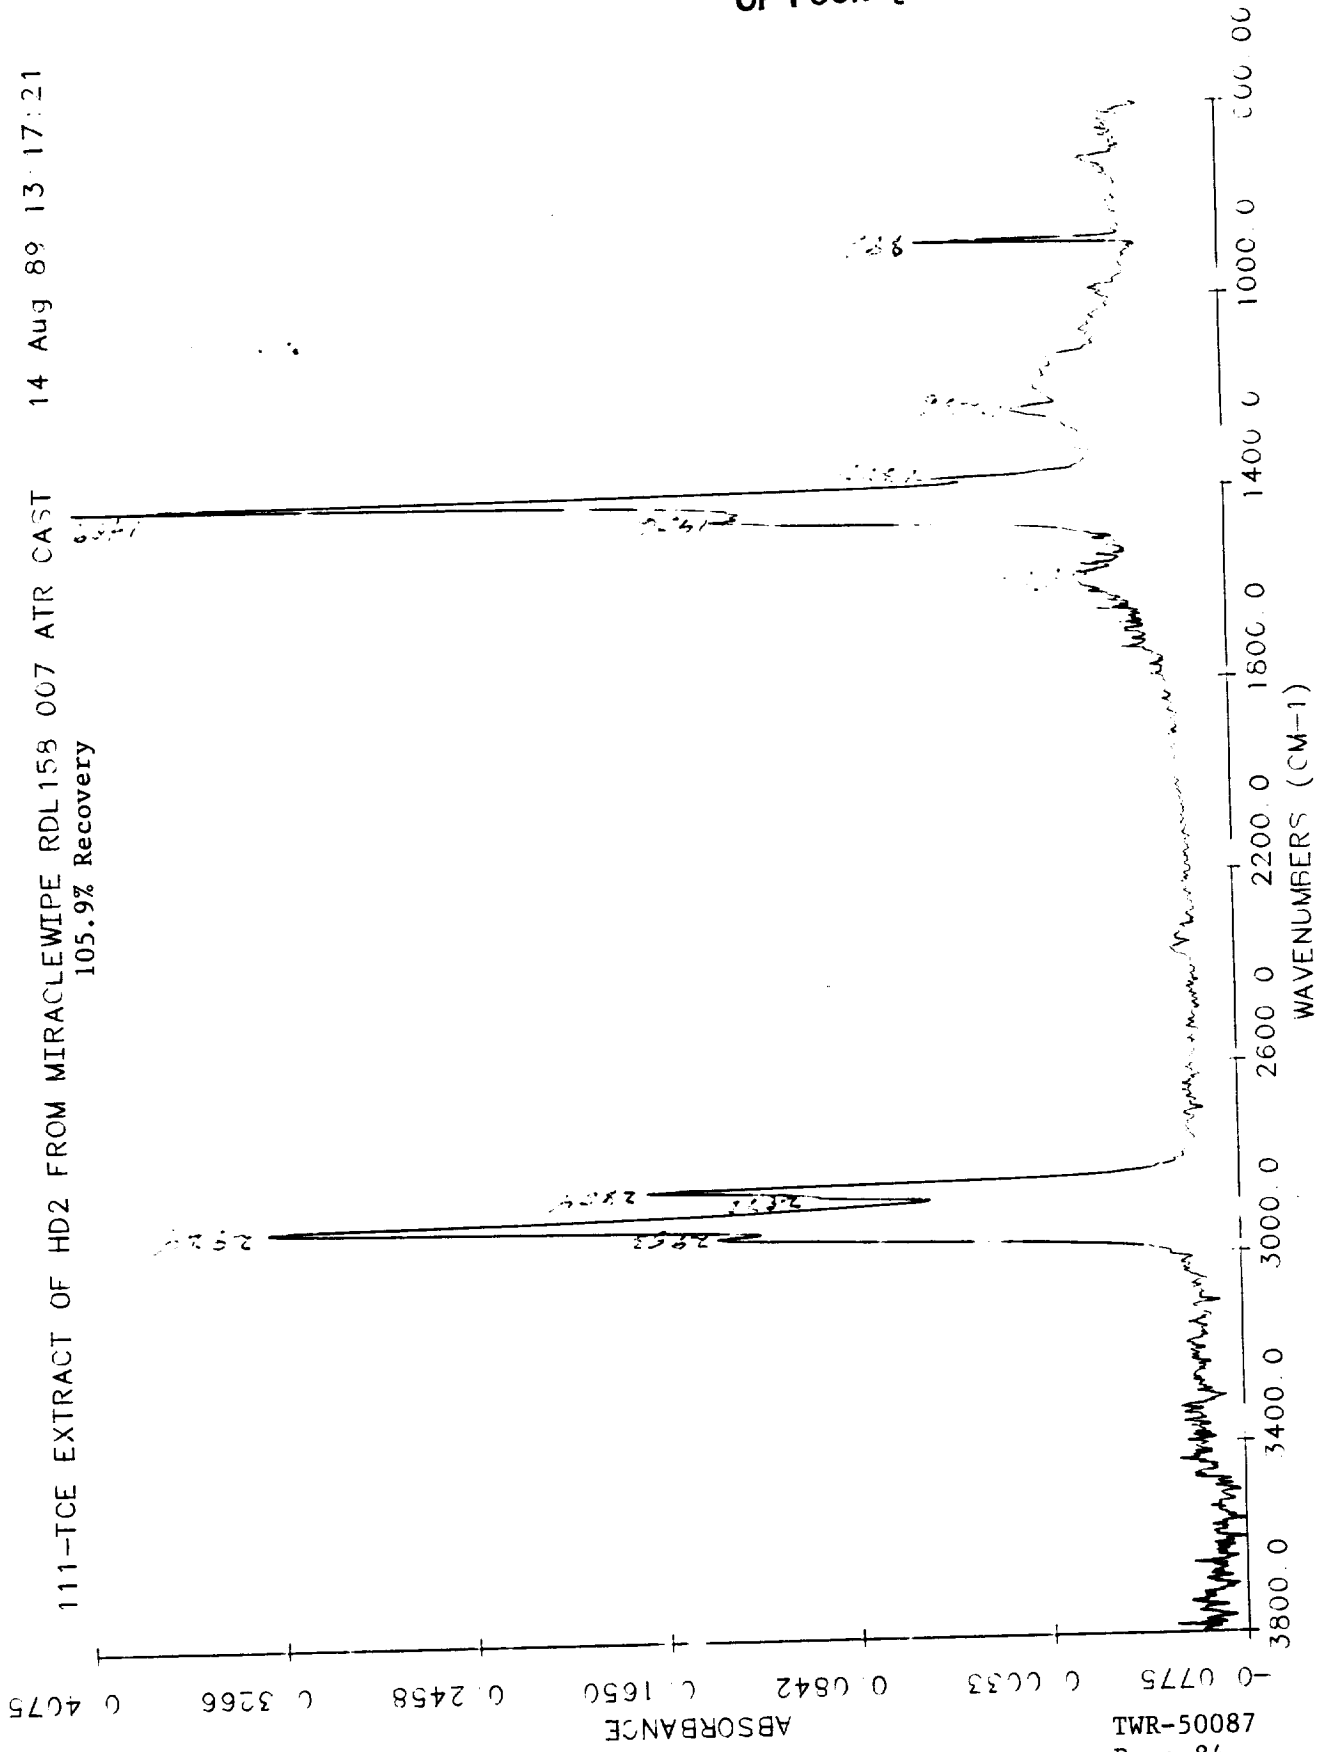

ORIGINAL PAGE IS
OF POOR QUALITY

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 47.



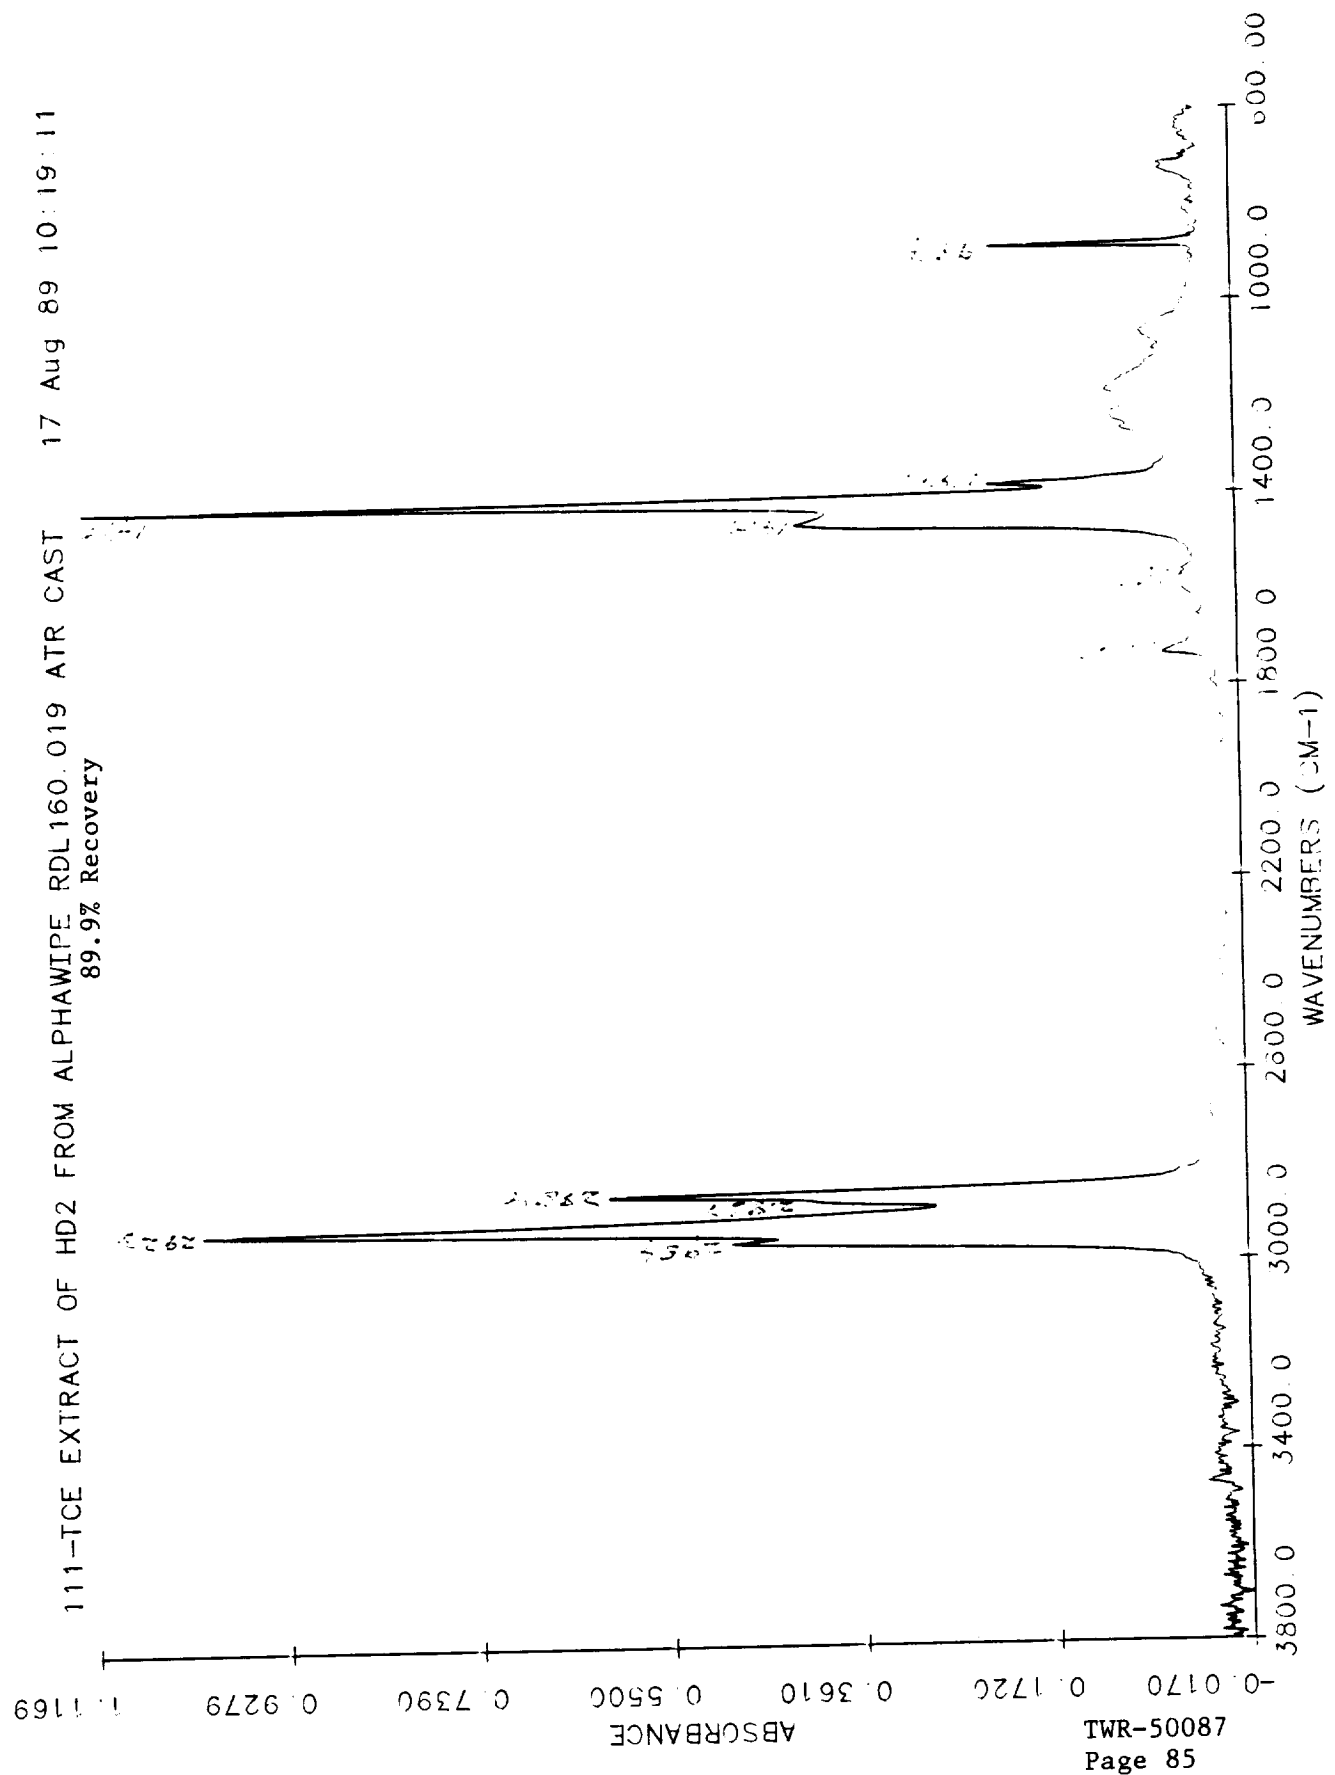


Figure 48.

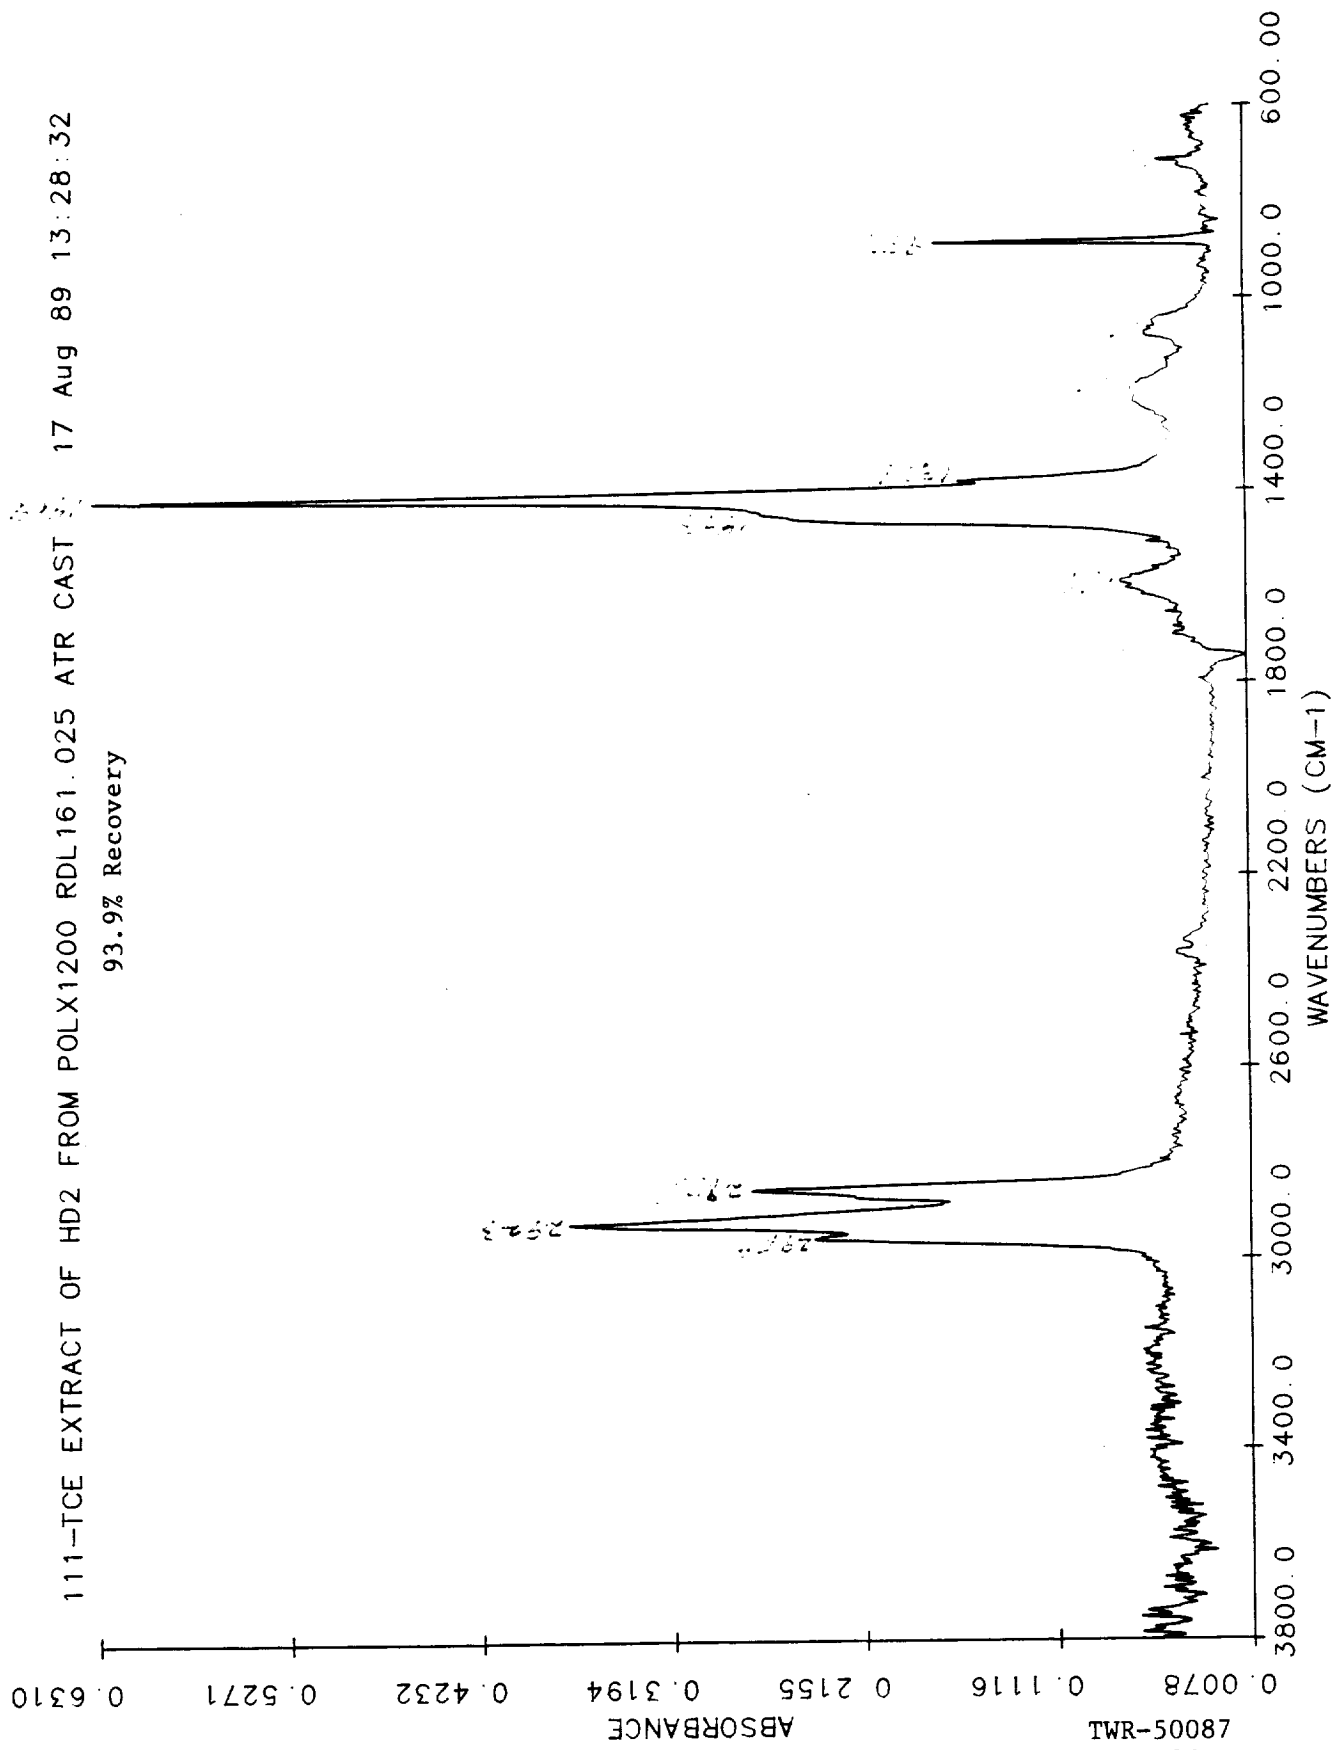


ORIGINAL PAGE IS
OF POOR QUALITY

Figure 49.

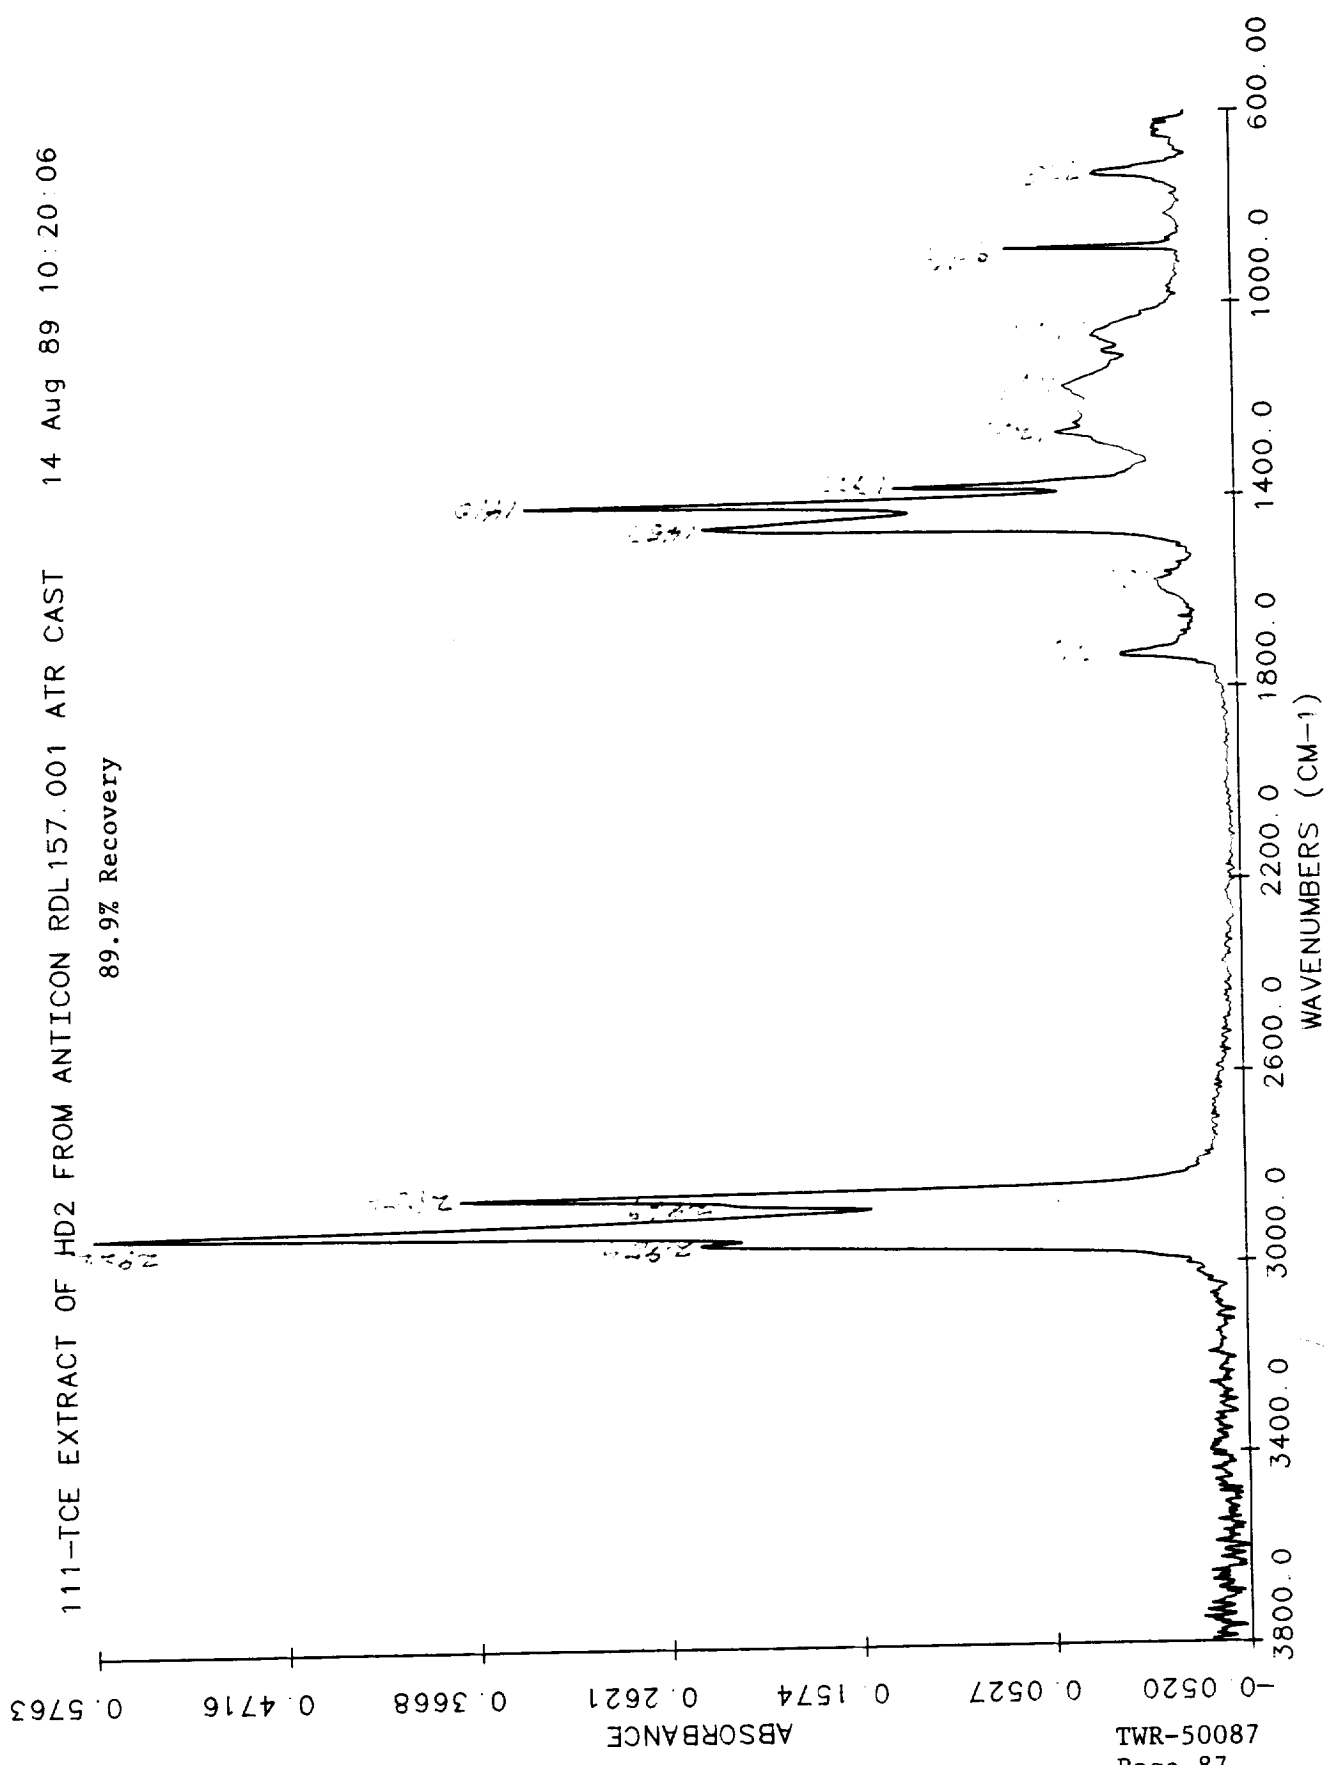


ORIGINAL PAGE IS
OF POOR QUALITY

Figure 50.

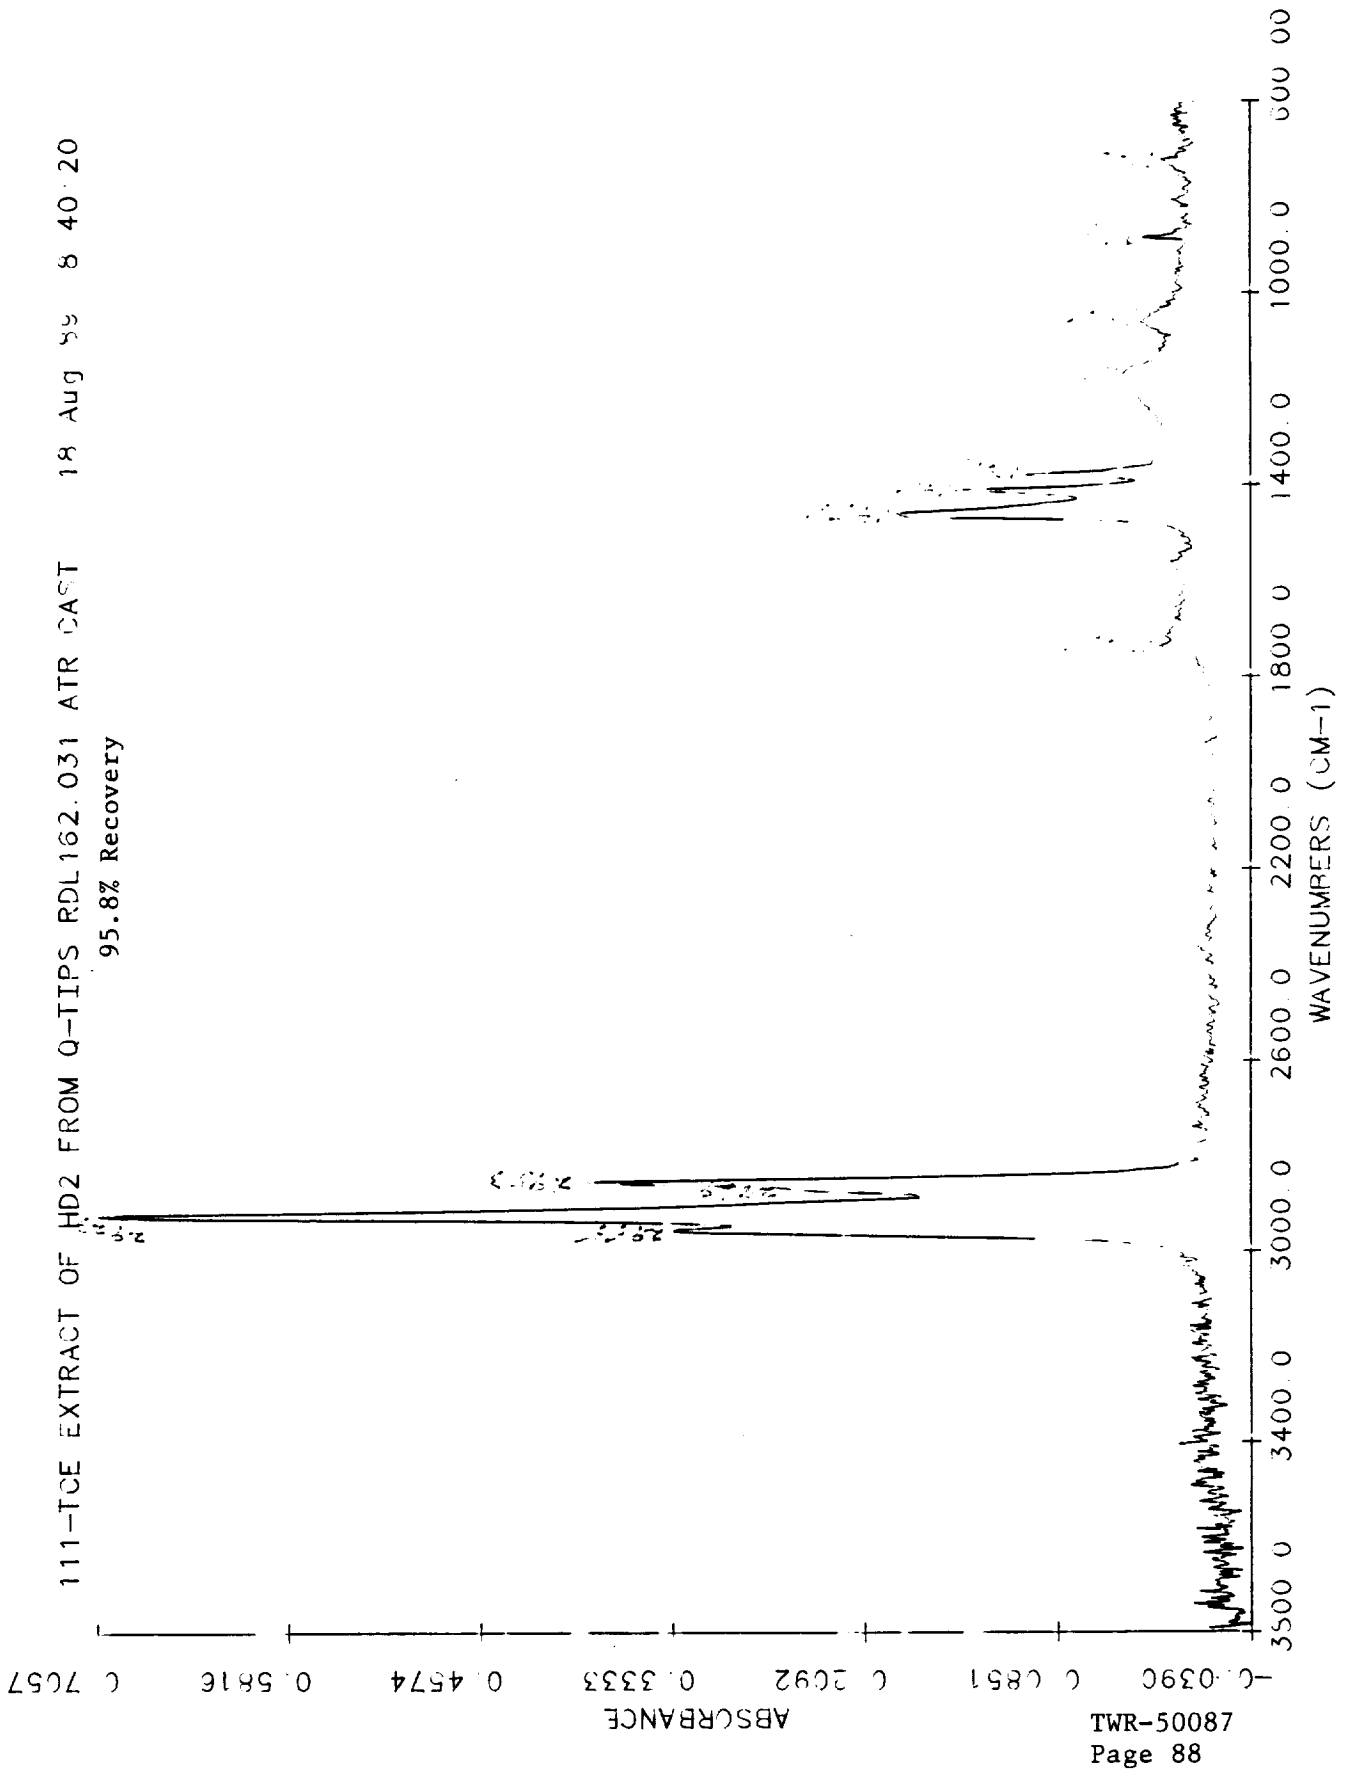

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 51.
FREON TF EXTRACT OF HD2 FROM FABWIPE RDL165.B28 ATR CAST
28 Aug 99 13:40:52
90.9% Recovery

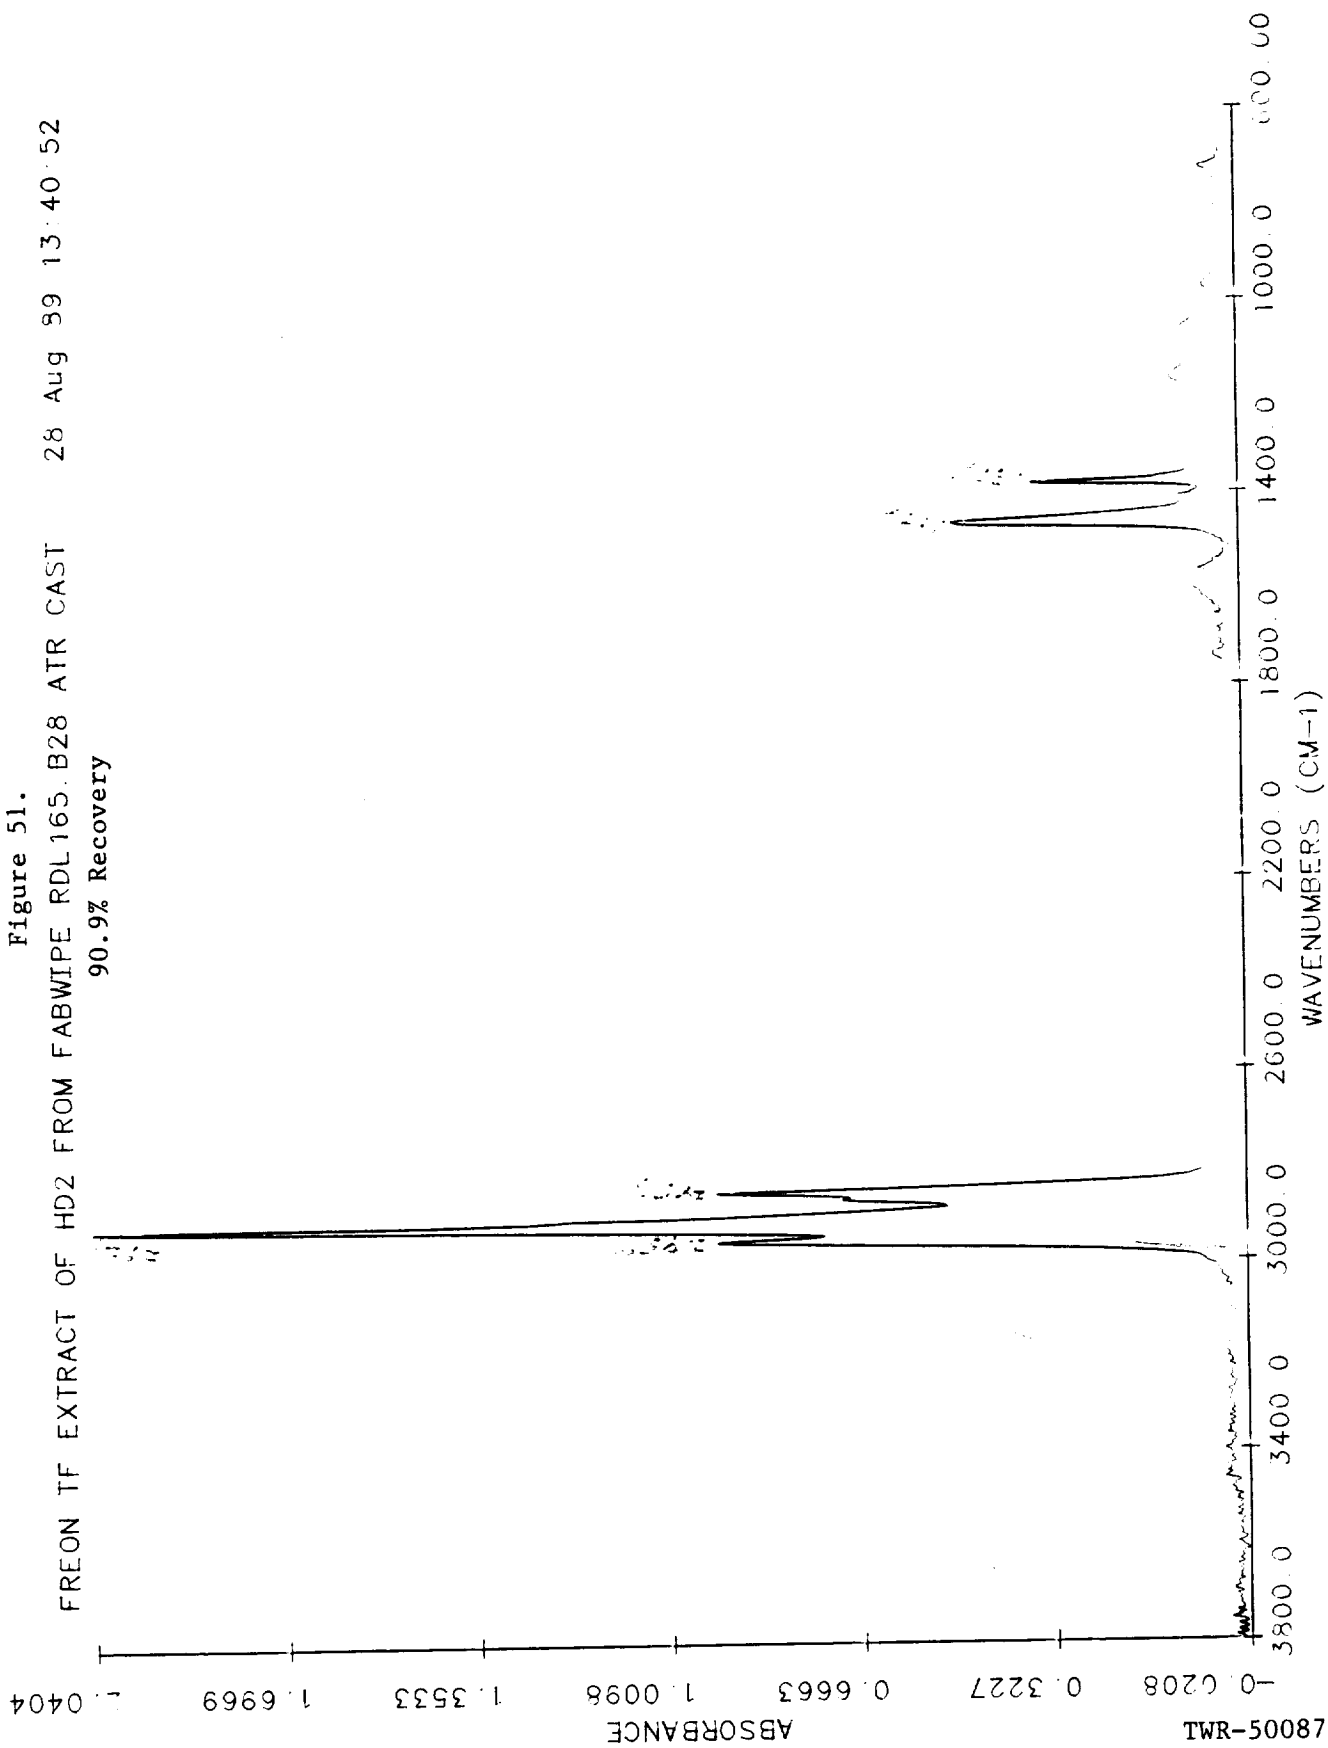

ORIGINAL PAGE IS
OF POOR QUALITY


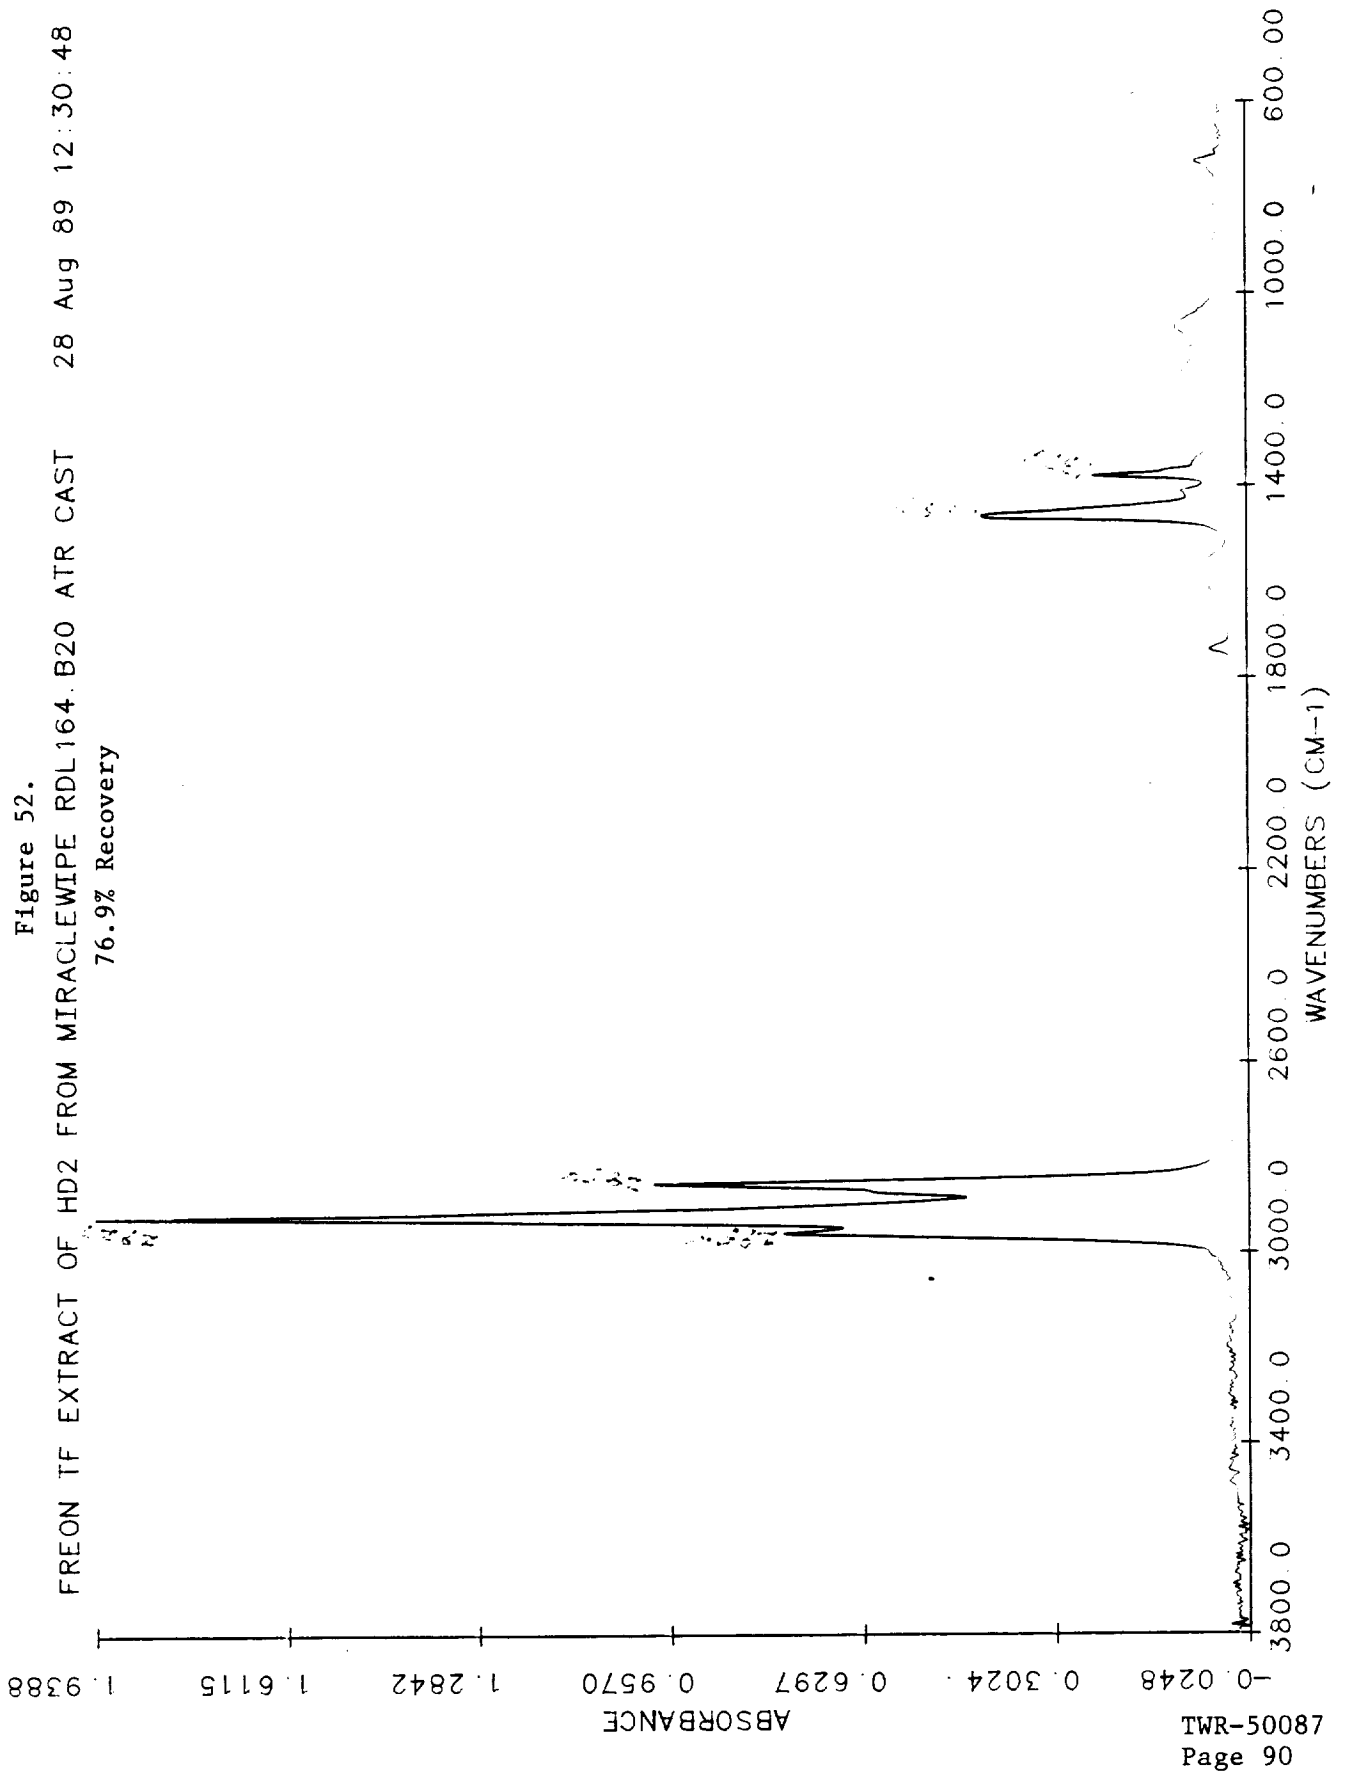


Figure 53.

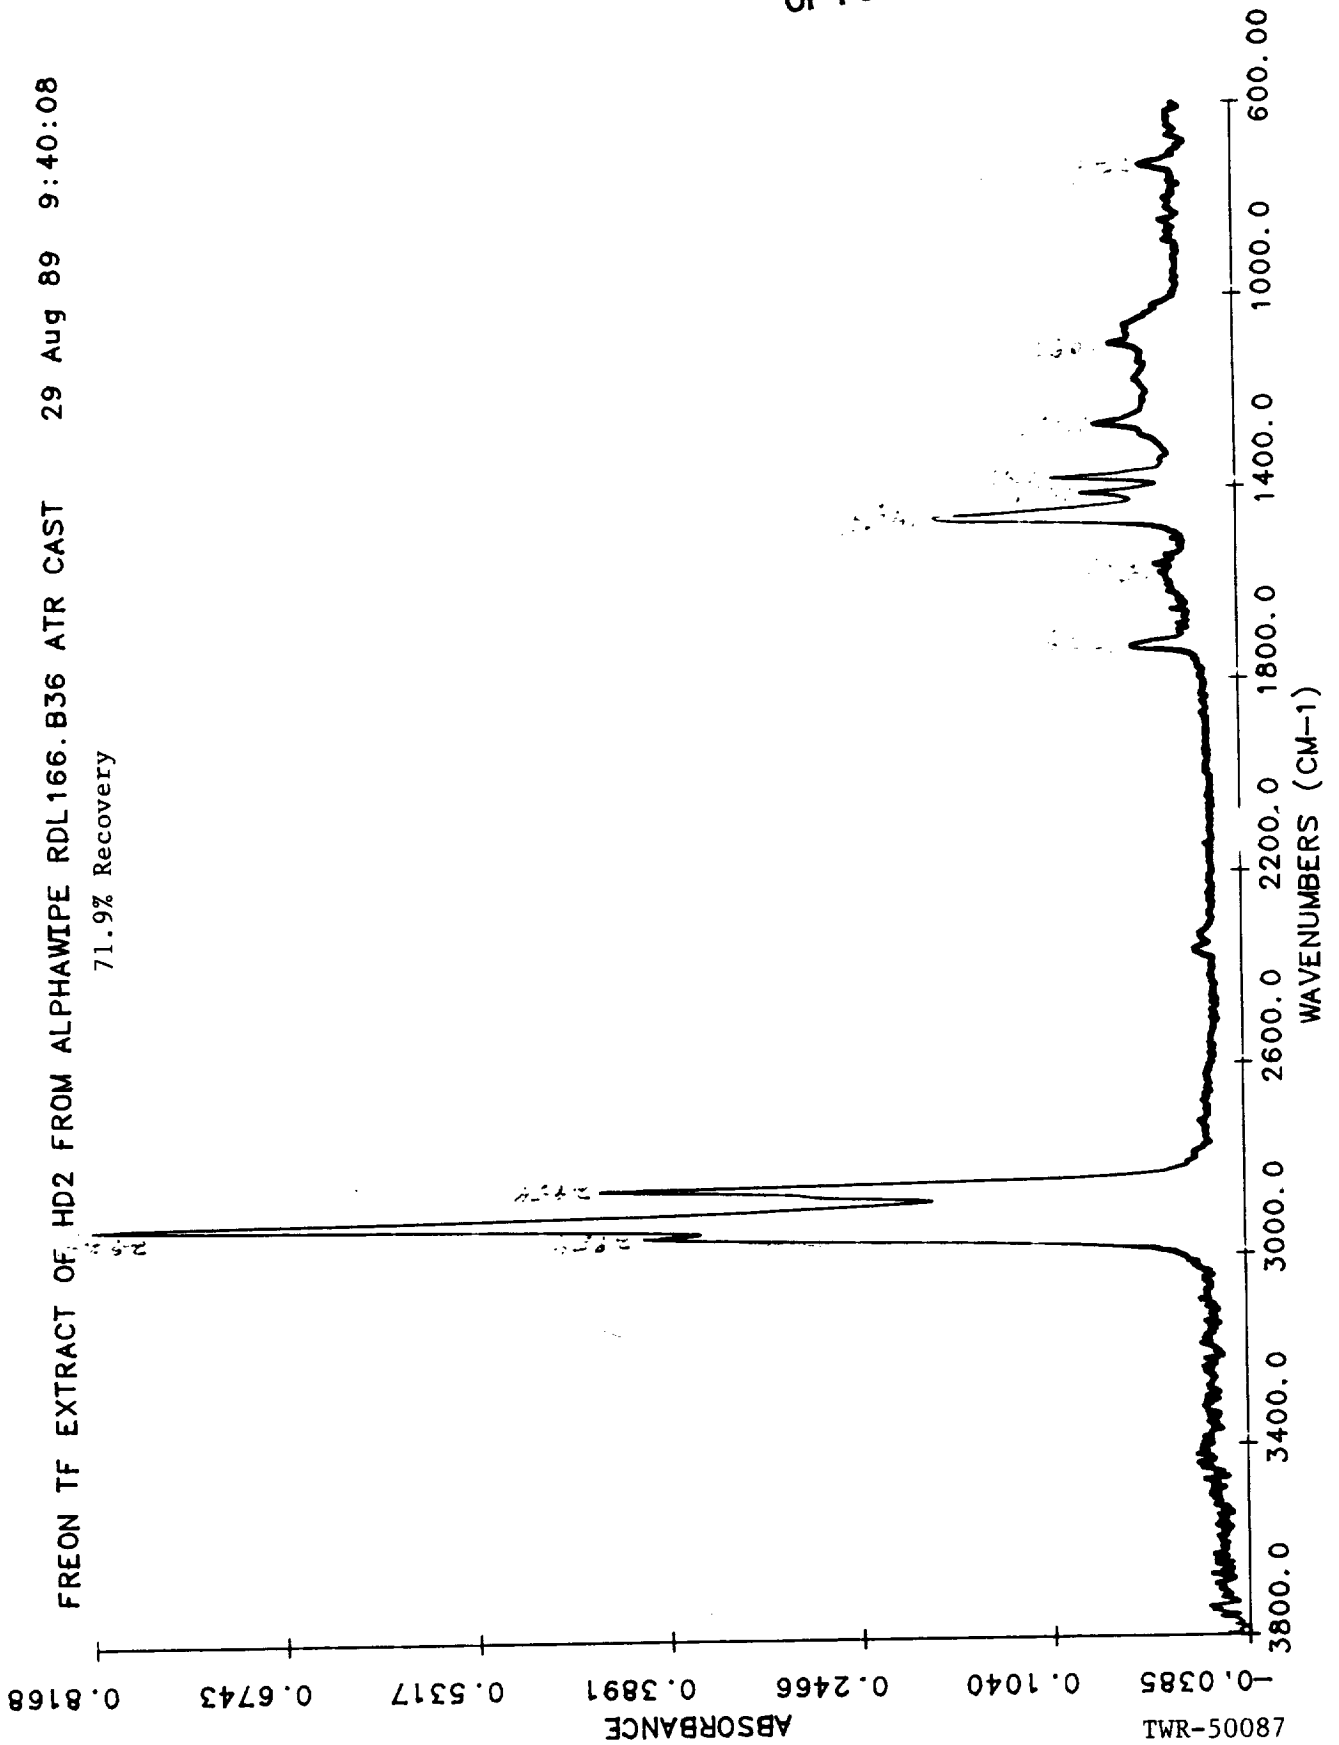

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 54.



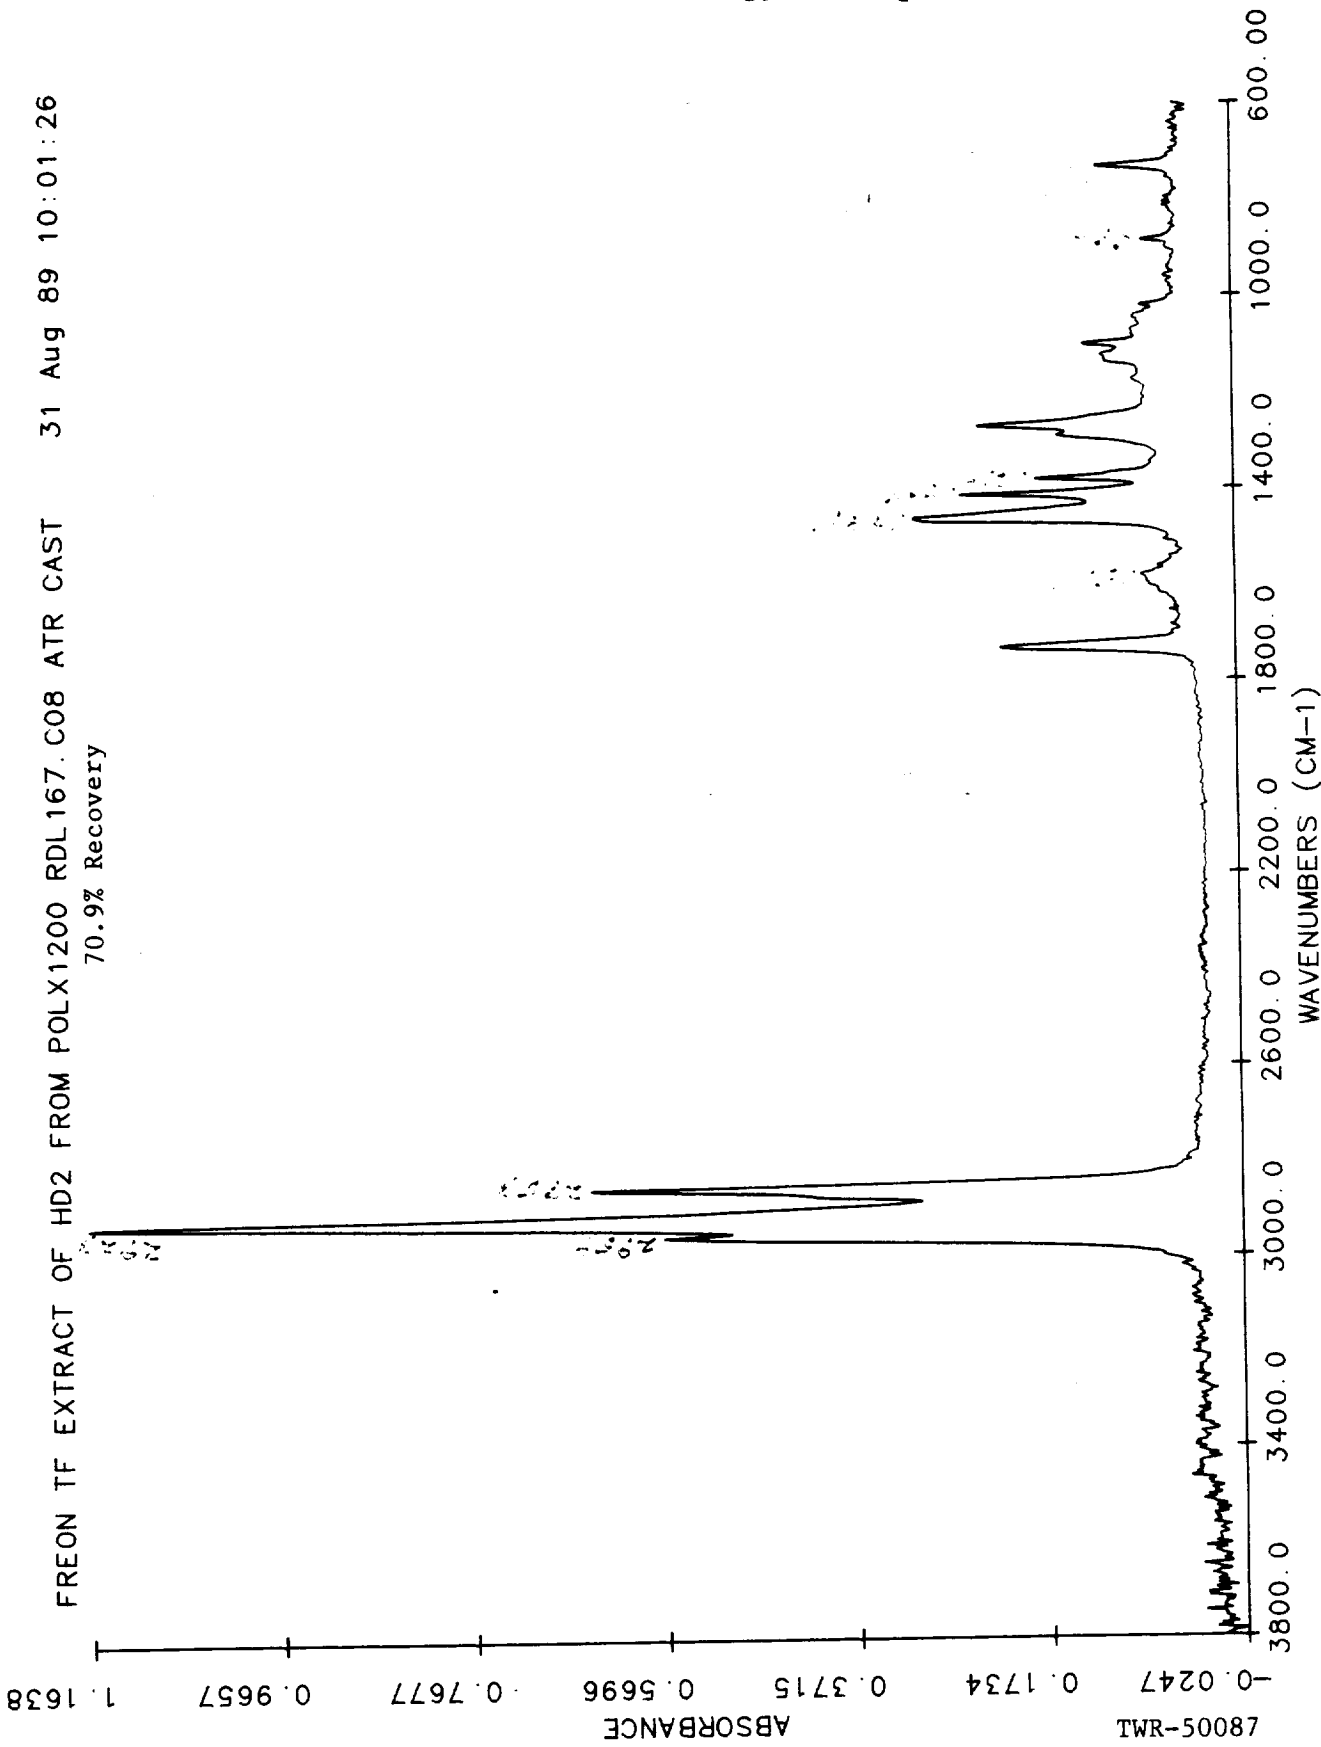


Figure 55.

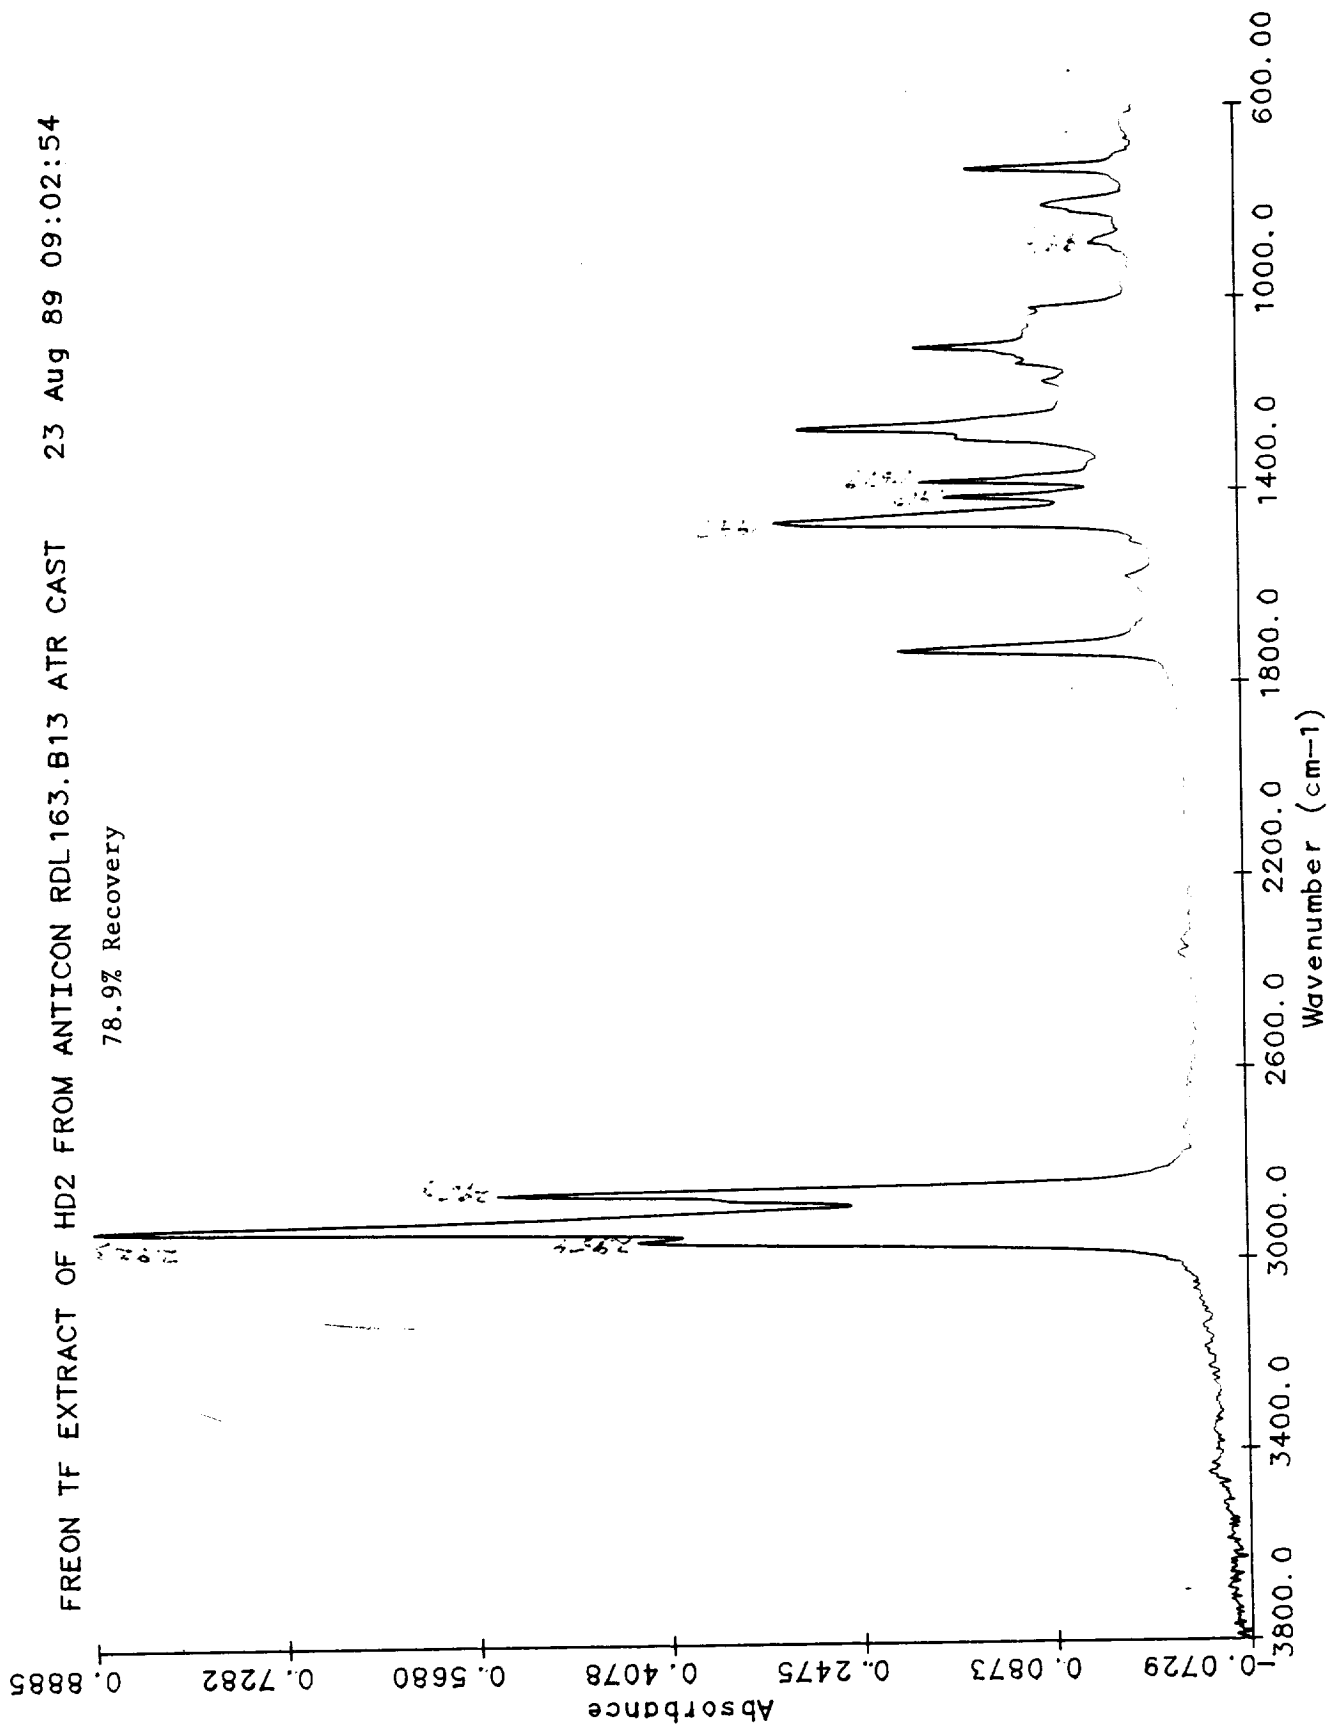

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 56.

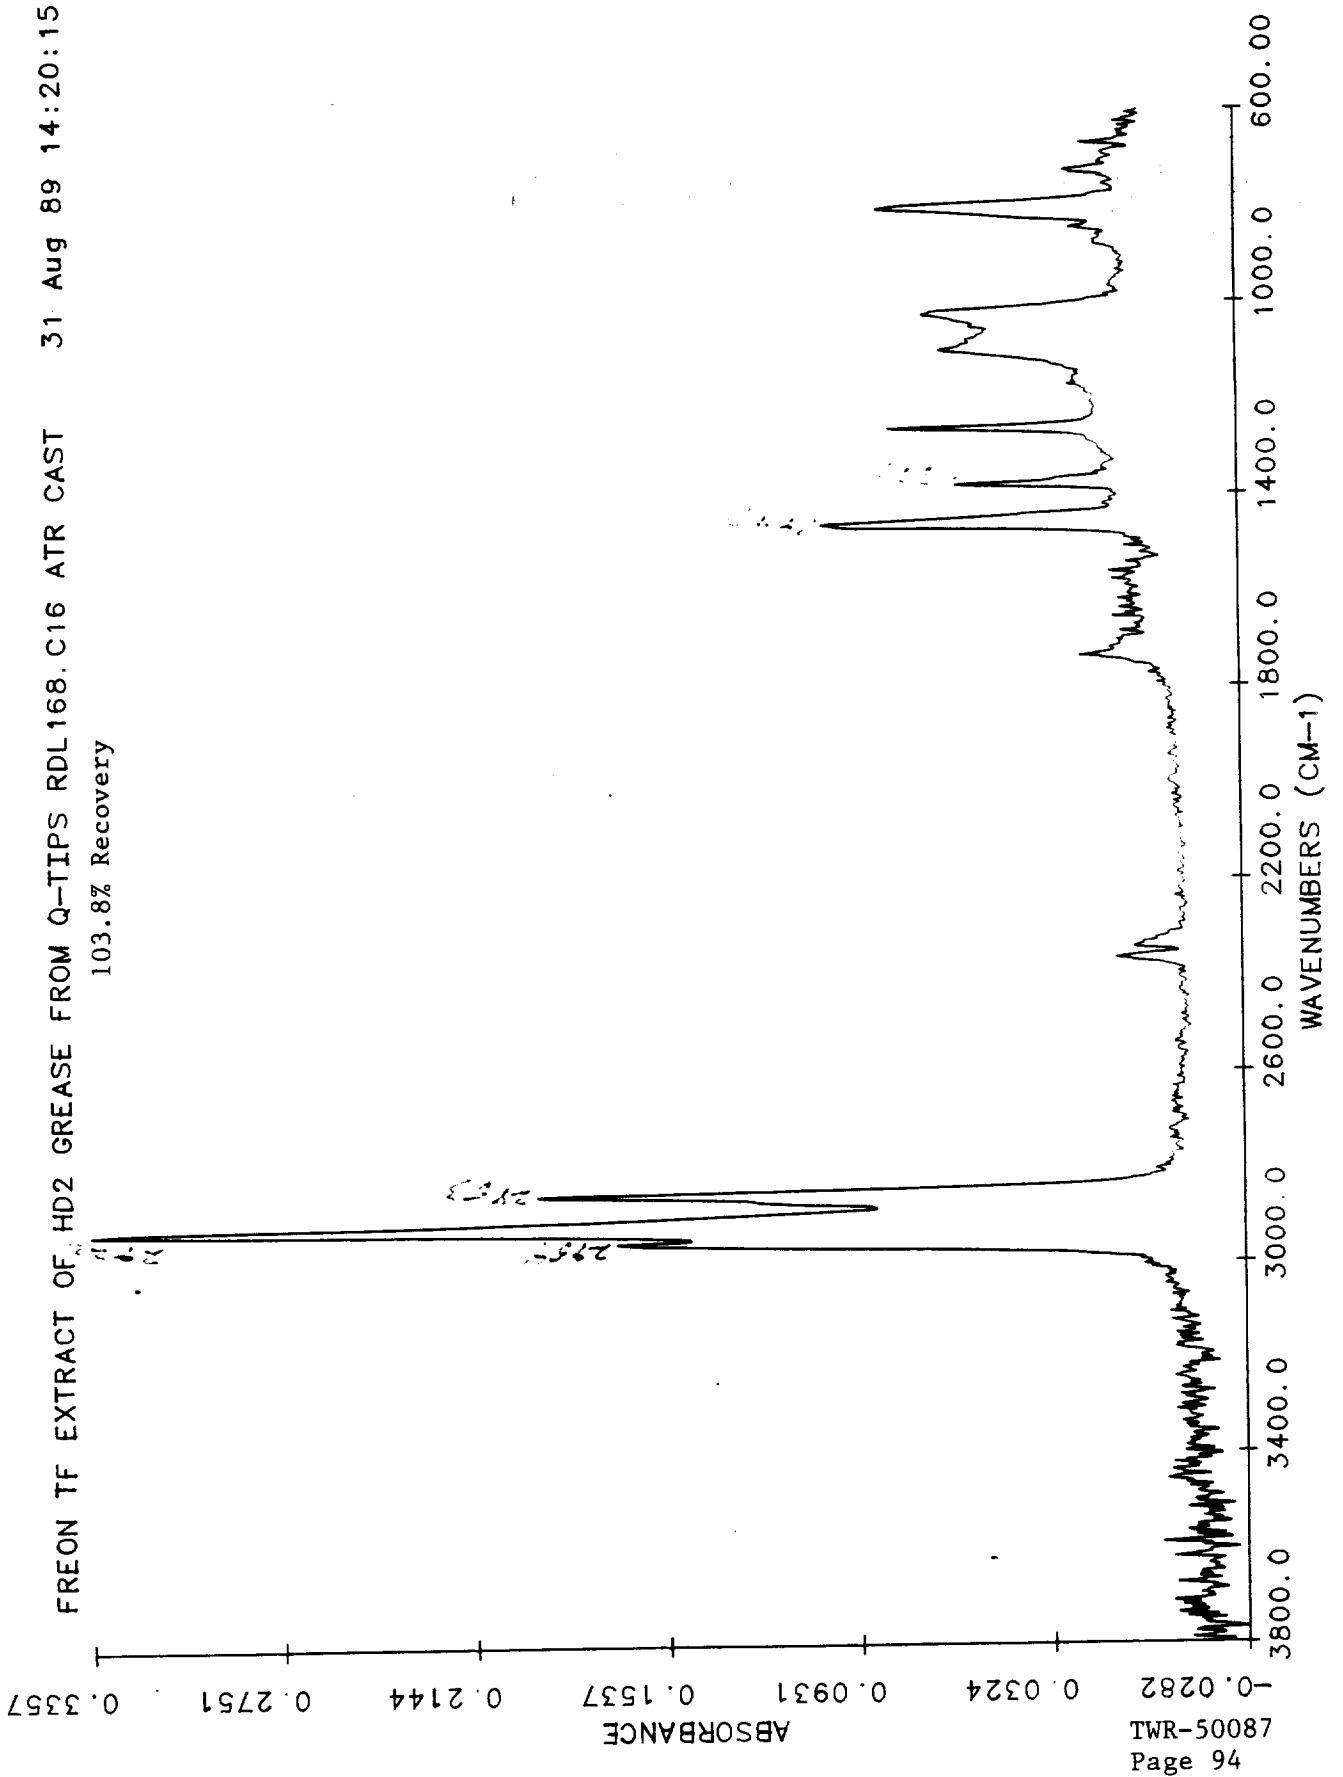

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 57.


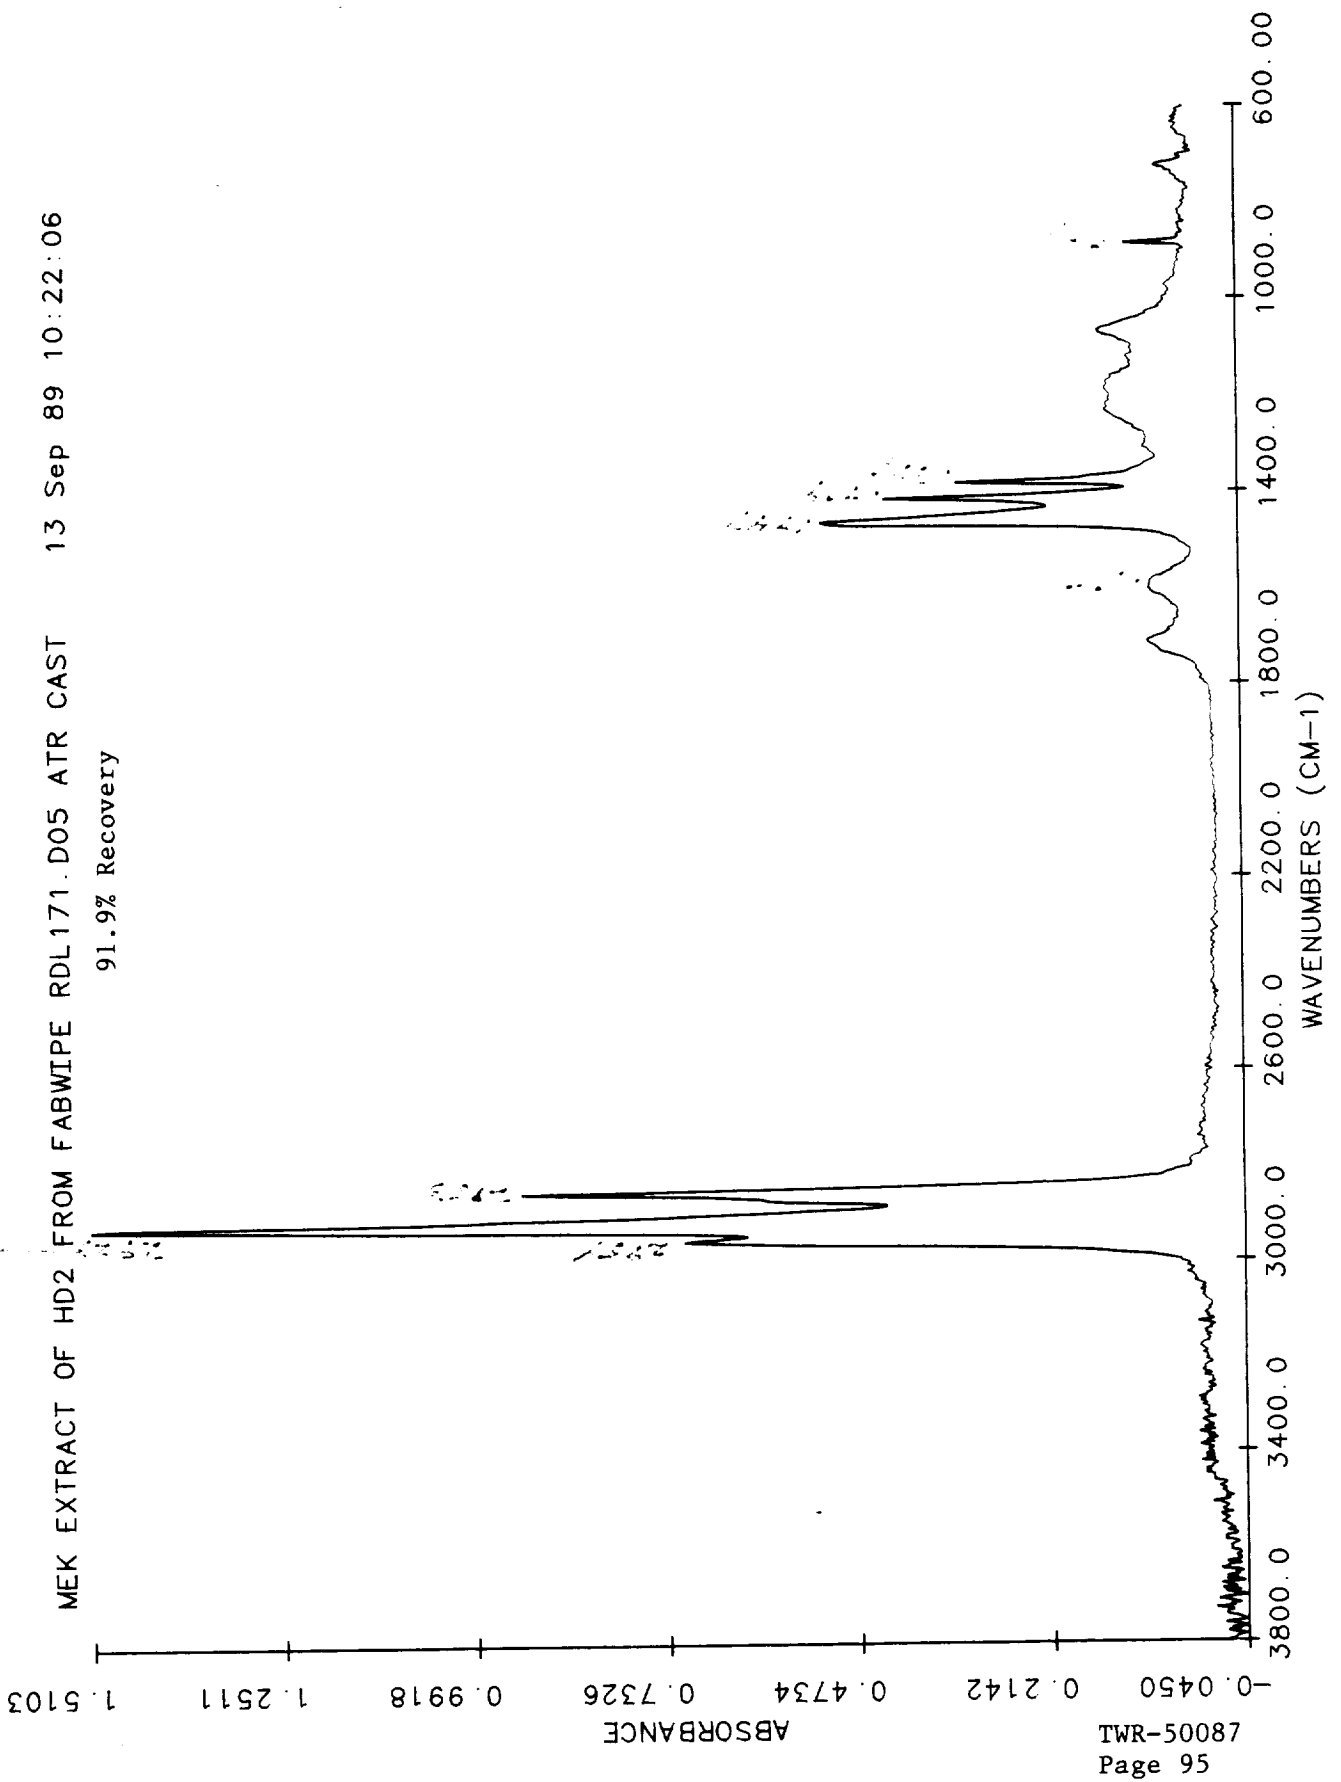



Figure 58.

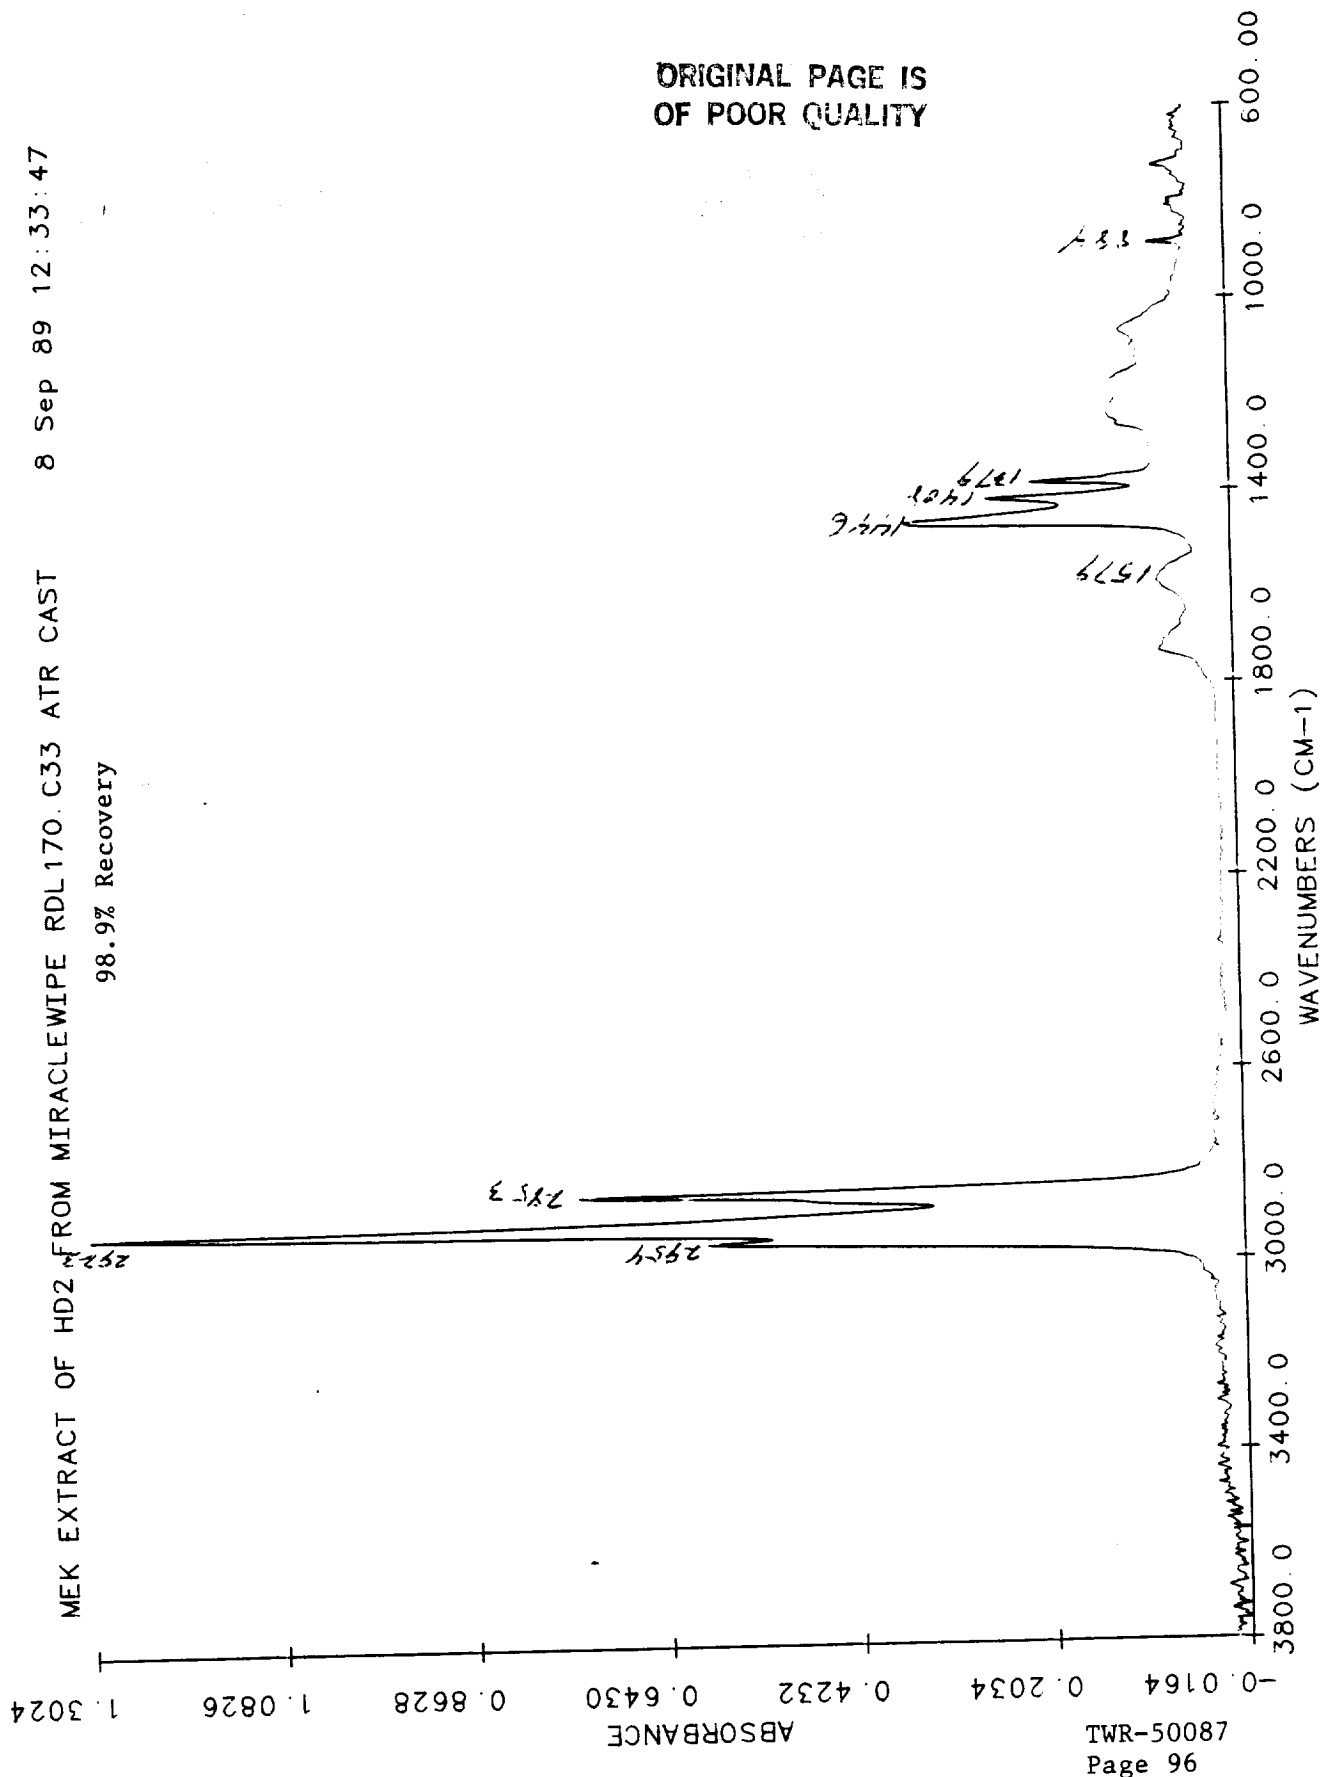

MEK EXTRACT OF HD2 FROM ALPHAWIPE RDL172.D13 ATR CAST
86.9% Recovery

Figure 59.

13 Sep 89 12:39:44

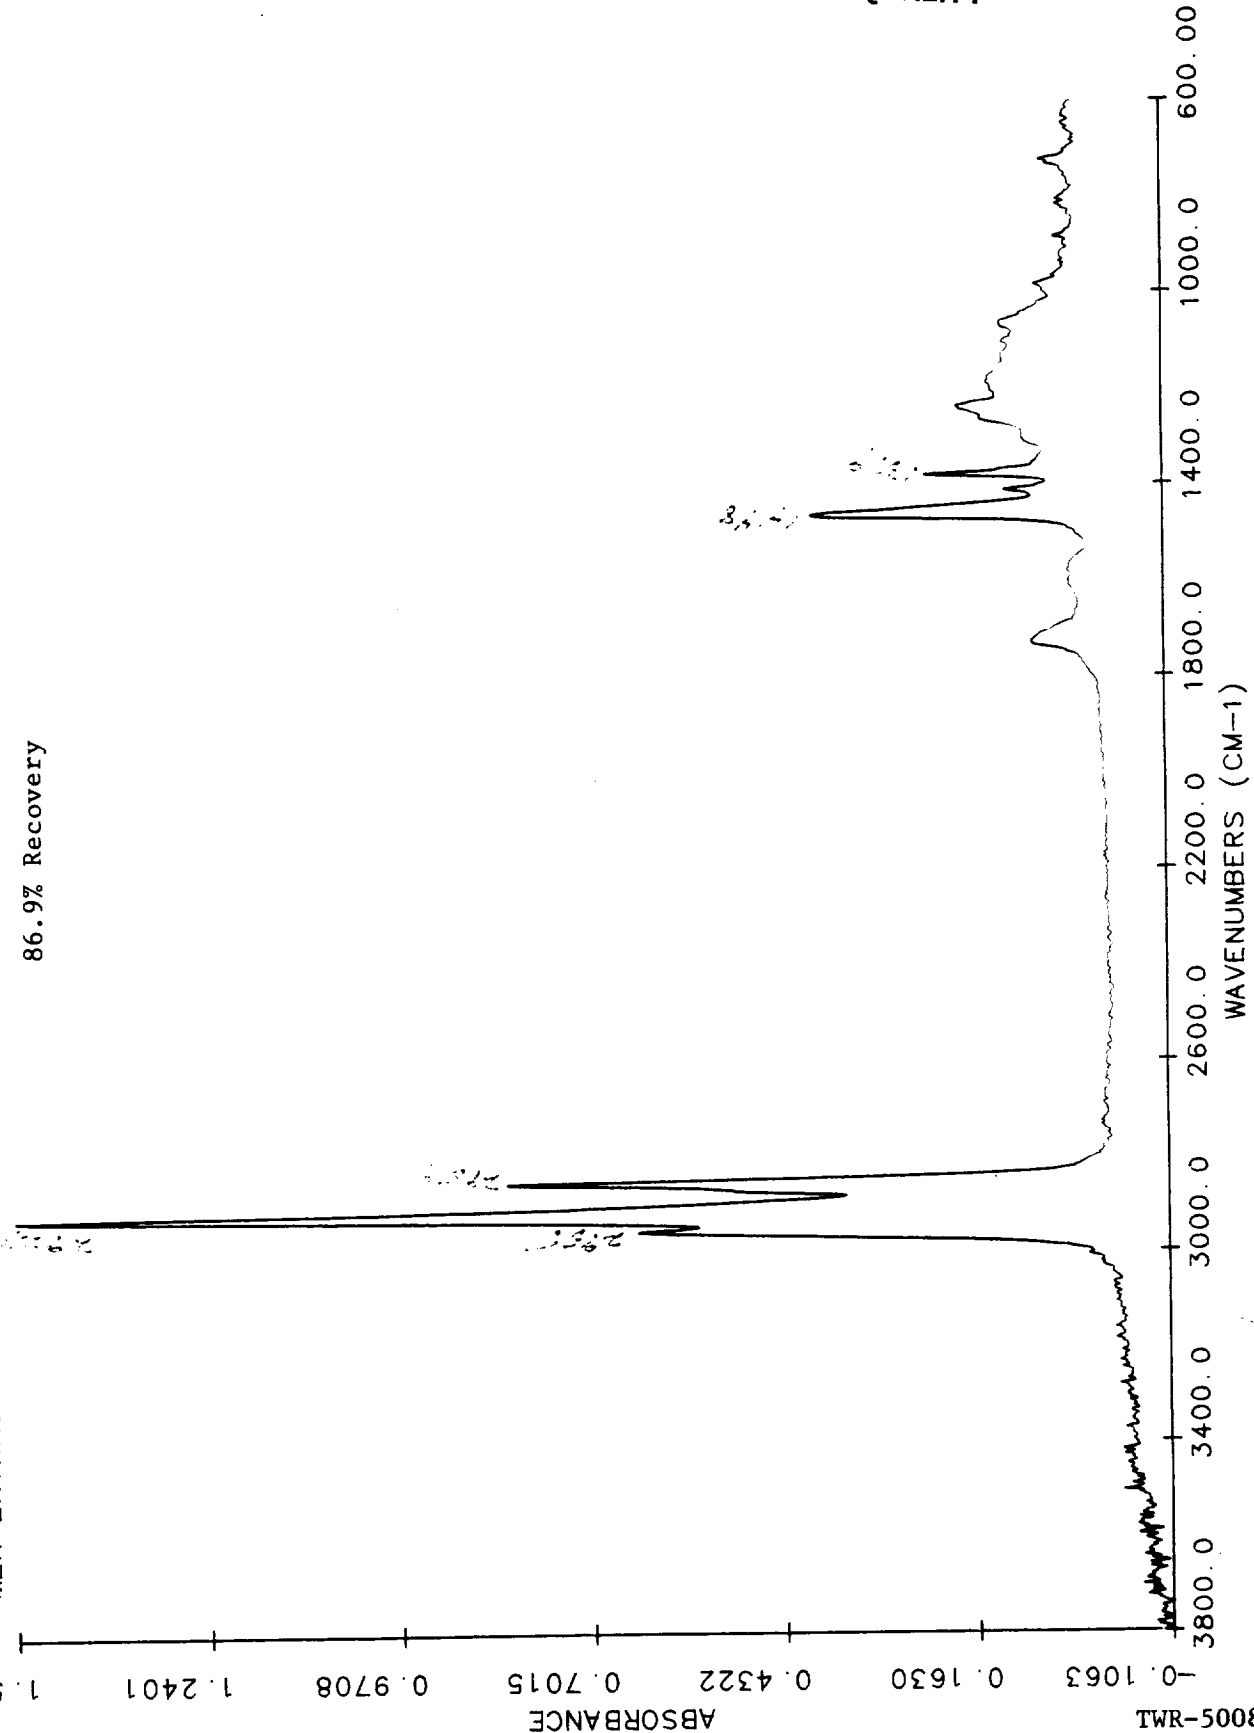

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 60.

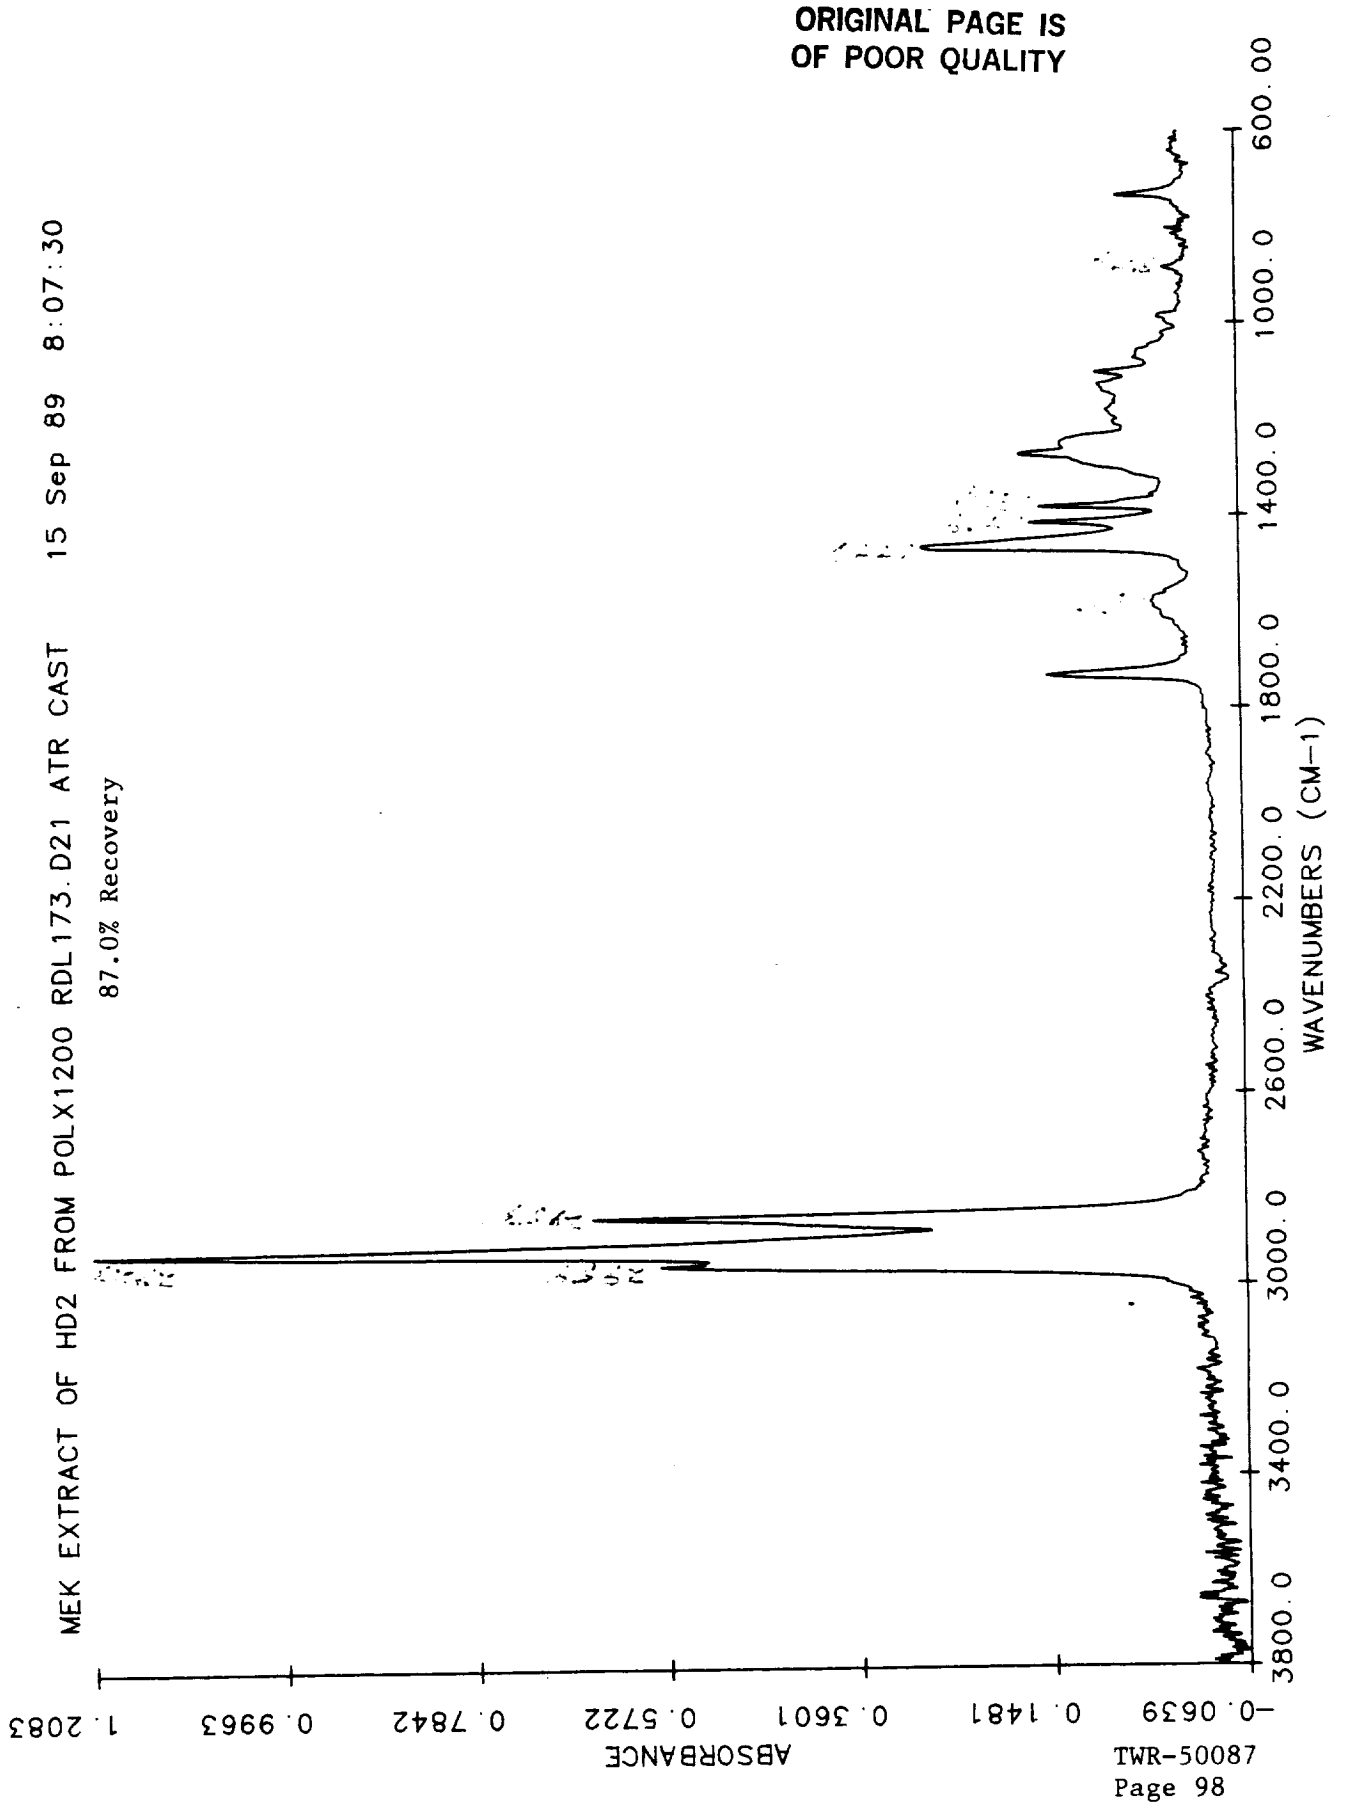


Figure 61.

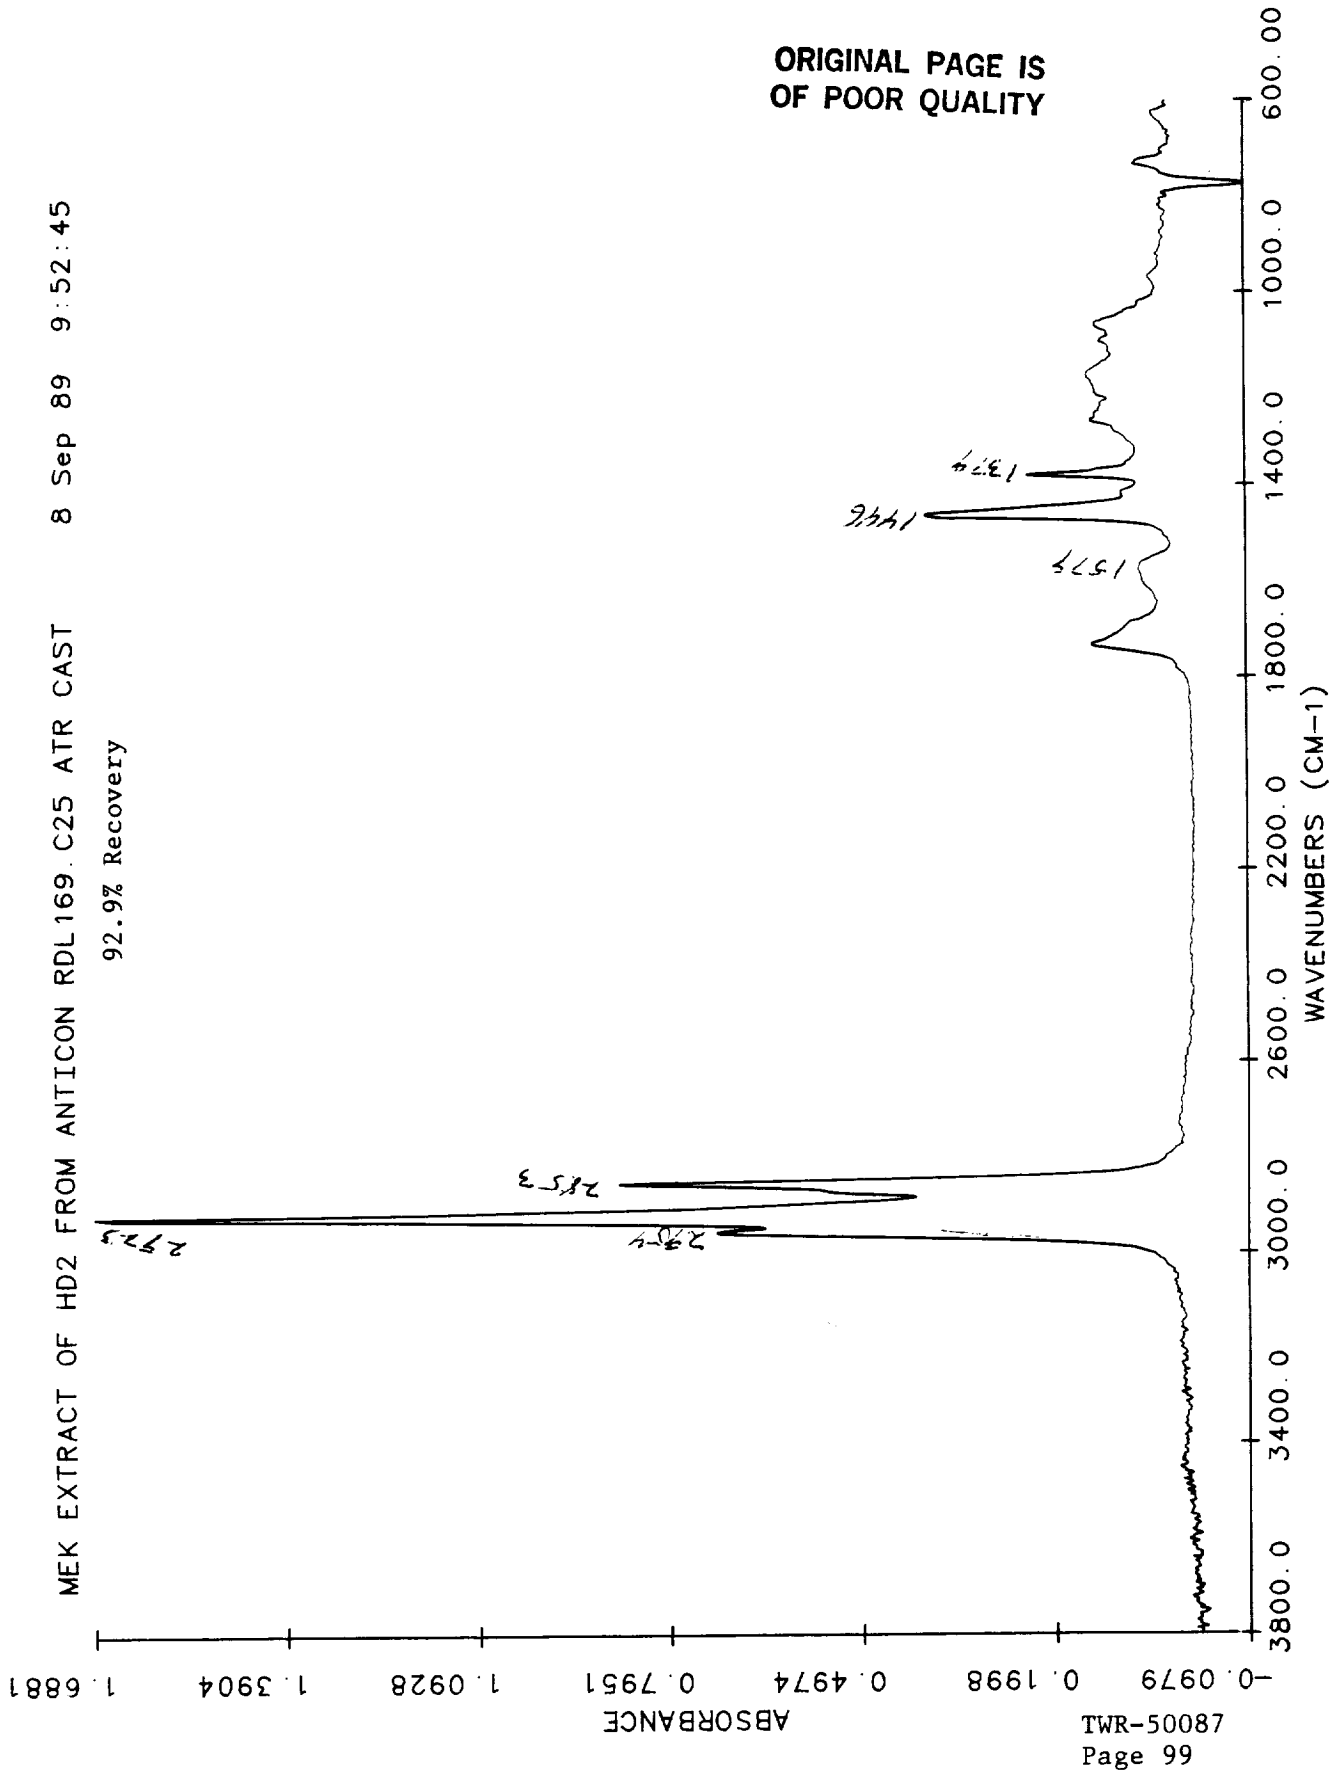


Figure 62.

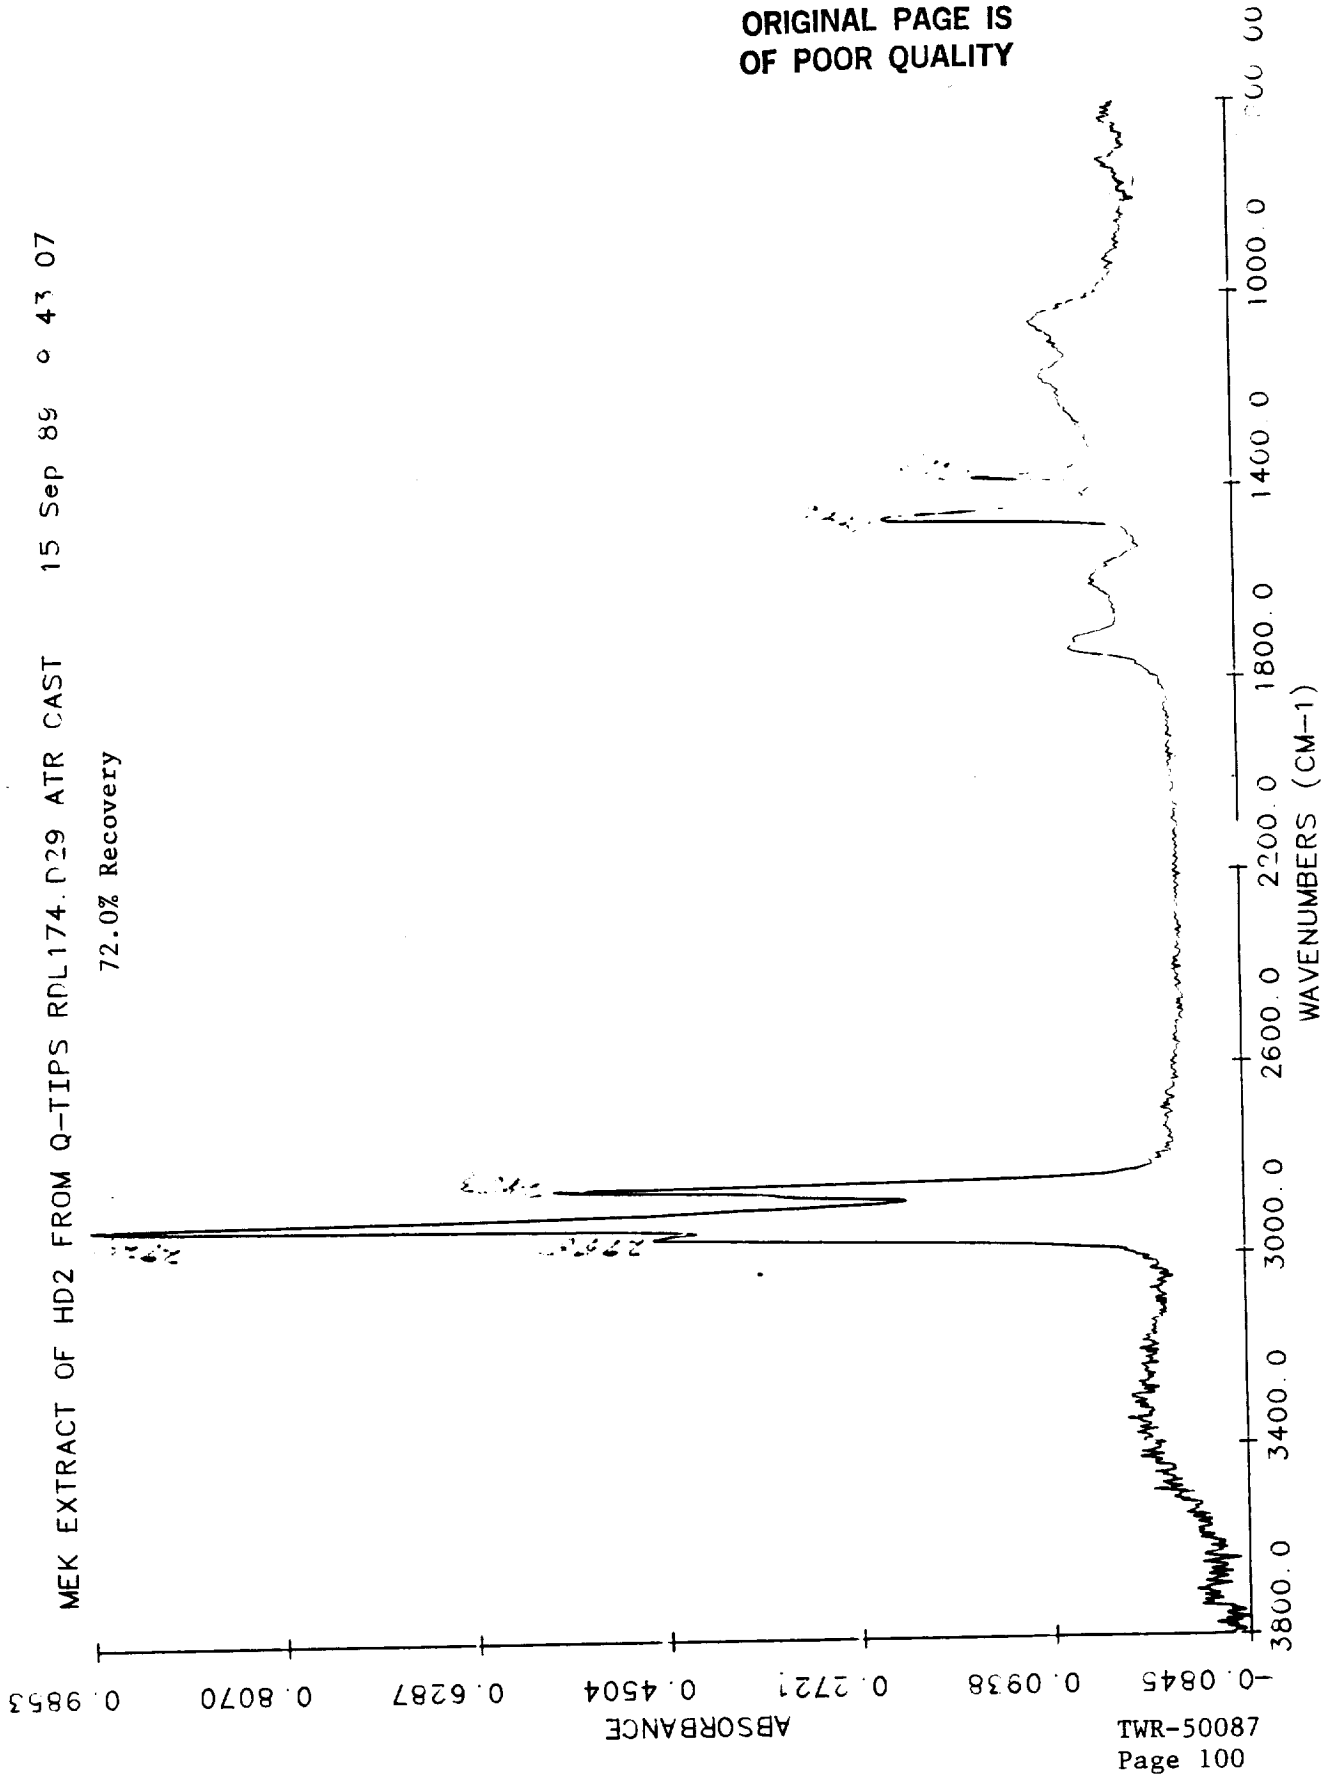


Figure 63.
TCE SHAKEN EXTRACT OF HD2 FROM ANTICON RDL176.E01 ATR CAST 09 Oct 88 08:01:08

100.9% Recovery

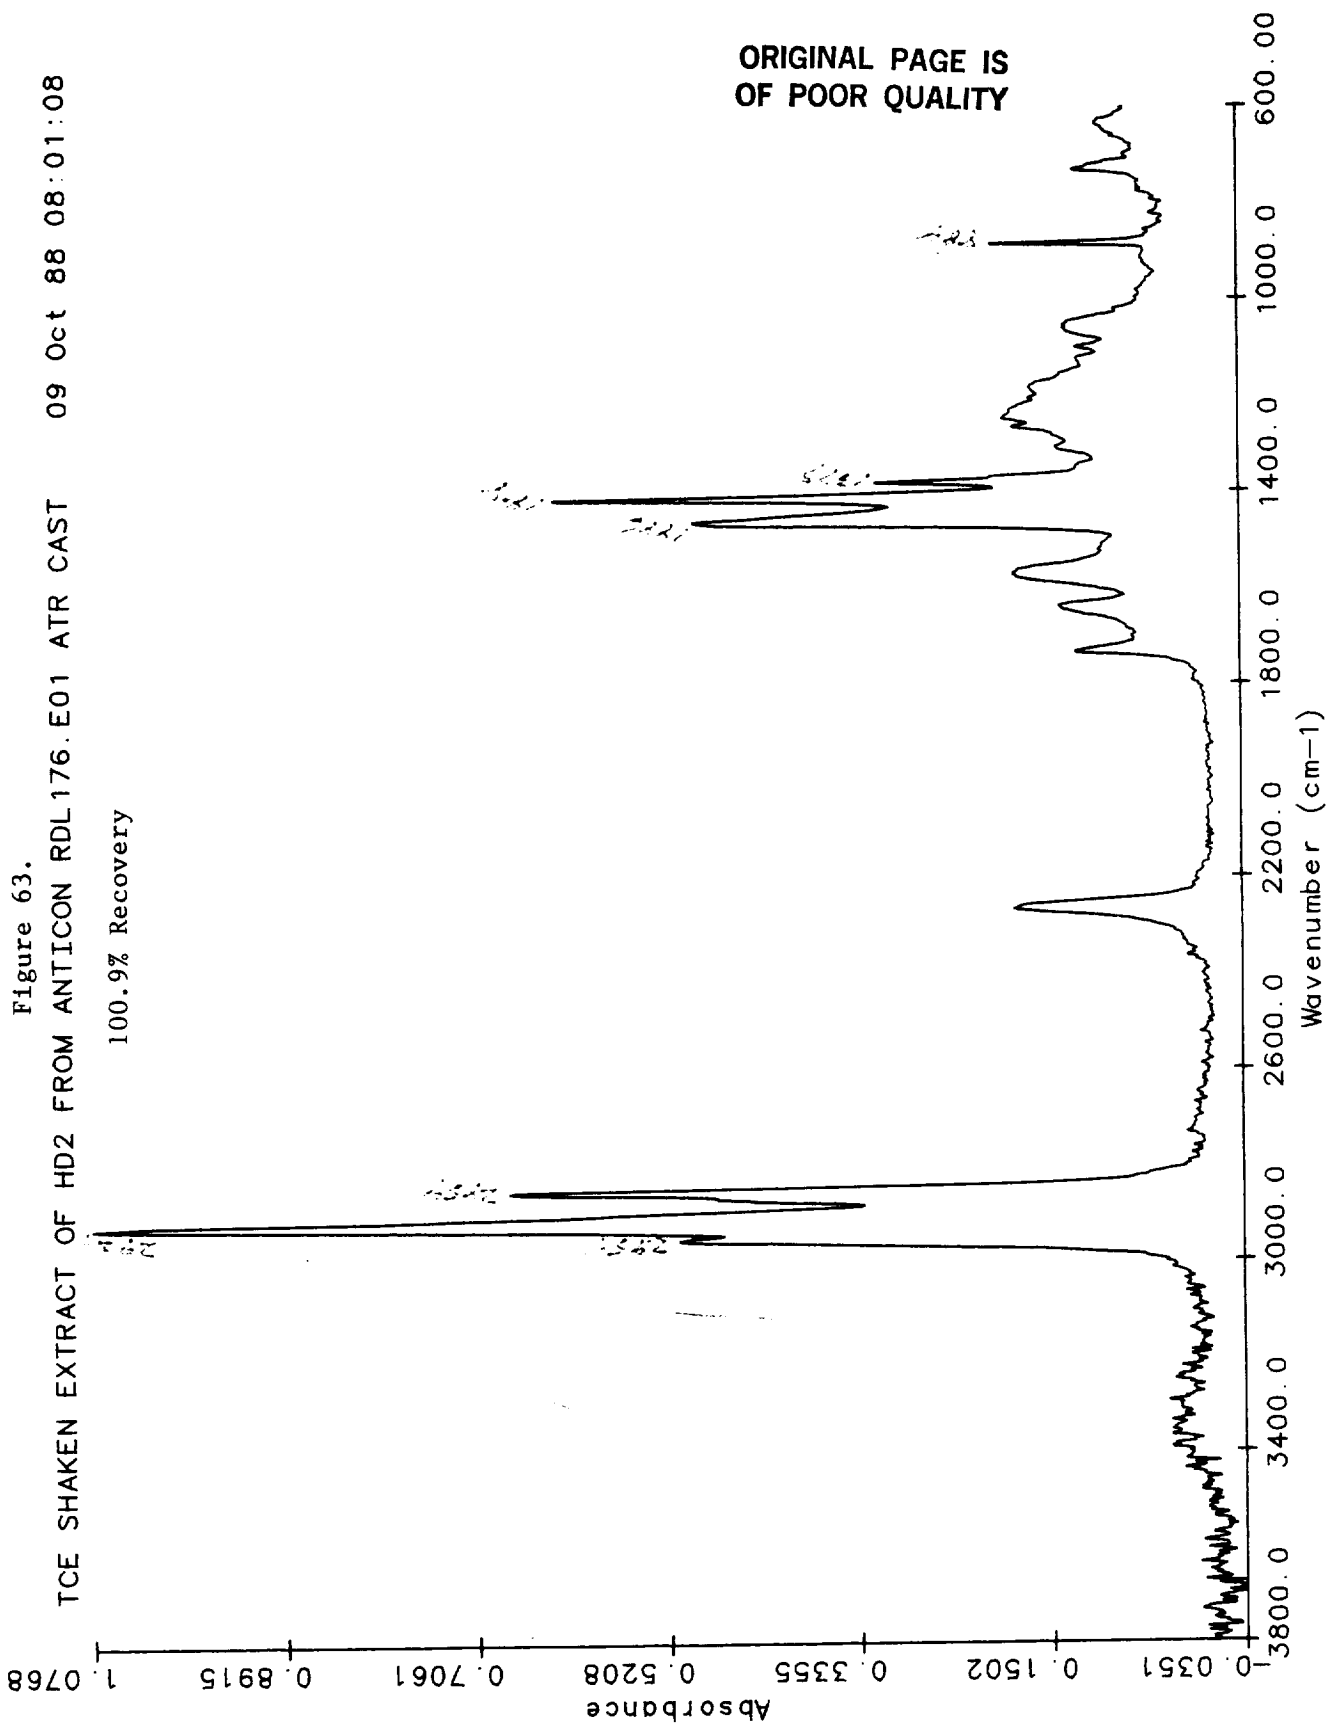


Figure 64.
FREON SHAKEN EXTRACT OF HD2 FROM FABWIPE RDL176.E08 ATR CAST 09 Oct 88 10:41:27
85.9% Recovery

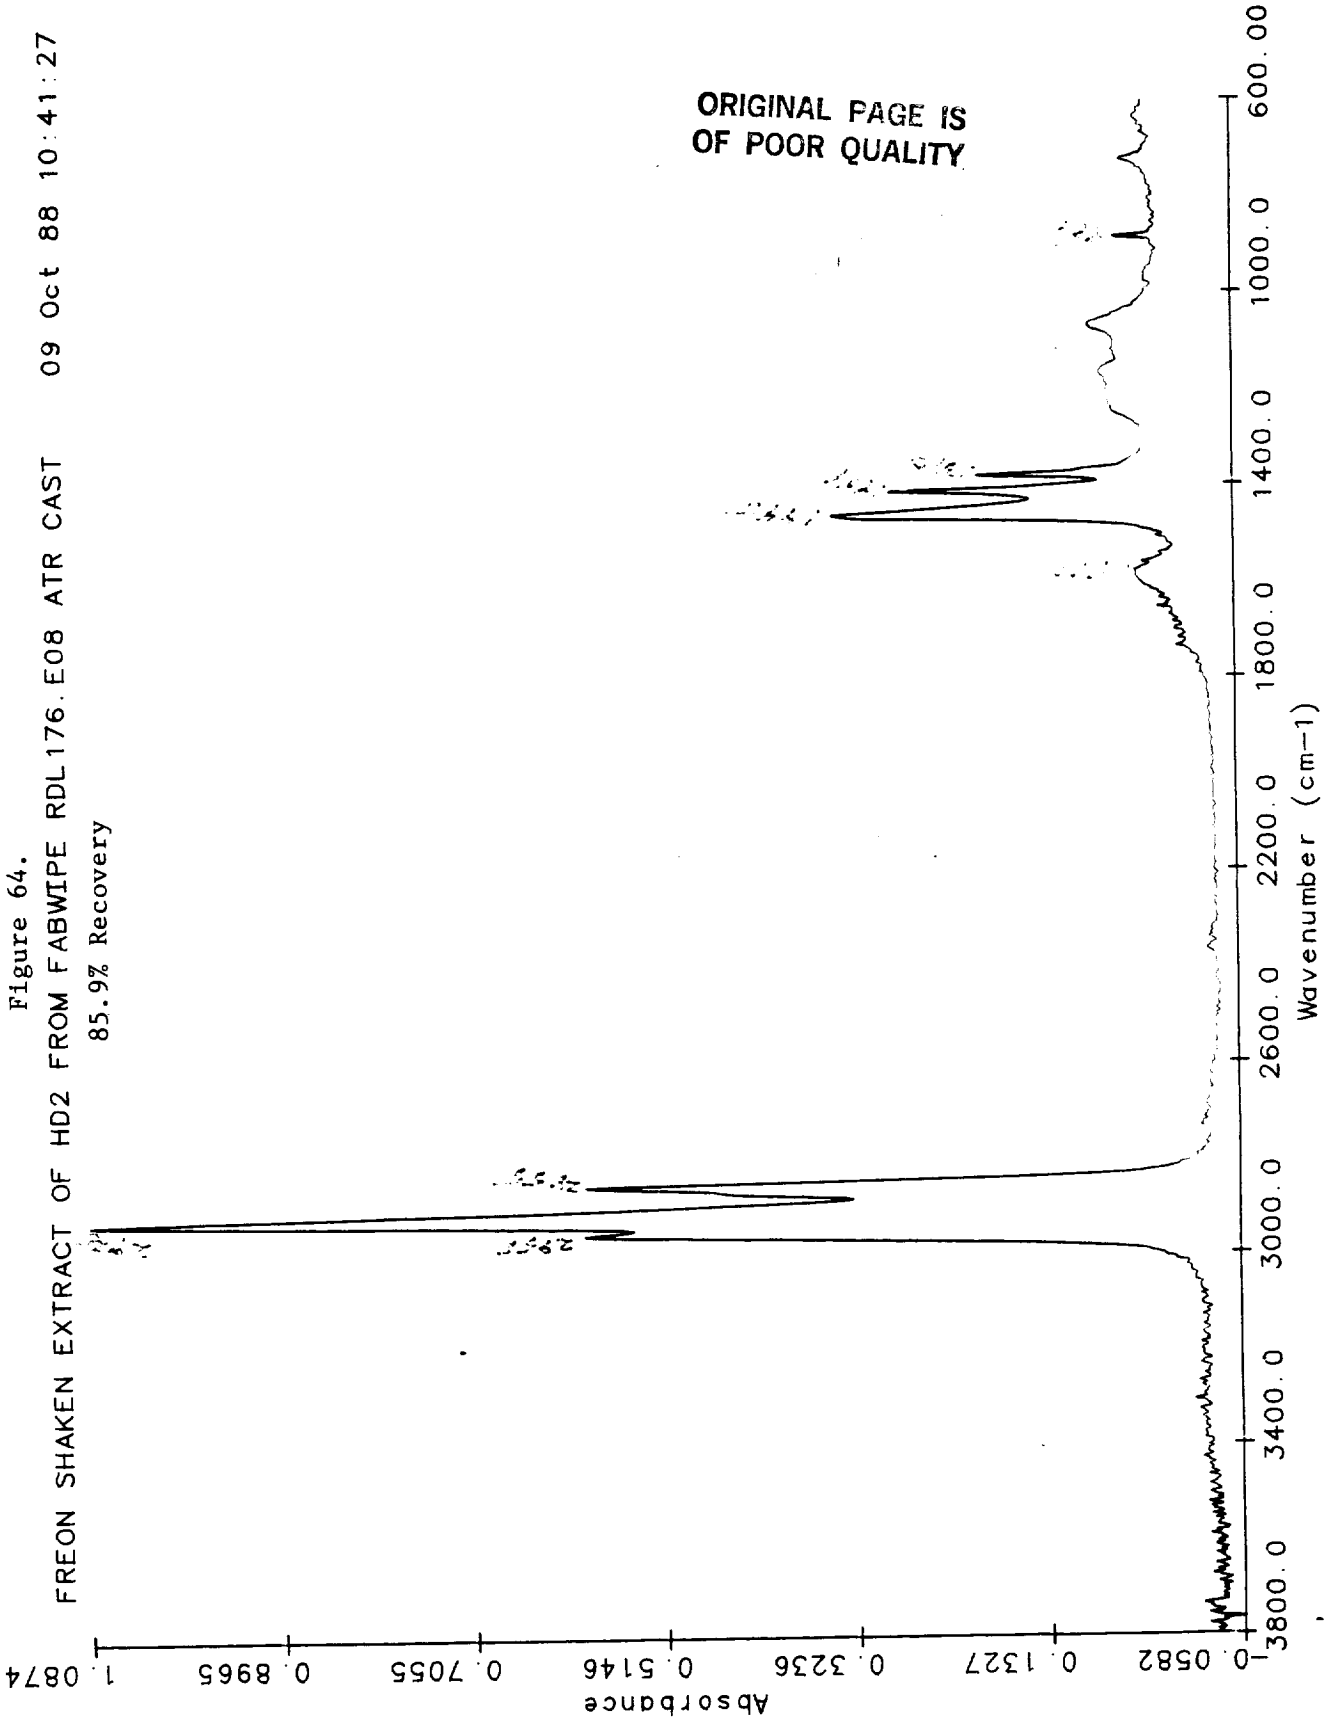


Figure 65.
FREON SHAKEN EXTRACT OF HD2 FROM MIRACLEWIPE RDL176.E07 ATR CAS 09 Oct 88 10:35:17
80.9% Recovery


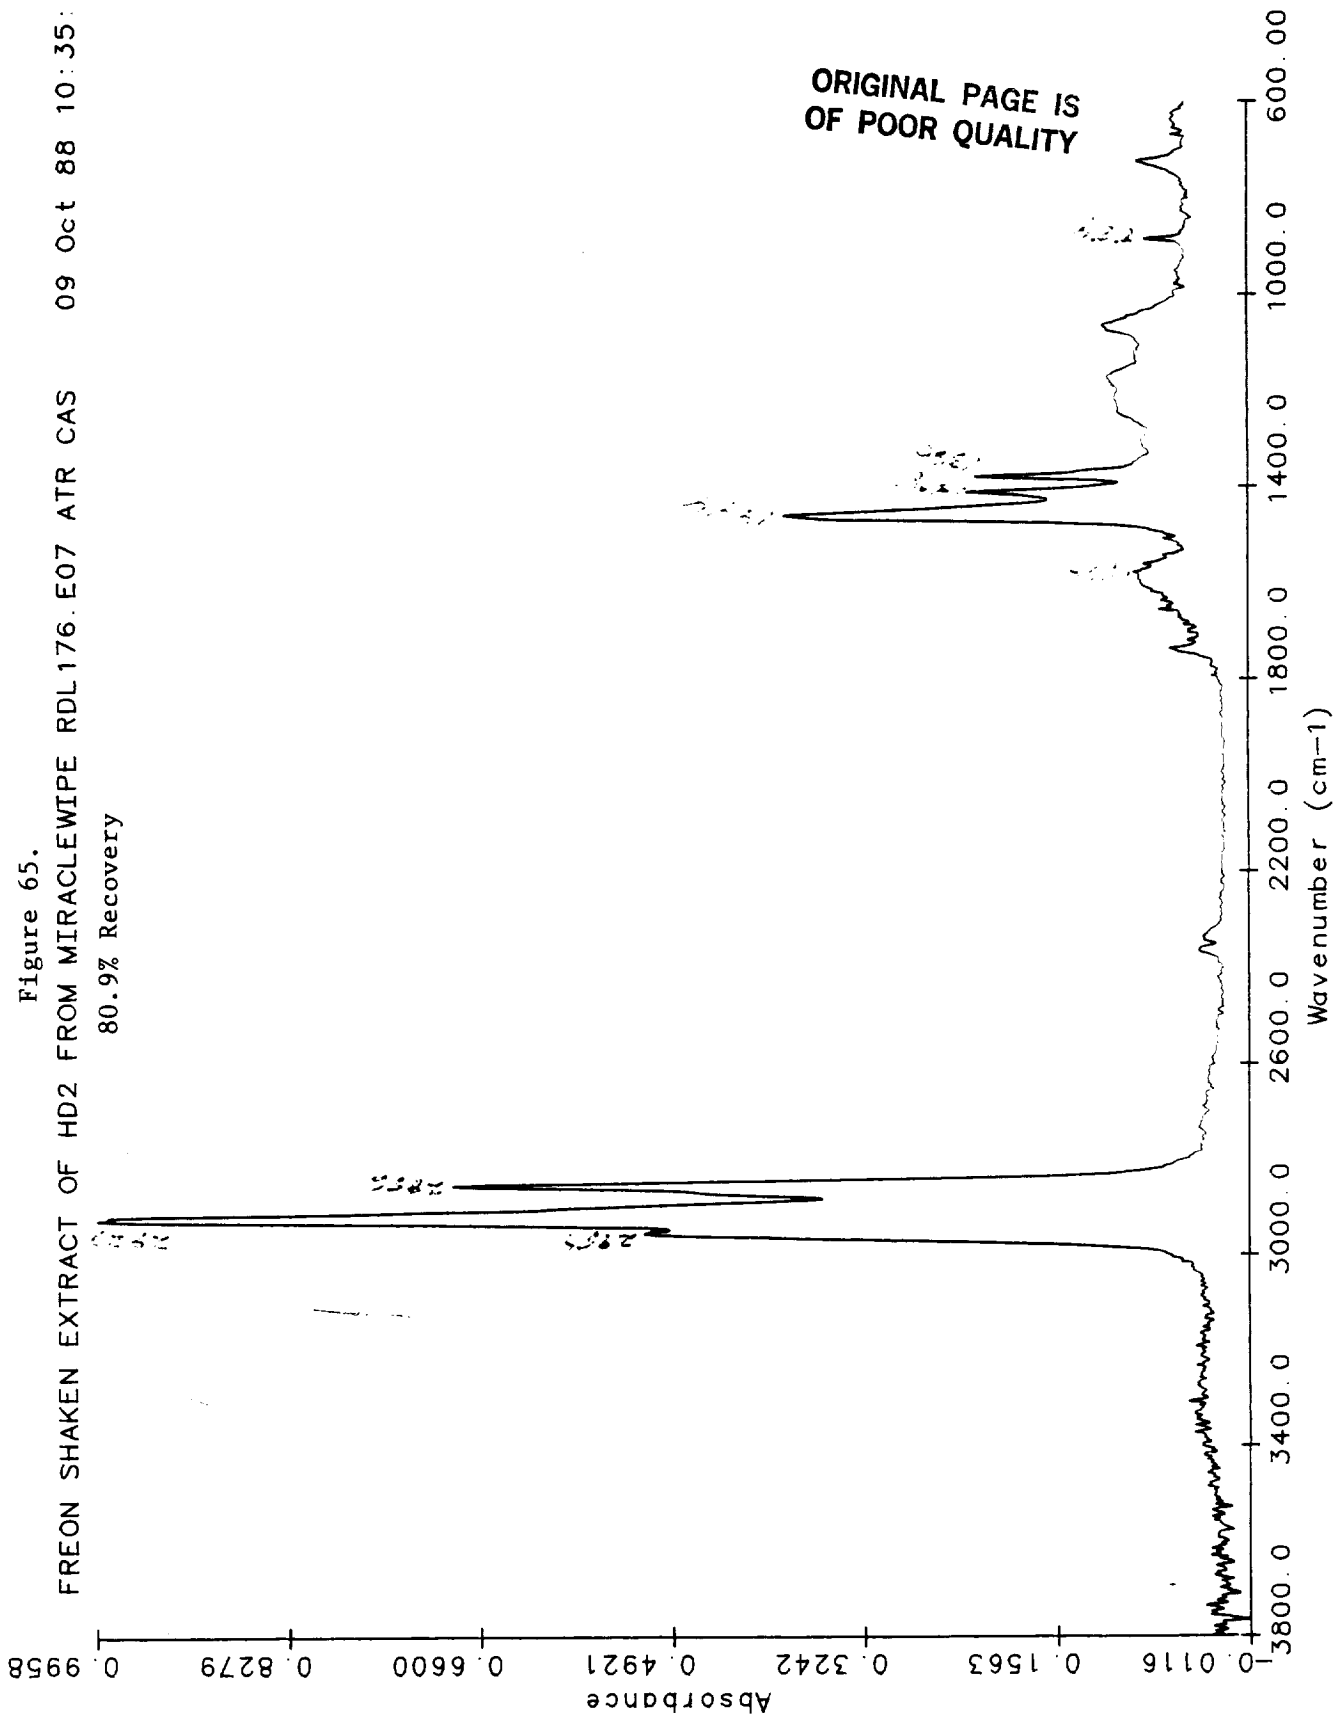


Figure 66.
FREON SHAKEN EXTRACT OF HD2 FROM ANTICON RDL176.E06 09 Oct 88 10:28:27


77.9% Recovery

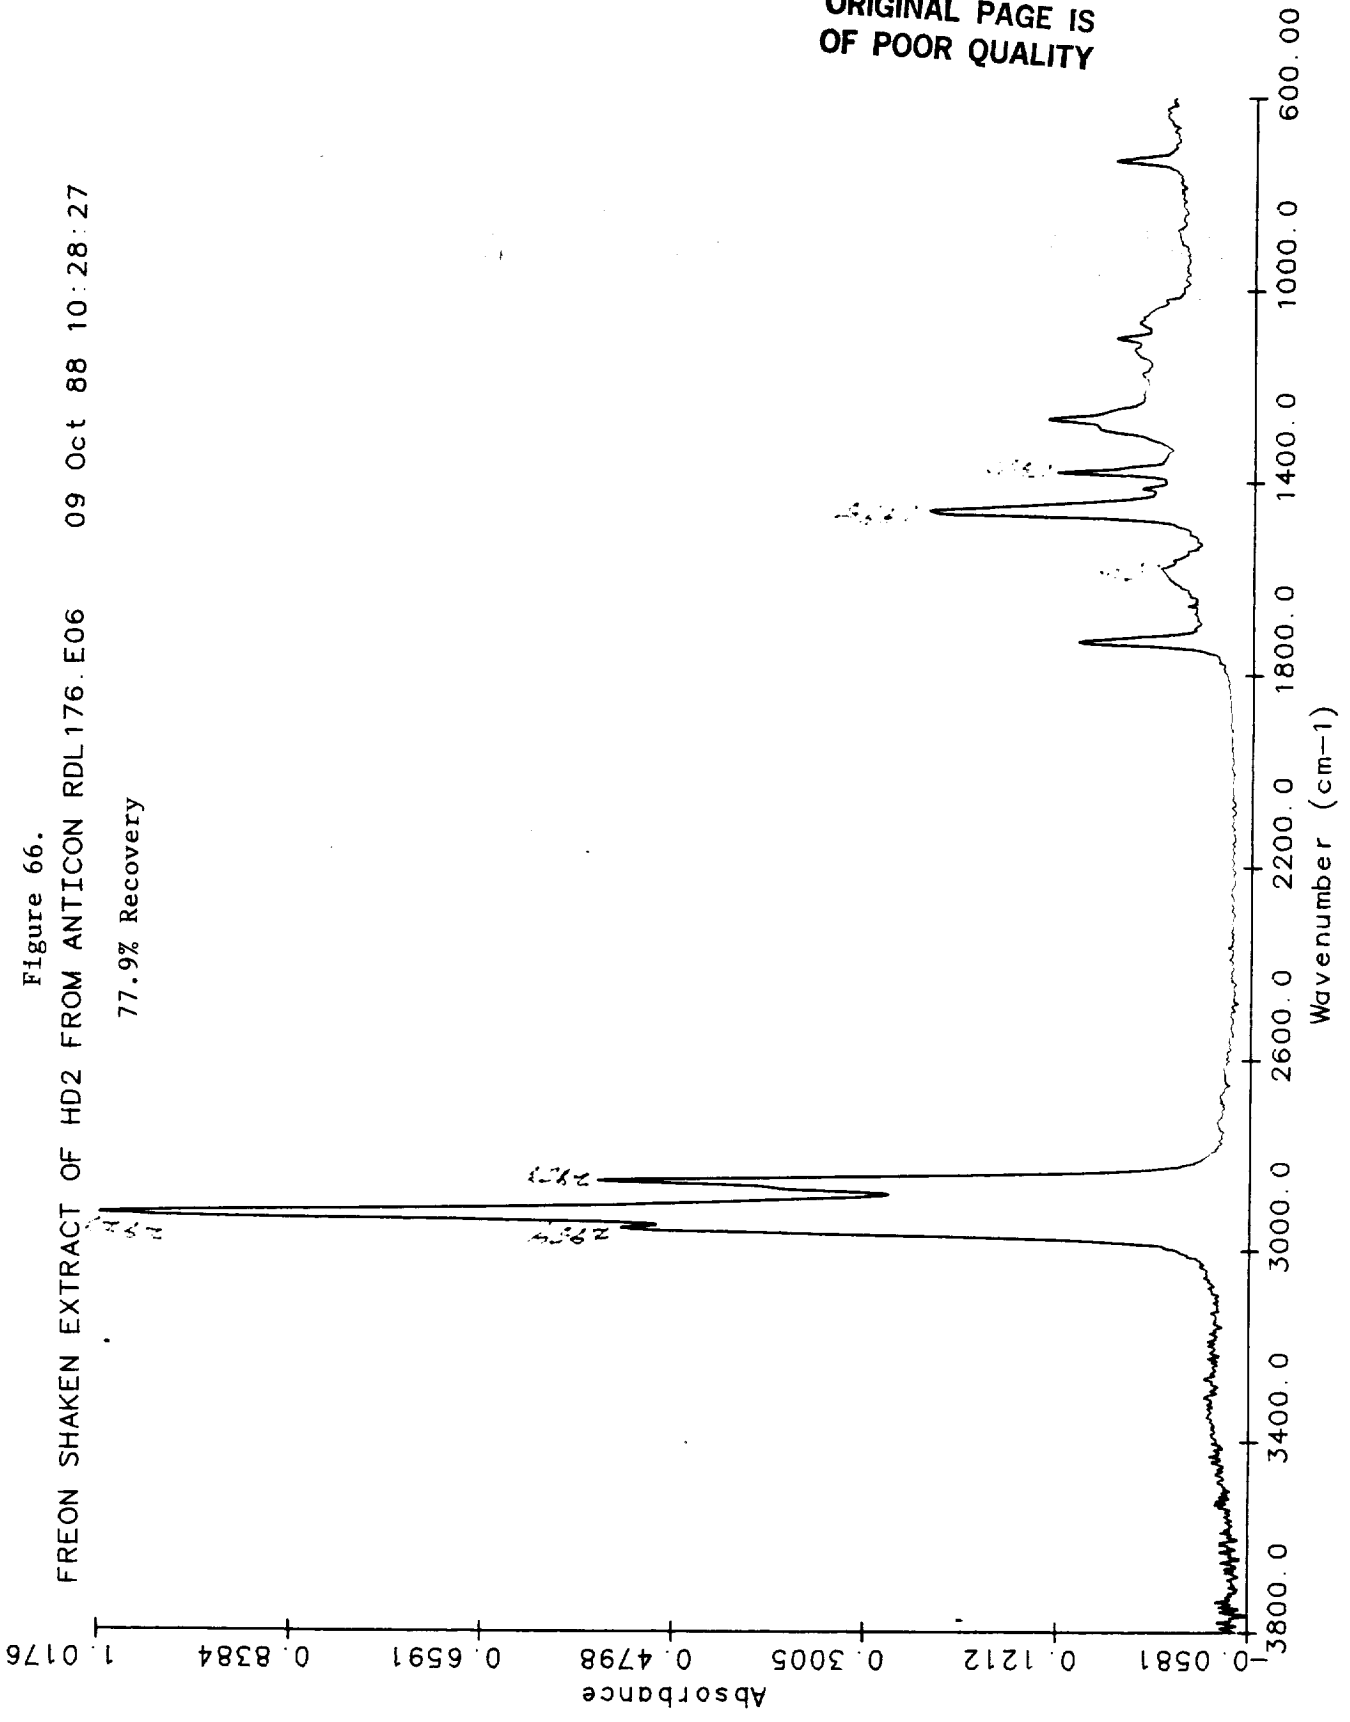

MEK SHAKEN EXTRACT OF HD2 FROM FABWIPE RDL177.E15 ATR CAST 09 Oct 88 12:10:18


Figure 67.

104.9% Recovery

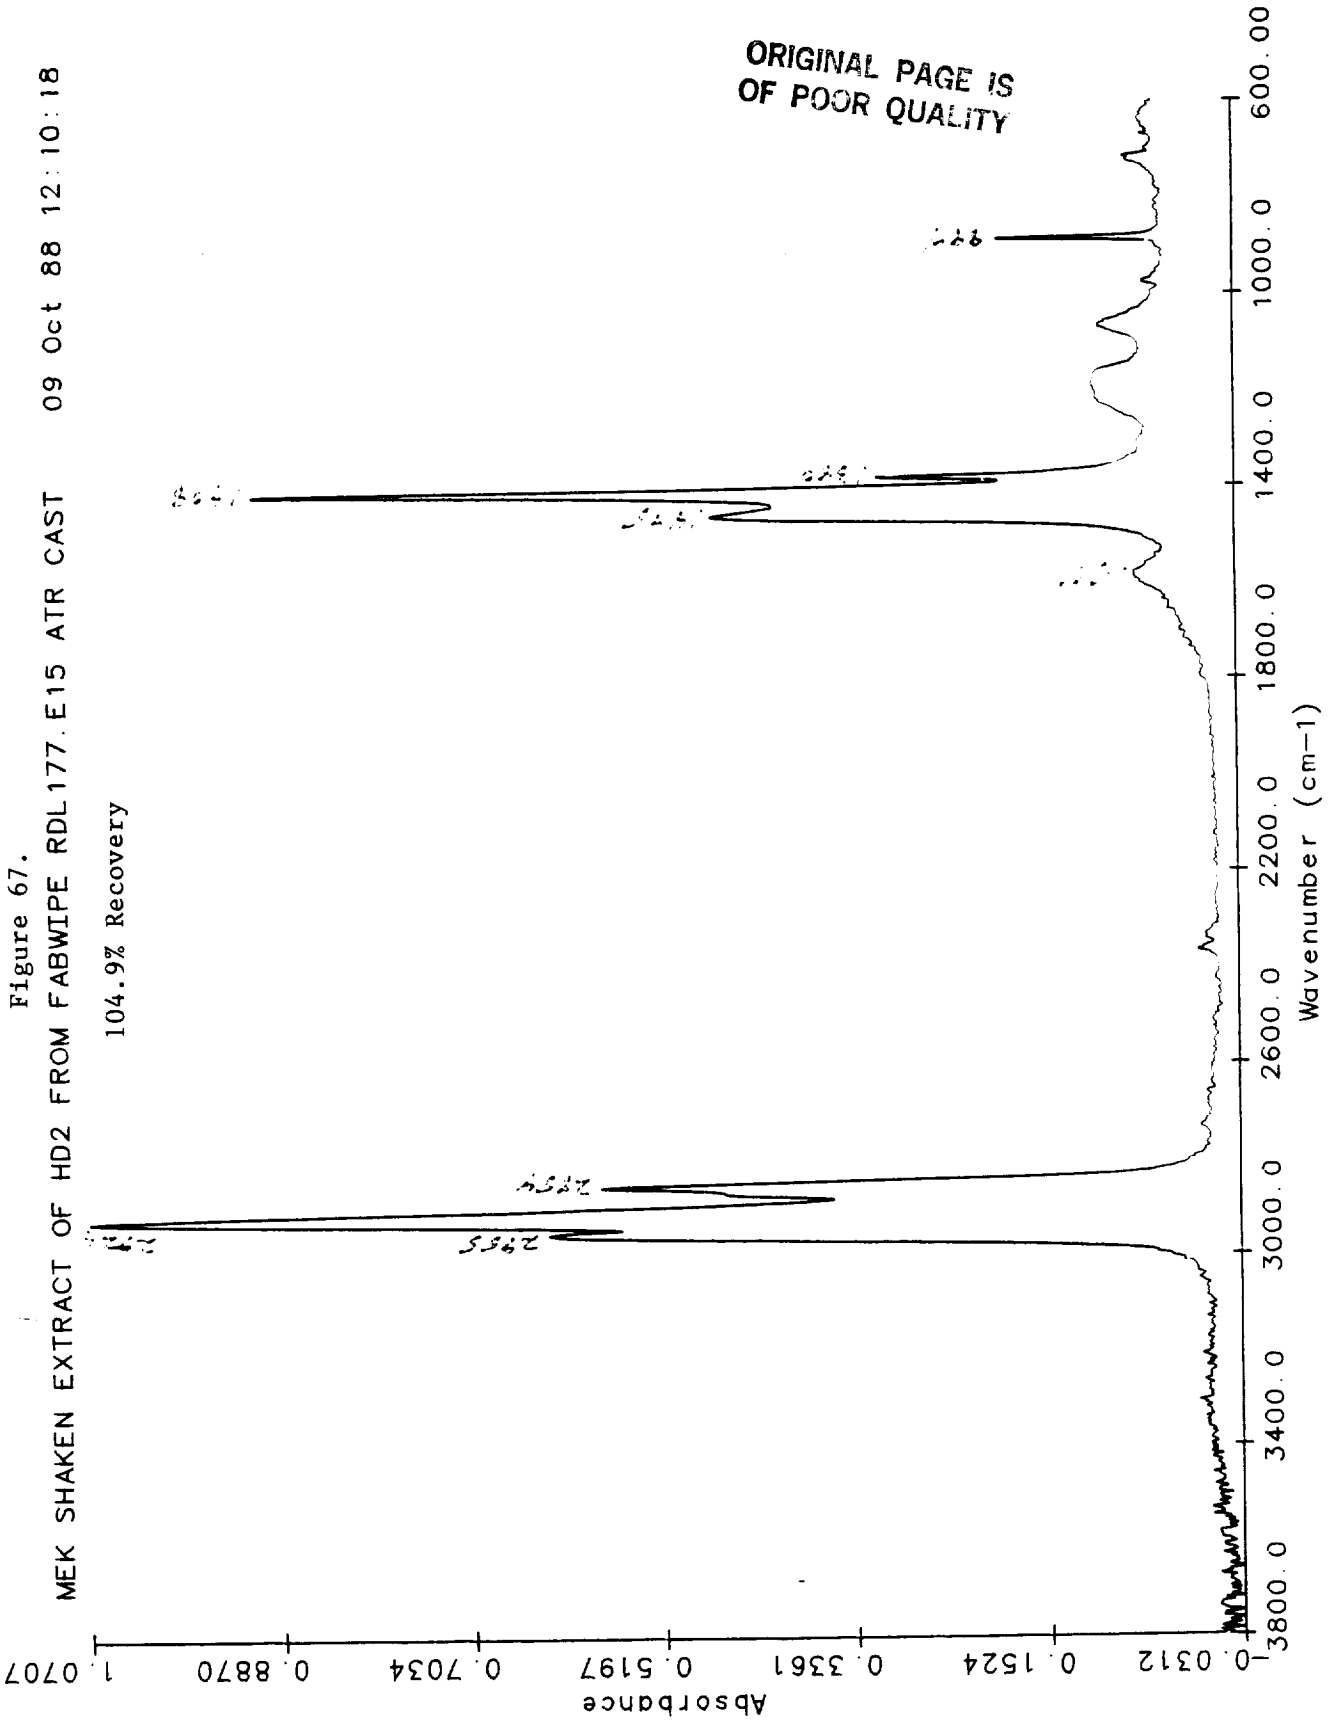

ORIGINAL PAGE IS
OF POOR QUALITY

MEK SHAKEN EXTRACT OF HD2 FROM MIRACLEWIPE RDL177.E14 ATR CAST 09 Oct 88 10:47:56
85.9% Recovery

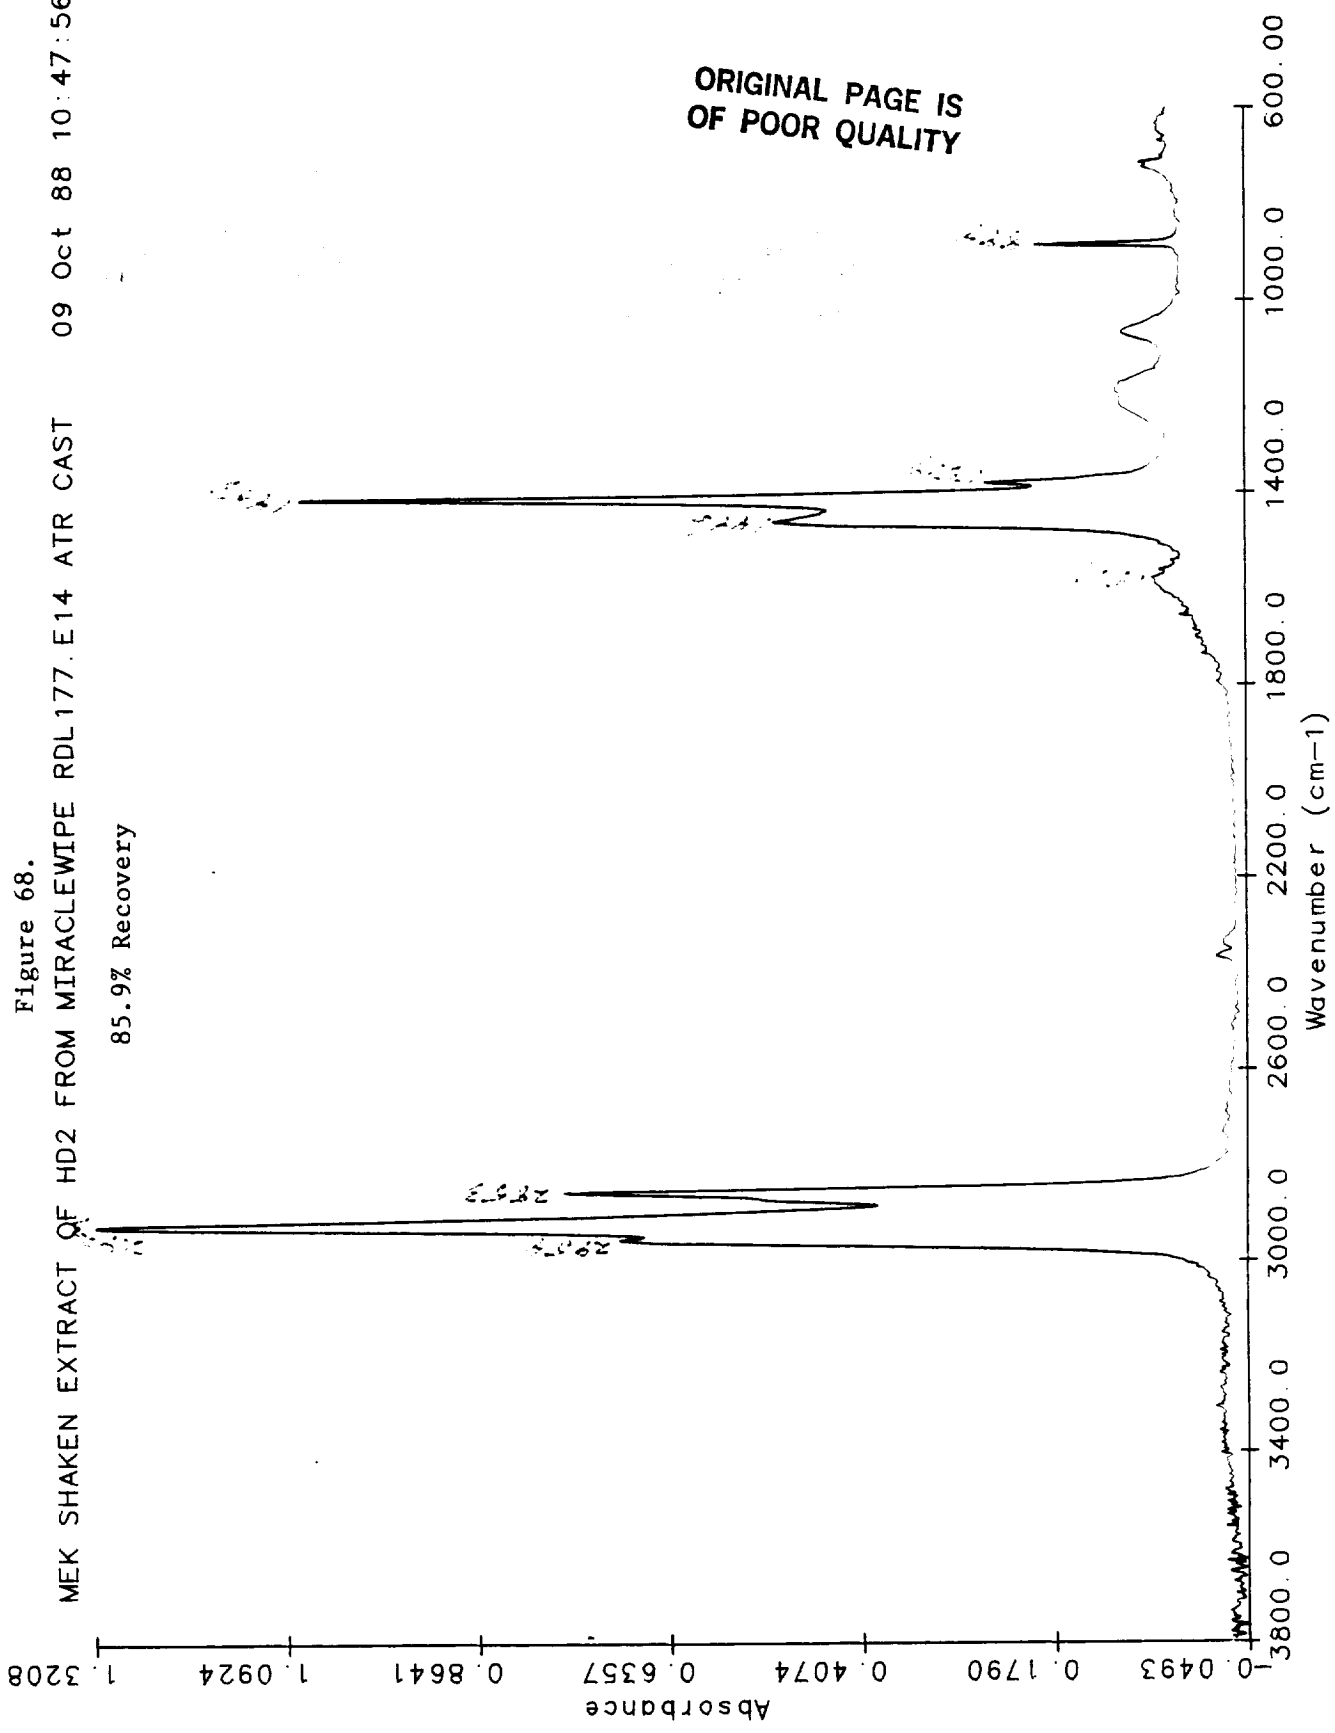

MEK SHAKEN EXTRACT OF HD2 FROM POLX1200 RDL177.E16 ATR CAST

09 Oct 88 12:16:51

88.9% Recovery

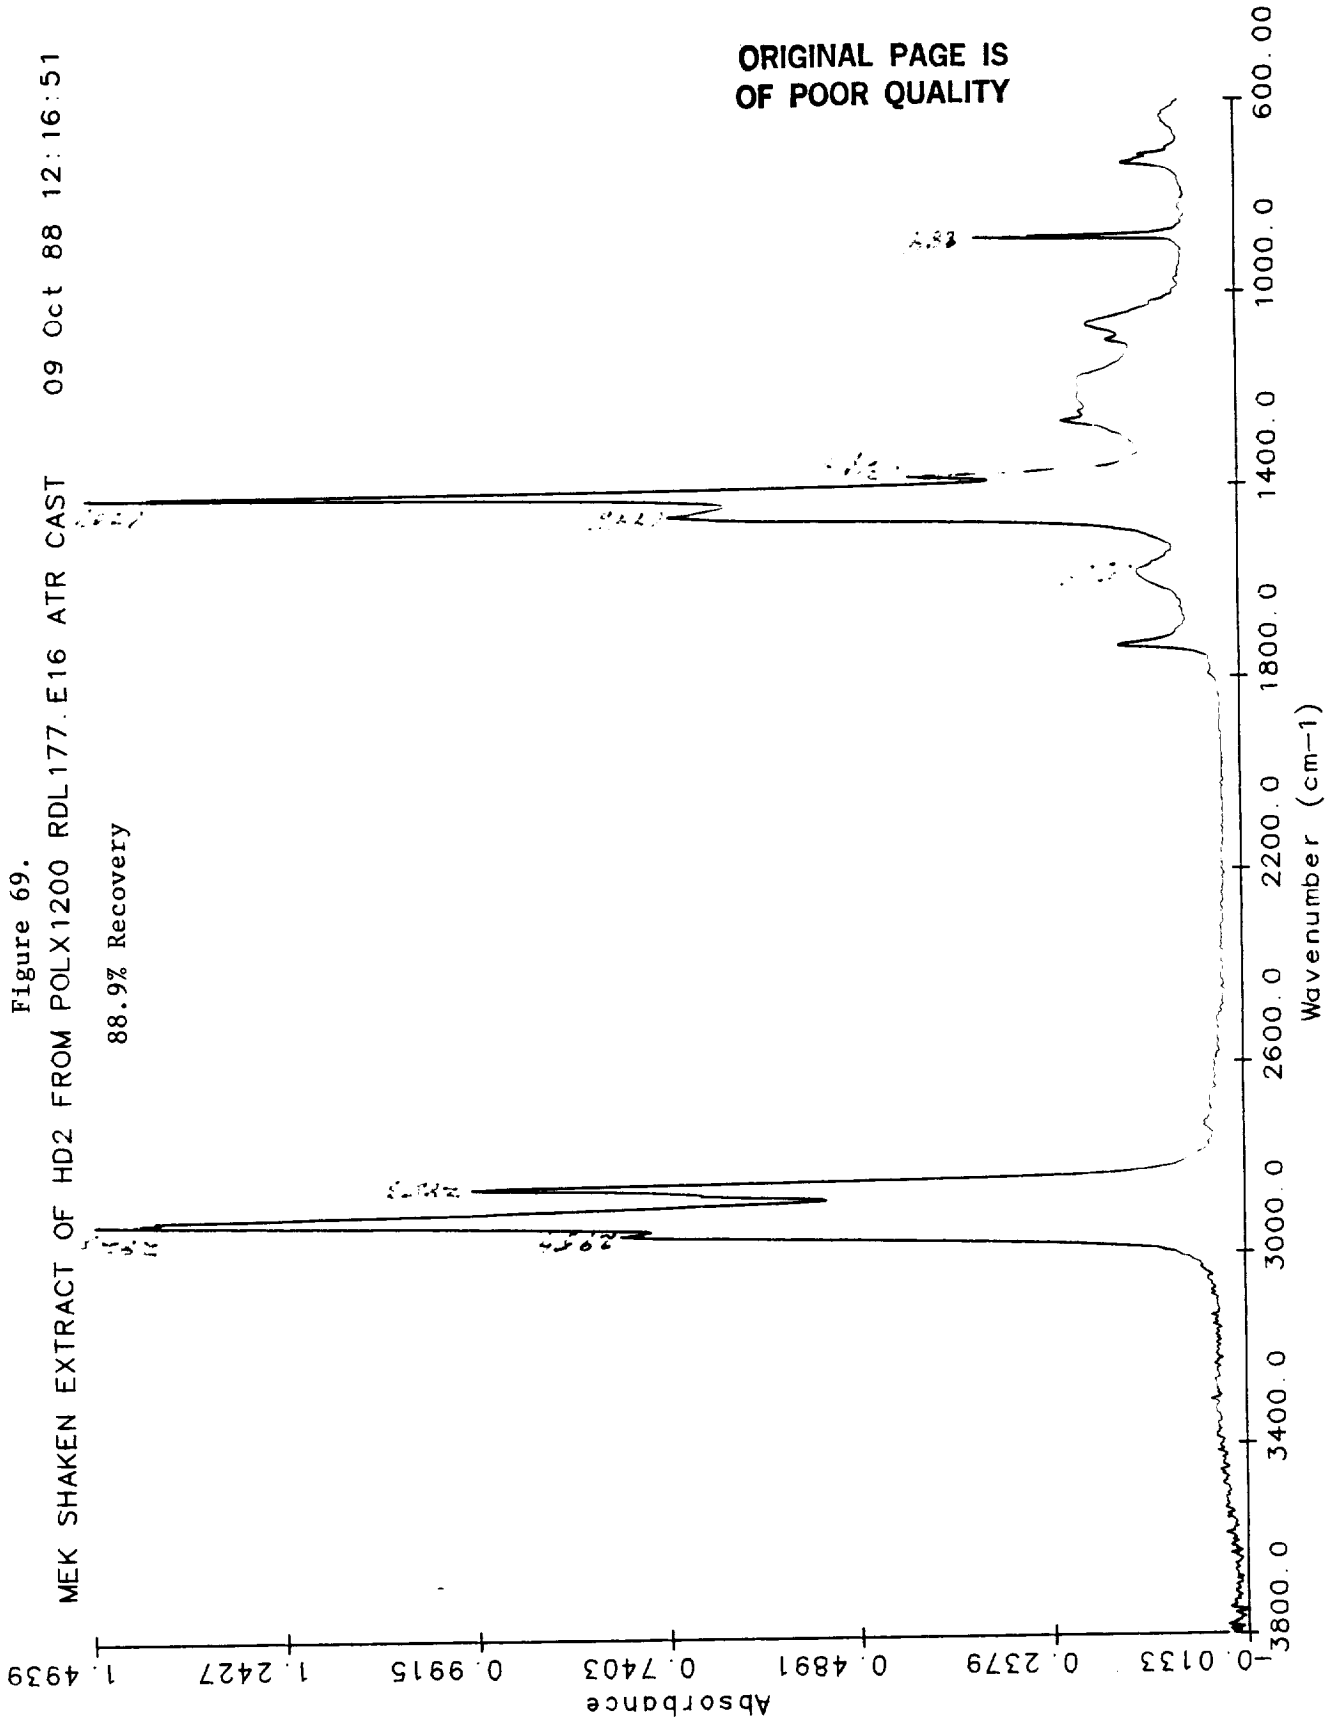


Figure 70.

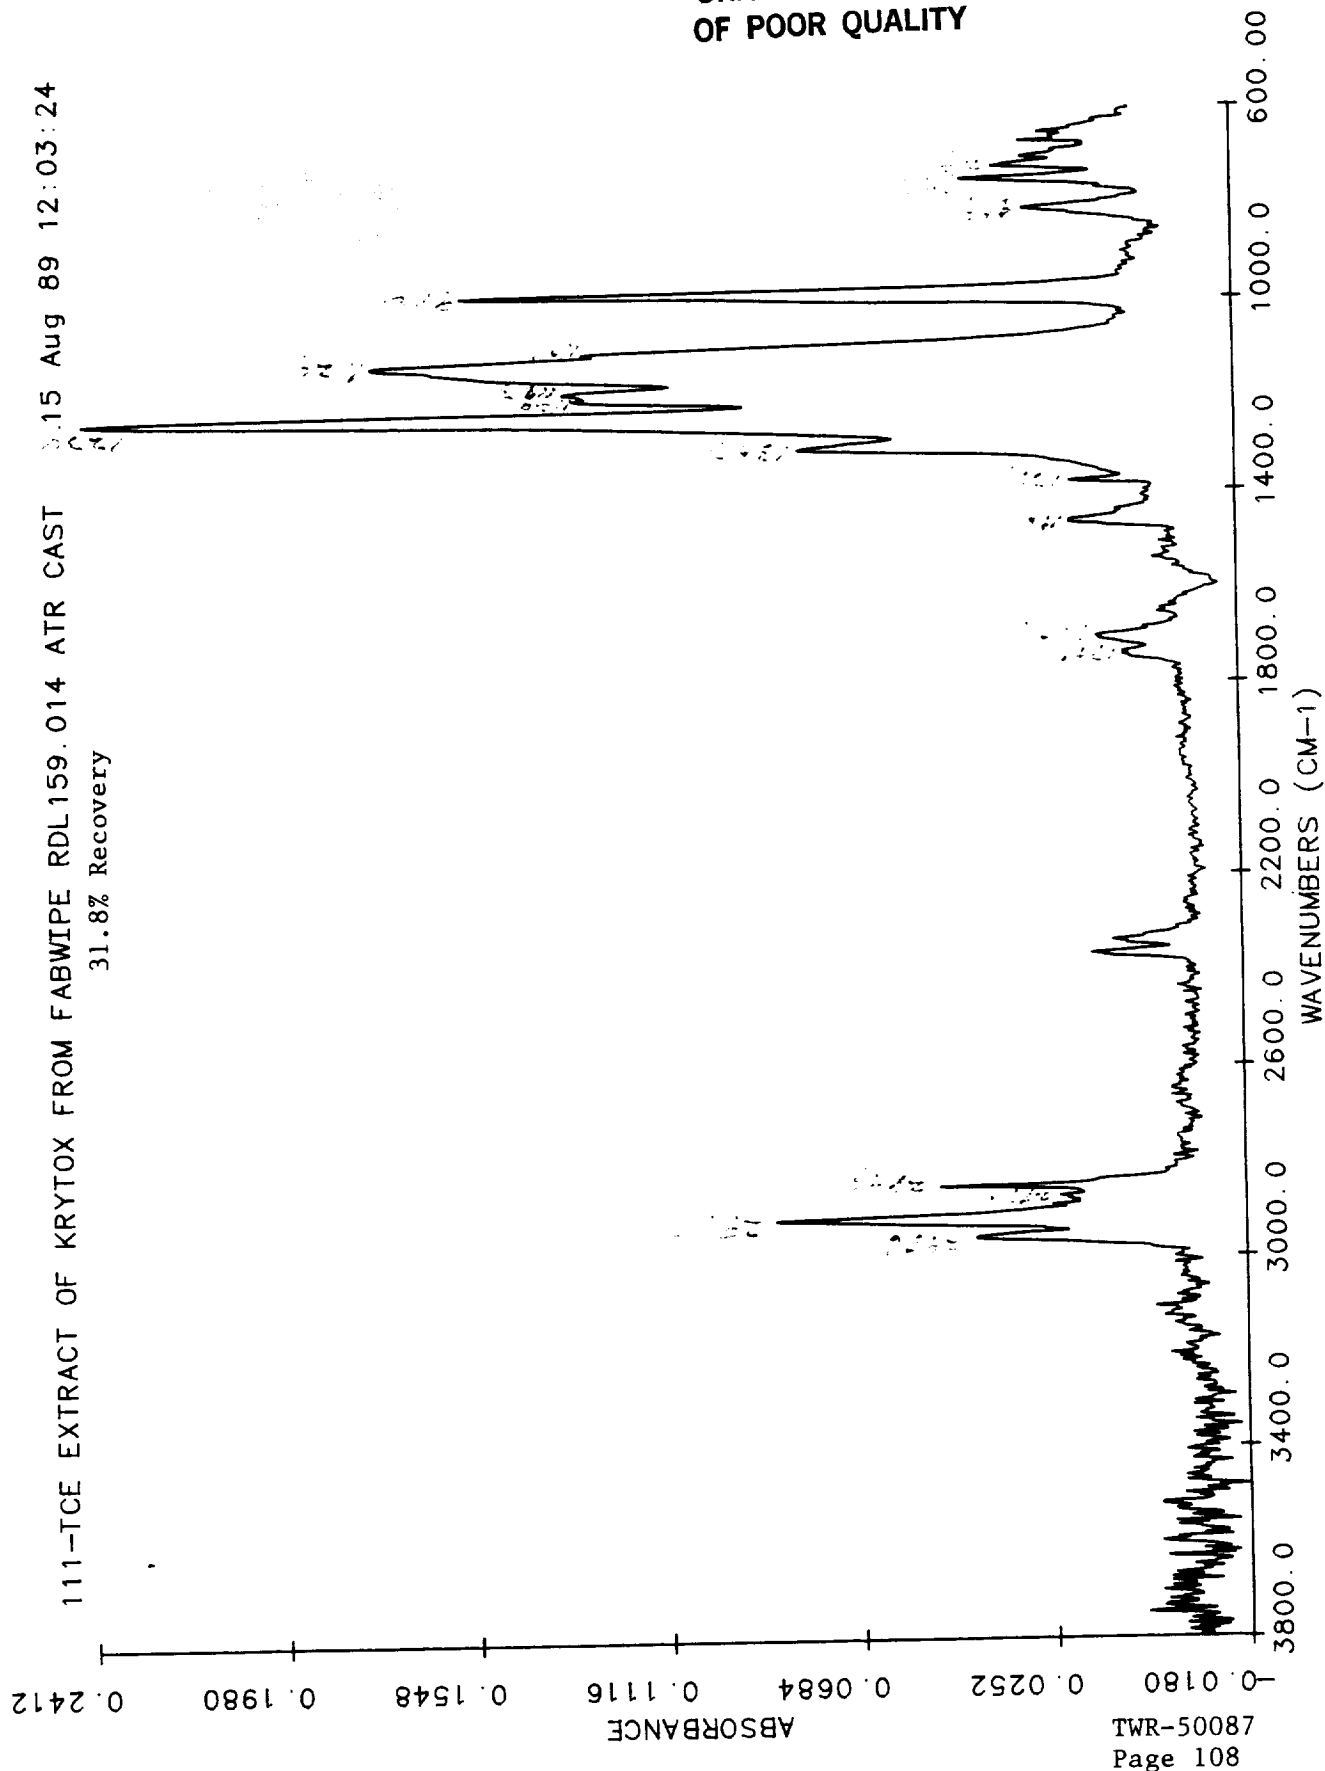


Figure 71.

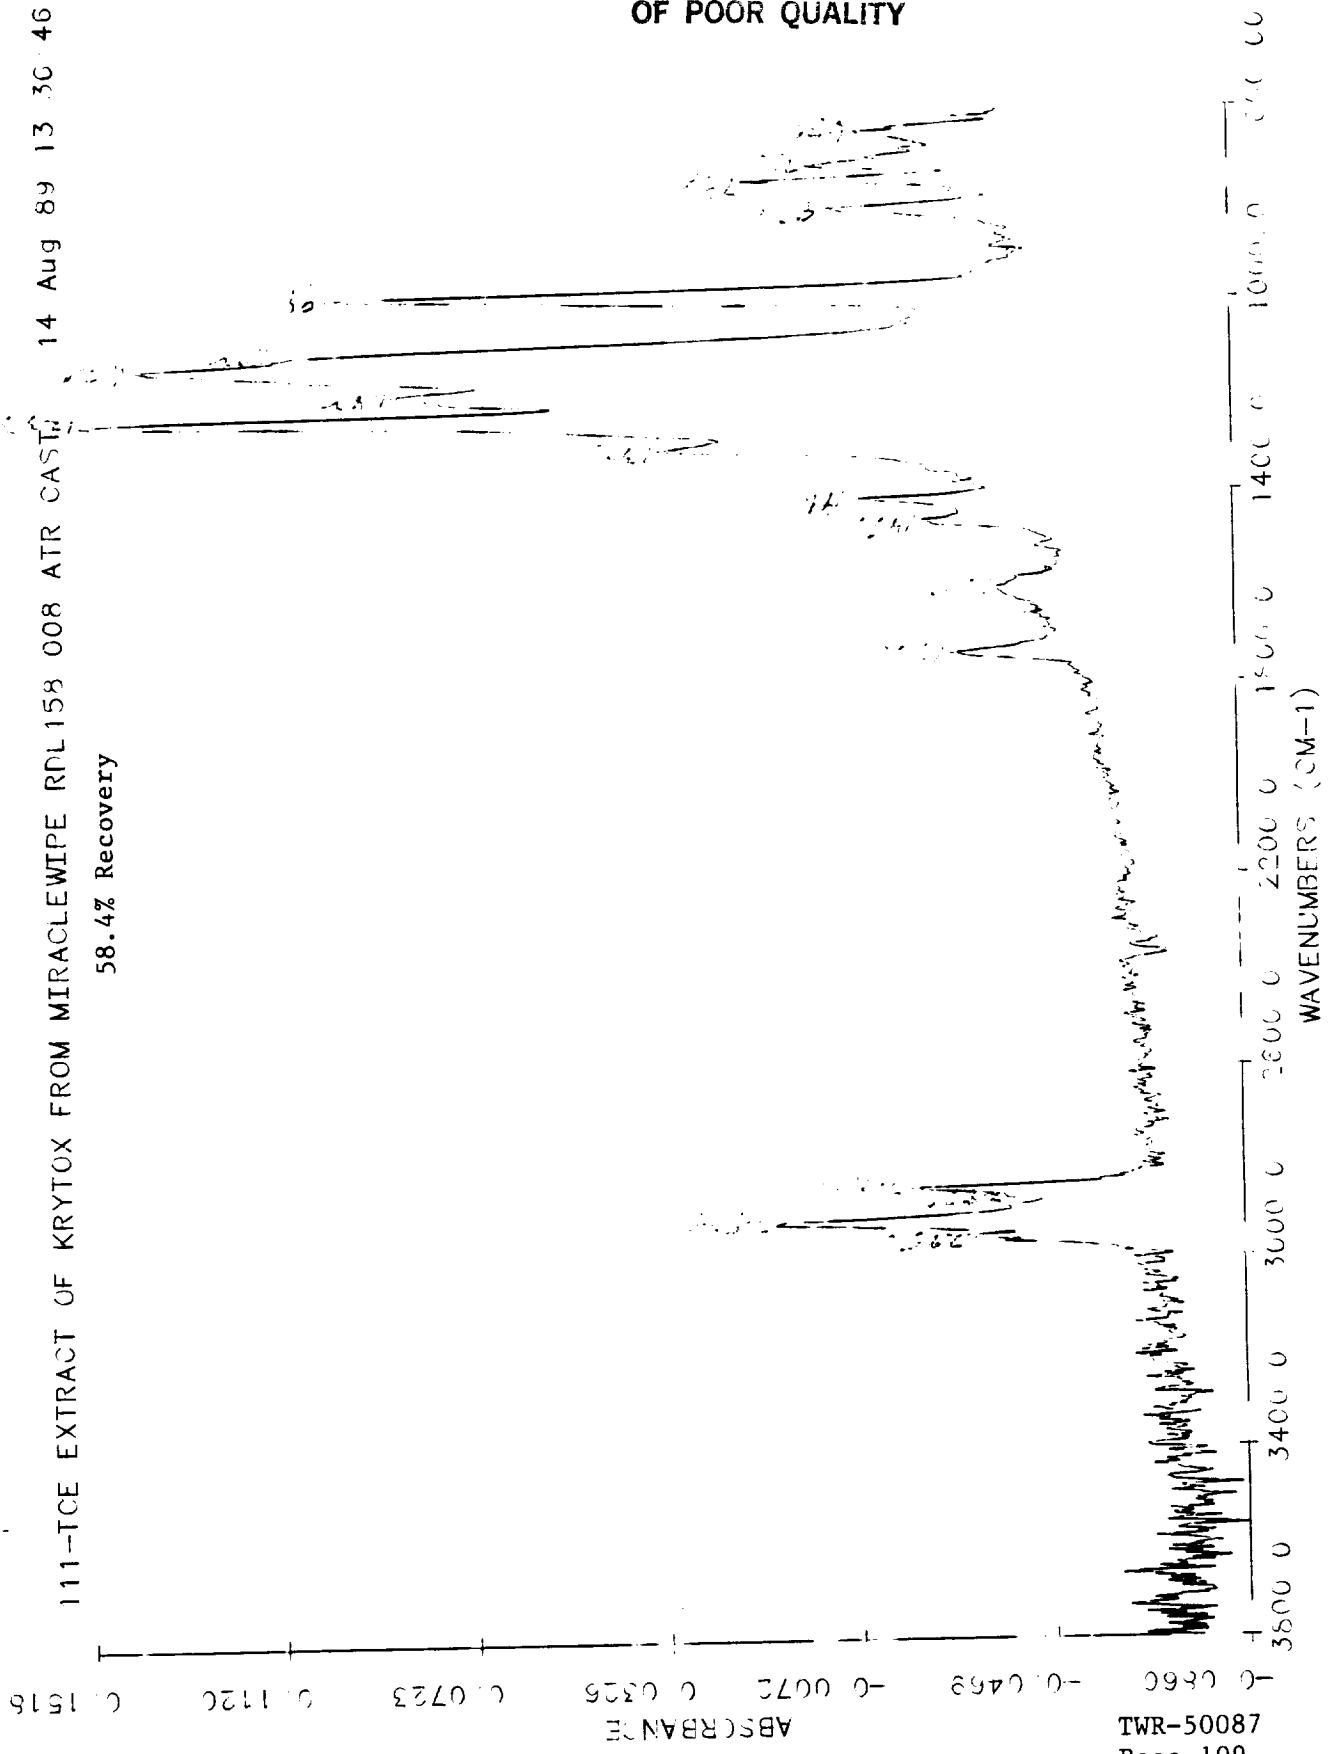


Figure 72.

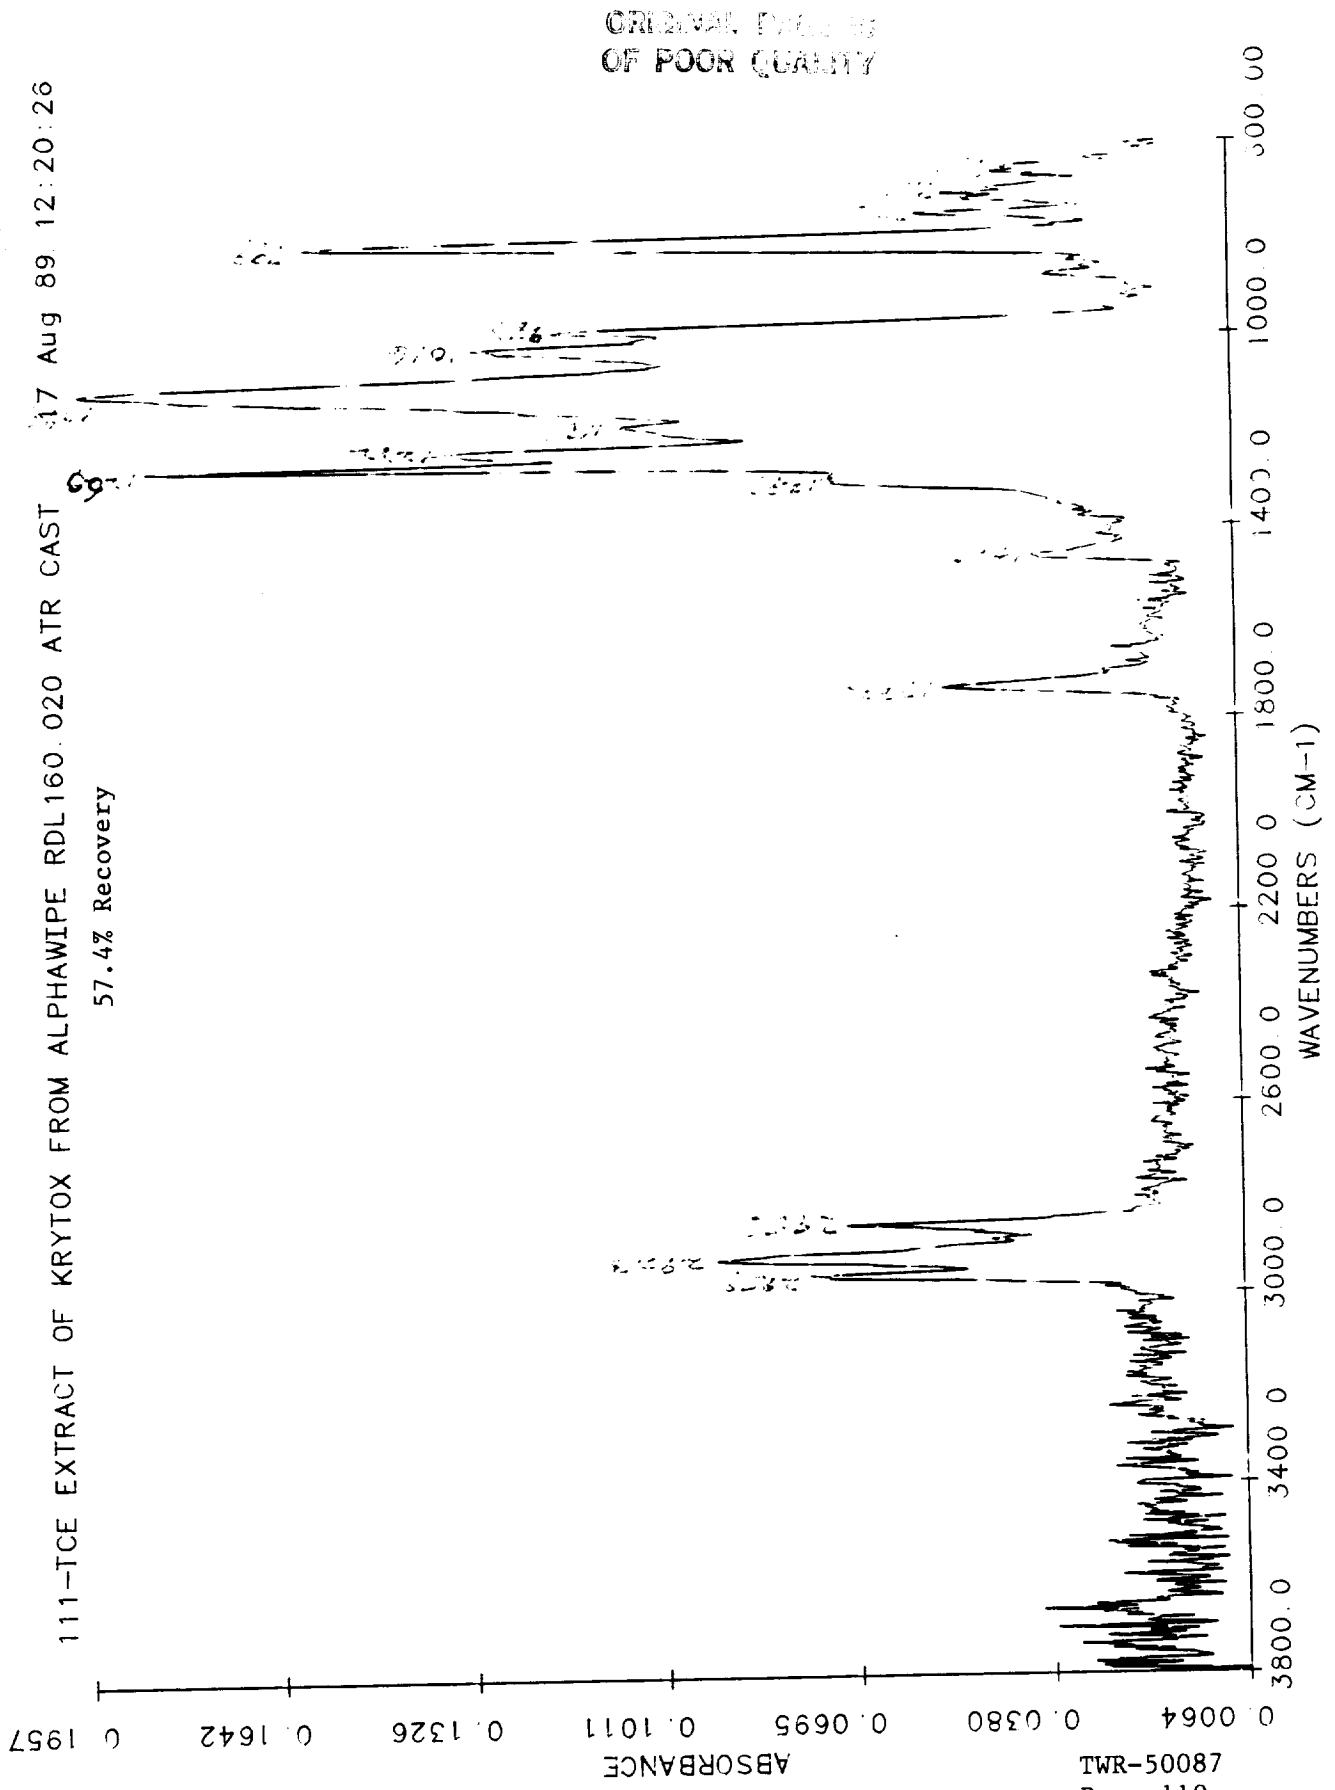


Figure 73.


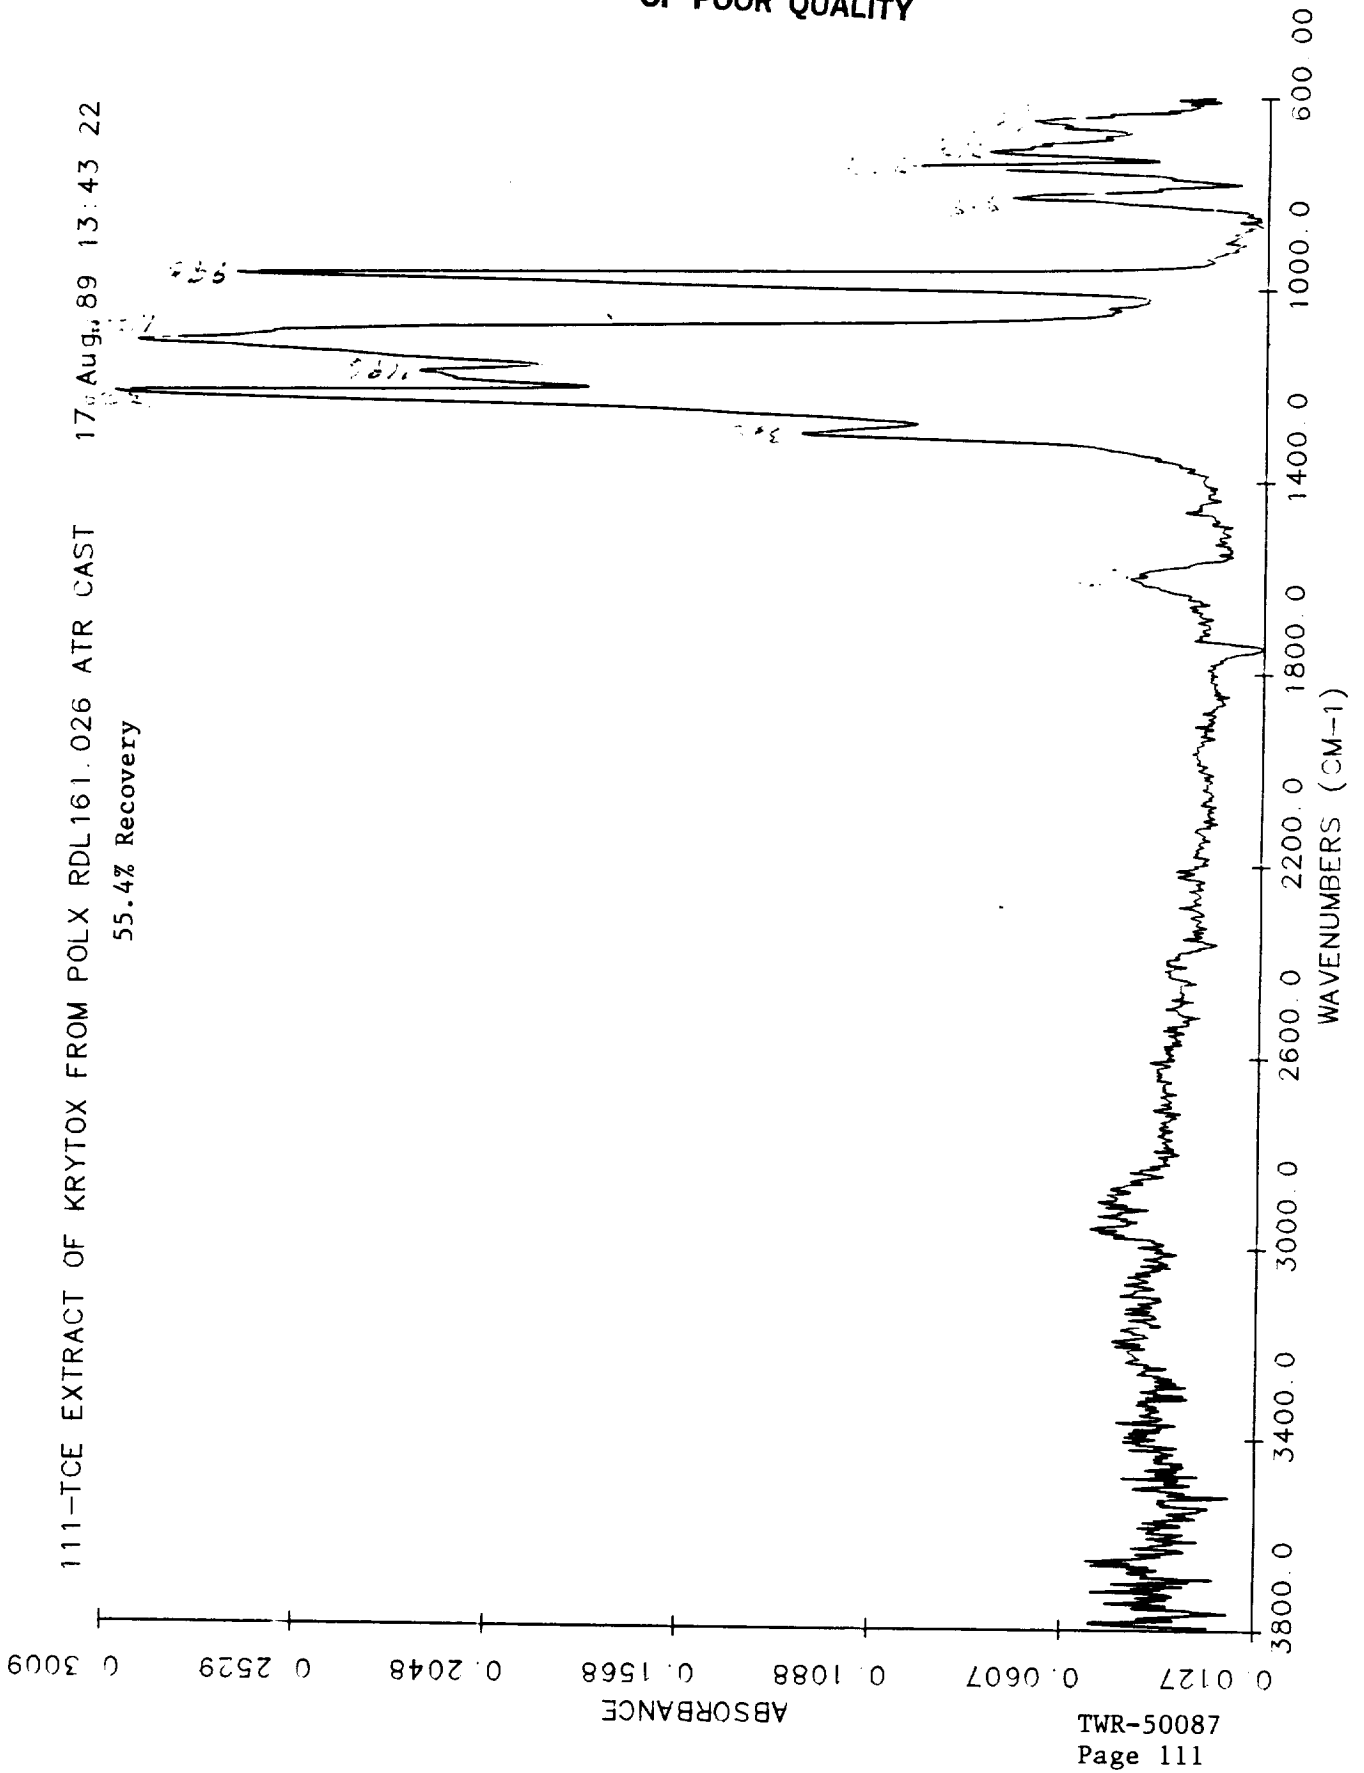


Figure 74.

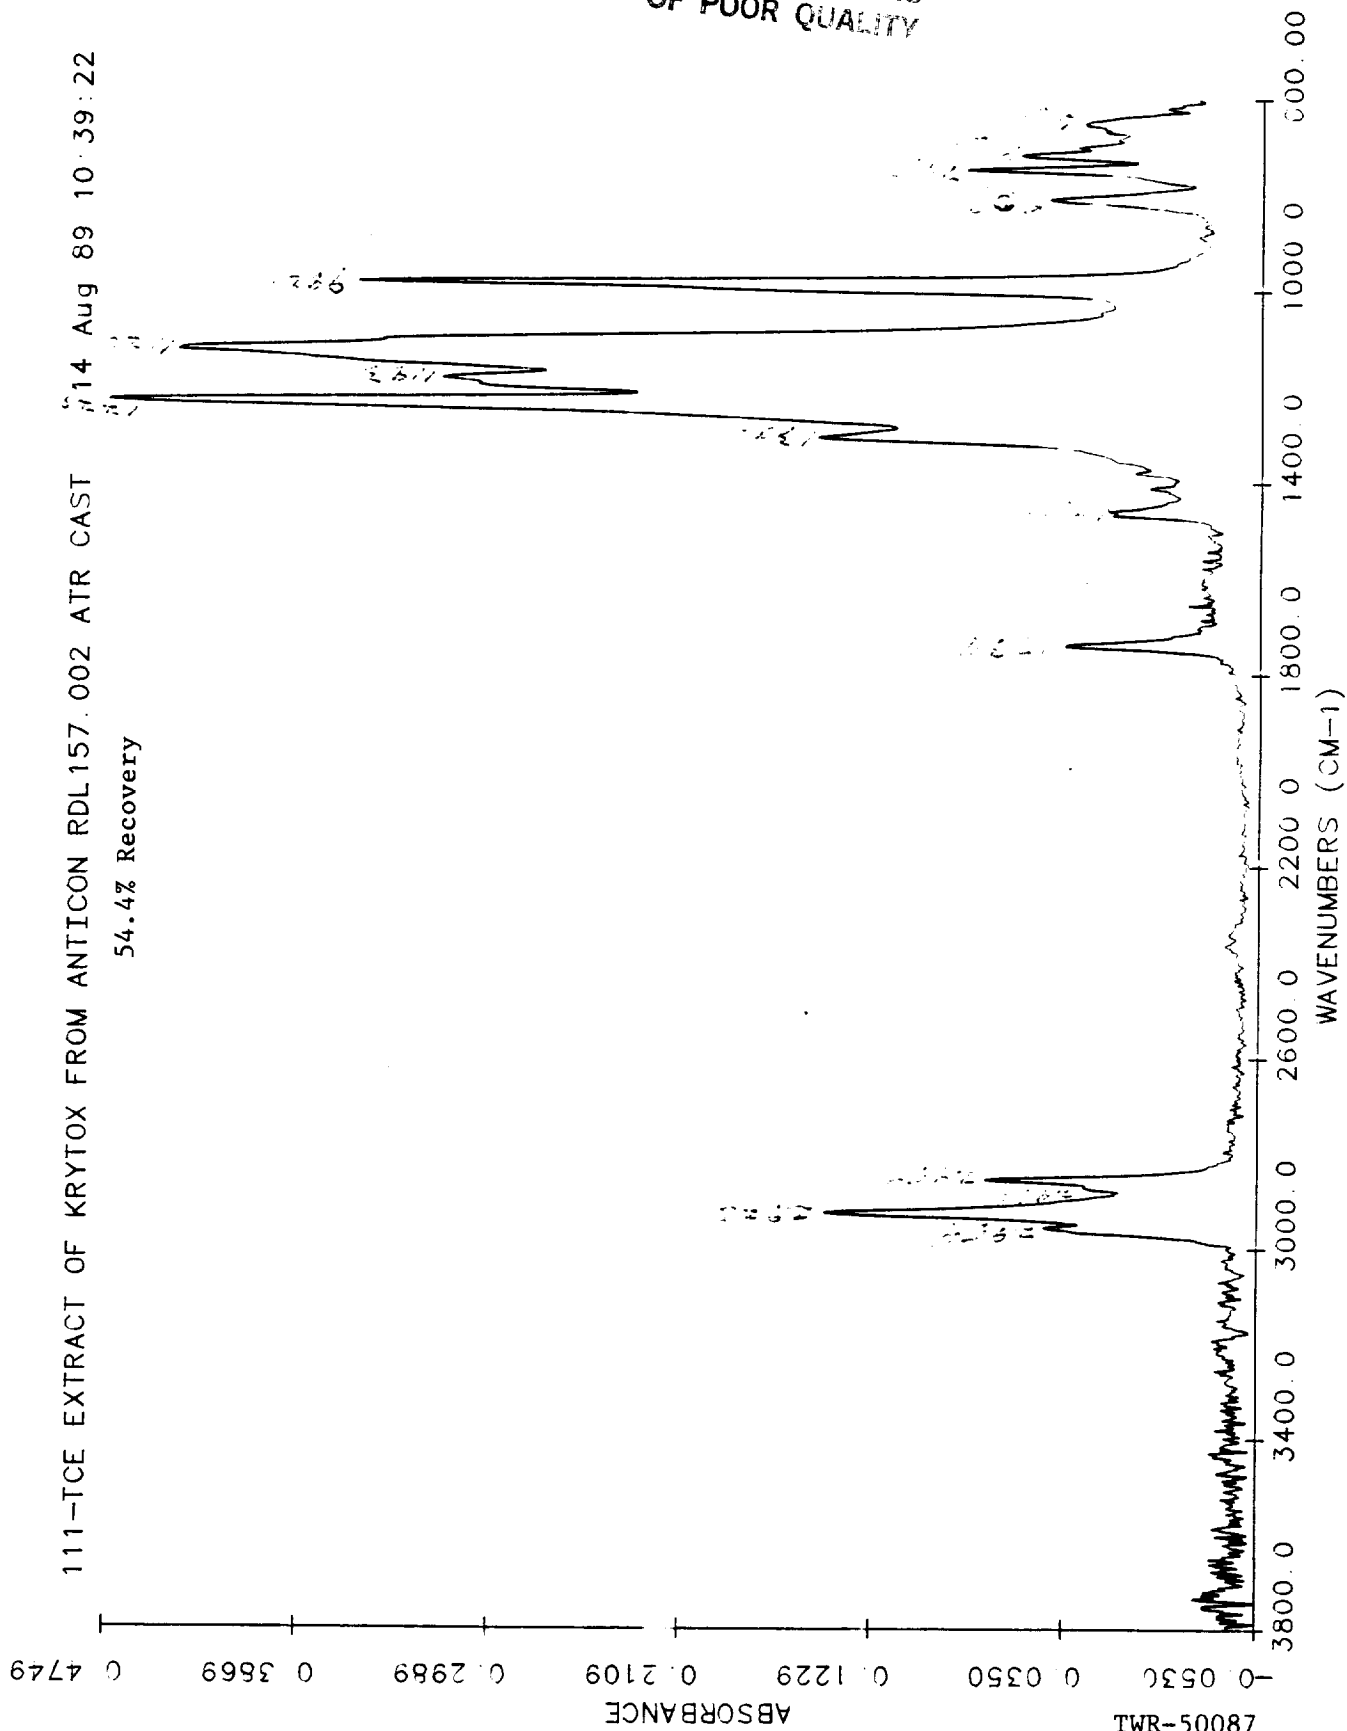

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 75.


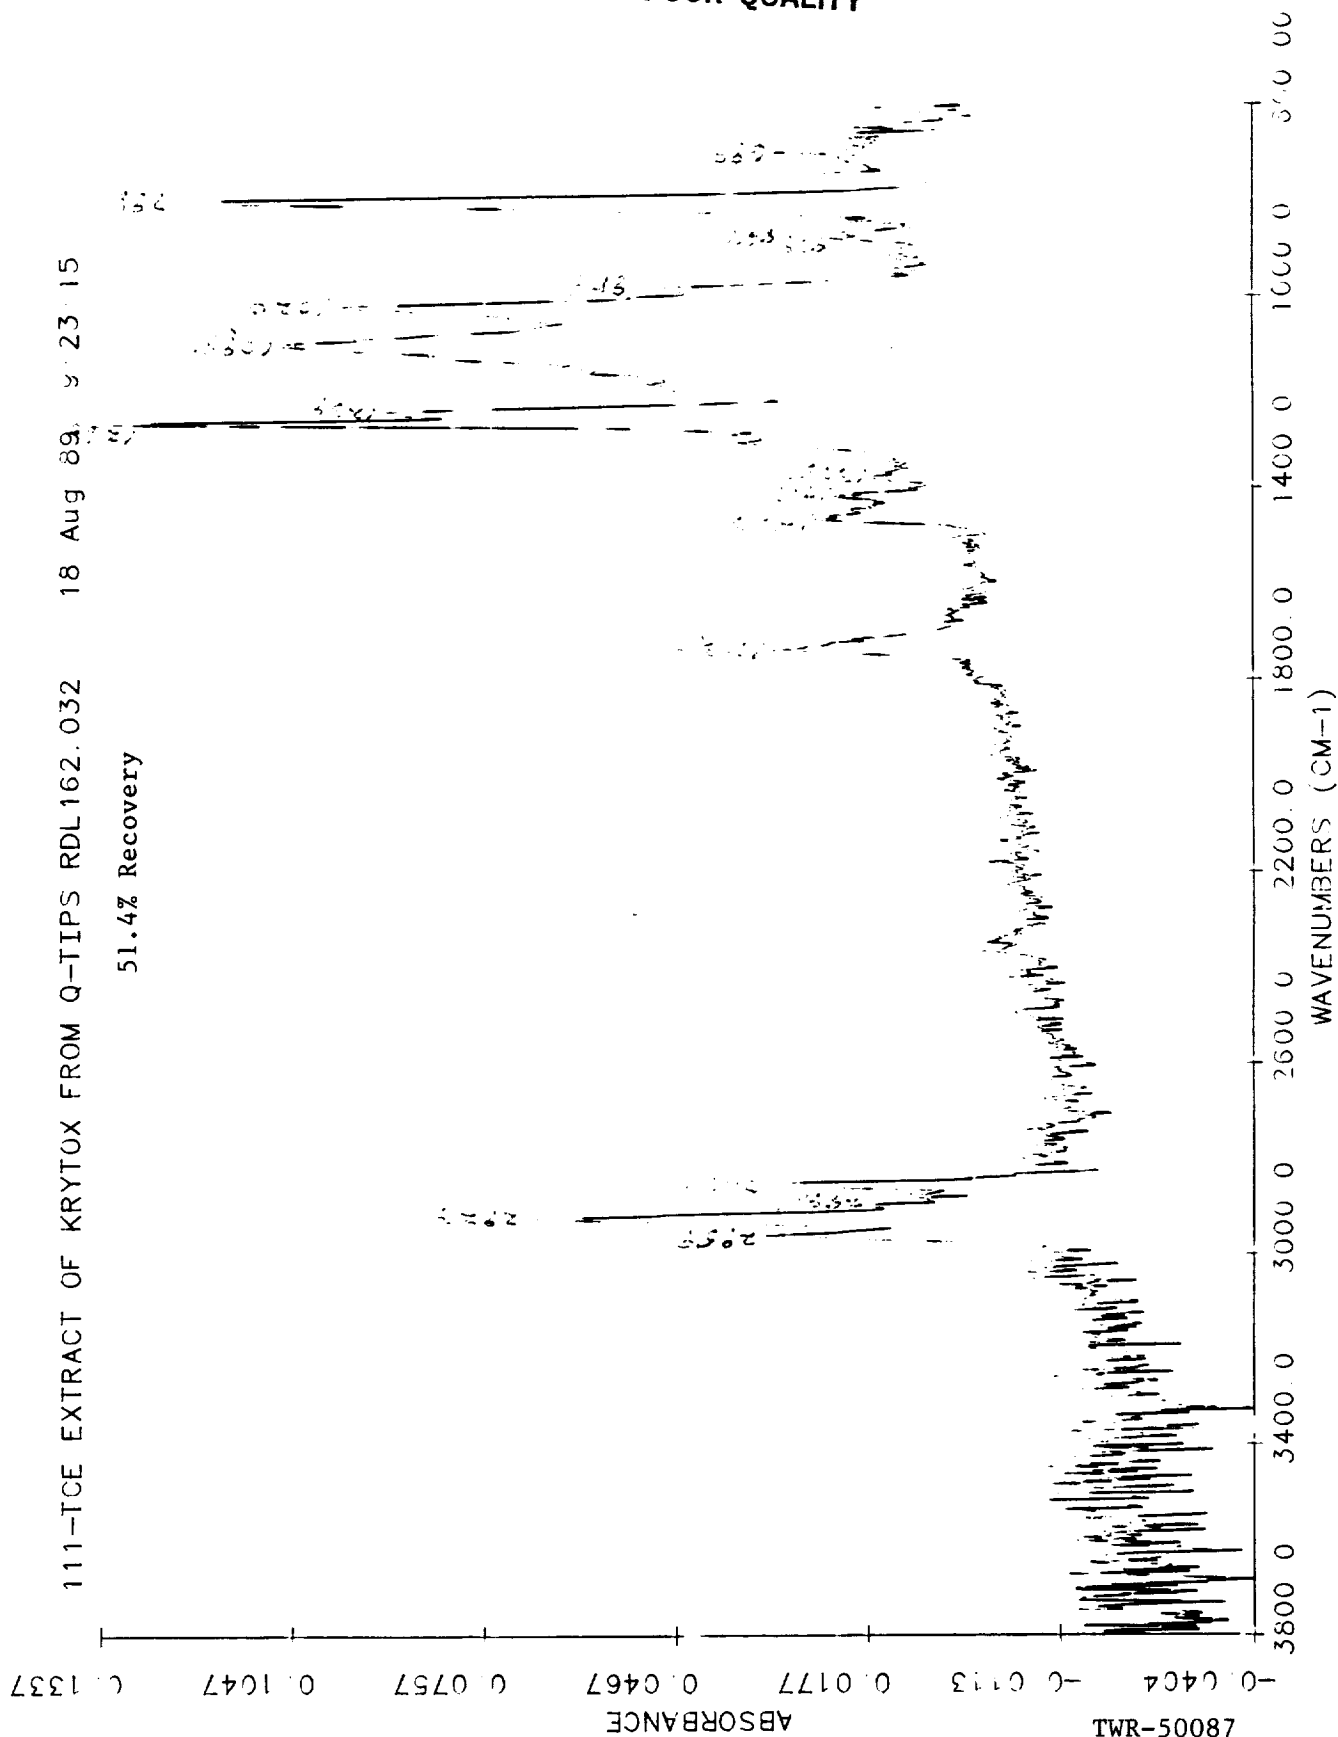


Figure 76.
FREON TF EXTRACT OF KRYTOX FROM FABWIPE RDL165.B29 ATR CAST 28 Aug 89 13:49:11

88.0% Recovery

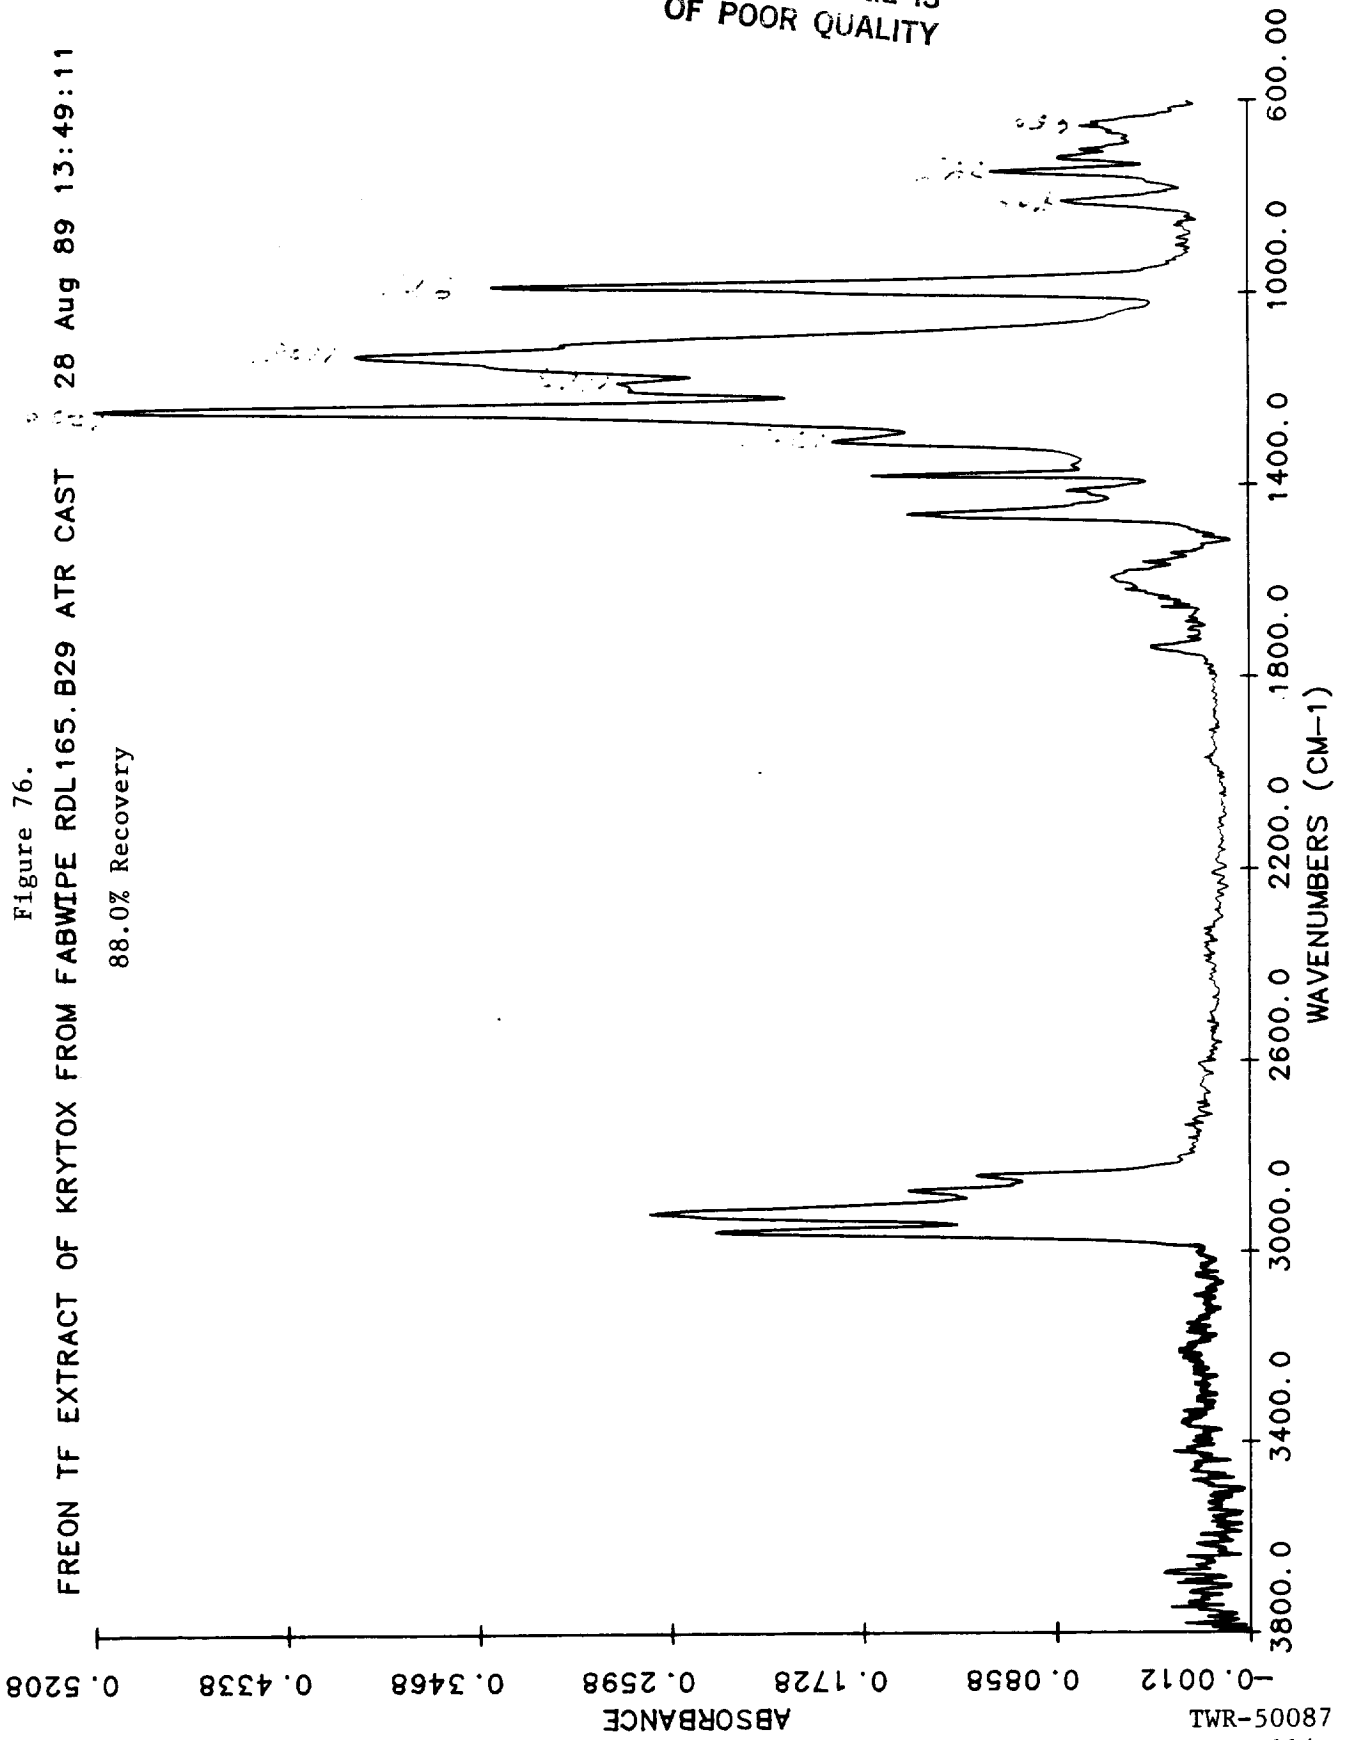

ORIGINAL PAGE IS
OF POOR QUALITY

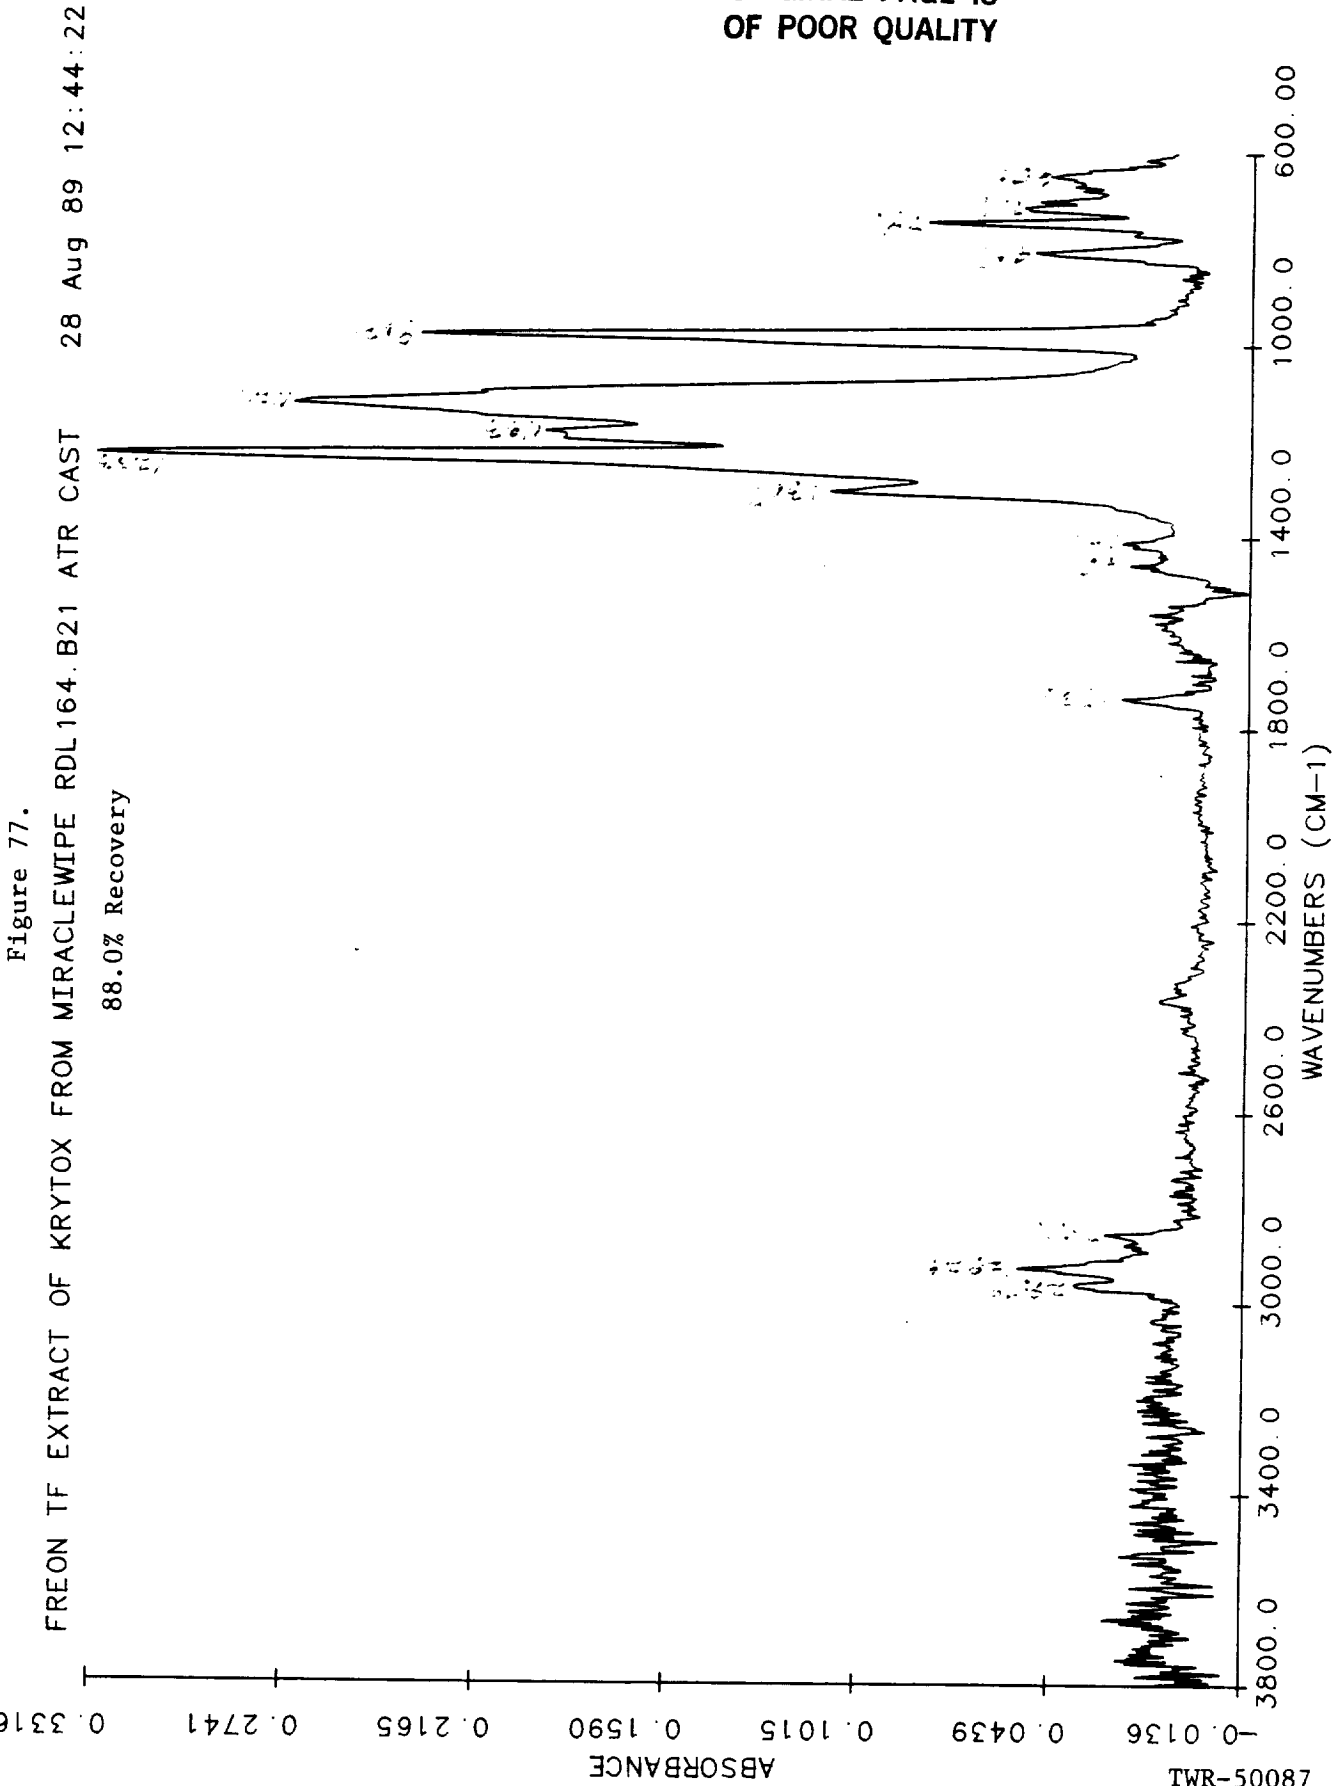


Figure 78.

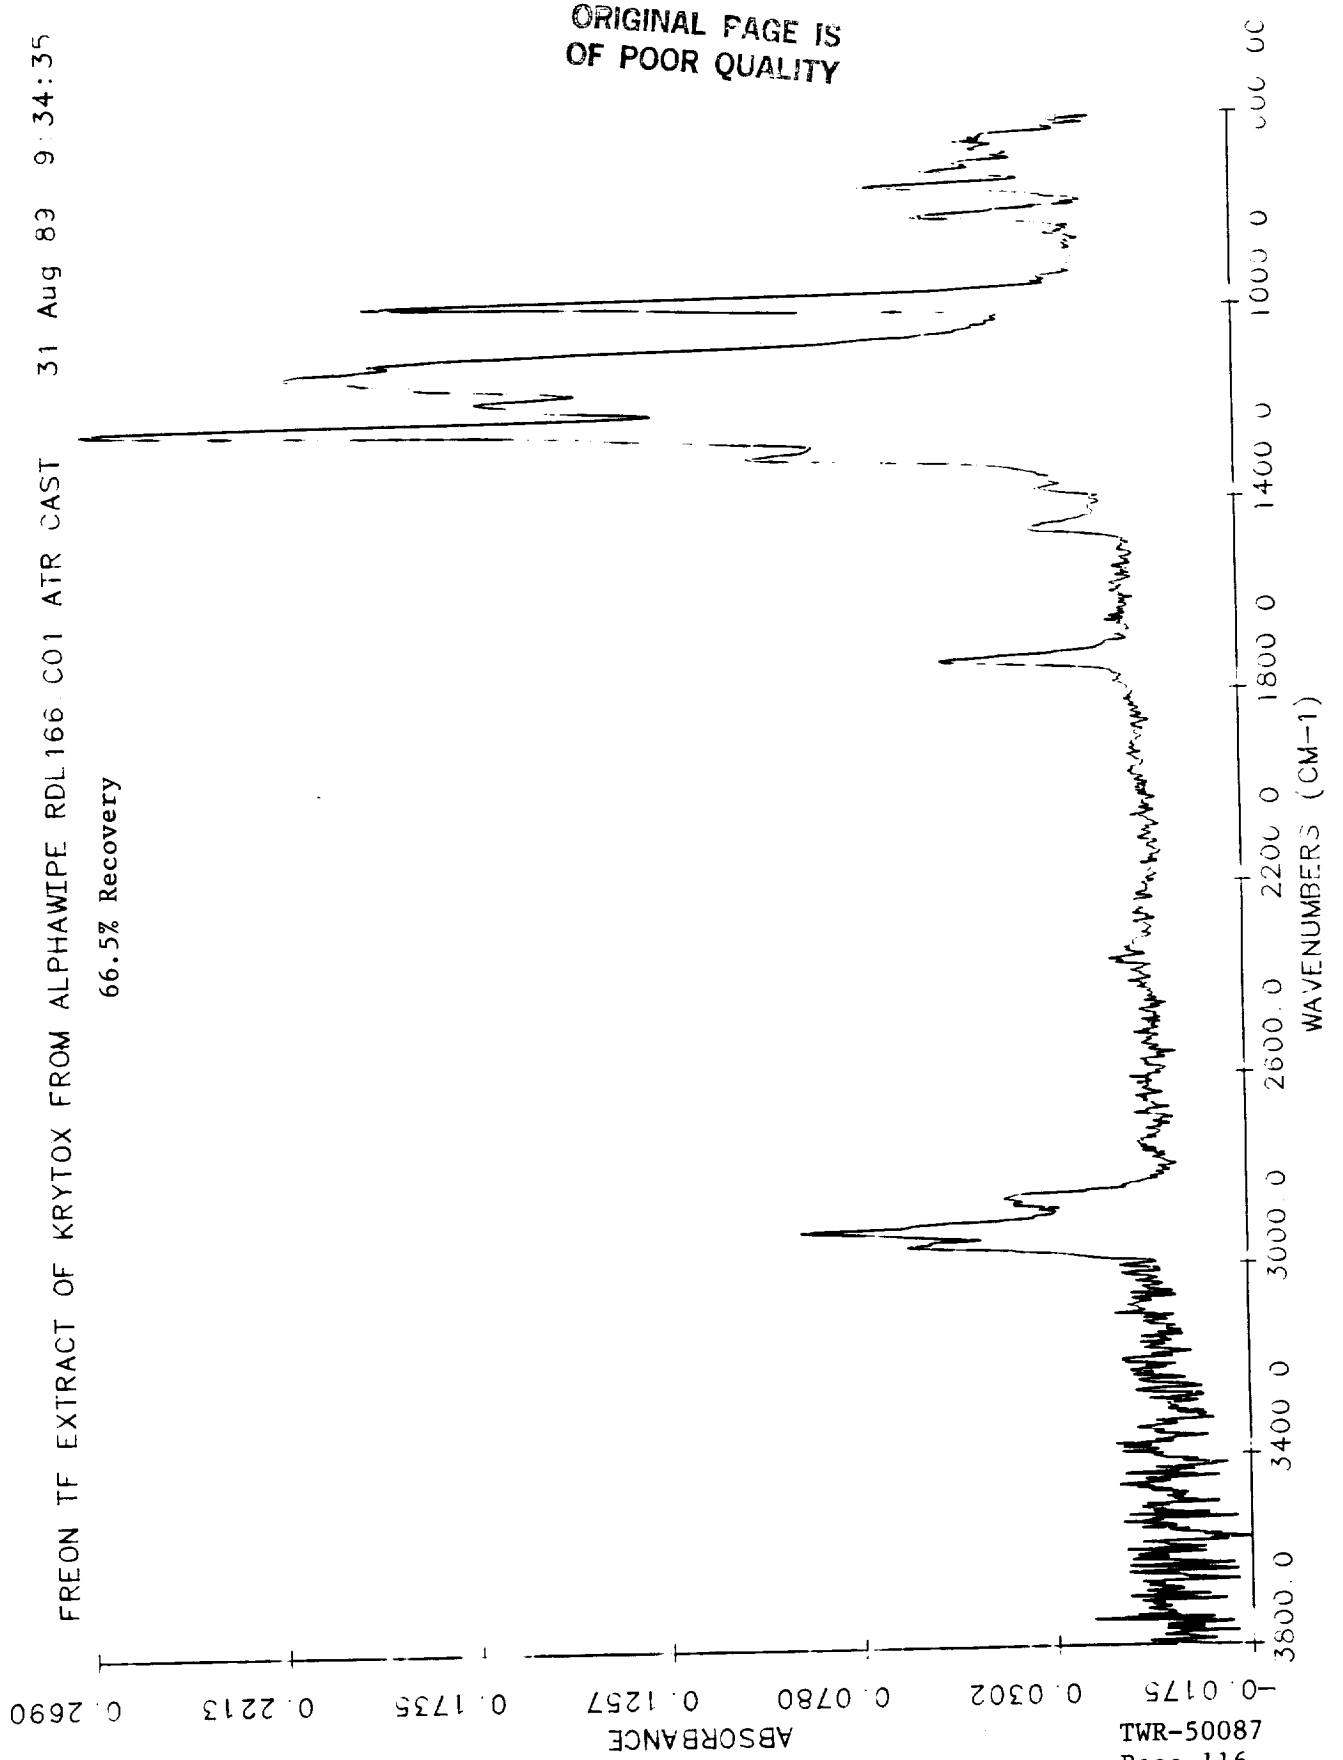


Figure 79.

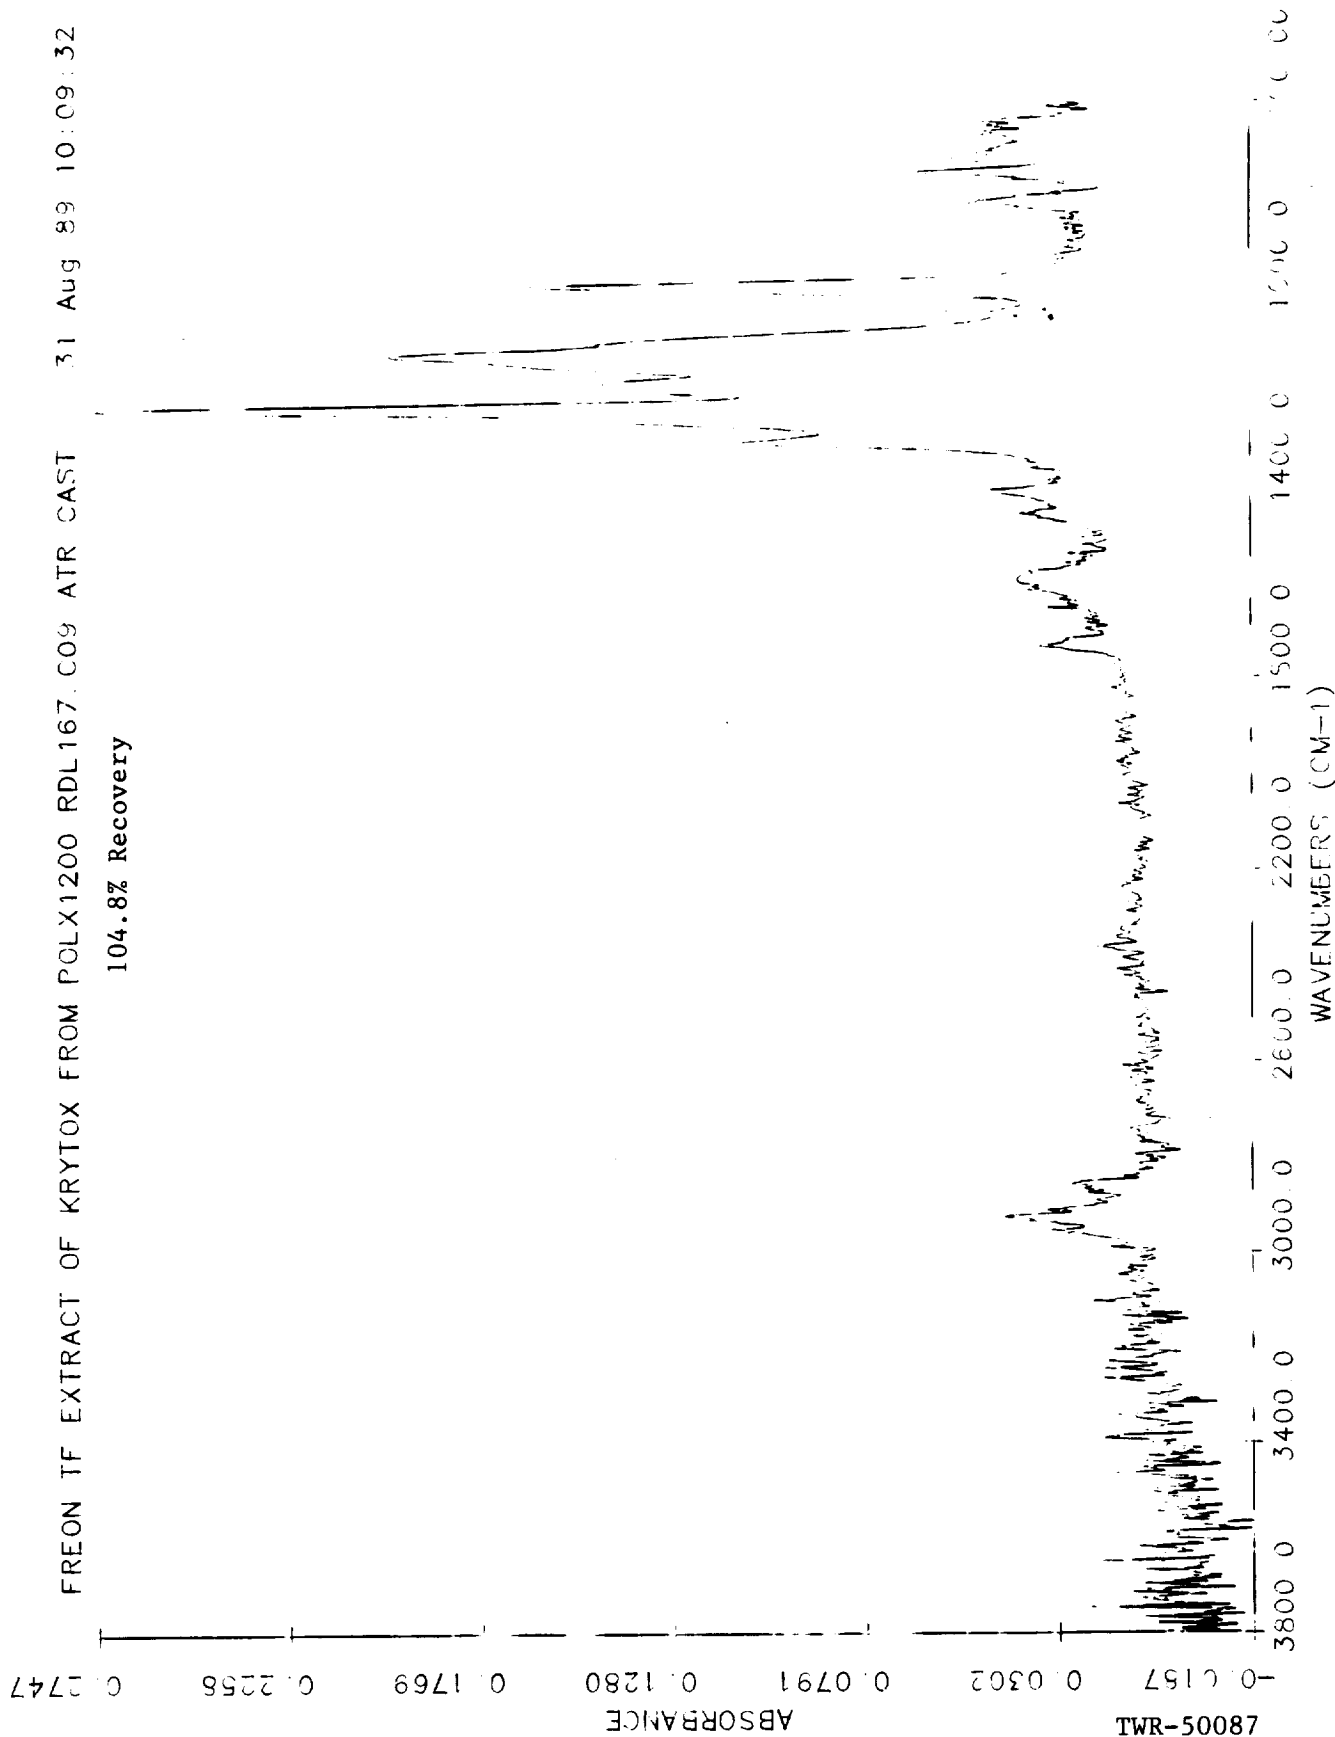


Figure 80.

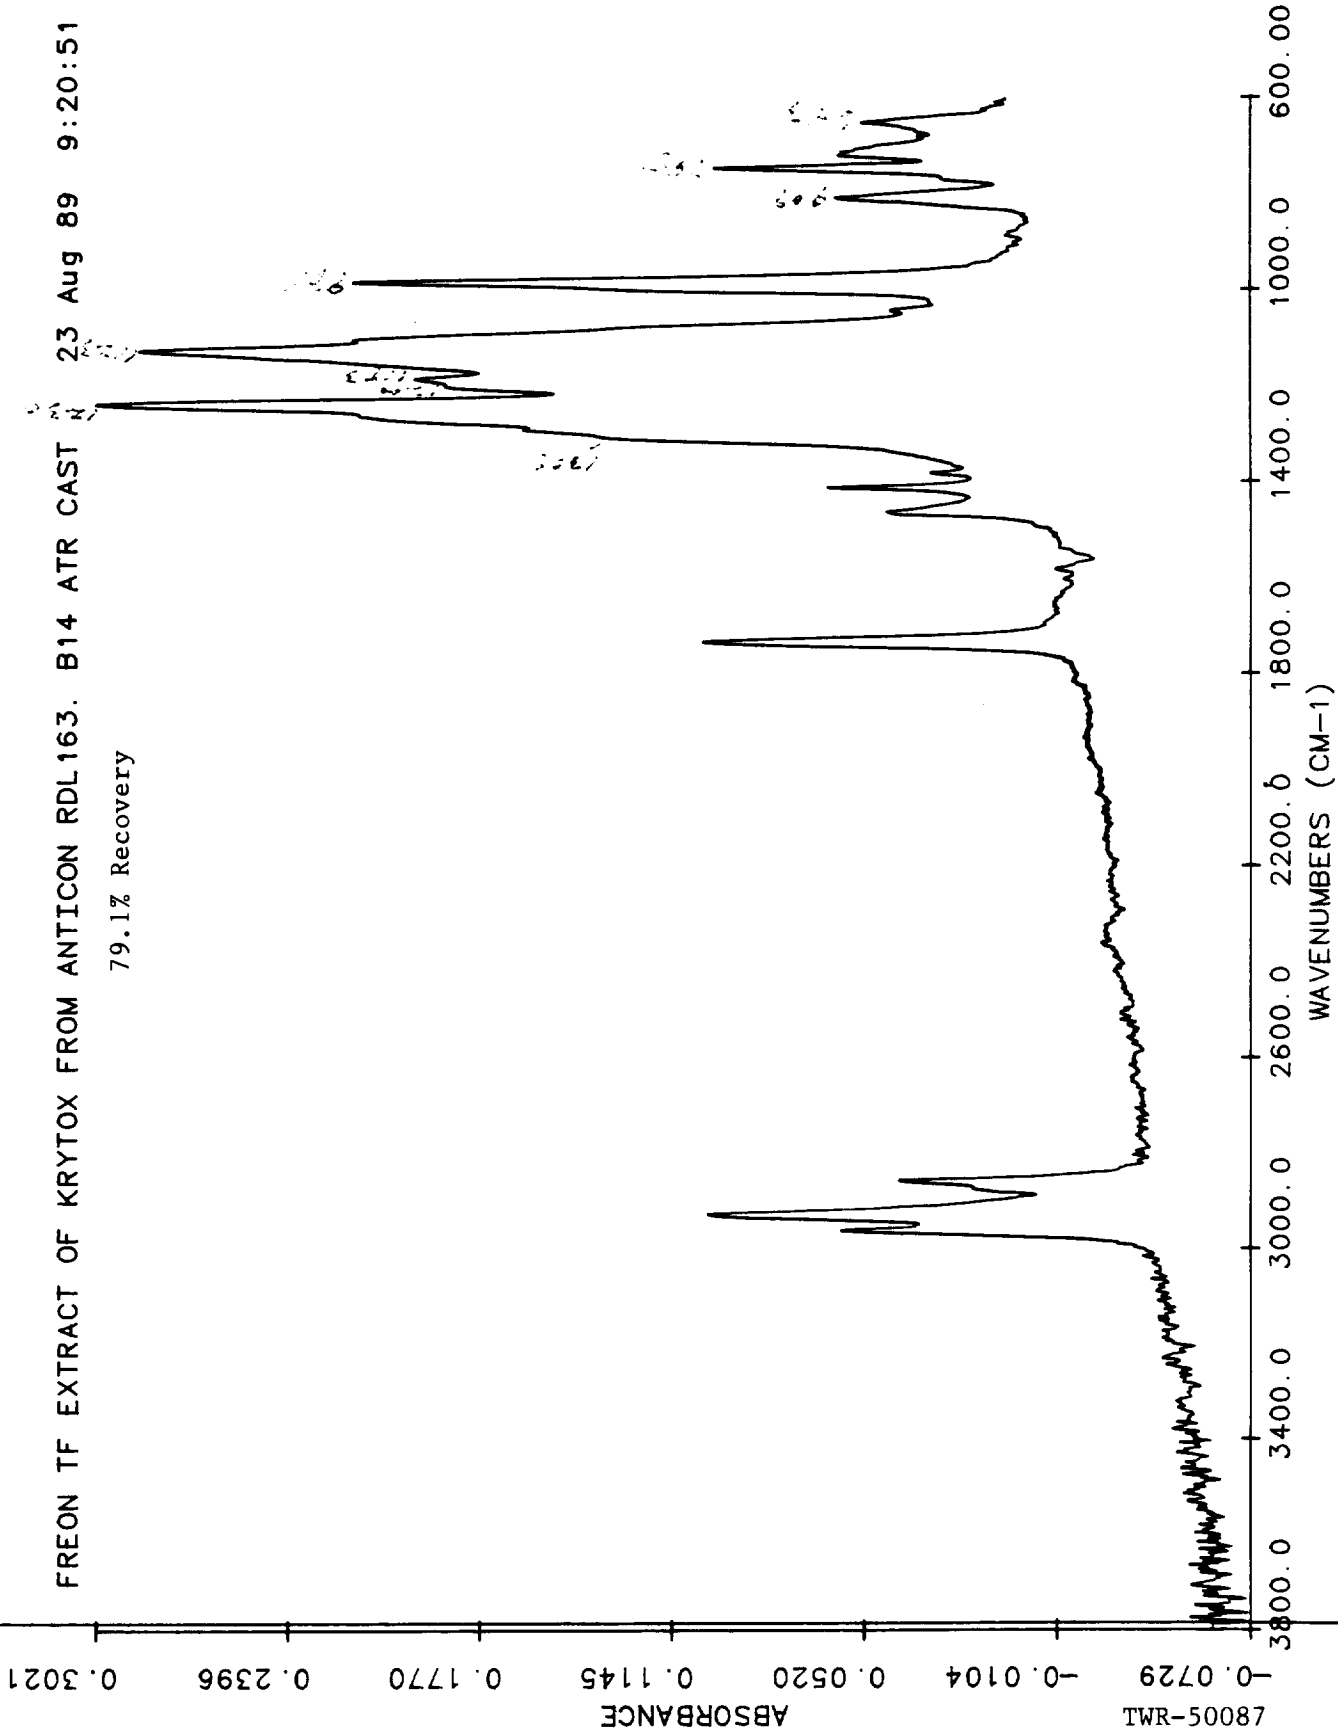


Figure 81.

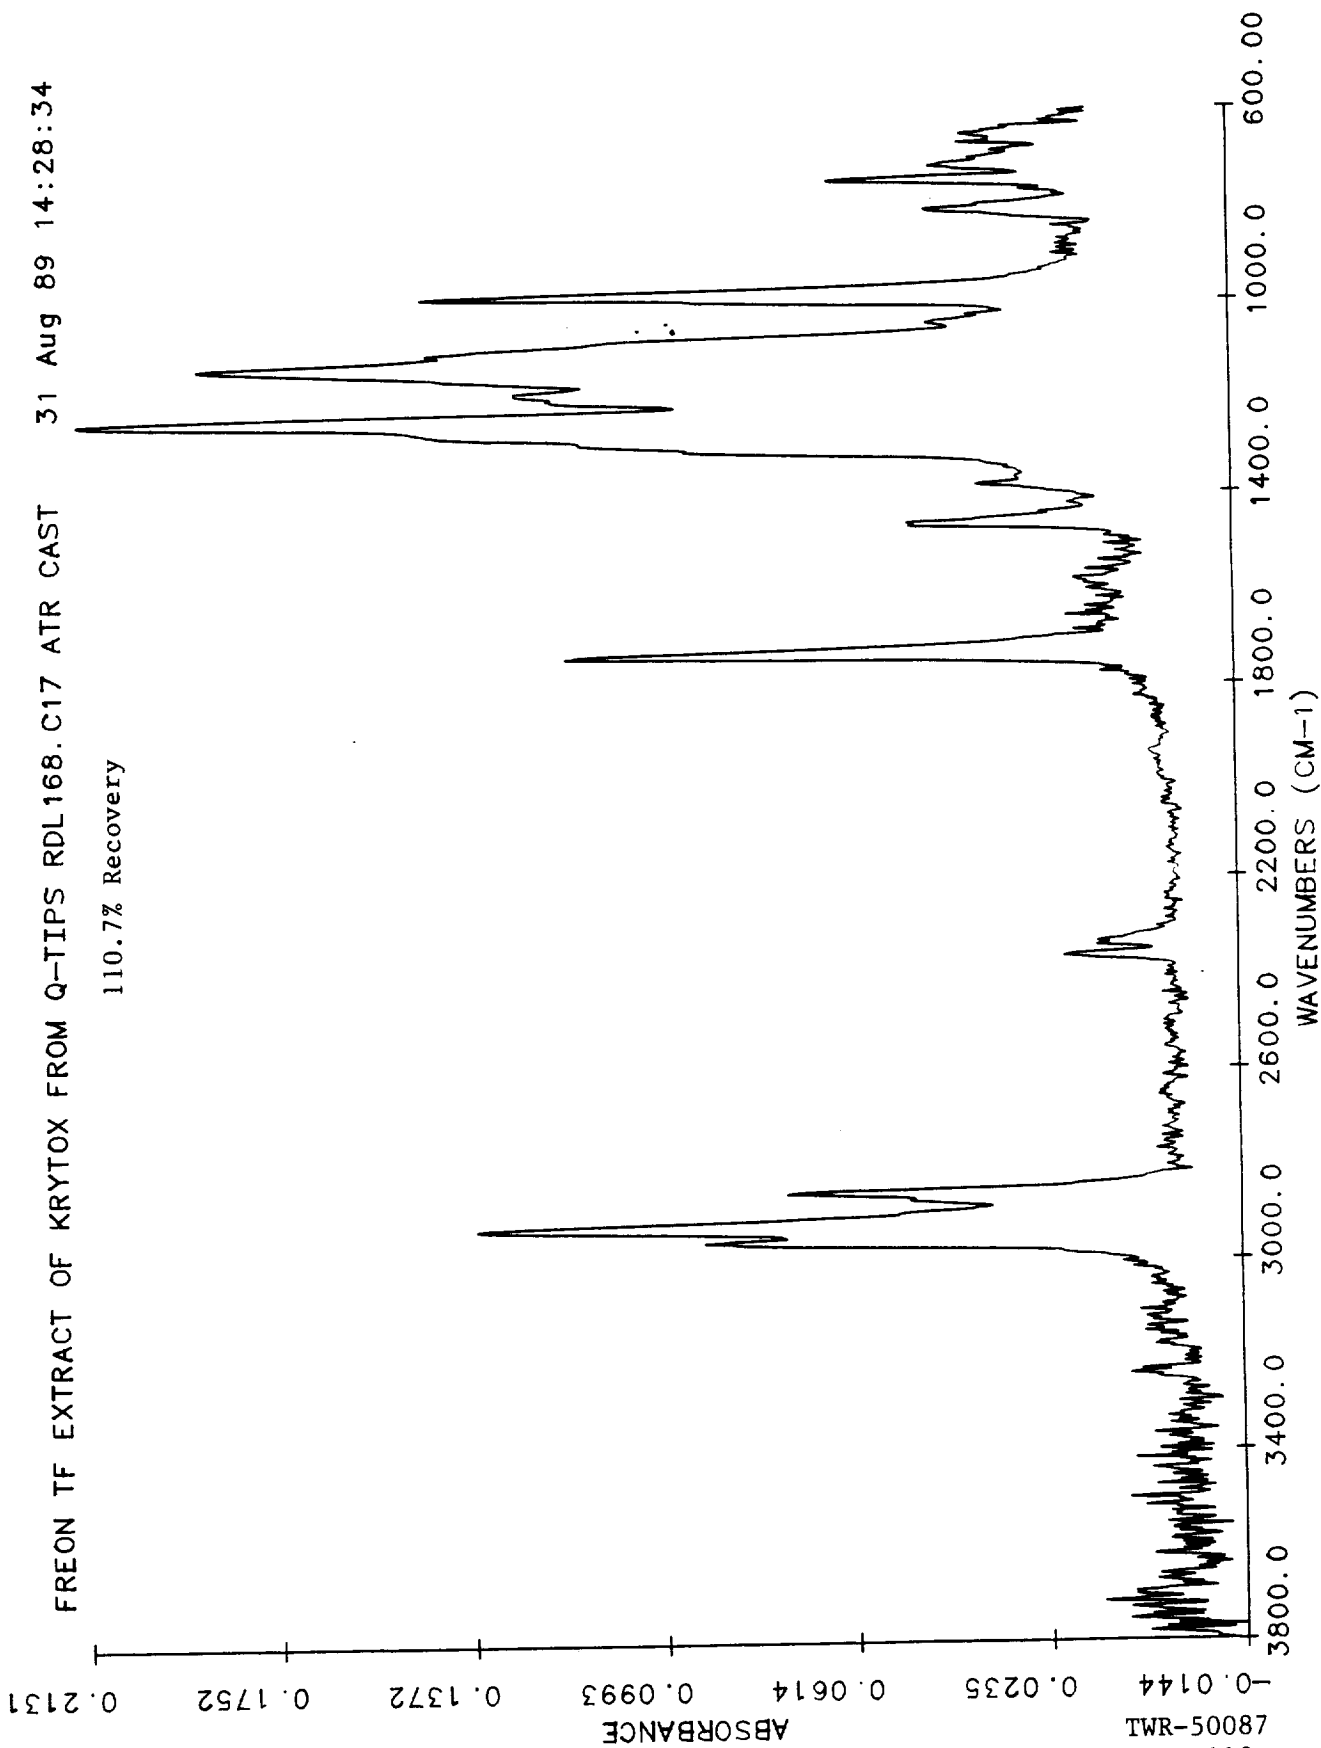


Figure 82.

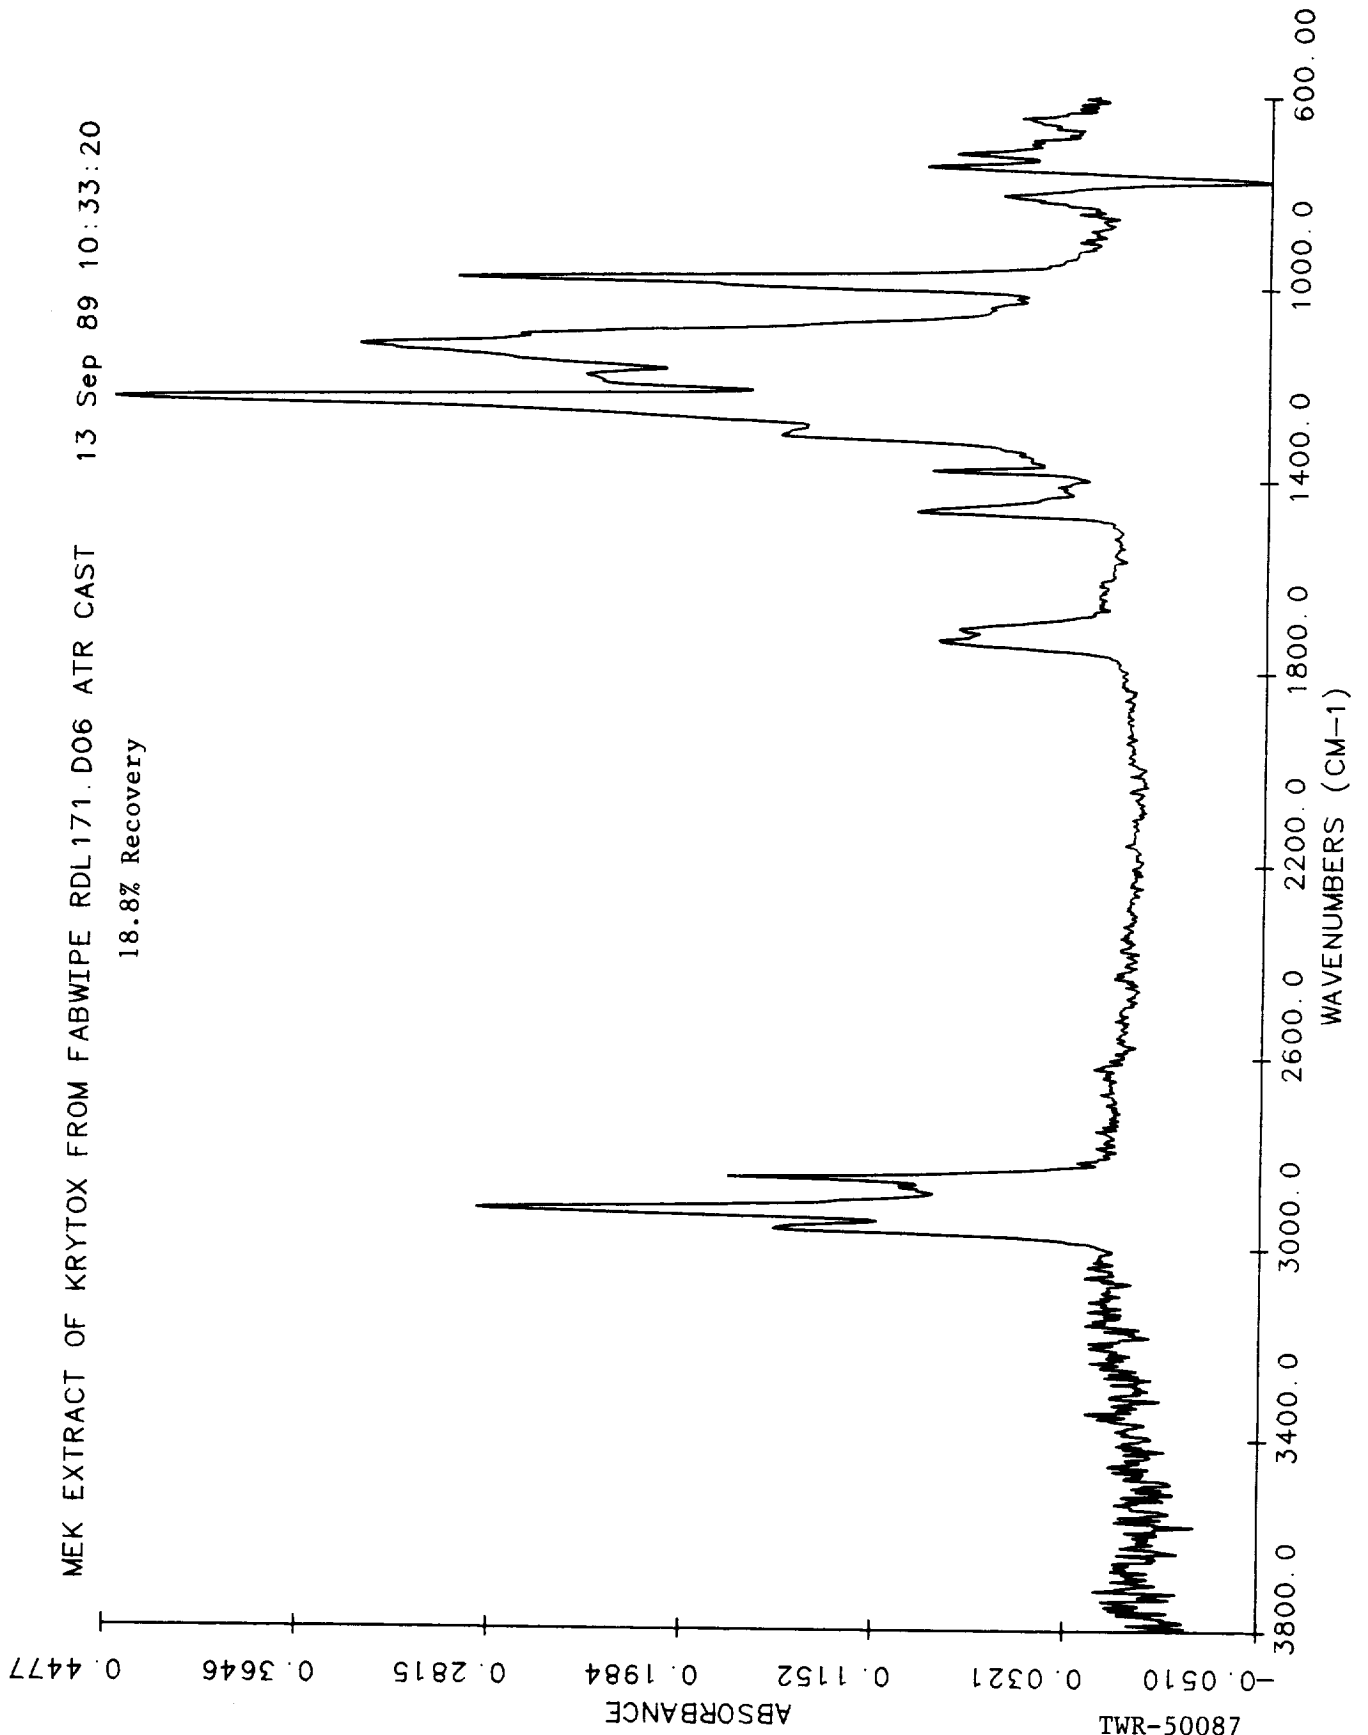


Figure 83.

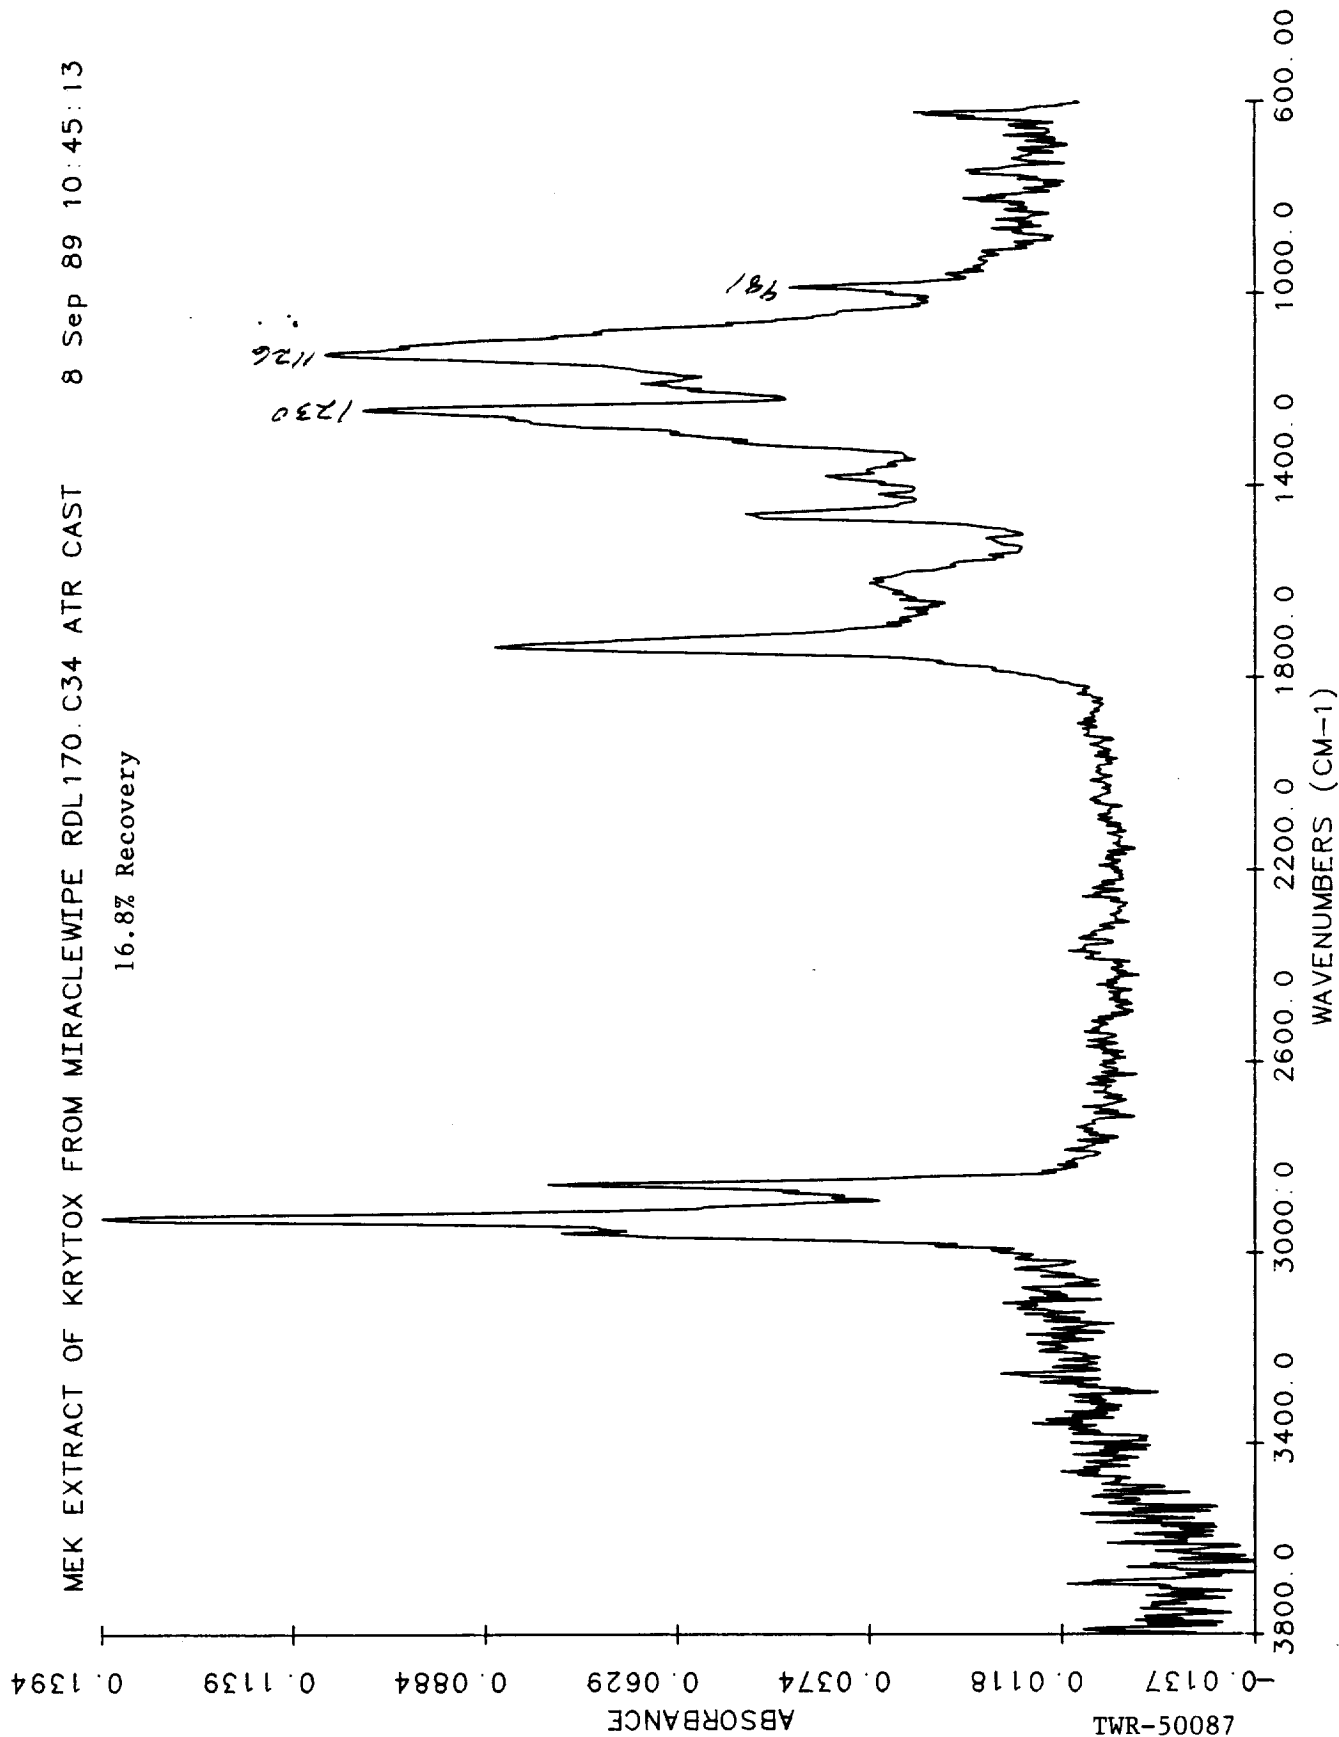


Figure 84.

MEK EXTRACT OF KRYTOX FROM ALPHAWIPE RDL172.D14 ATR CAST 13 Sep 89 12:48:09

12.9% Recovery

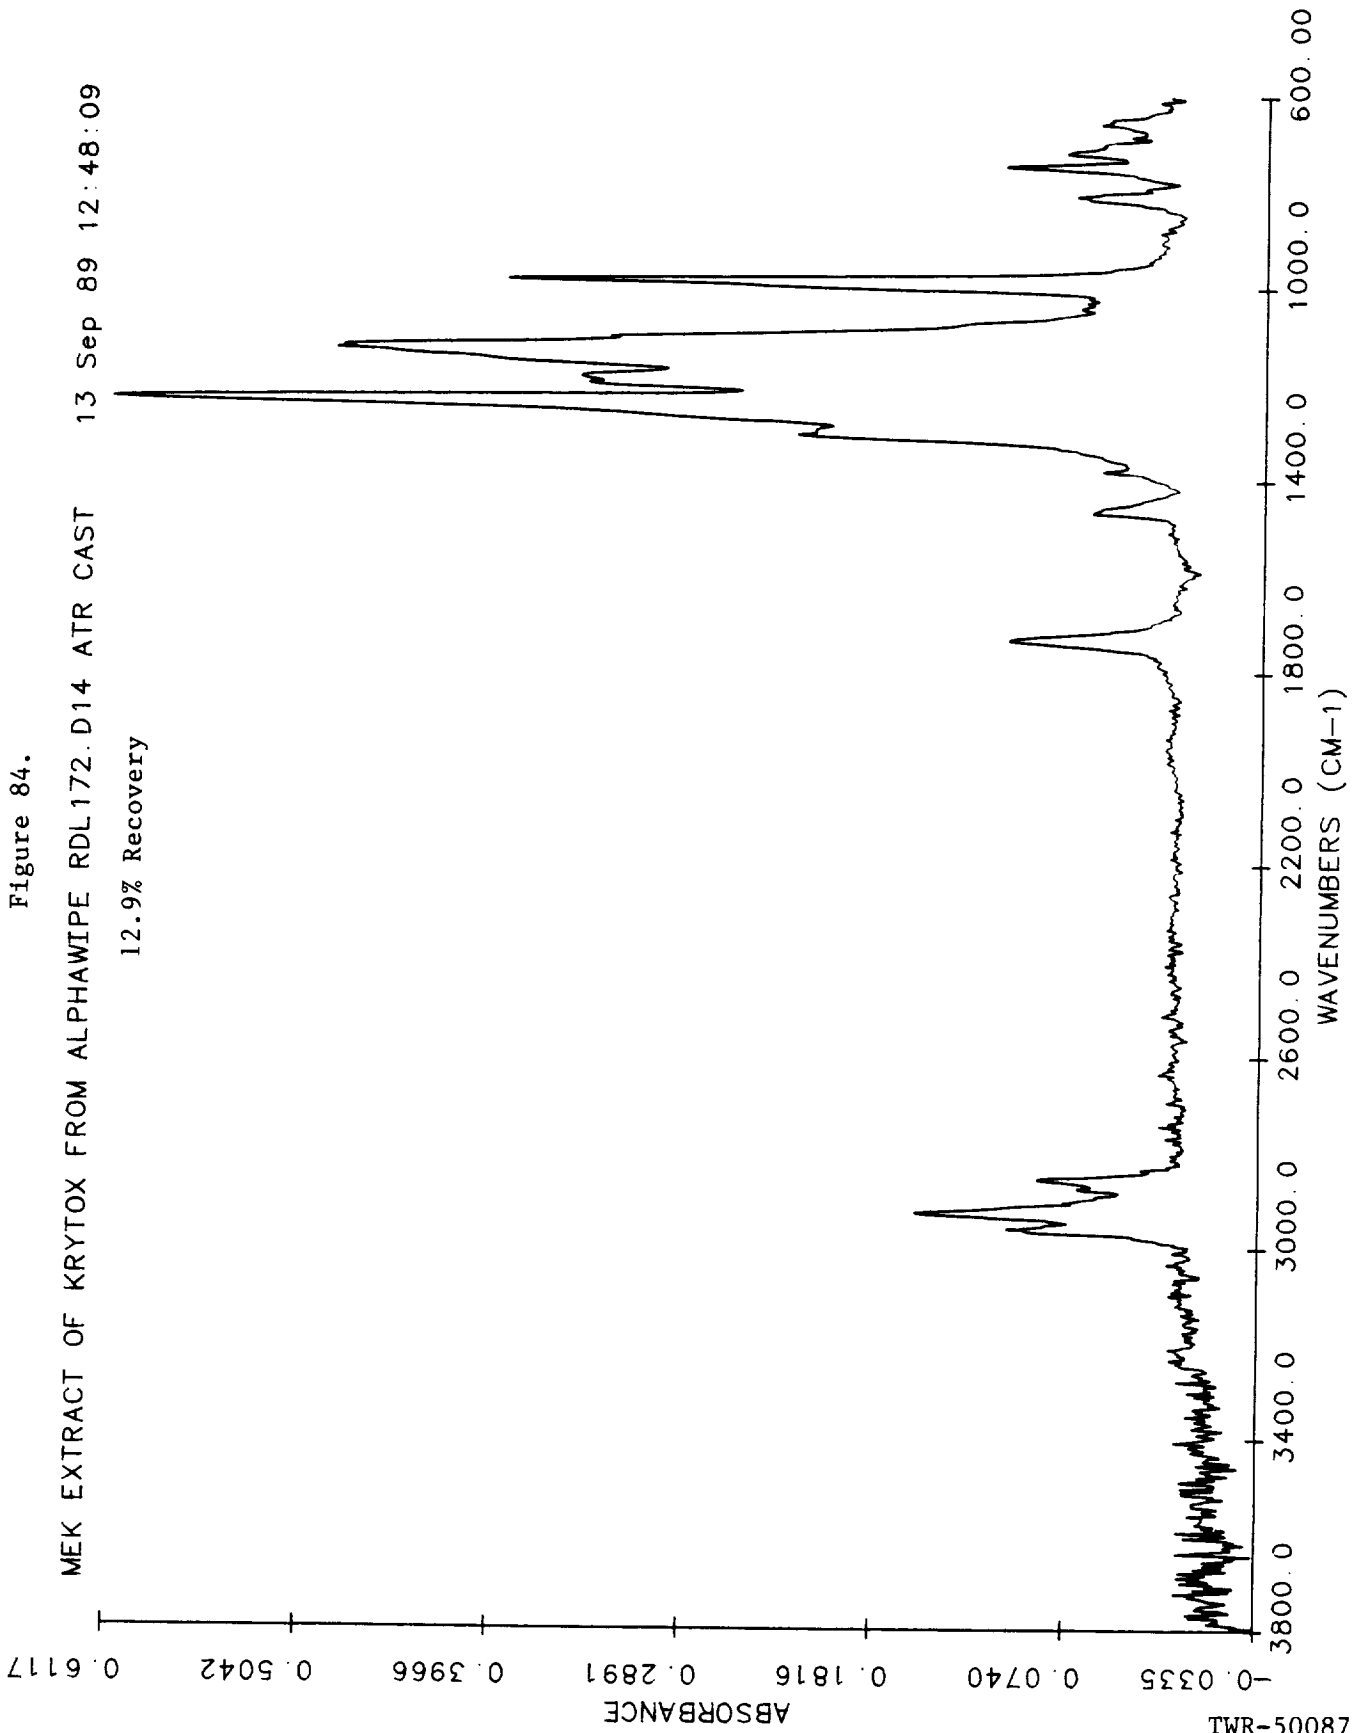


Figure 85.



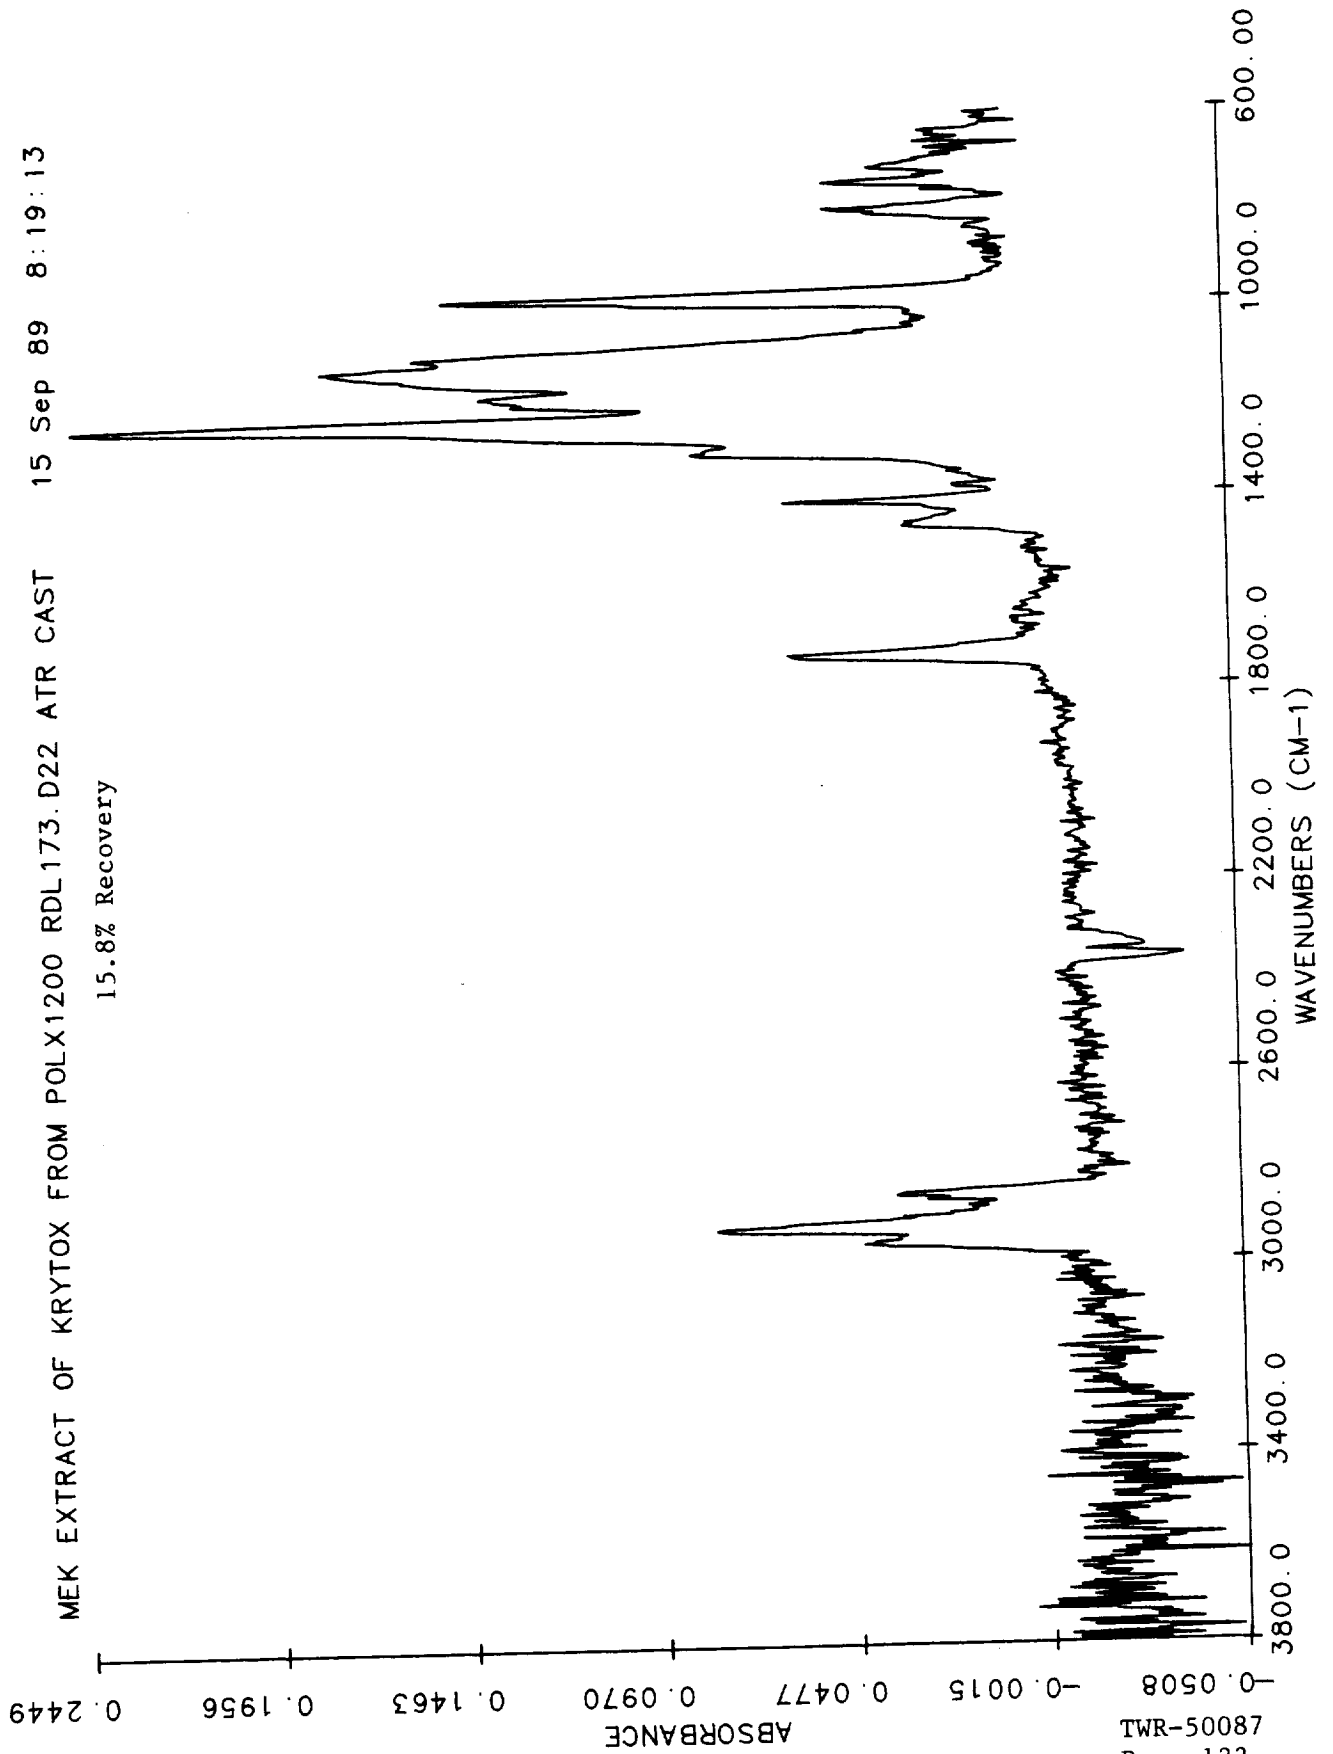


Figure 86.

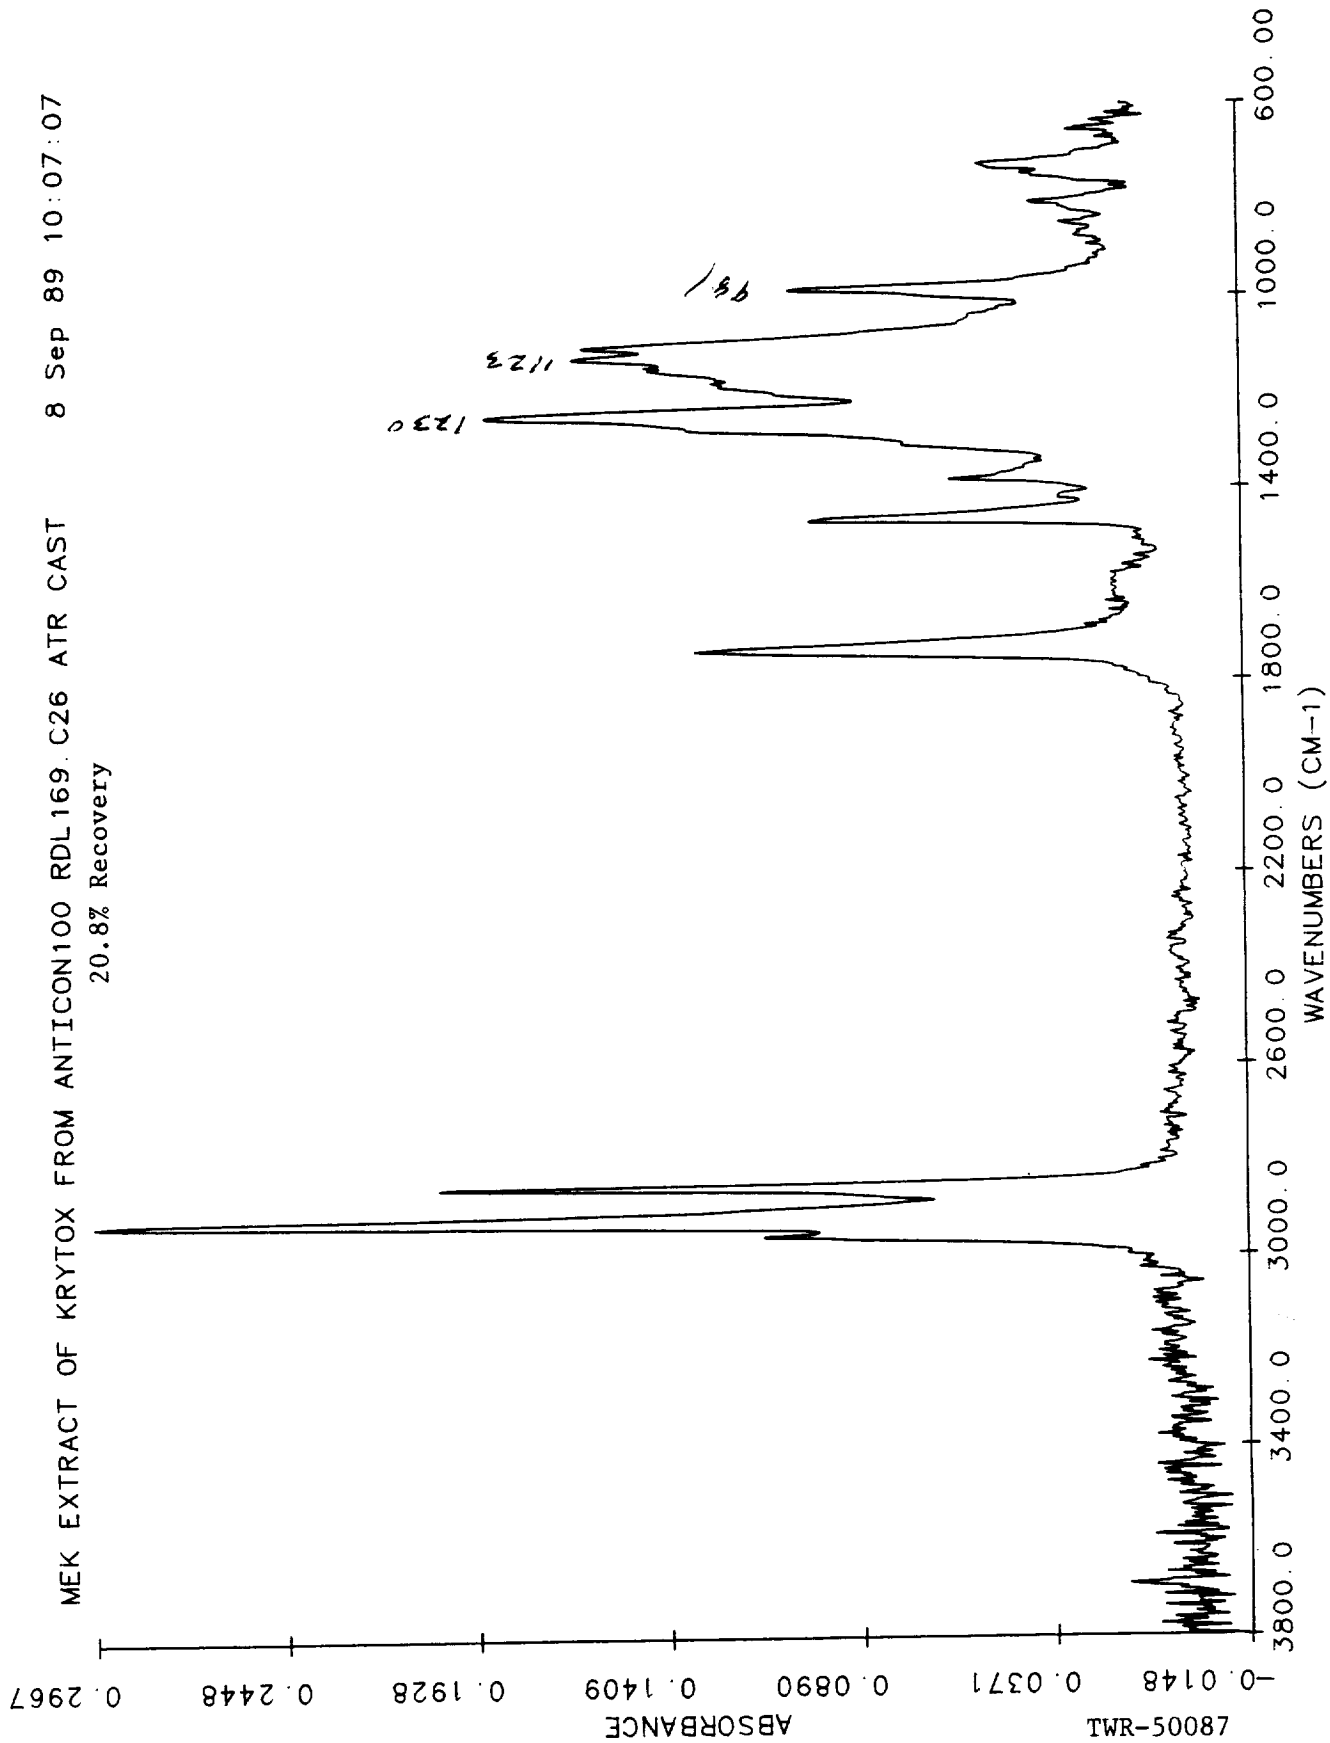

ORIGINAL PAGE IS
OF POOR QUALITY


Figure 87.

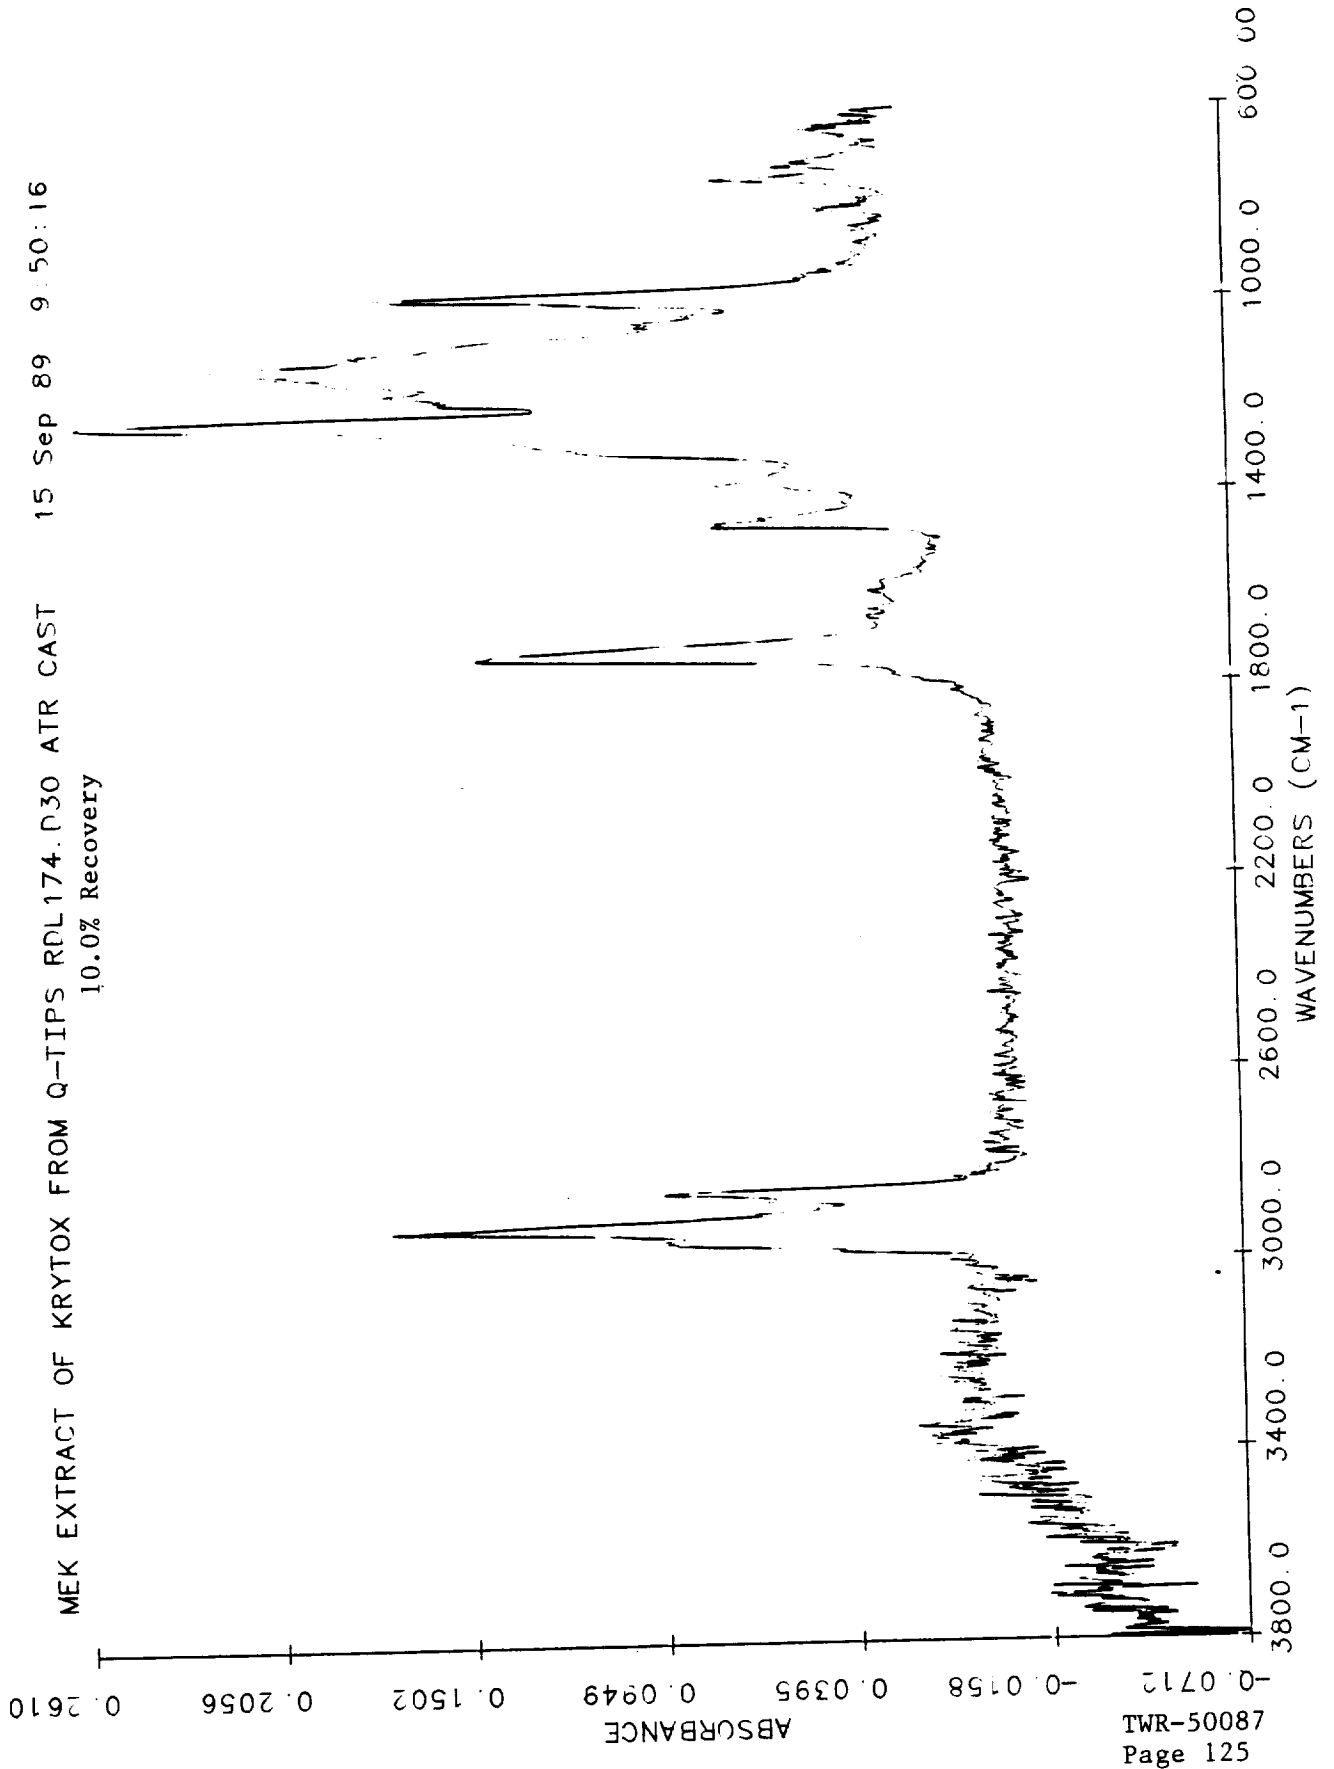


TCE SHAKEN EXTRACT OF KRYTOX FROM MIRACLEWIPE RDL176.E02 ATR CA 09 Oct 88 09:44:54

Figure 88.

68.2% Recovery

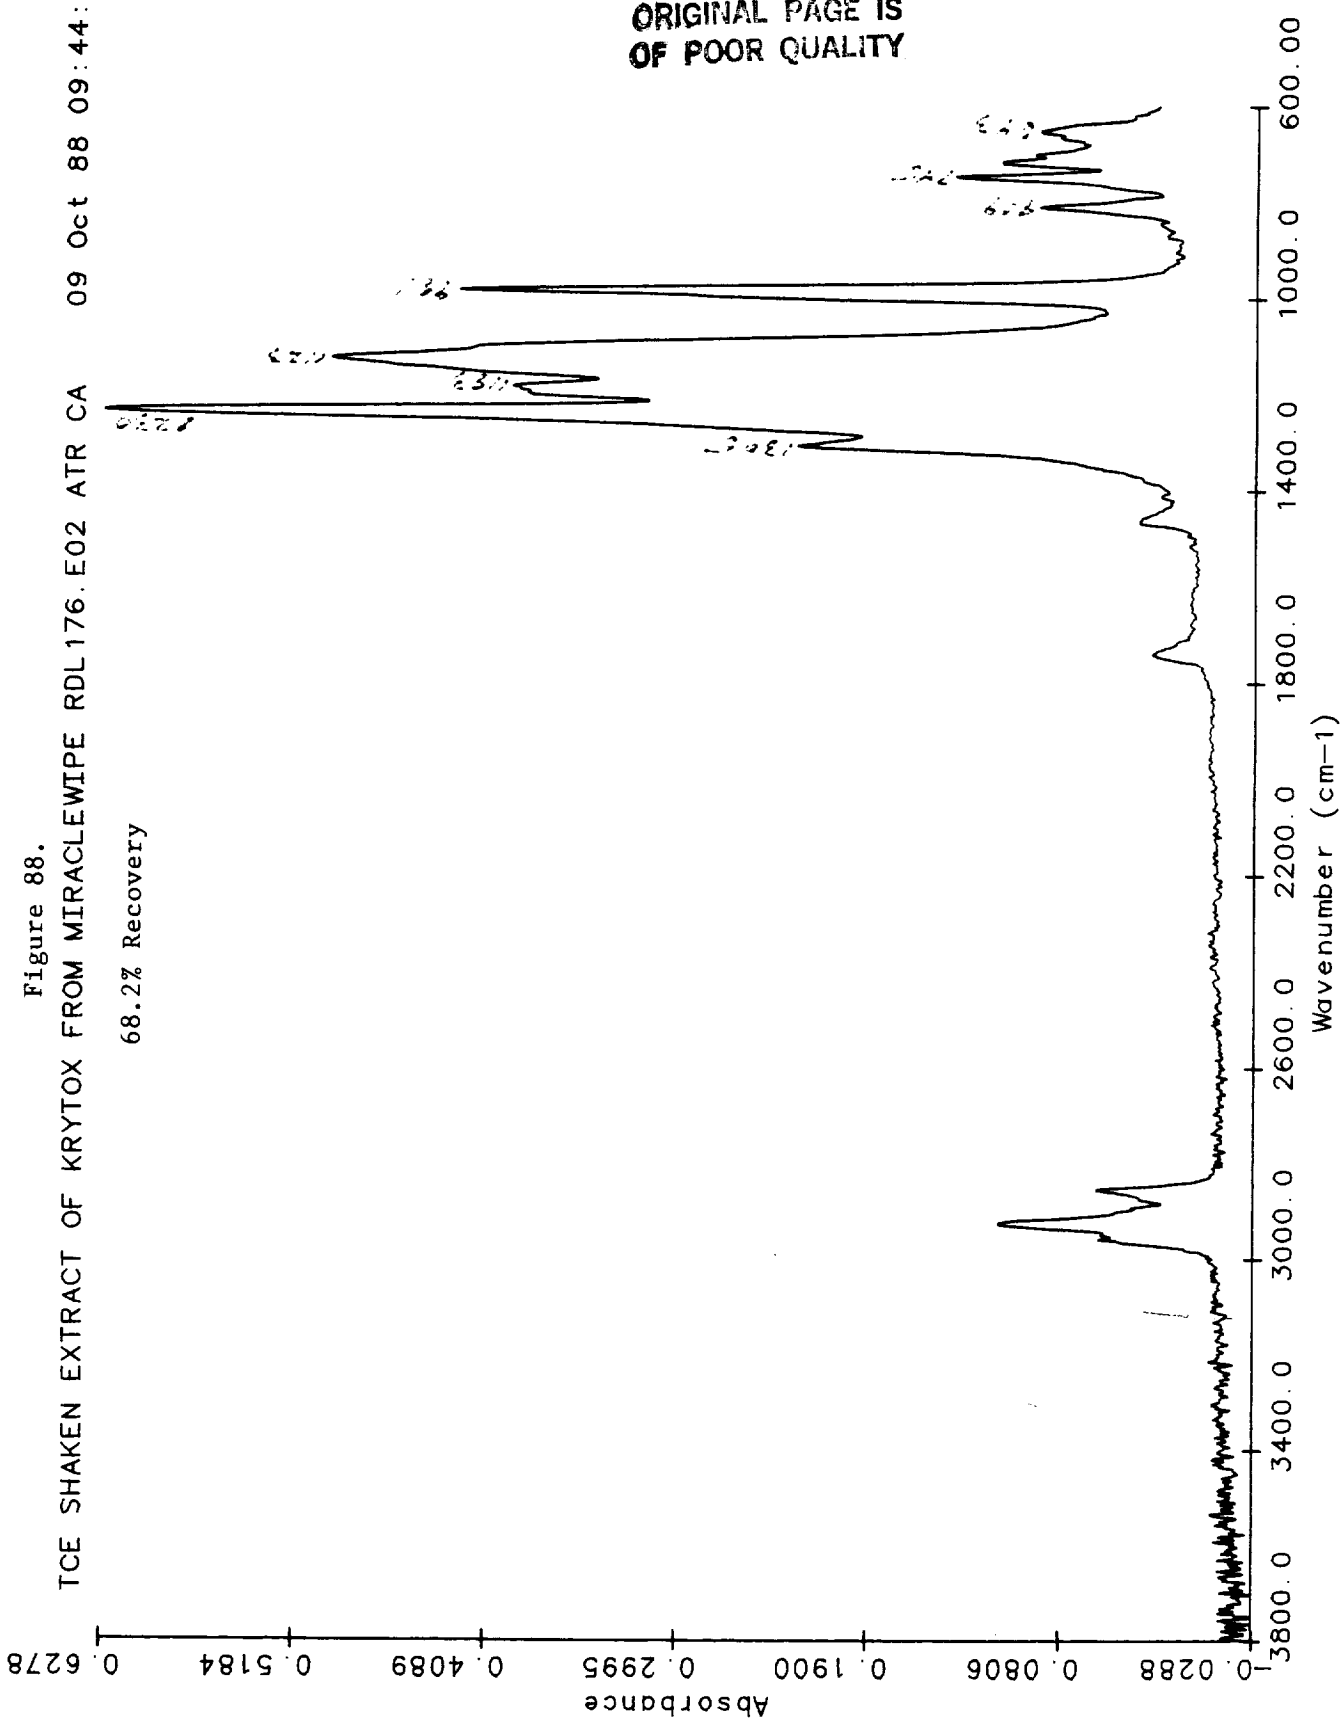

ORIGINAL PAGE IS
OF POOR QUALITY

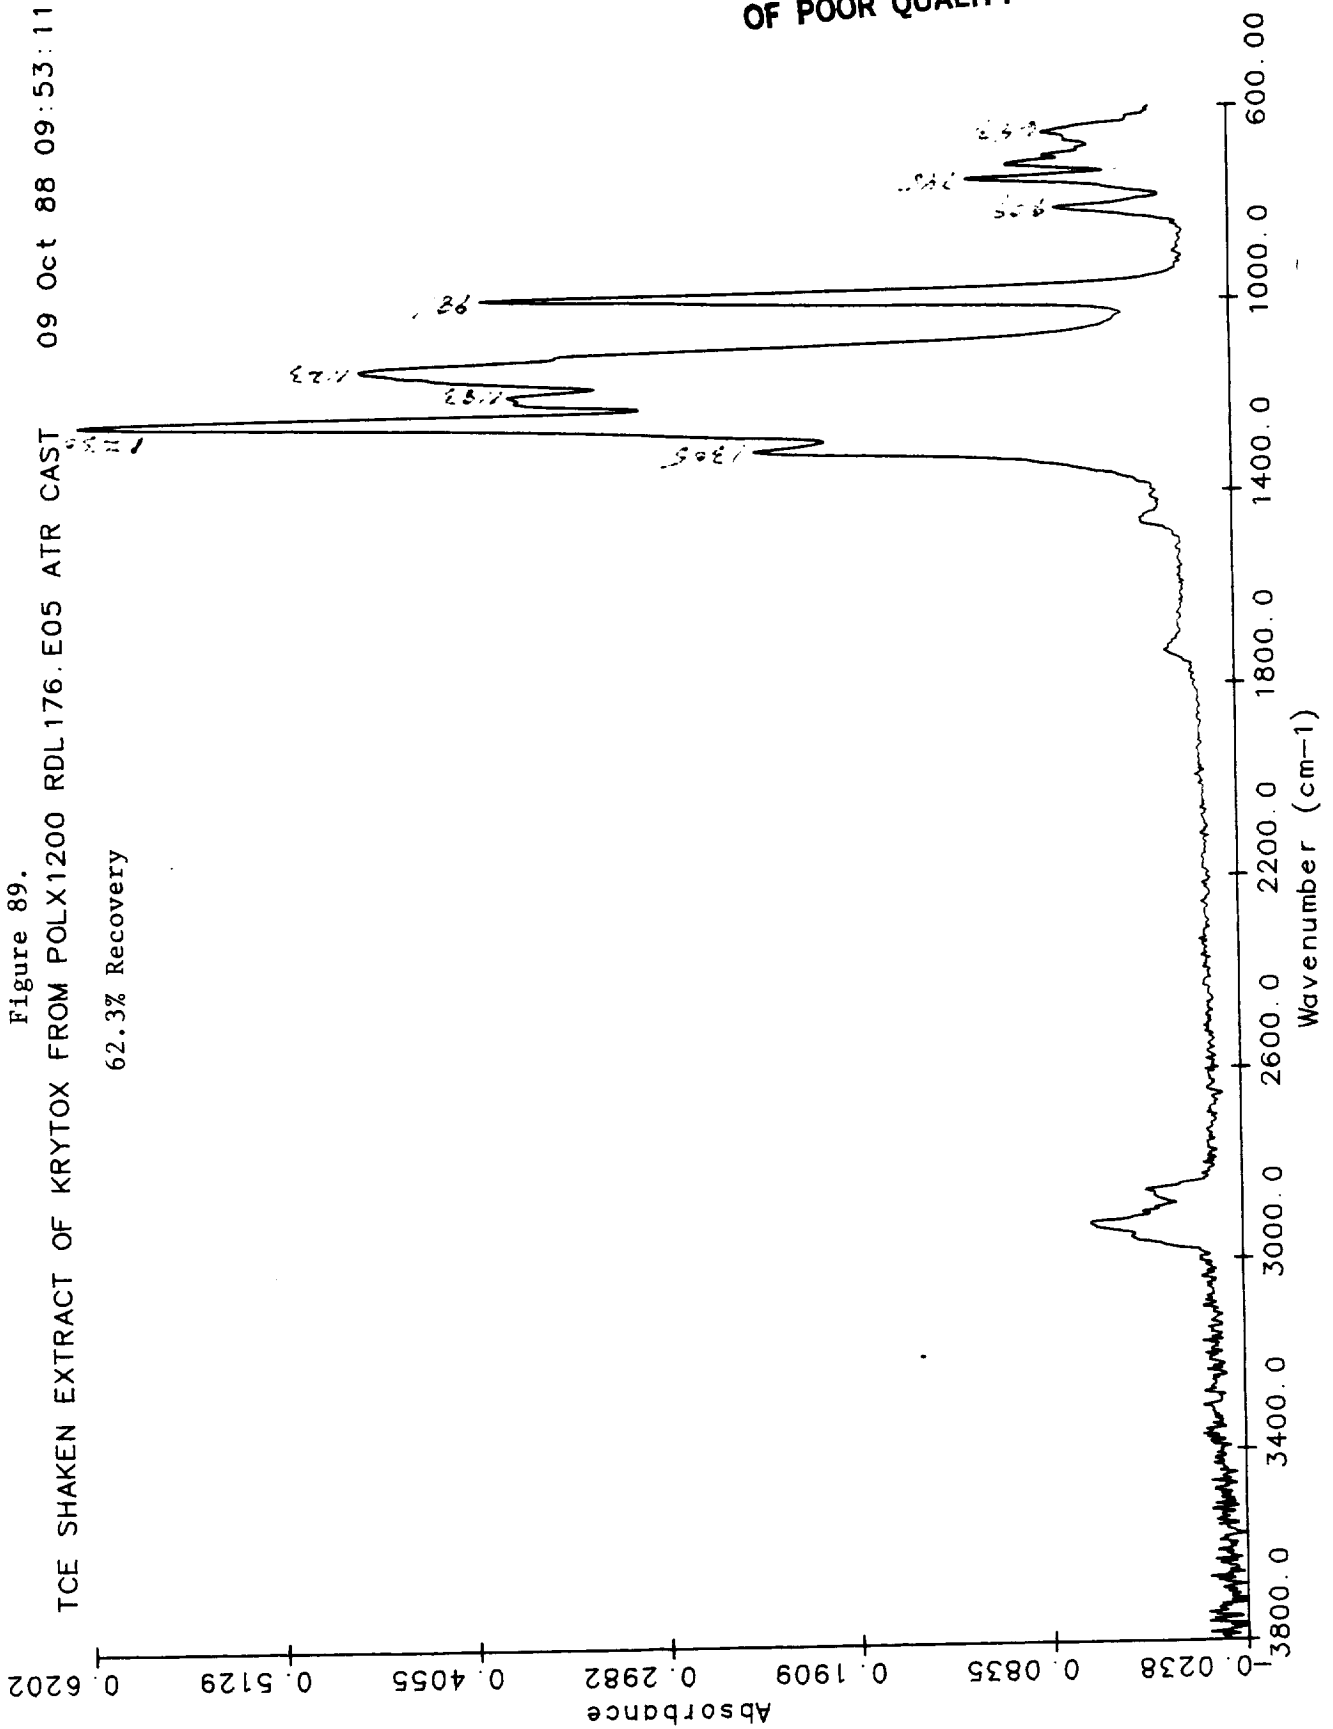

ORIGINAL PAGE IS
OF POOR QUALITY

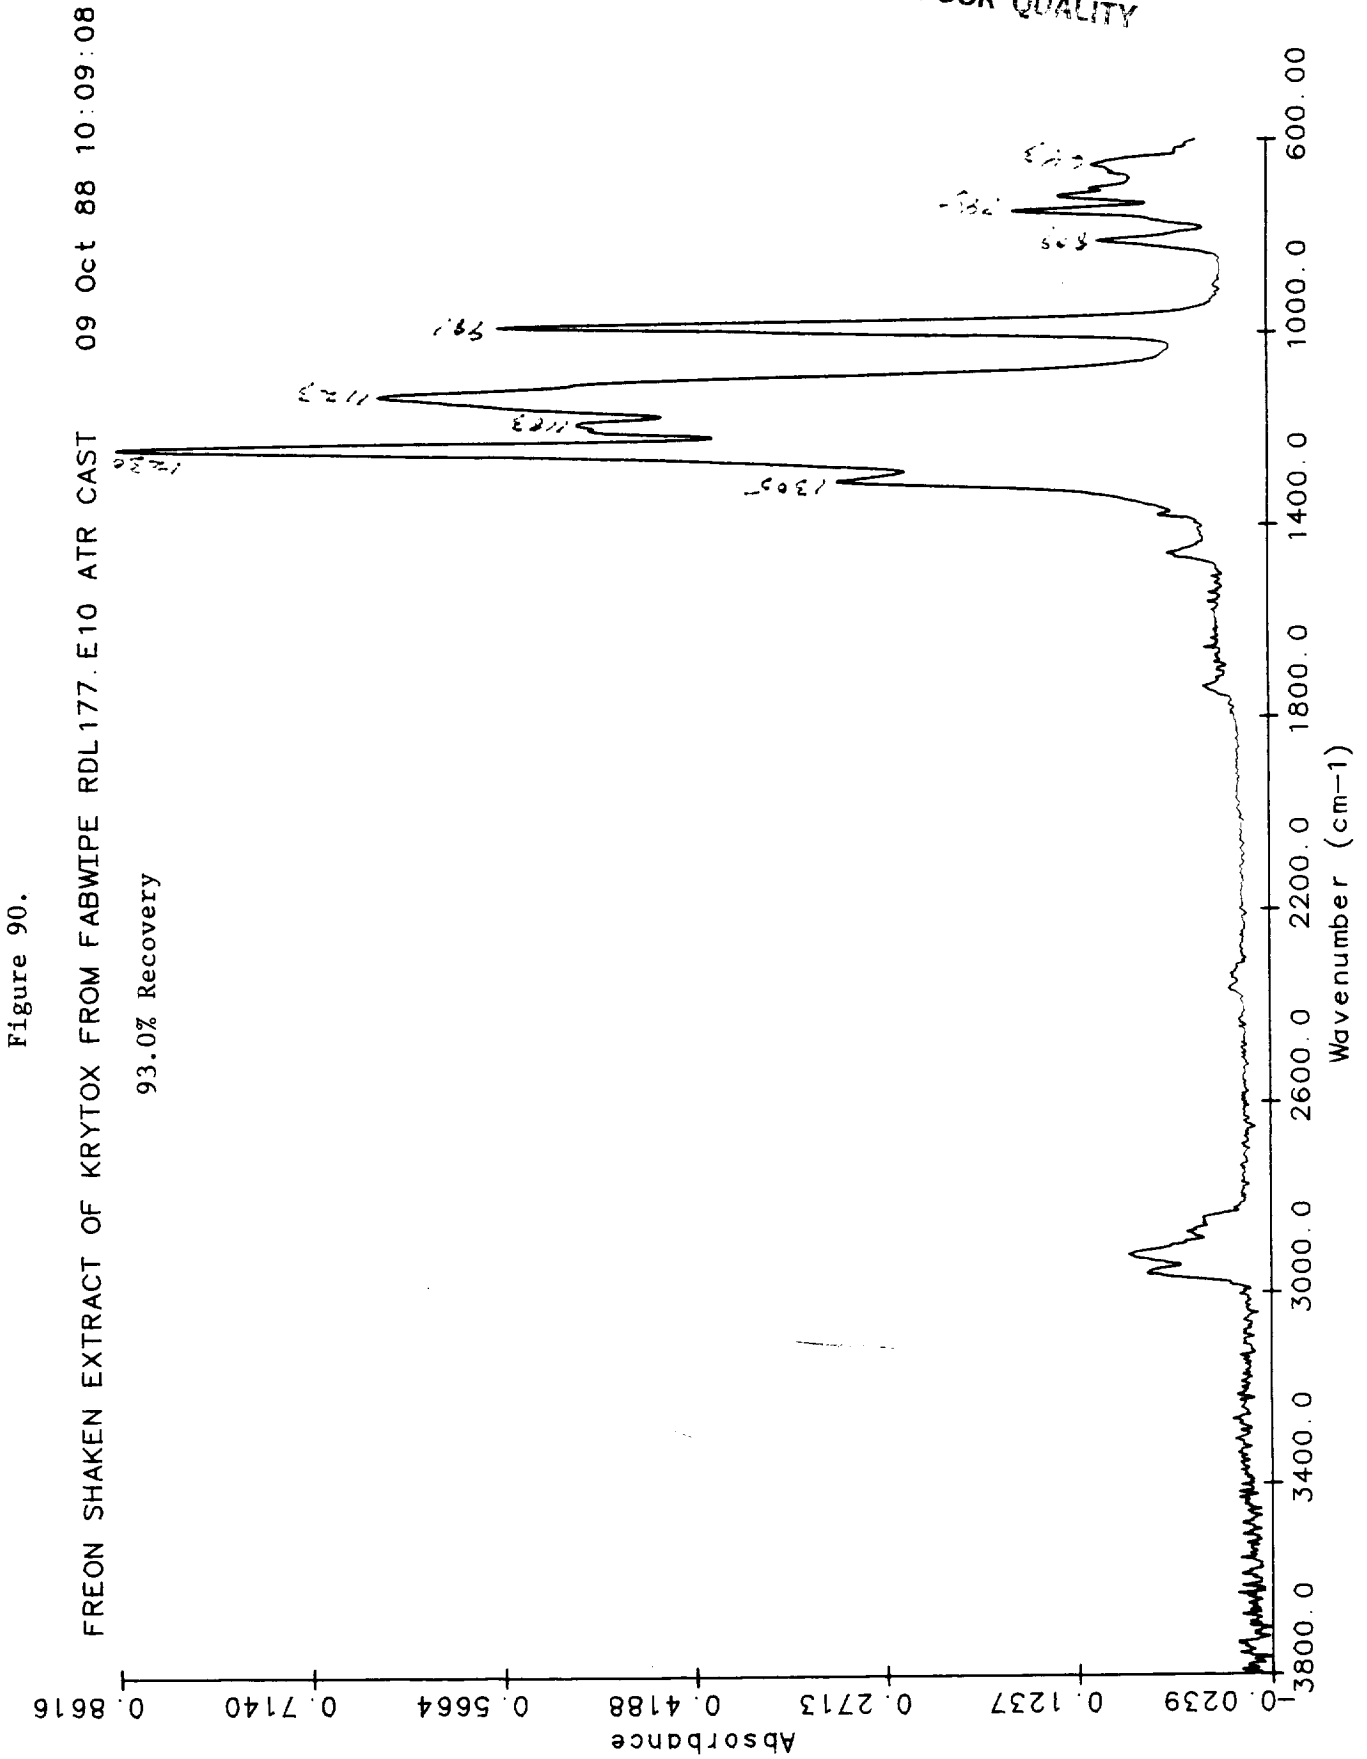


Figure 91.
FREON SHAKEN EXTRACT OF KRYTOX FROM ALPHAWIPE RDL177.E11 ATR CA
88.0% Recovery

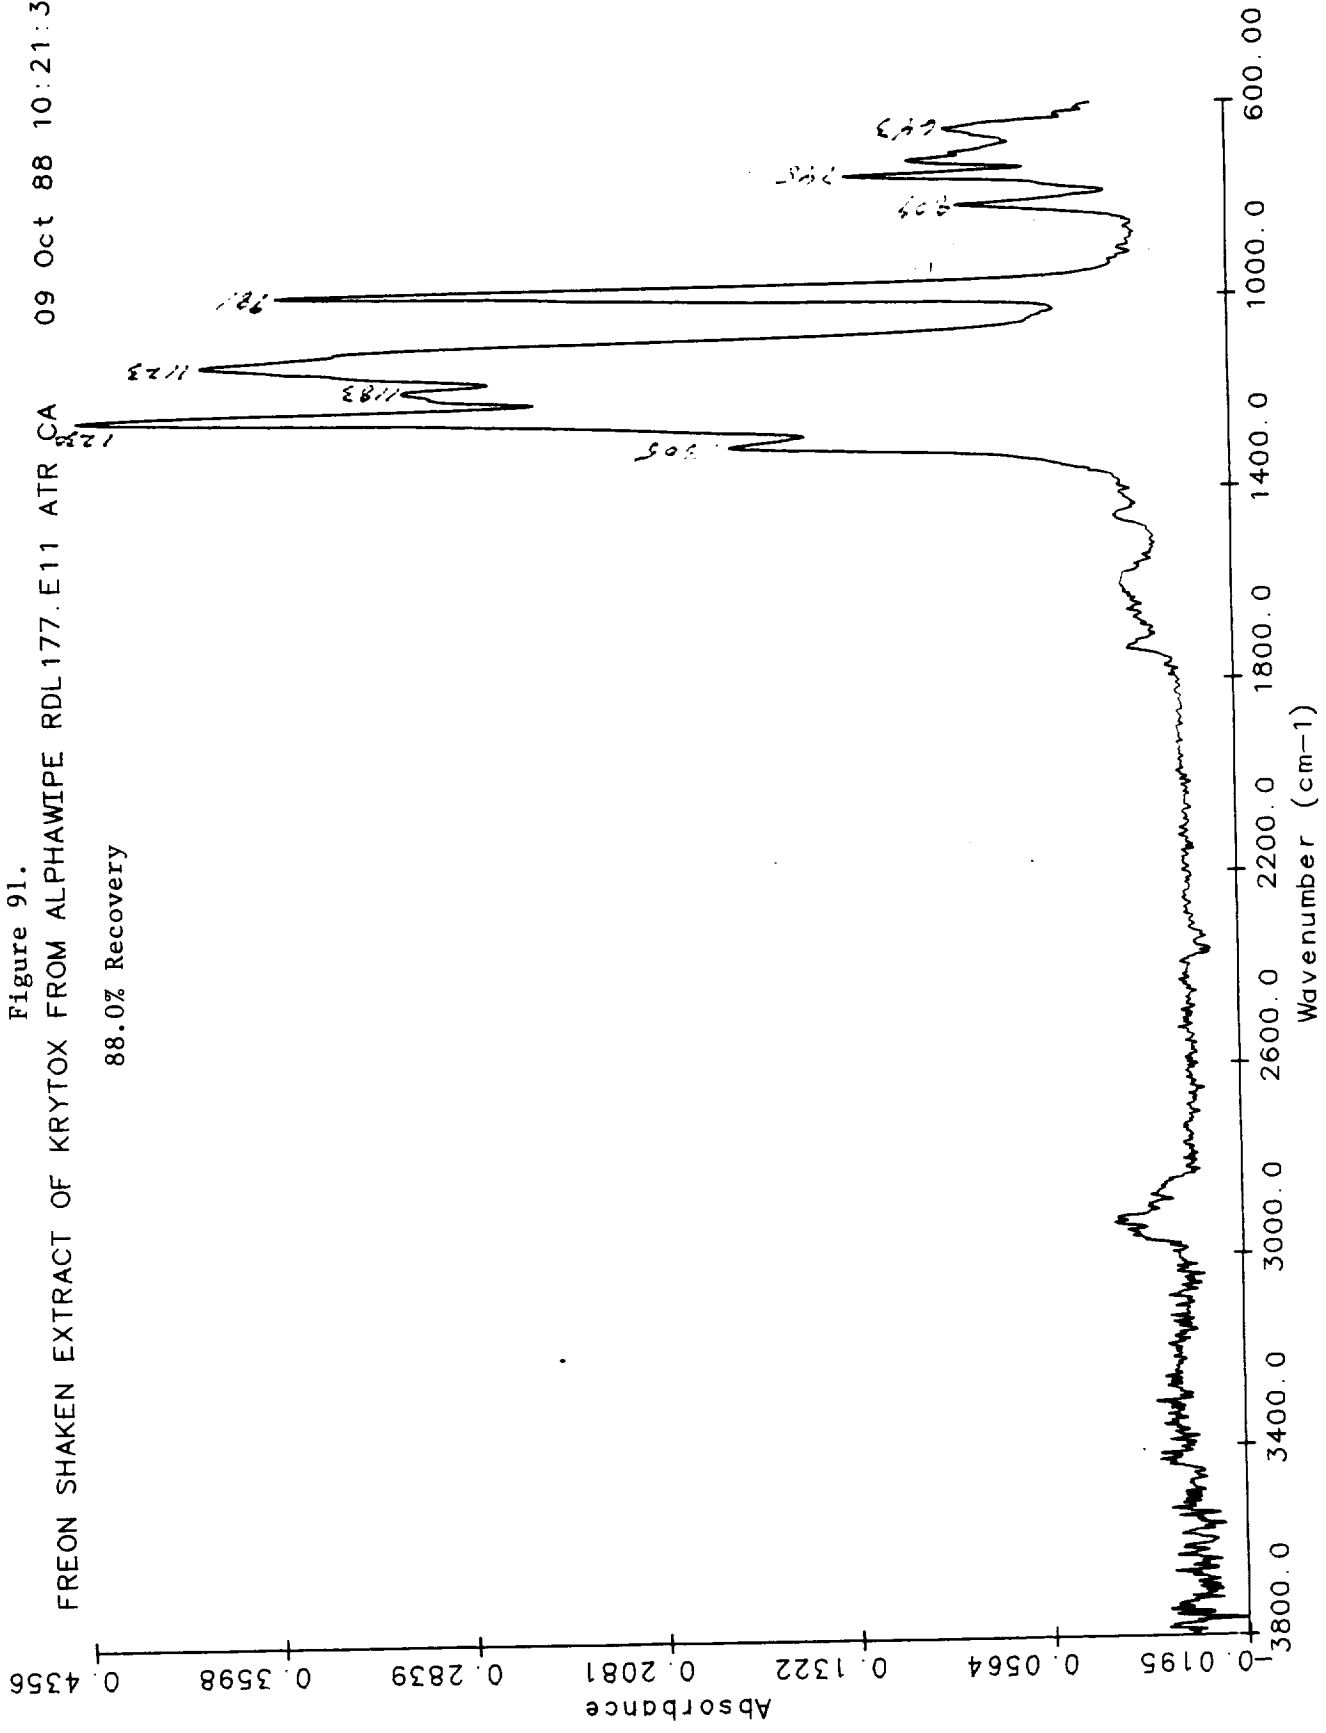


Figure 92.
FREON SHAKEN EXTRACT OF KRYTOX FROM ANTICON RDL176.E09 ATR CAST
87.0% Recovery


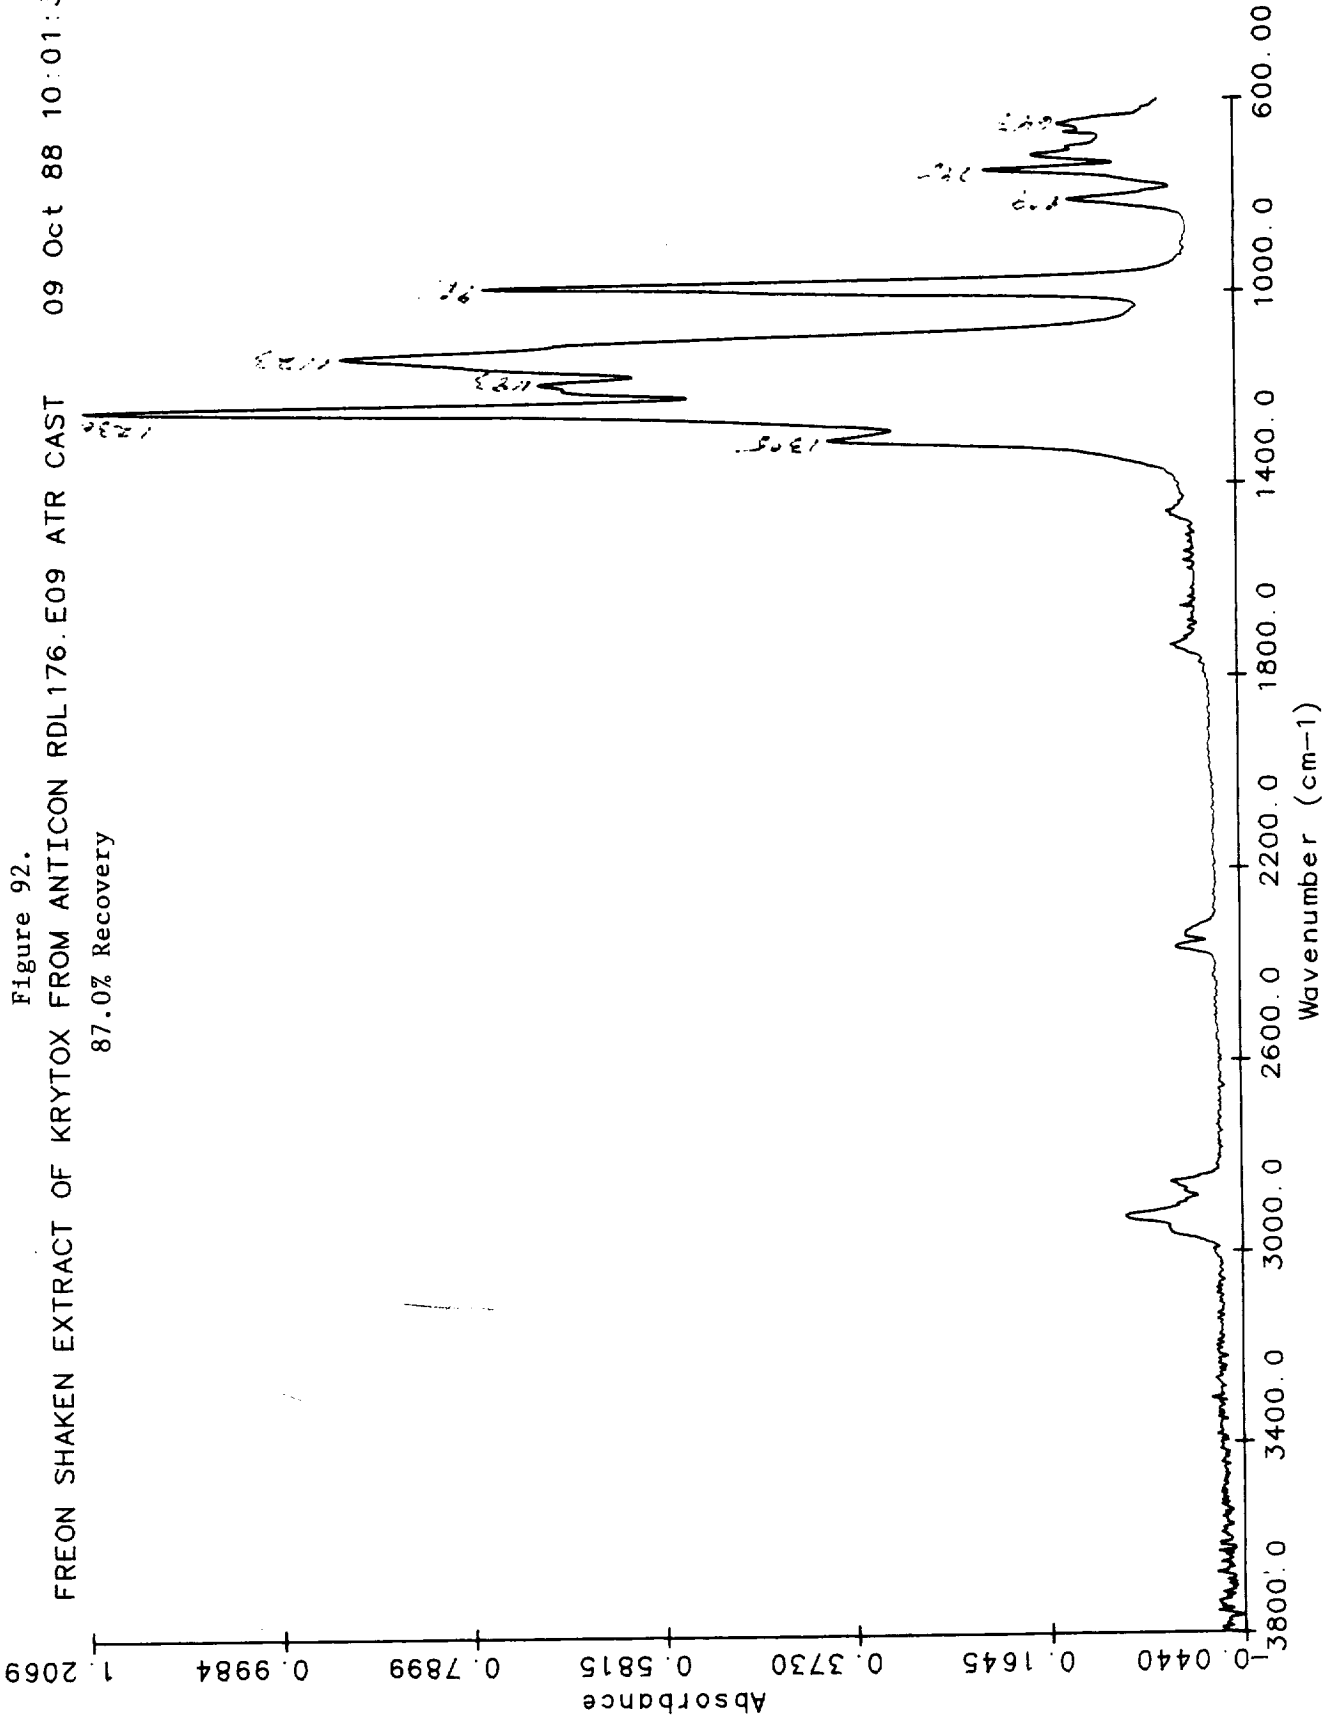


Figure 93.

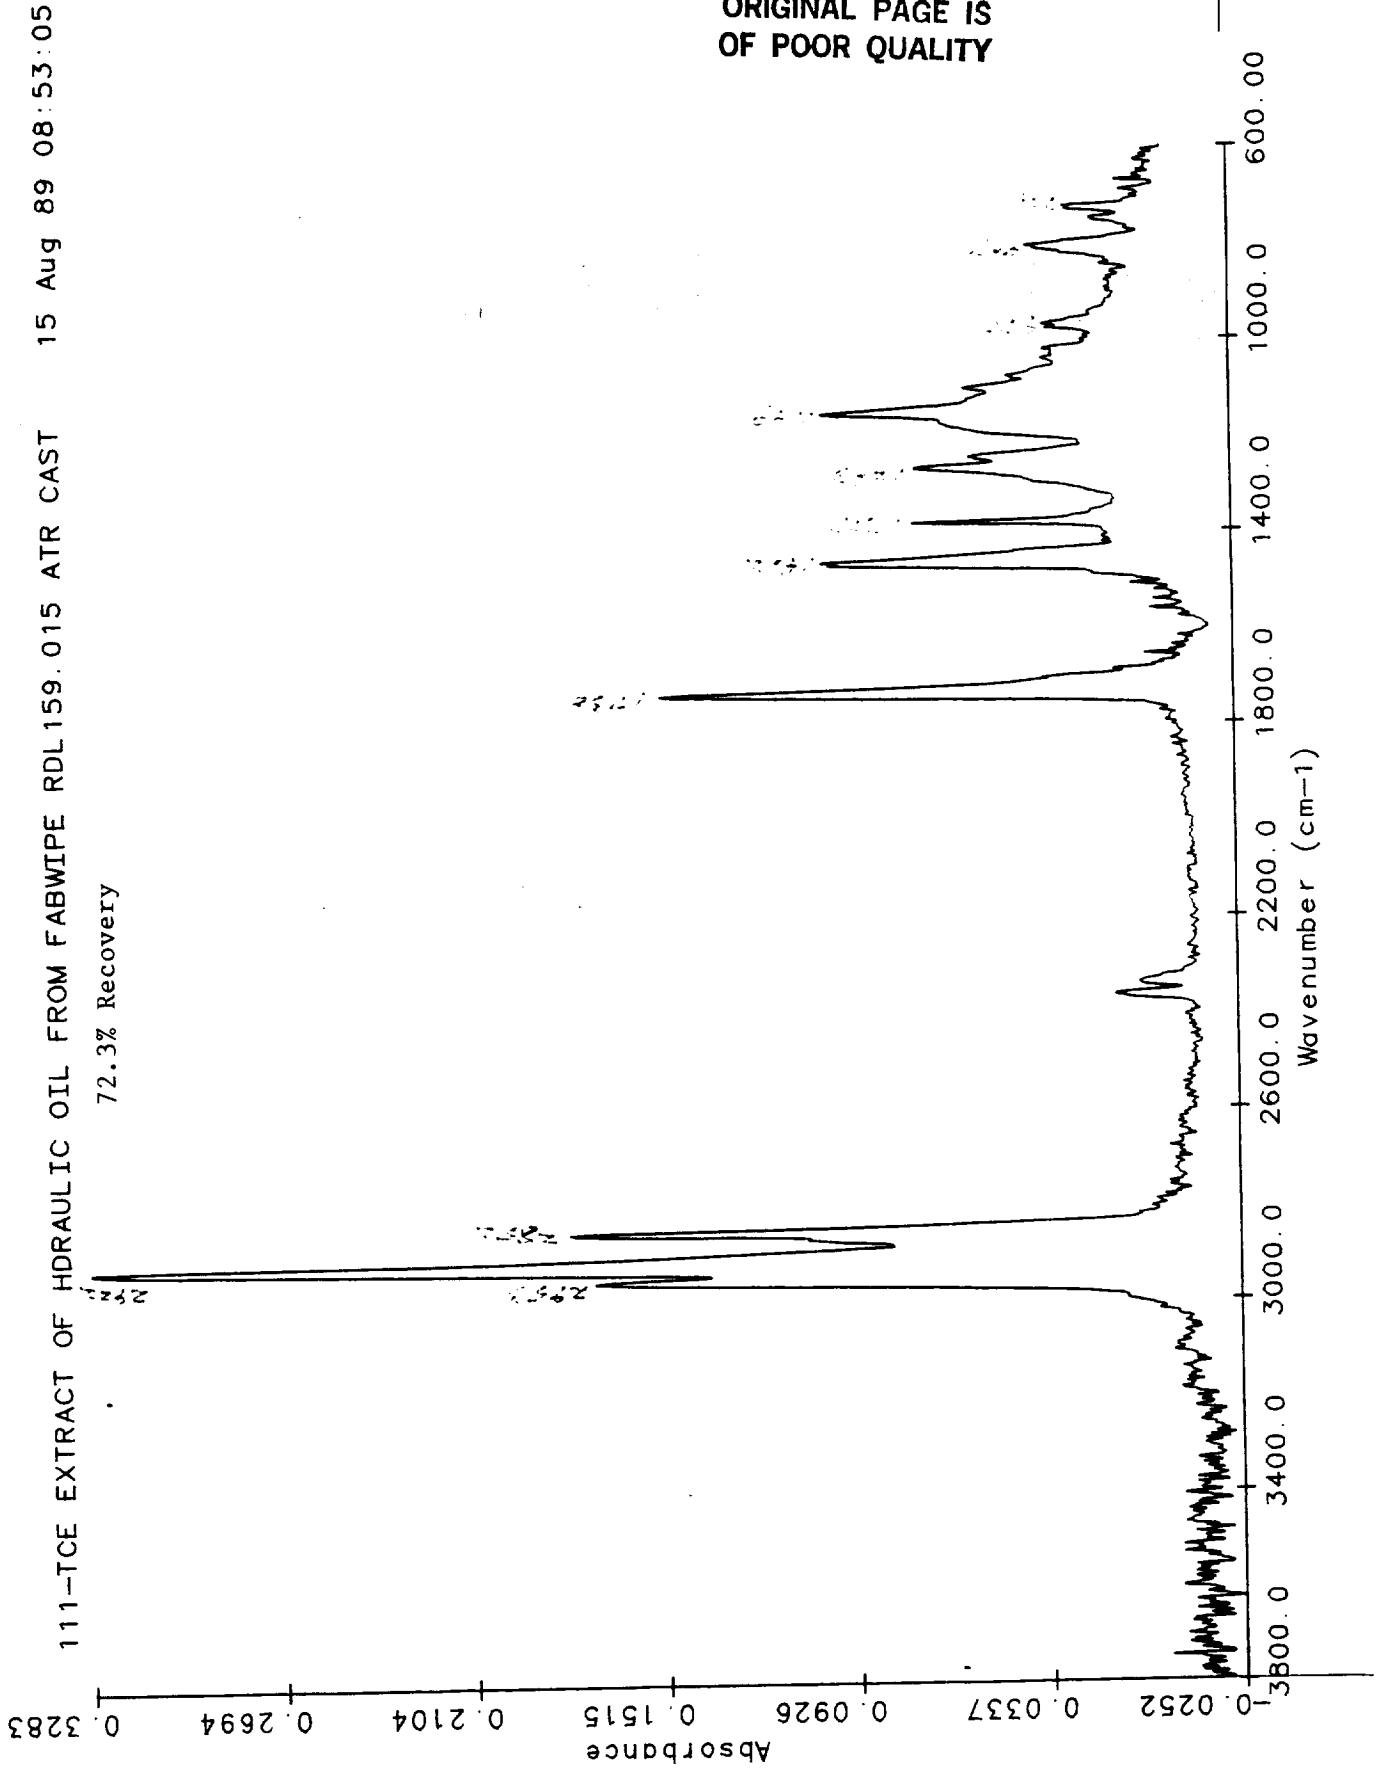

ORIGINAL PAGE
OF POOR QUALITY

Figure 94.

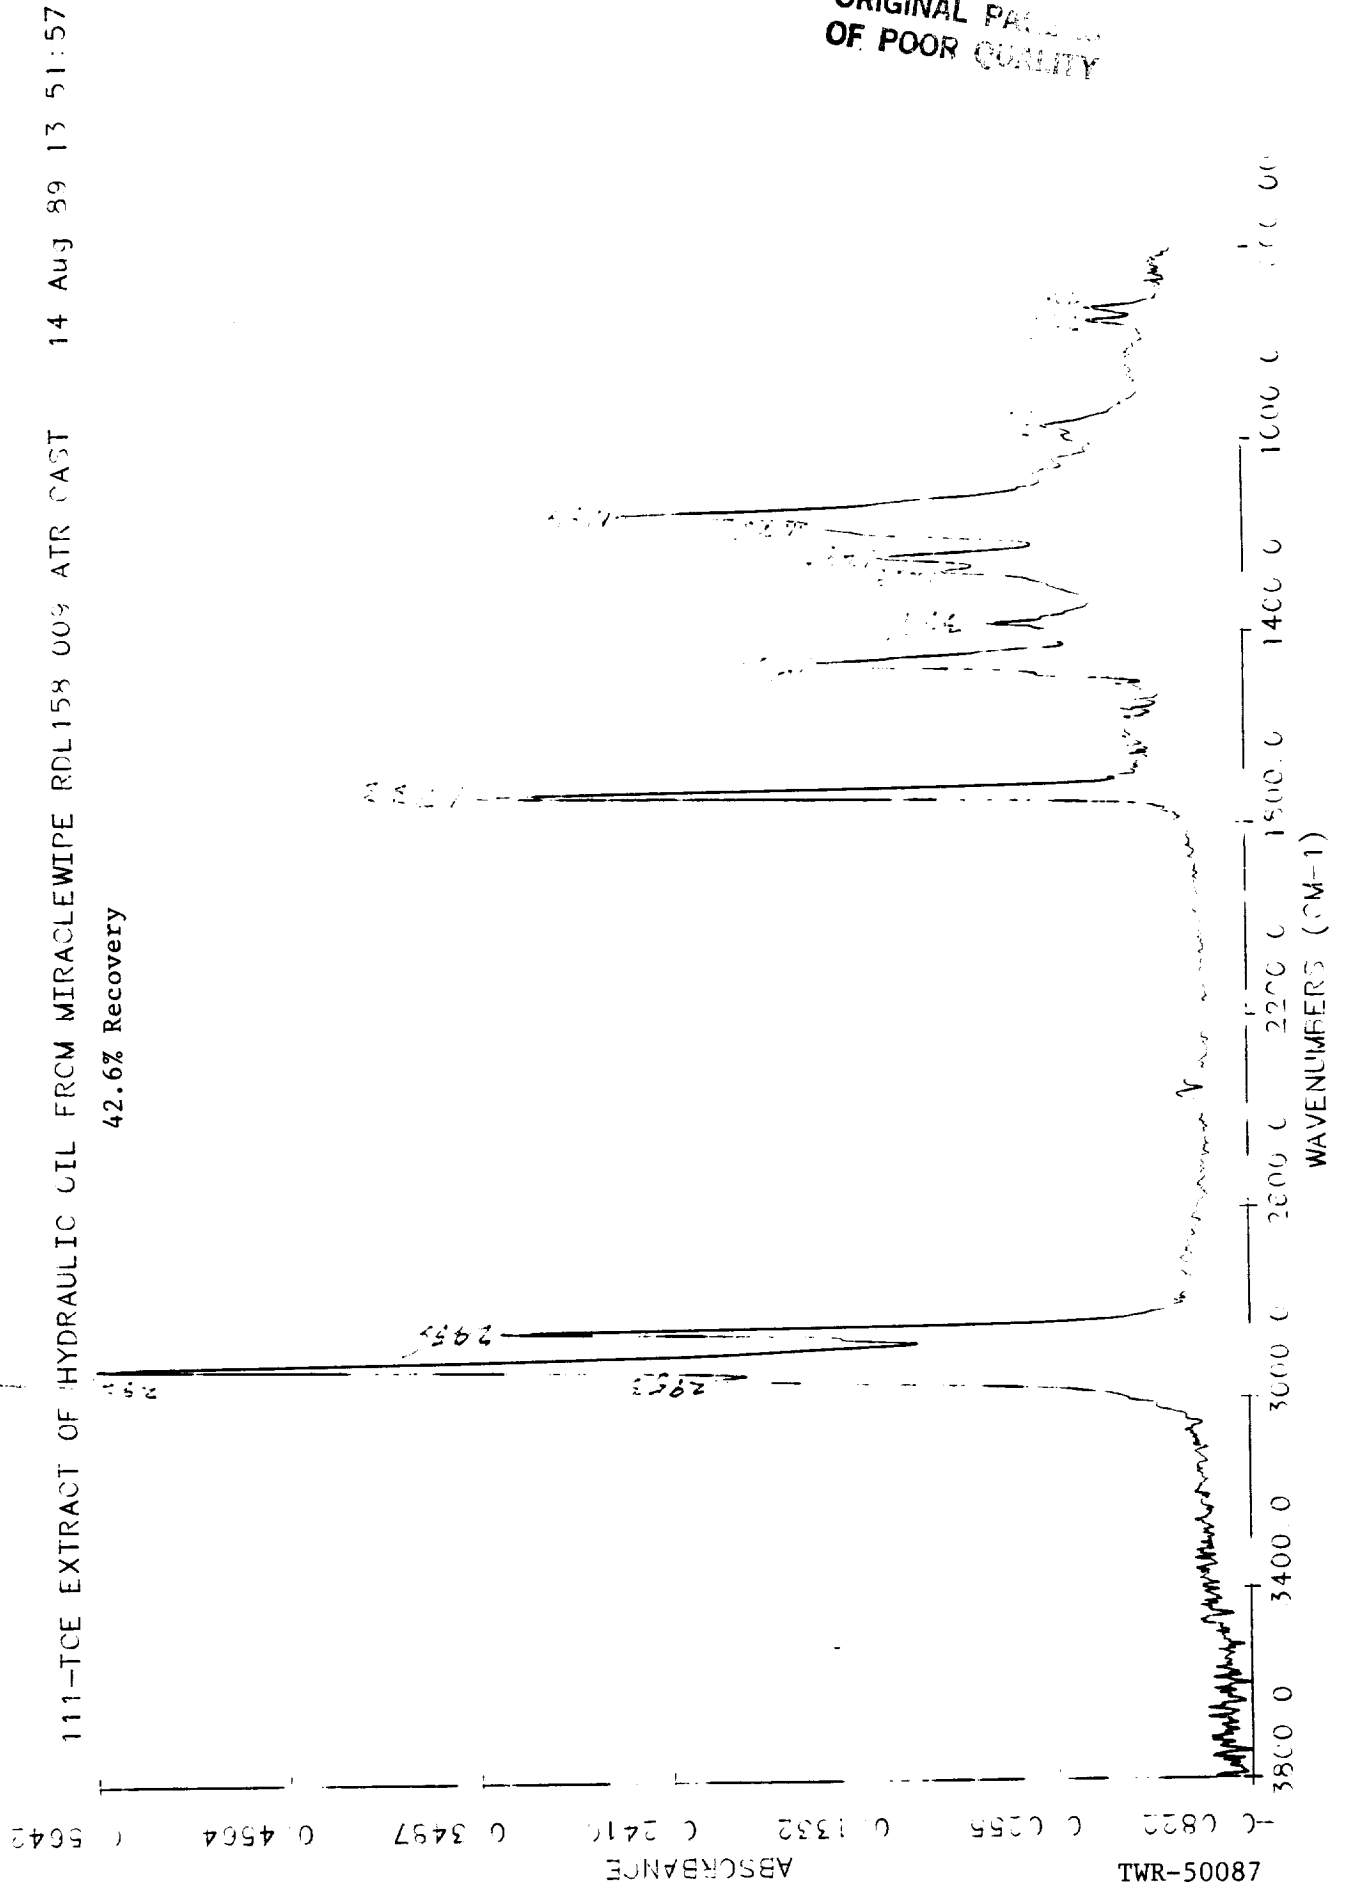


Figure 95.

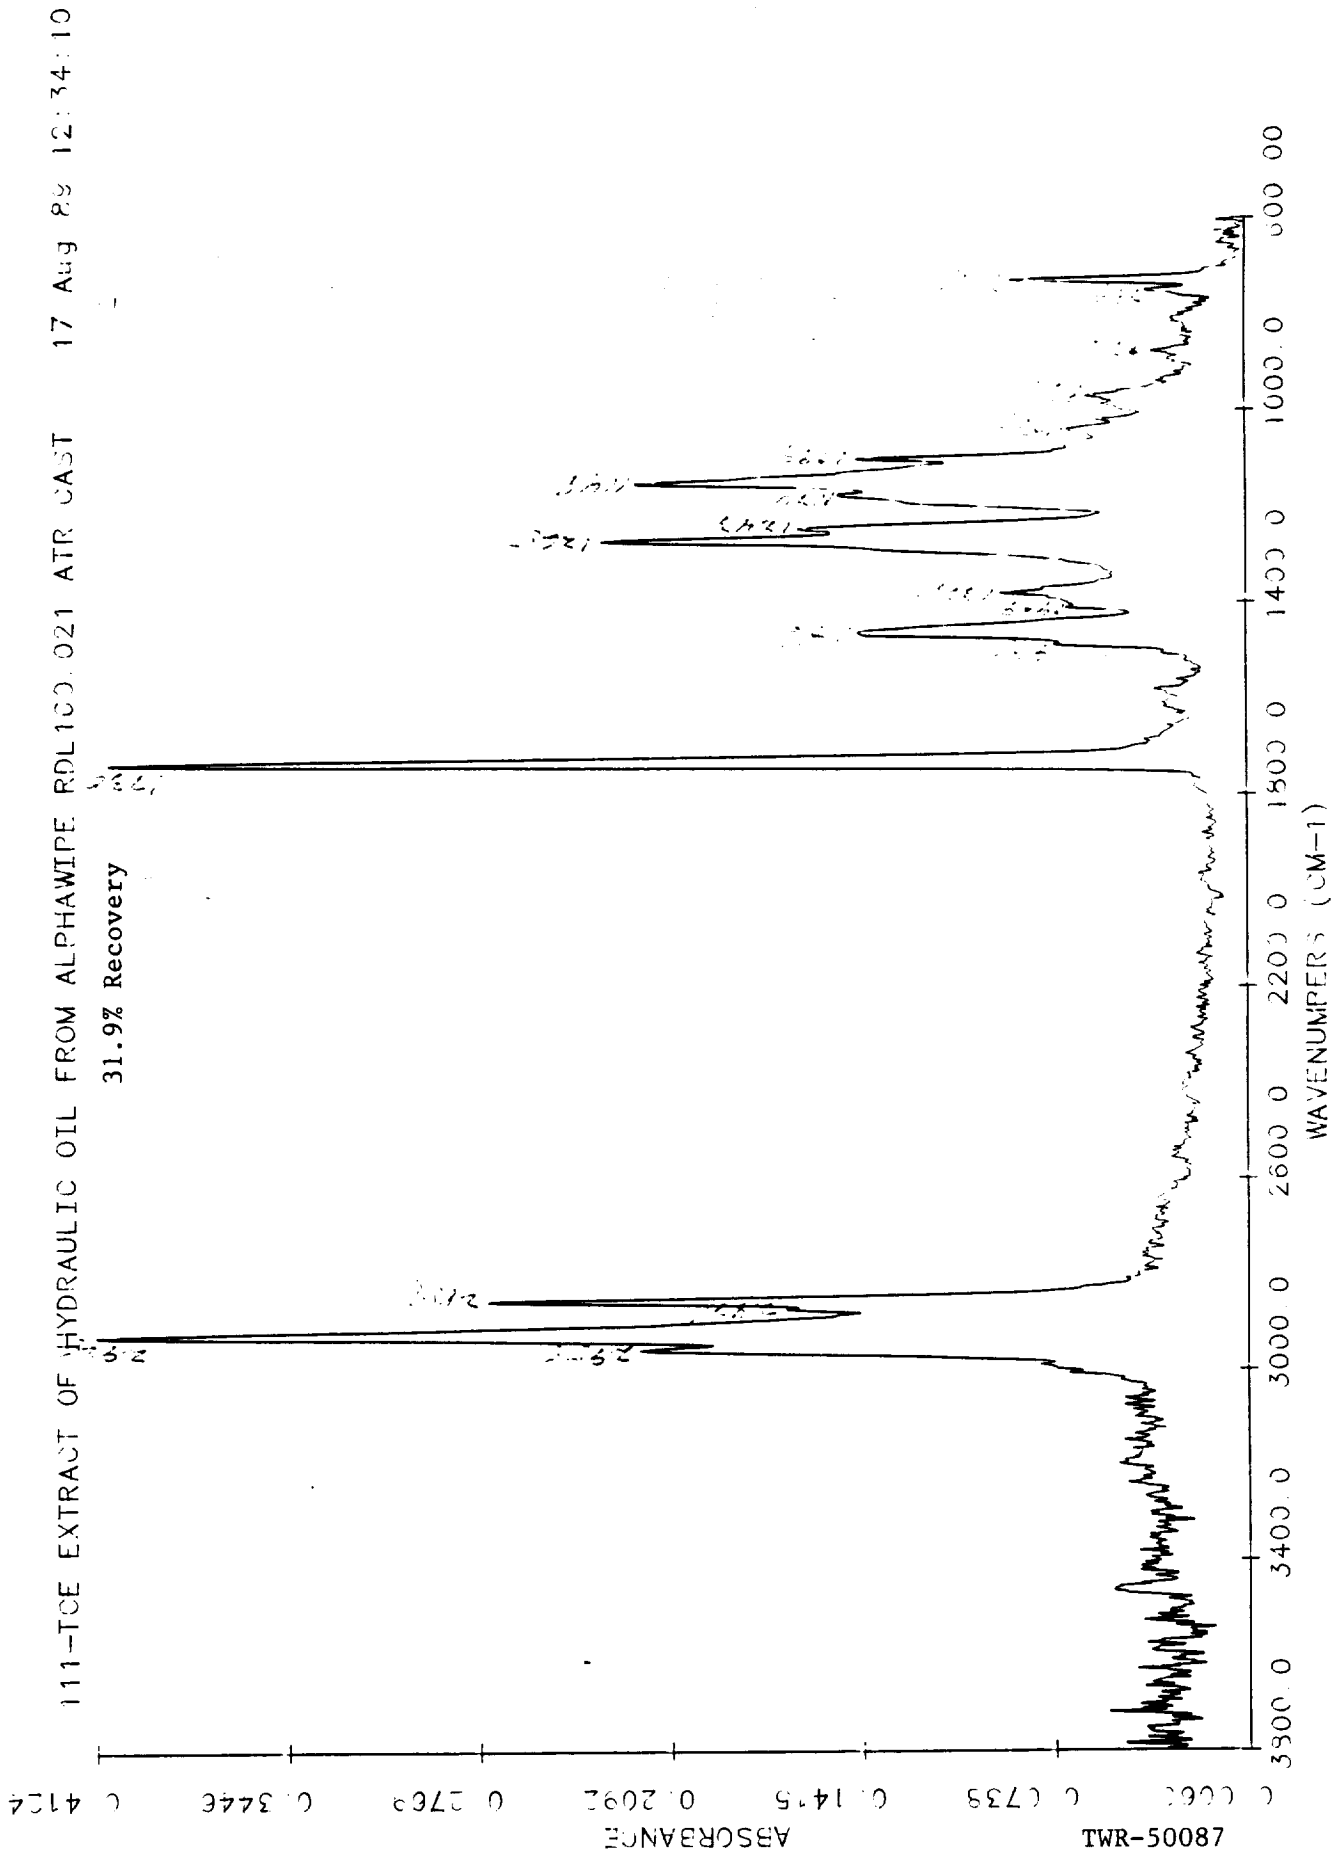


Figure 96.

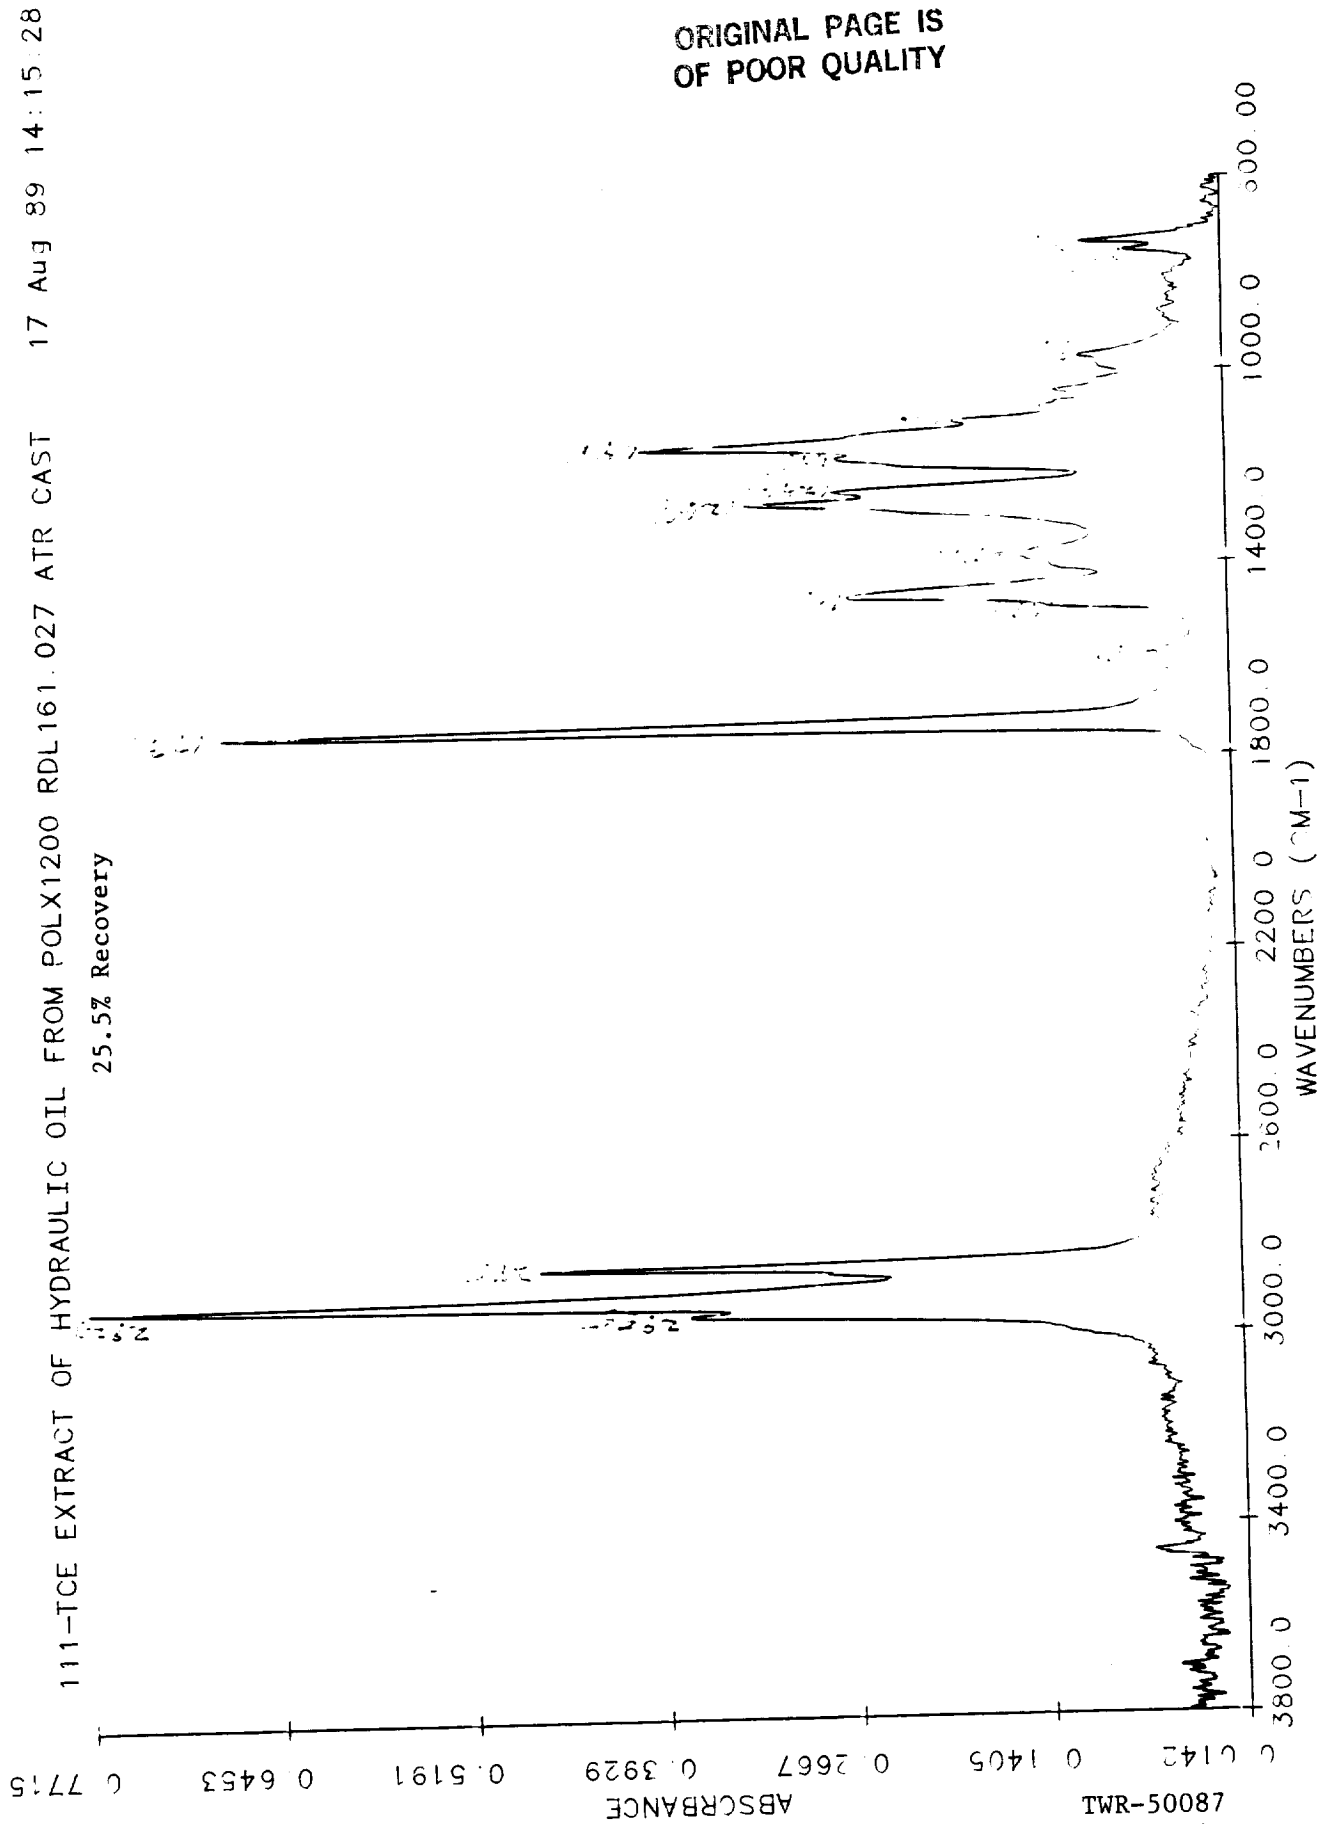


Figure 97.

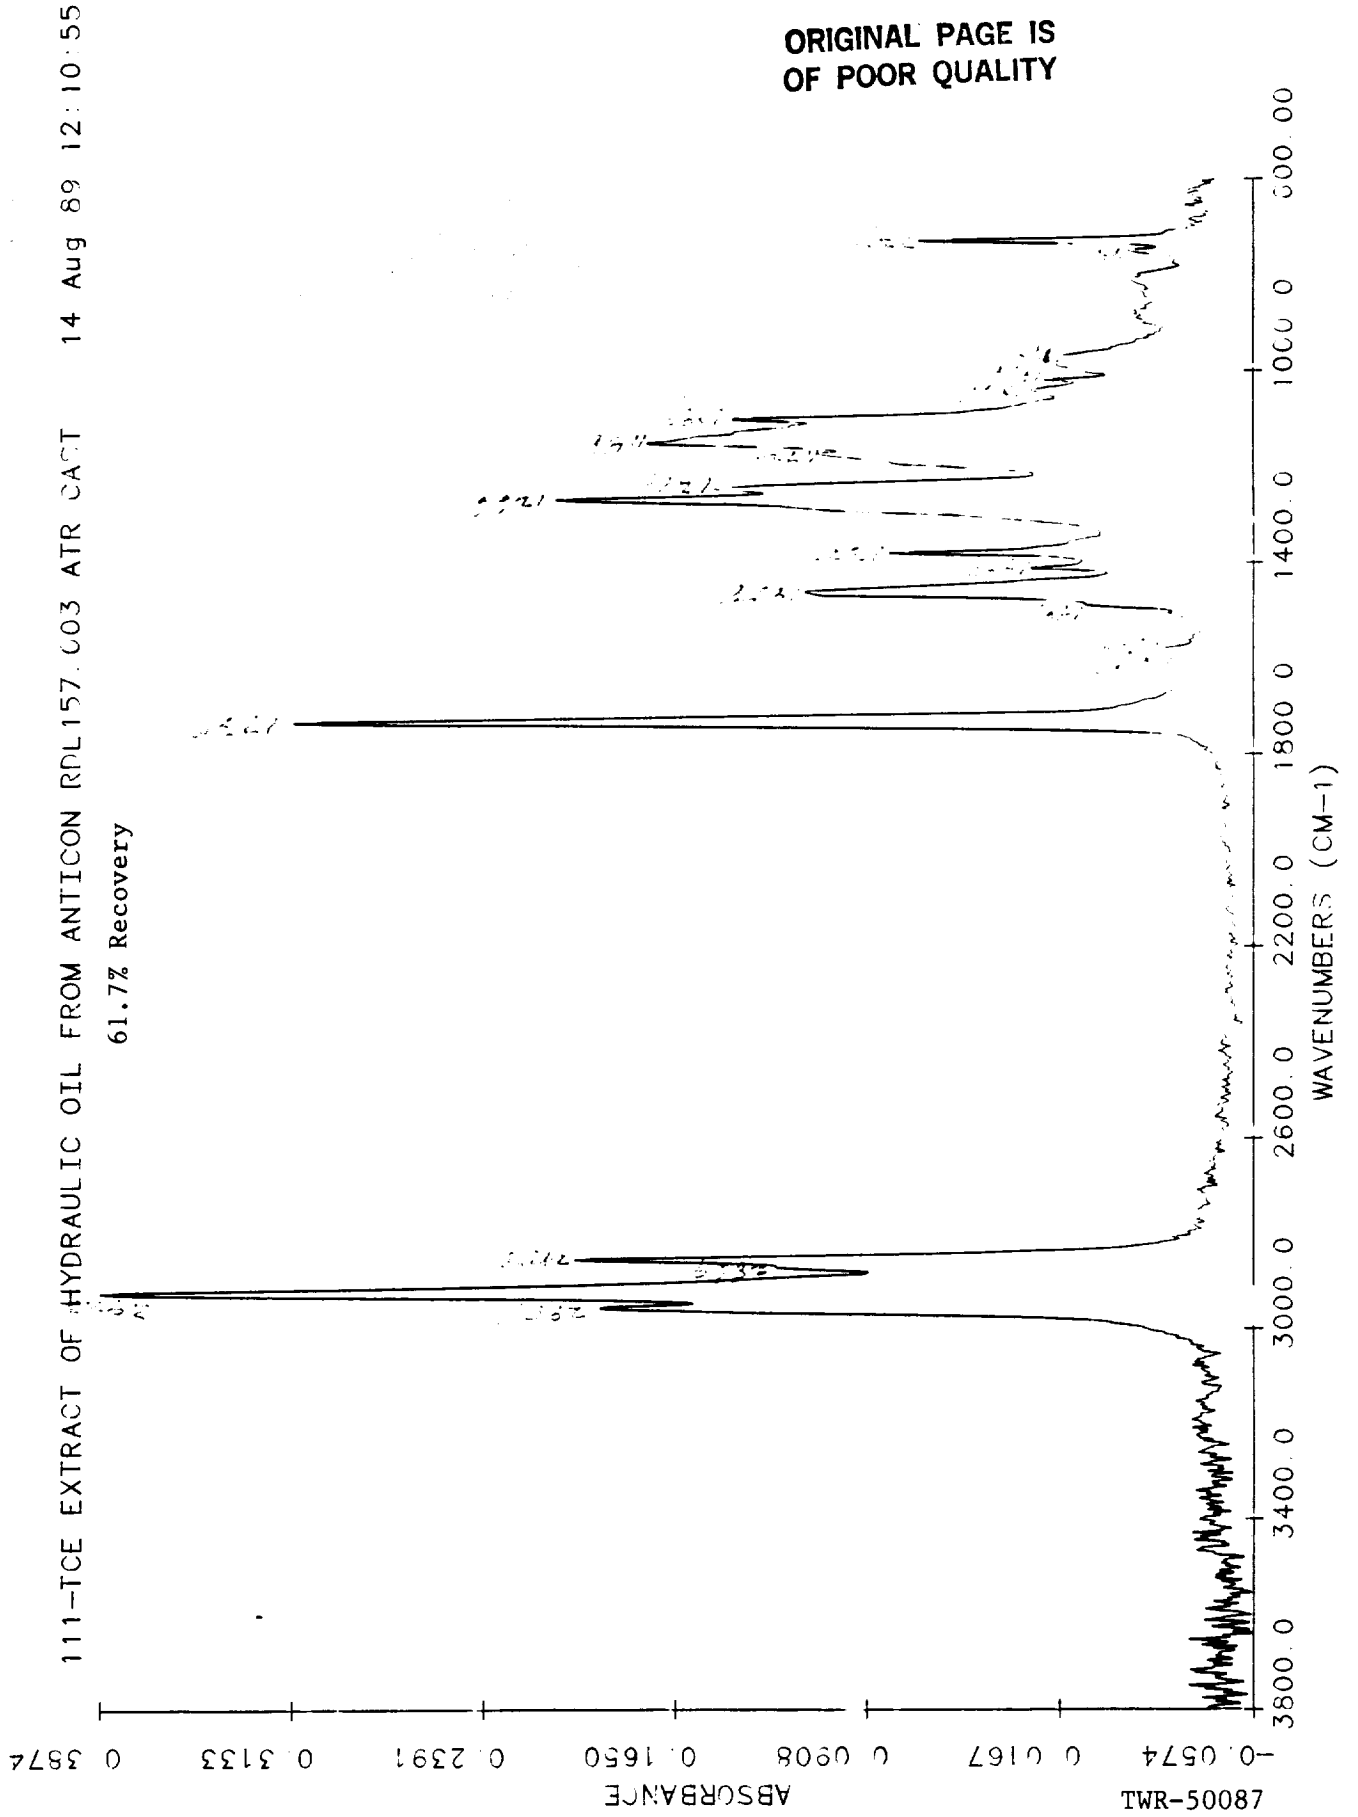


Figure 98.


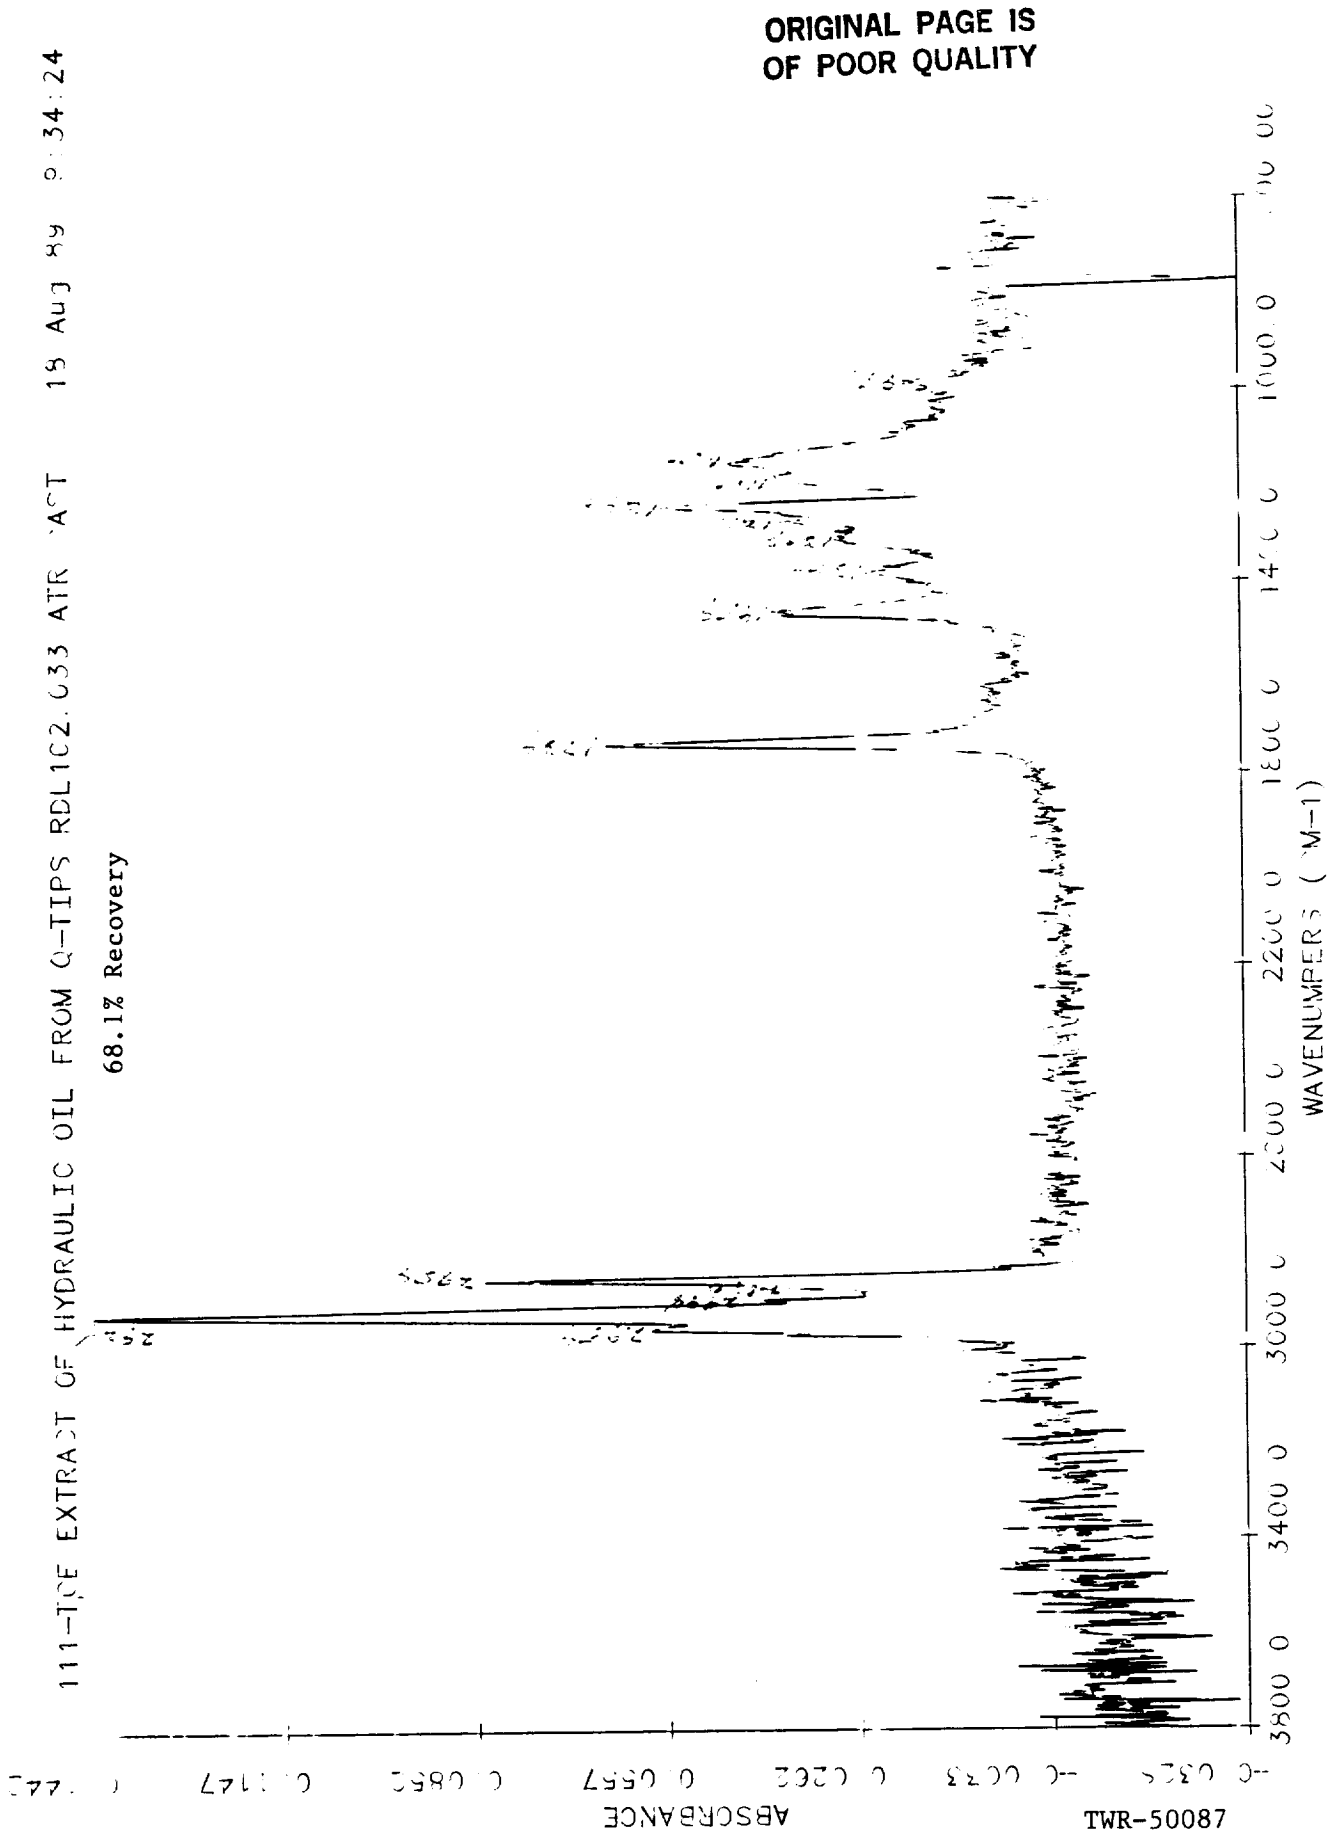


Figure 99.
FREON TF EXTRACT OF HYDRAULIC OIL FROM FABWIPE RDL165.B30 ATR CAST 28 Aug 89 13:56:06

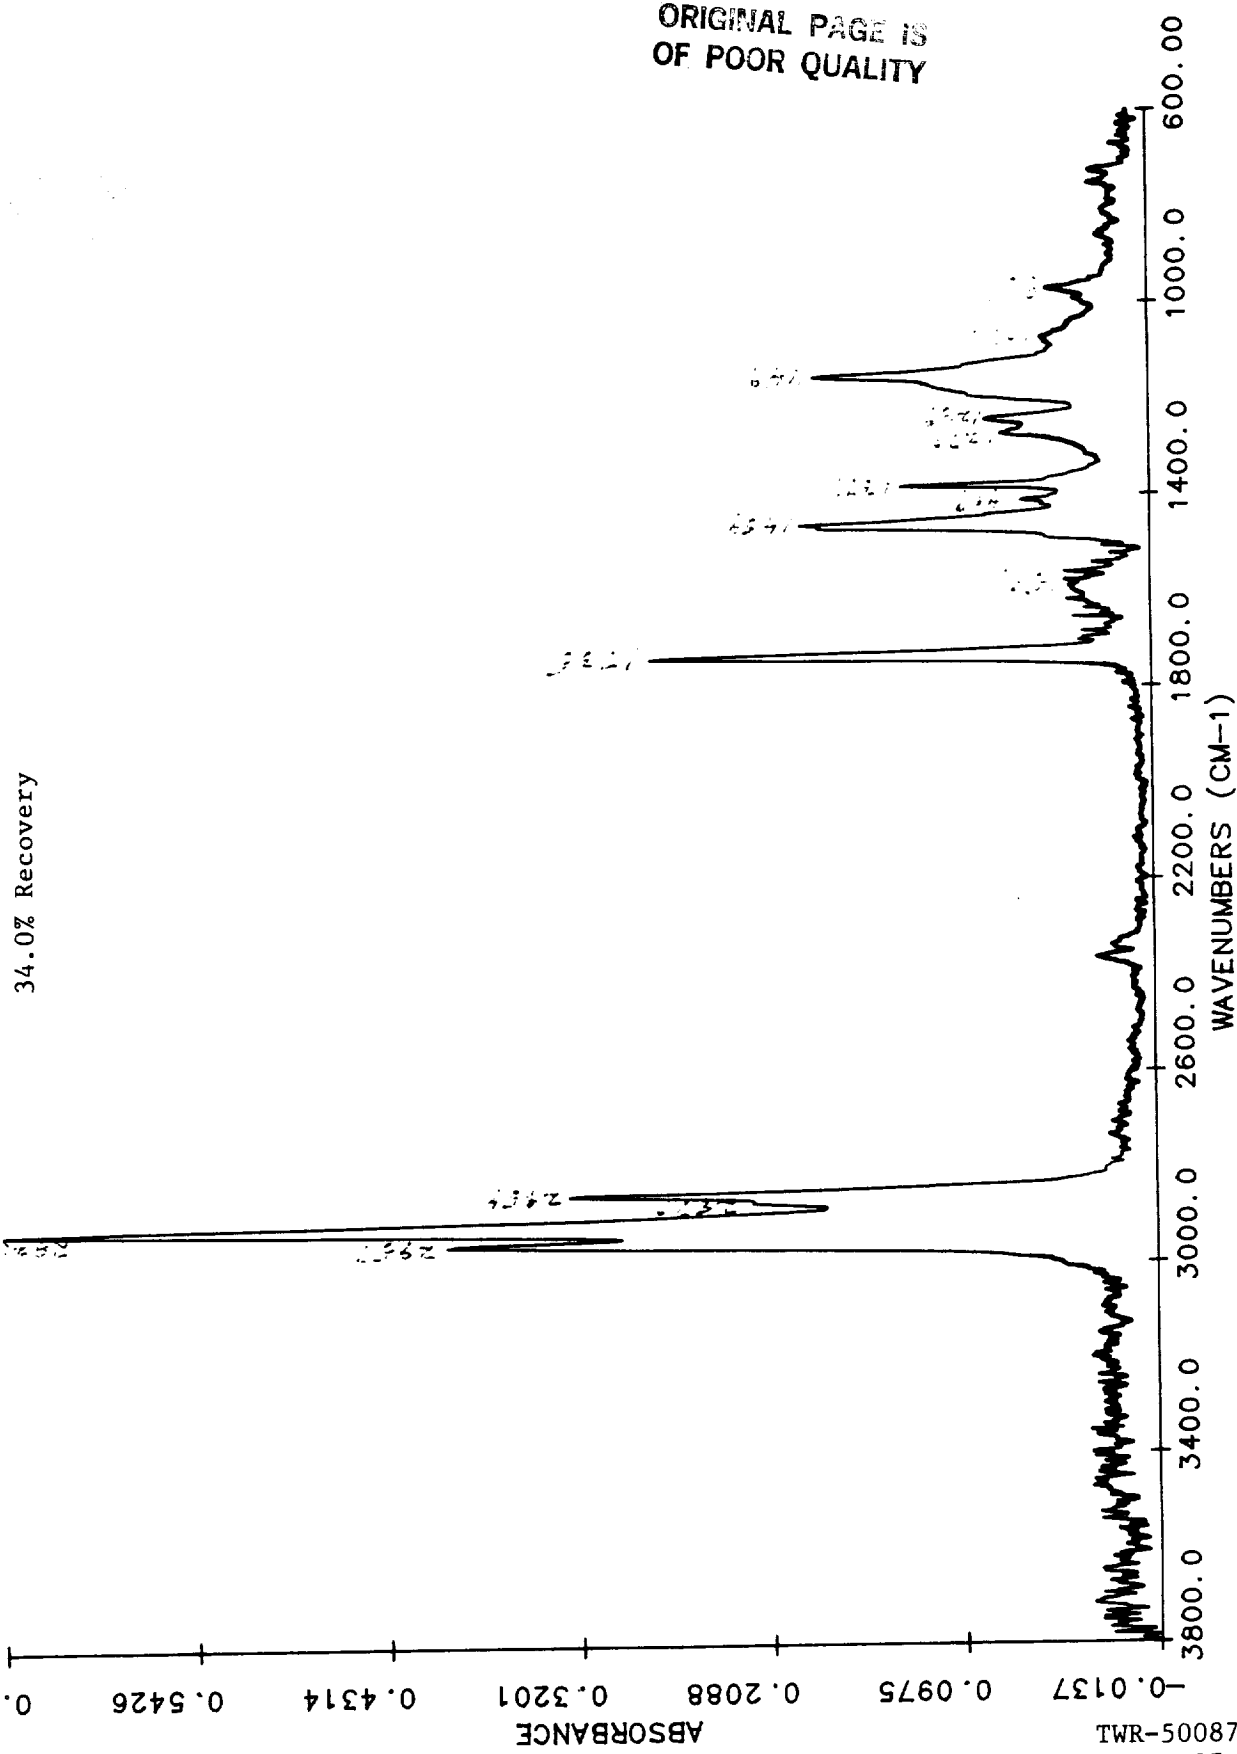

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 100.
FREON TF EXTRACT OF HYDRAULIC OIL FROM MIRACLEWIPE RDL164.B22 ATR CAST 28 Aug 89 12:55:01

46.8% Recovery

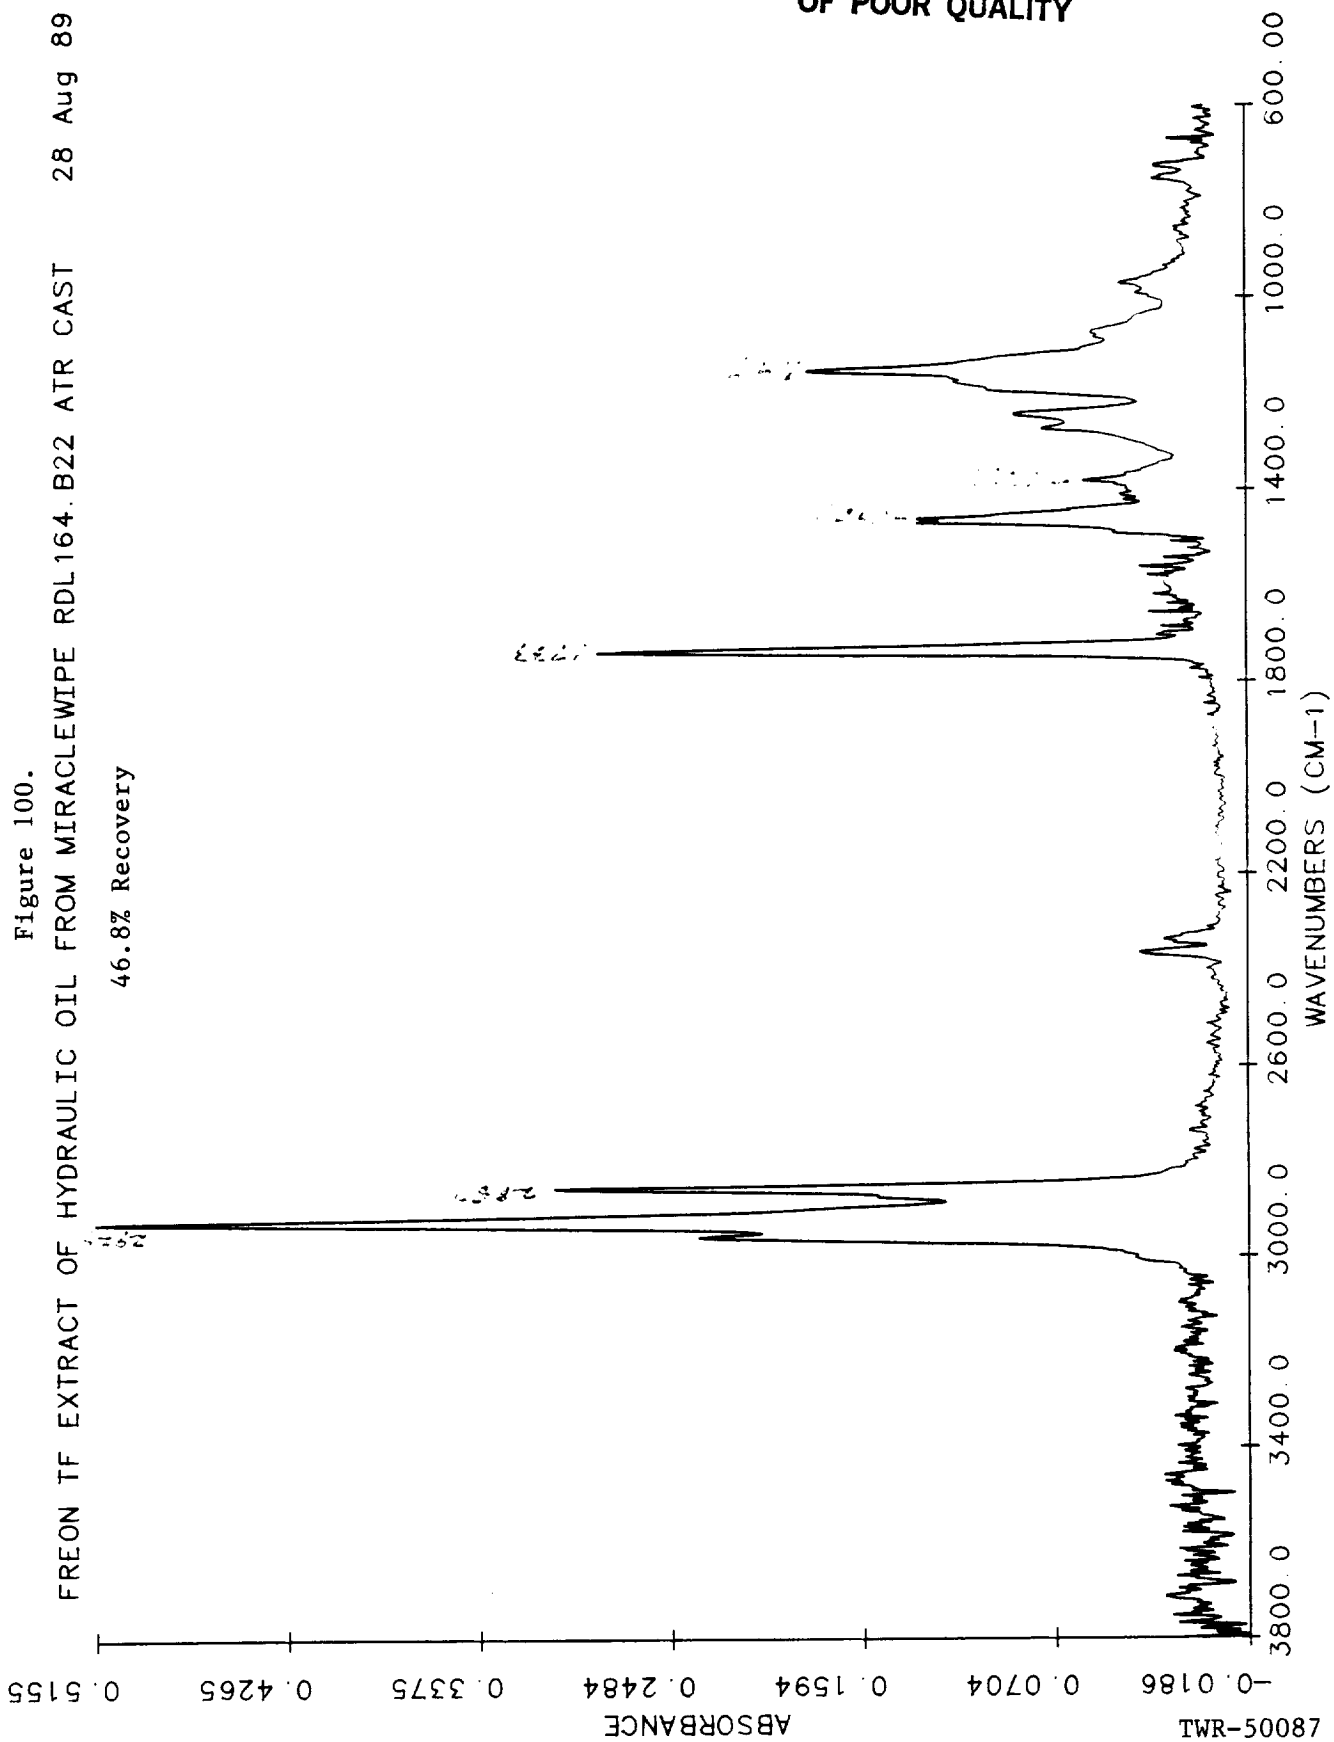


Figure 101.

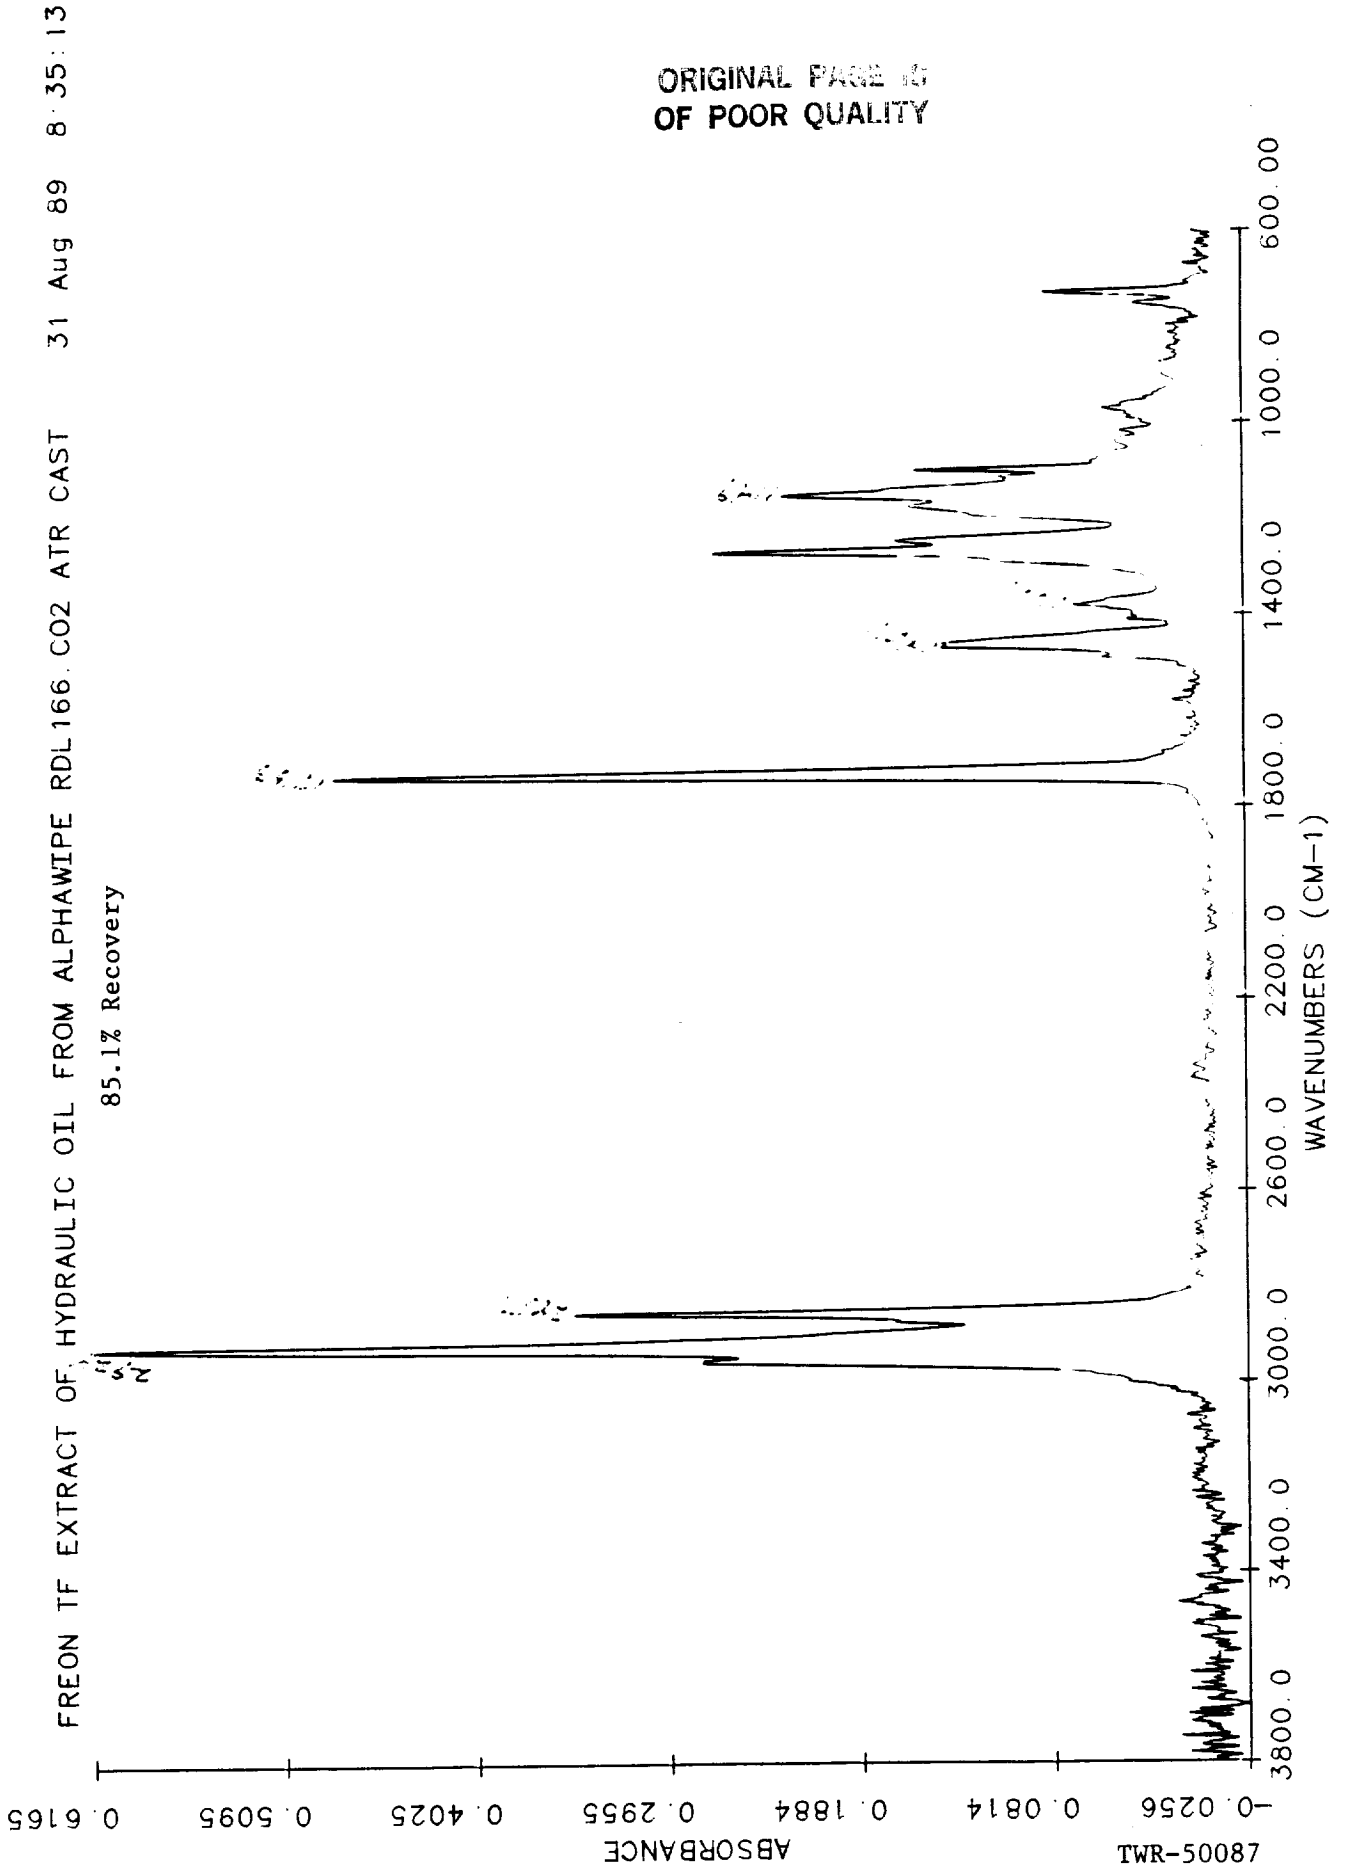


Figure 102.


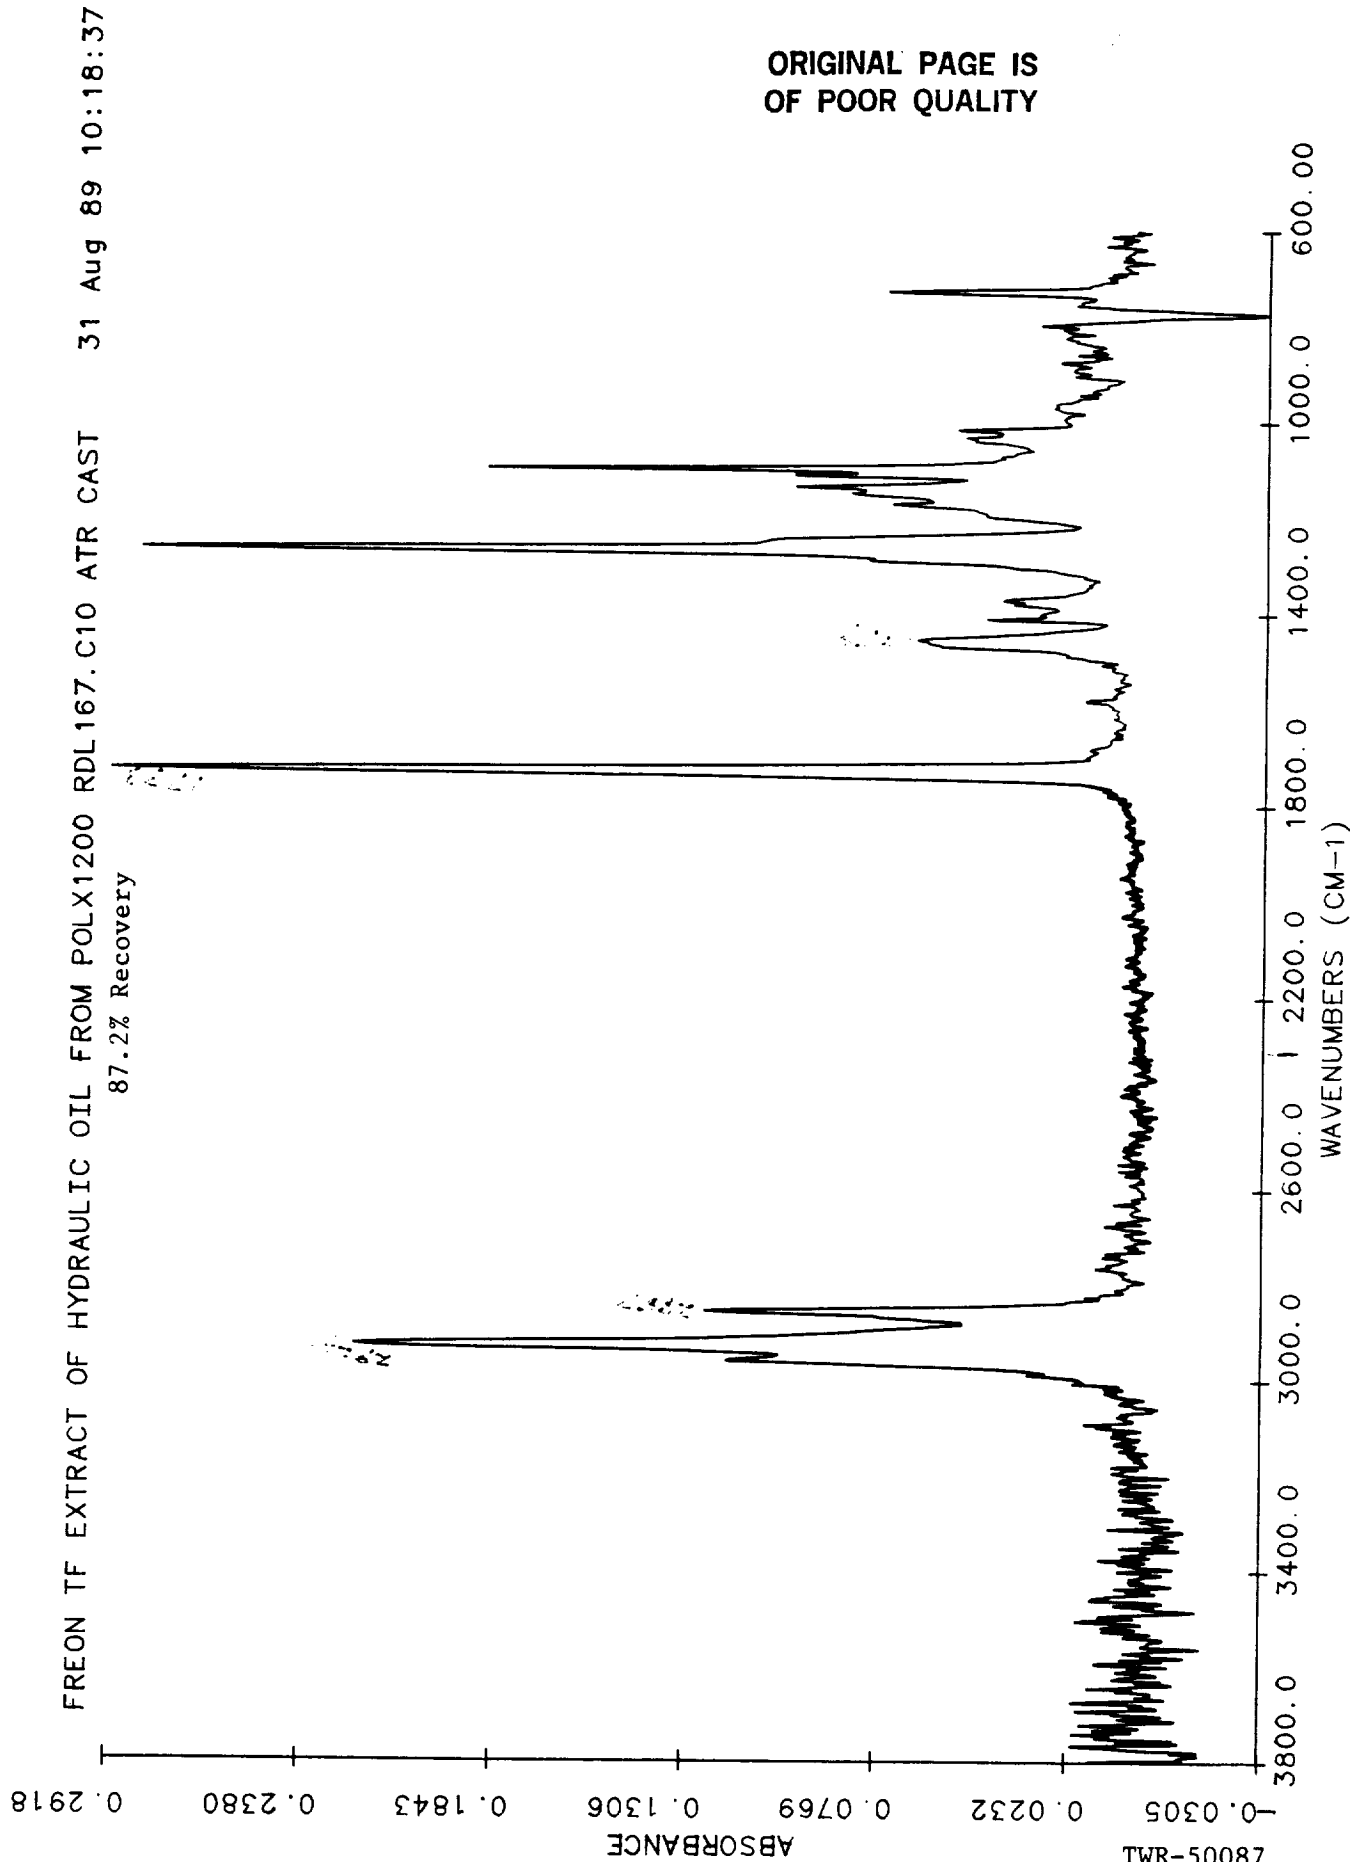


Figure 103.

FREON TF EXTRACT OF HYDRAULIC OIL FROM ANTICON RDL163.B15 ATR CAST 23 Aug 89 9:41:54

31.9% Recovery

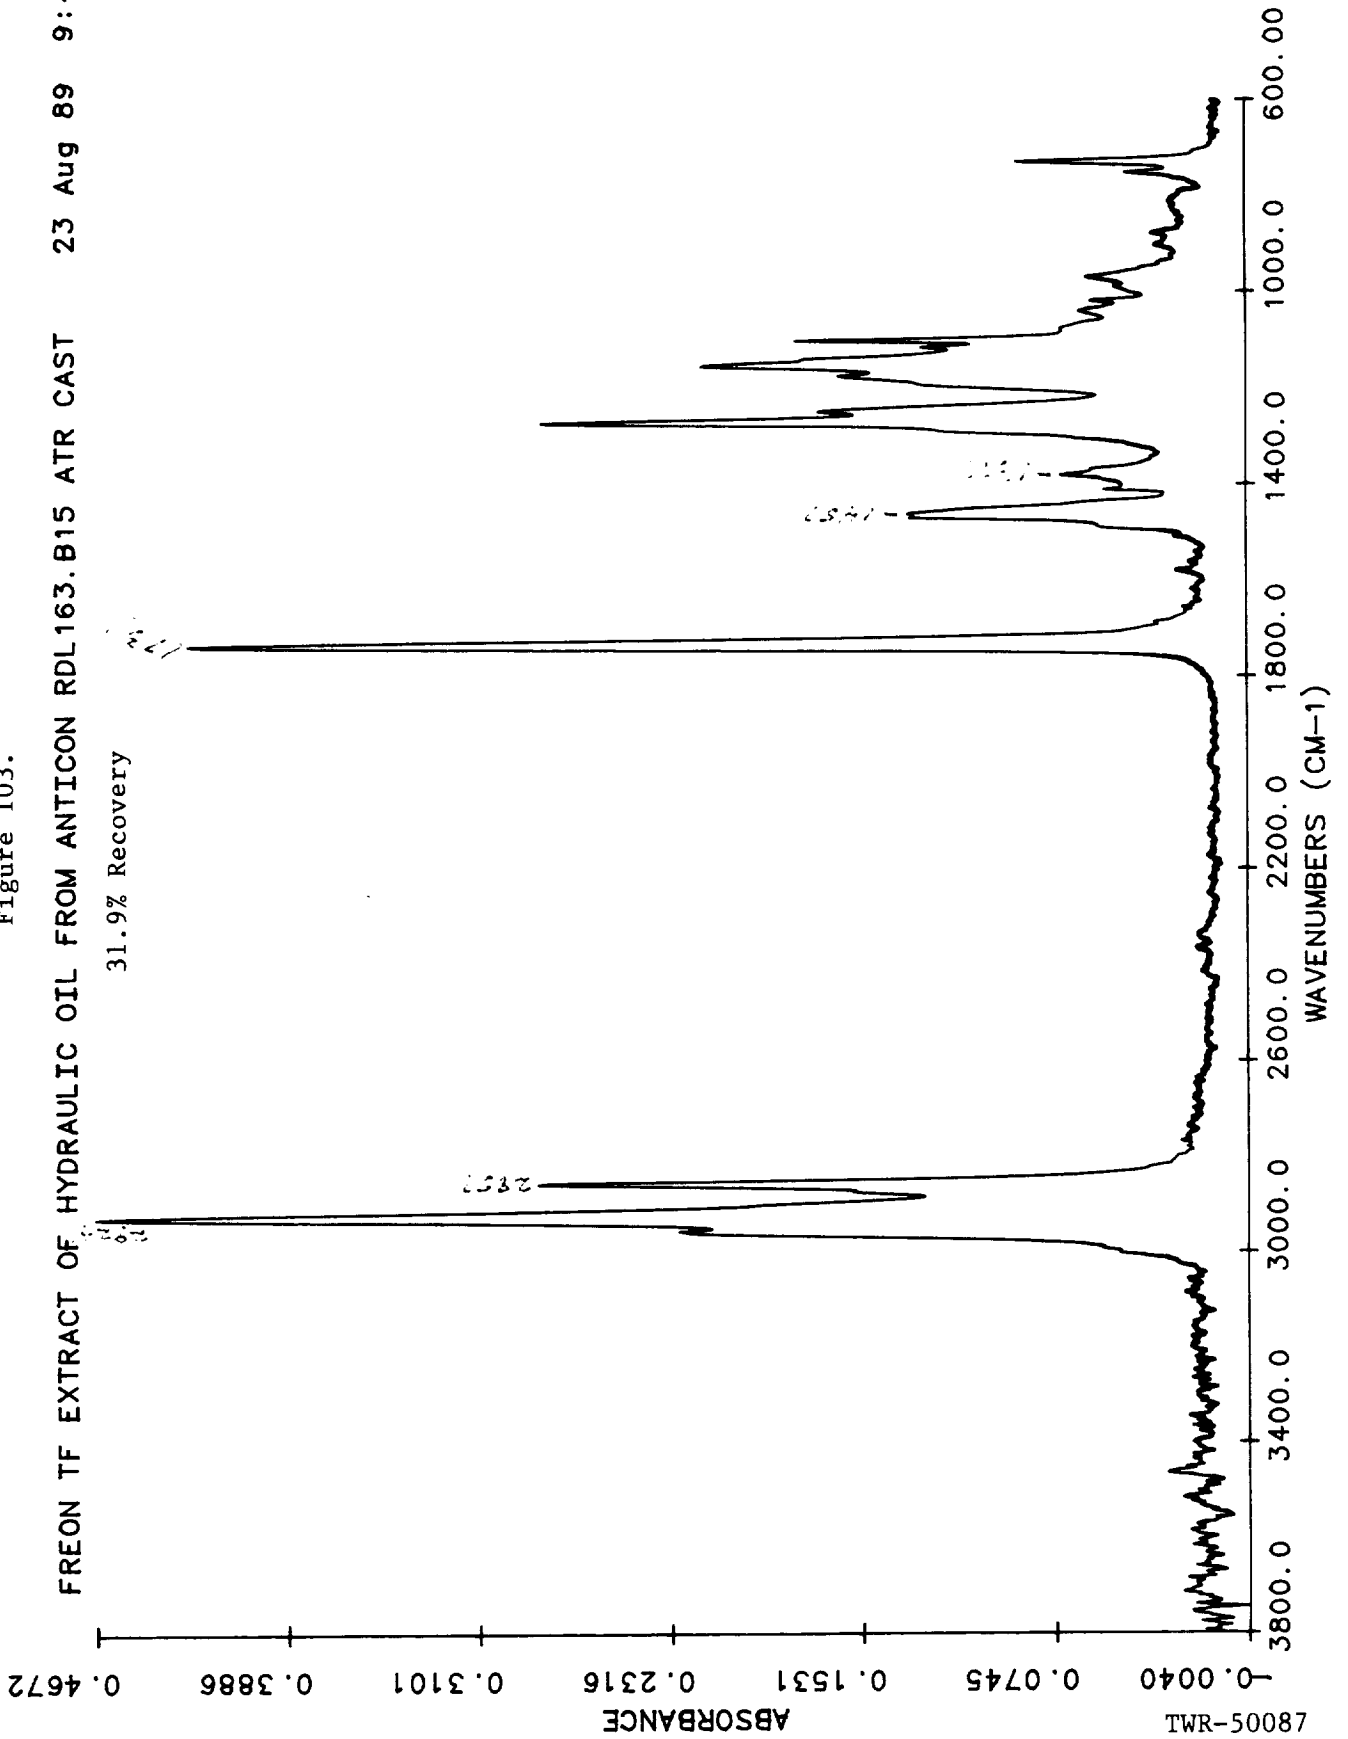

ORIGINAL PAGE IS
OF POOR QUALITY

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 104.

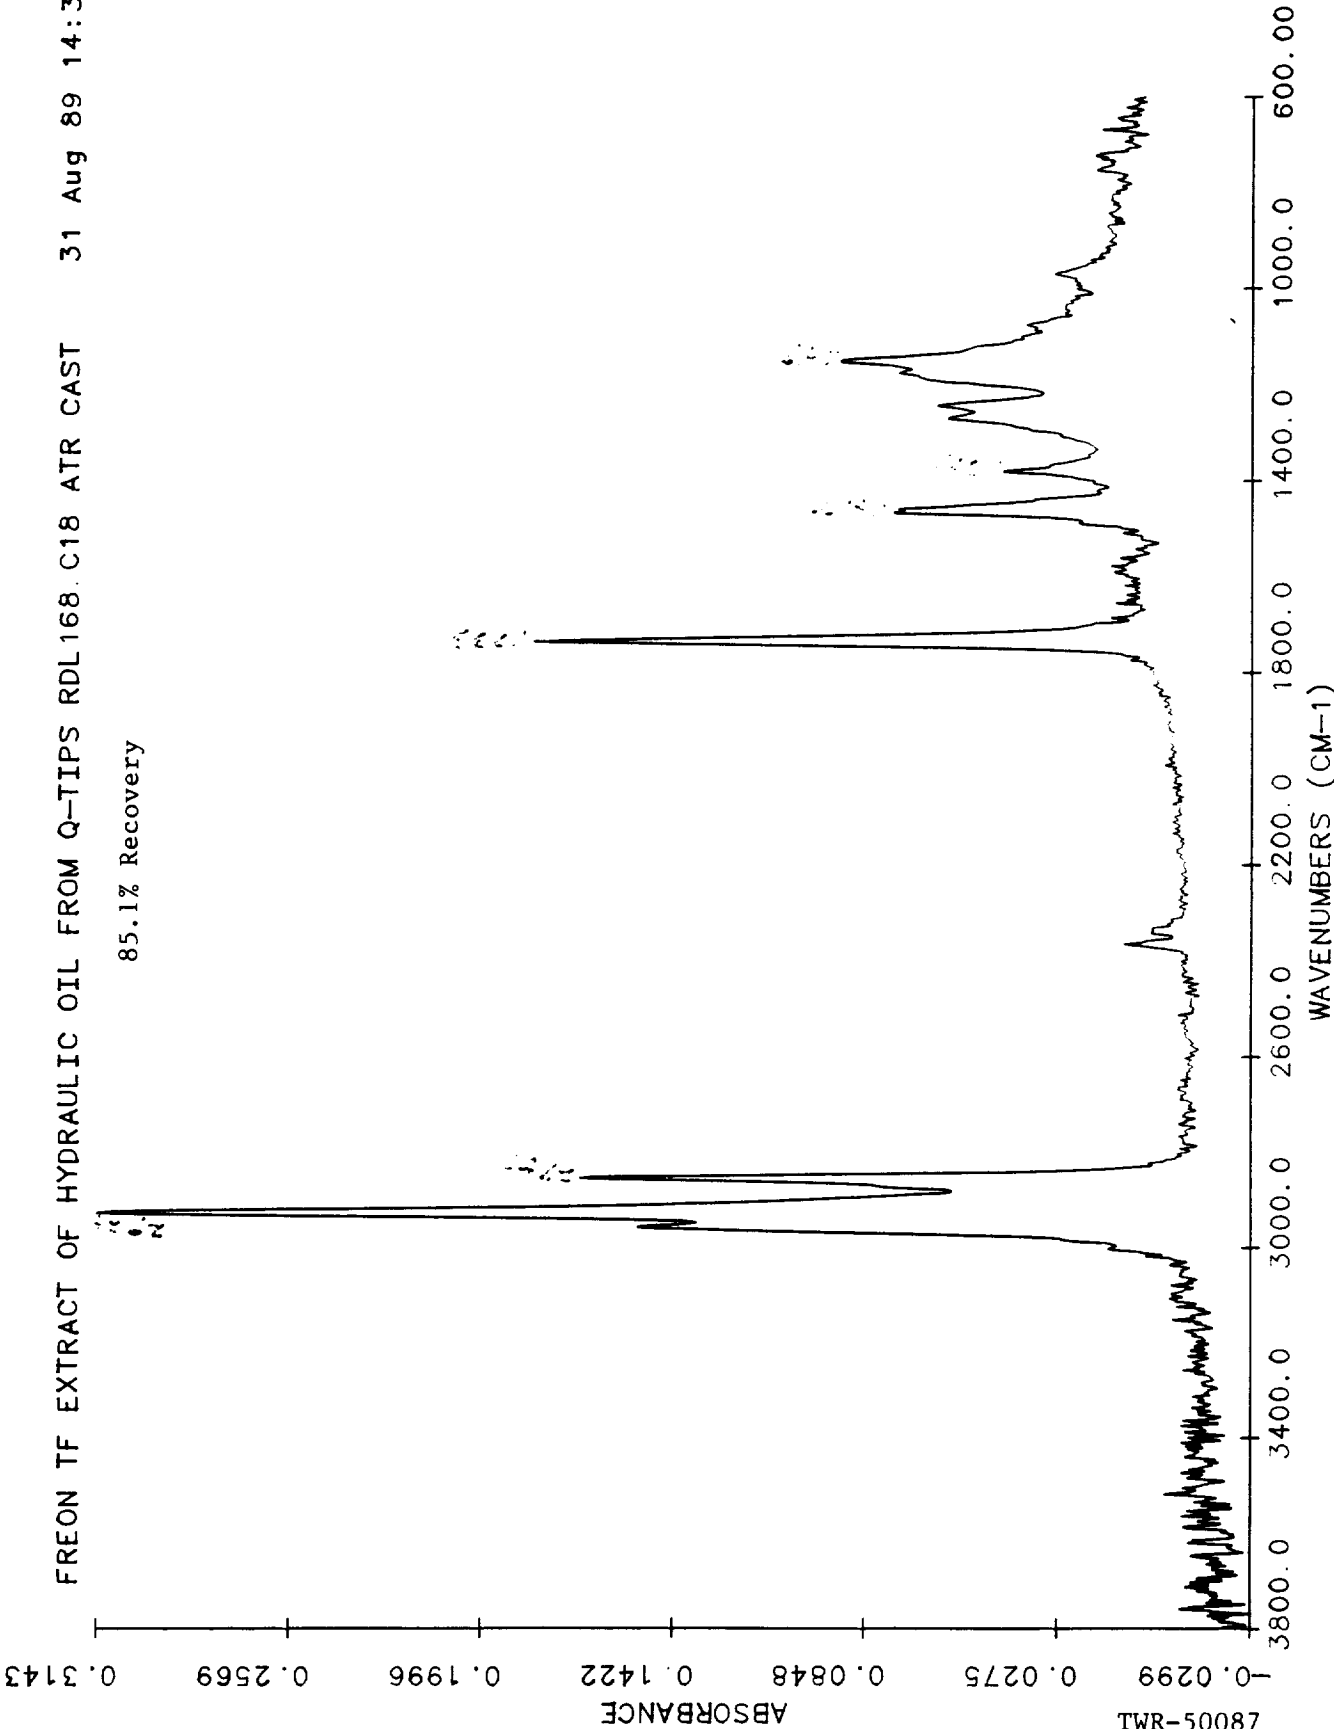


Figure 105.



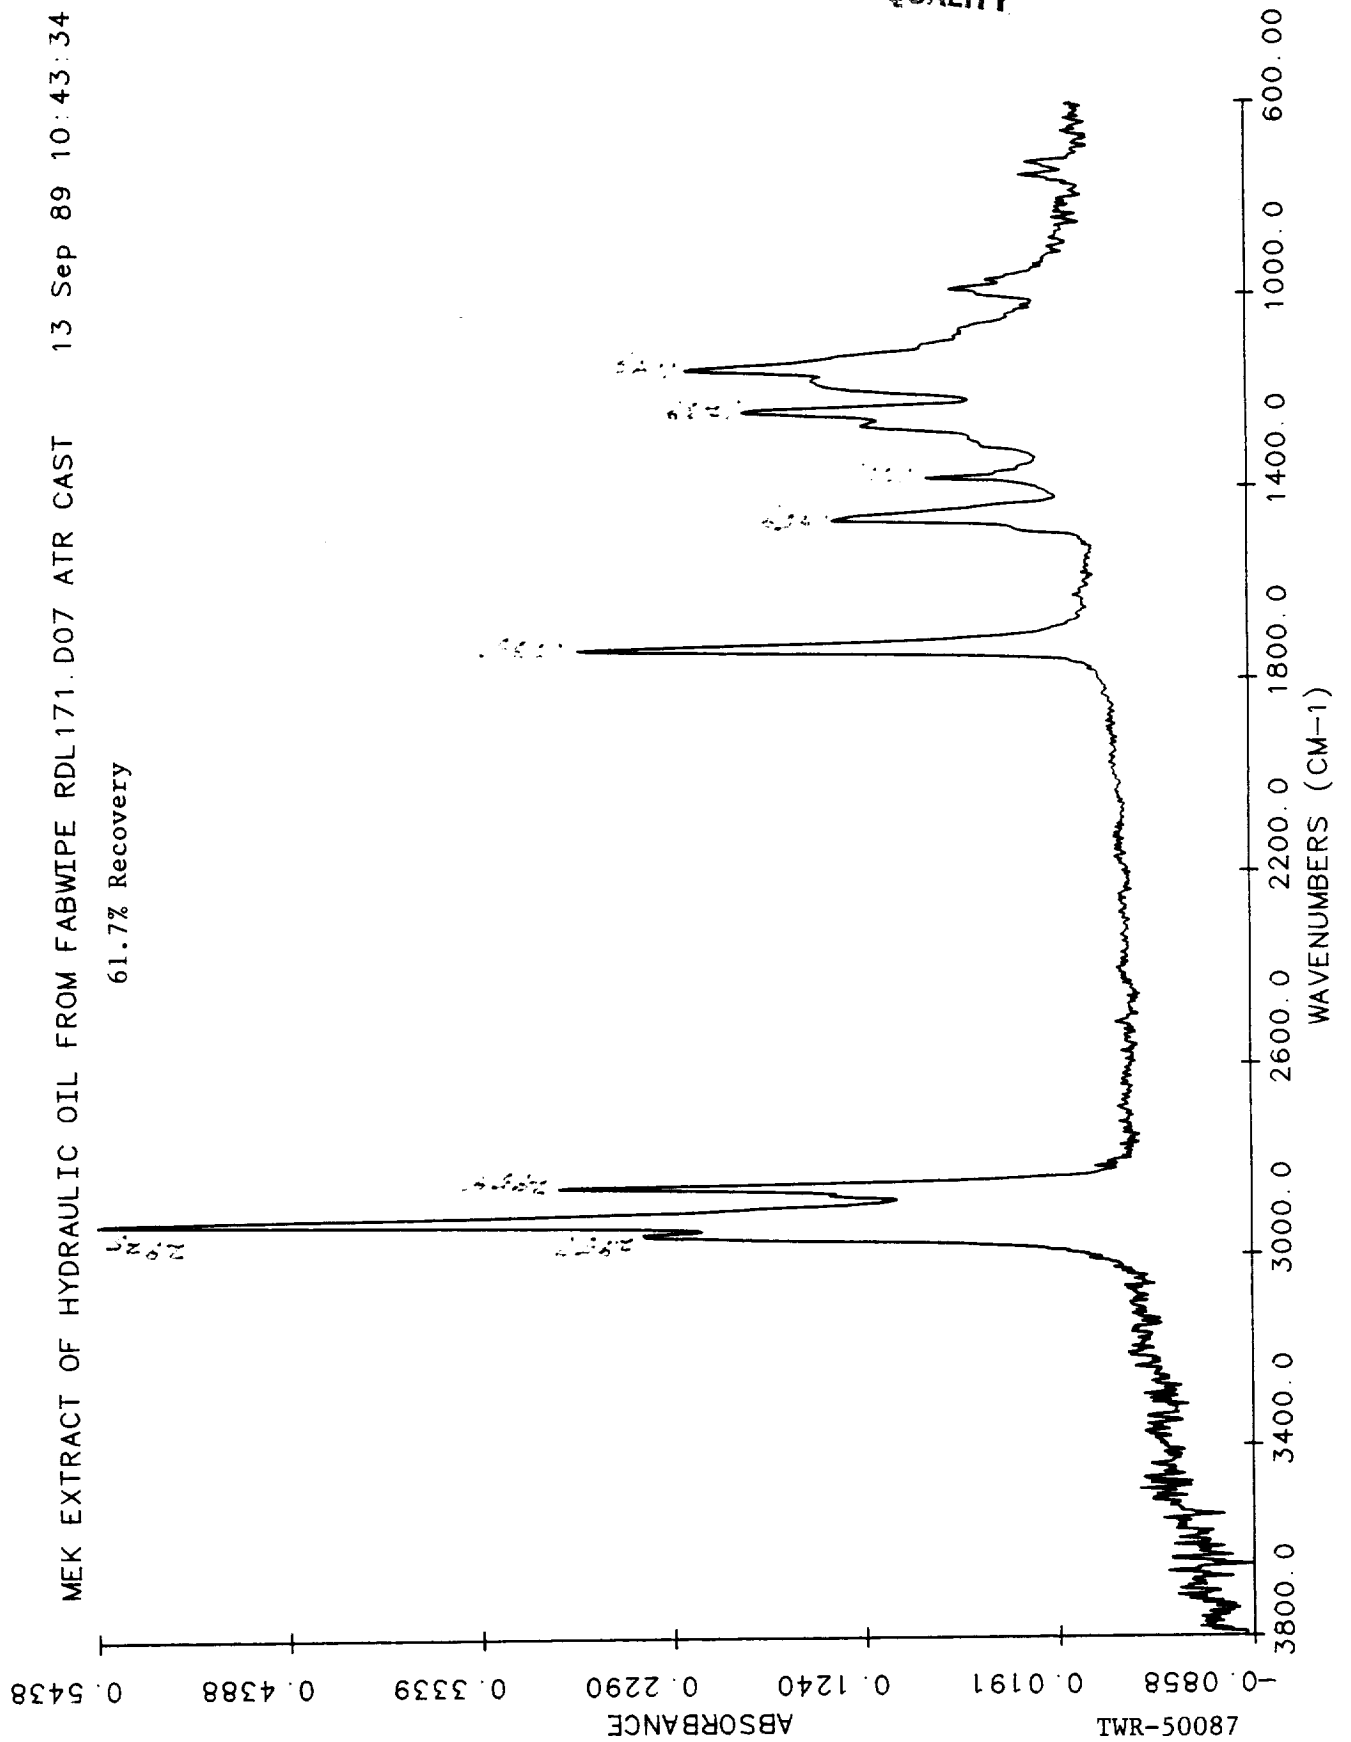


Figure 106.

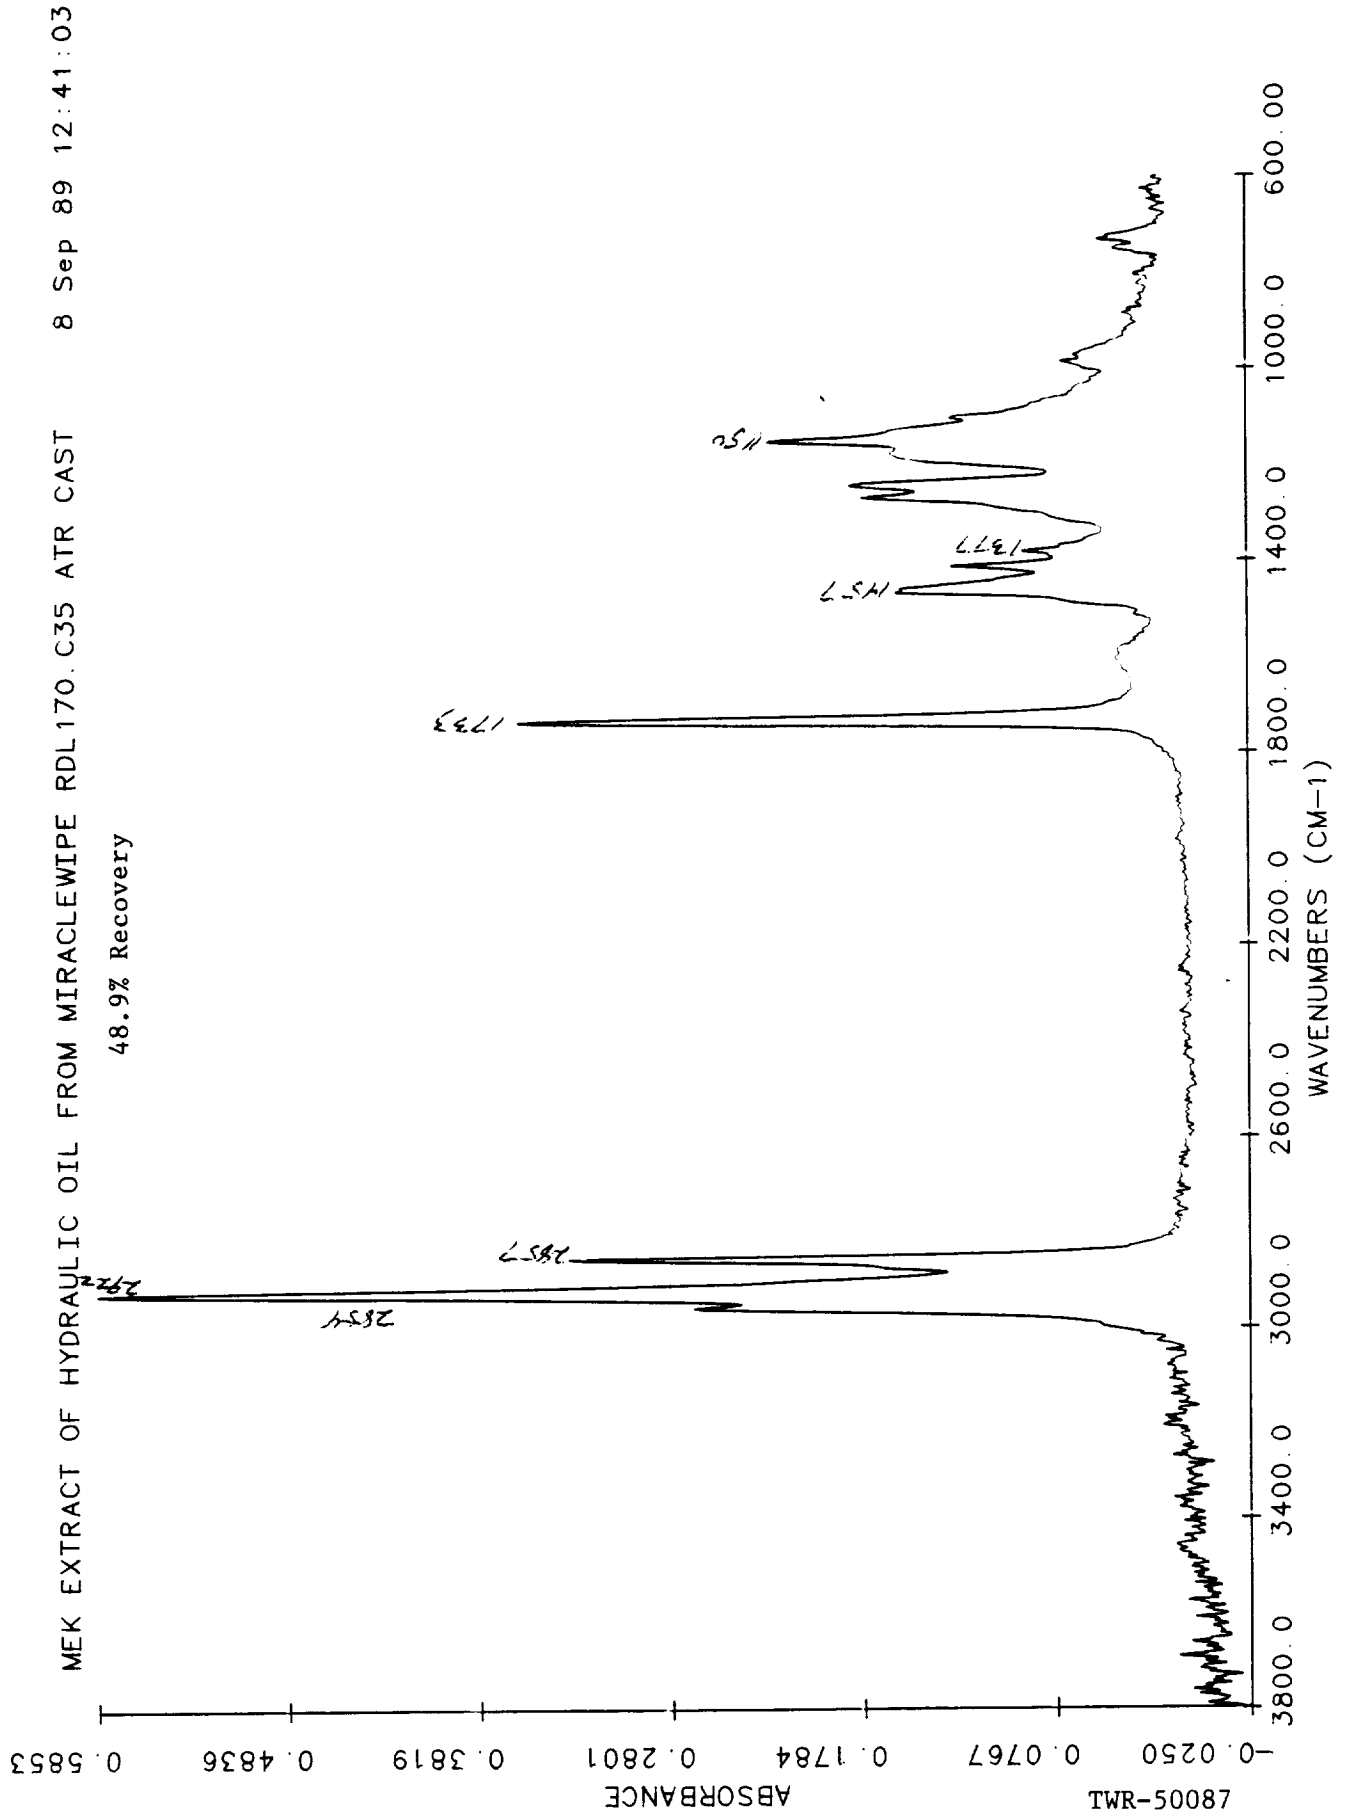

MEK EXTRACT OF HYDRAULIC OIL FROM ALPHAWIPE RDL172.D15 ATR CAST 13 Sep 89 12:58:13

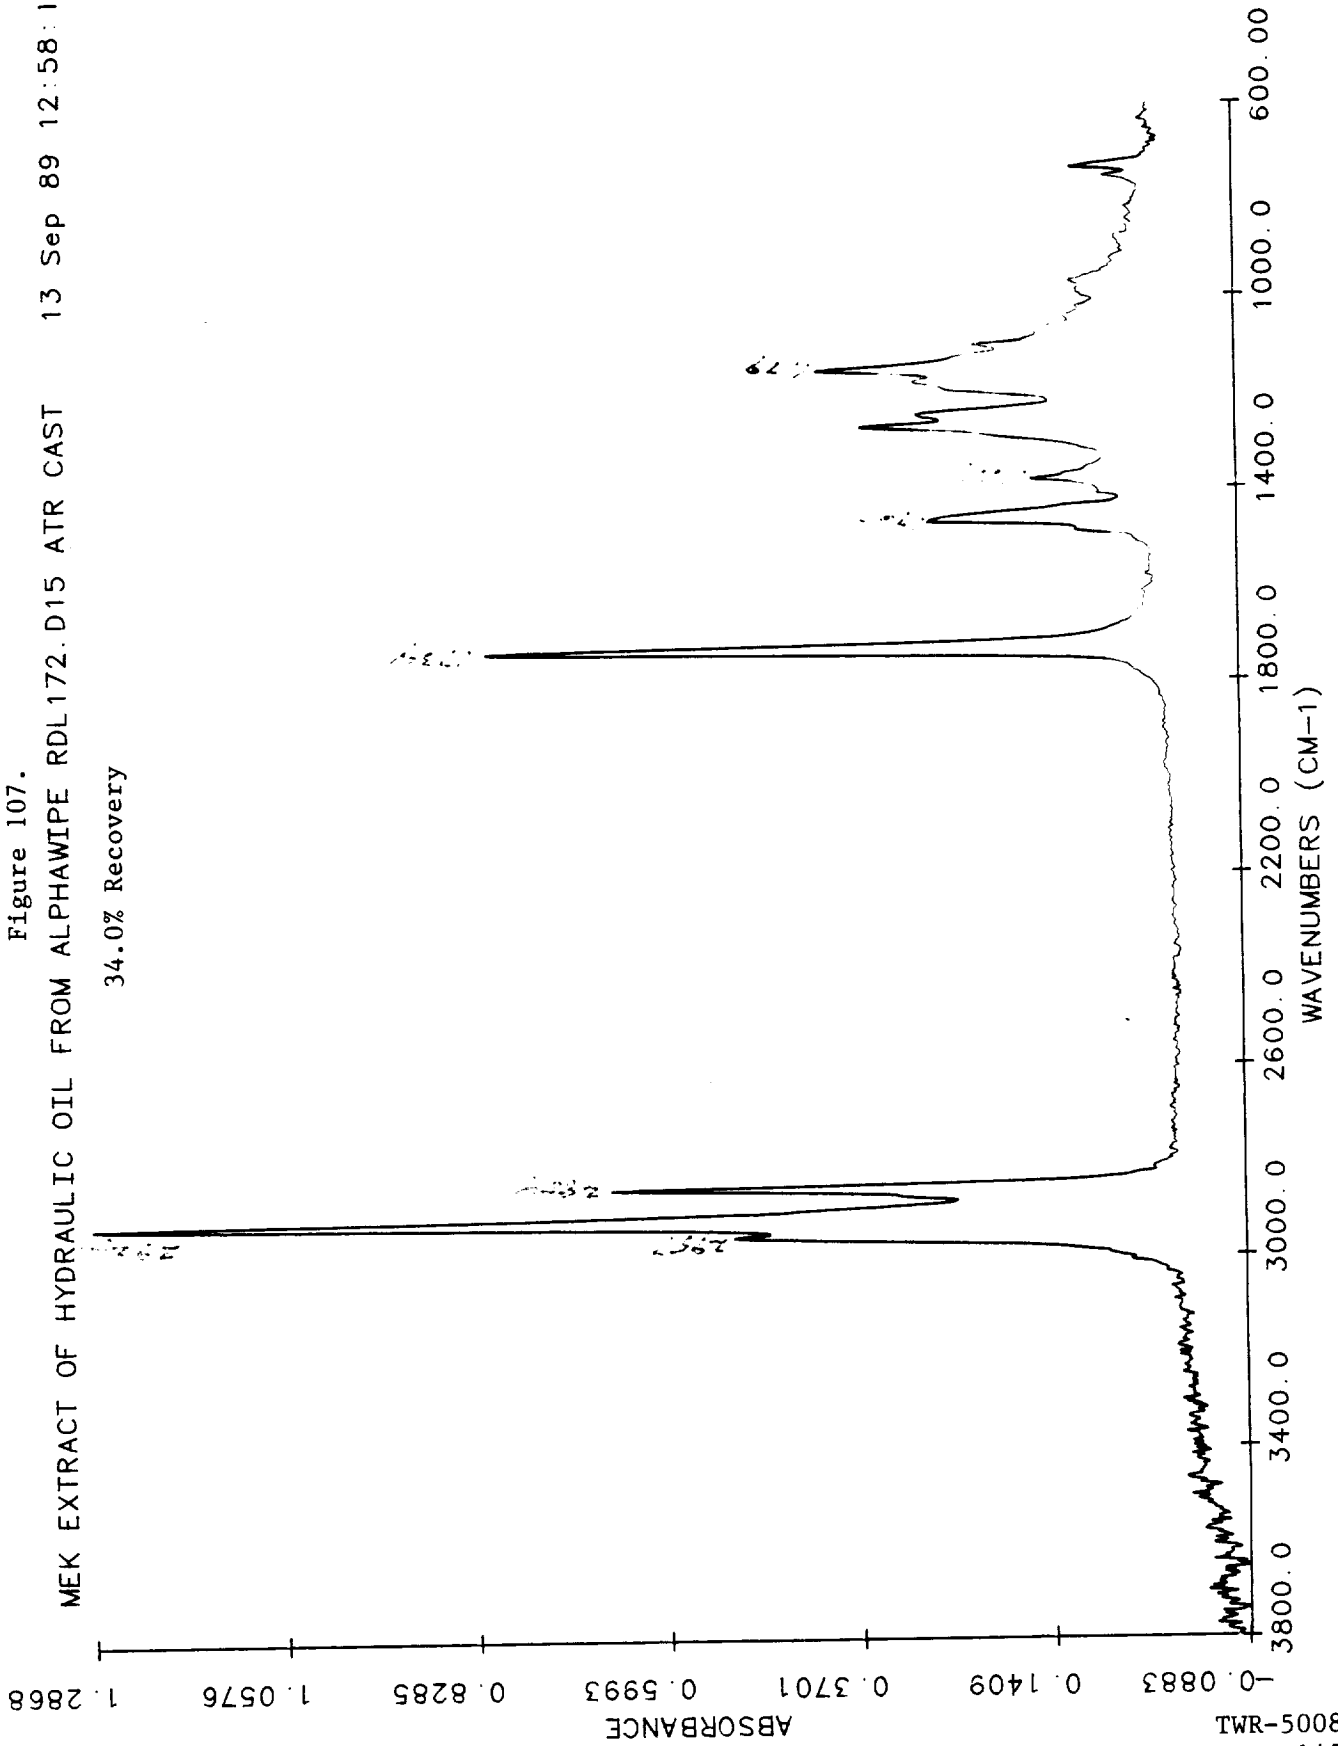

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 108.


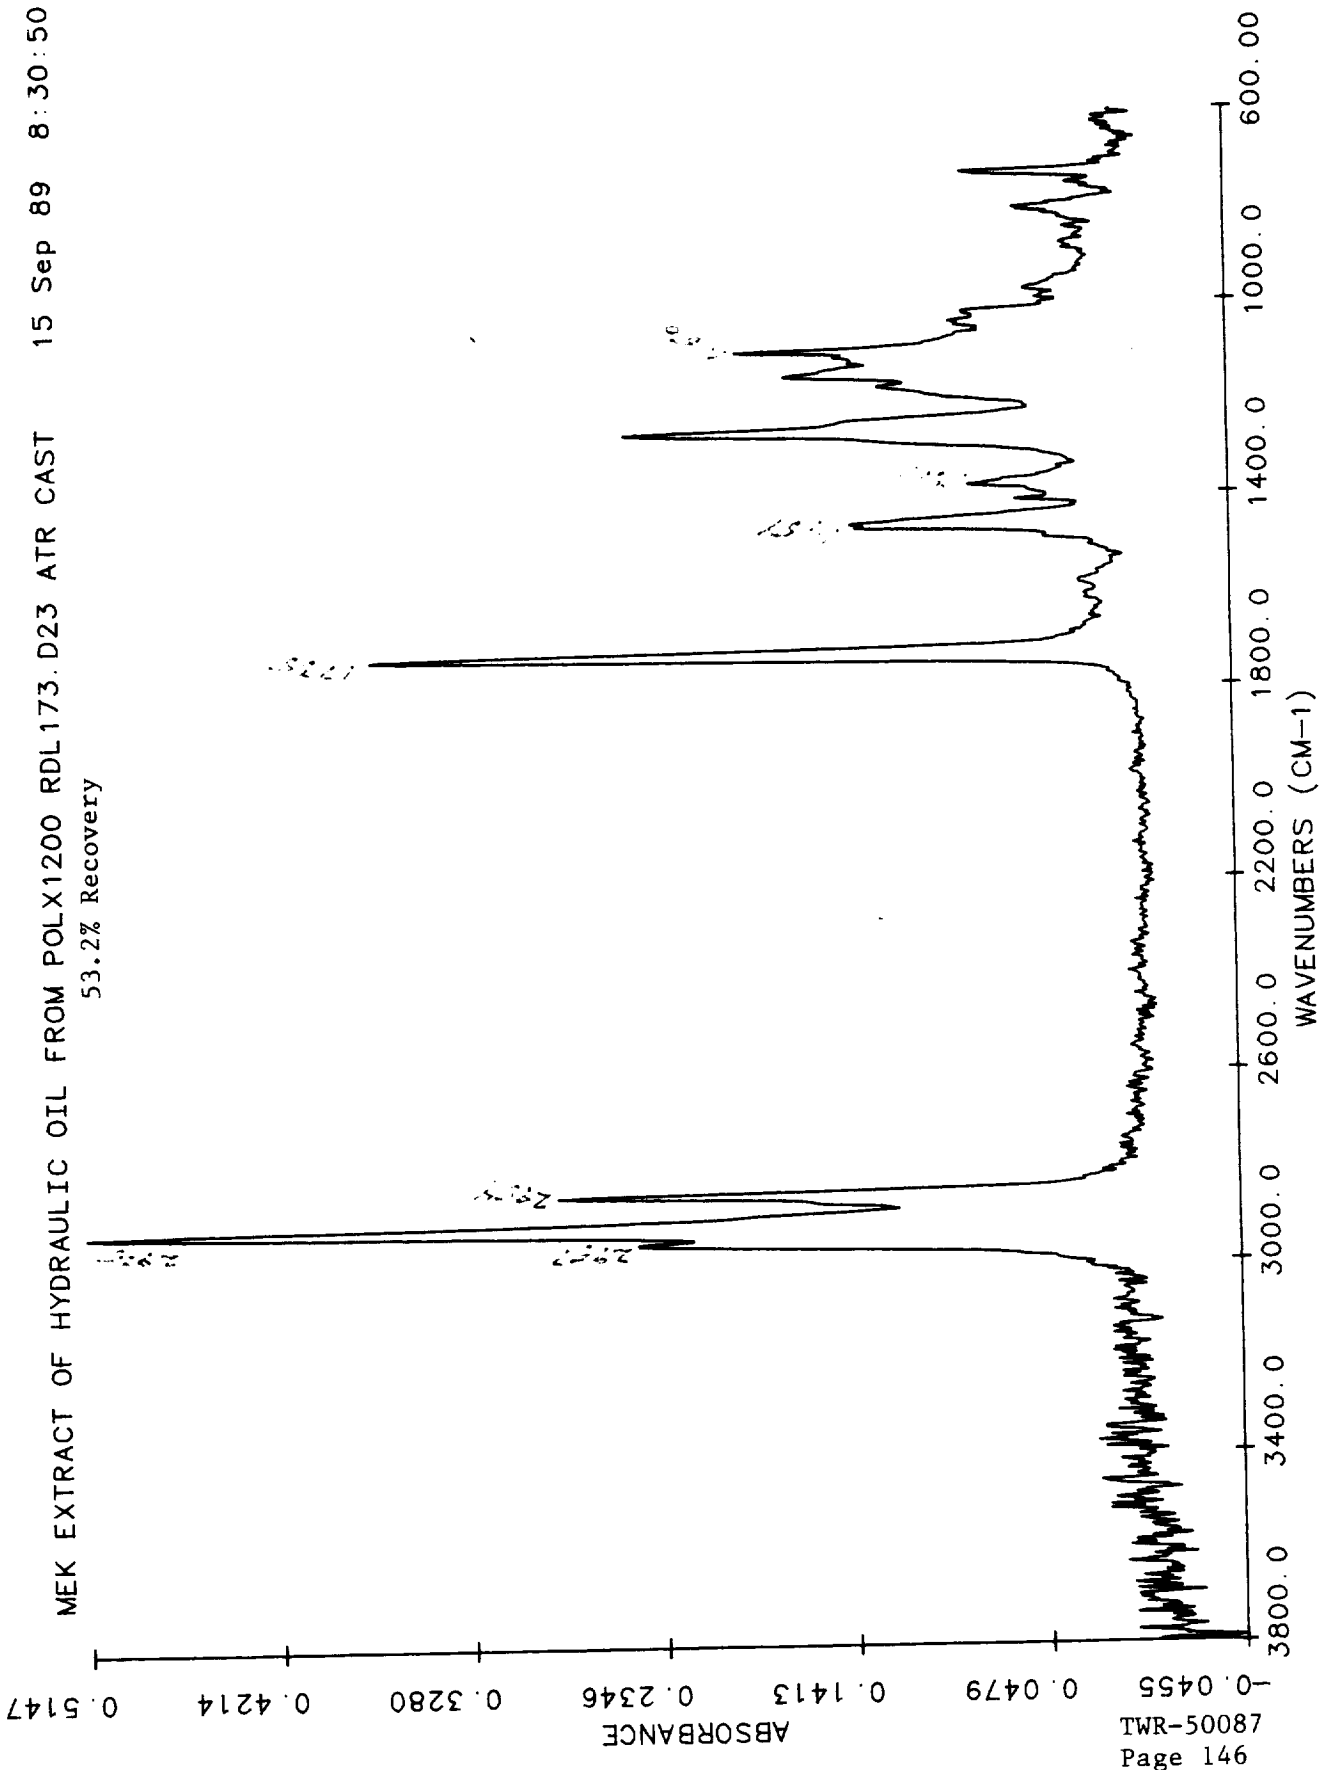


Figure 109.

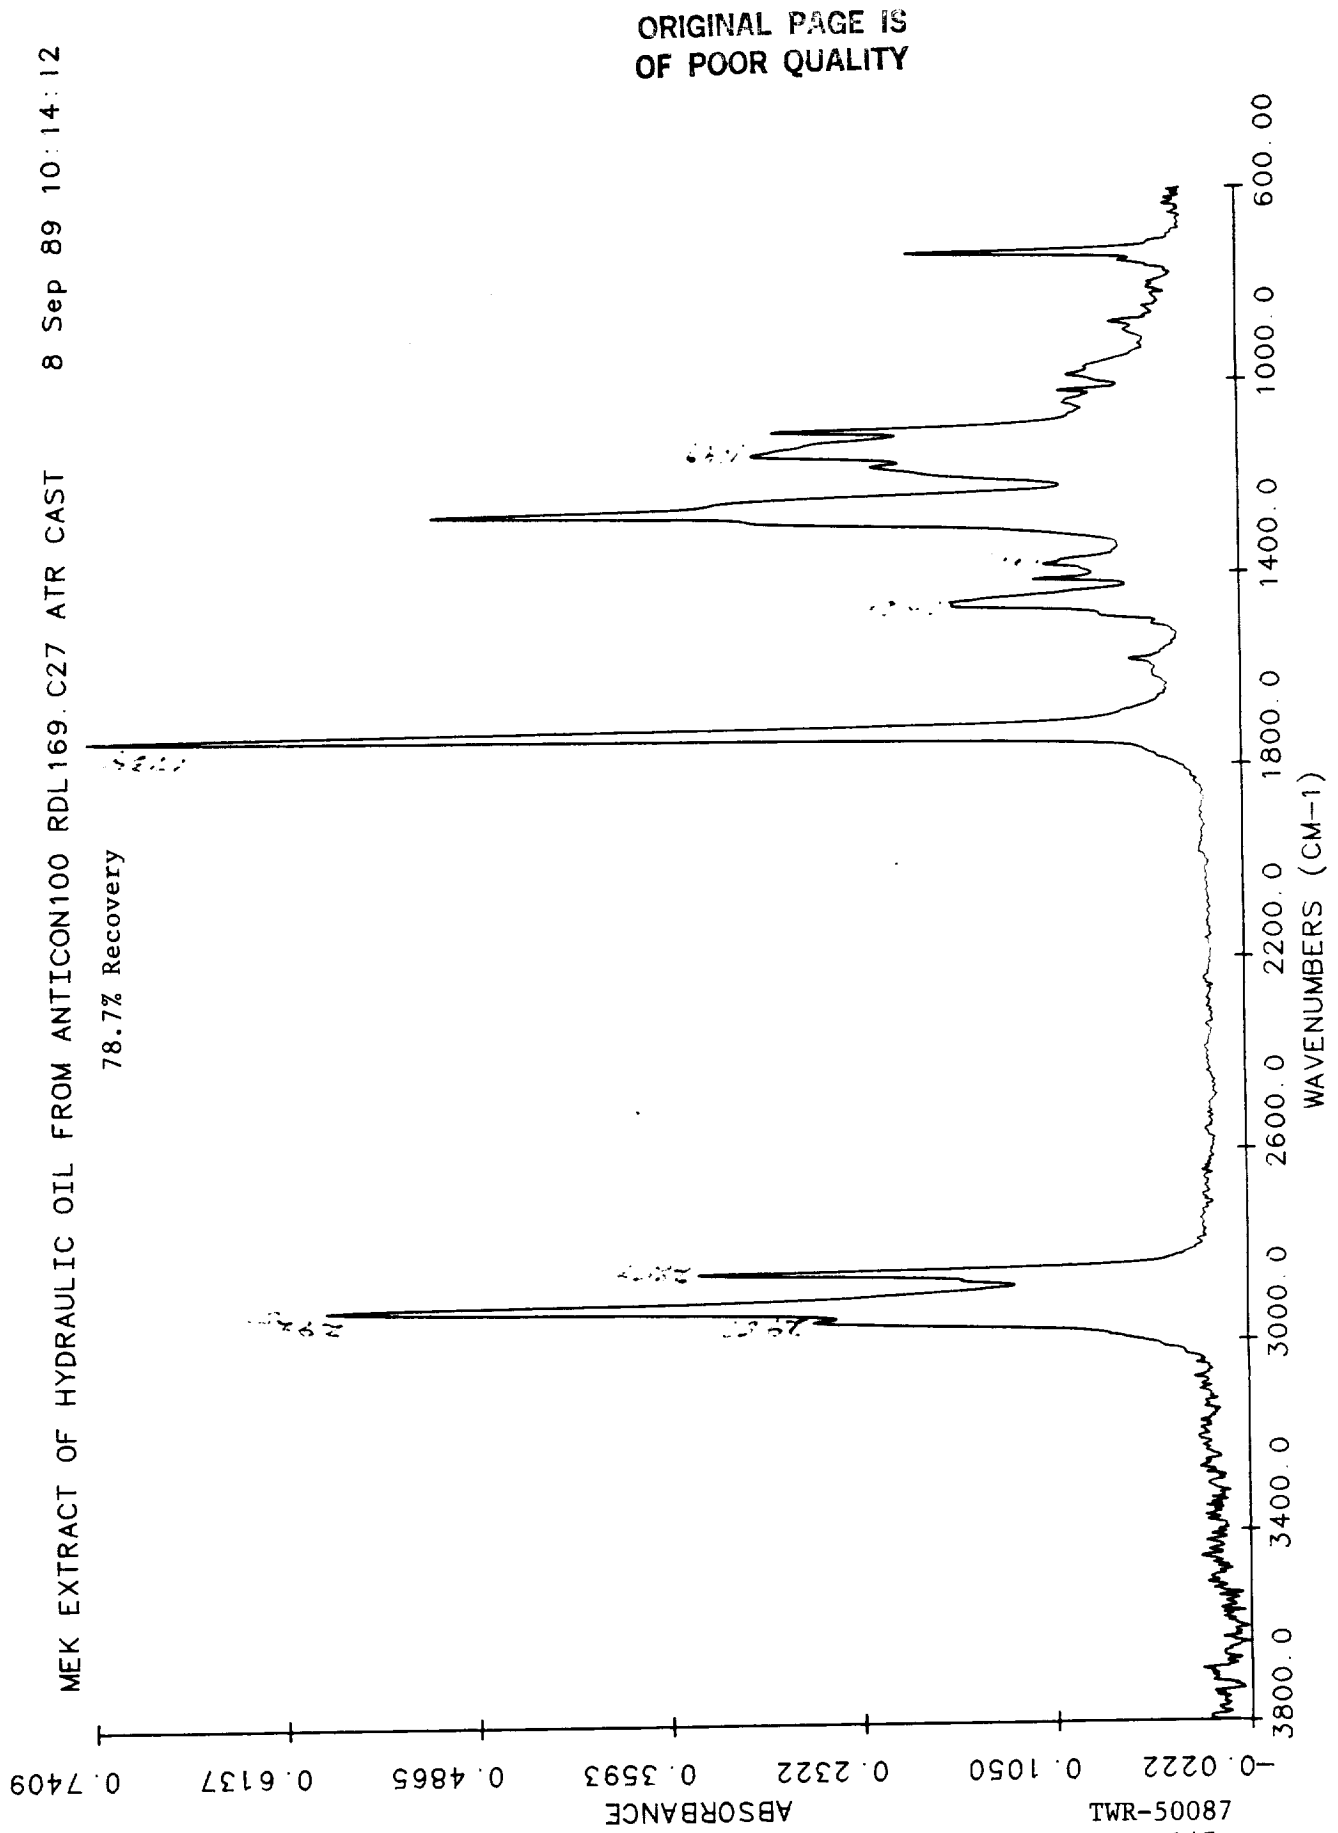

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 110.


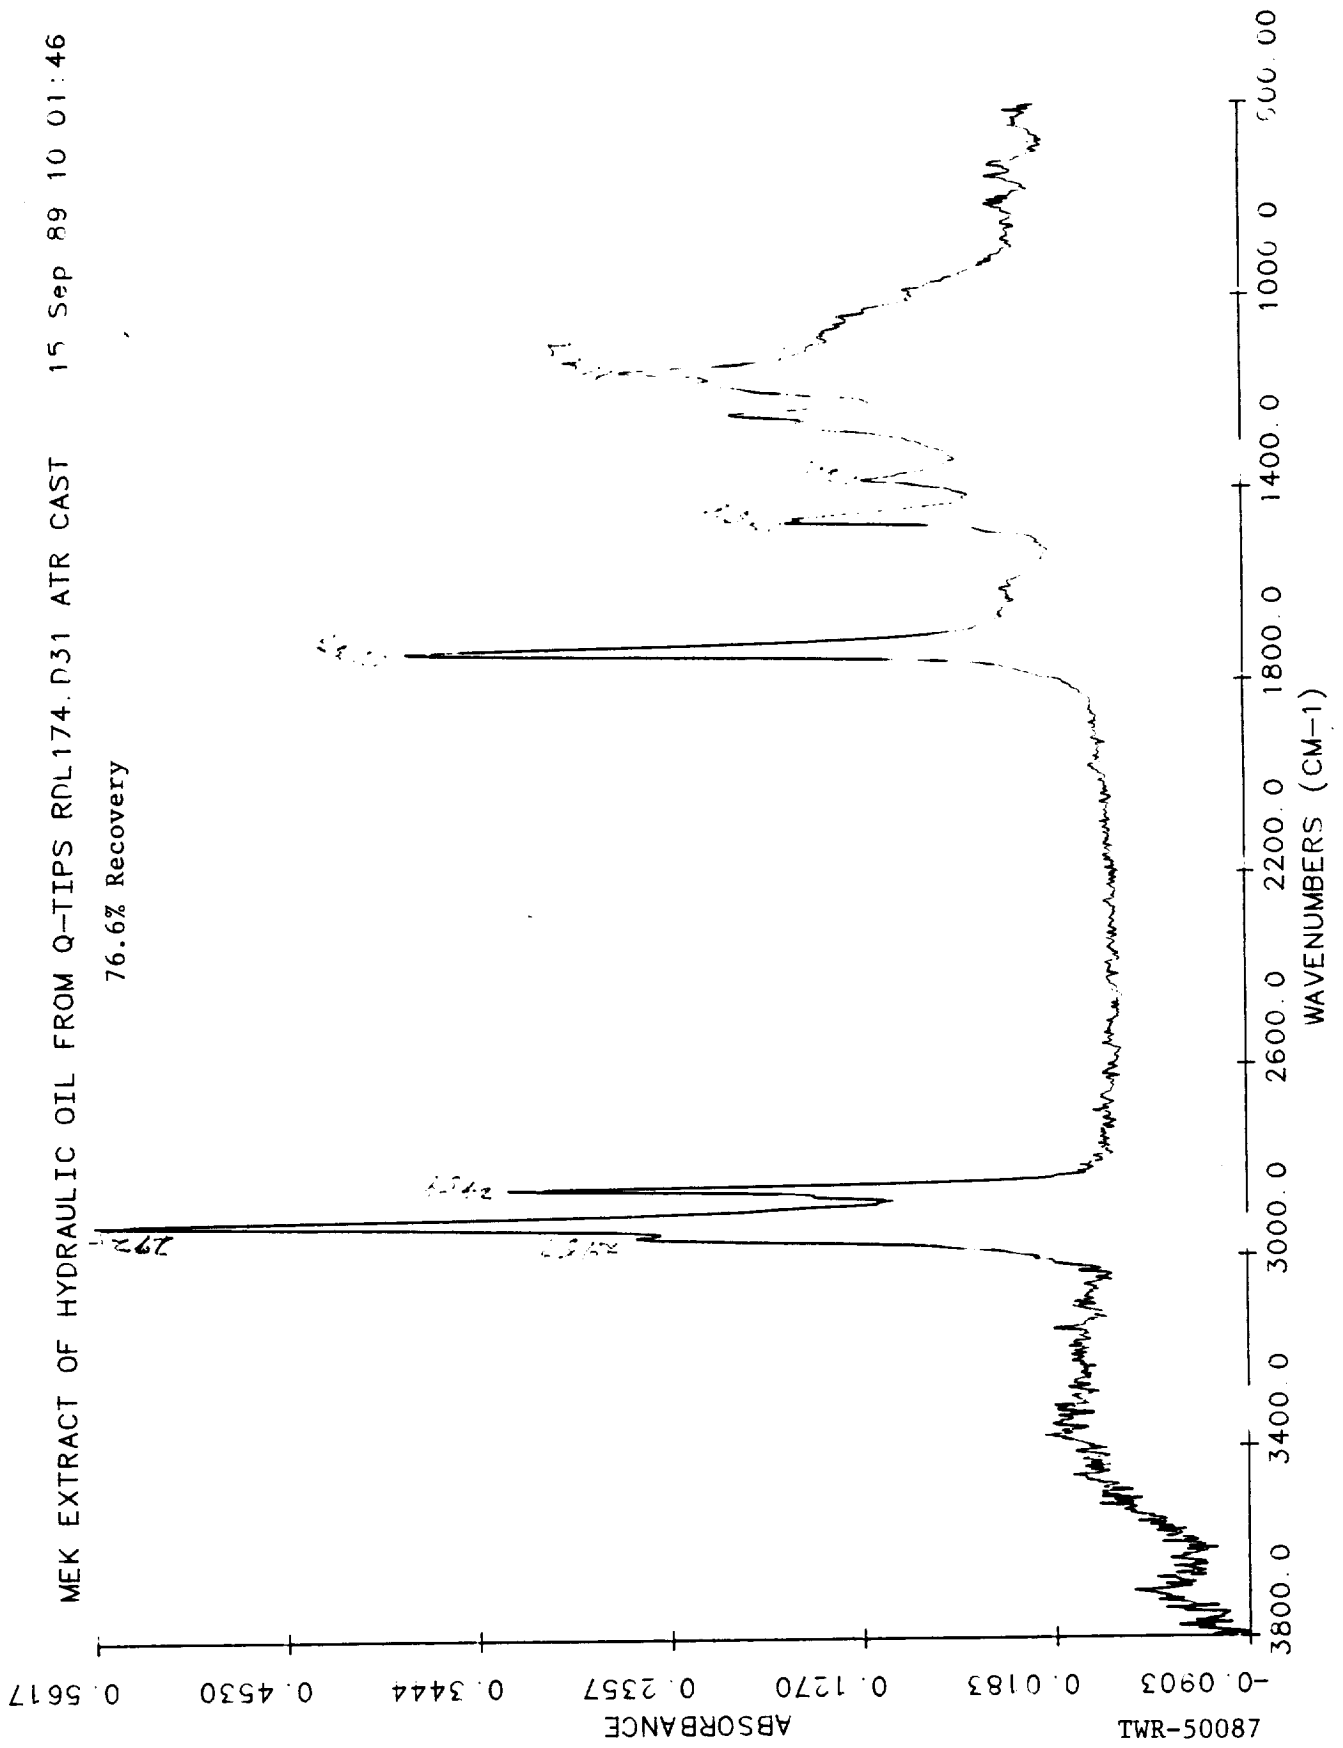



Figure III.
TCE SHAKEN EXTRACT OF HYDRAULIC OIL FROM FABWIPE RDL176.E03 ATR 09 Oct 88 08:44:18

37.1% Recovery

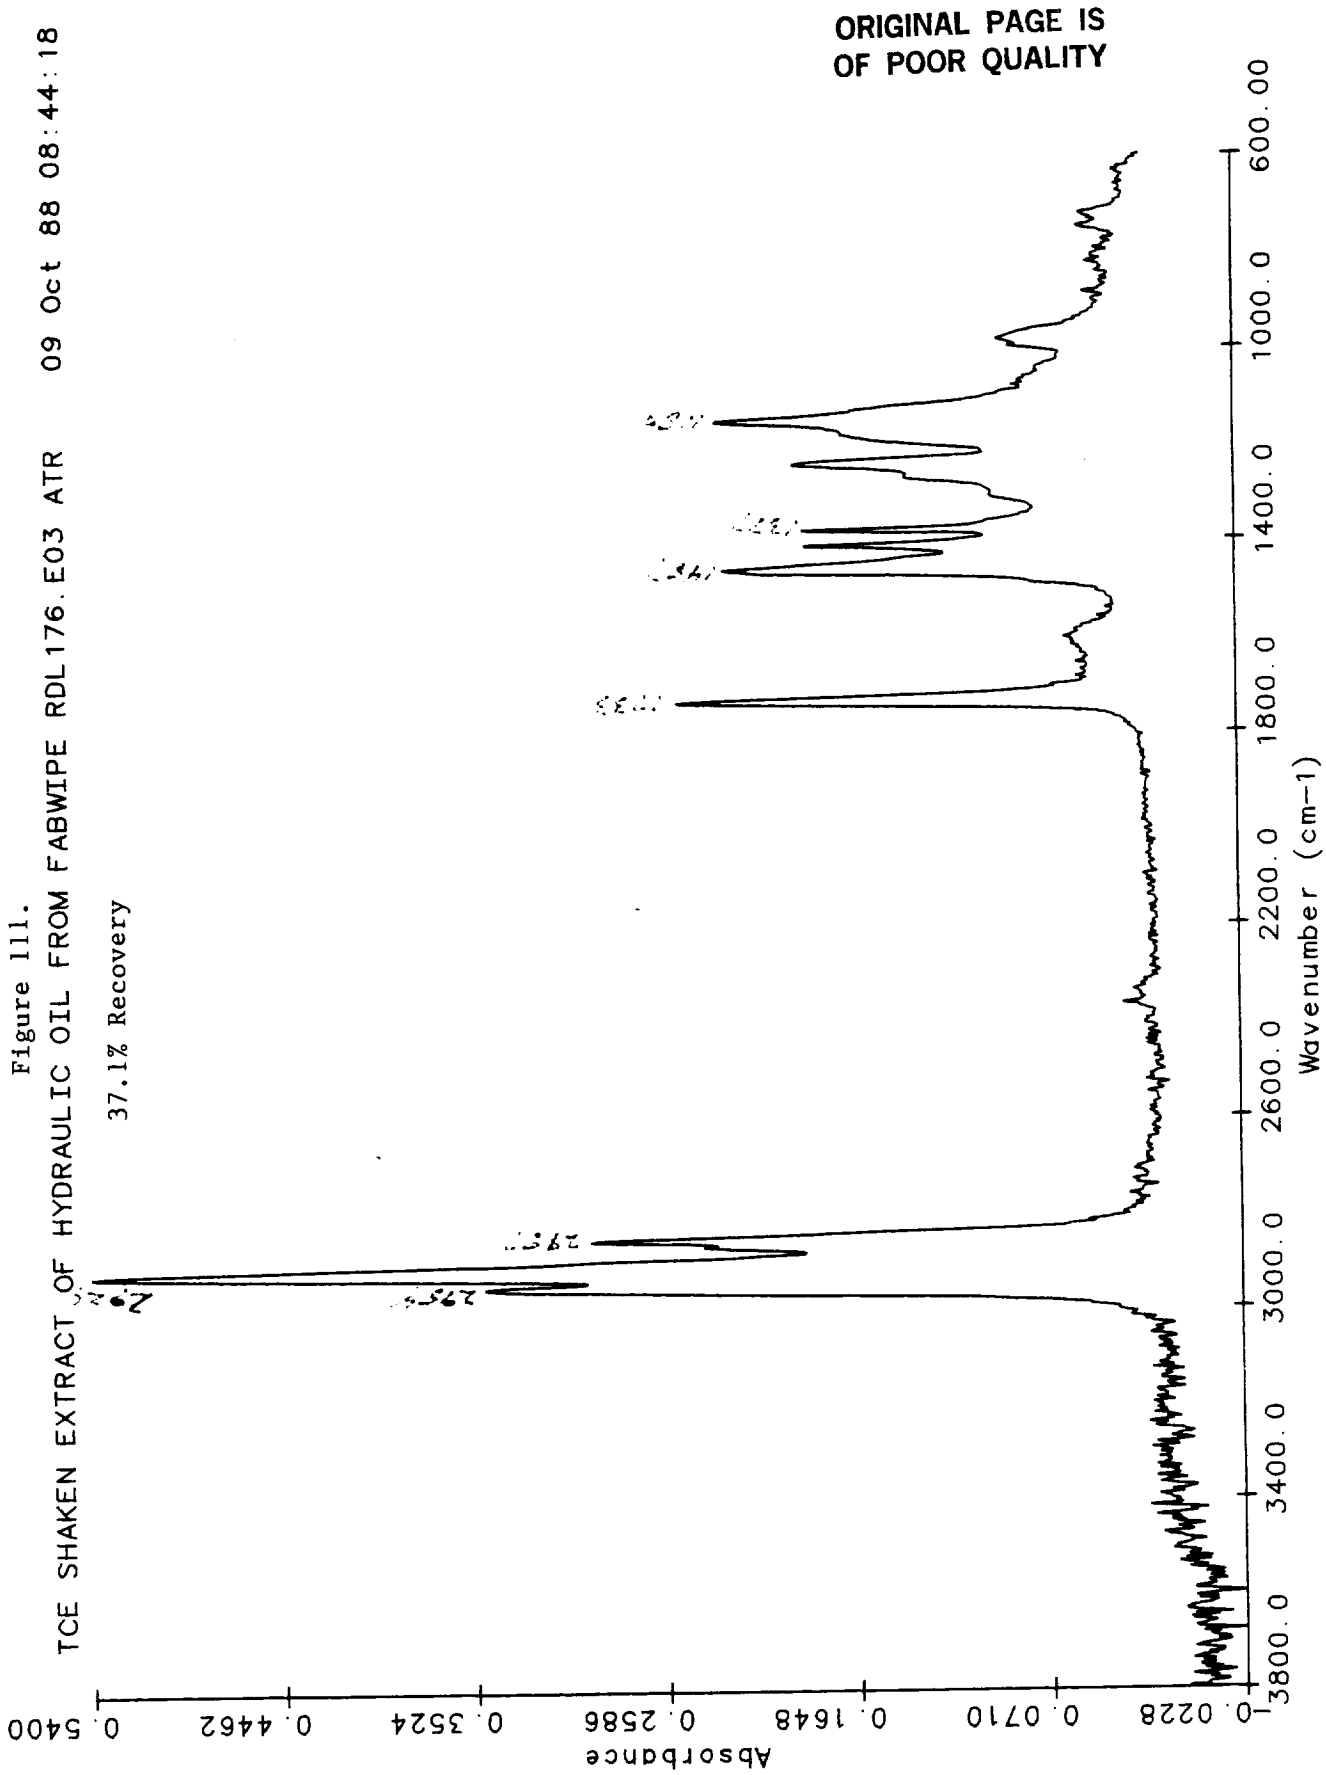


ORIGINAL PAGE IS
OF POOR QUALITY

Figure 112.
TCE SHAKEN EXTRACT OF HYDRAULIC OIL FROM Q-TIPS RDL176.E04 ATR 09 Oct 88 08:52:44

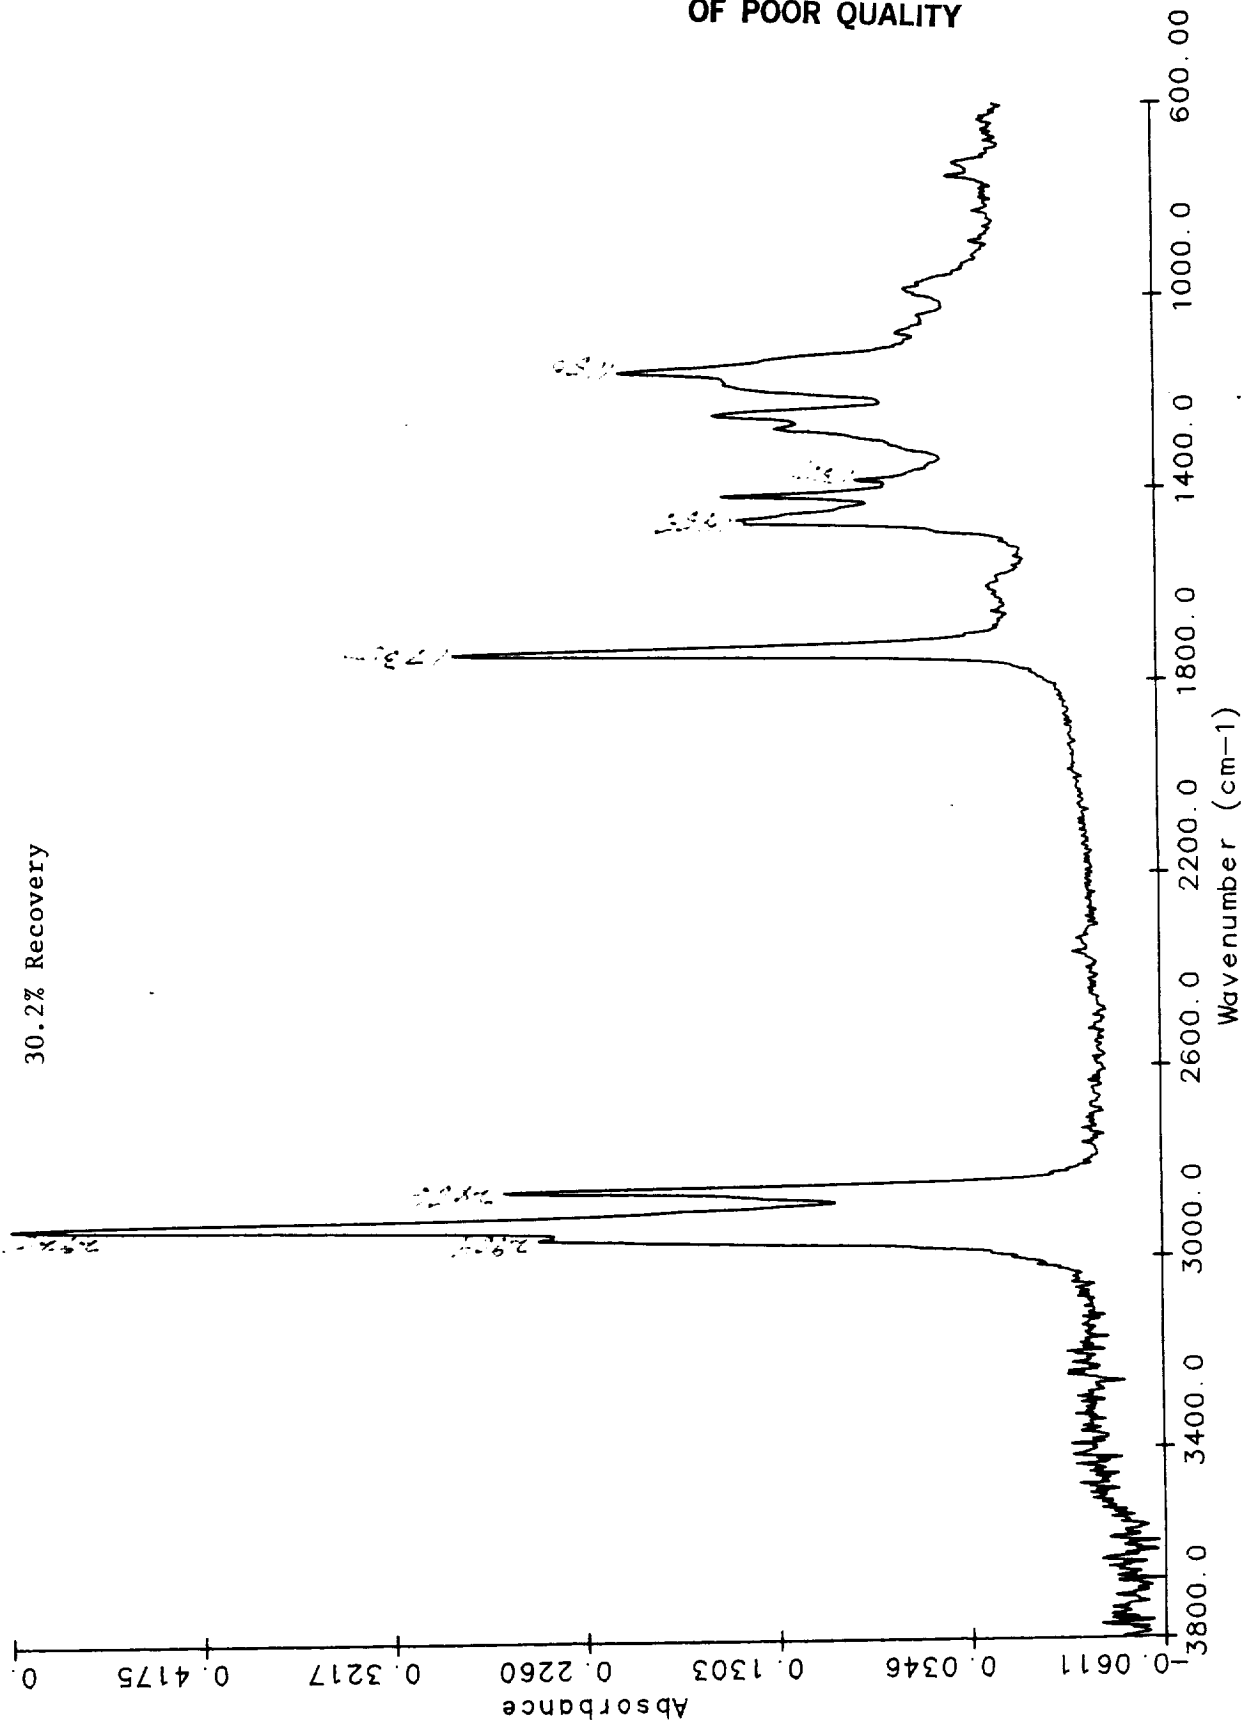

ORIGINAL PAGE IS
OF POOR QUALITY


ORIGINAL PAGE IS
OF POOR QUALITY

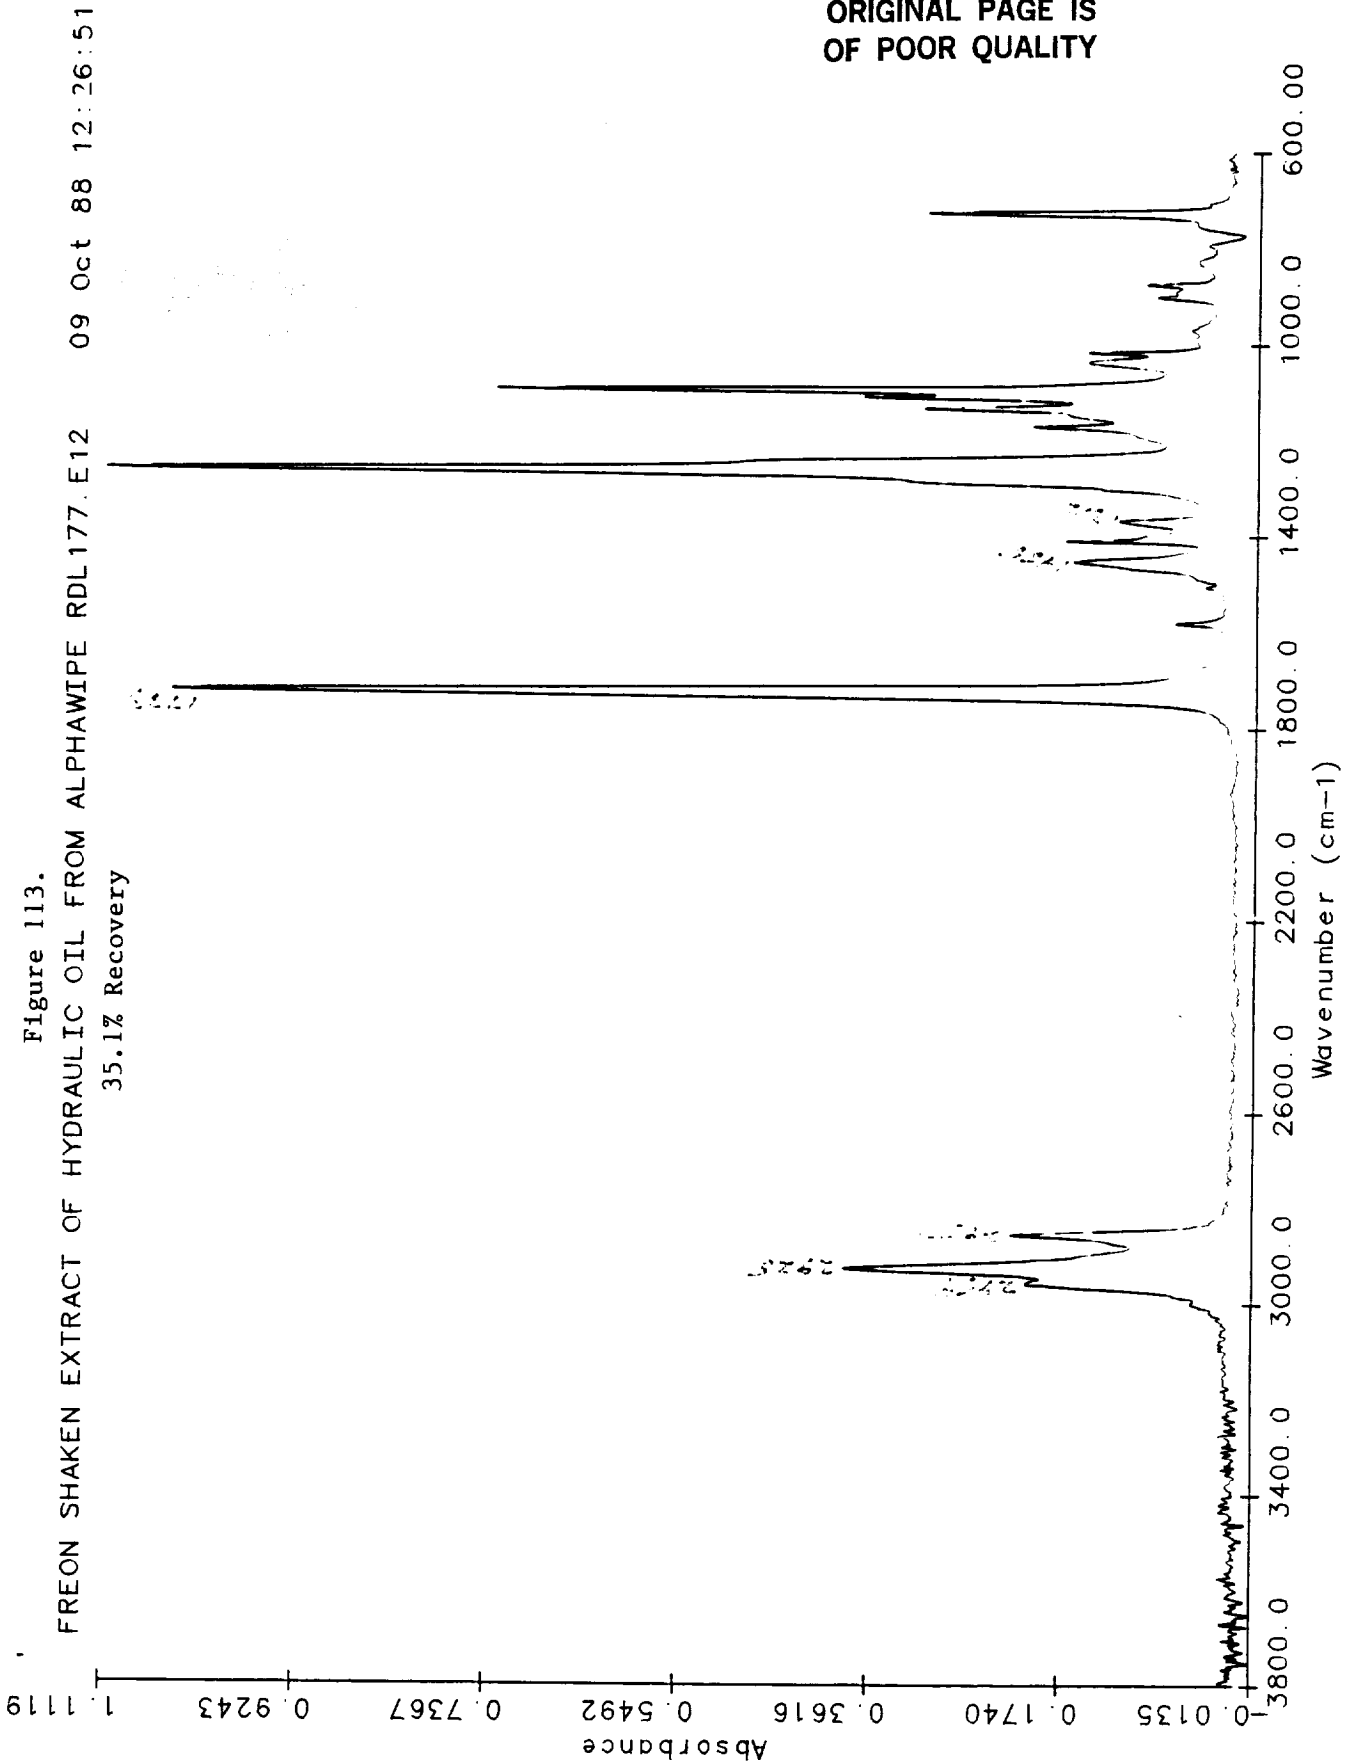

FREON SHAKEN EXTRACT OF HYDRAULIC OIL FROM QTIPS RDL177.E13 ATR 09 Oct 88 12:37:09

Figure 114.

26.2% Recovery

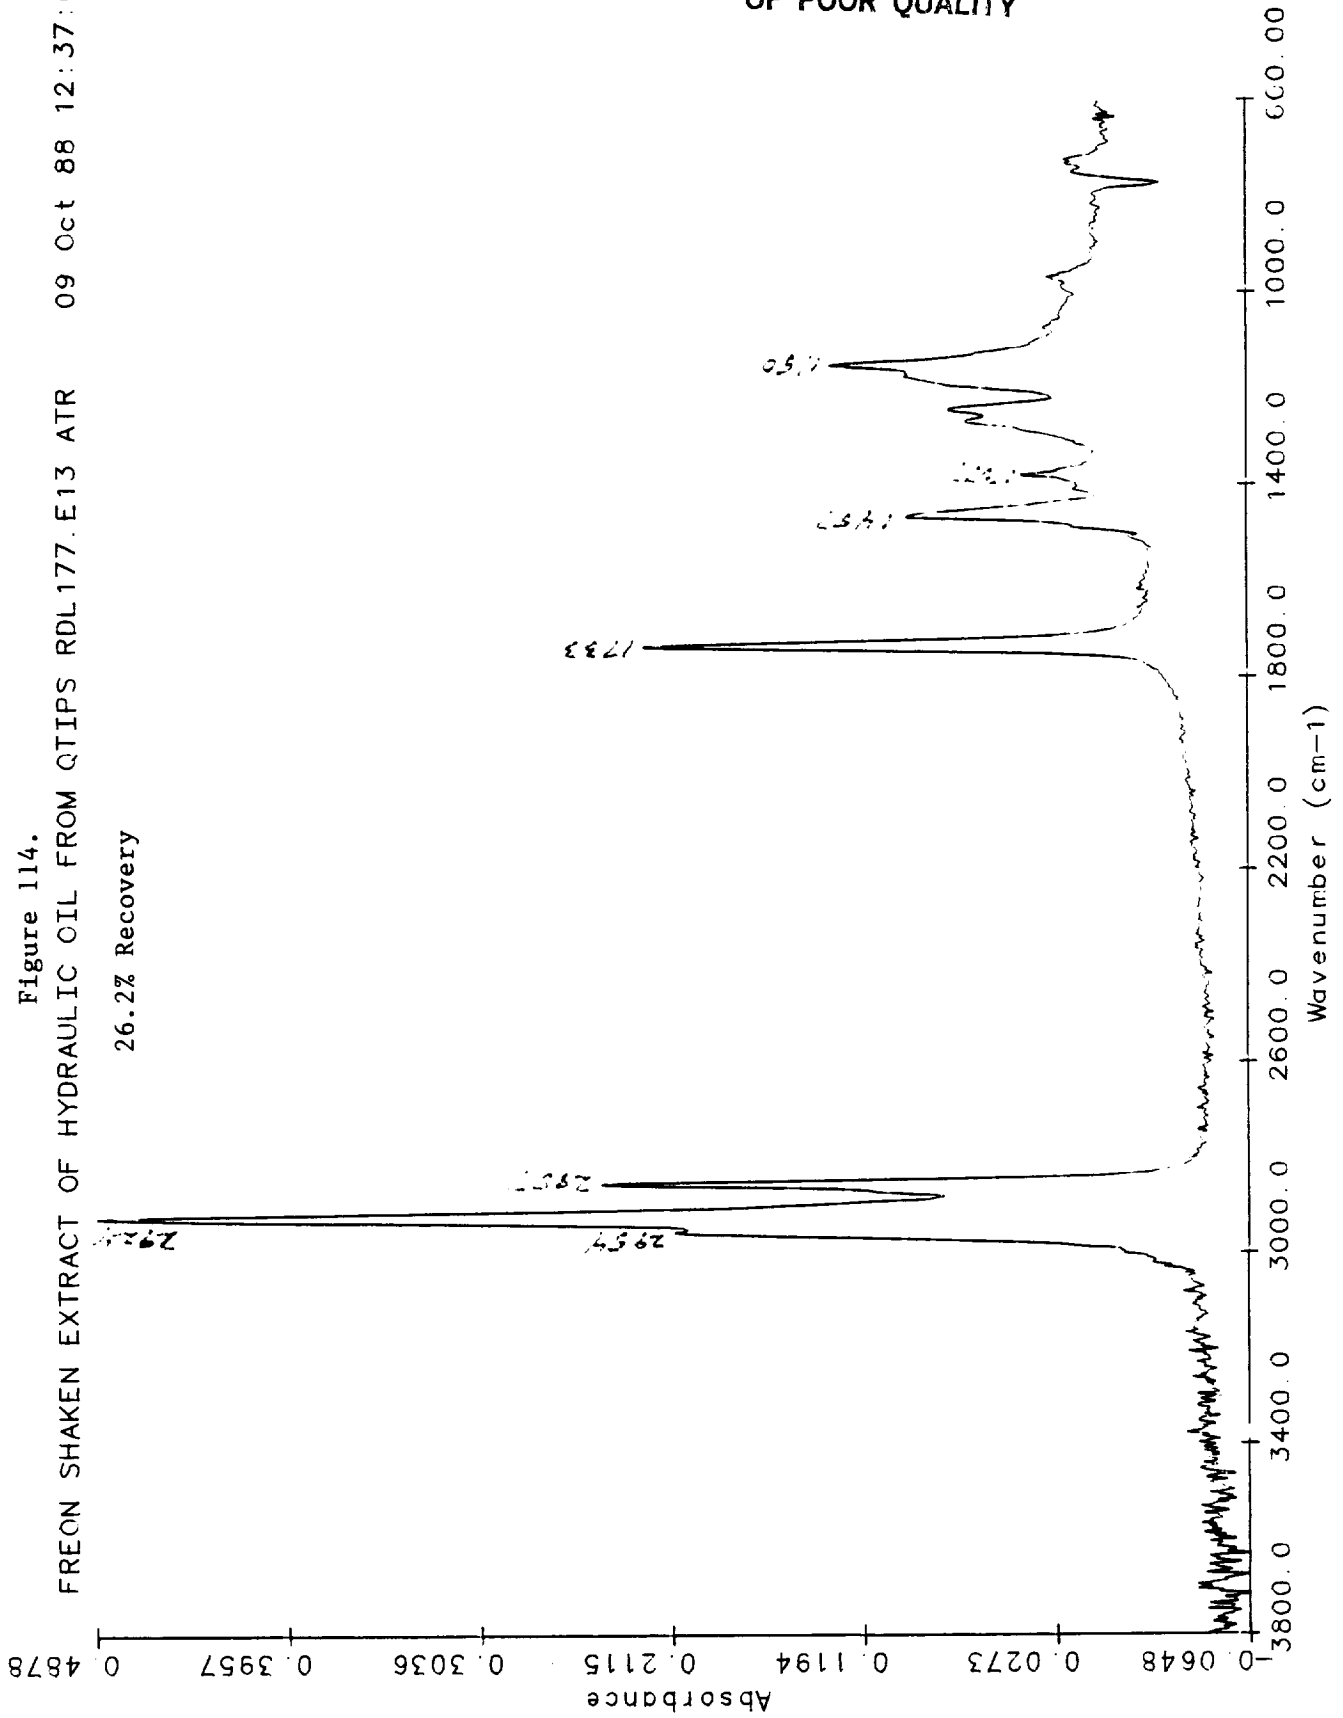


ORIGINAL PAGE IS OF POOR QUALITY

MEK SHAKEN EXTRACT OF HYDRAULIC OIL FROM FABWIPE RDL177.E18 ATR 09 Oct 88 12:50:20


Figure 115.
32.1% Recovery

ORIGINAL PAGE IS
OF POOR QUALITY

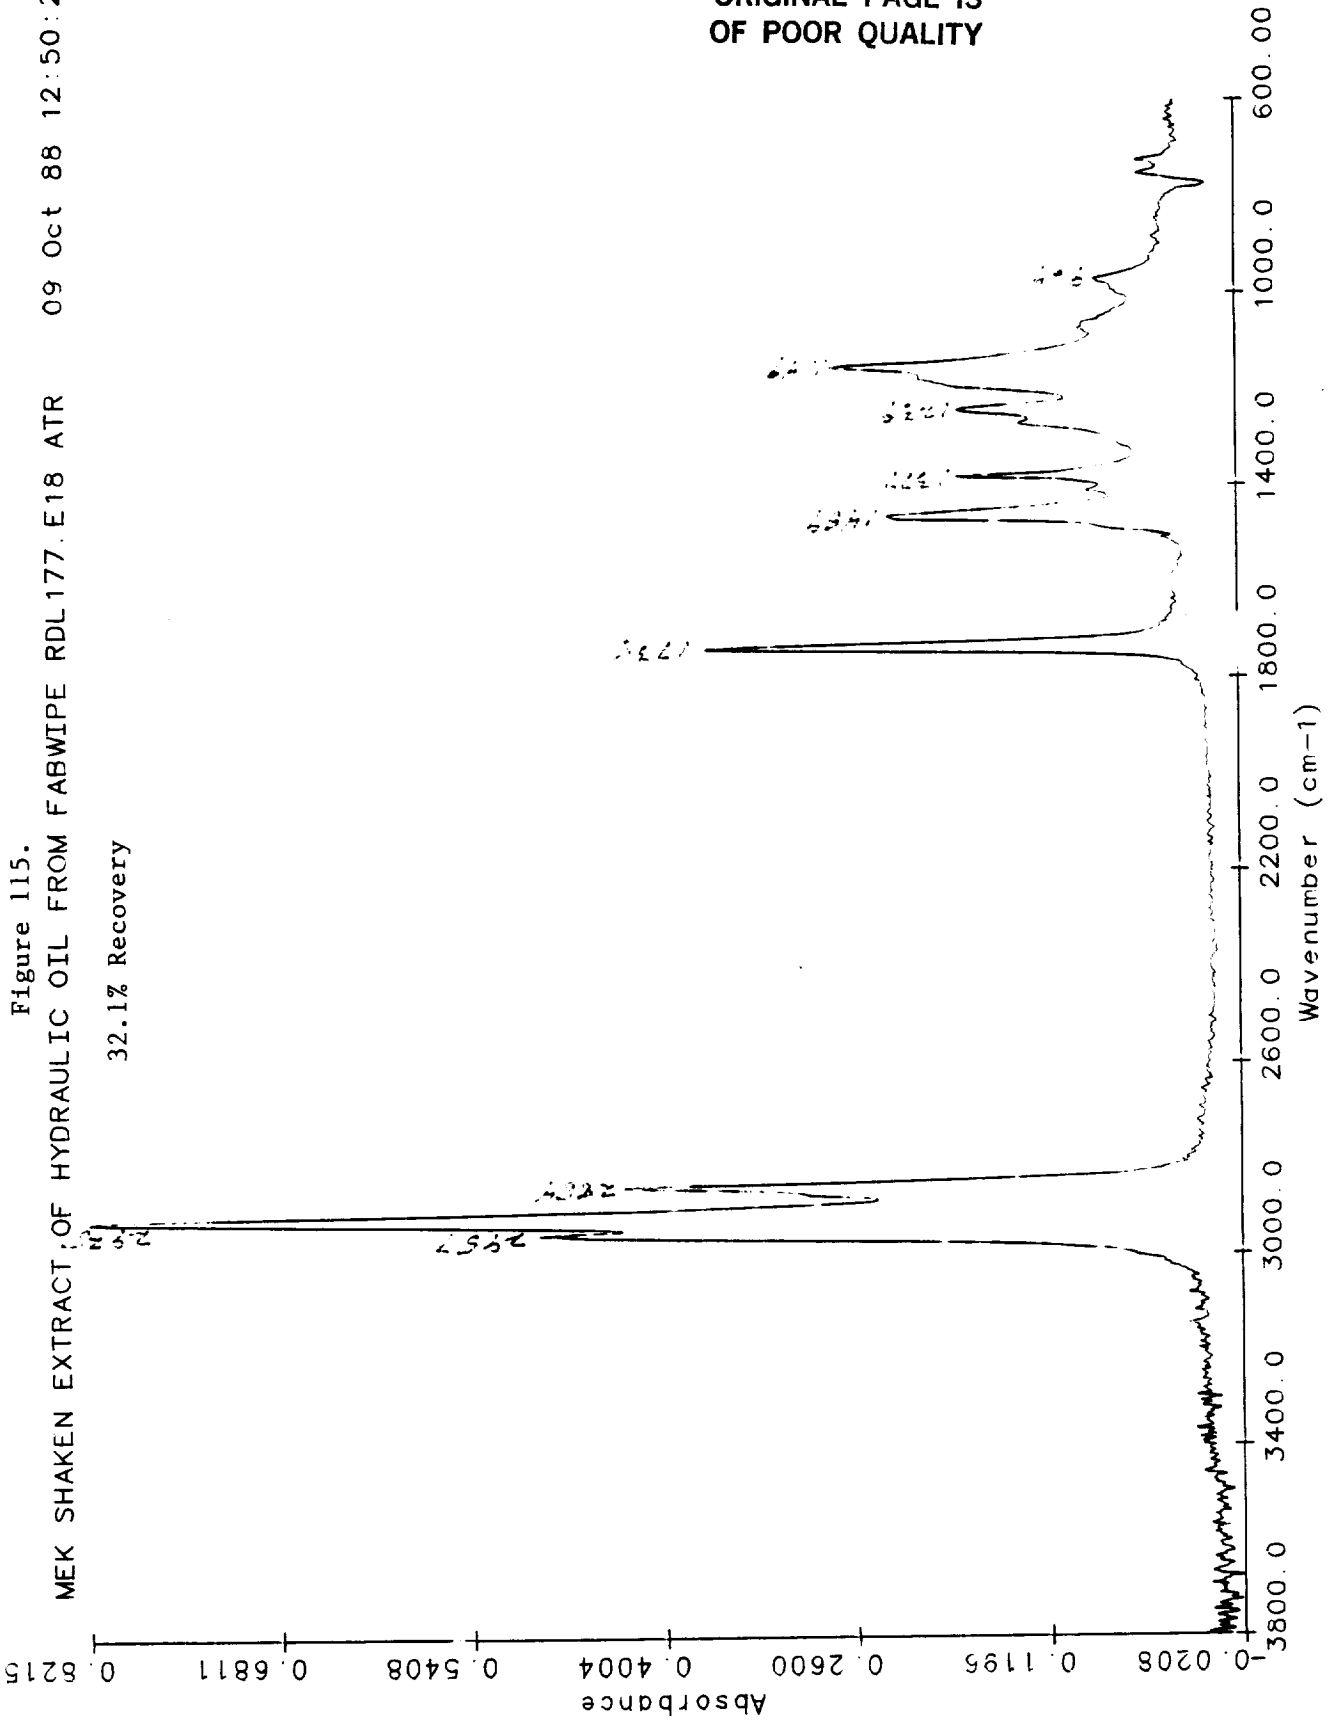

MEK SHAKEN EXTRACT OF HYDRAULIC OIL FROM ANTICON RDL177.E17 ATR 09 Oct 88 12:43:57

Figure 116.
32.1% Recovery

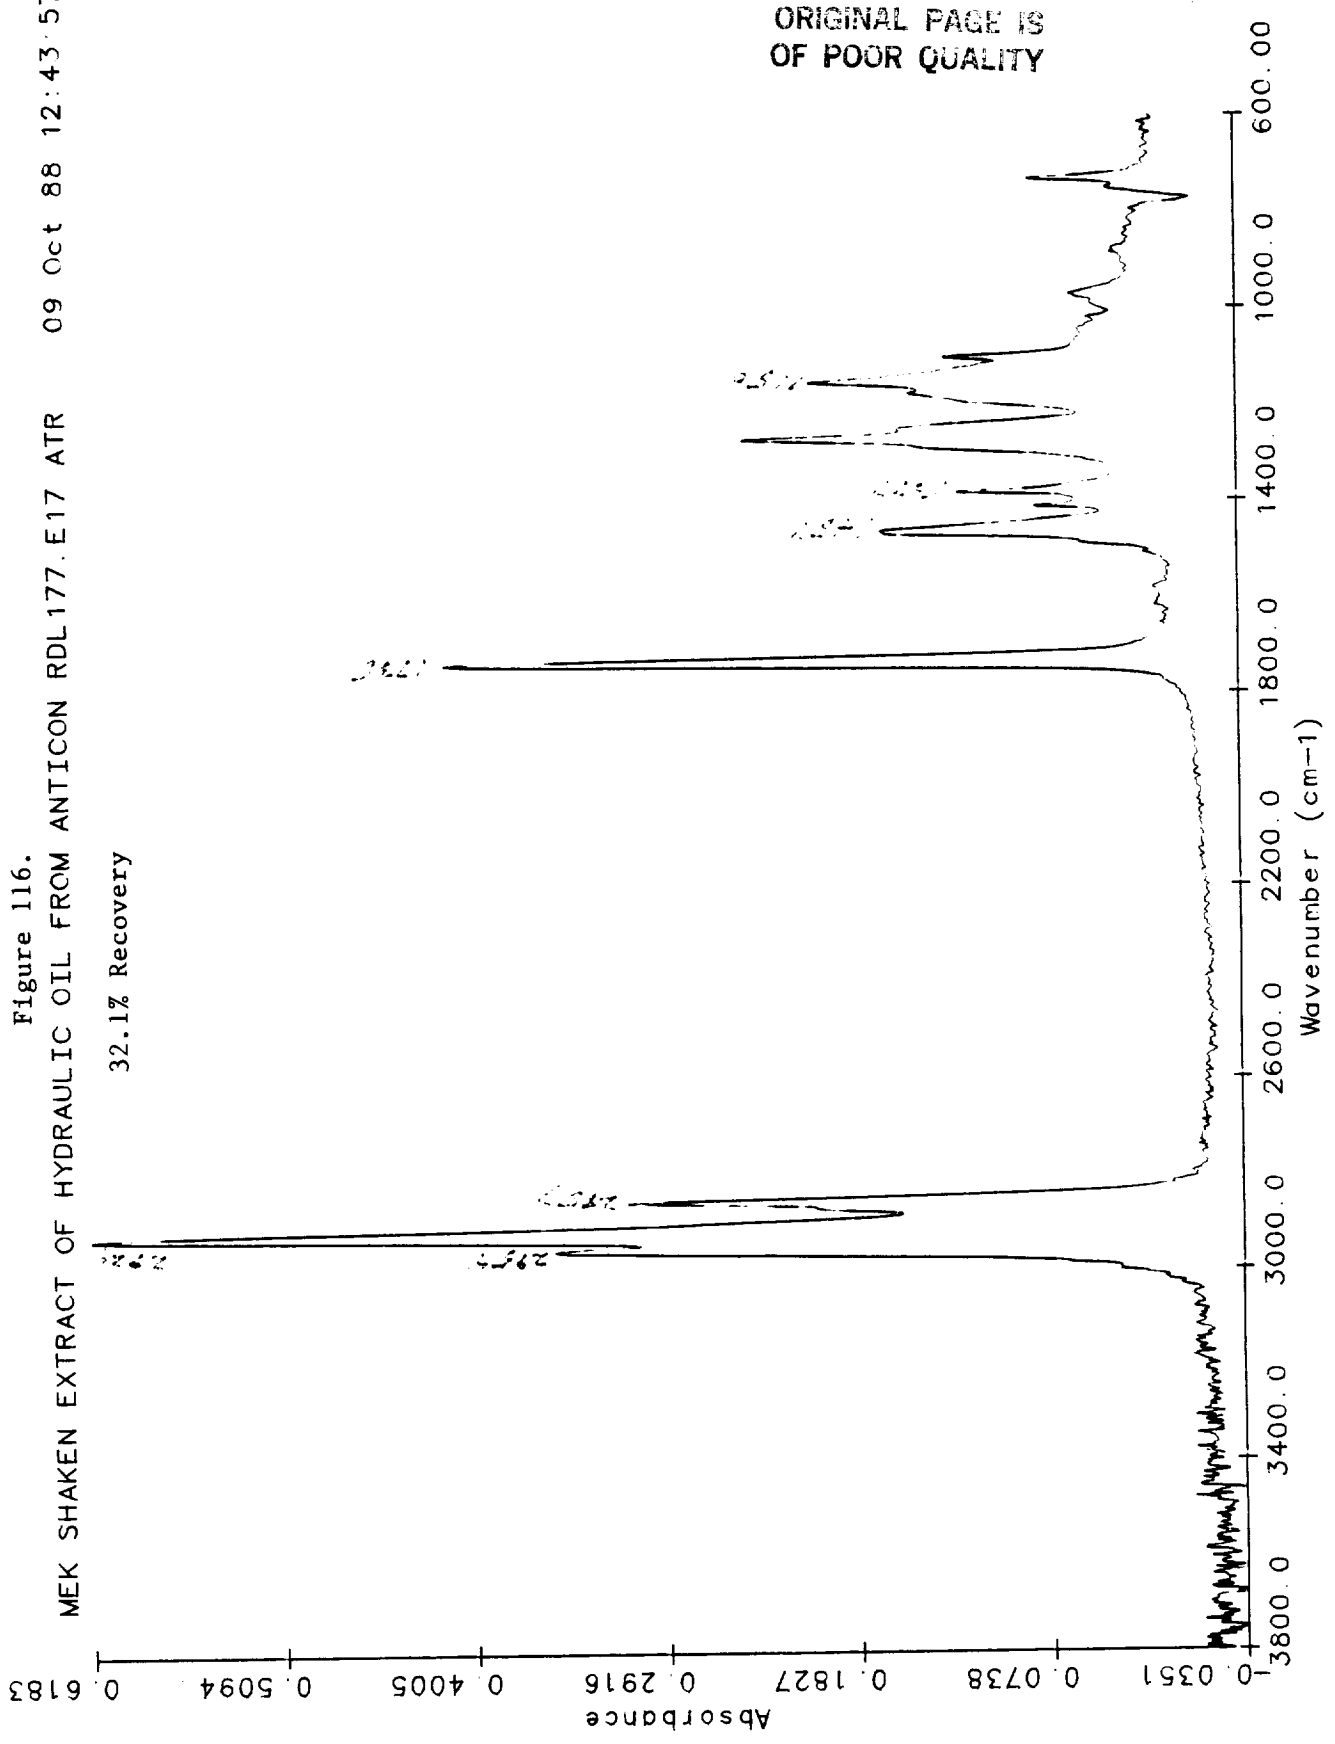

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 117.

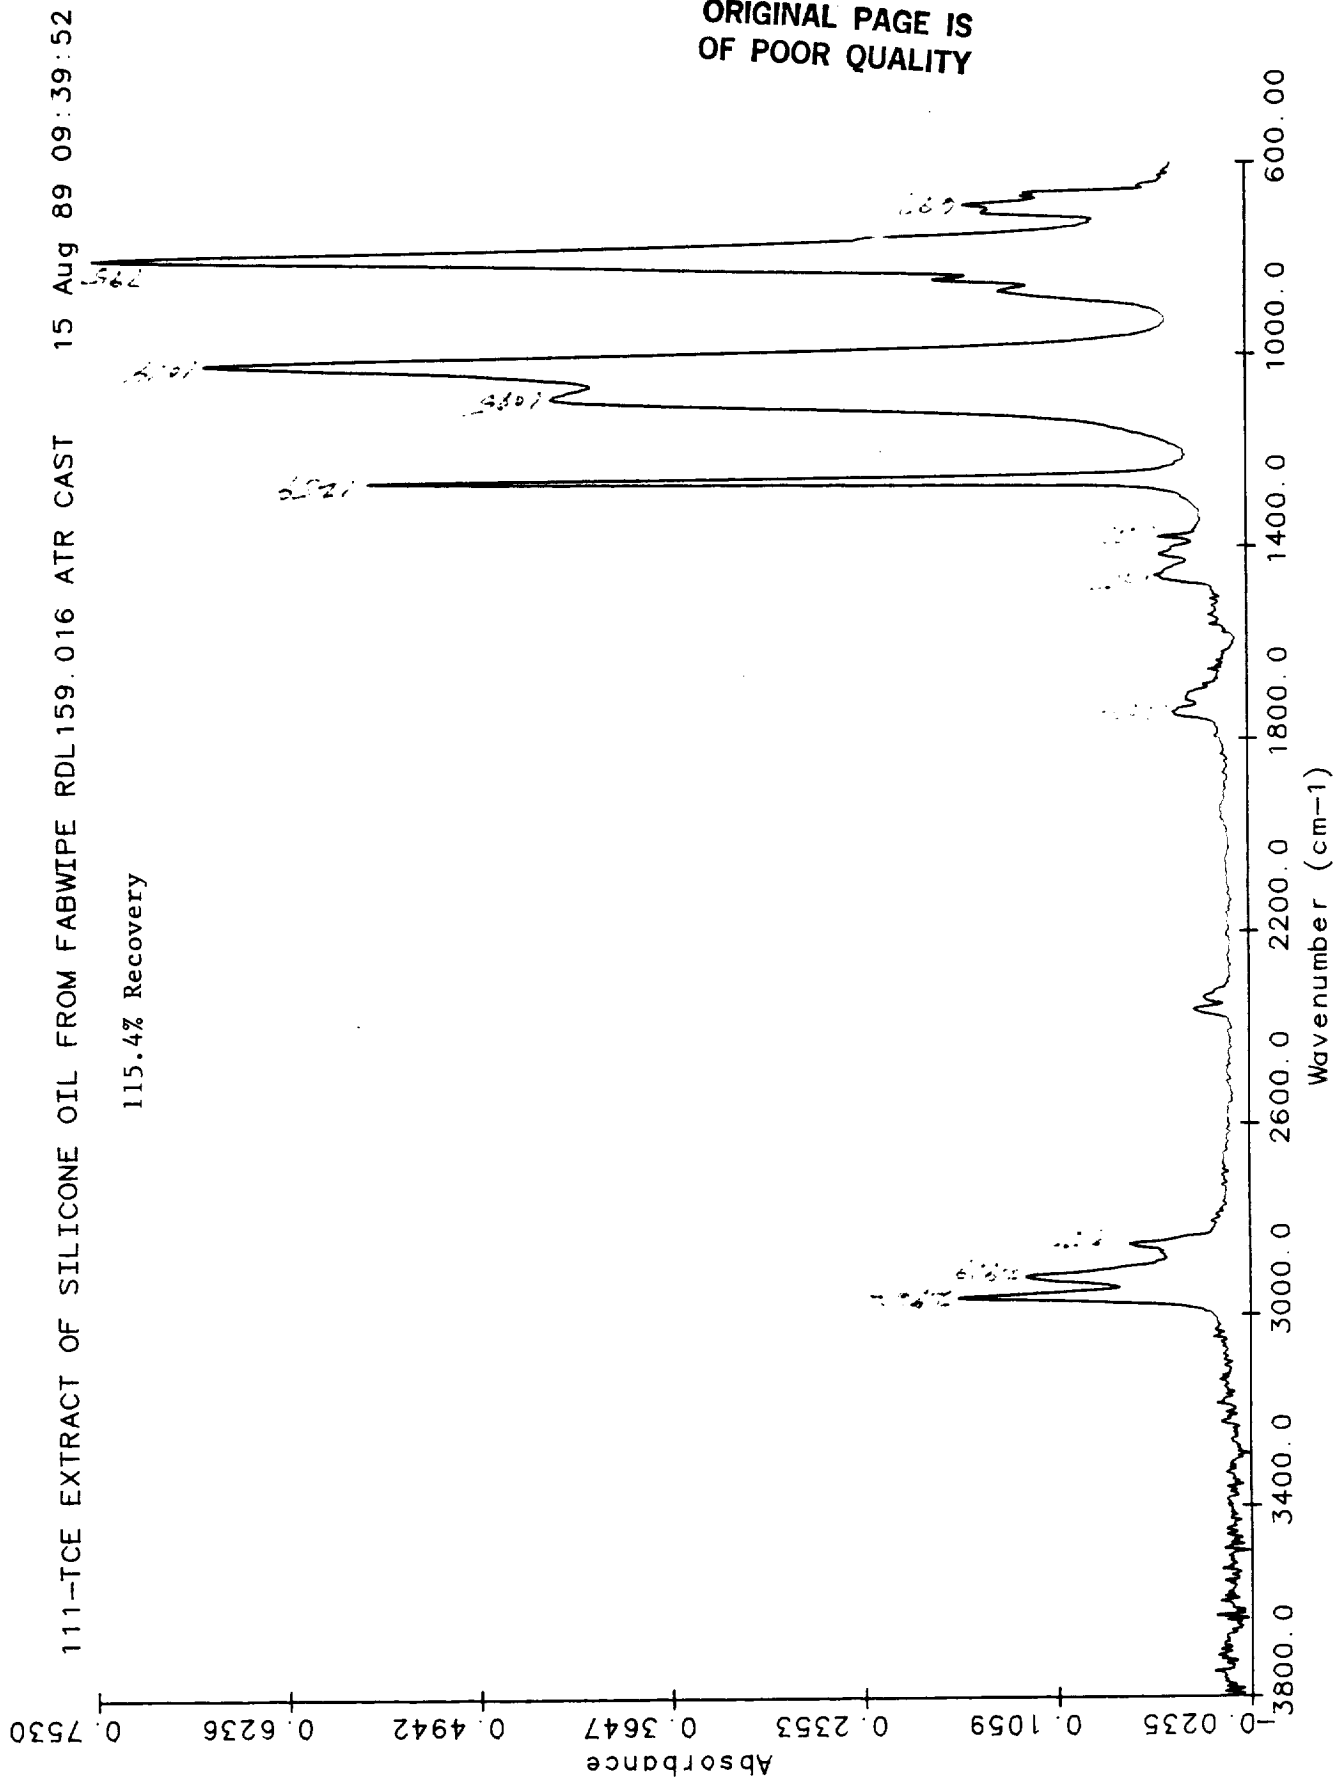


Figure 118.

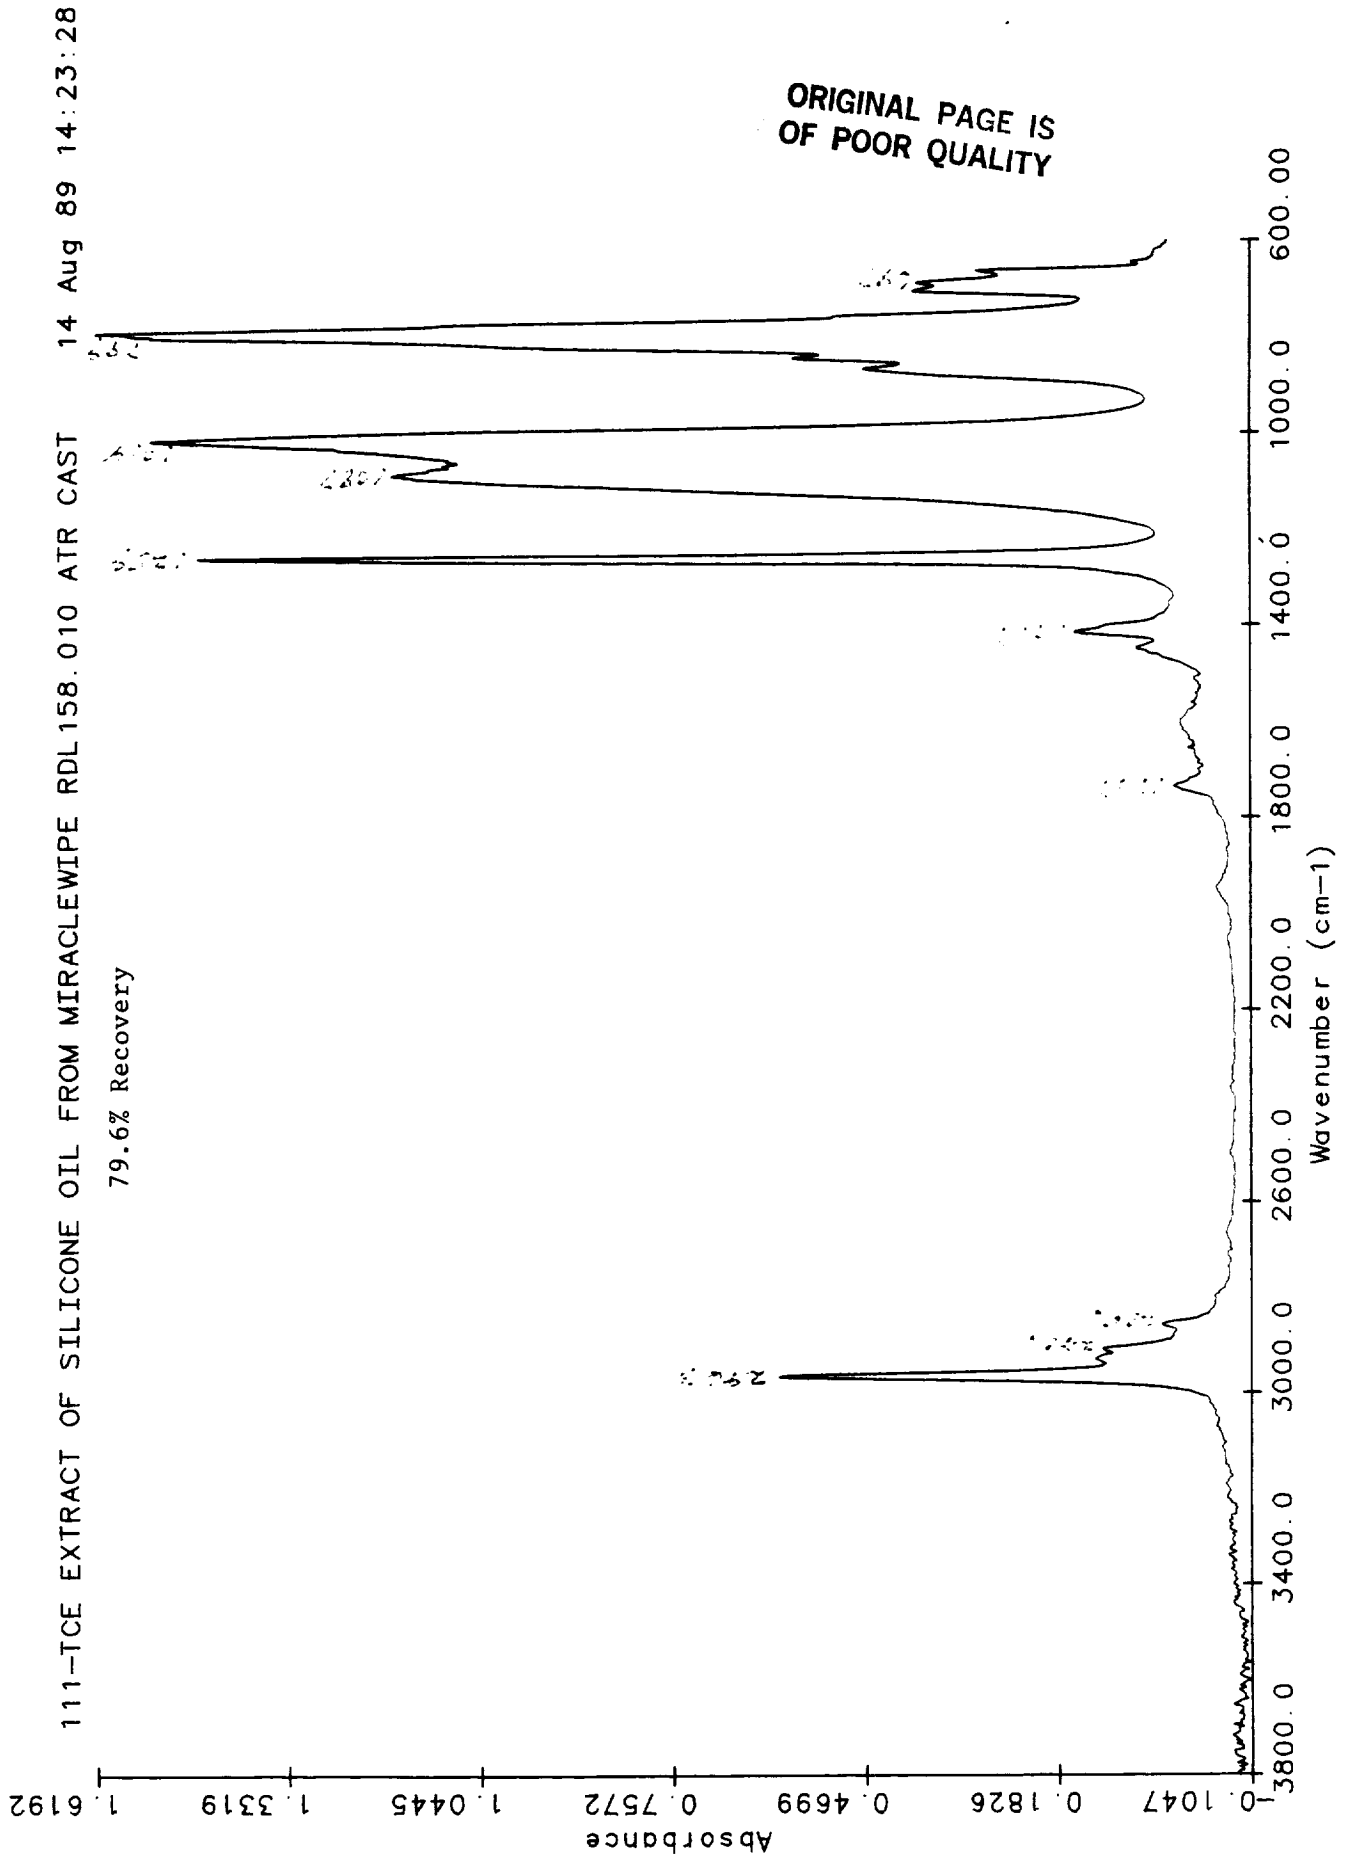


Figure 119.

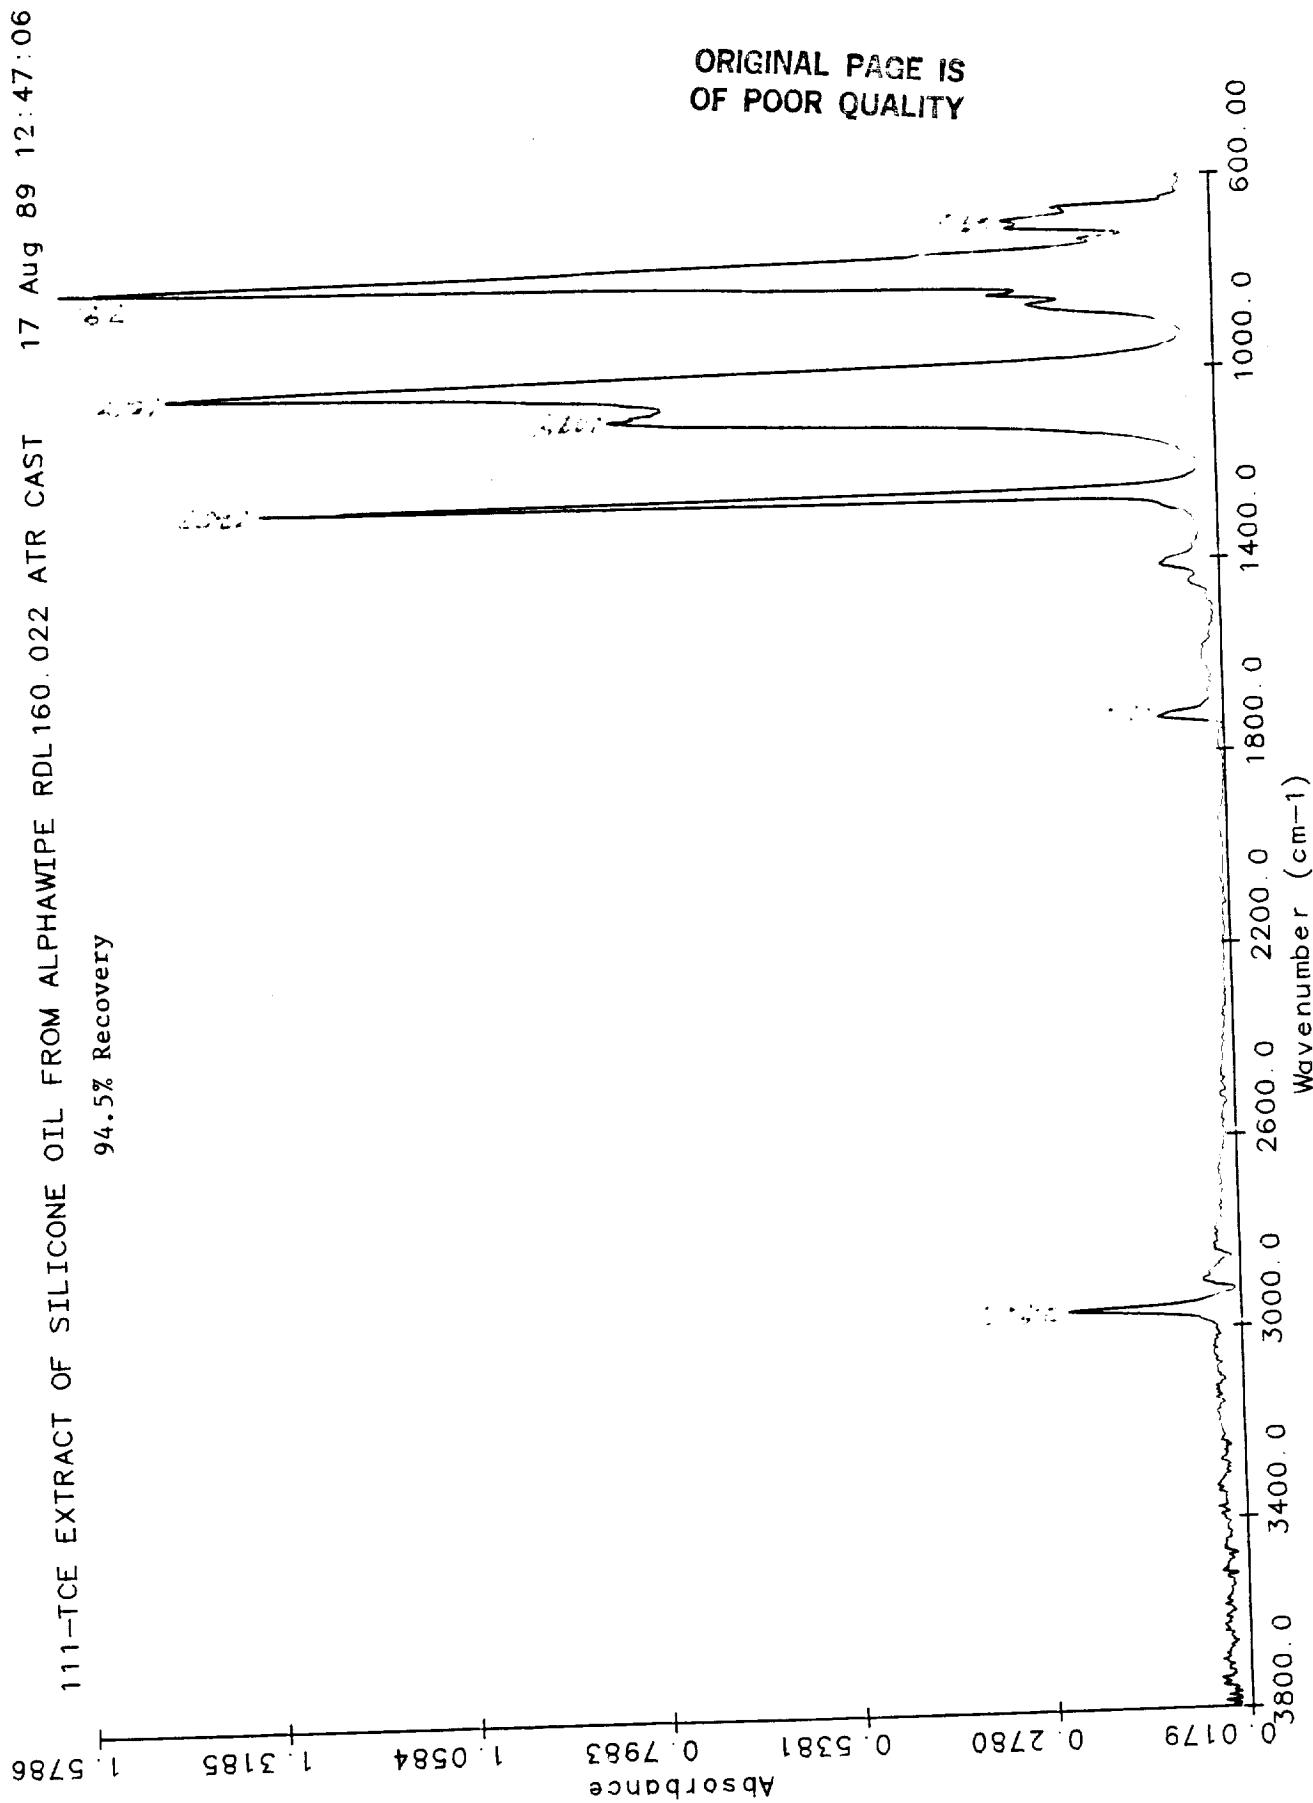


Figure 120.


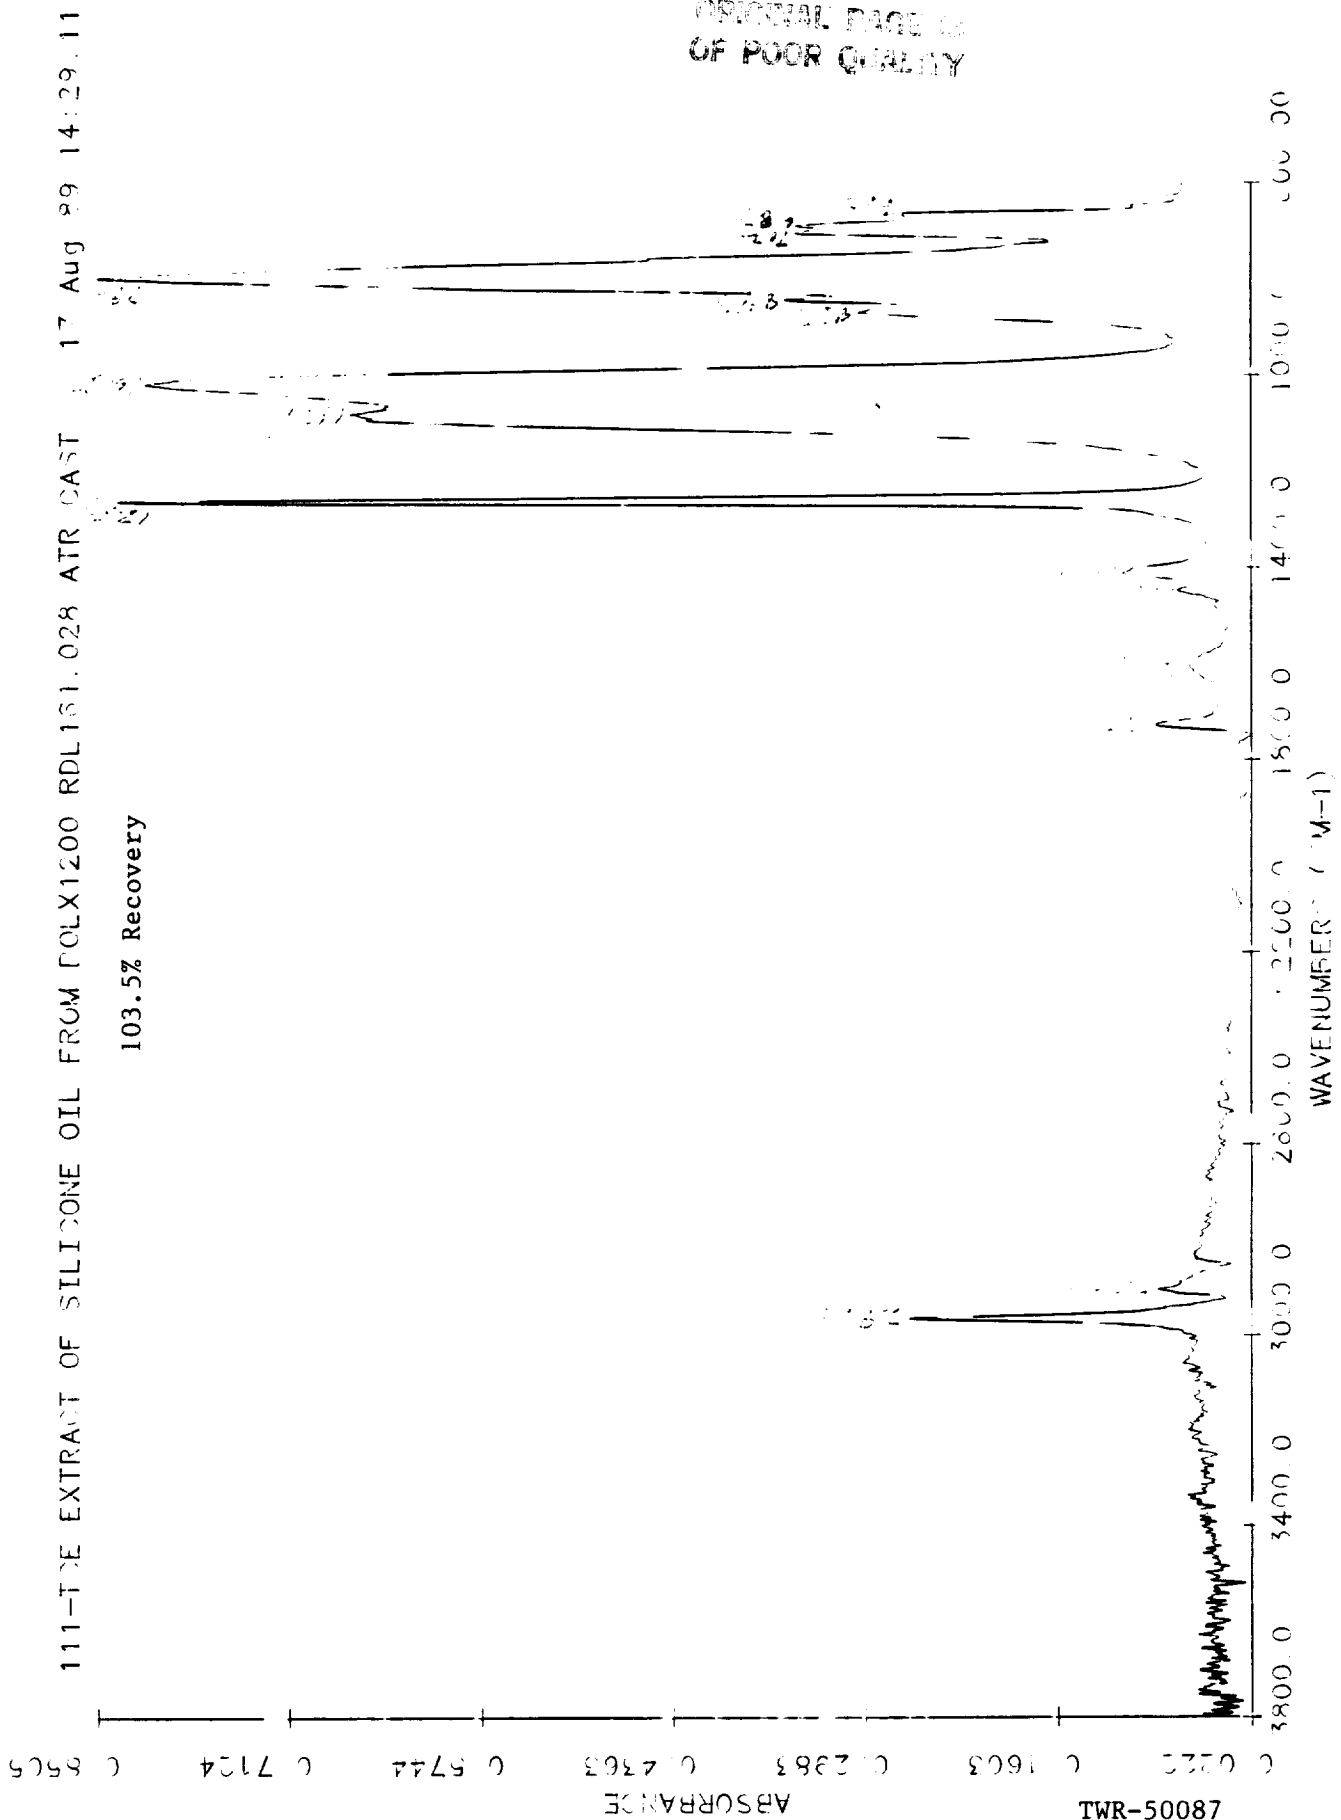


Figure 121.

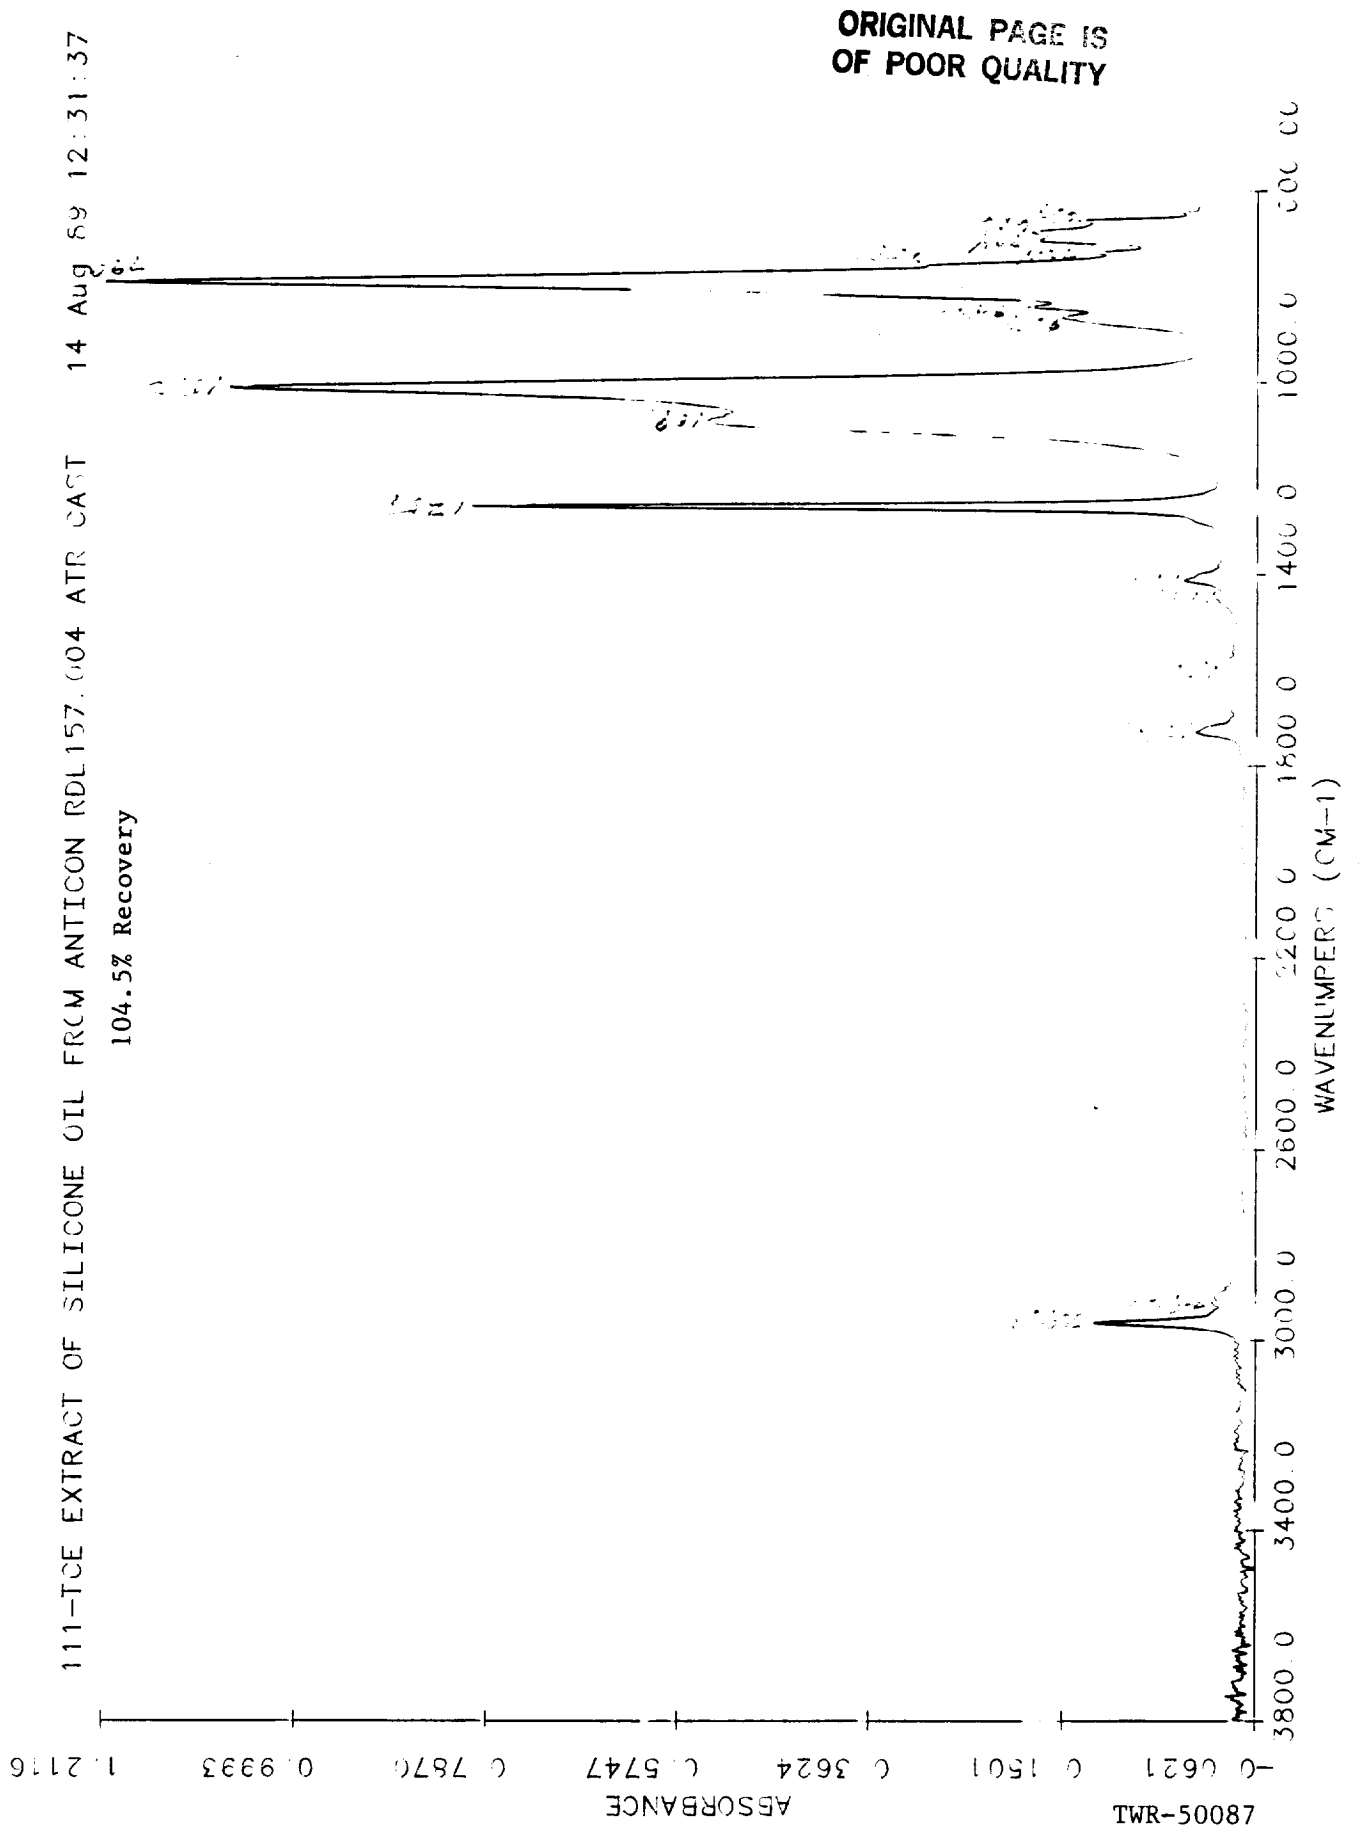

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 122.


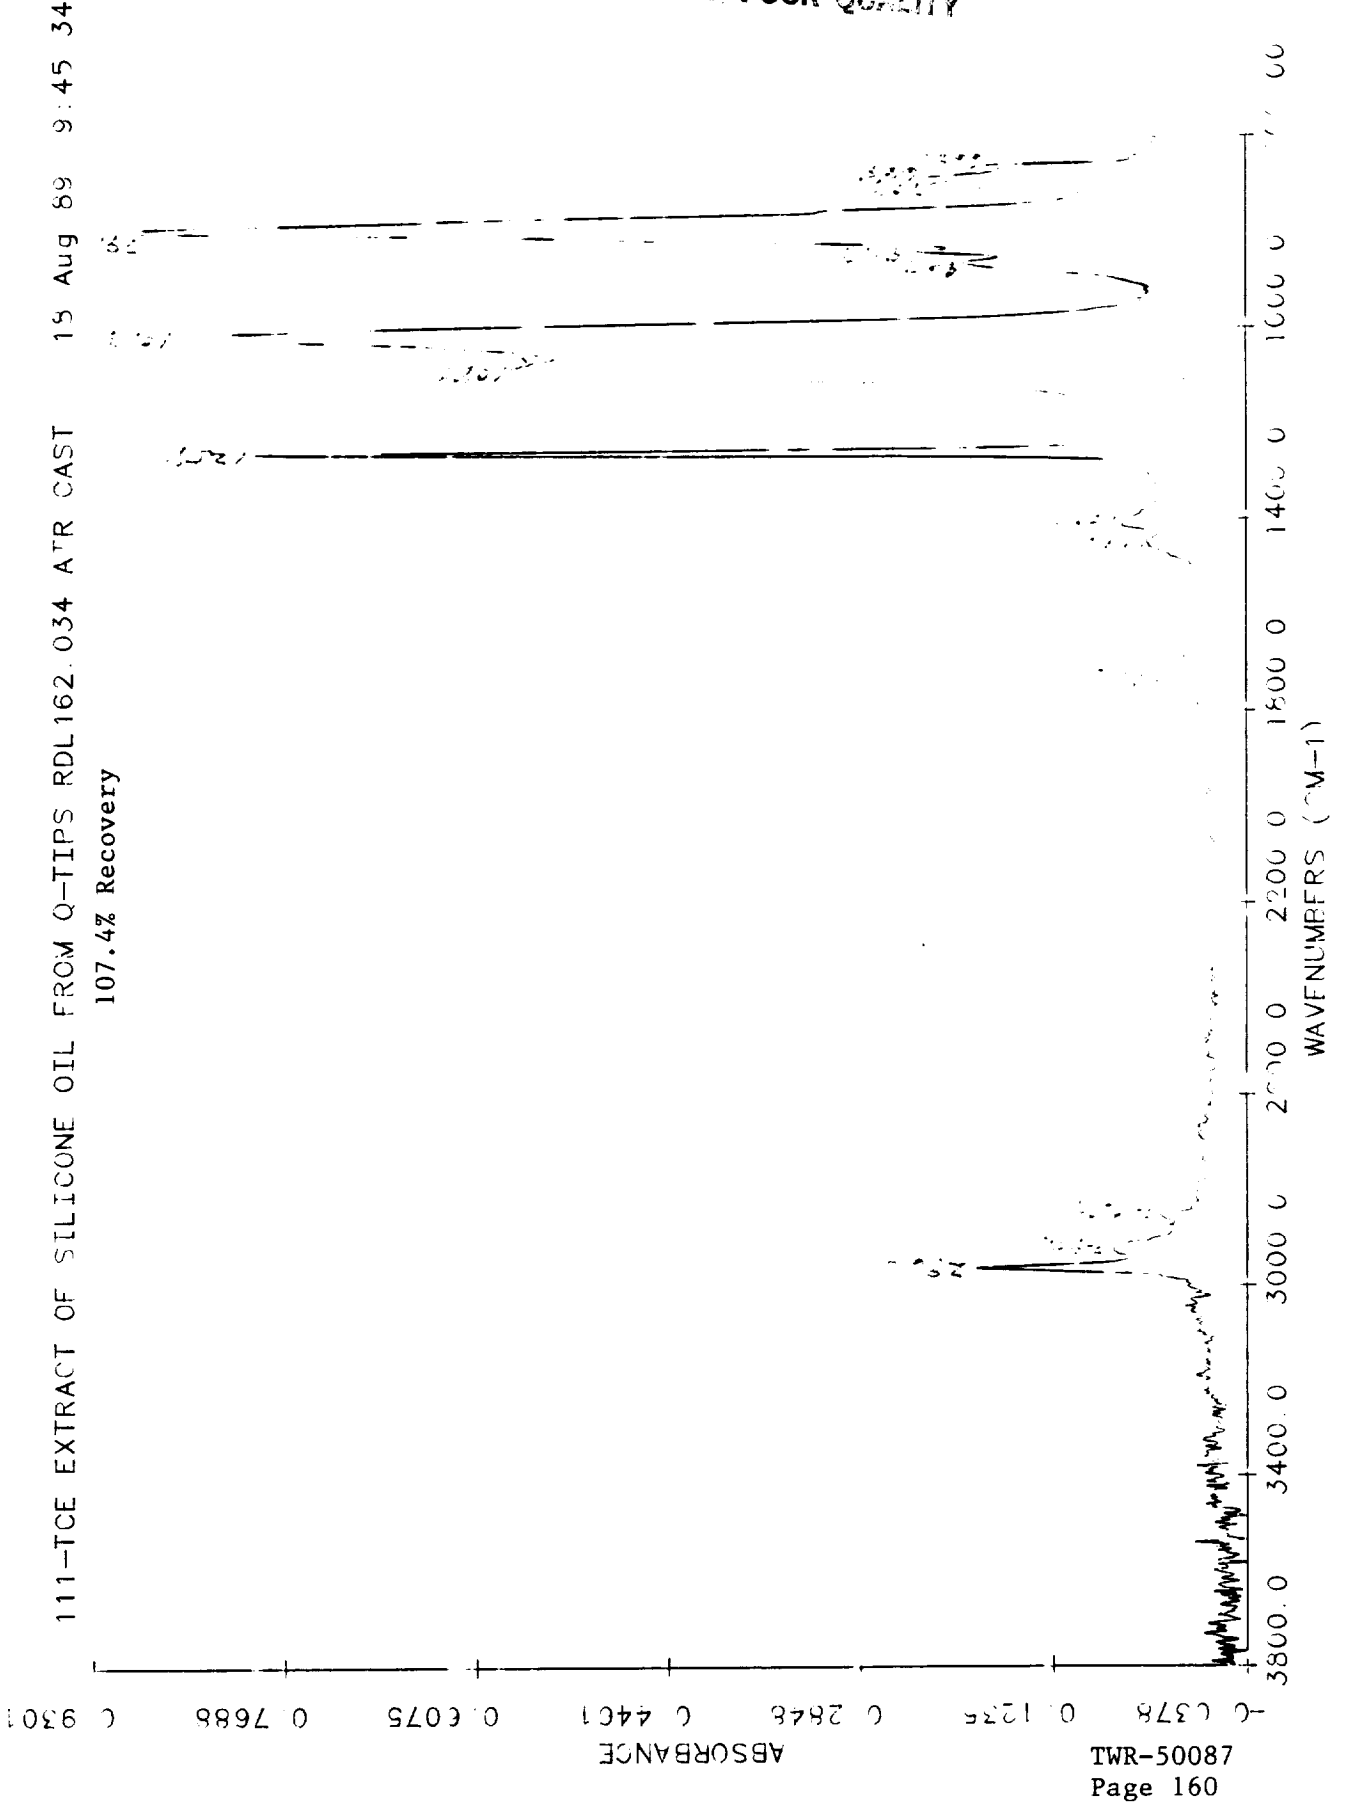


Figure 123.

FREON TF EXTRACT OF SILICONE OIL FROM FABWIPE RDL165.B31 ATR CAST 28 Aug 89 14:32:08

47.8% Recovery

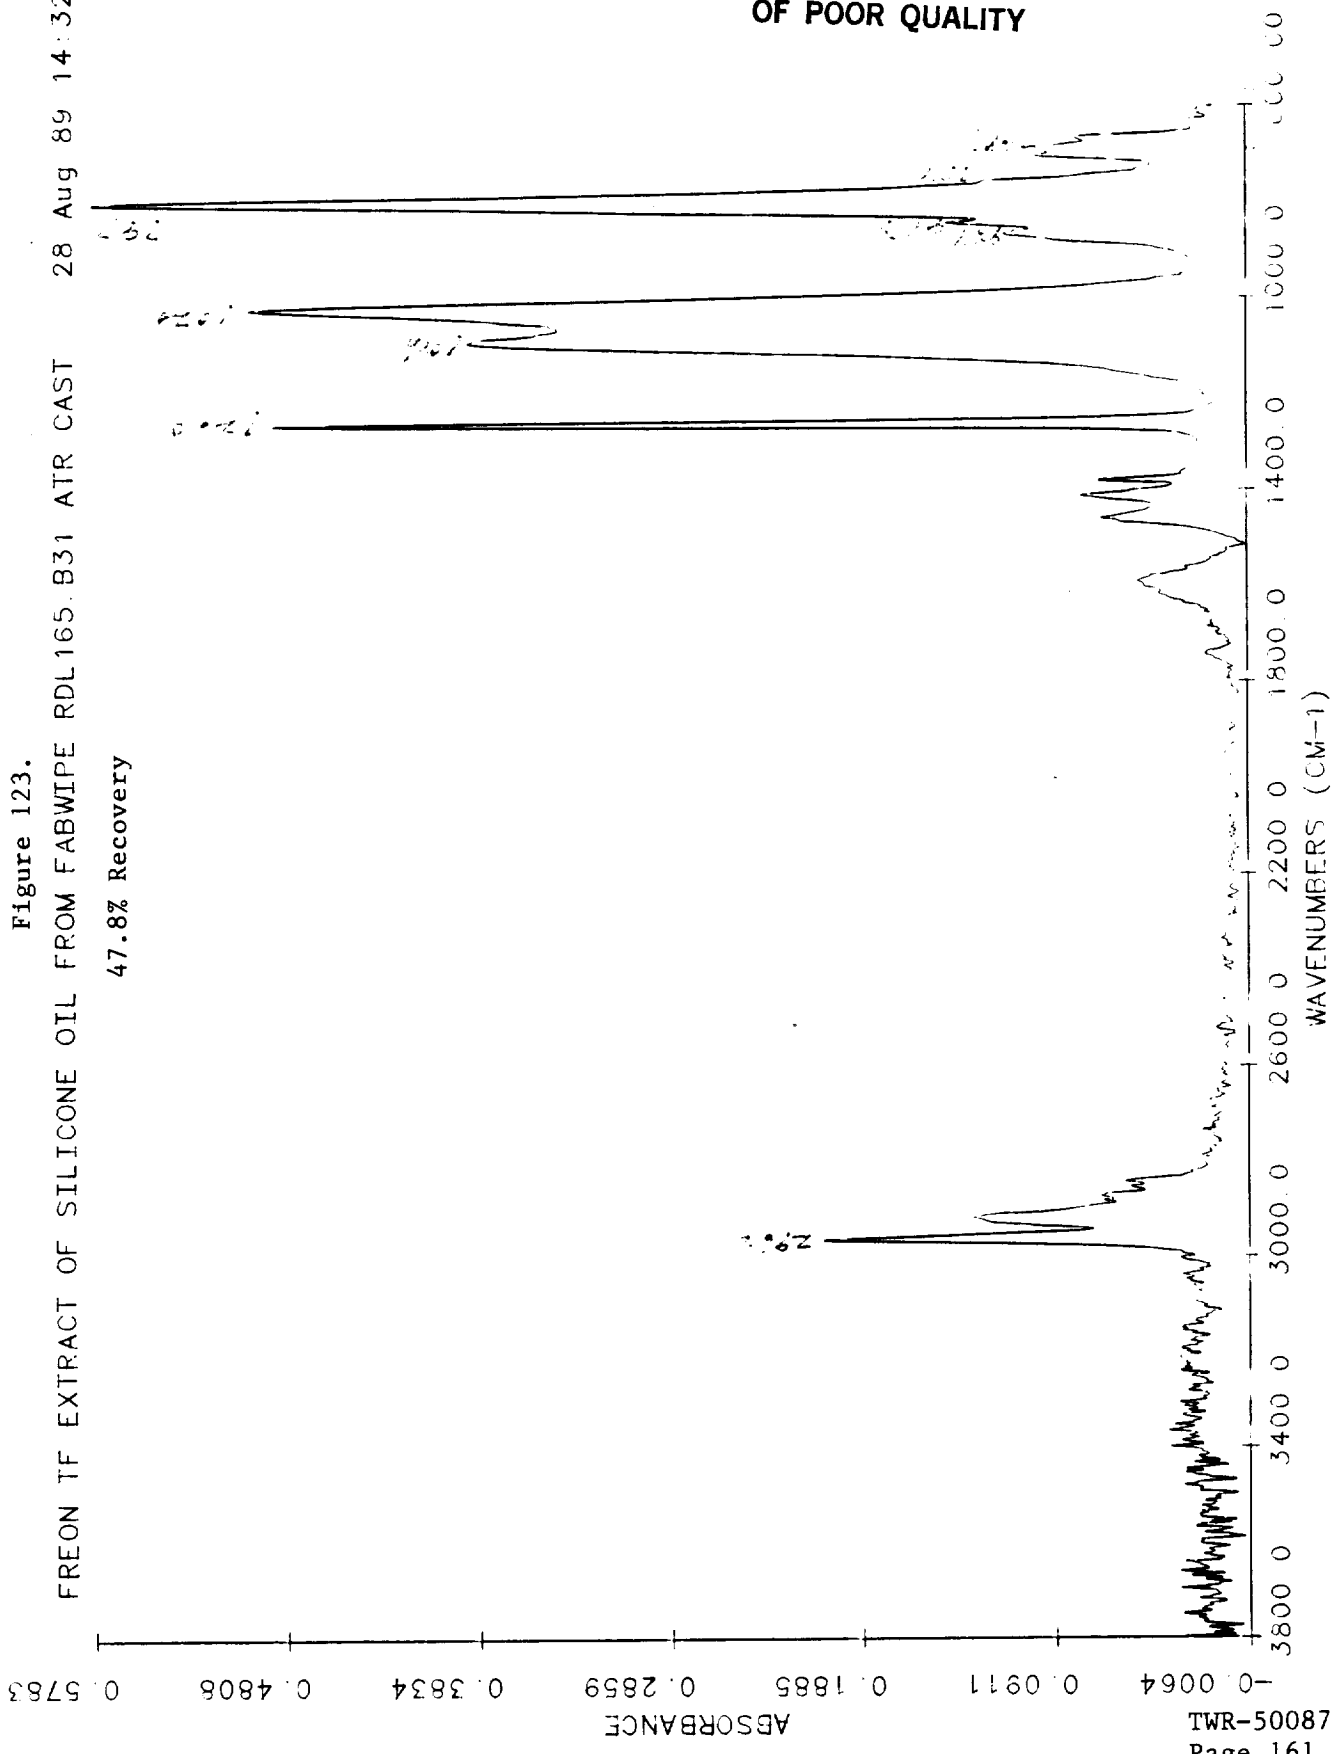

ORIGINAL PAGE IS
OF POOR QUALITY

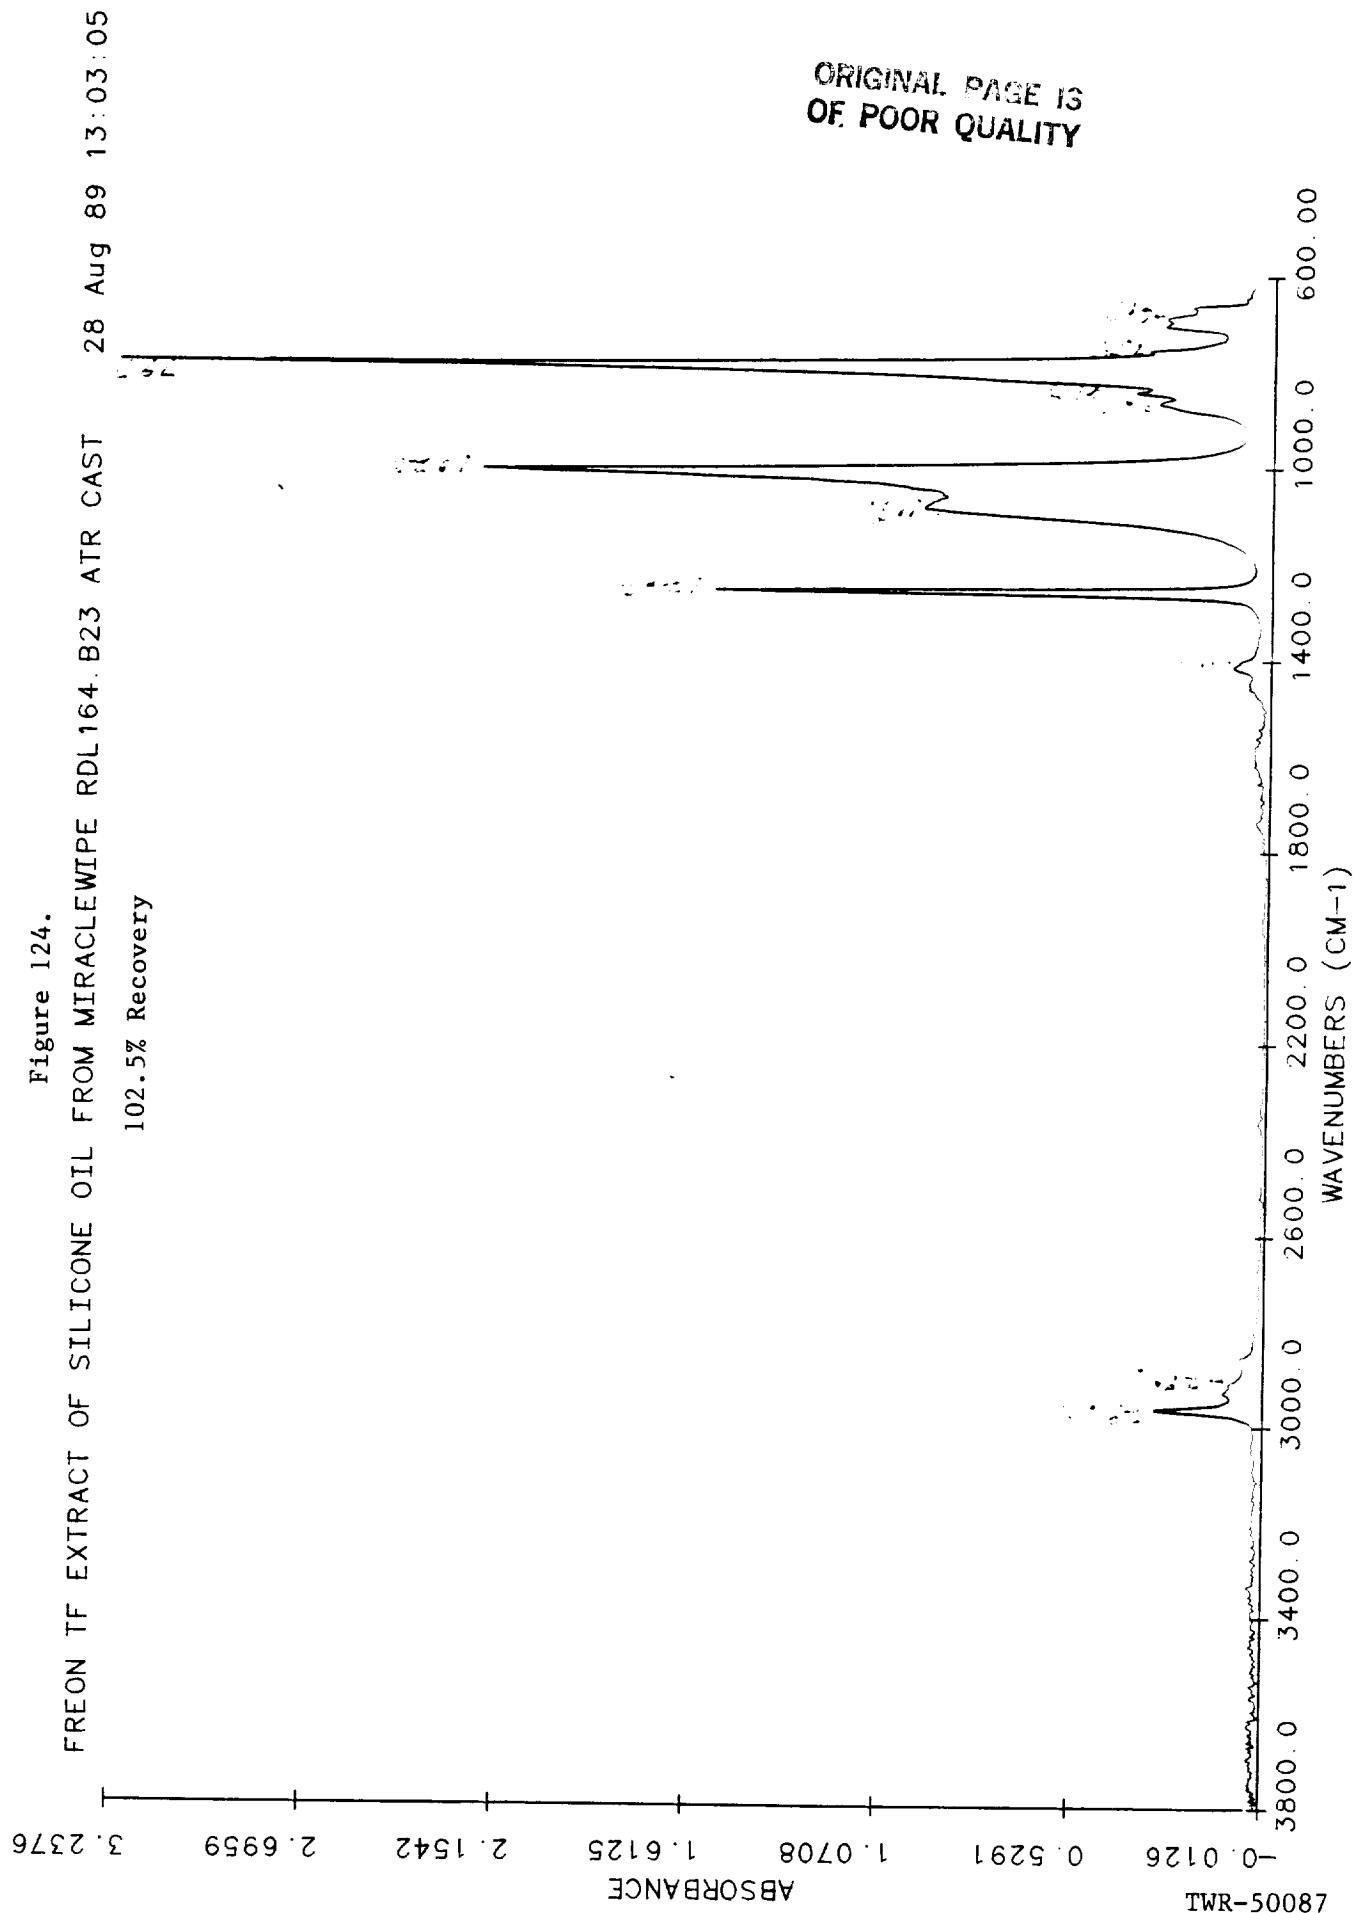


Figure 124.

FREON TF EXTRACT OF SILICONE OIL FROM MIRACLEWIPE RDL164.B23 ATR CAST
102.5% Recovery

Figure 125.


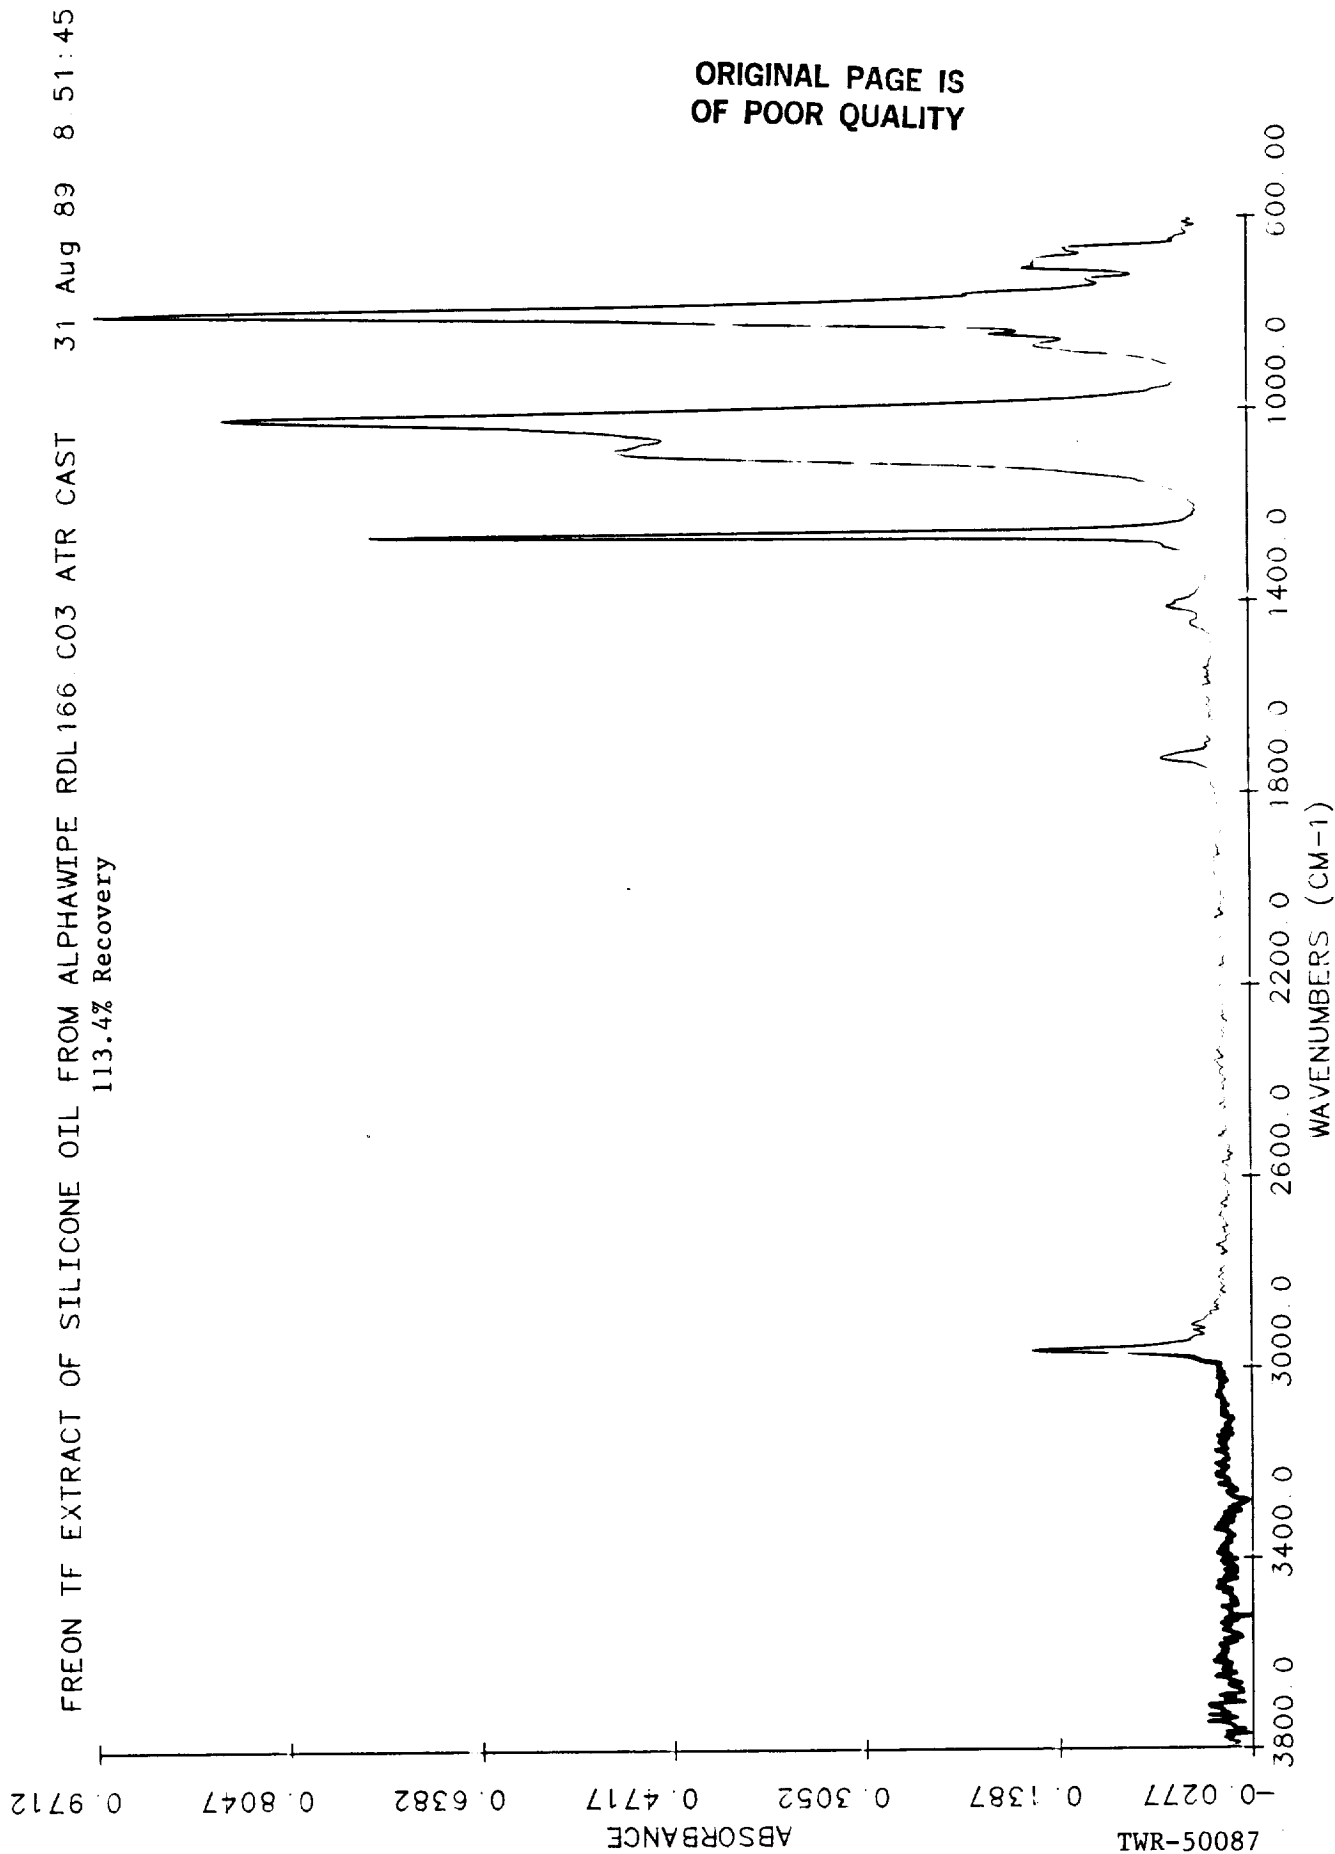


Figure 126.

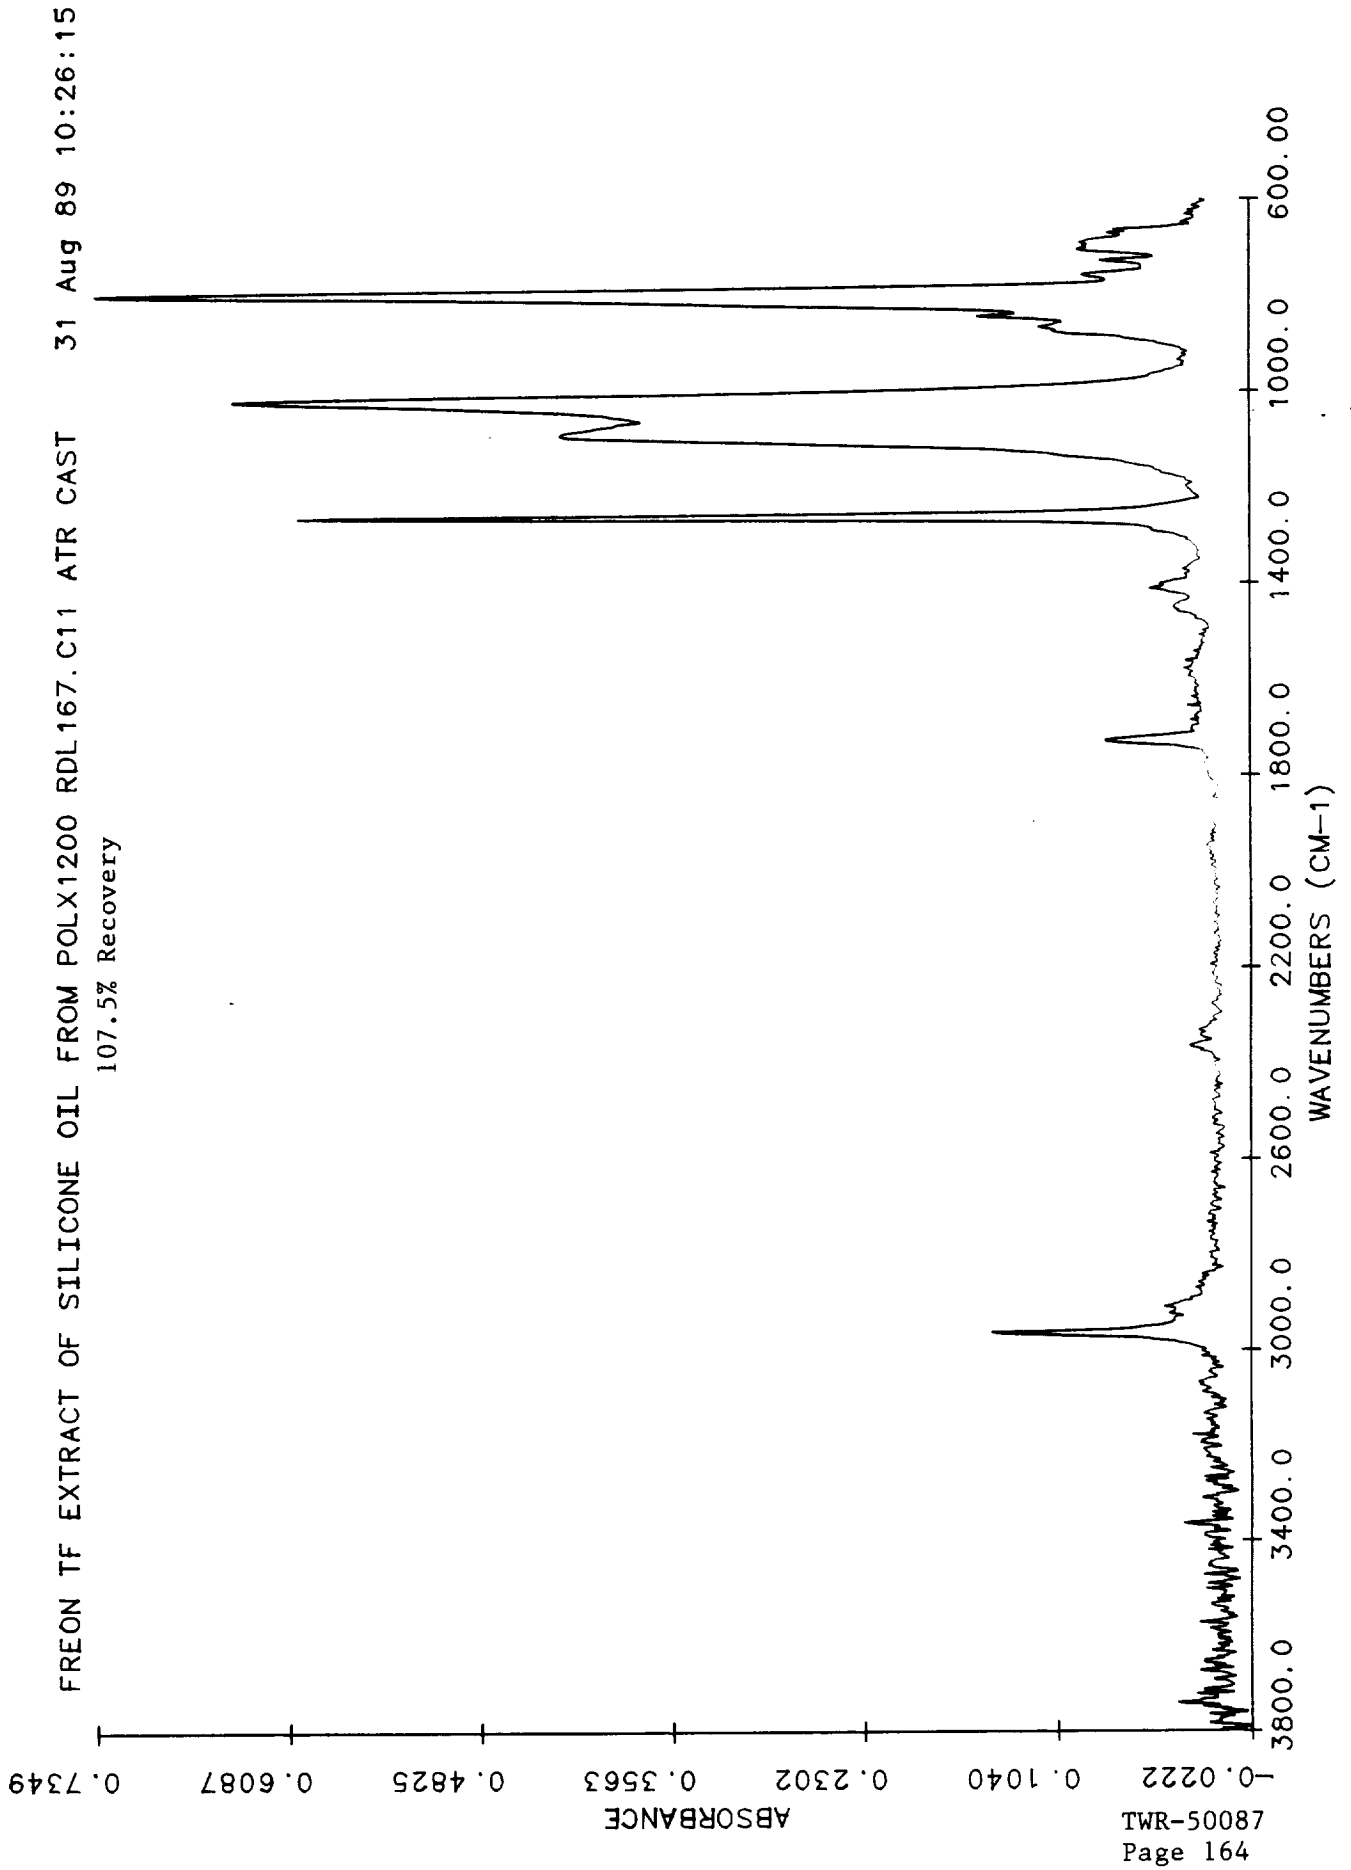

ORIGINAL PAGE IS
OF POOR QUALITY

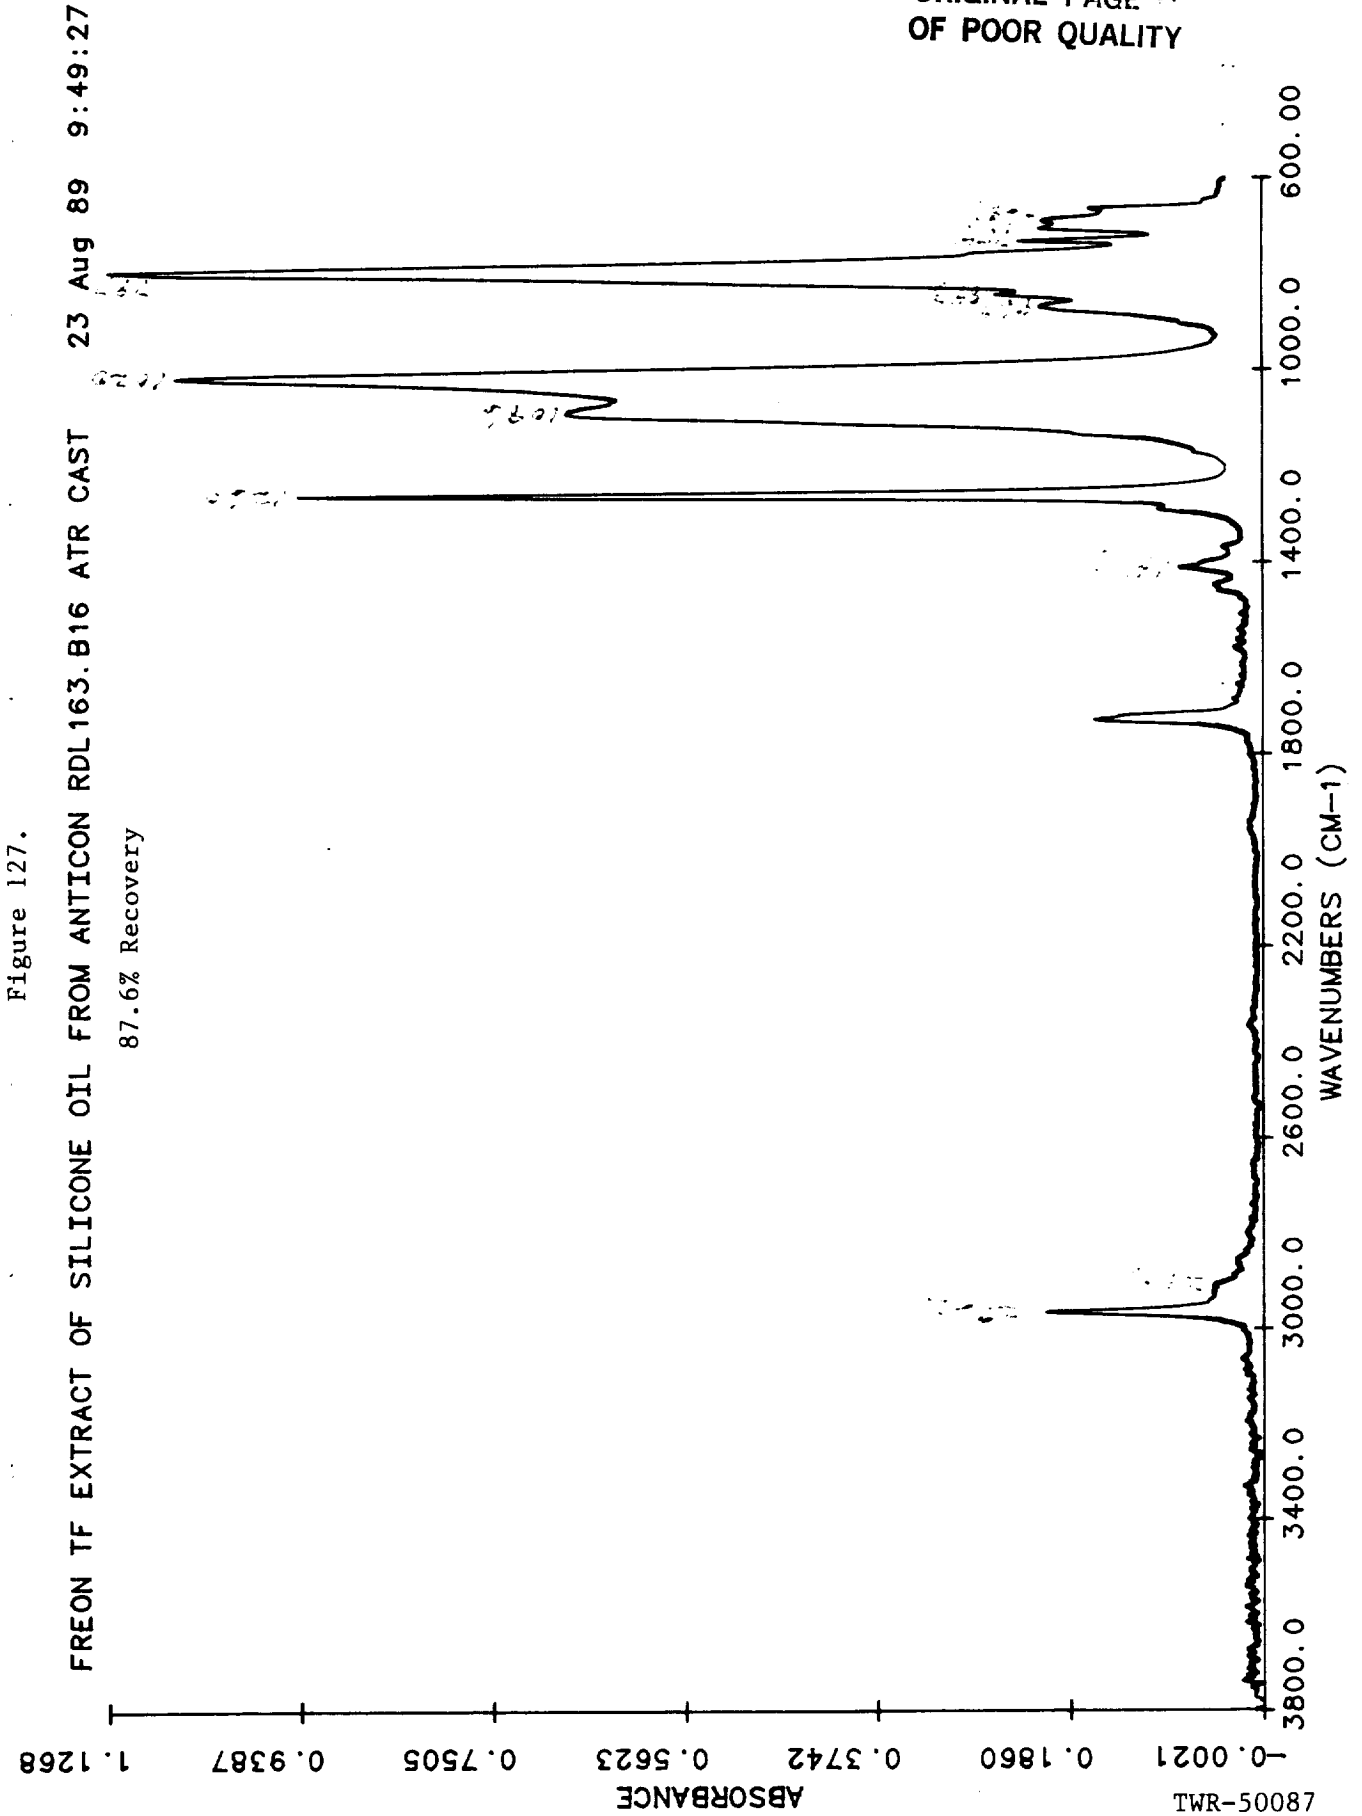


Figure 128.

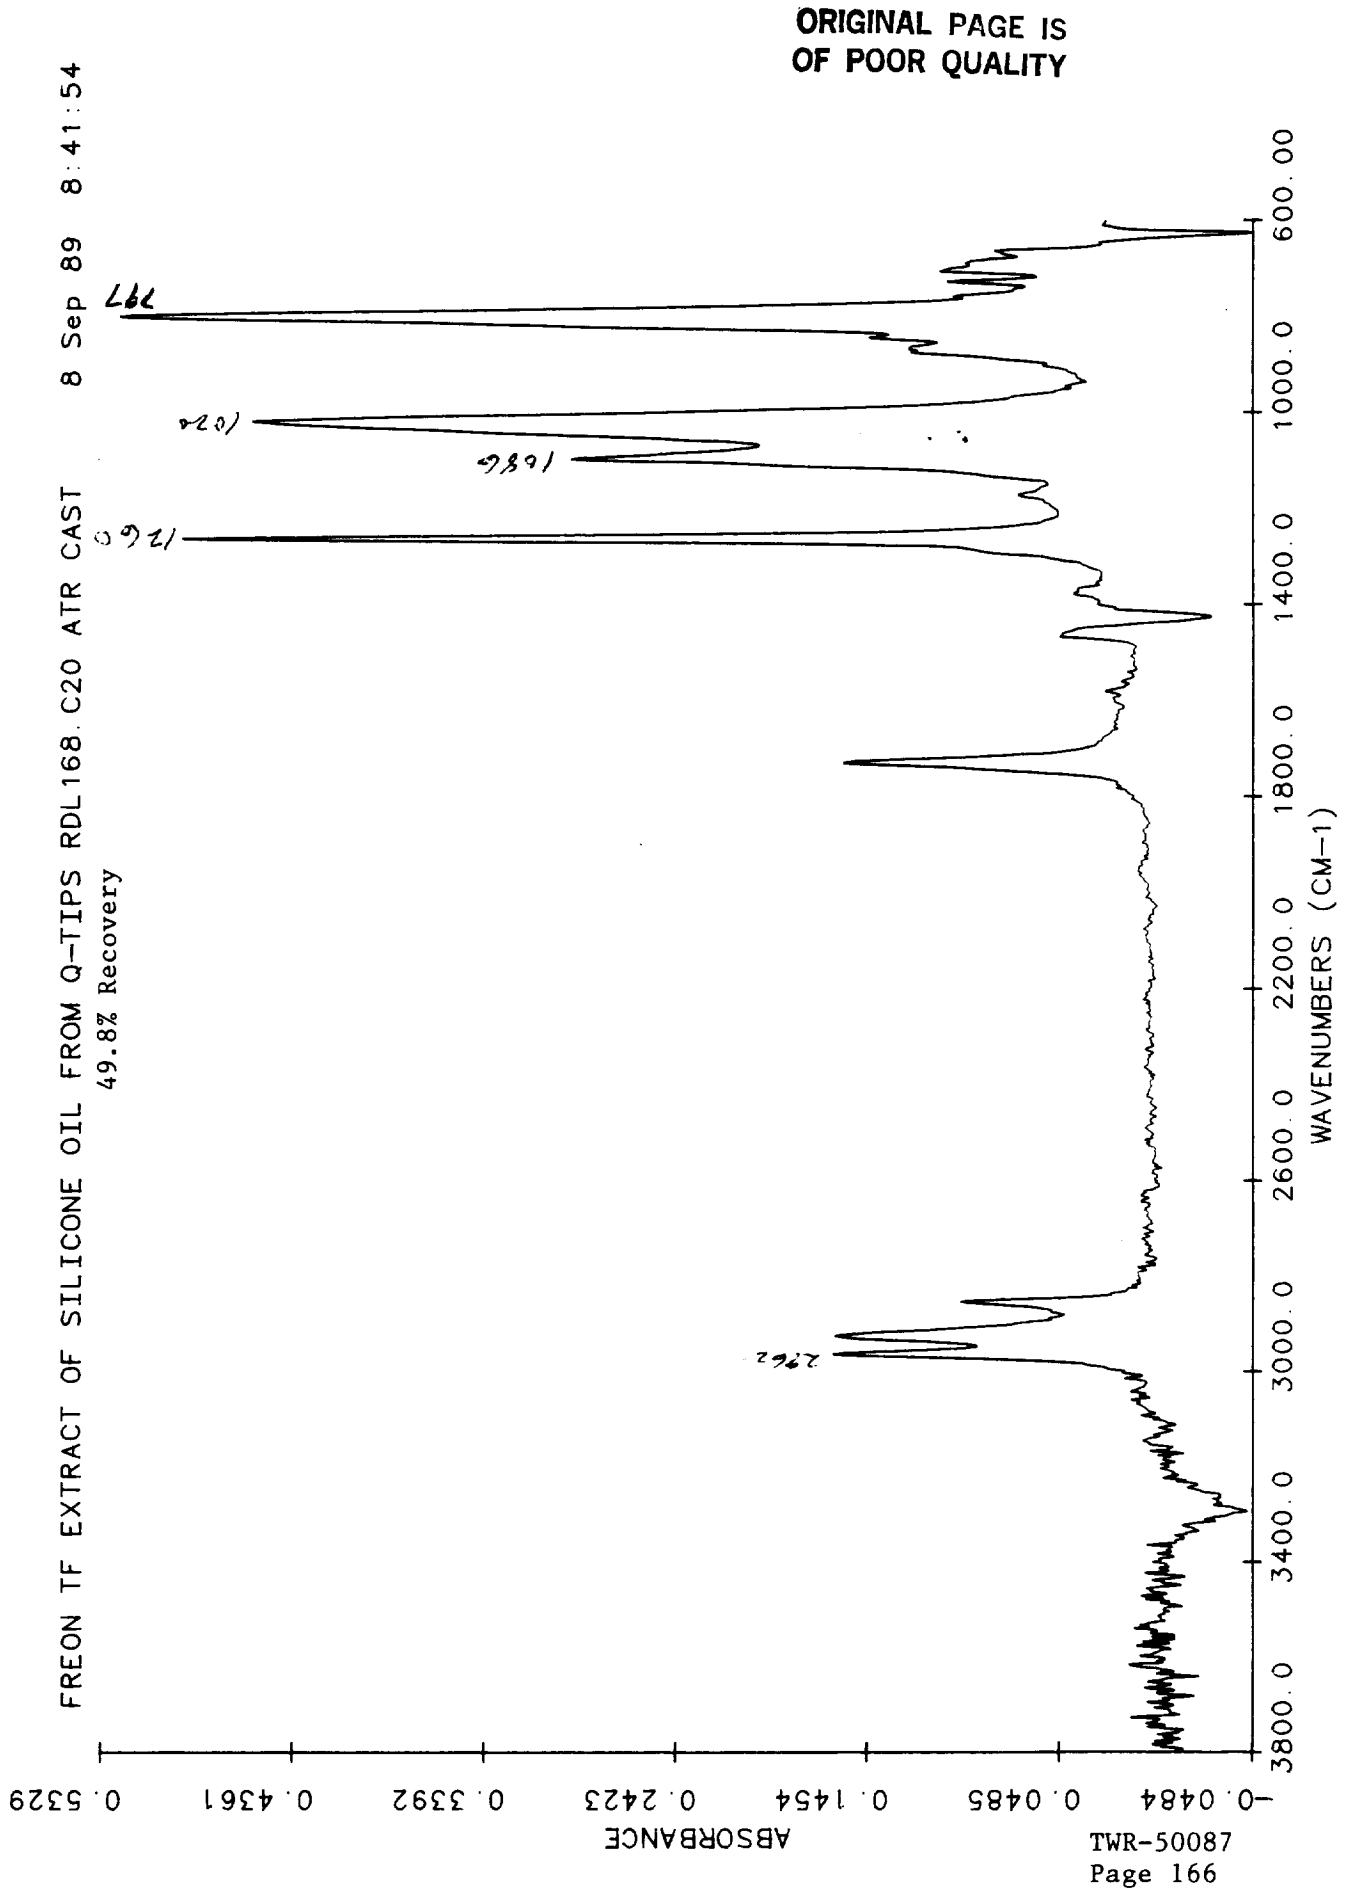


Figure 129.

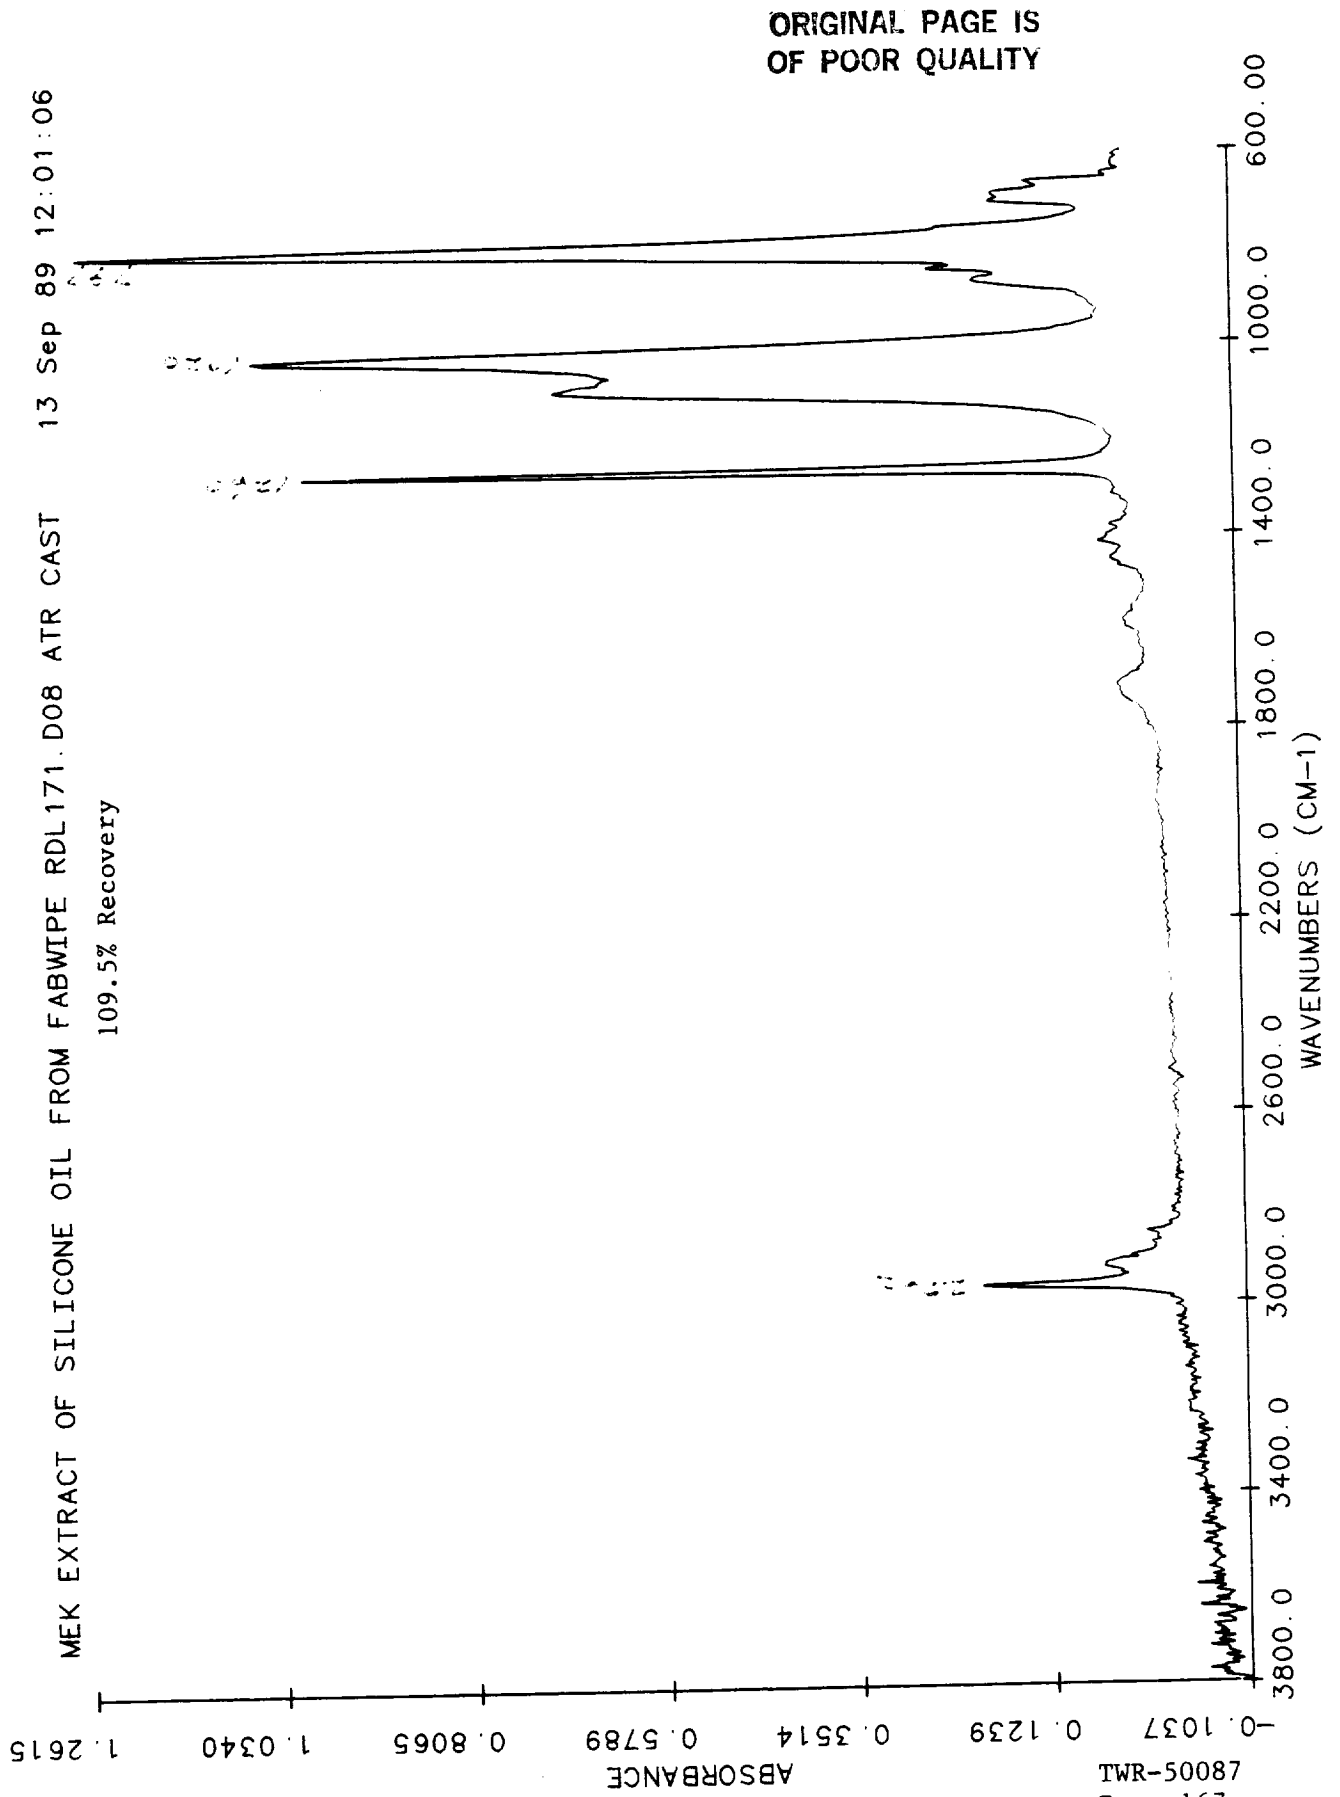


Figure 130.


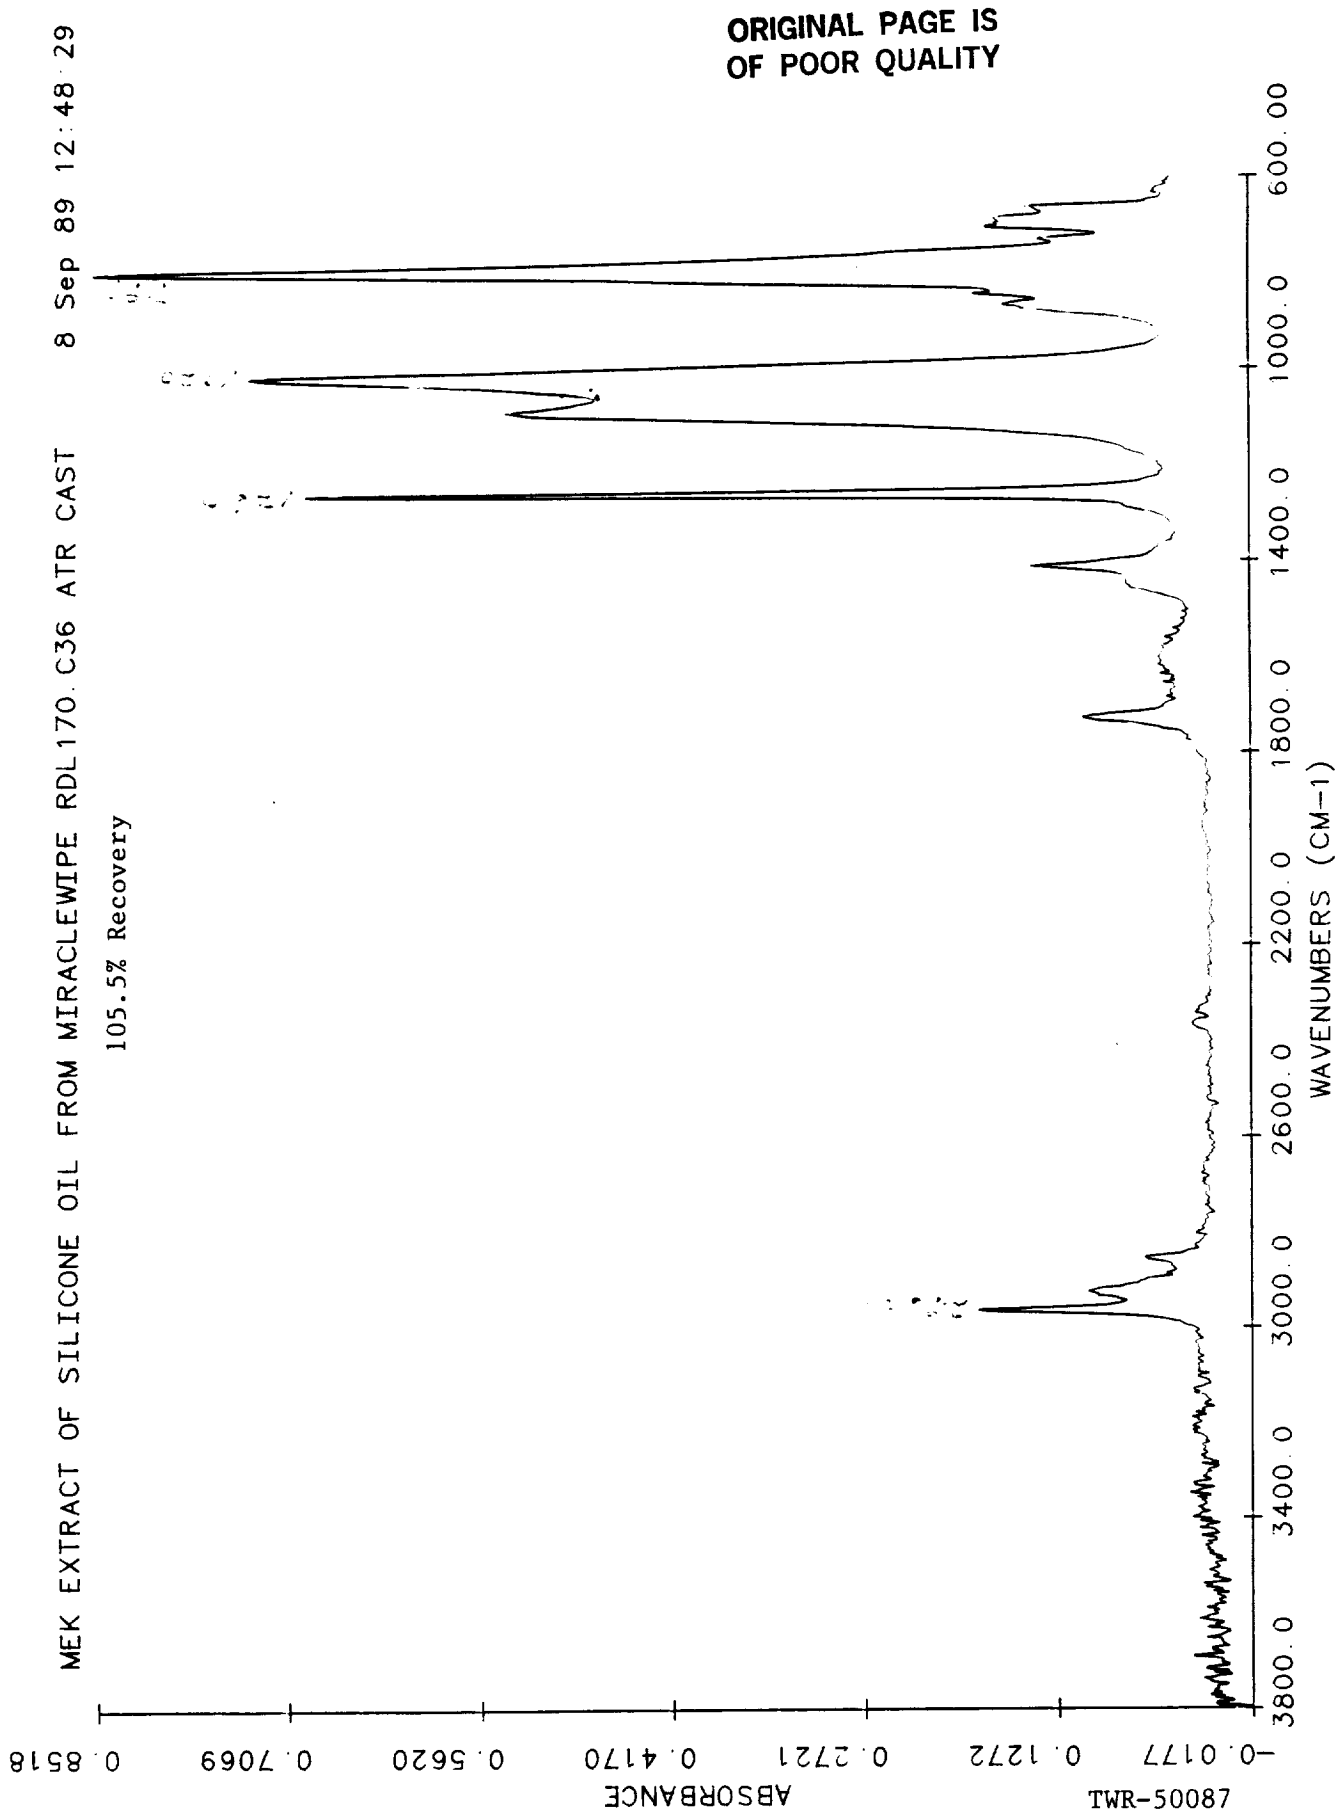


Figure 131.

MEK EXTRACT OF SILICONE OIL FROM ALPHAWIPE RDL172.D16 ATR CAST 13 Sep 89 13:05:31

104.5% Recovery

ORIGINAL PAGE IS OF POOR QUALITY

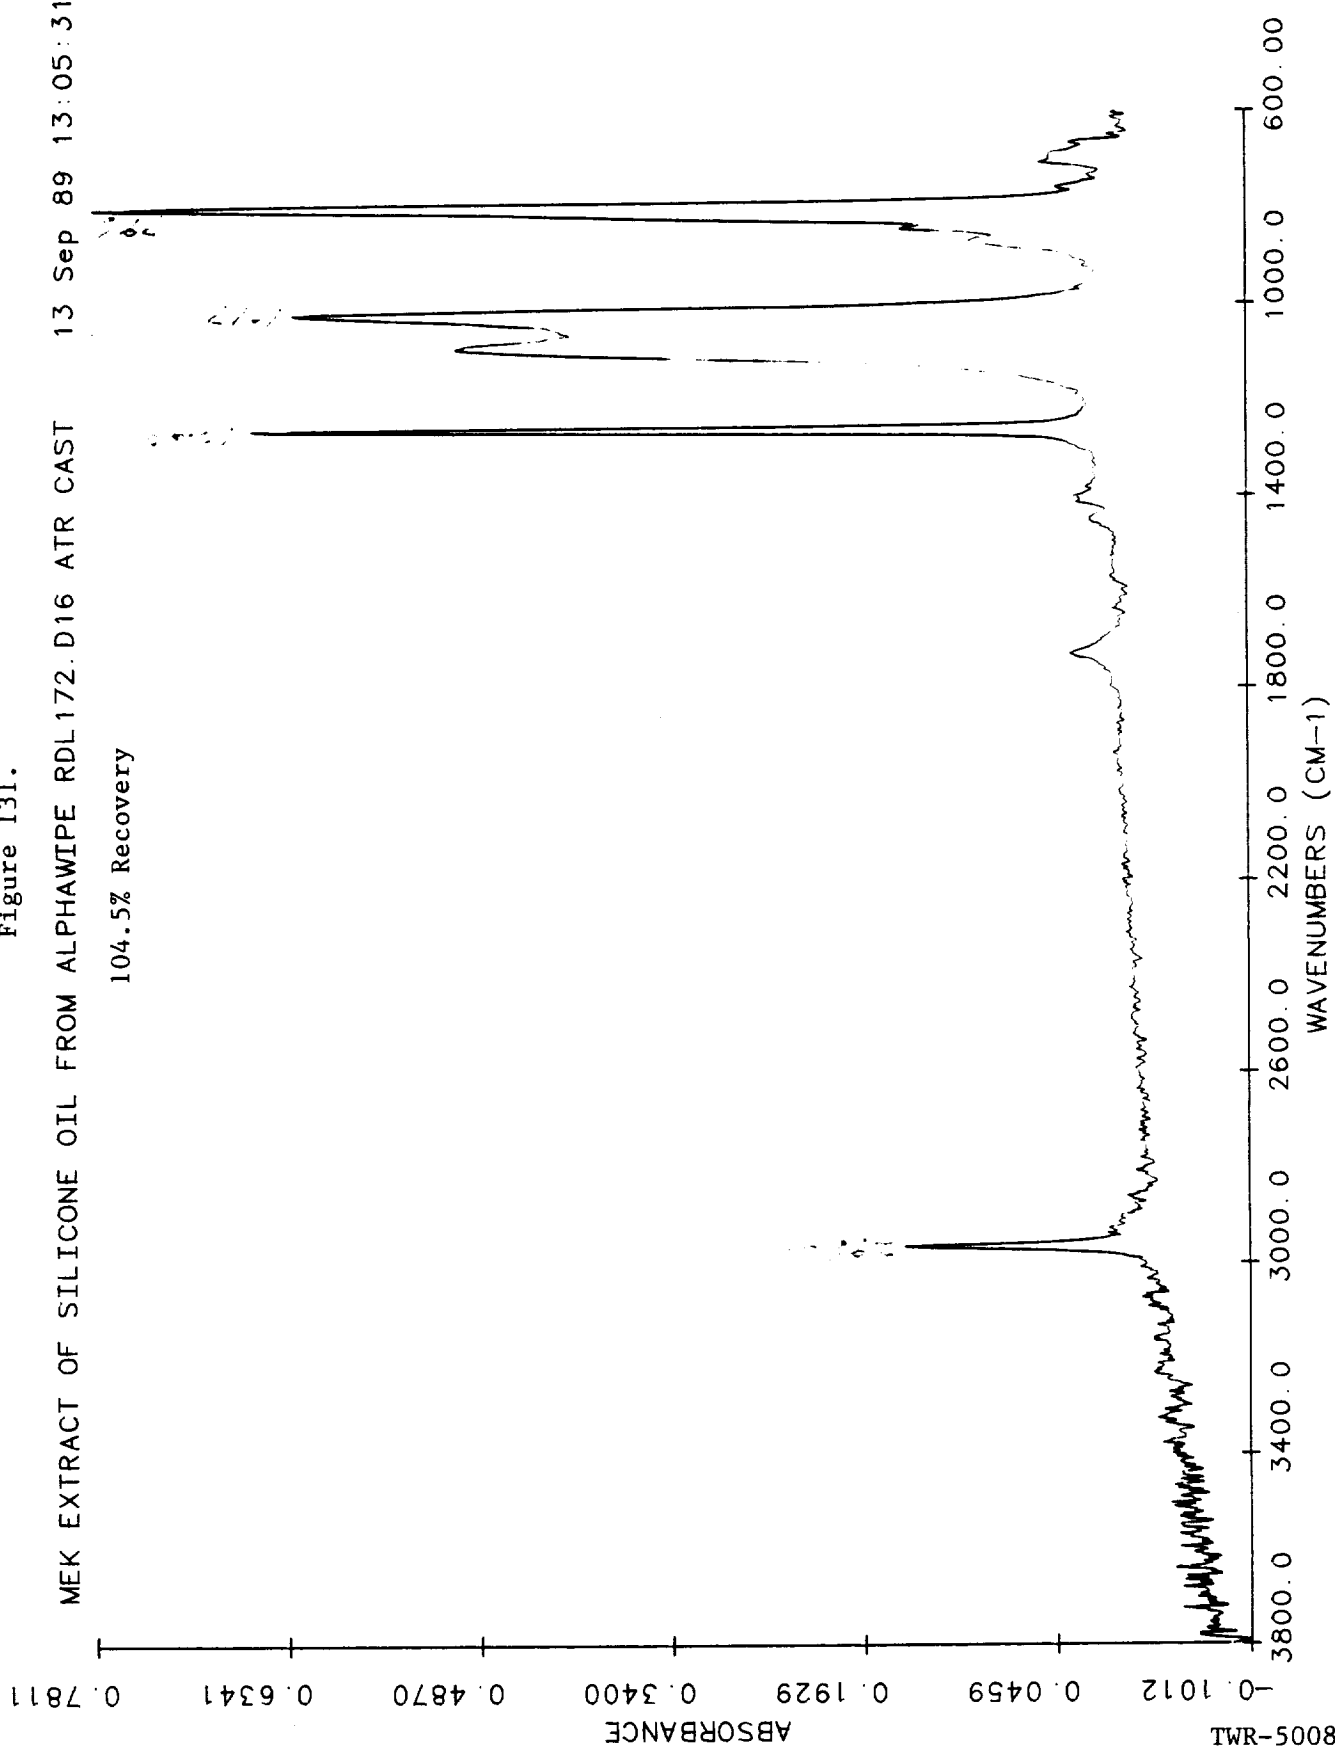

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 132.

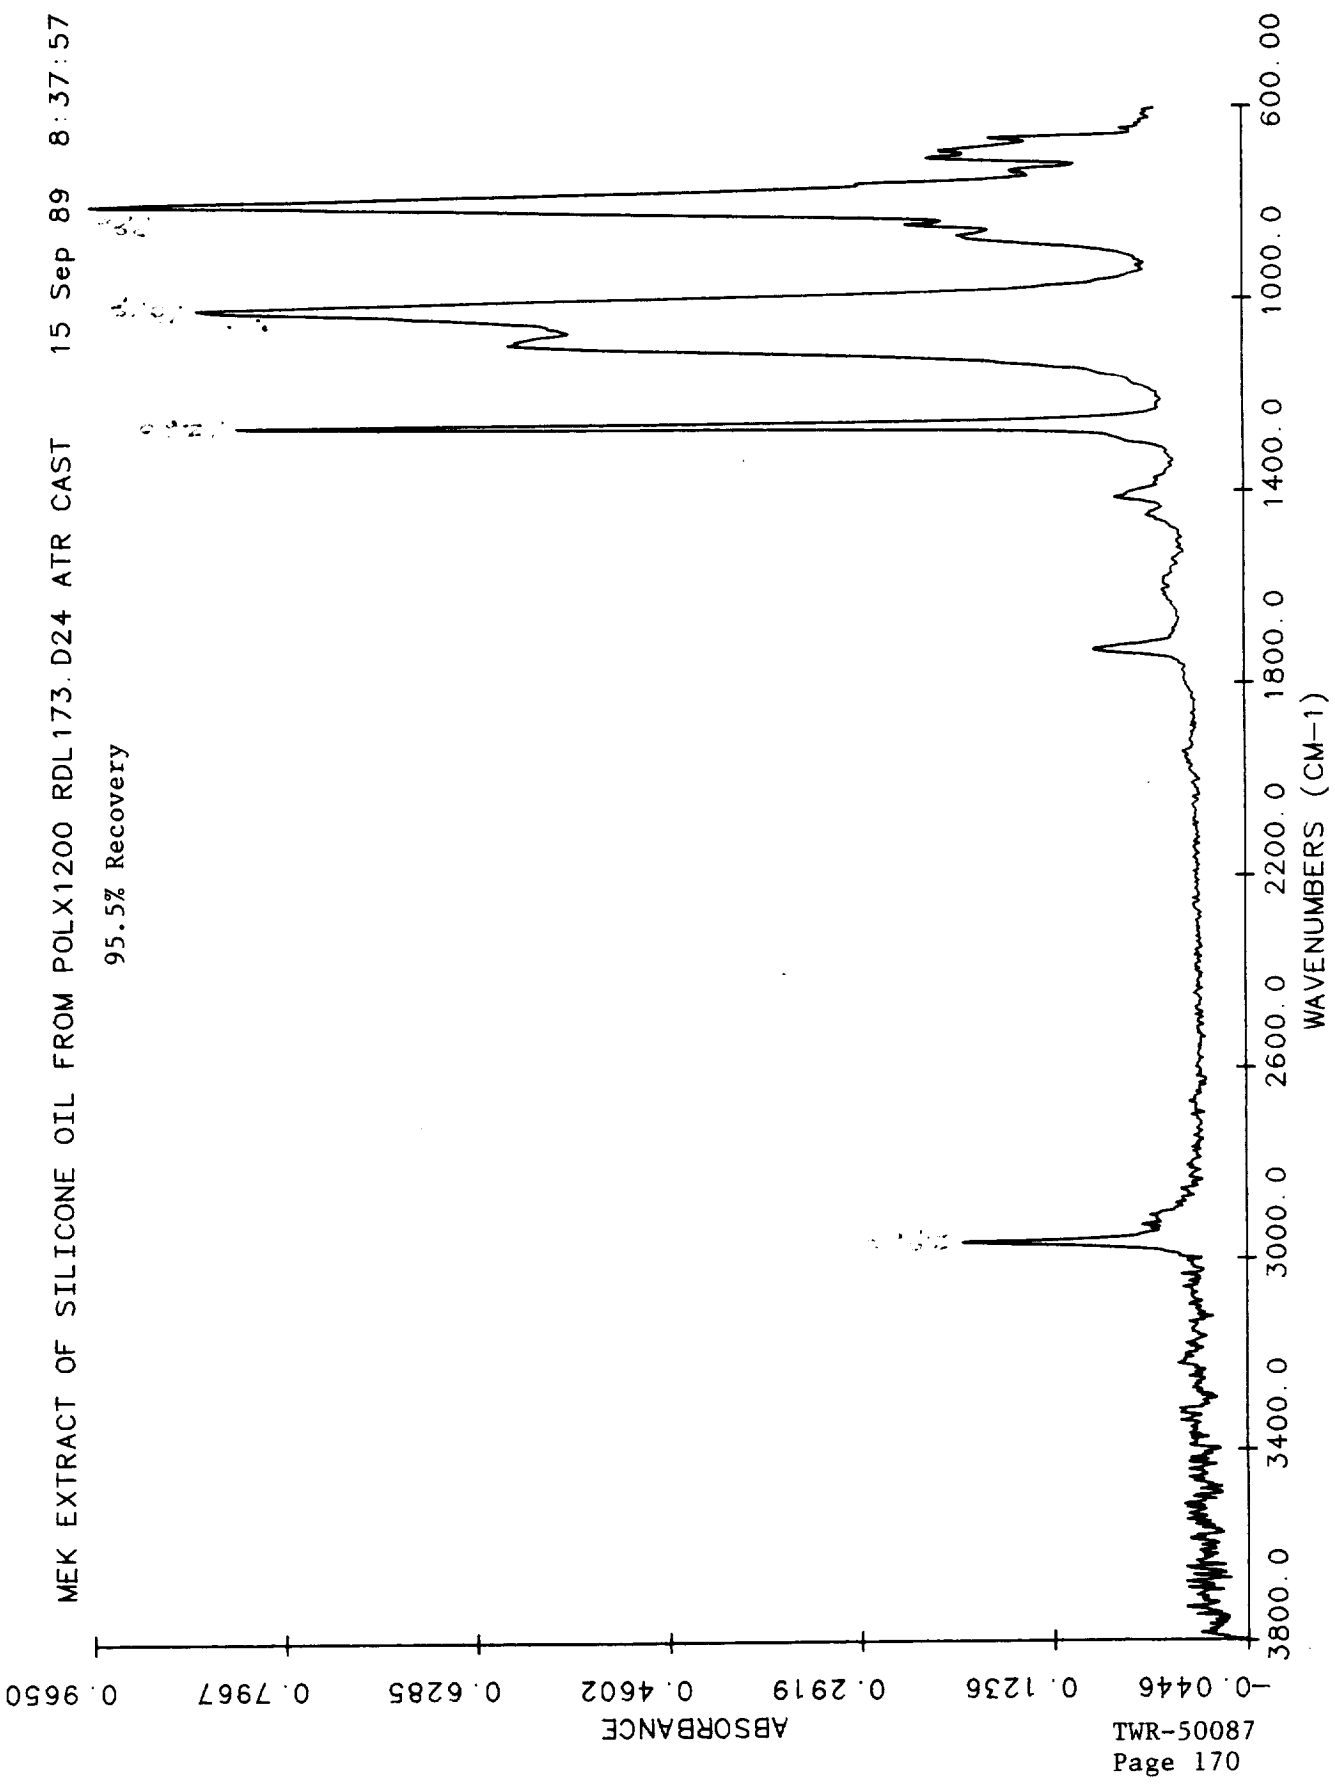


Figure 133.


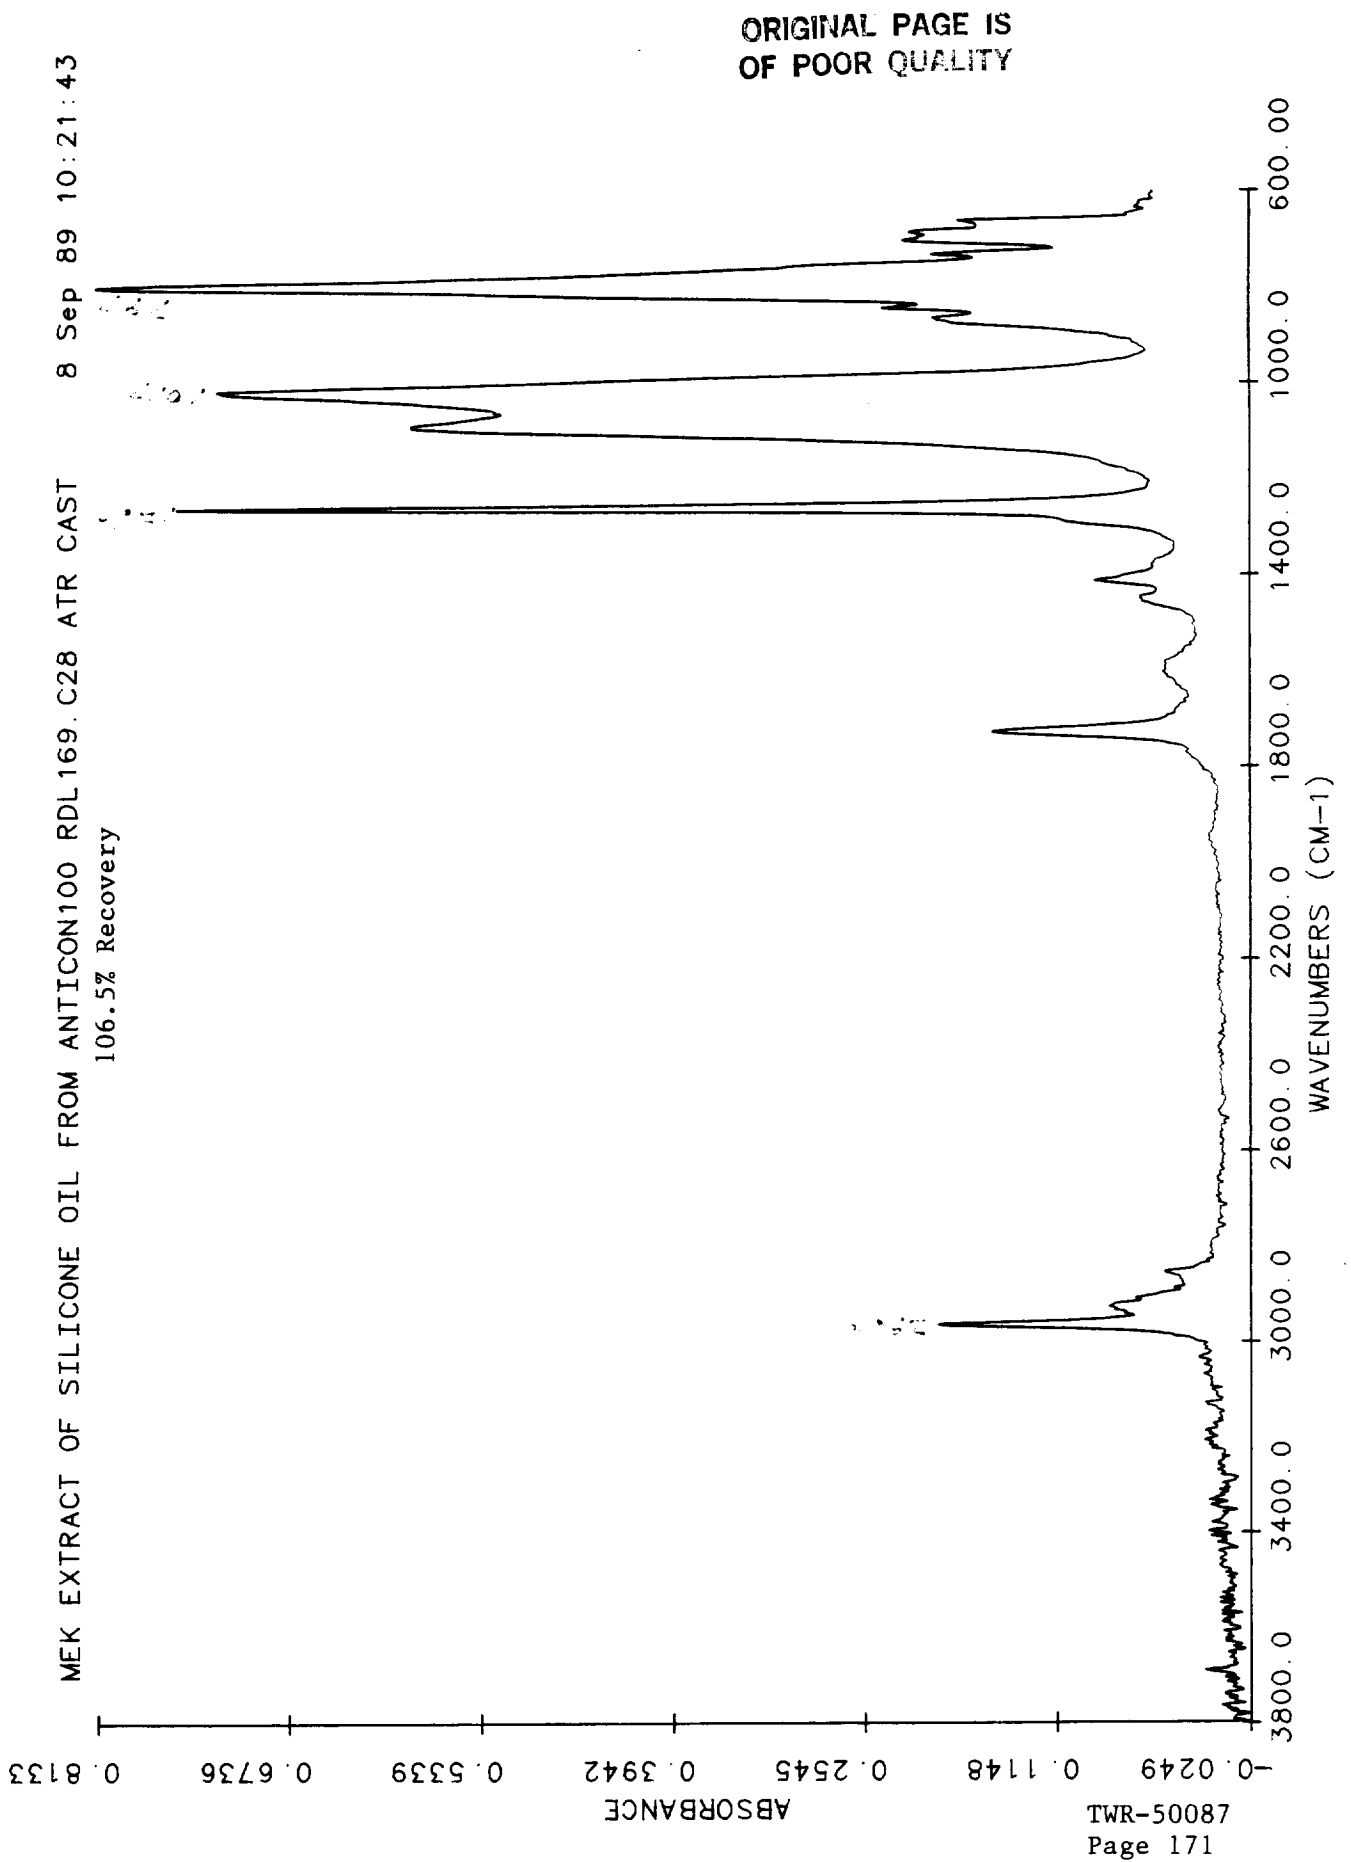


Figure 134.

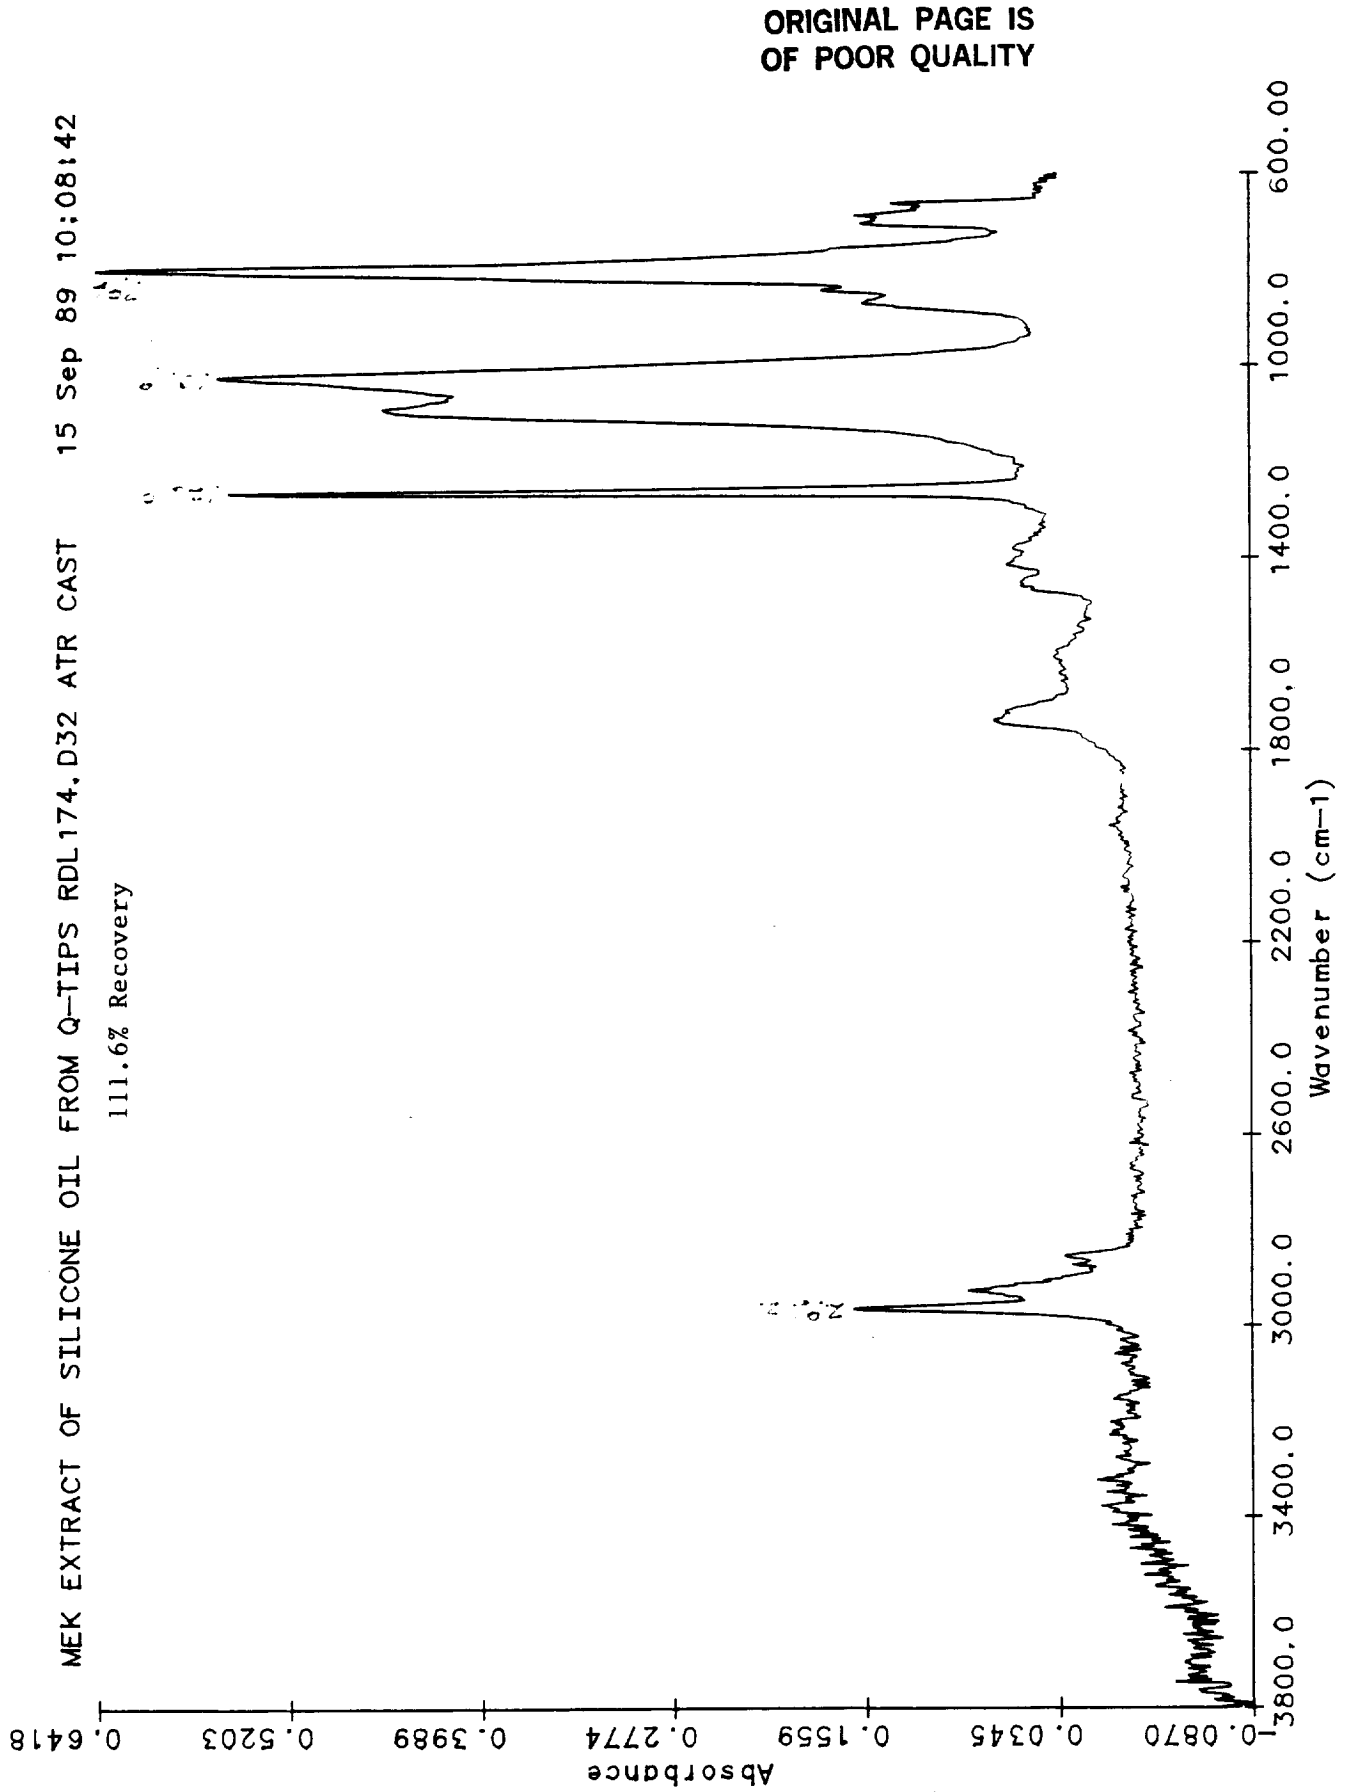

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 135.

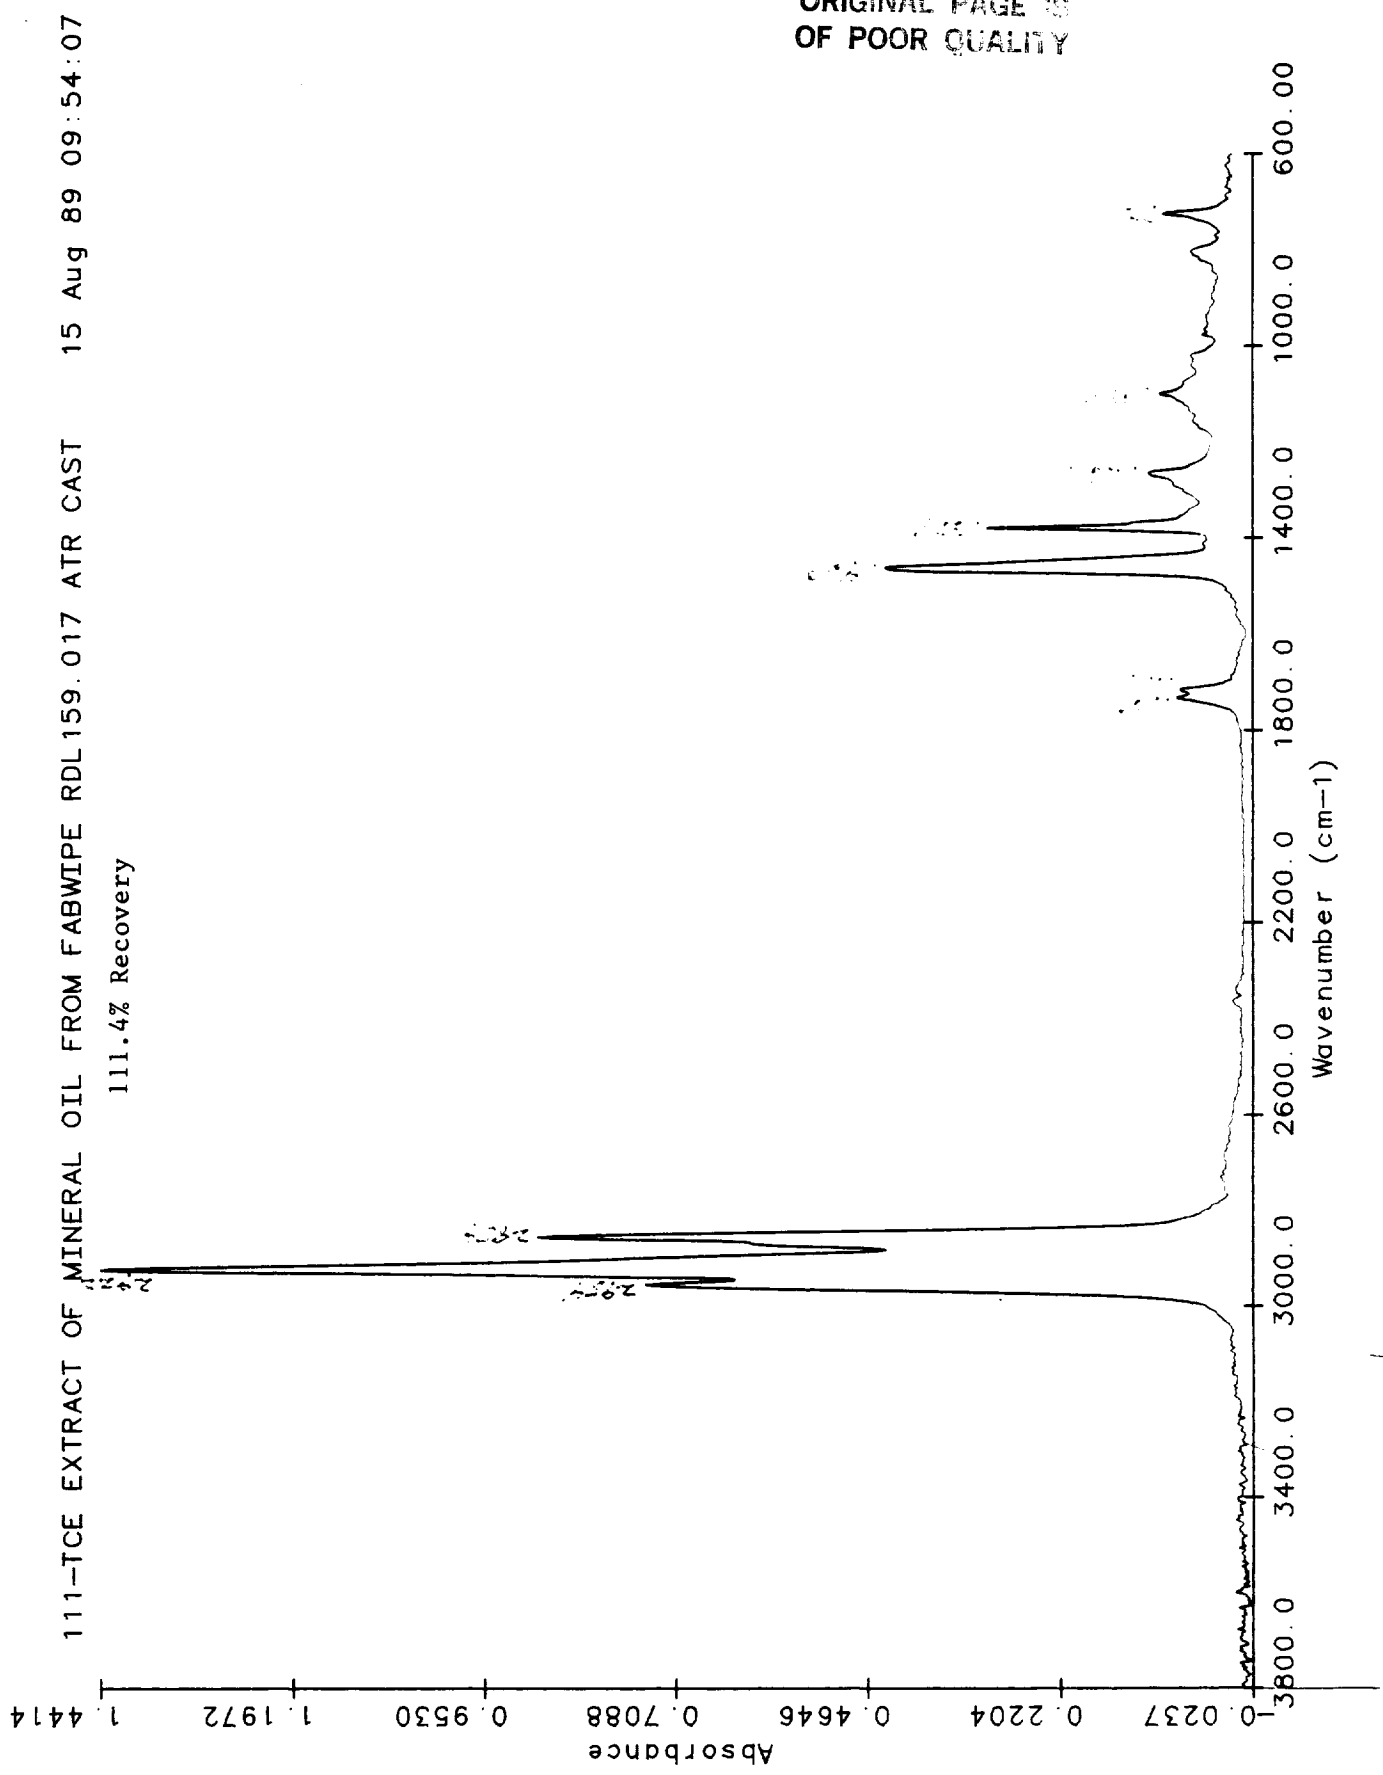


Figure 136.



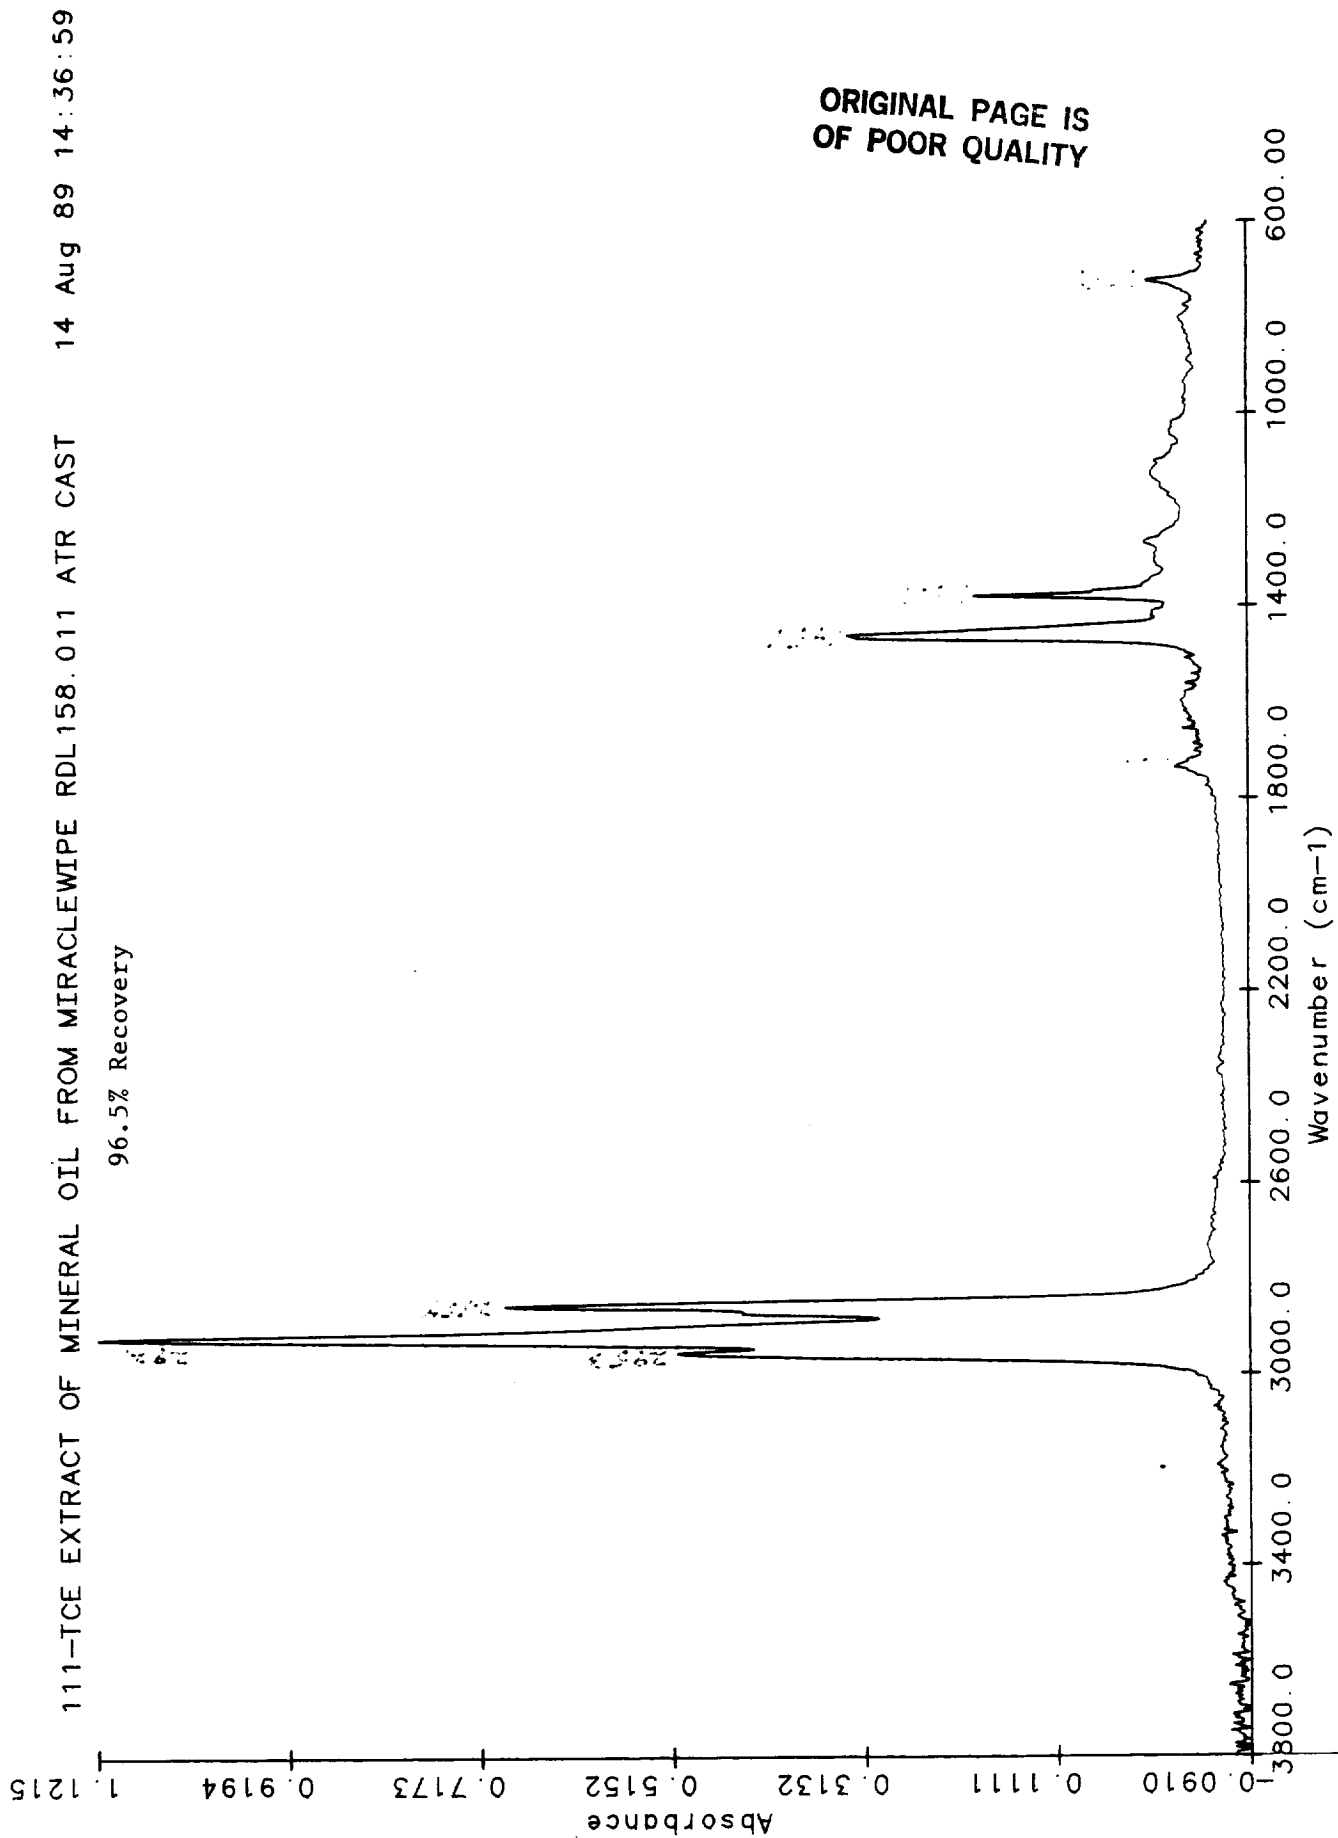


Figure 137.

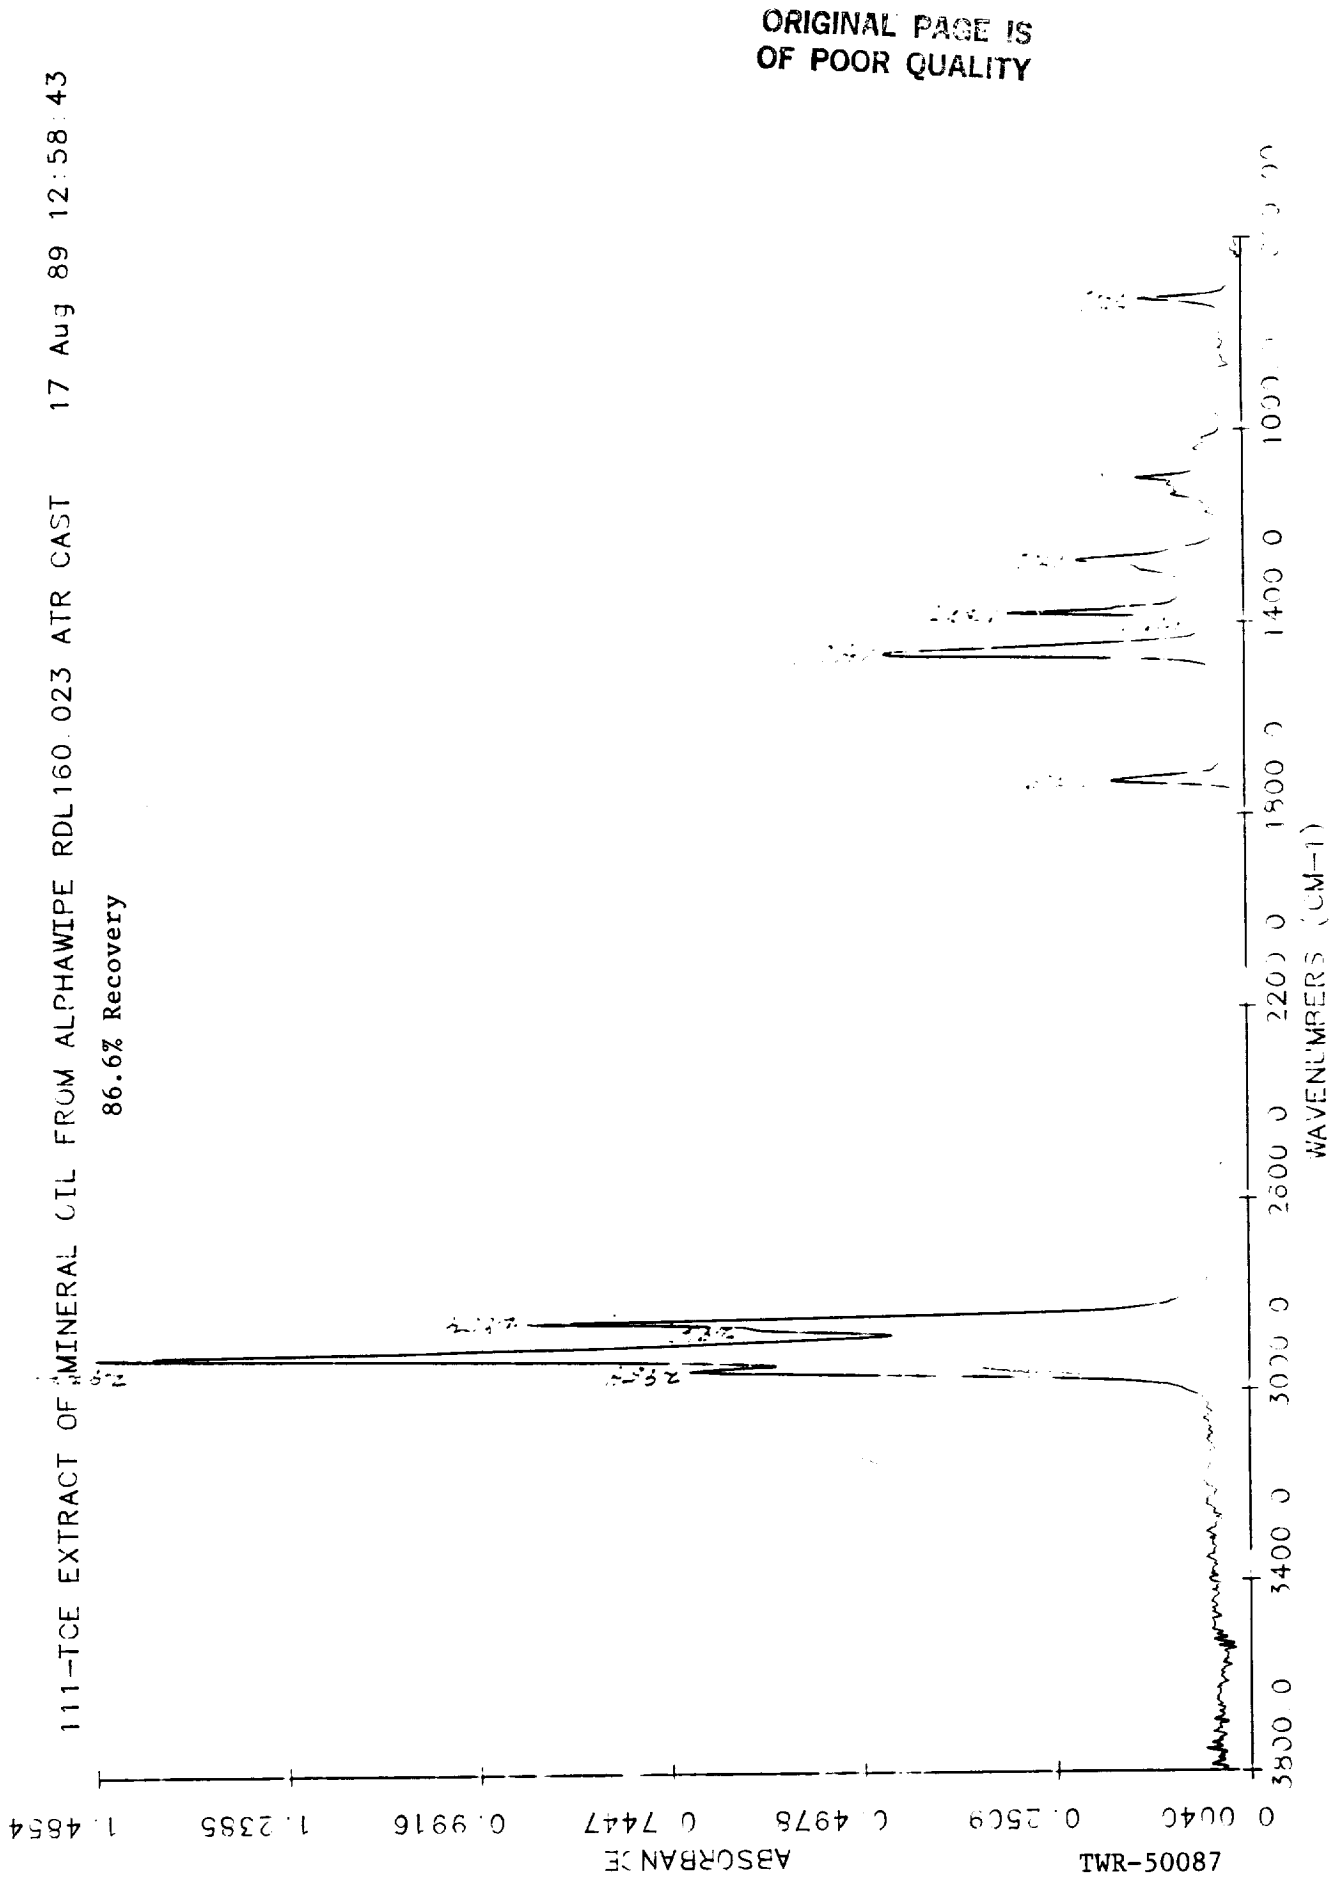

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 138.

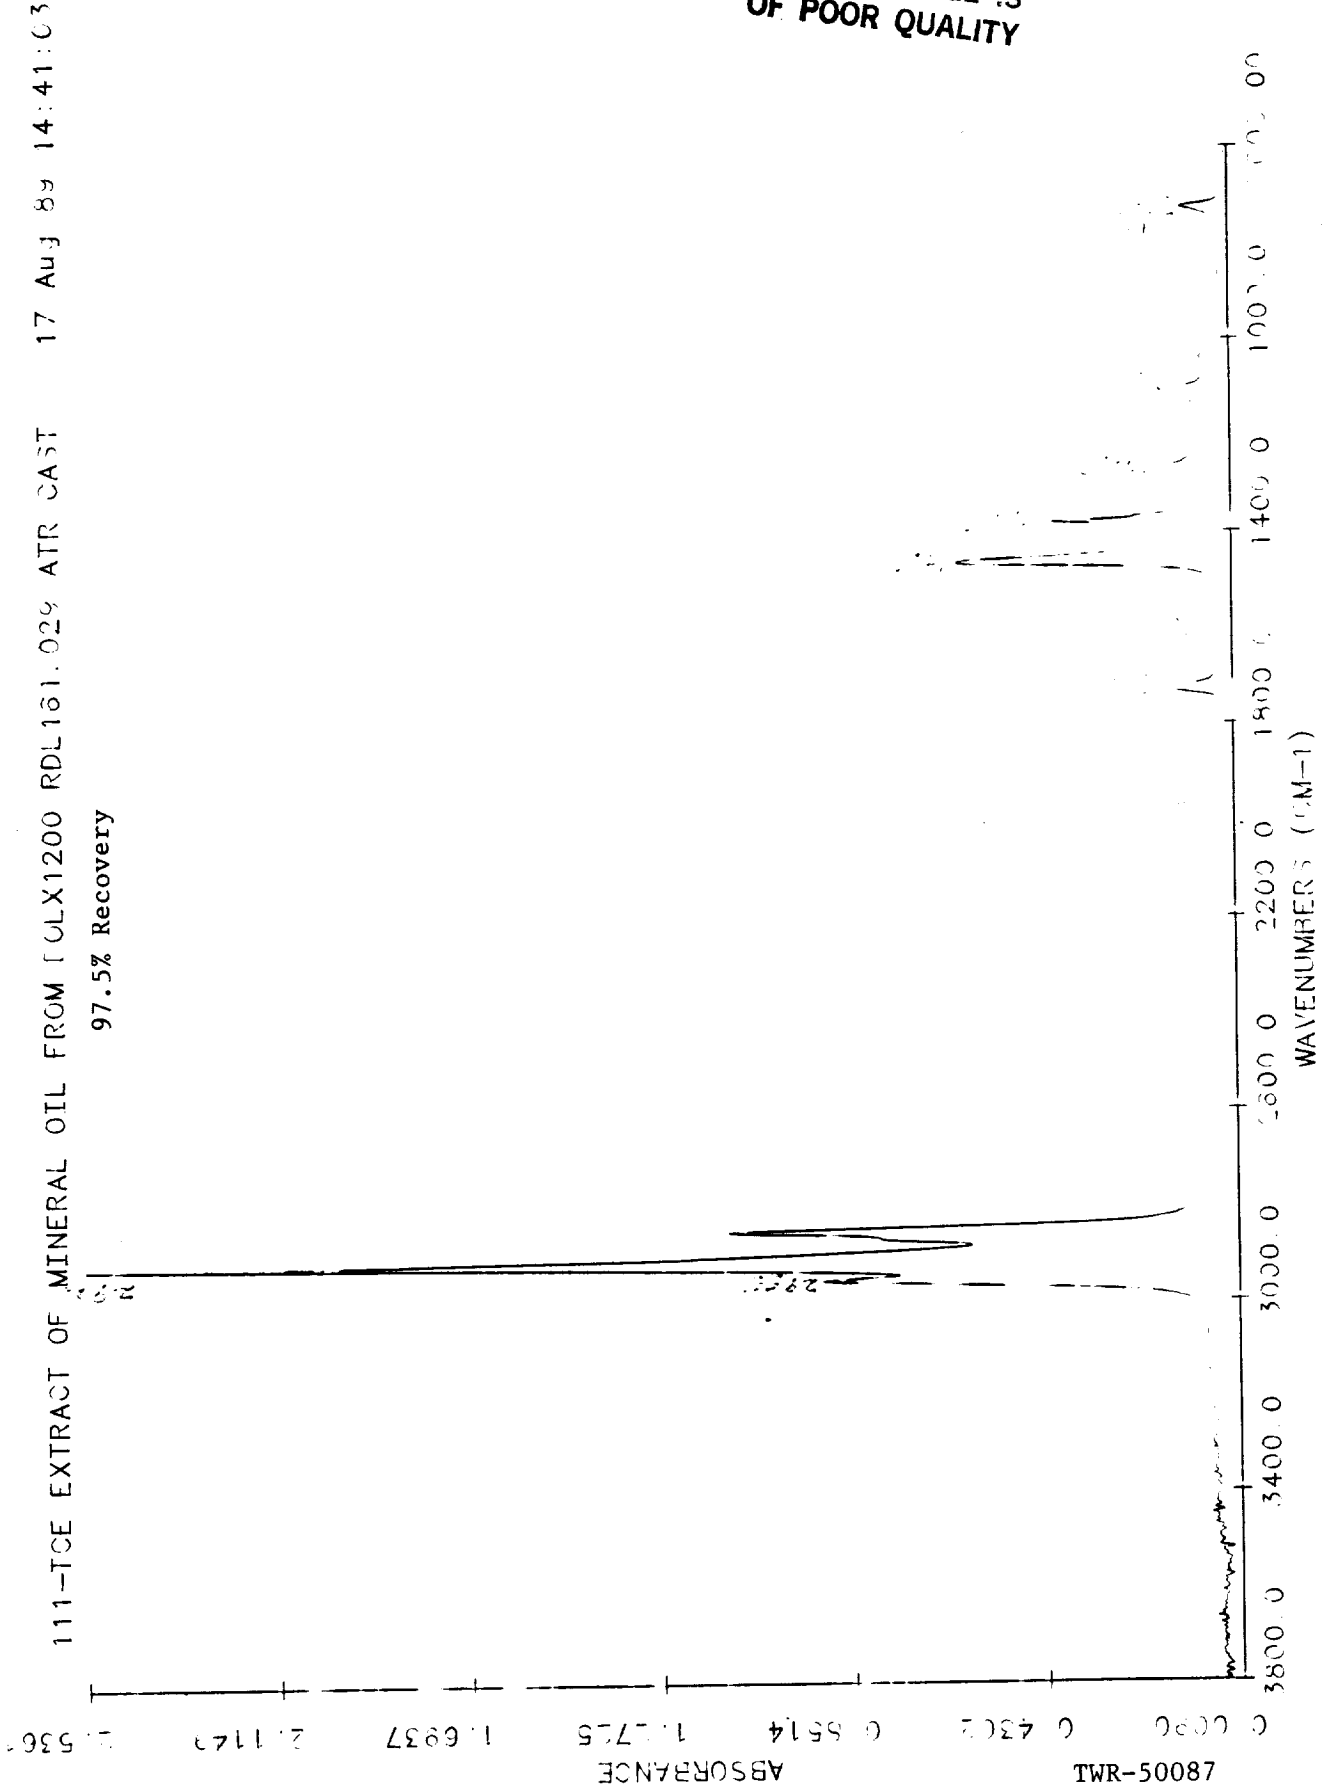

ORIGINAL PAGE IS
OF POOR QUALITY

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 139.


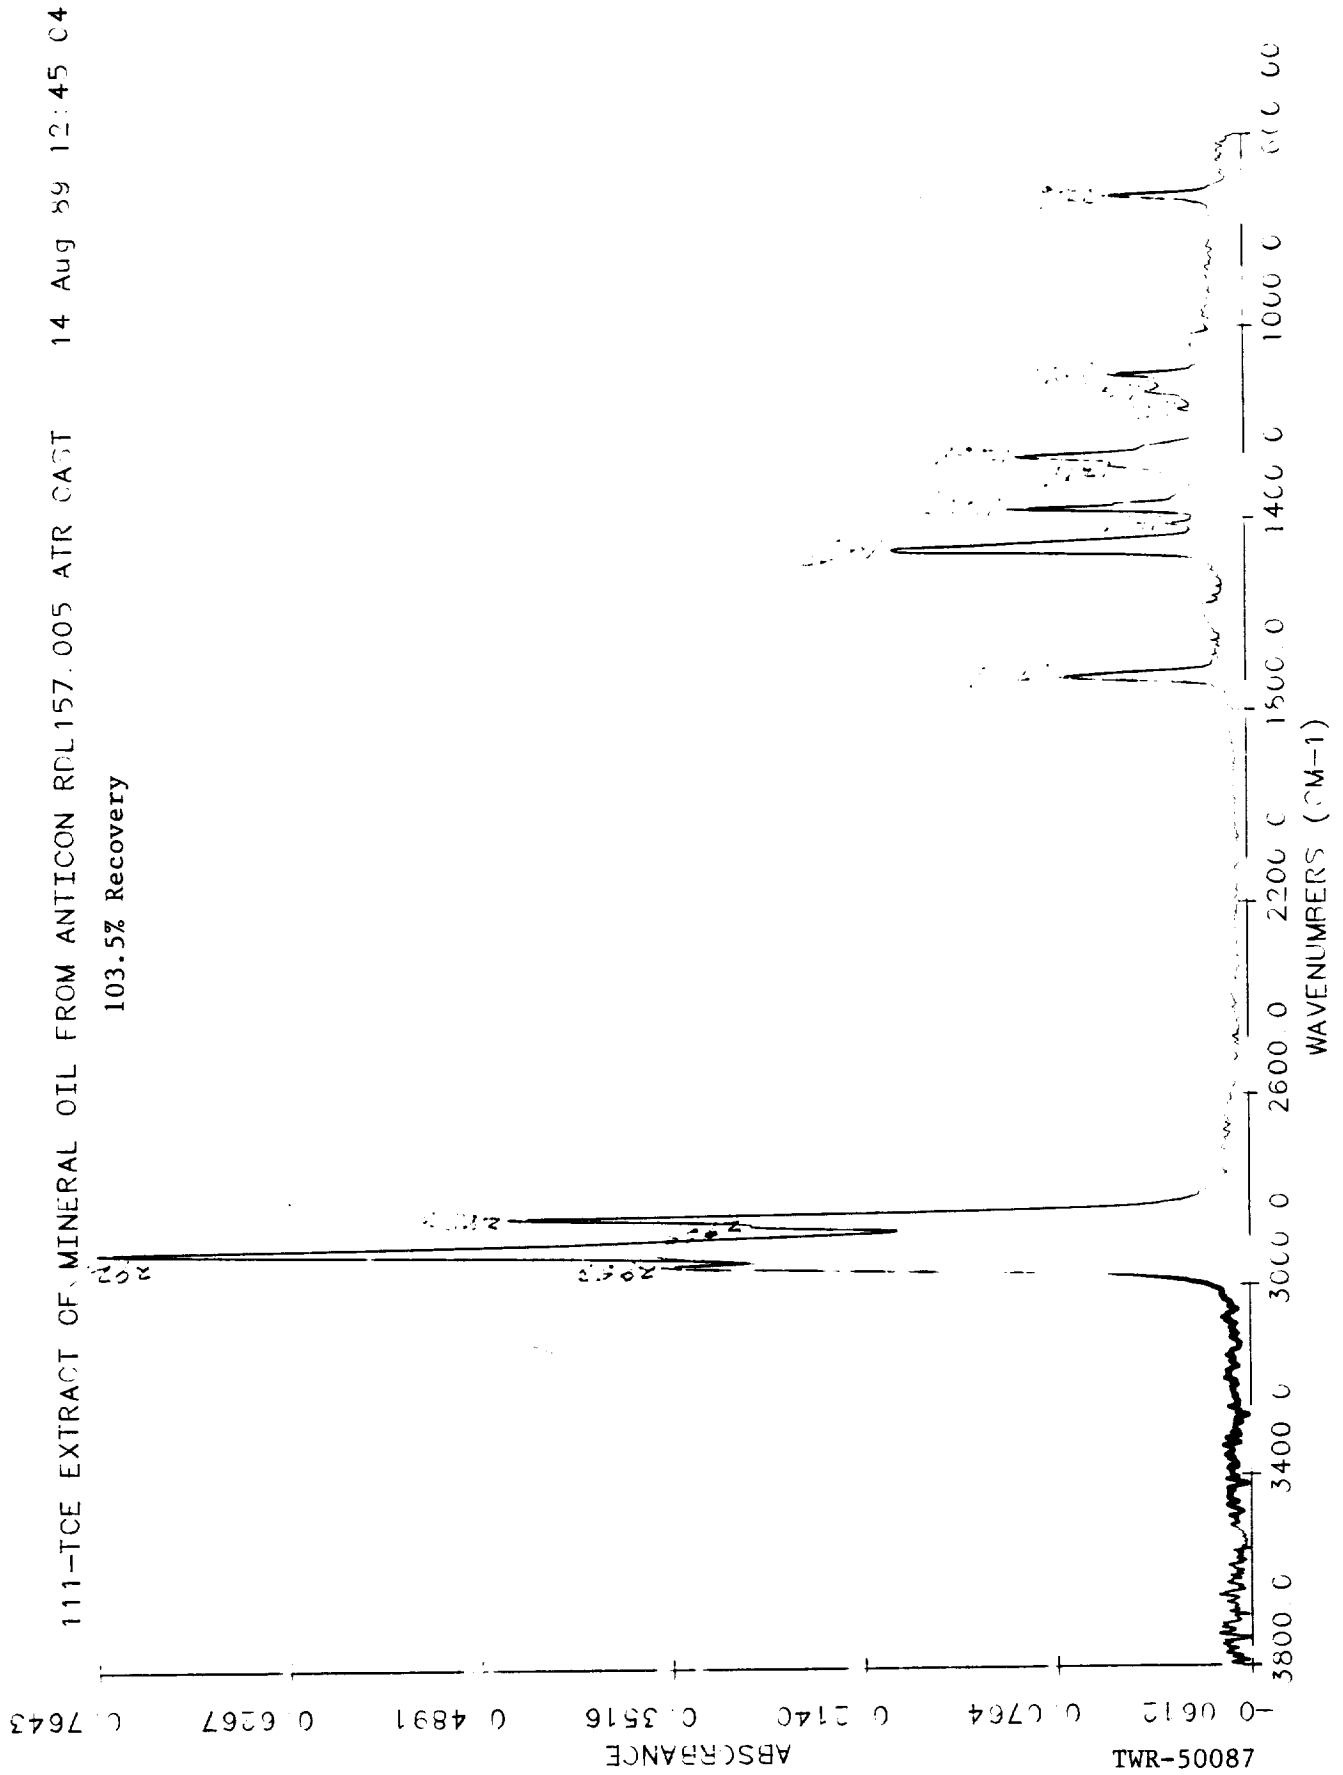


Figure 140.

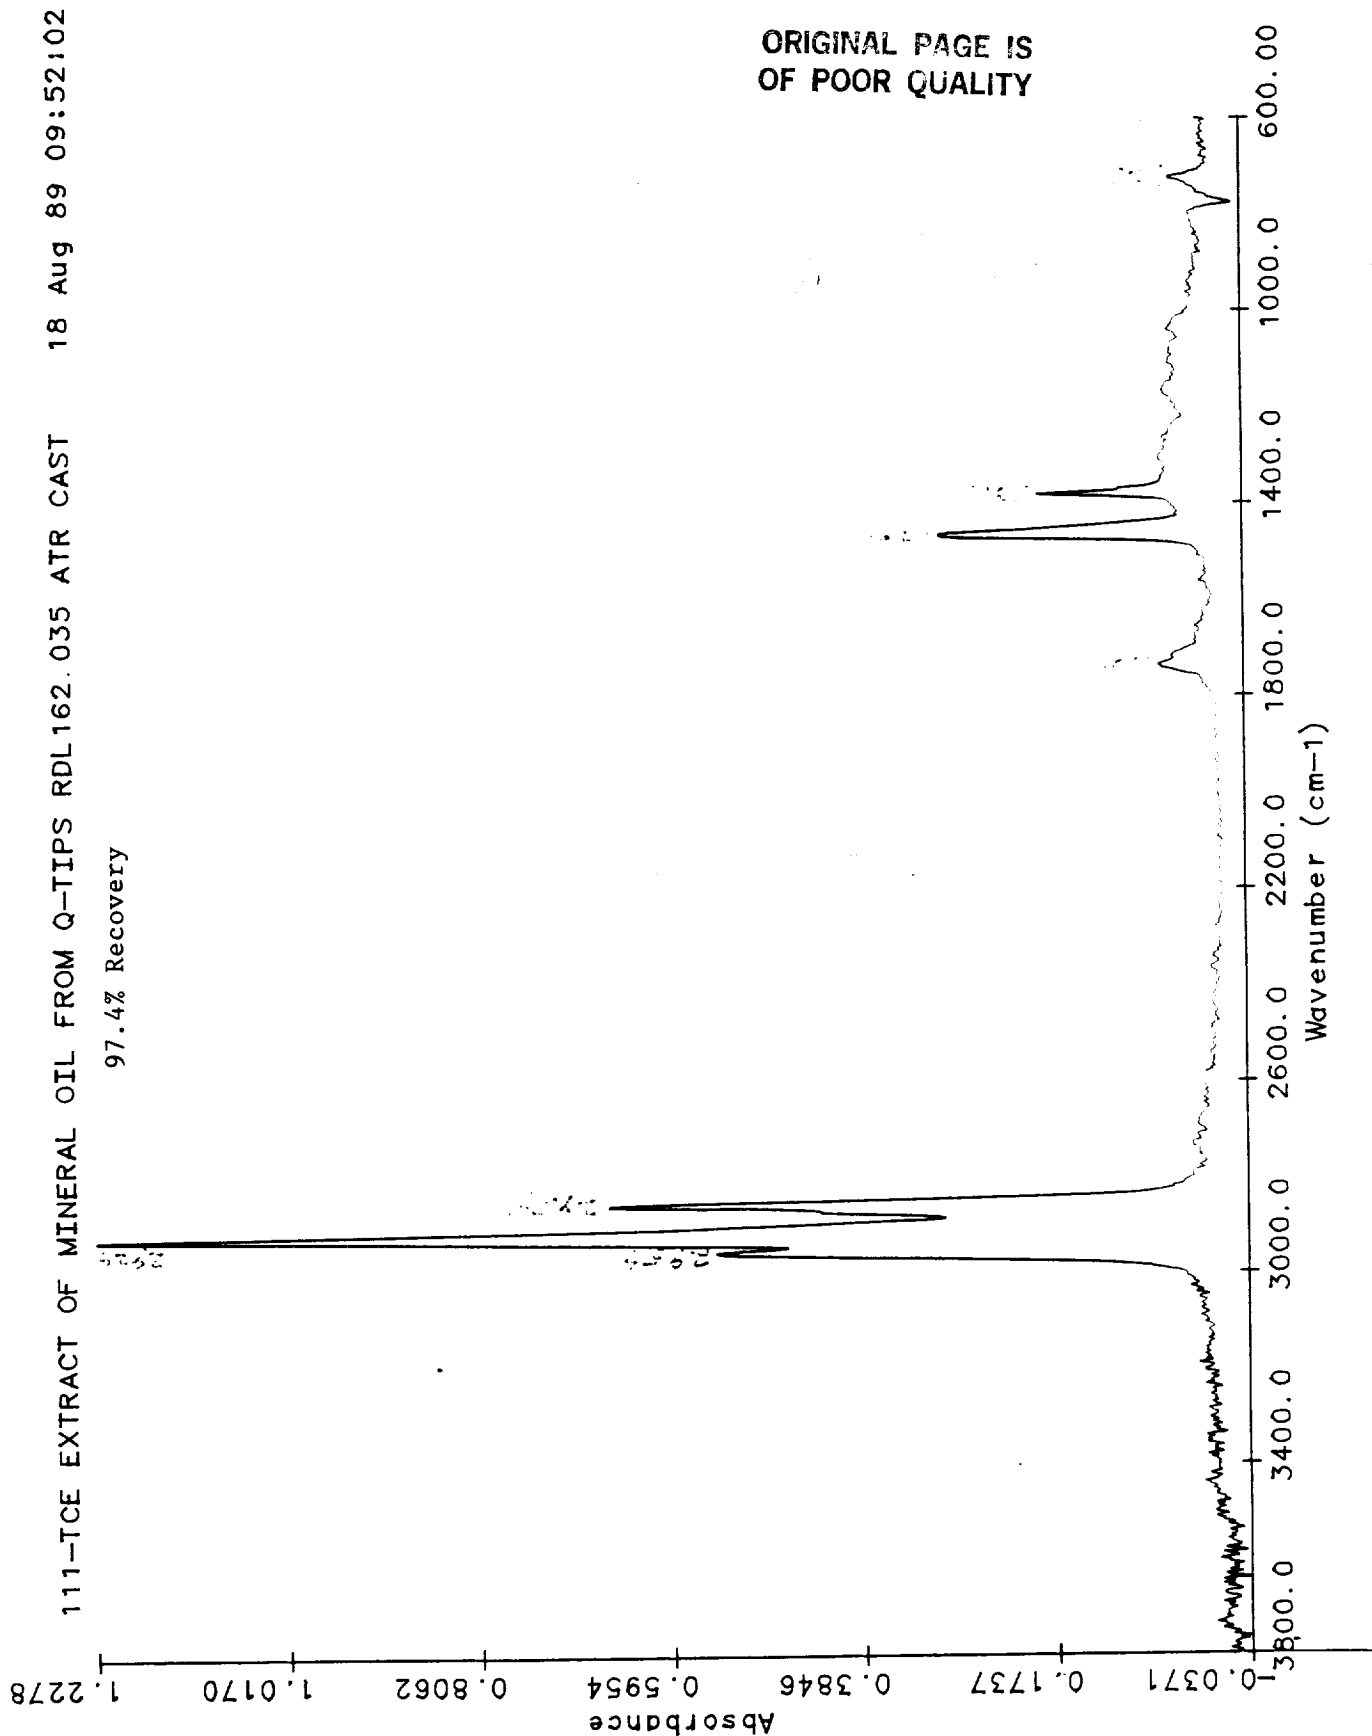

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 141.


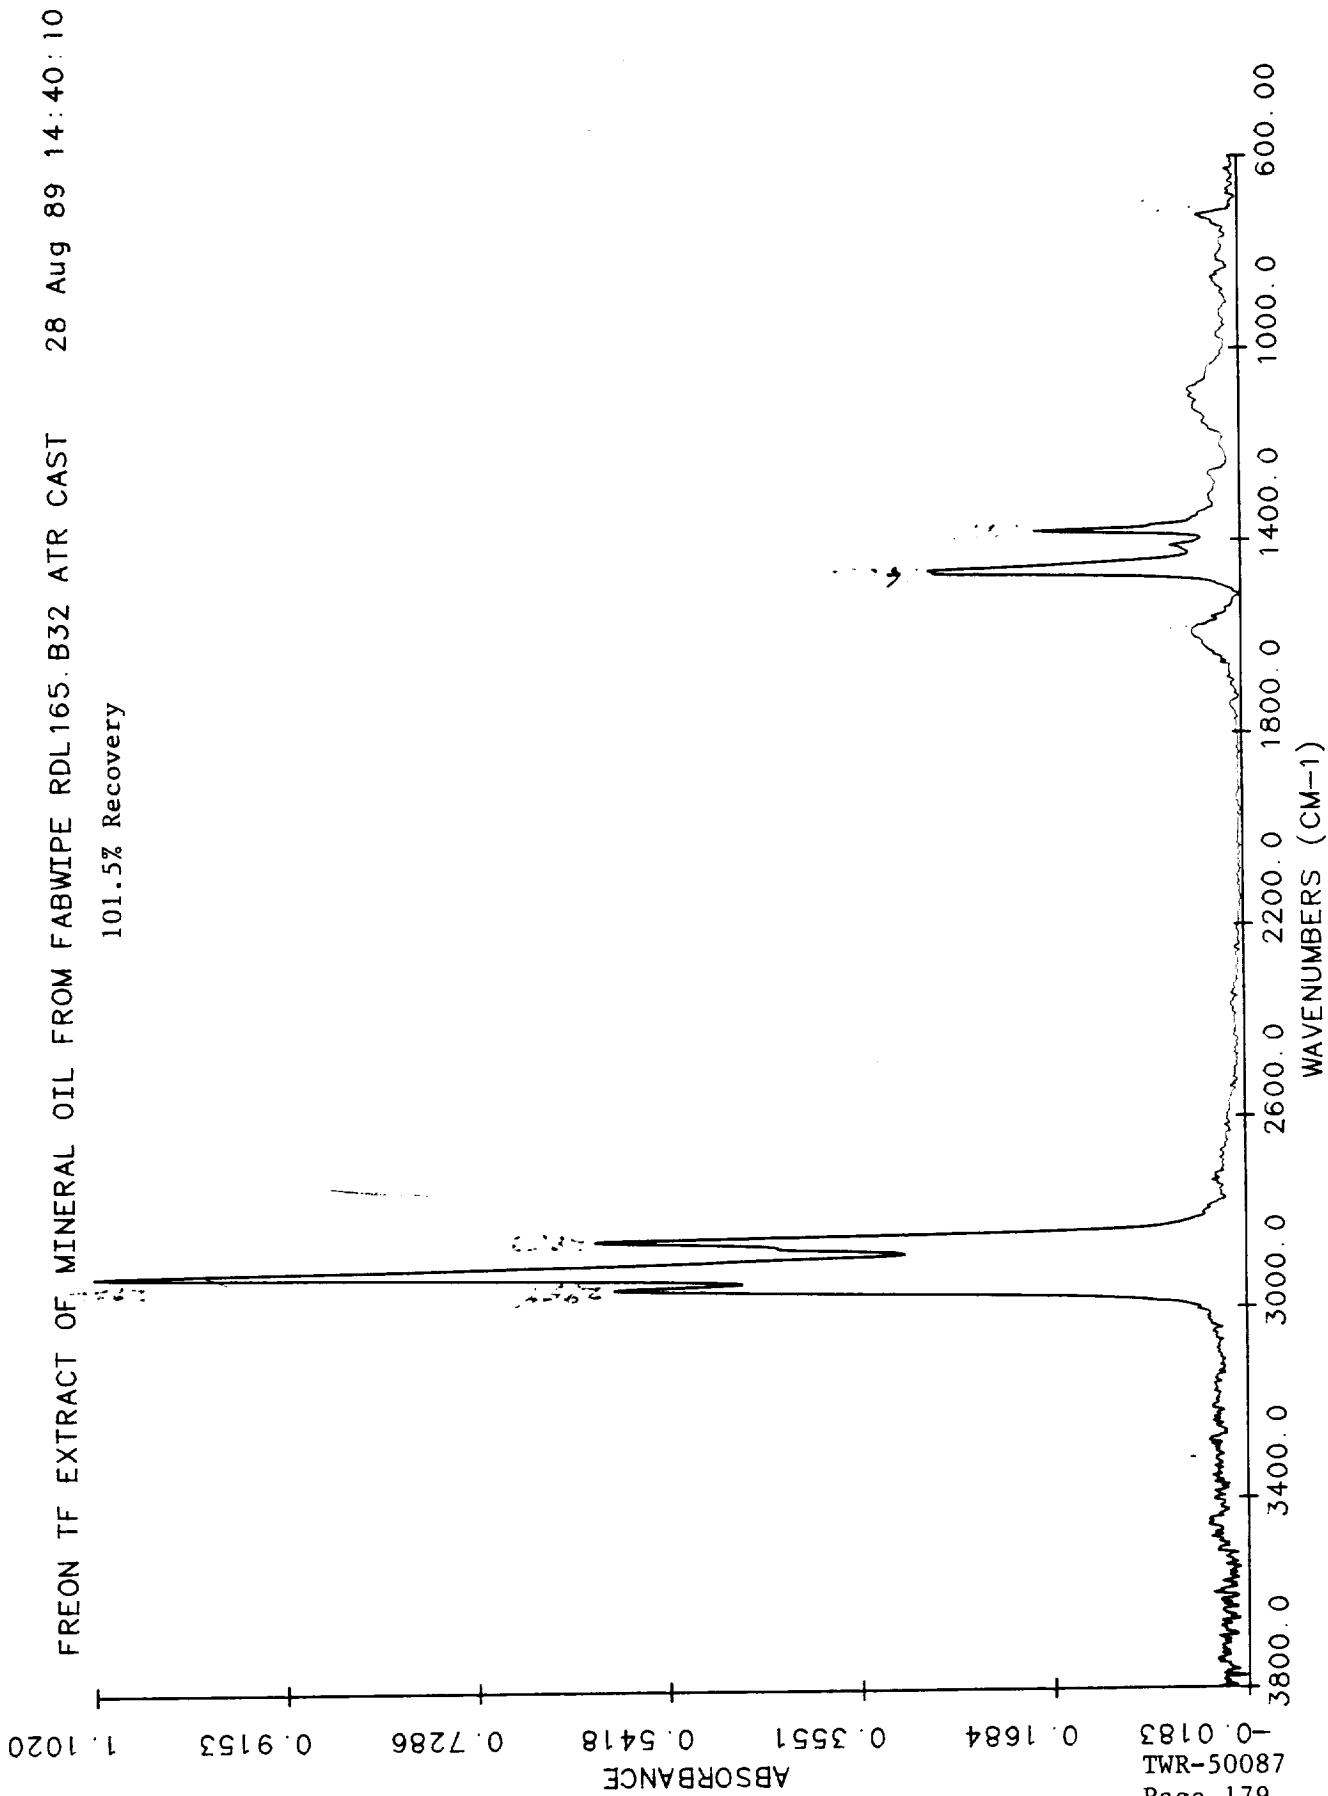


Figure 142.
FREON TF EXTRACT OF MINERAL OIL FROM MIRACLEWIPE RDL164.B24 ATR CAST 28 Aug 89 13:11:58
89.6% Recovery

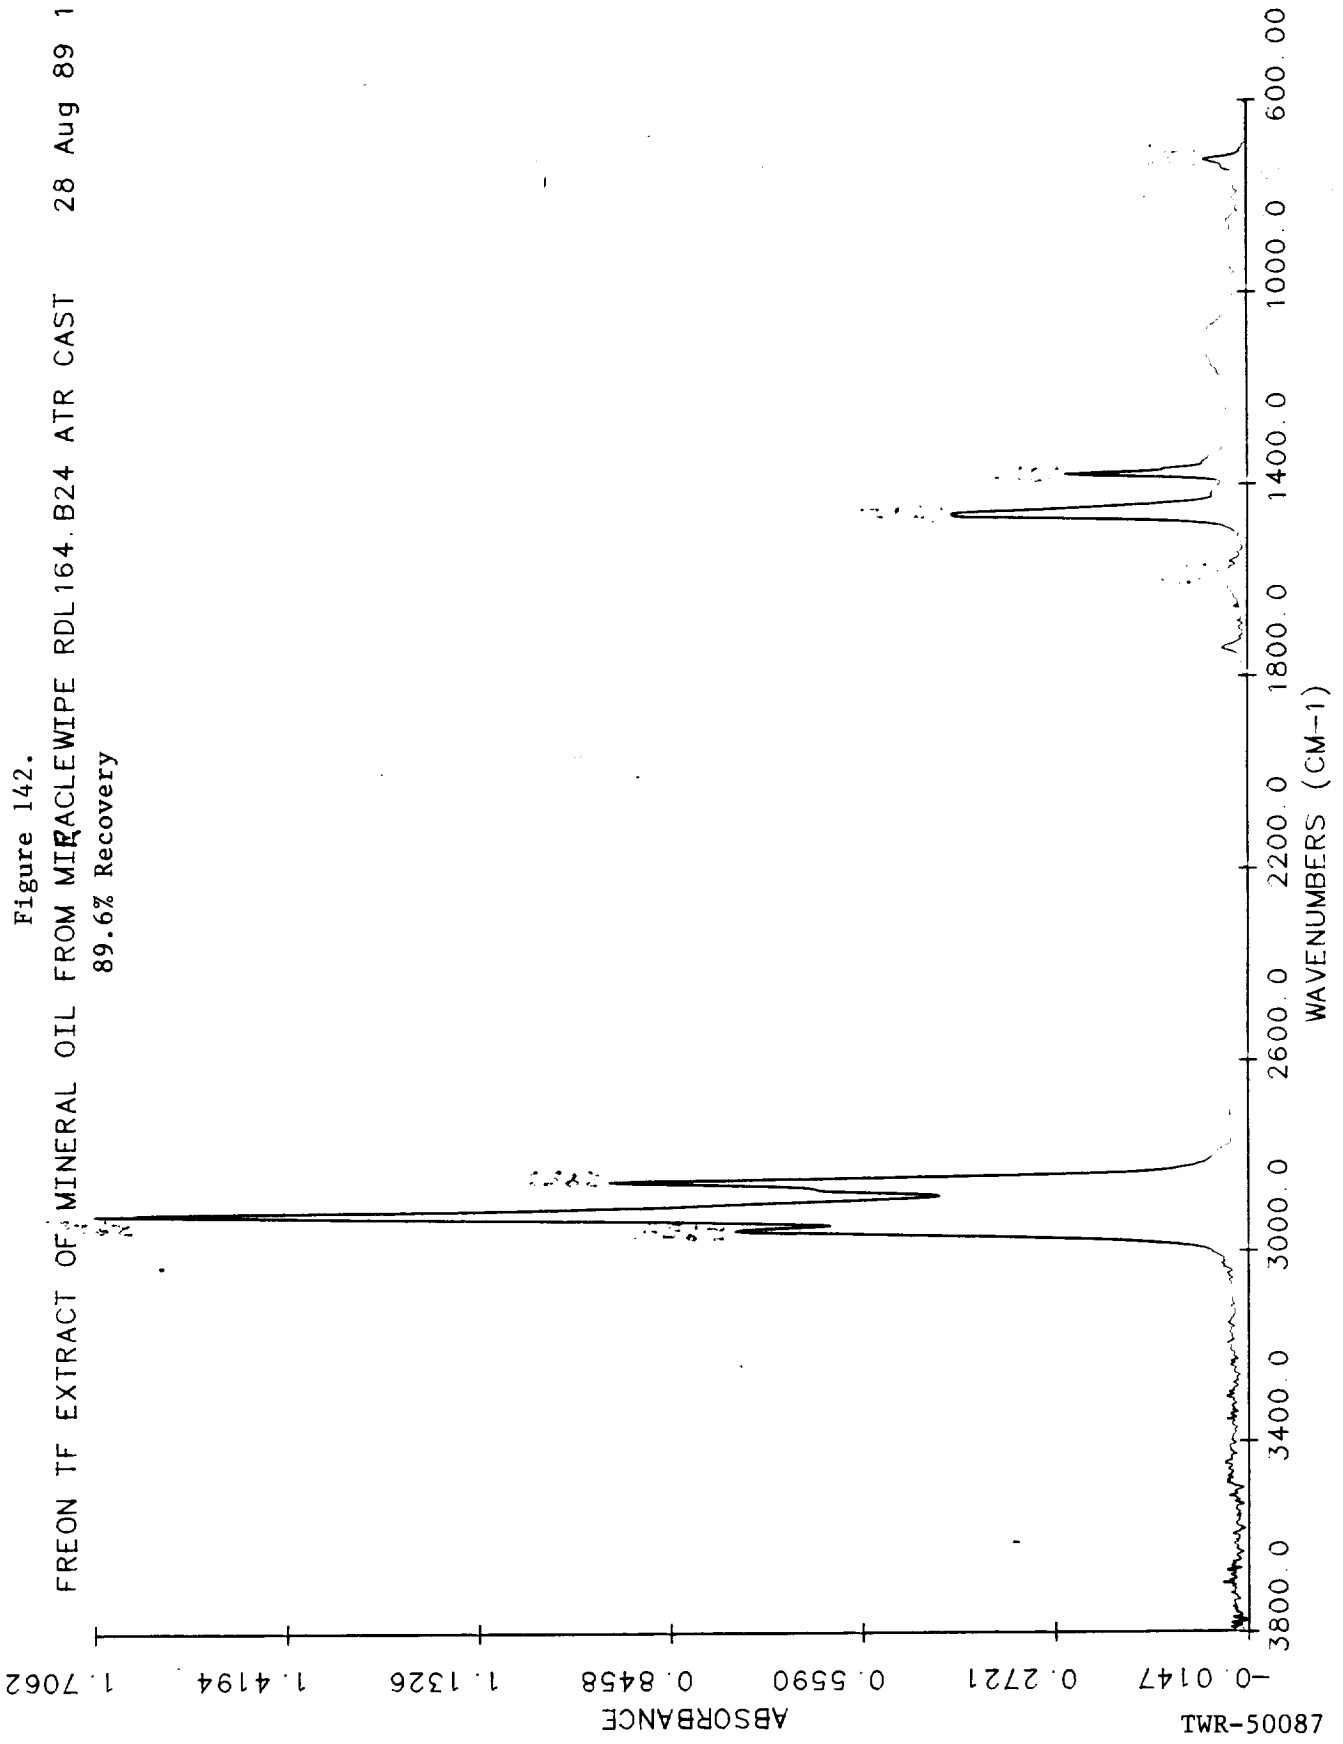

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 143.

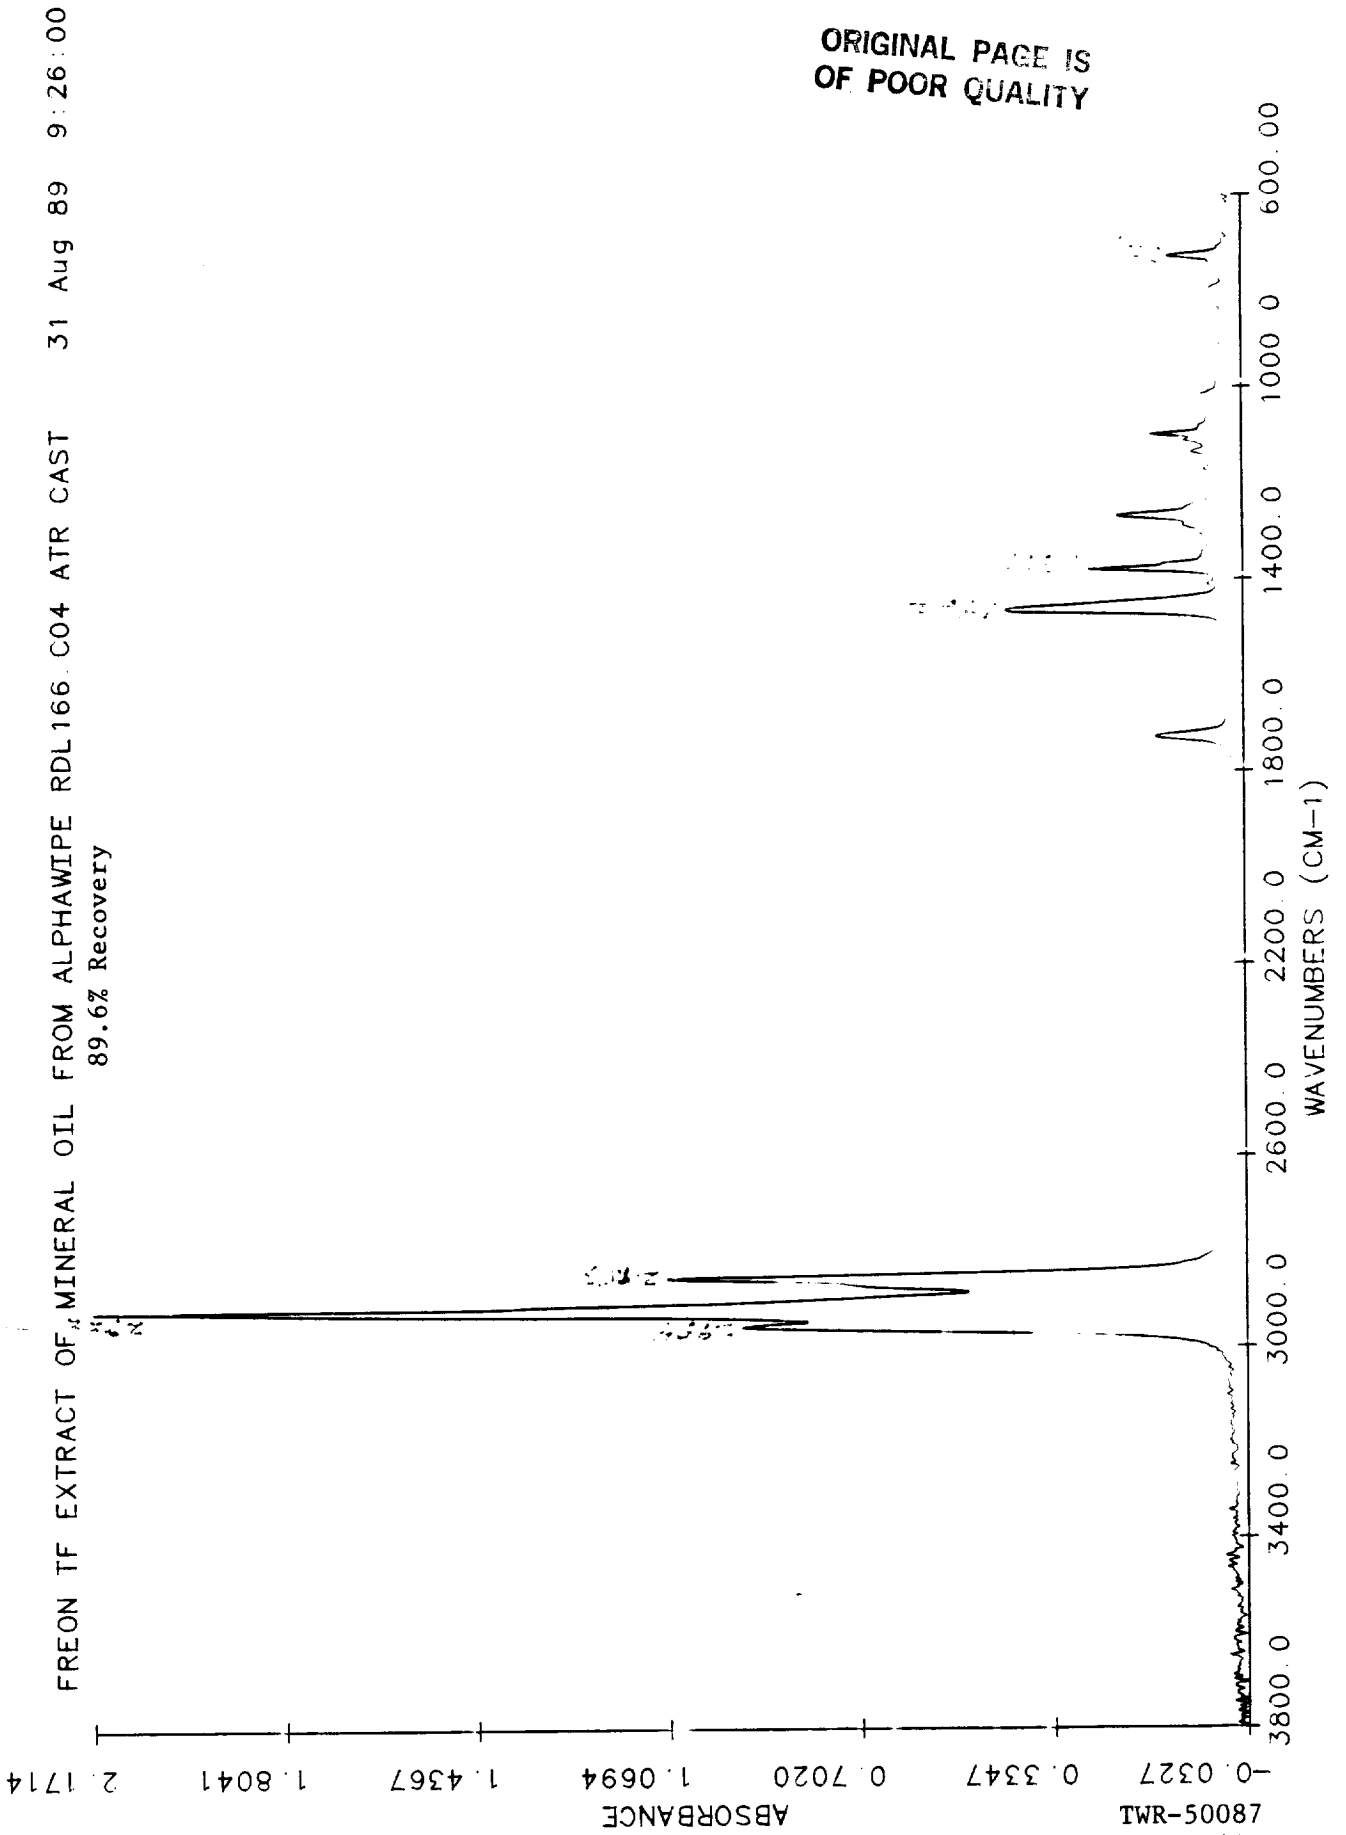


Figure 144.


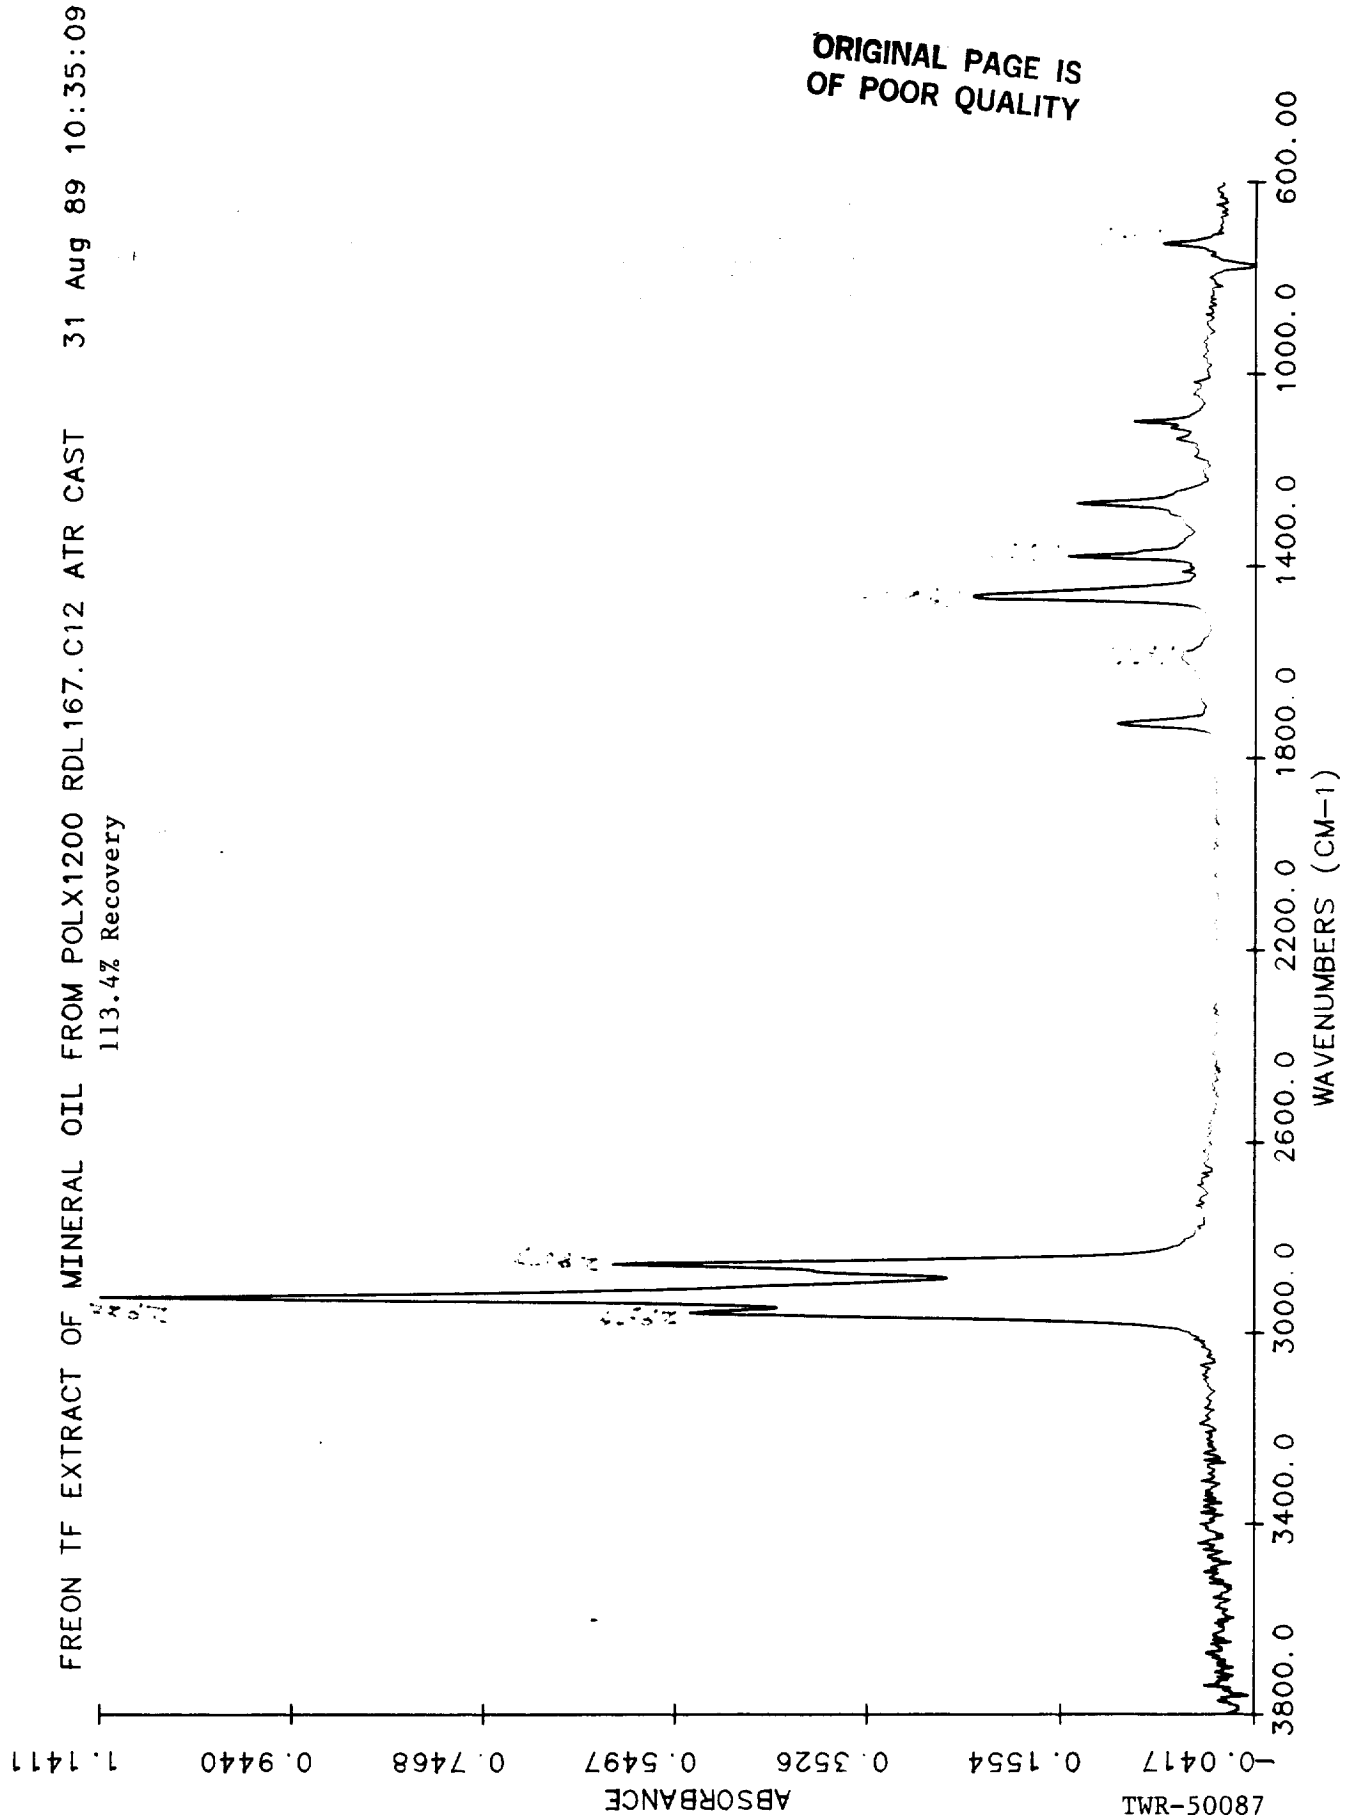


Figure 145.


FREON TF EXTRACT OF MINERAL OIL FROM ANTICON RDL163.B17 ATR CAST 23 Aug 89 9:55:10

84.6% Recovery

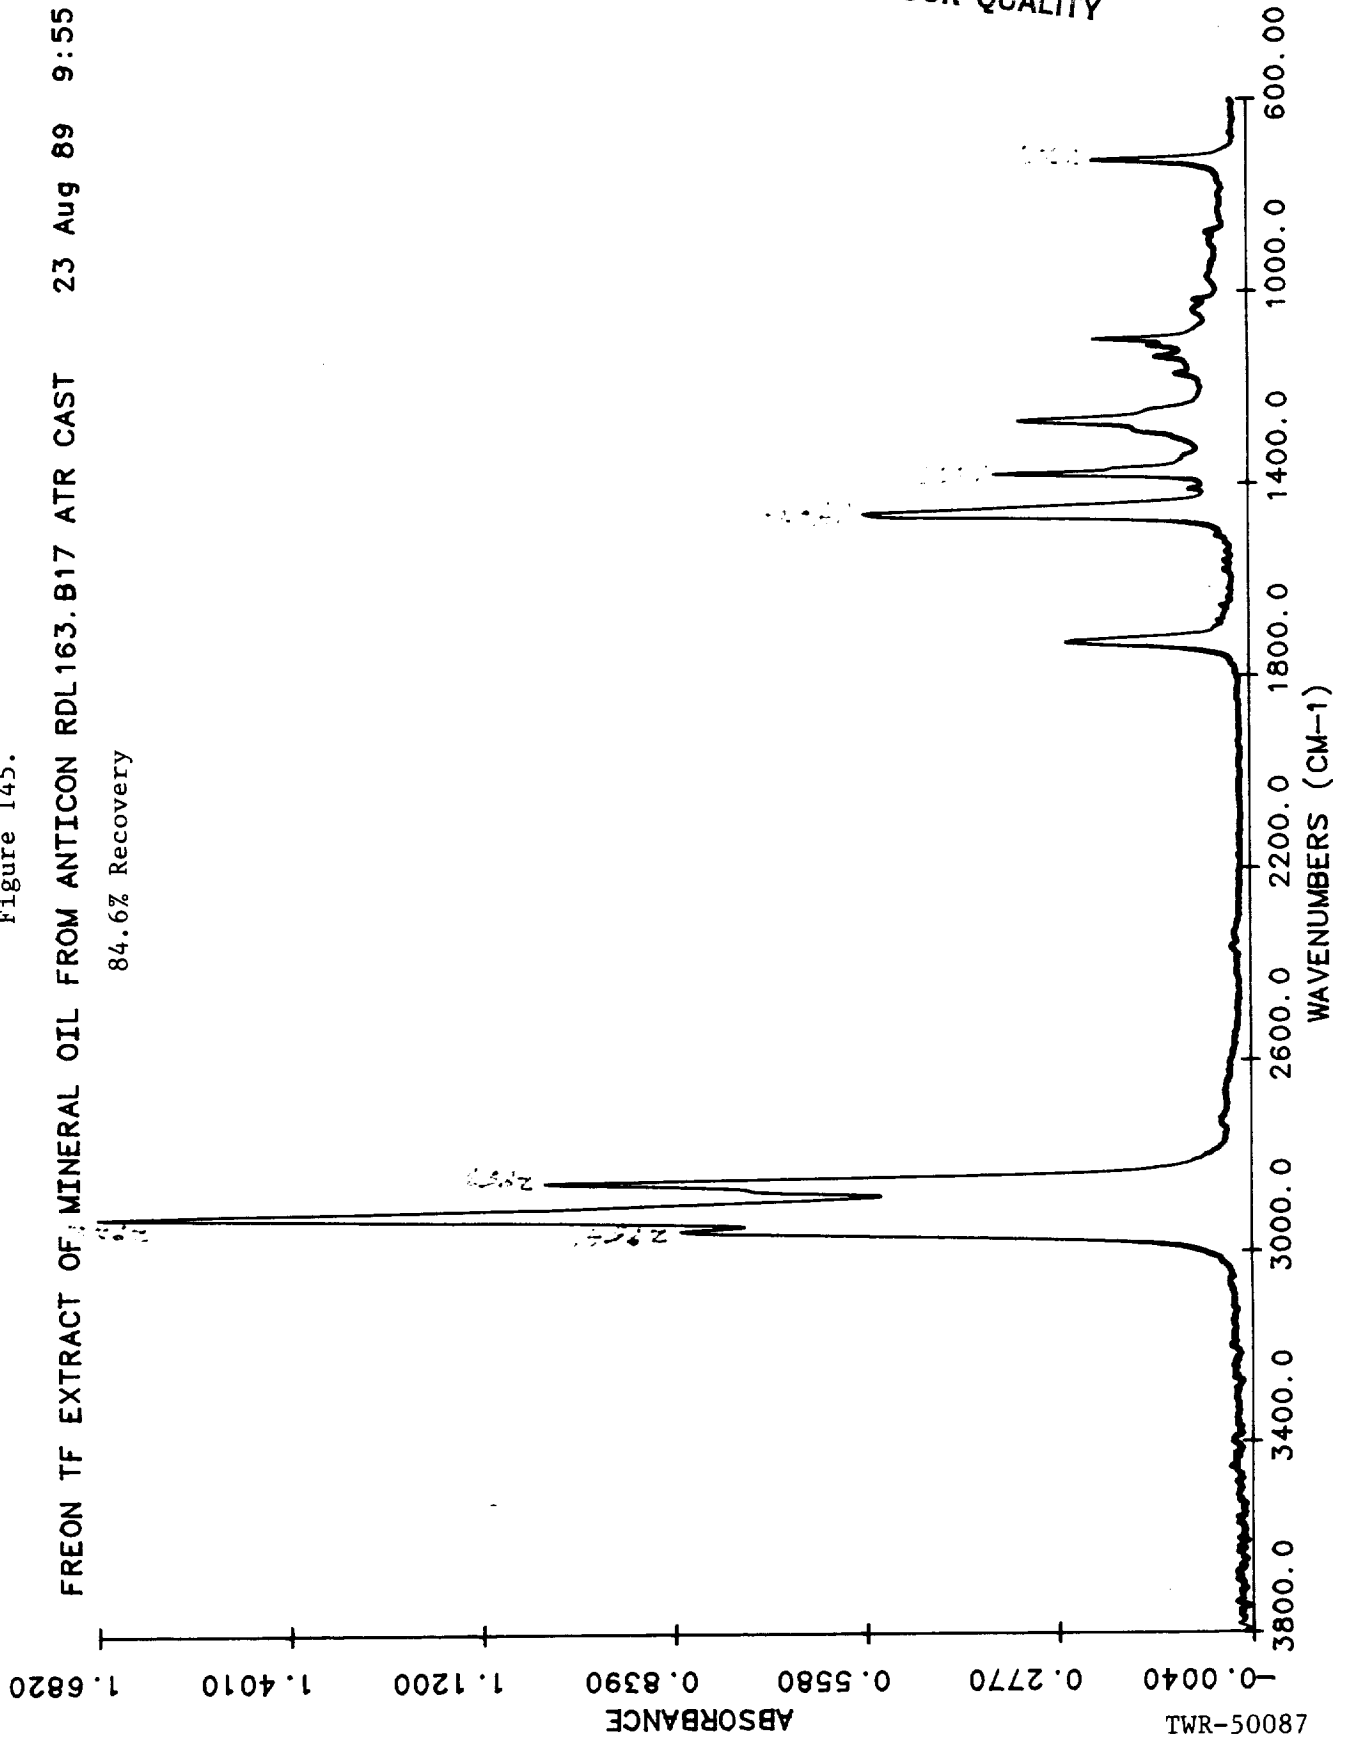

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 146.

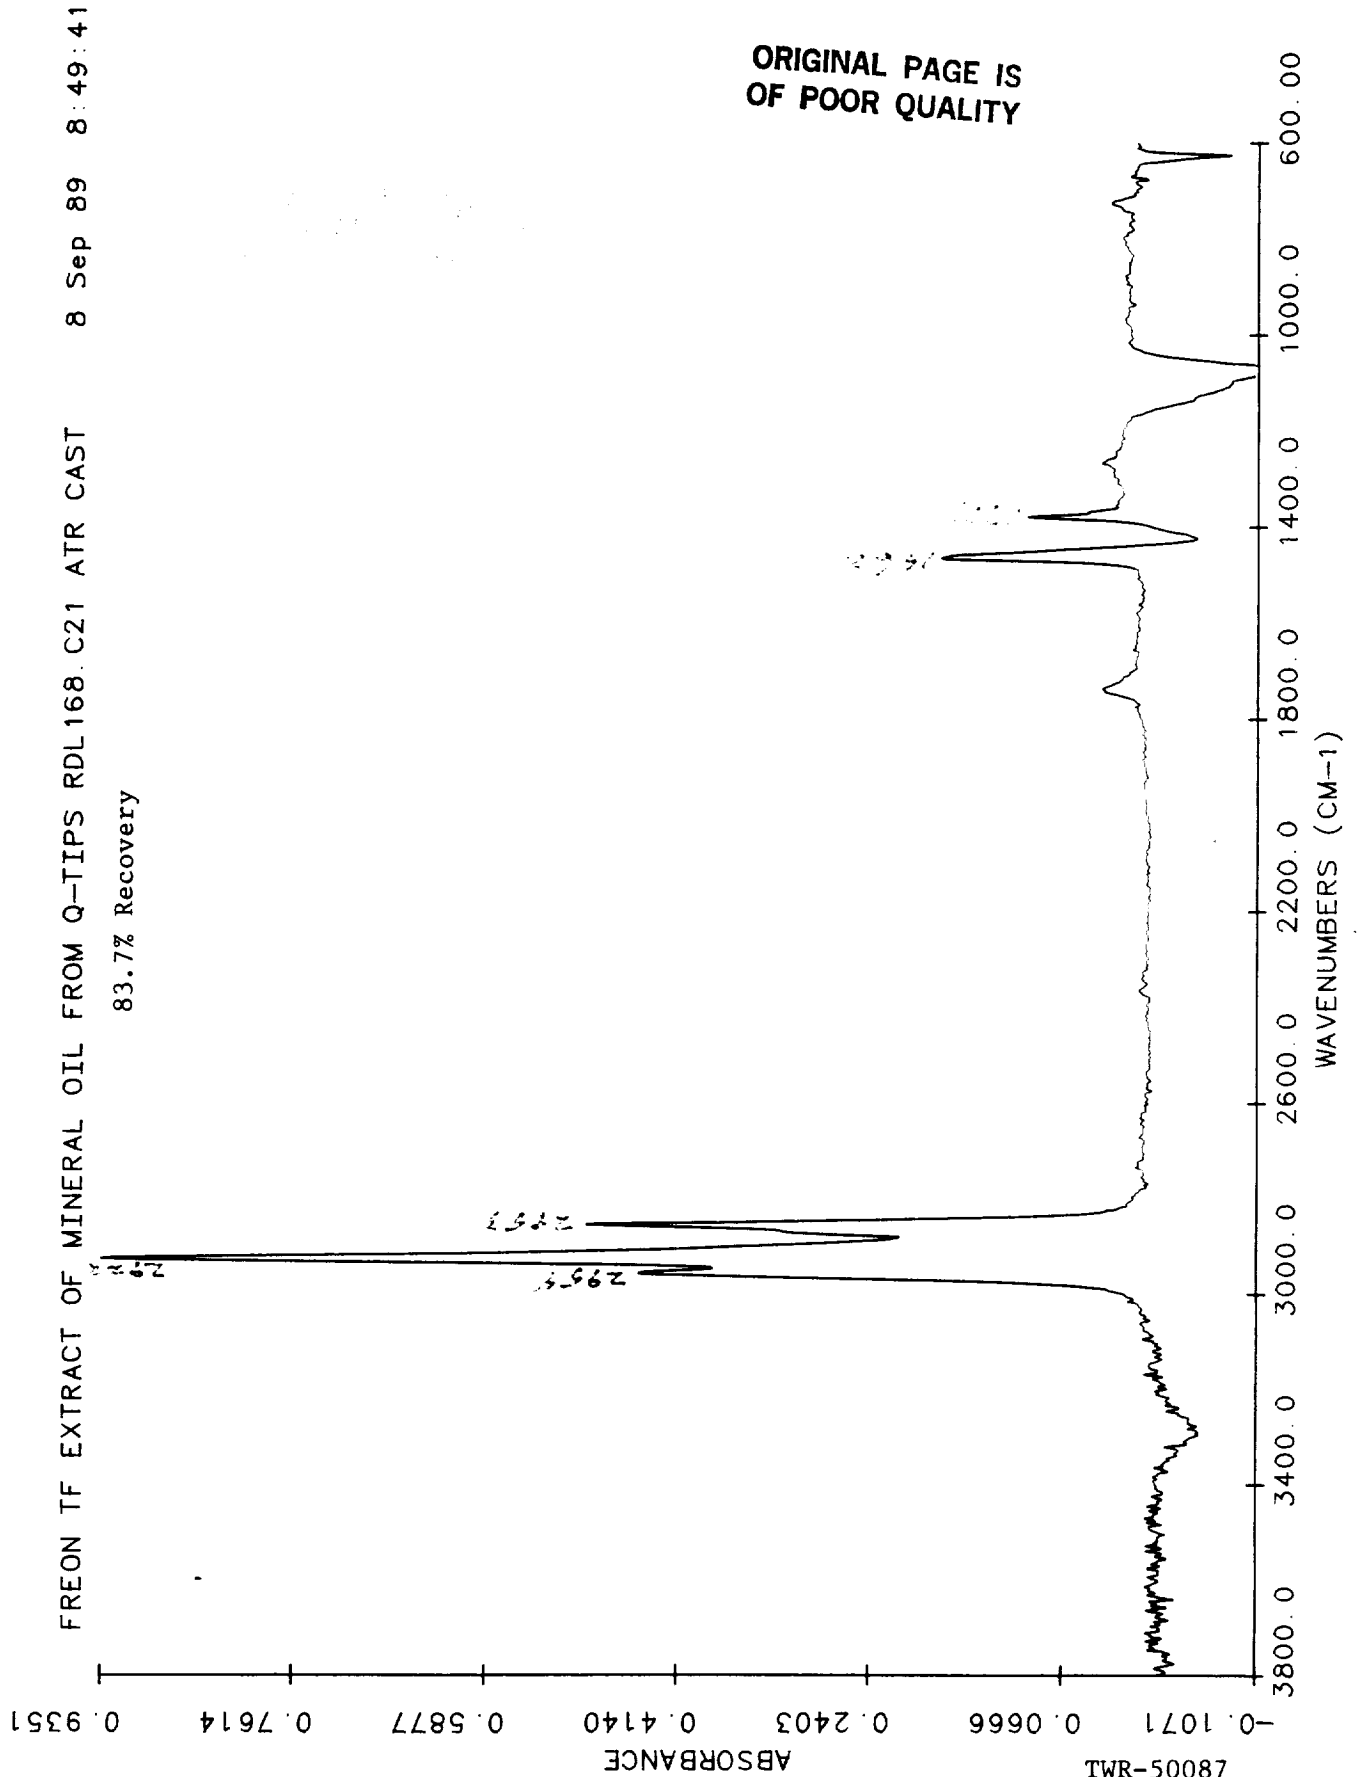

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 147.



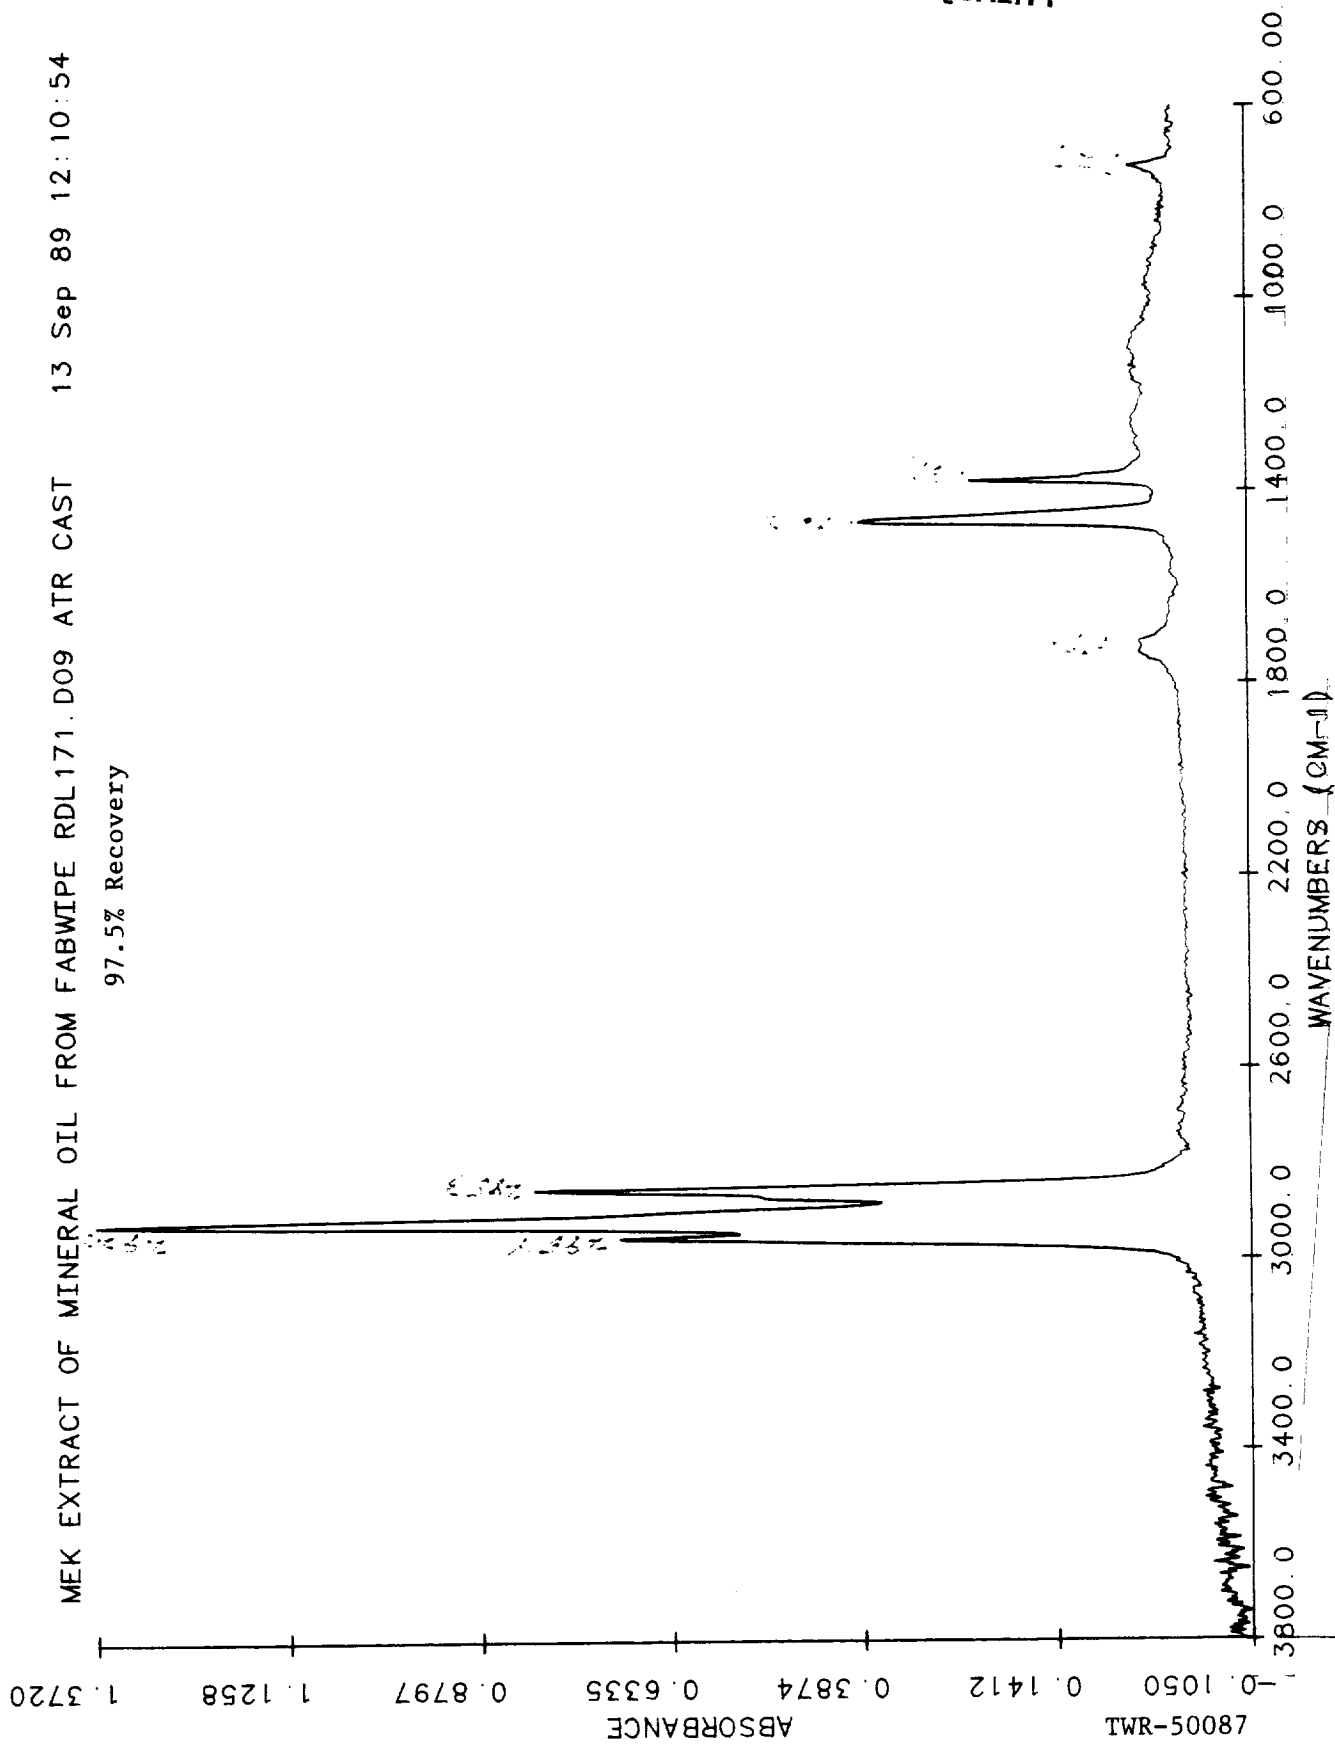


Figure 148.

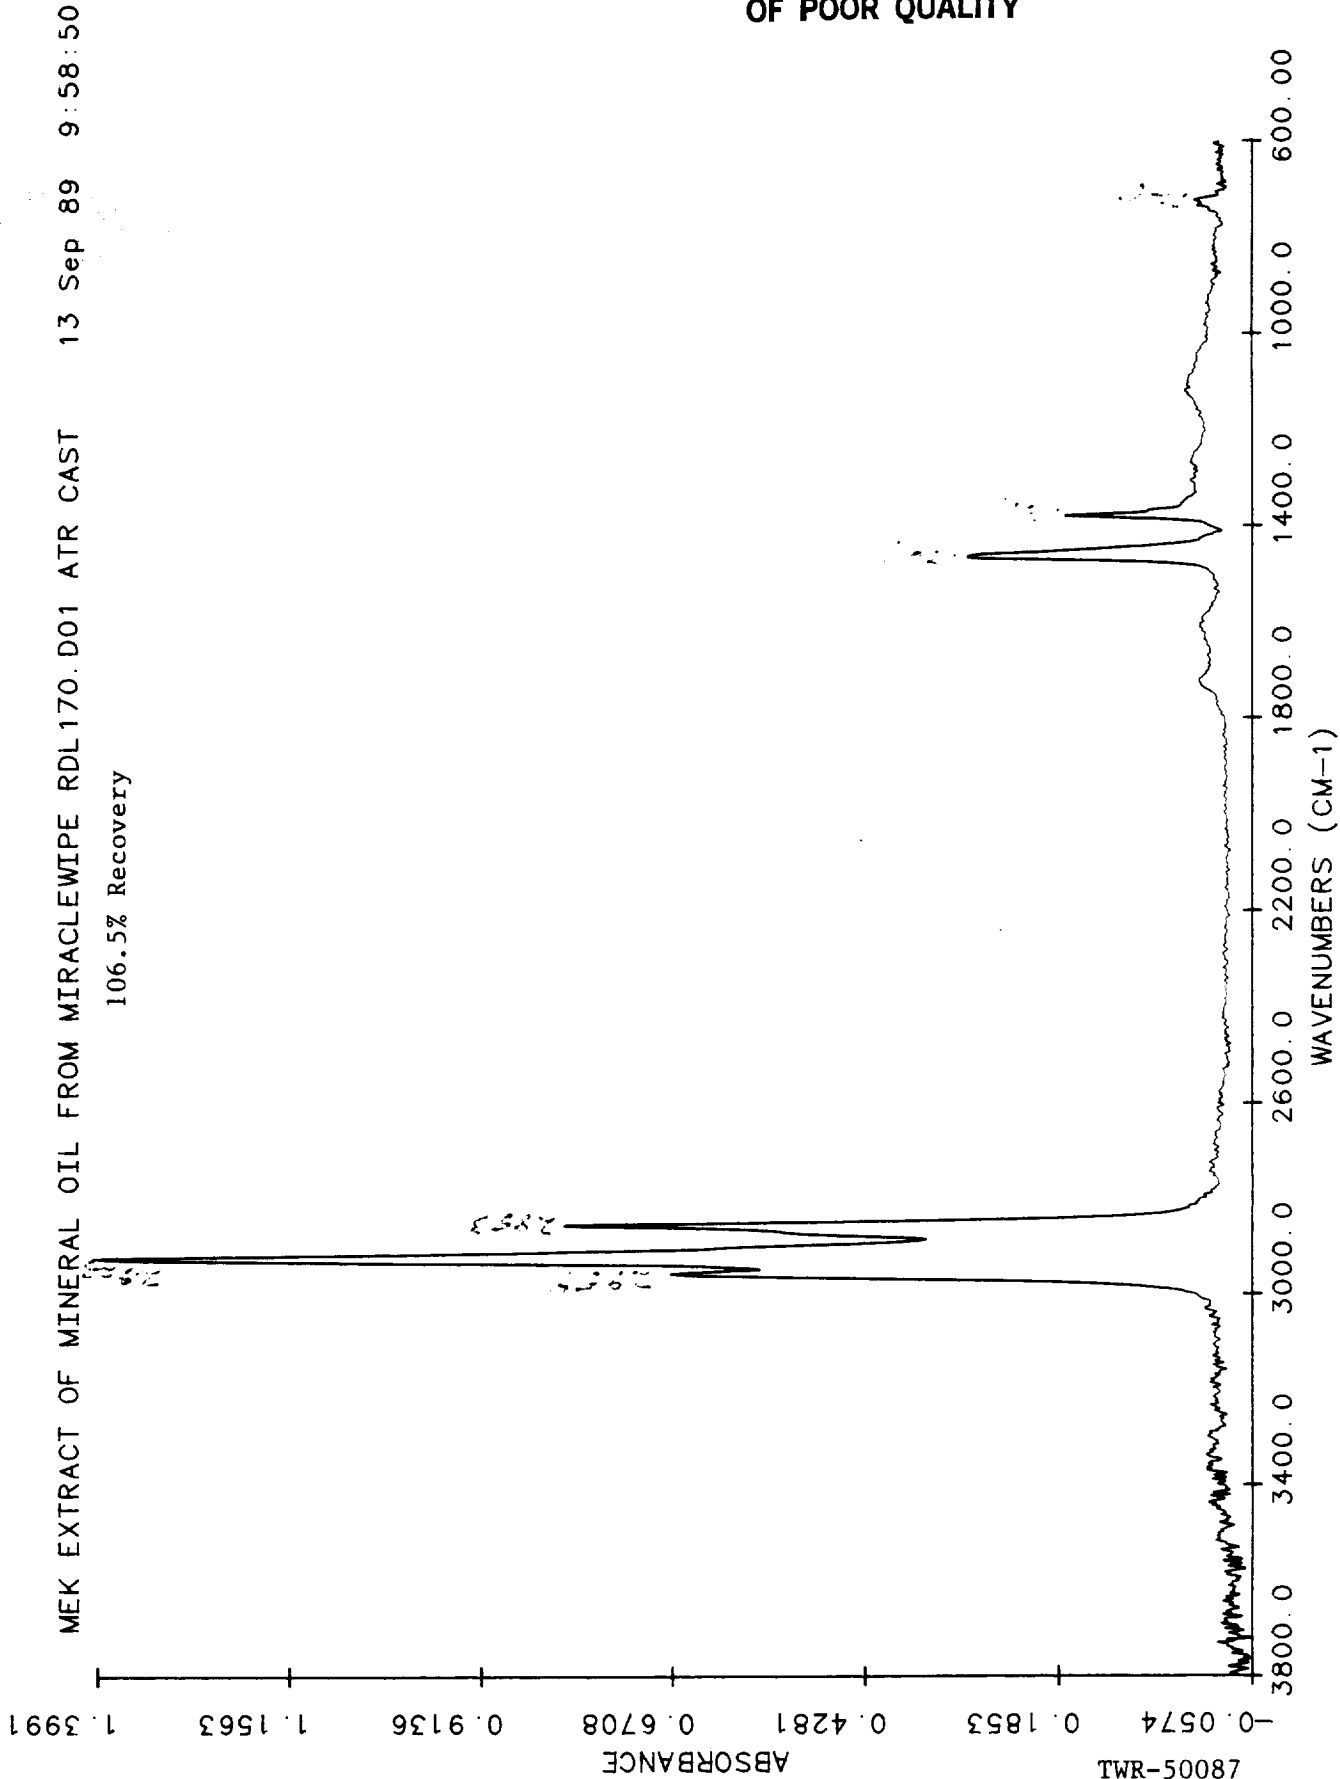

ORIGINAL PAGE IS
OF POOR QUALITY

MEK EXTRACT OF MINERAL OIL FROM ALPHAWIPE RDL172.D17 ATR CAST
68.7% Recovery

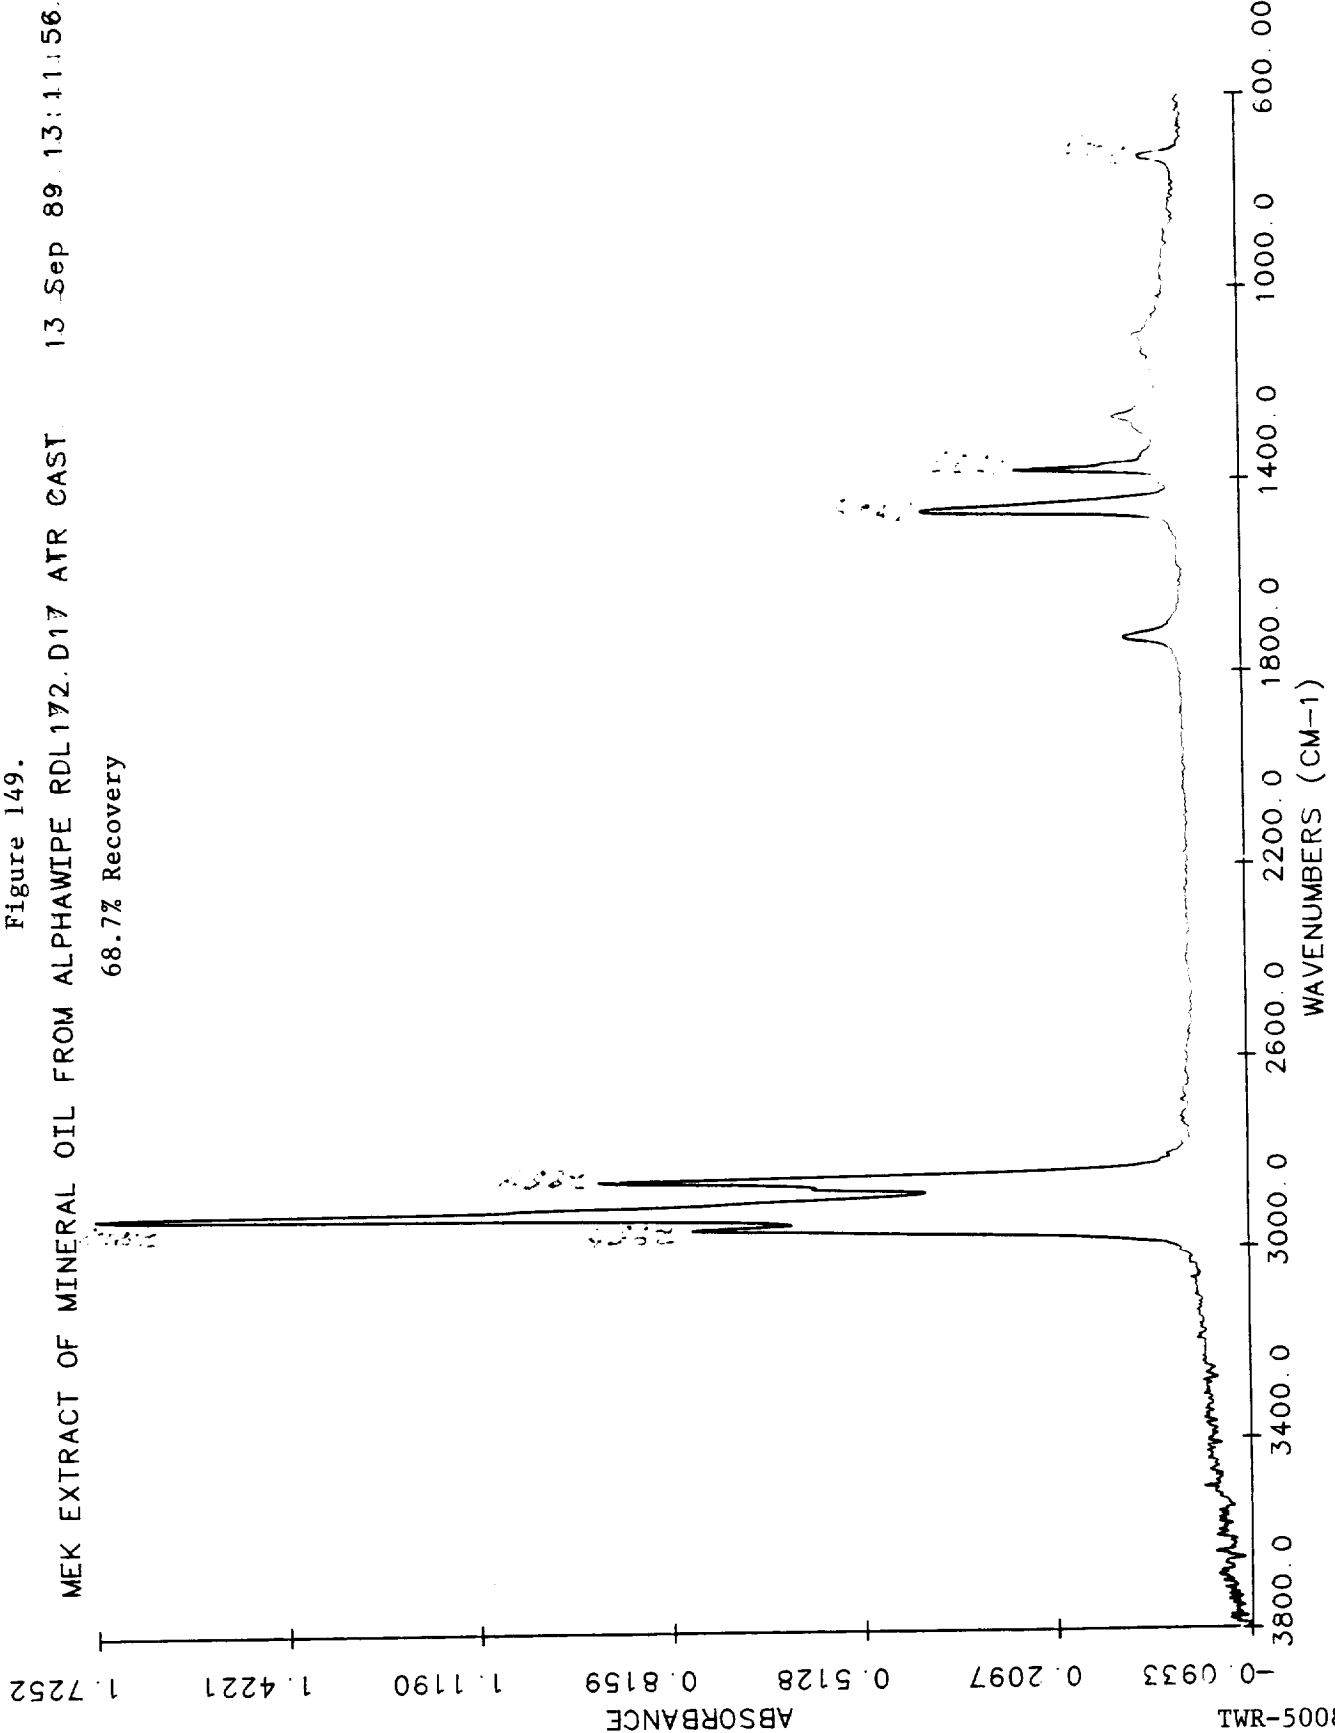

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 150.


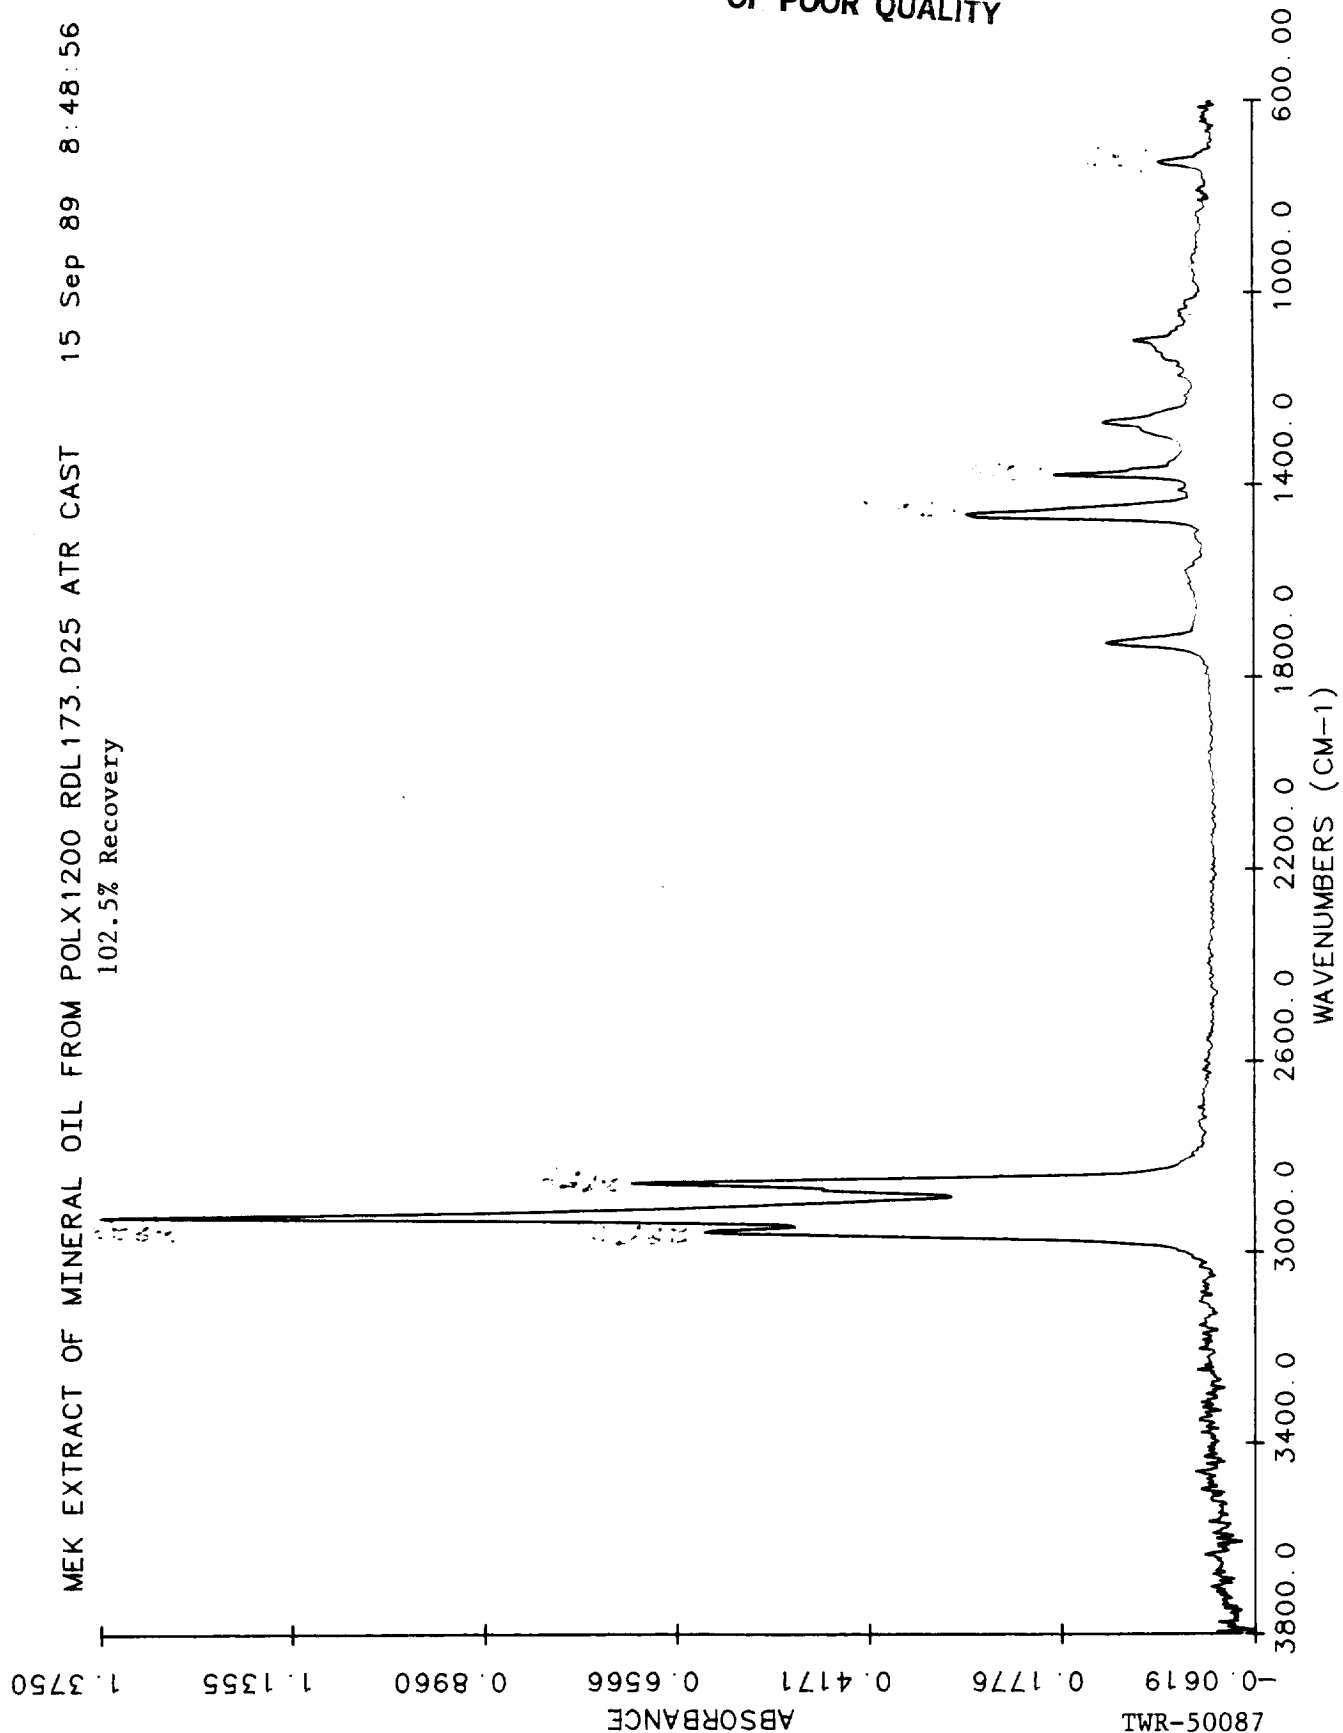


Figure 151.

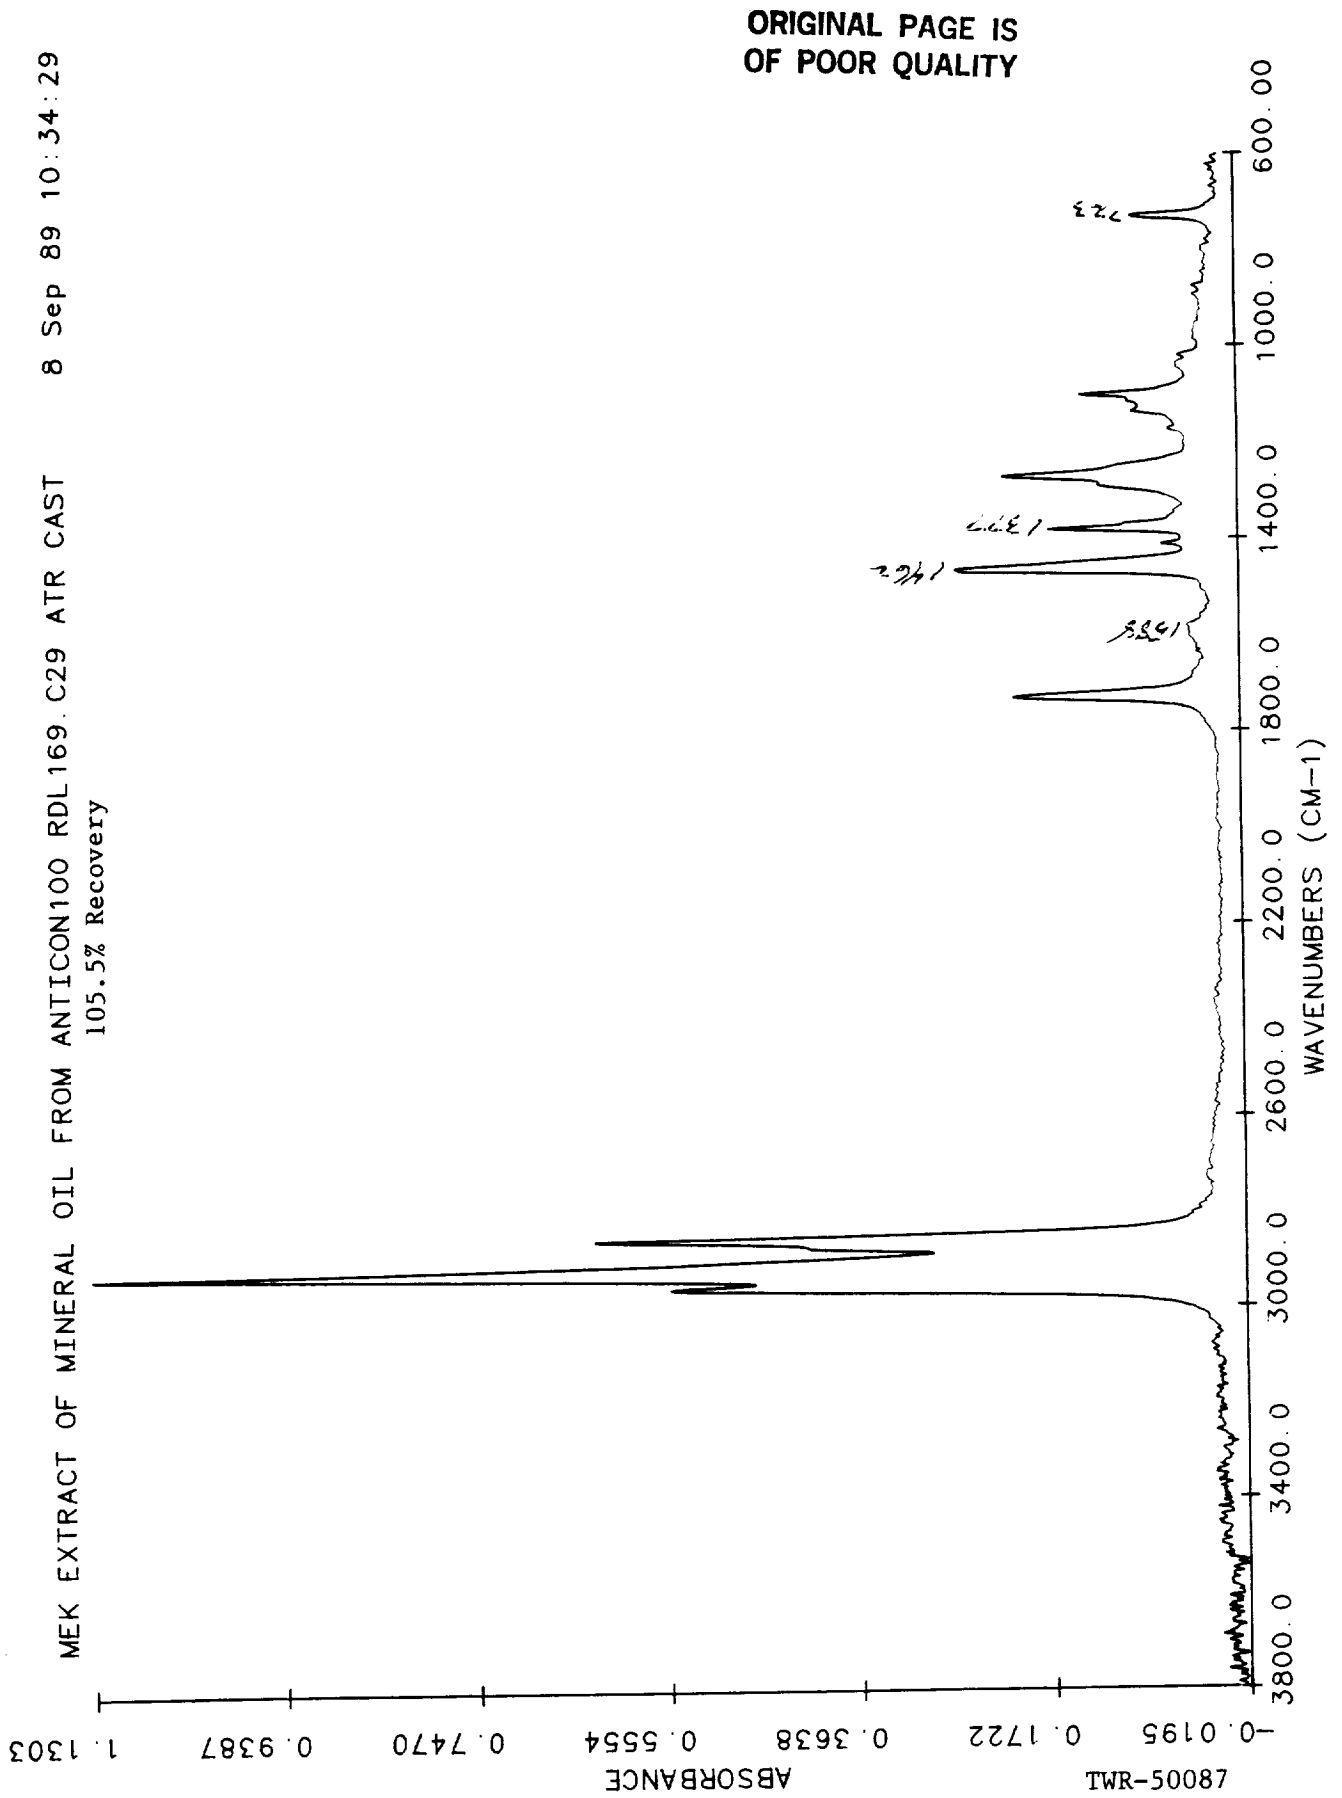

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 152.



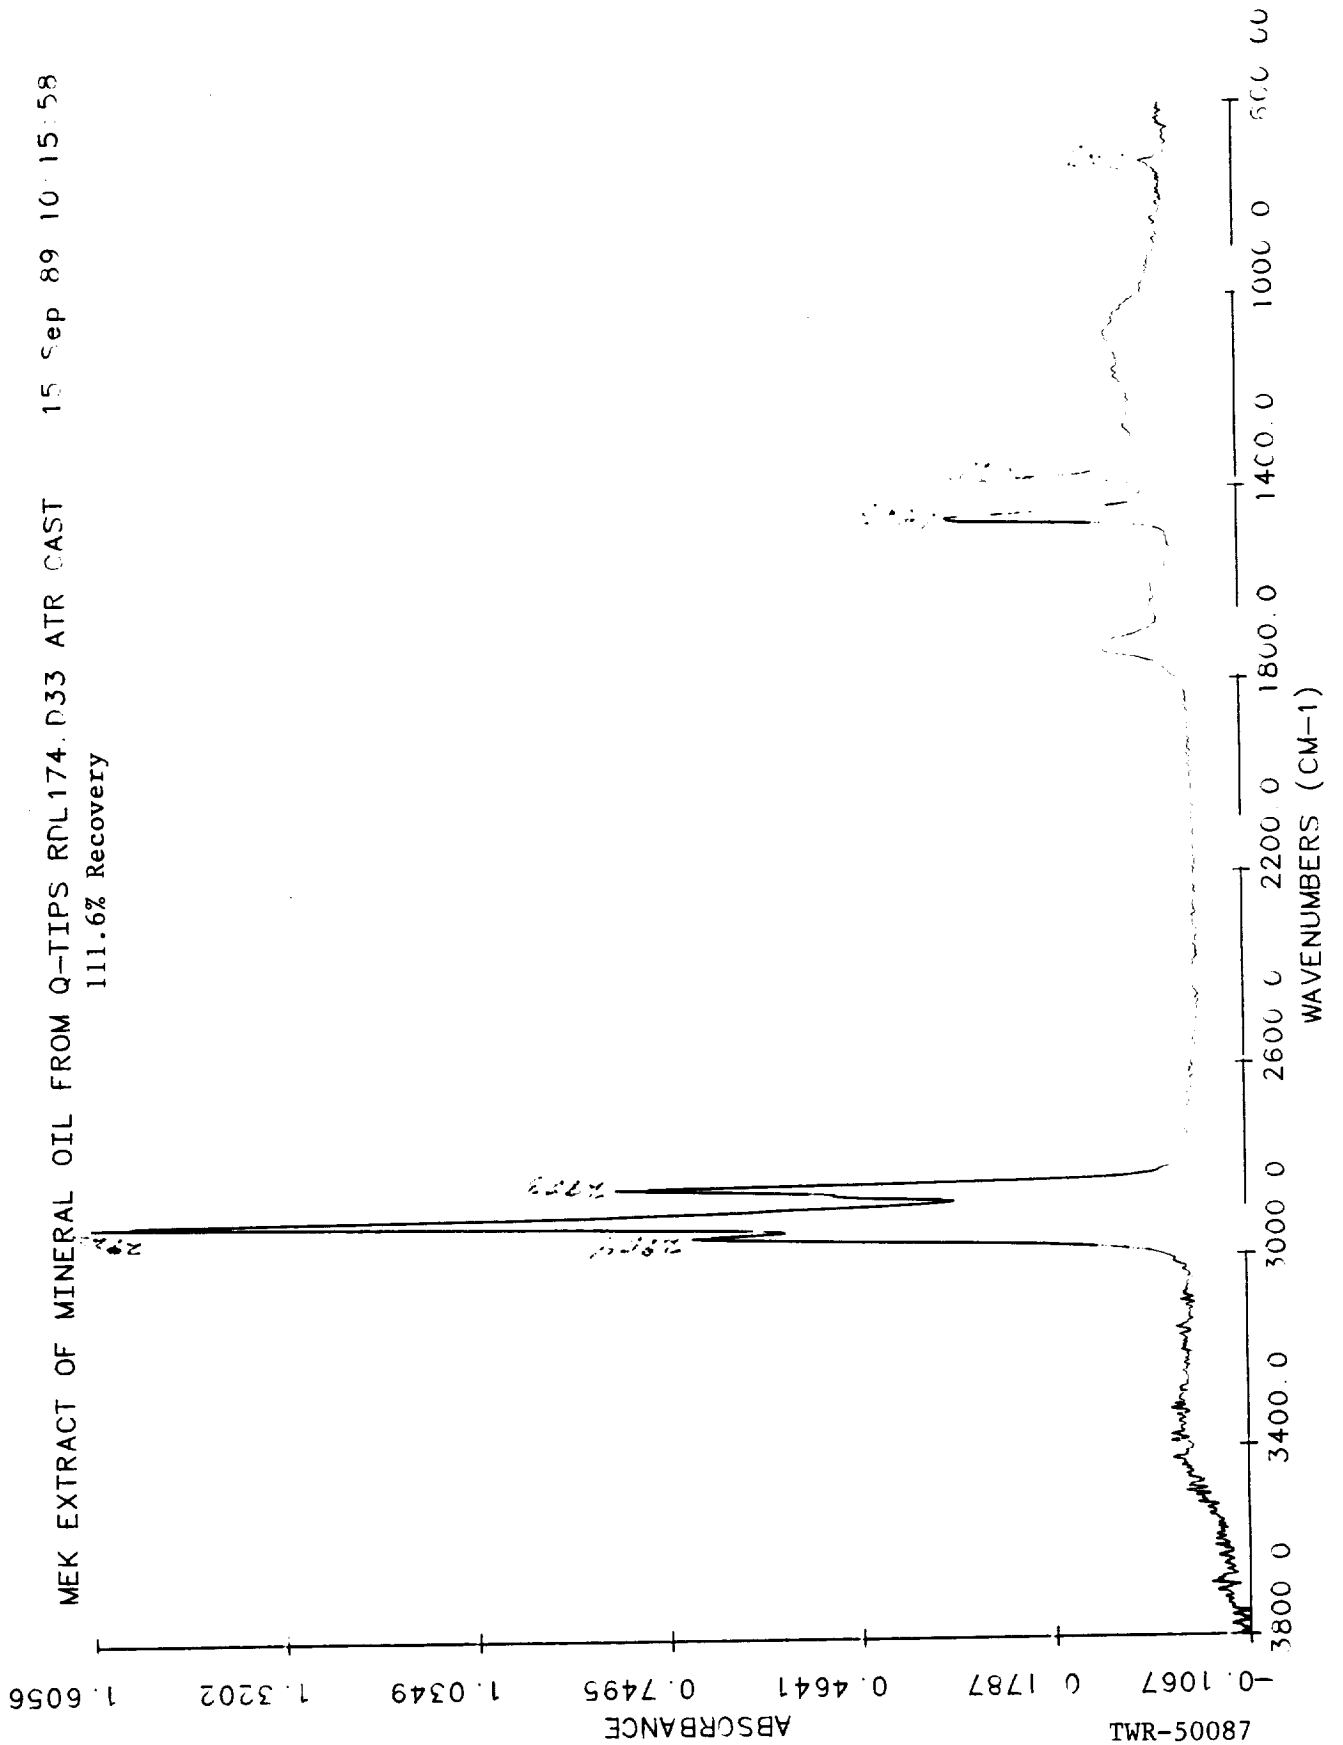


Figure 153.

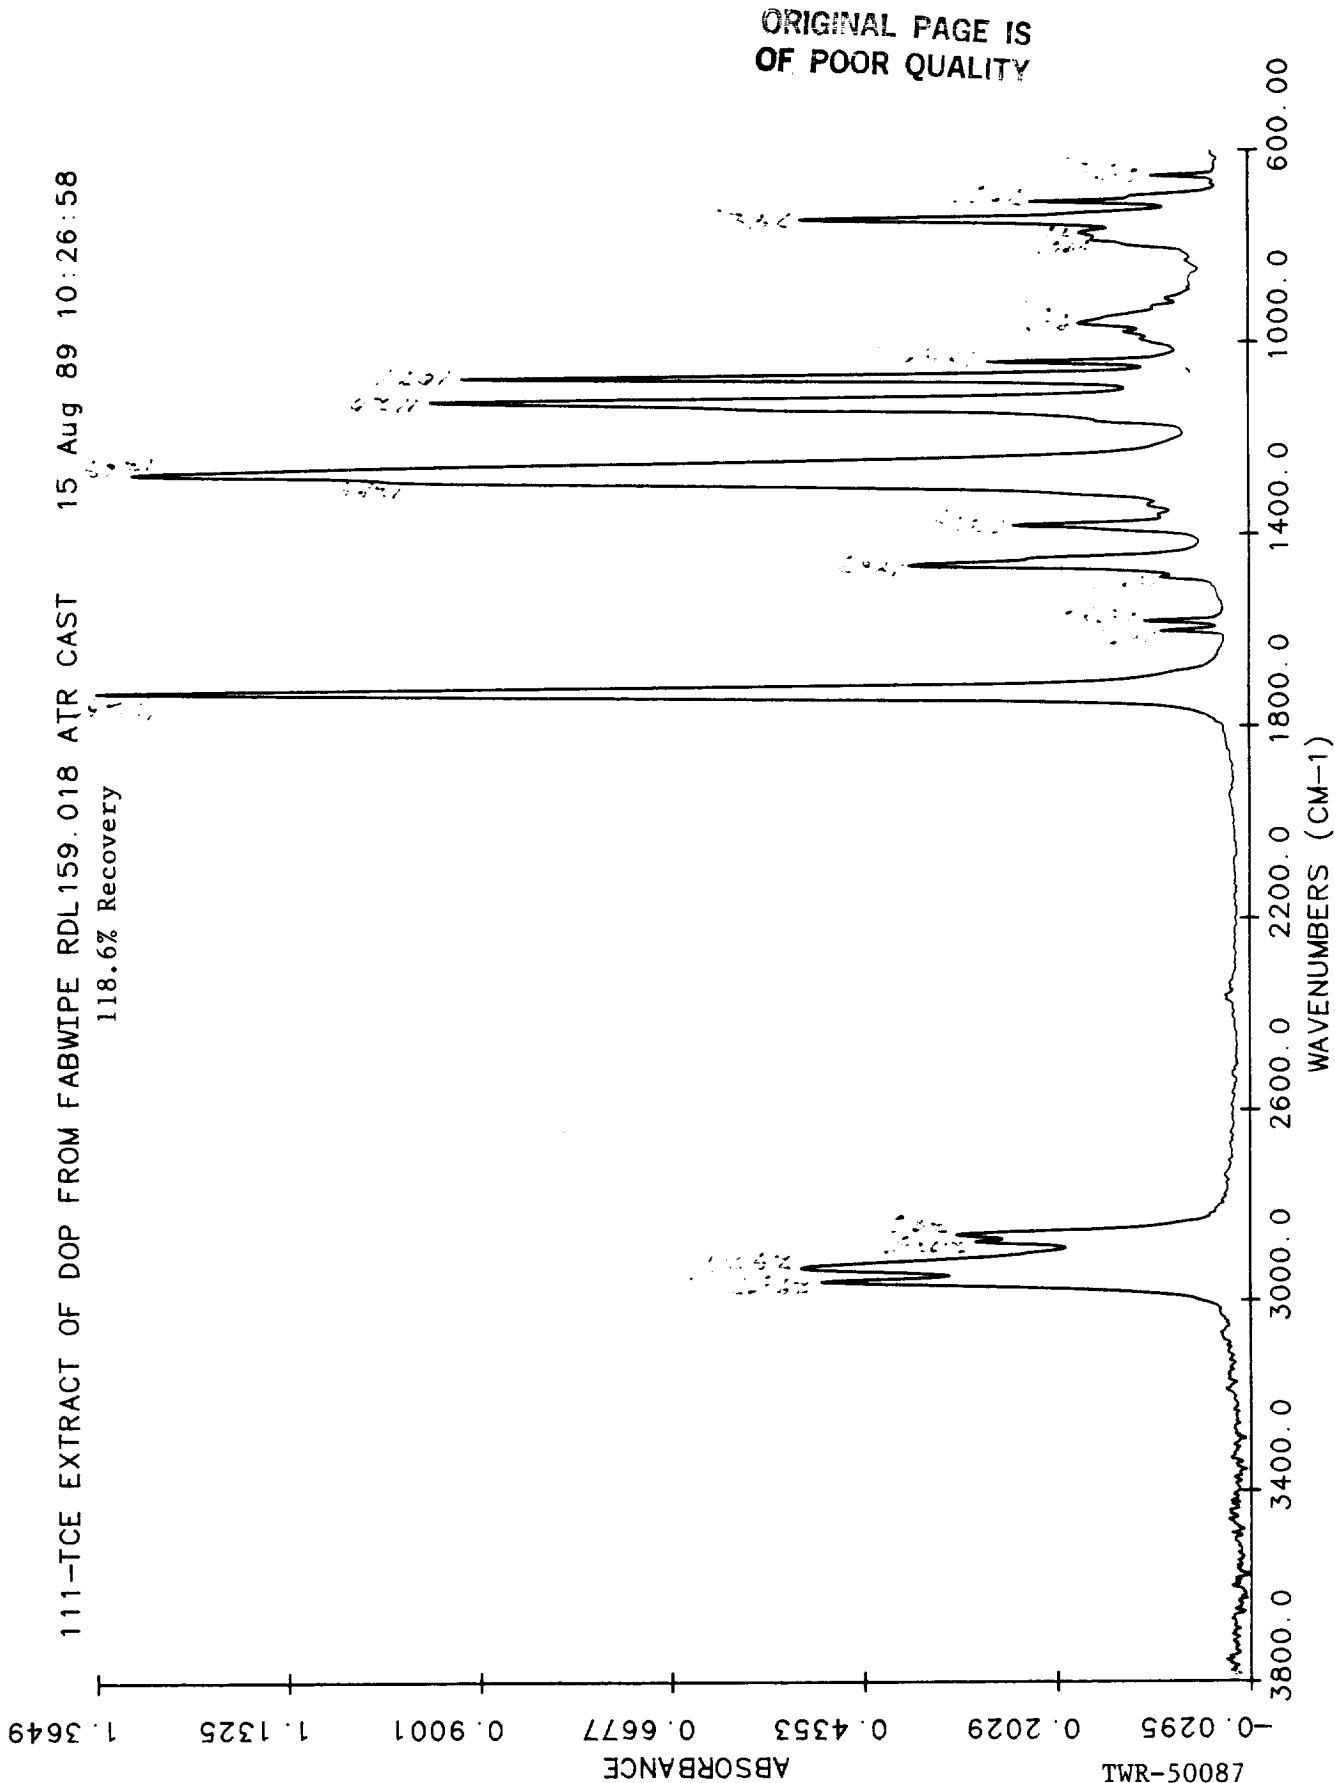


ORIGINAL PAGE IS
OF POOR QUALITY

Figure 154.

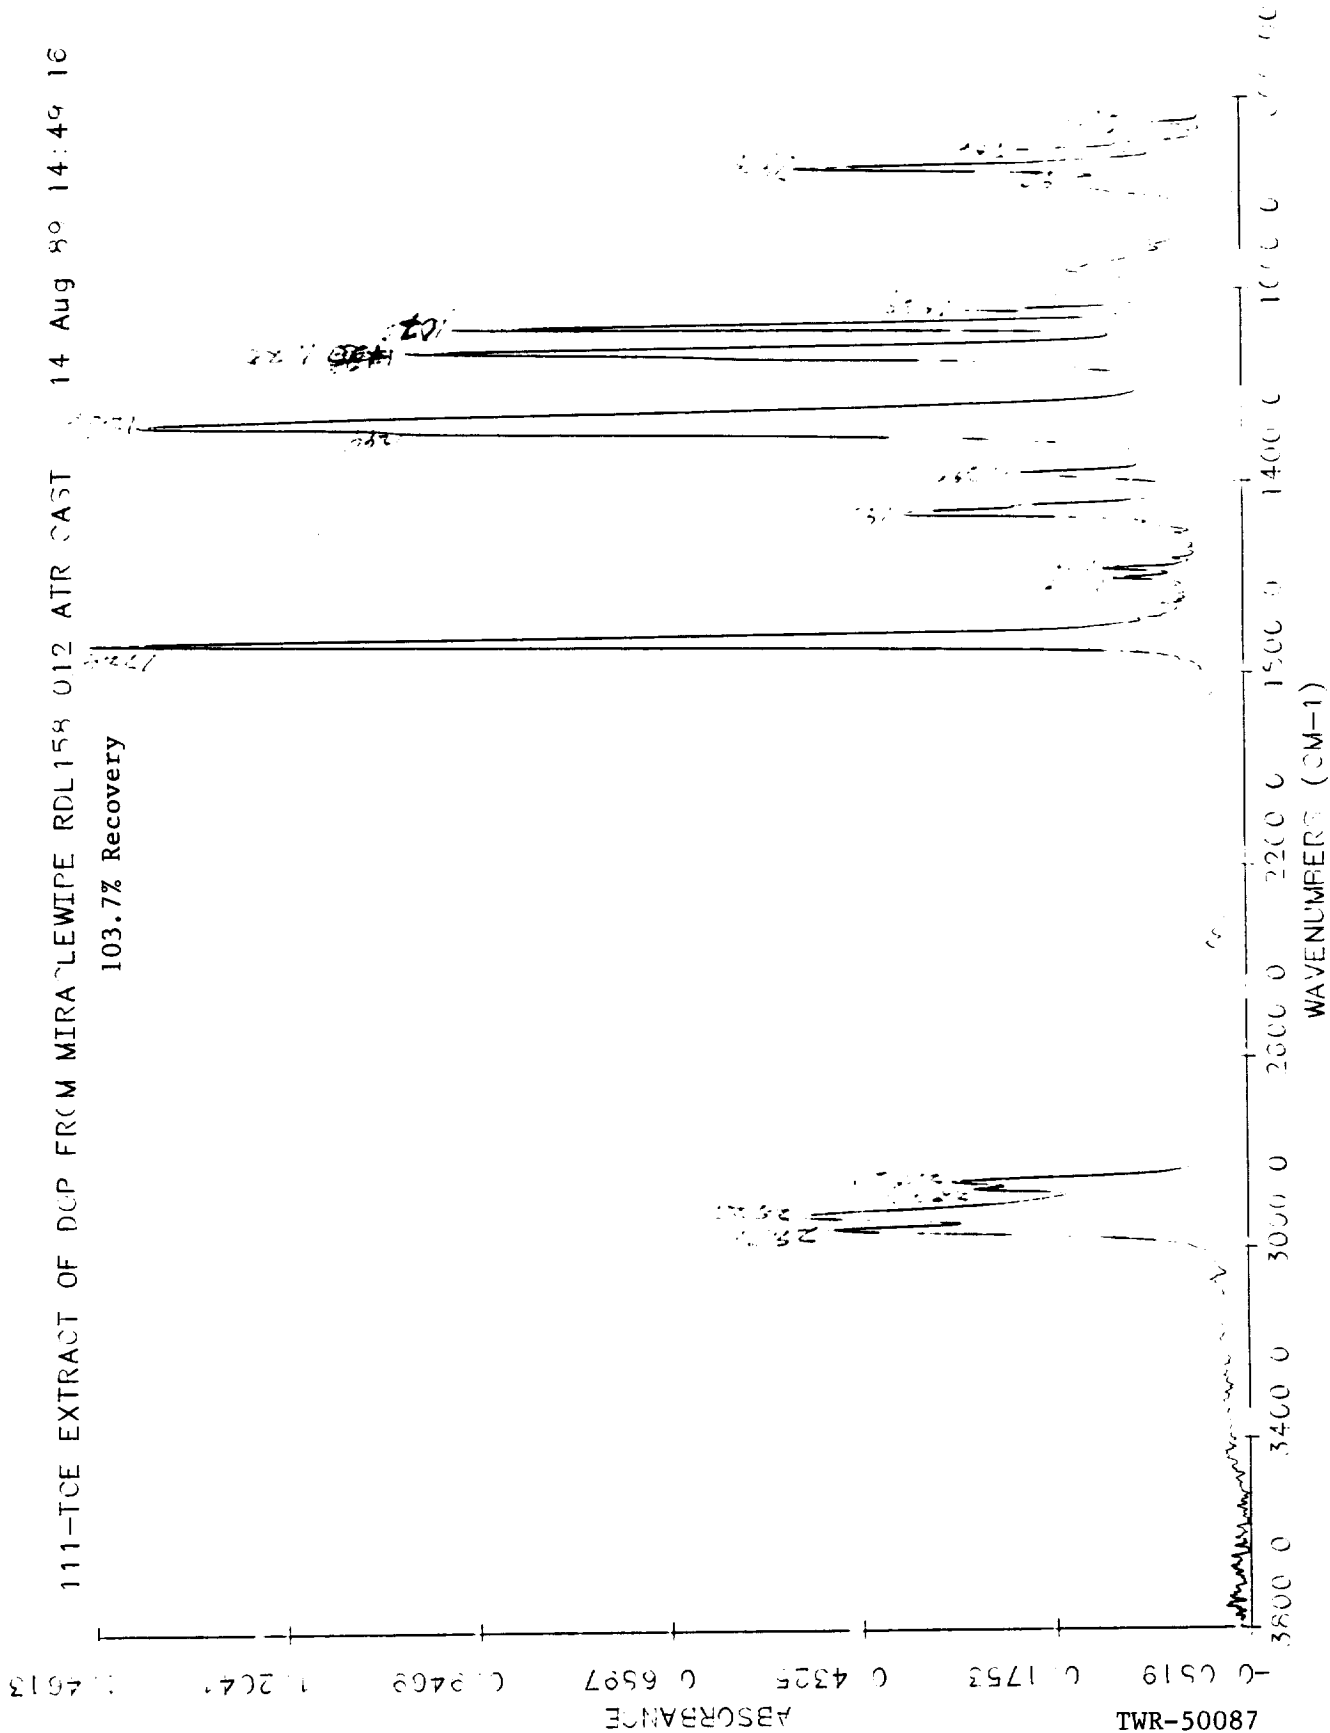


ORIGINAL PAGE IS
OF POOR QUALITY

Figure 155.

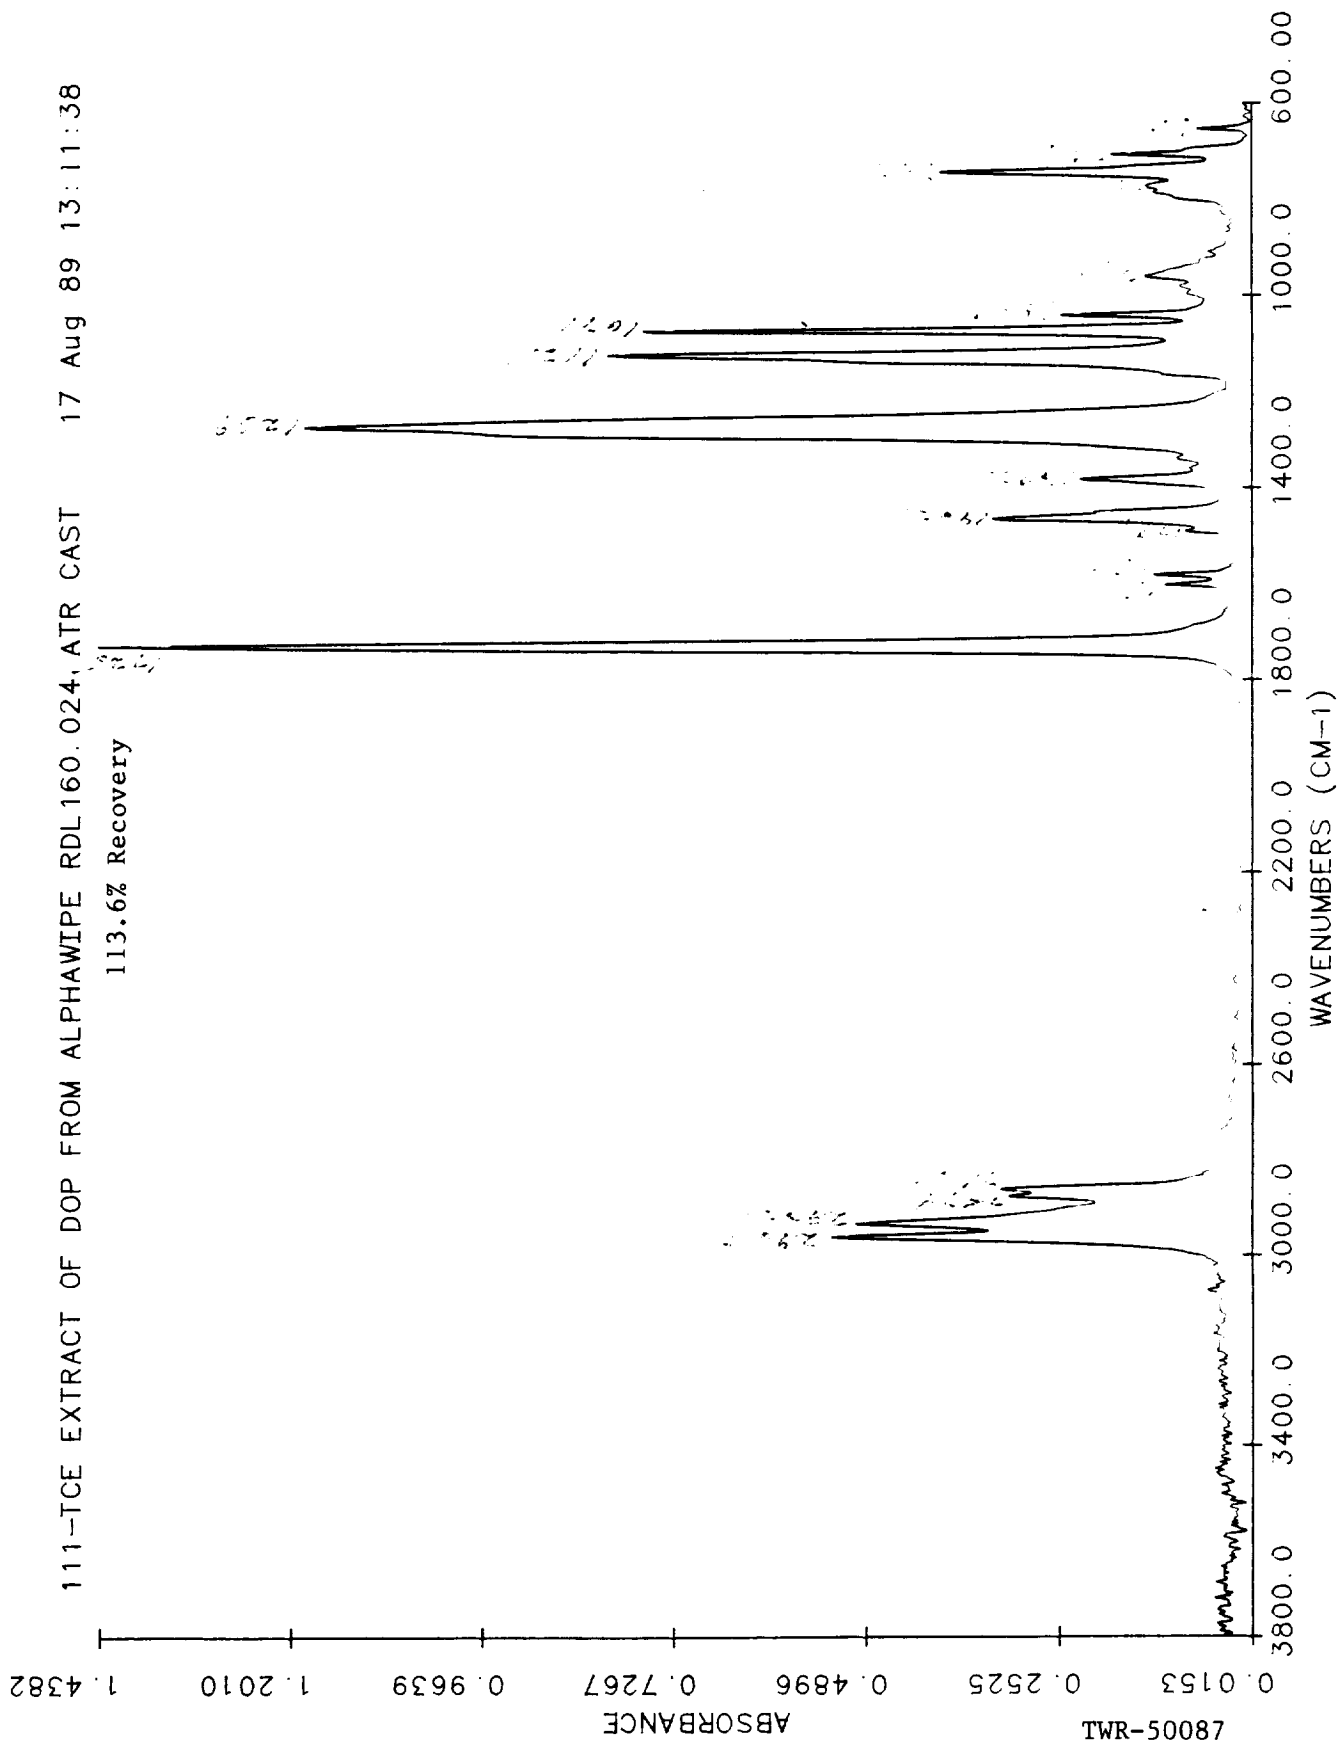

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 156.

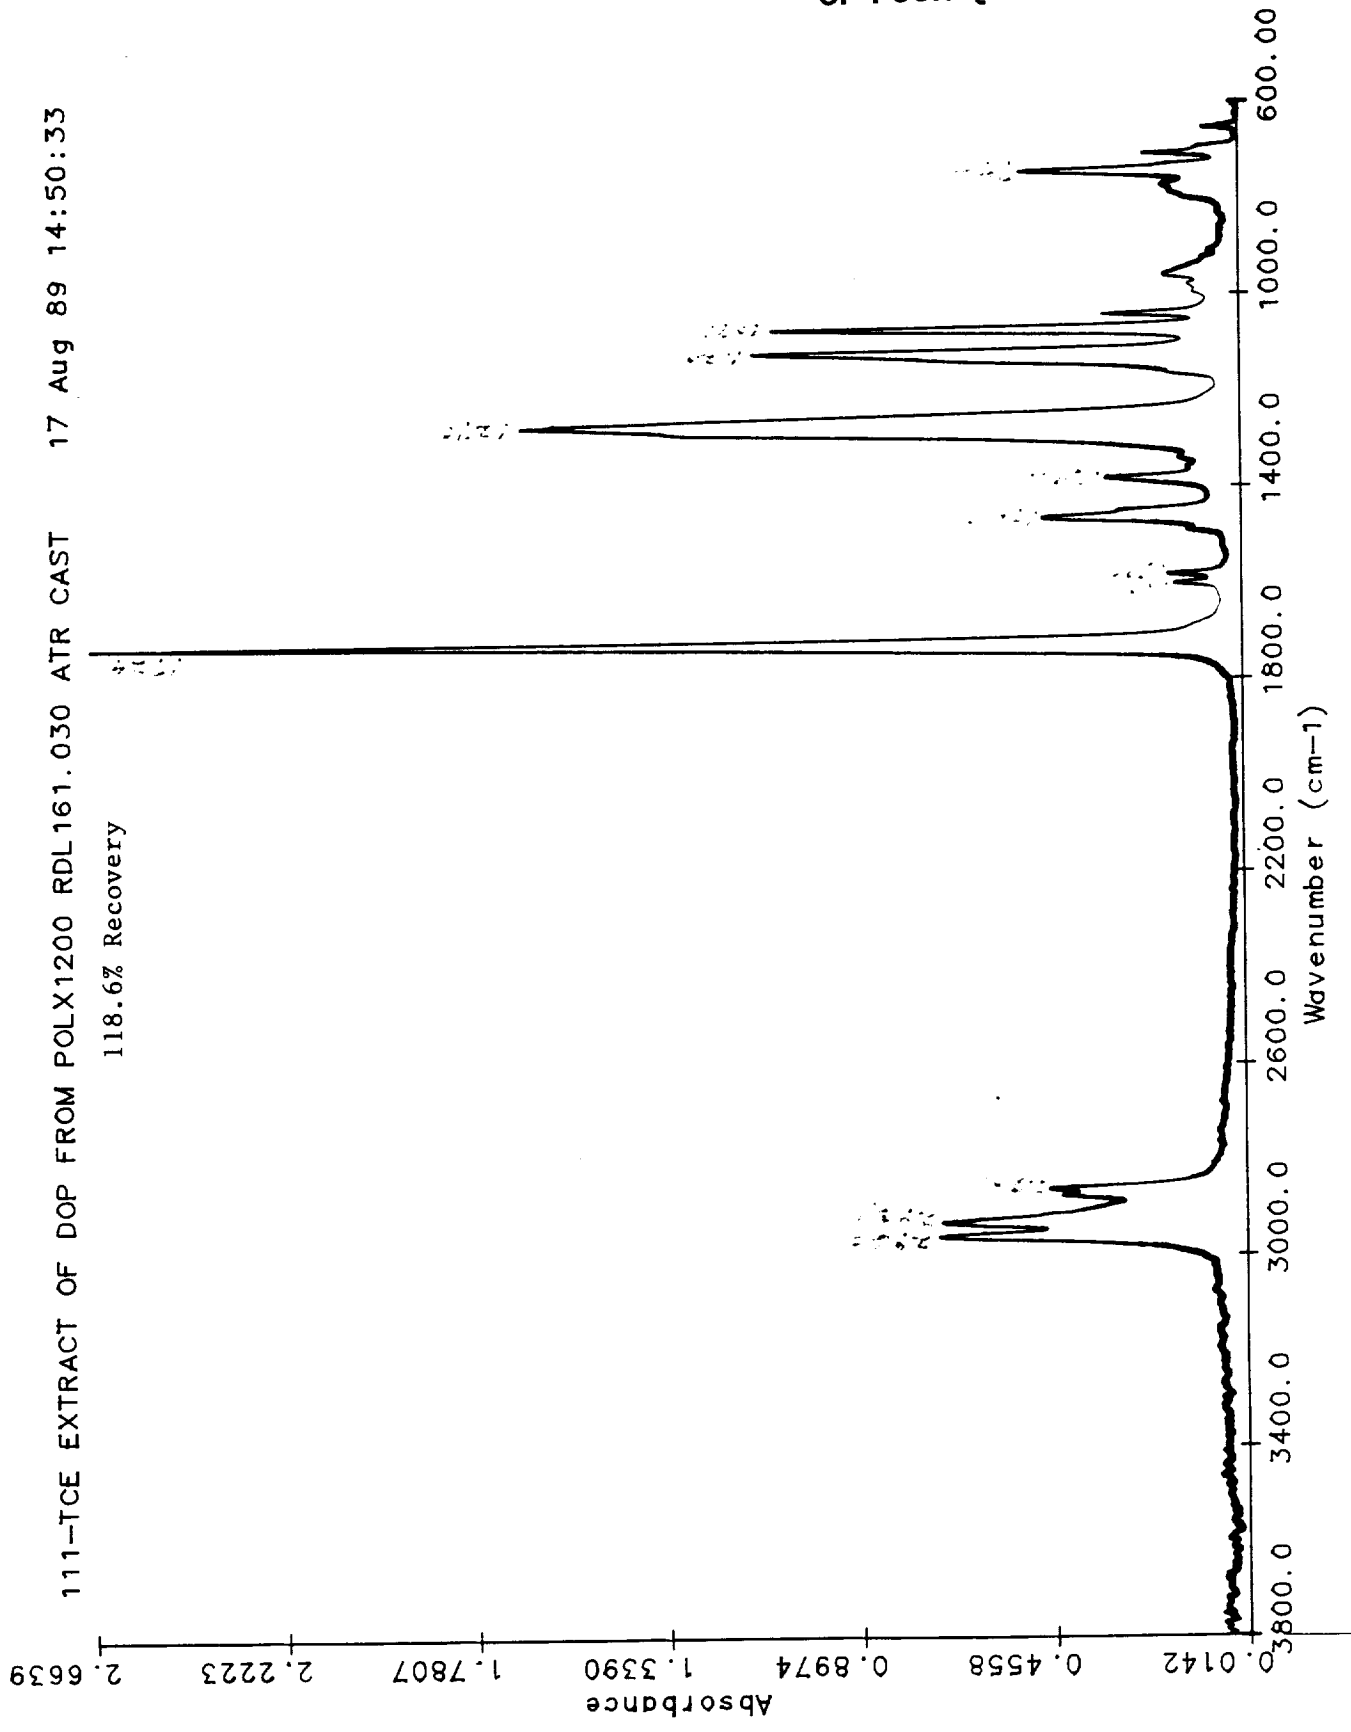

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 157.



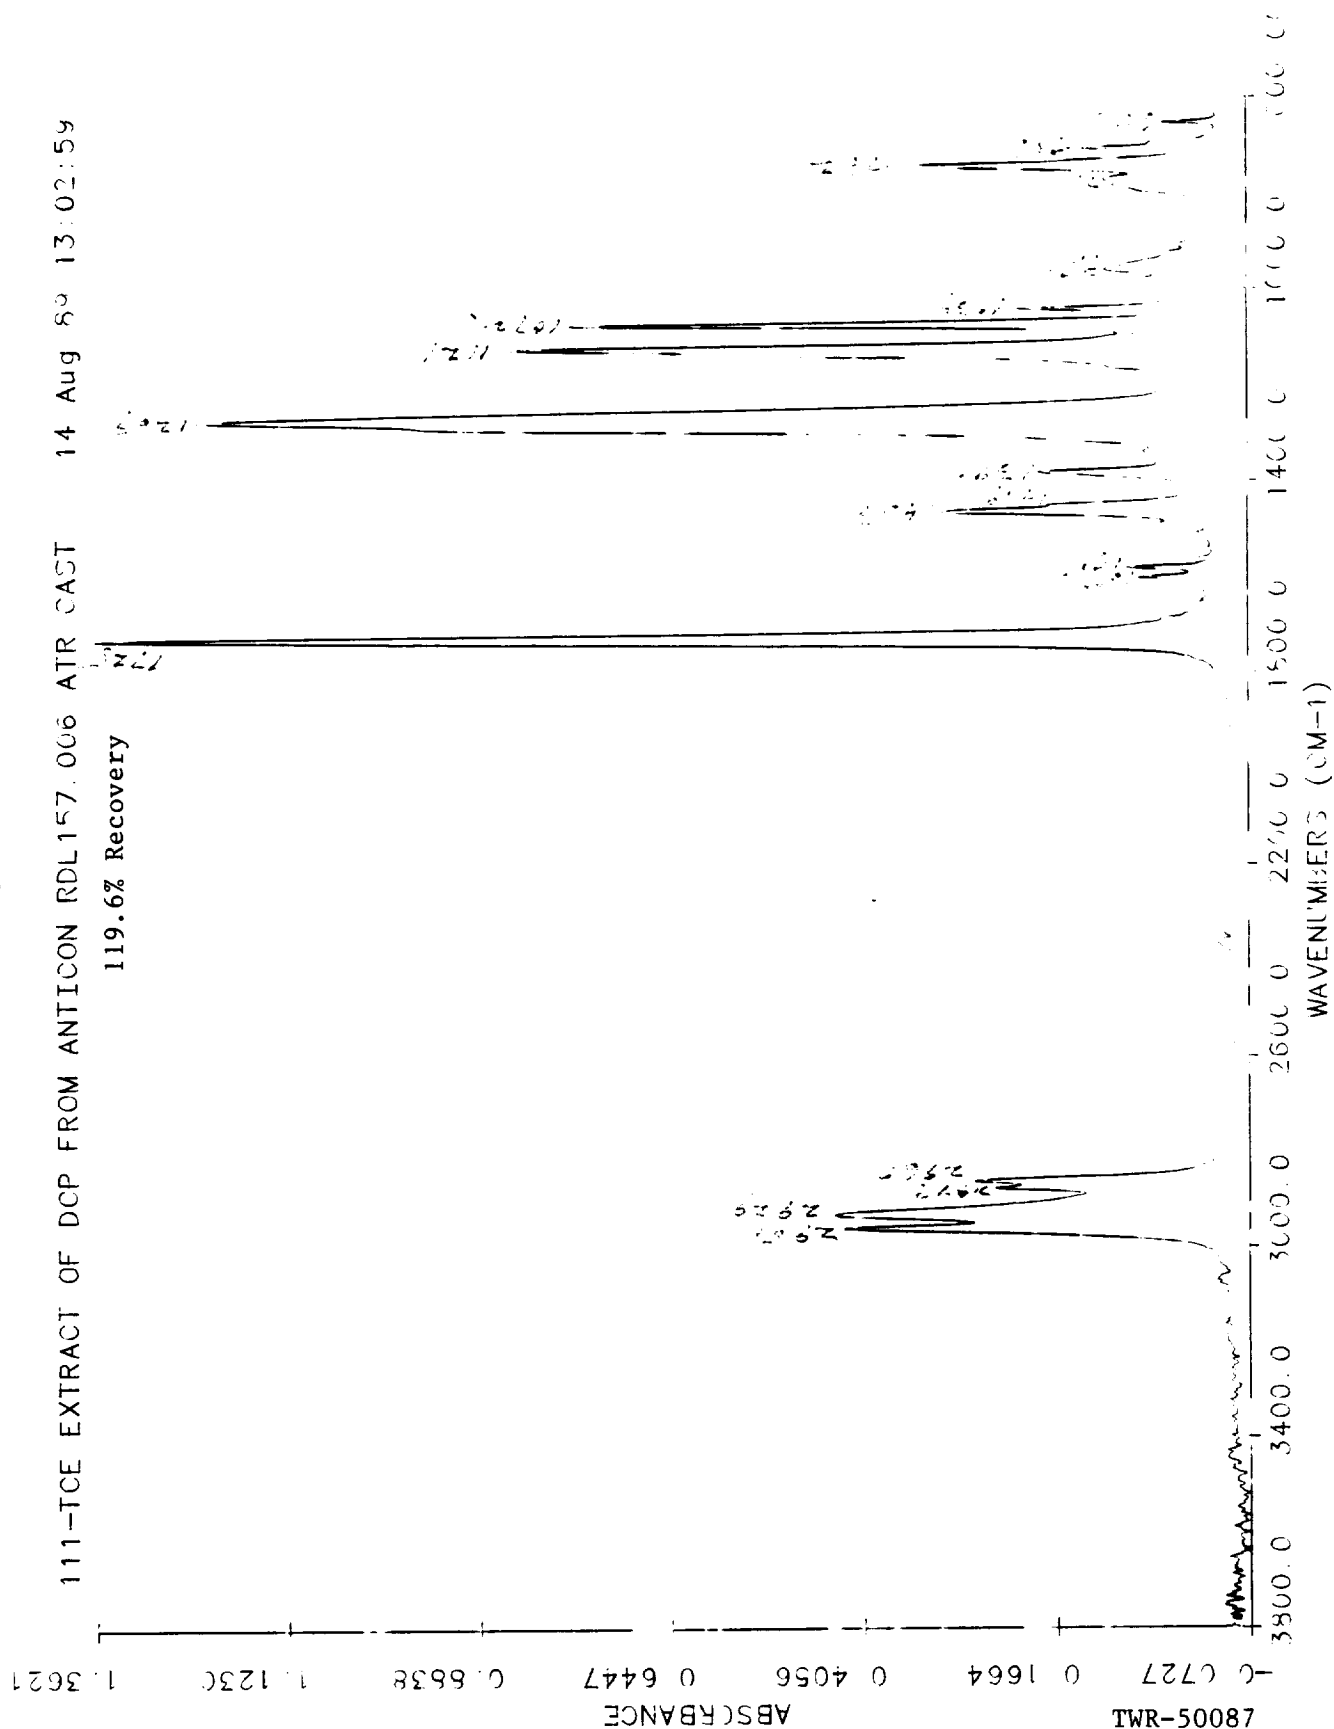


Figure 158.

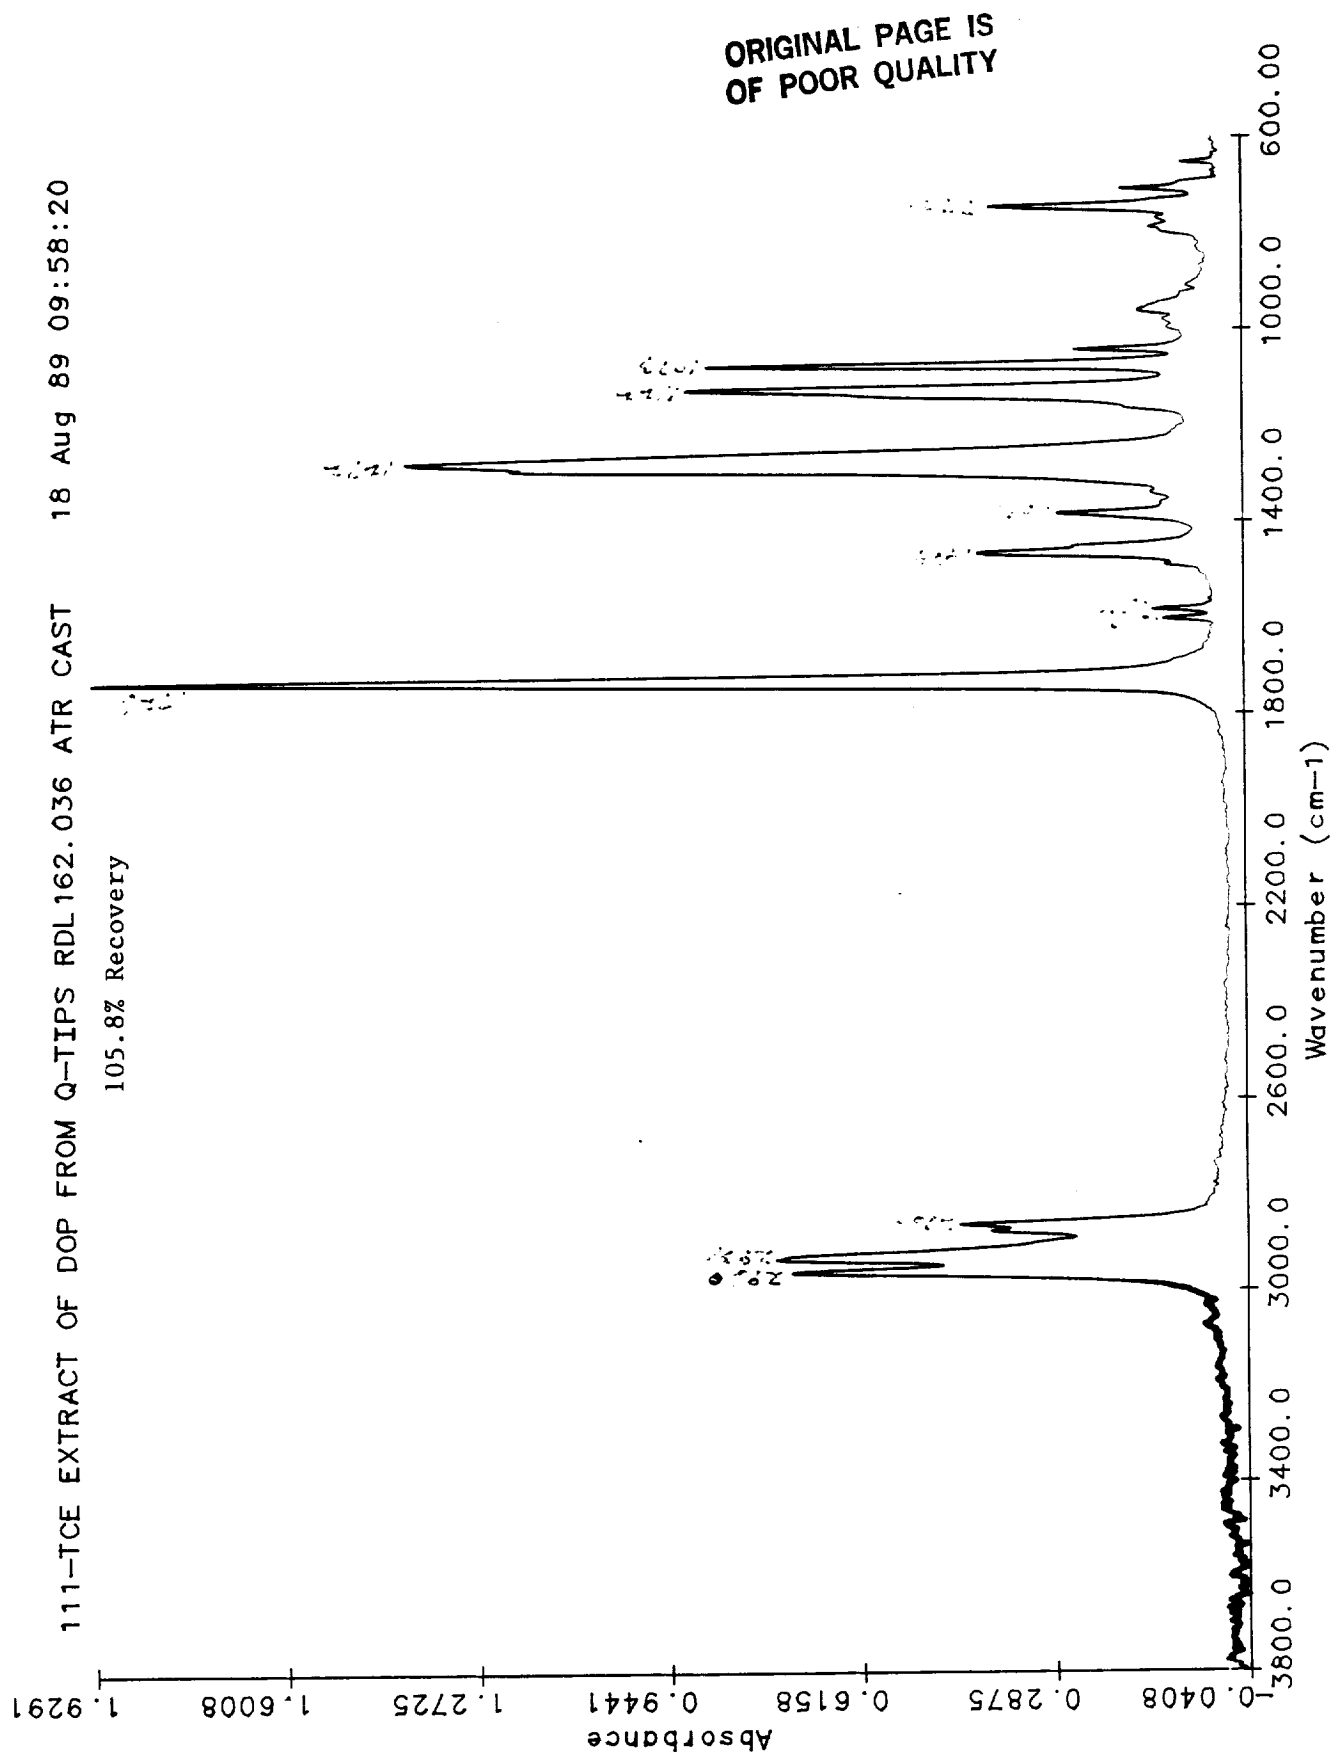

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 159.

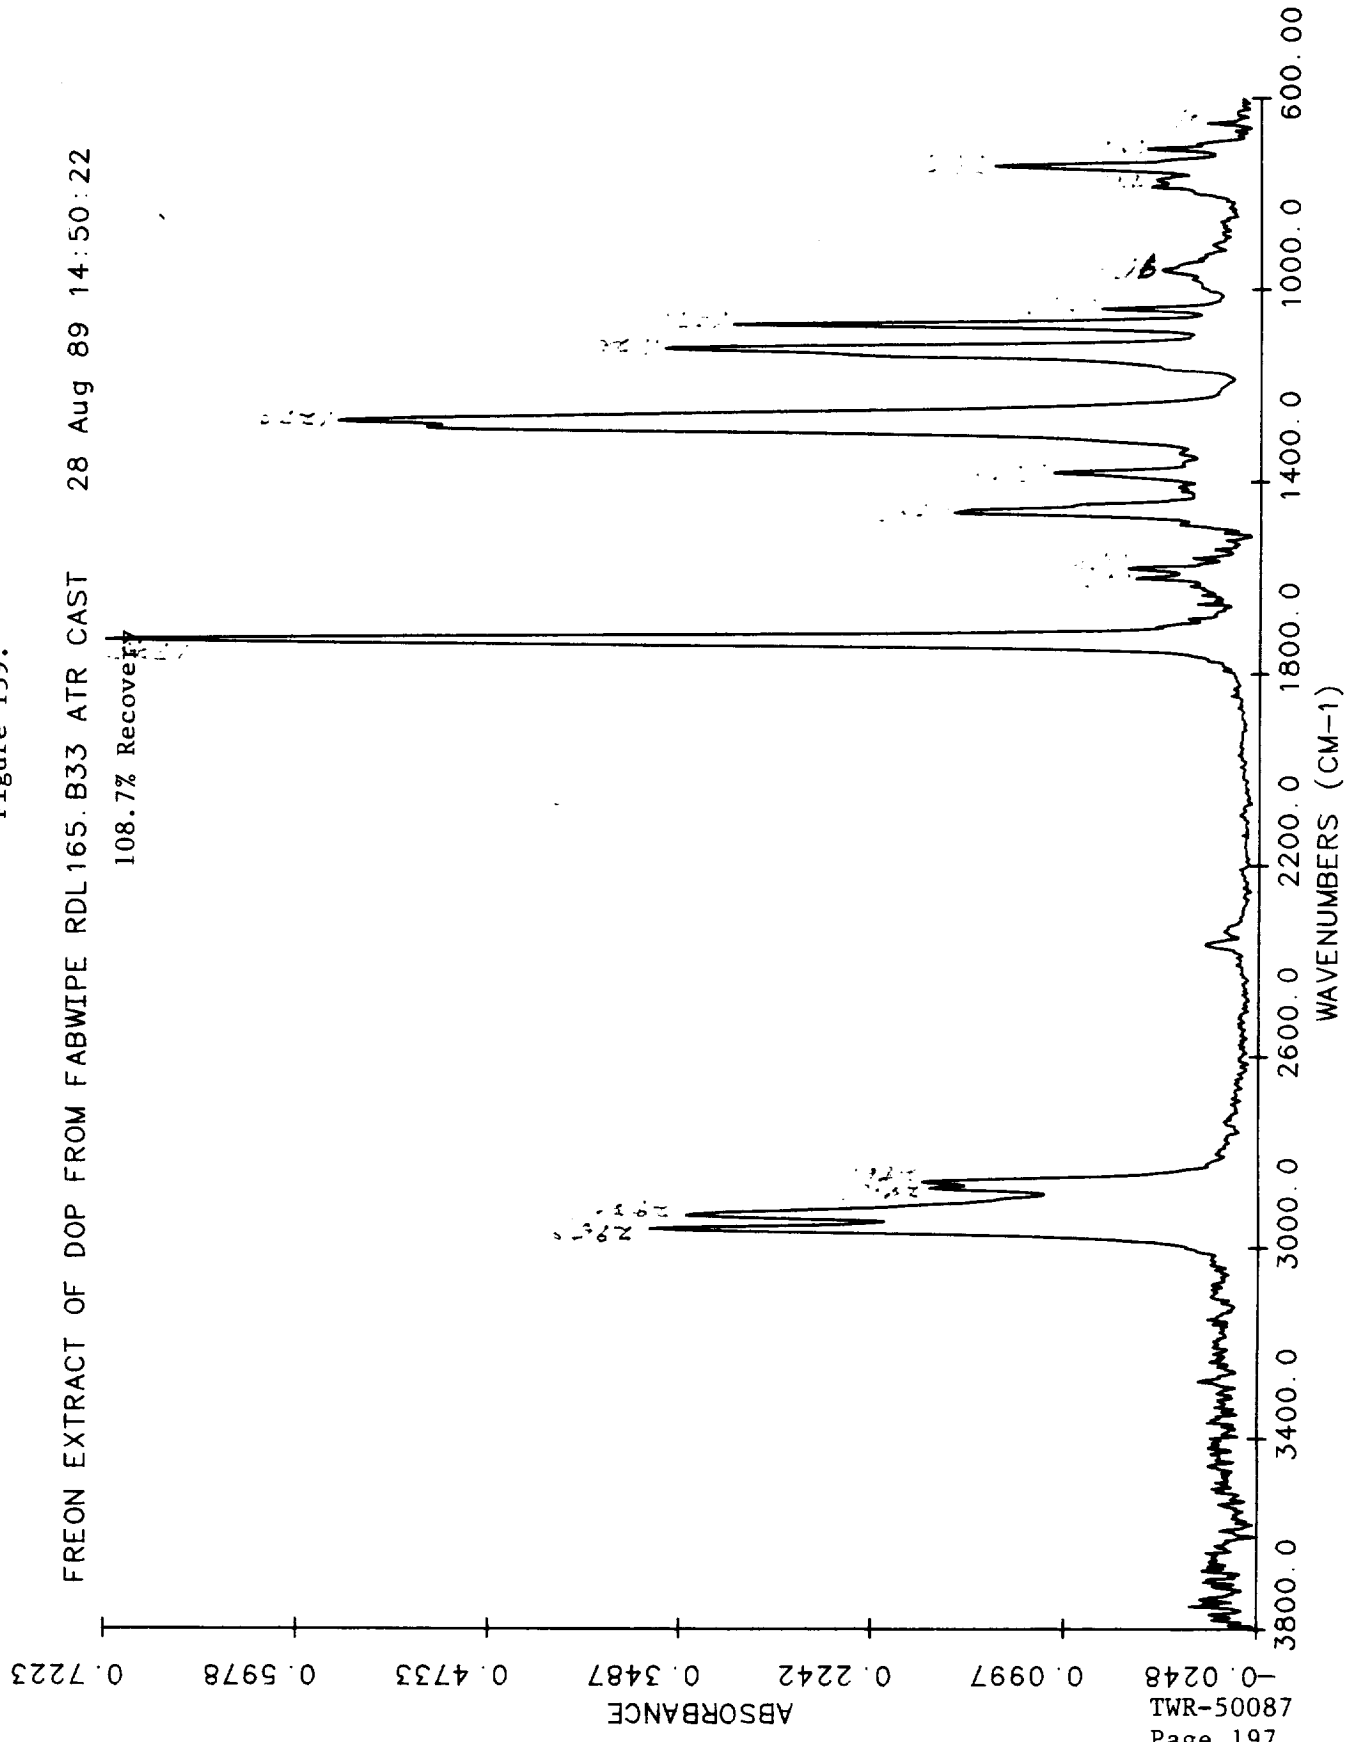

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 160.
FREON TF EXTRACT OF DOP FROM MIRACLEWIPE RDL164.B25 ATR CAST 28 Aug 89 13:18:43

110.7% Recovery

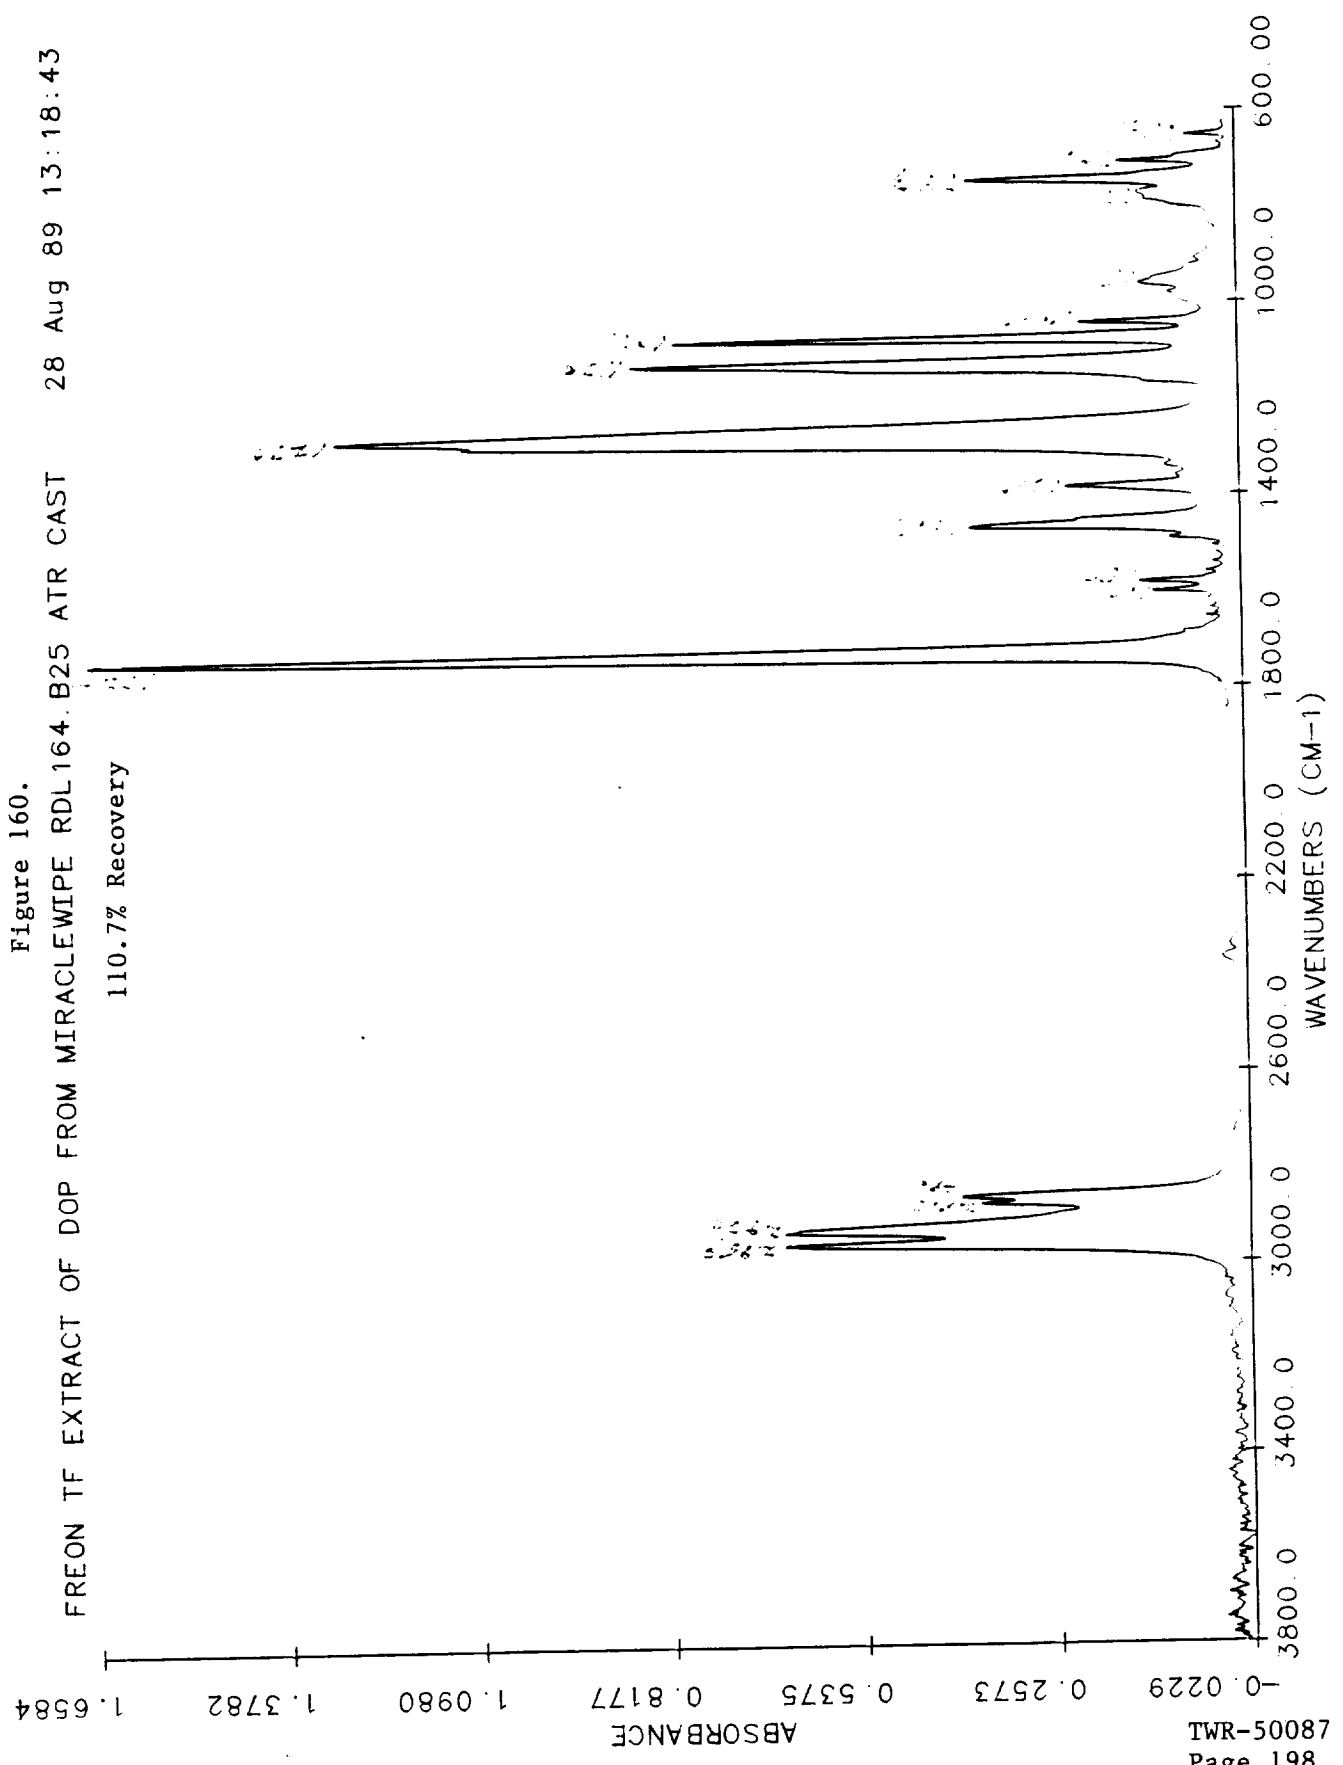


Figure 161.



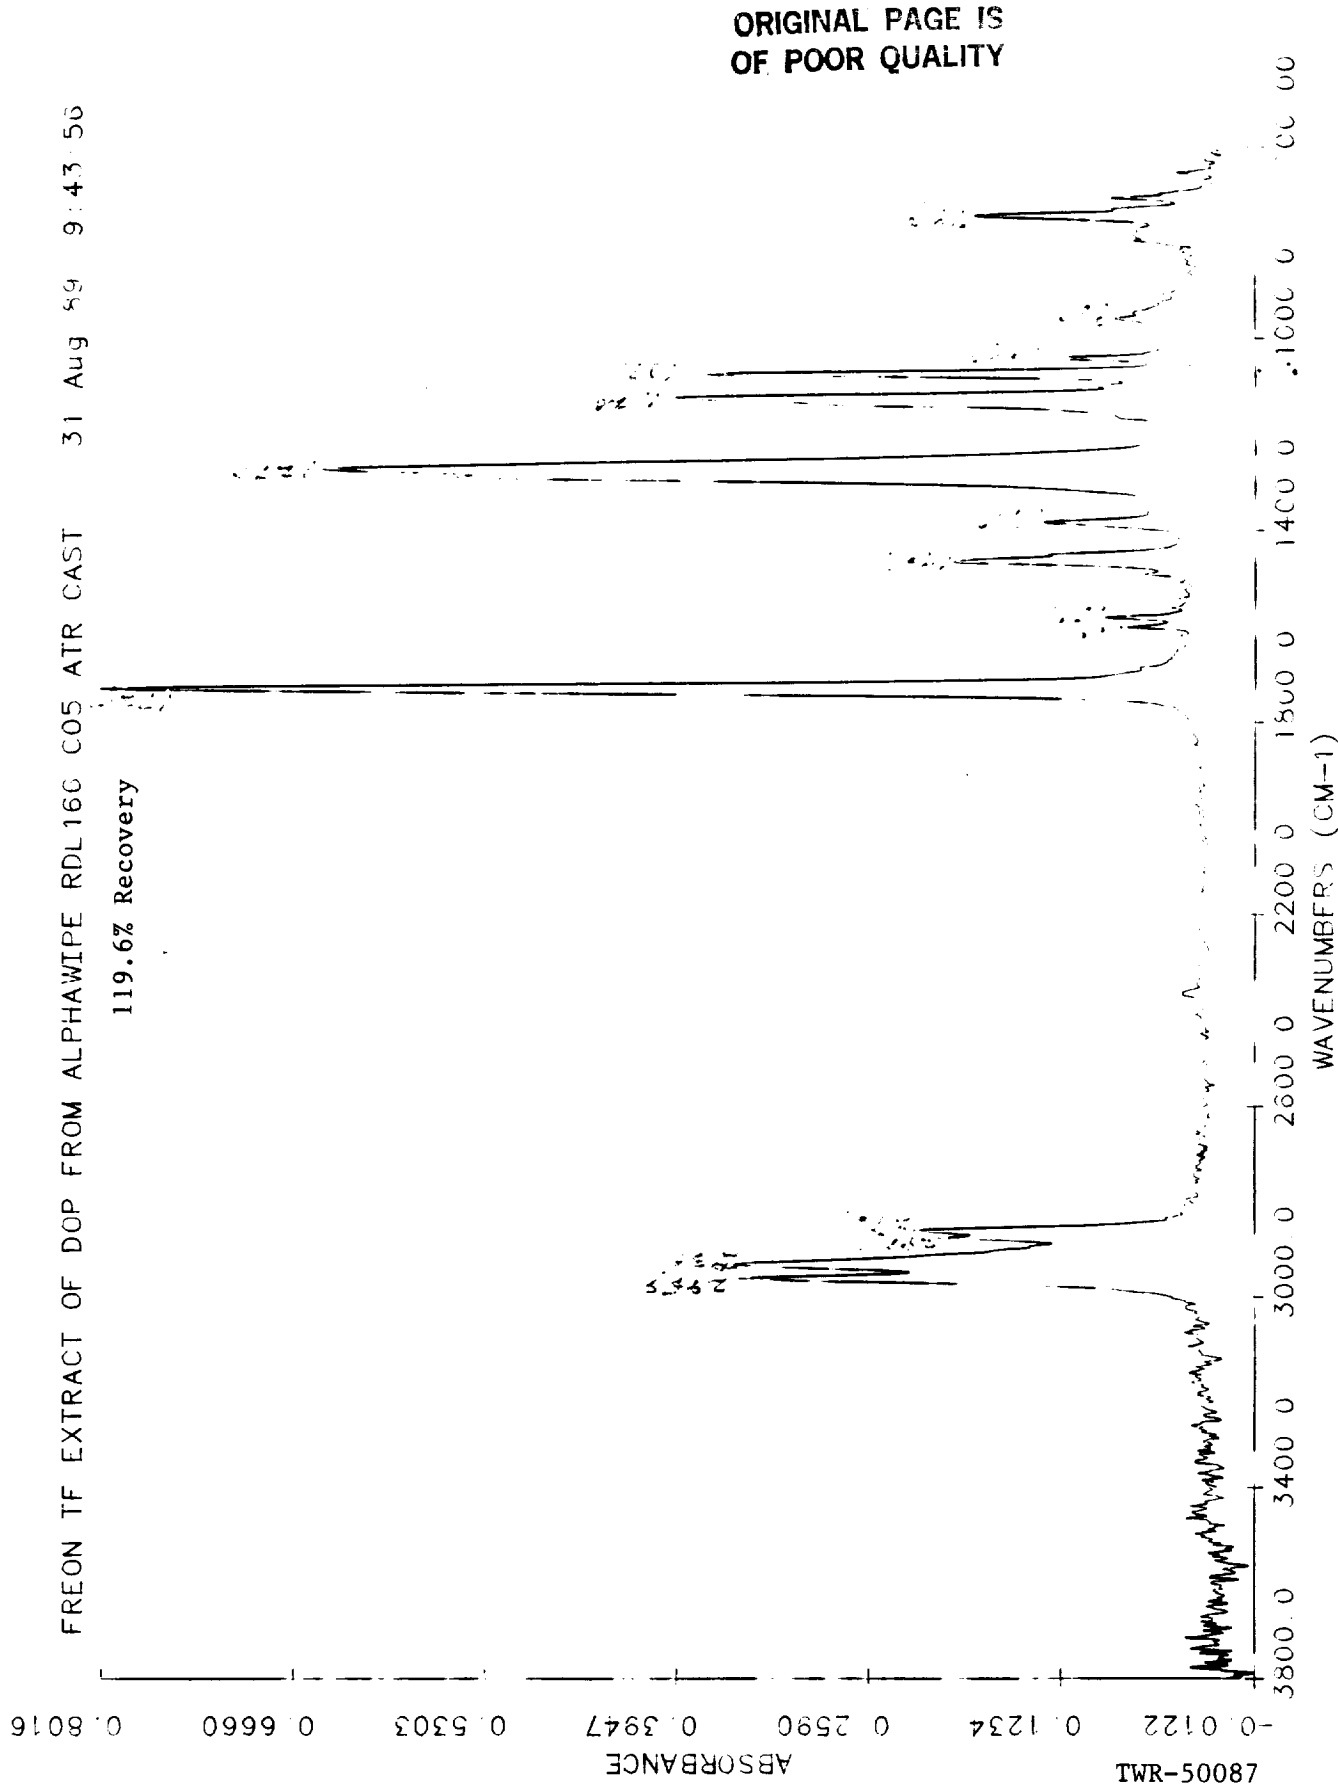


Figure 162.

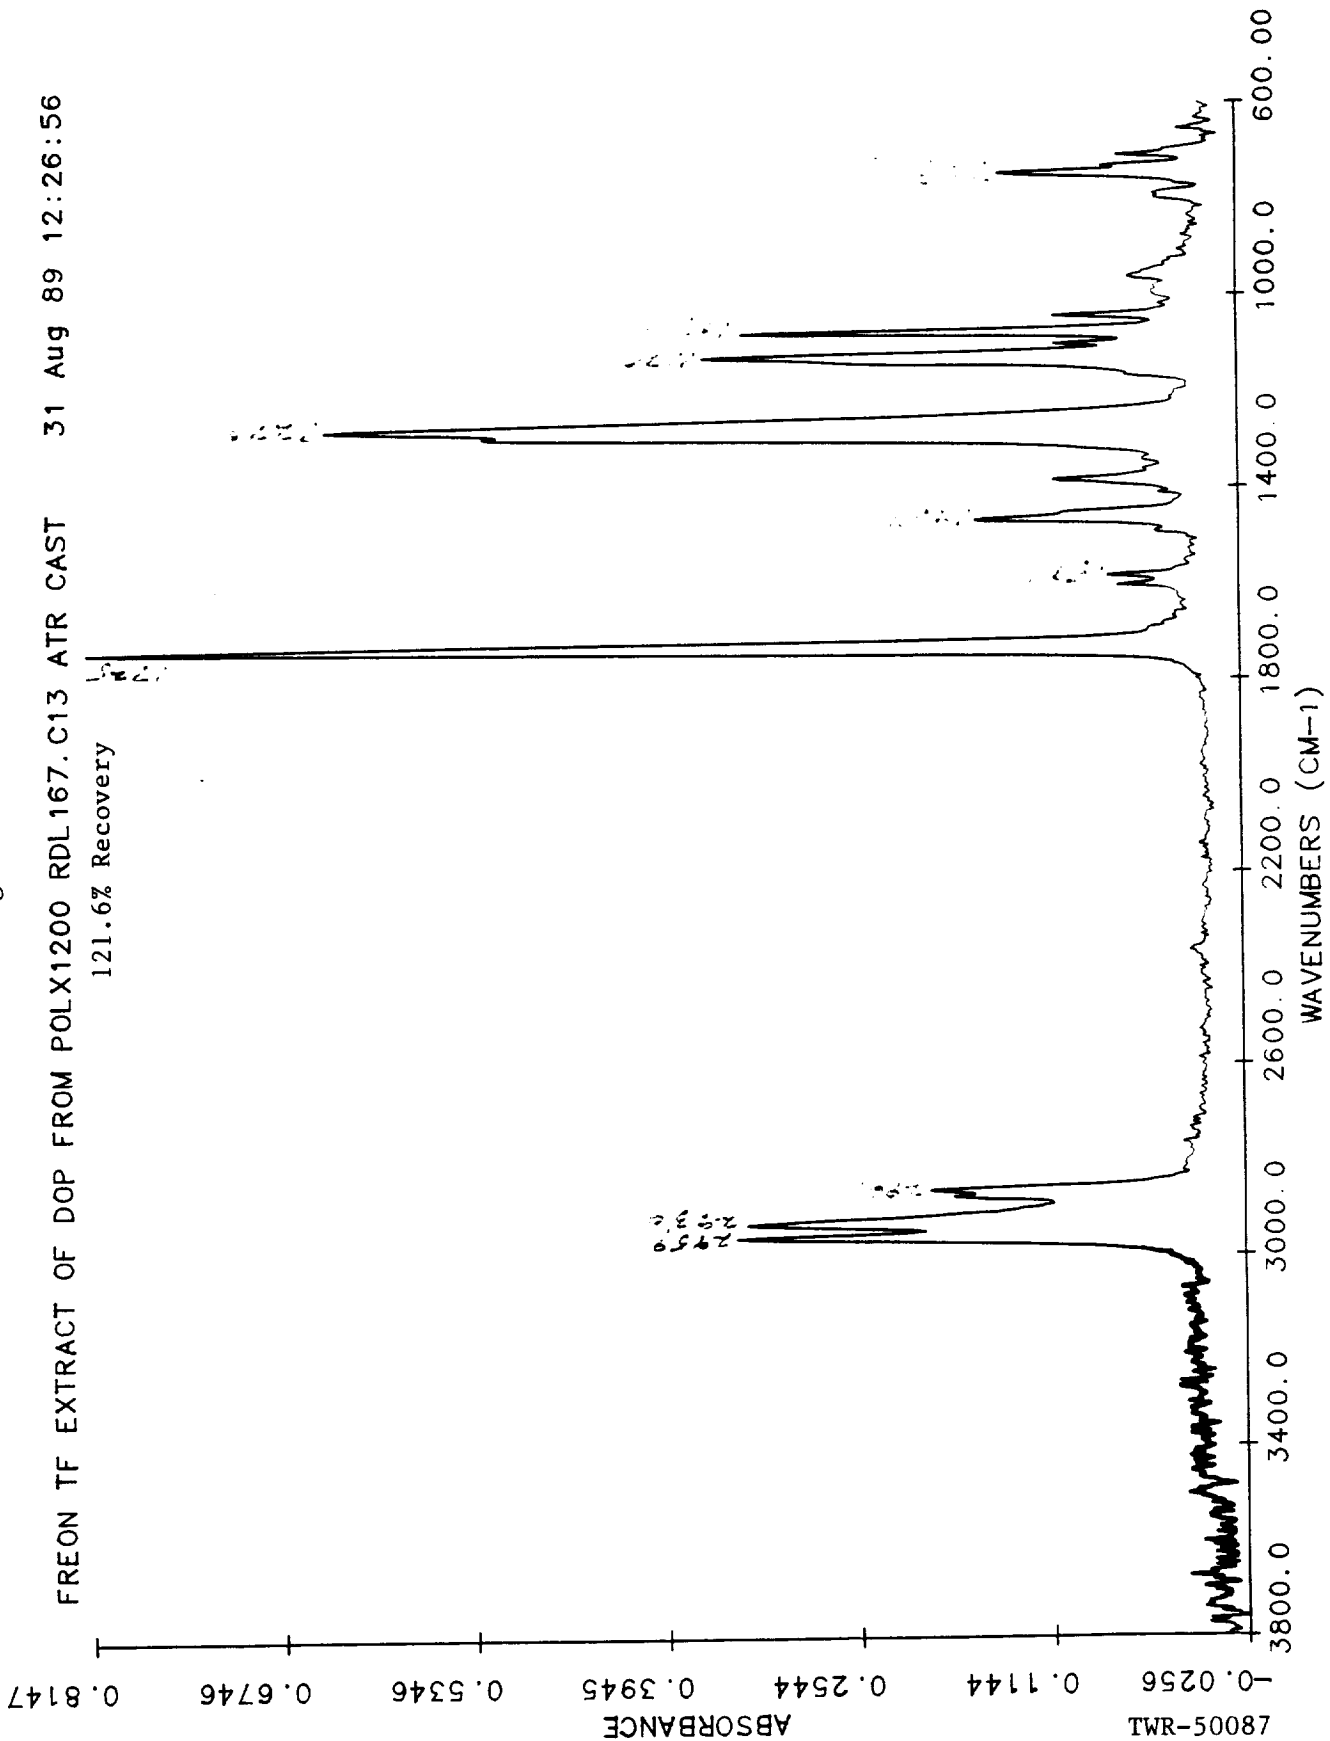


ORIGINAL PAGE IS
OF POOR QUALITY

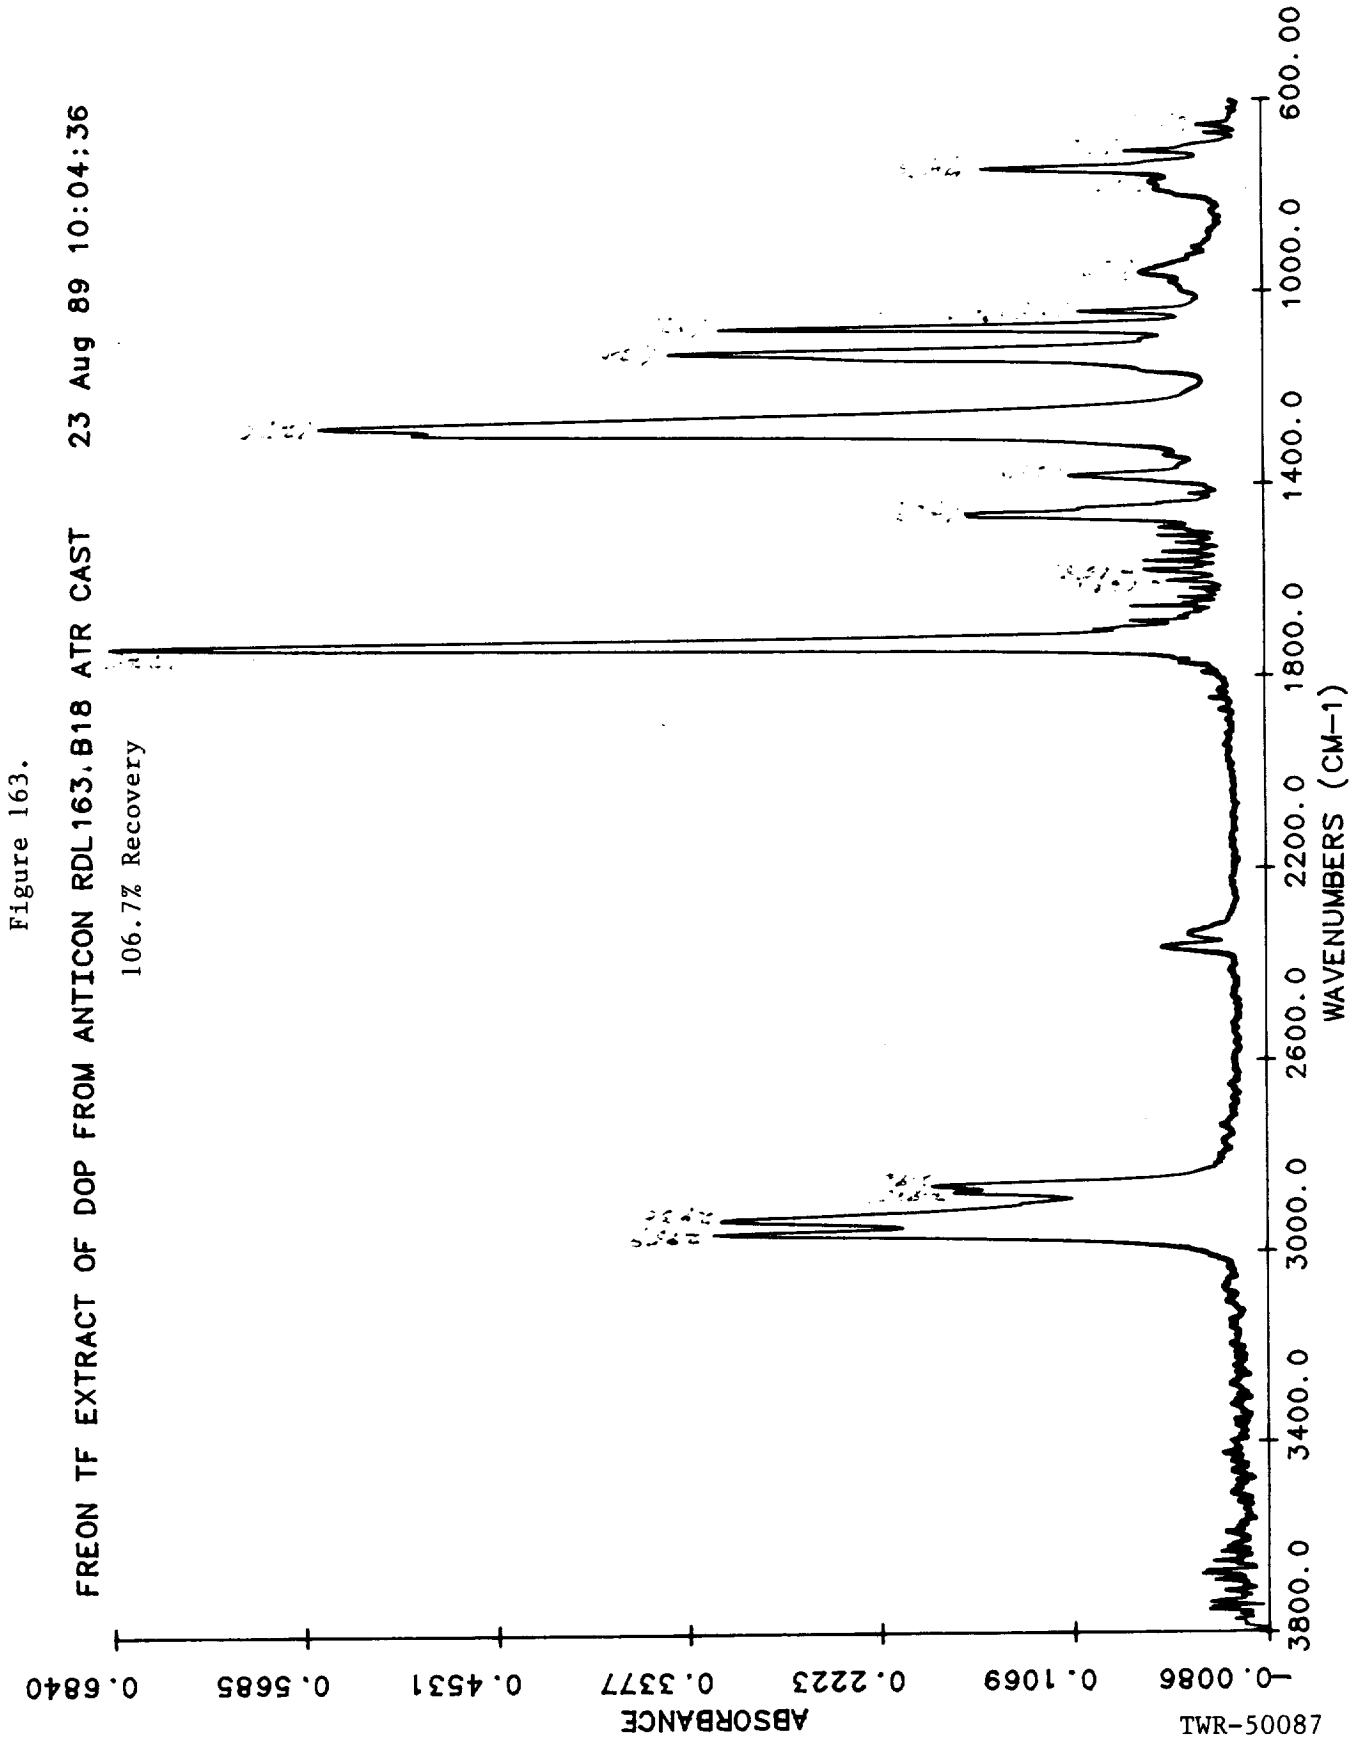

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 164.

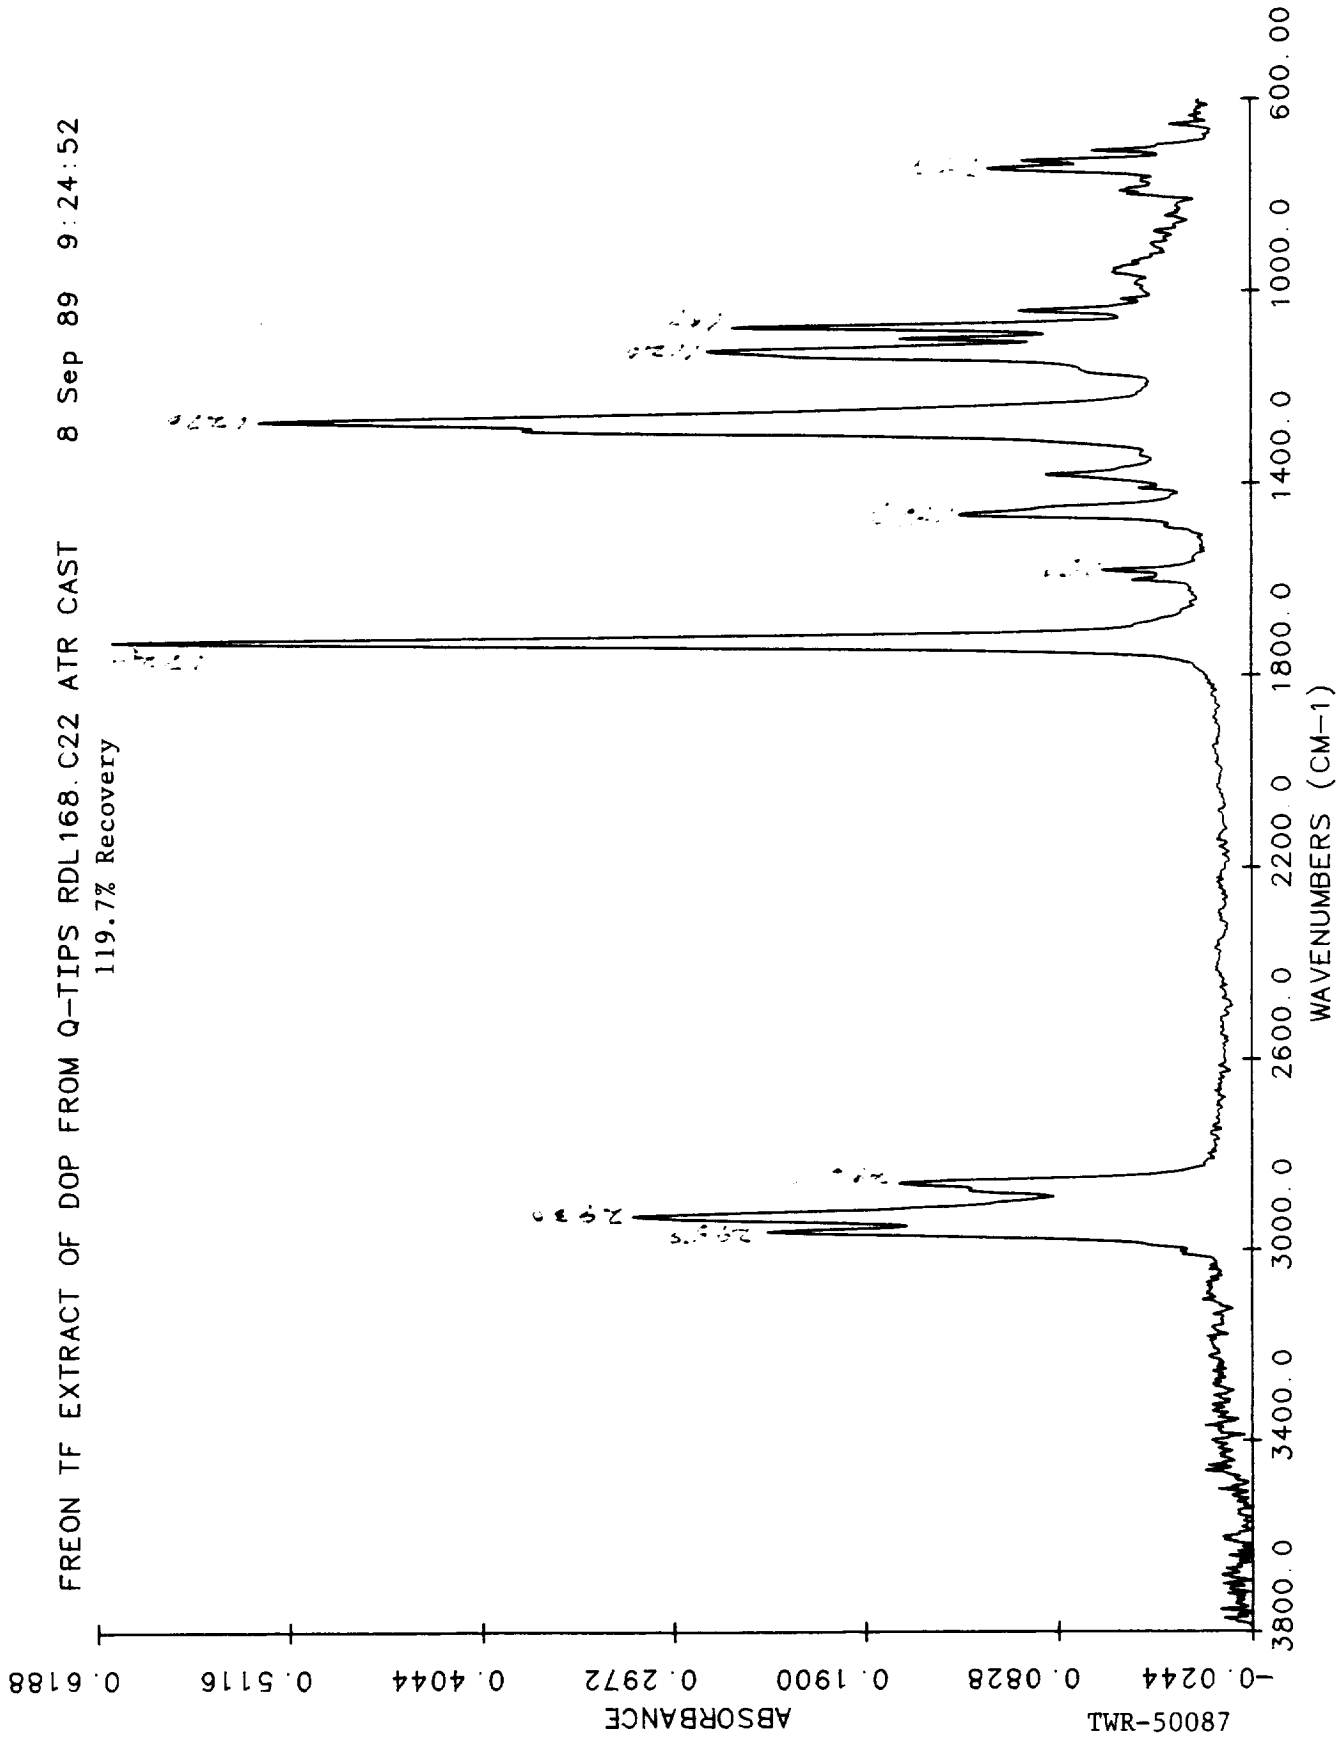

MEK EXTRACT OF DOP FROM FABWIPE RDL171.D10 ATR CAST
106.7% Recovery

13 Sep 89 12:17:19

ORIGINAL SOURCE IS
OF POOR QUALITY


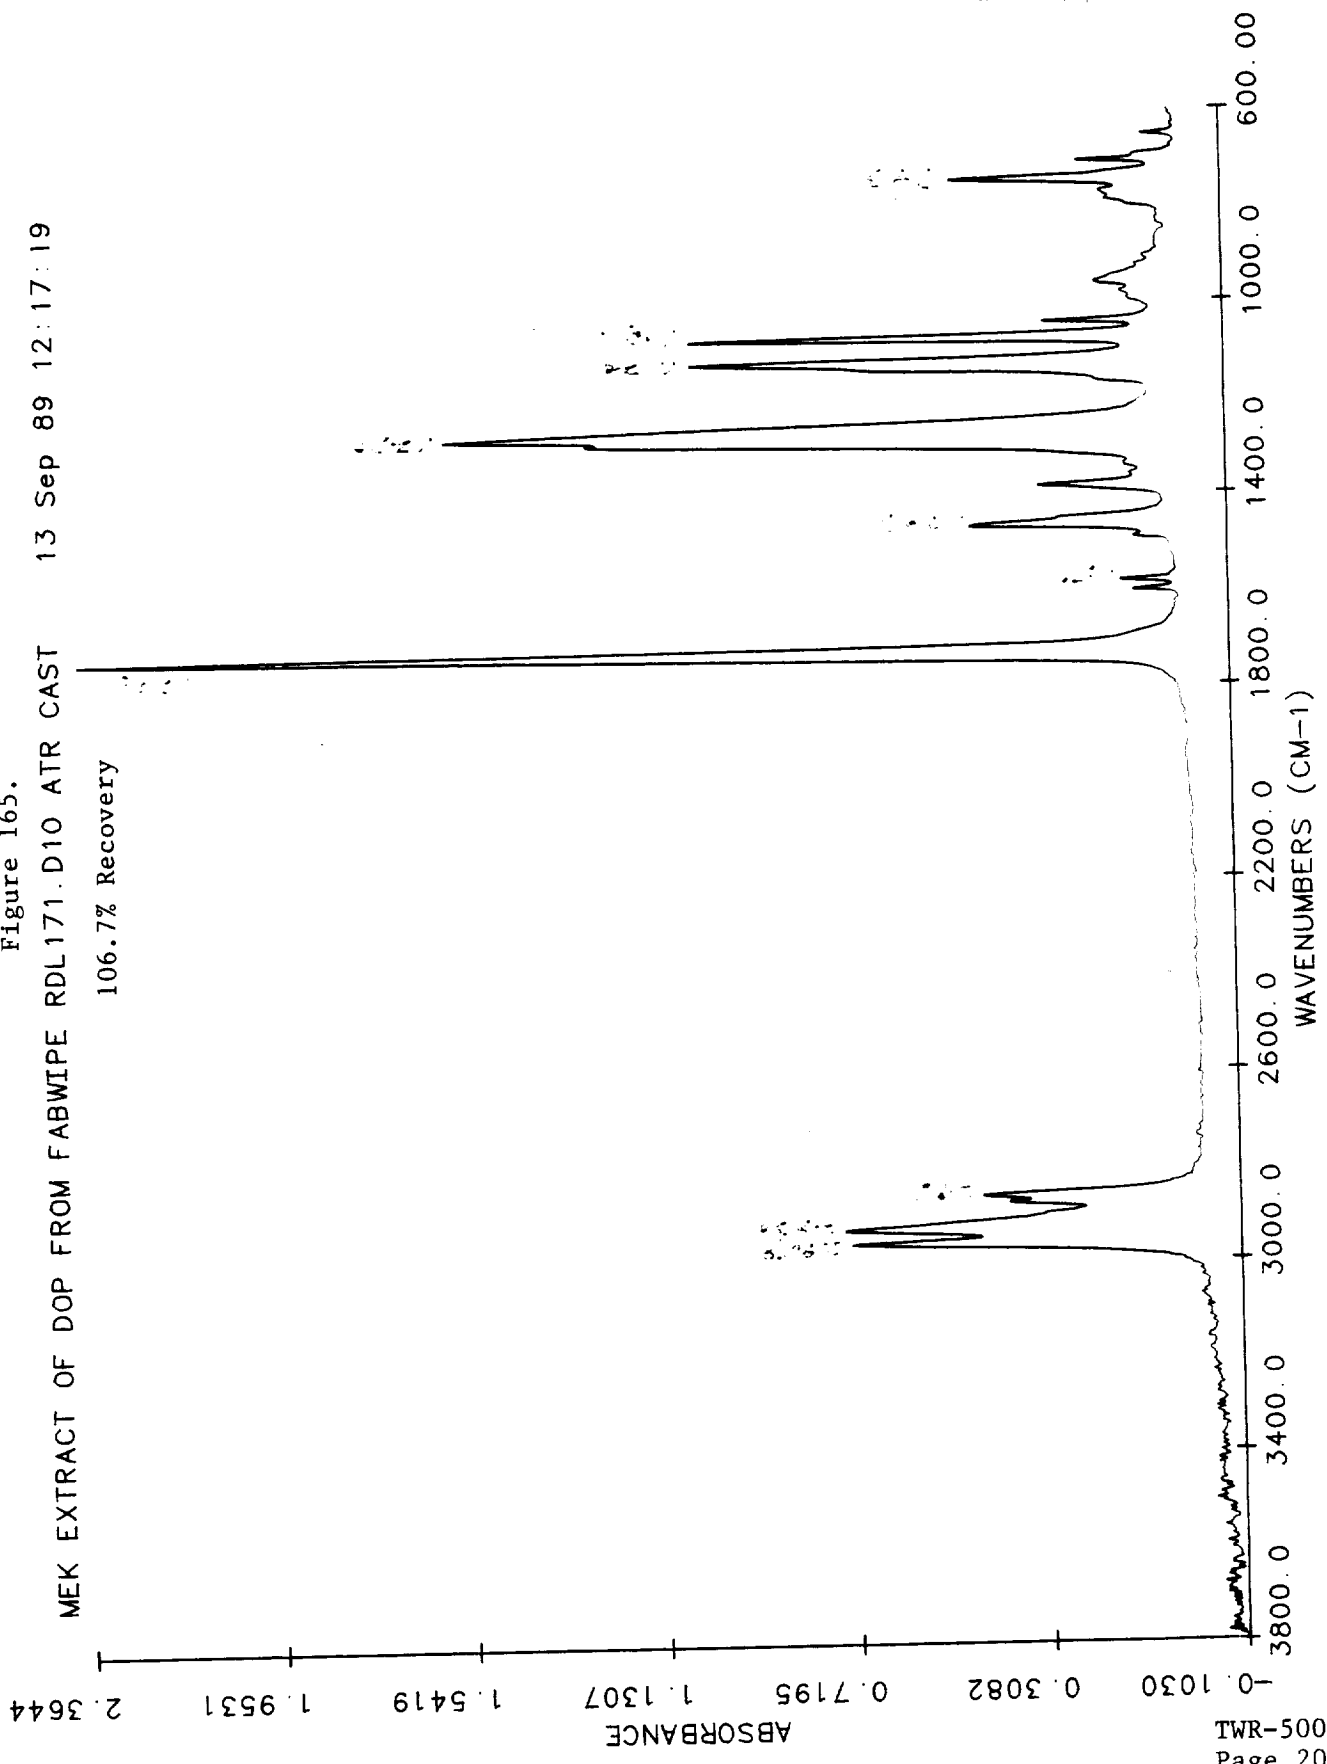


Figure 166.

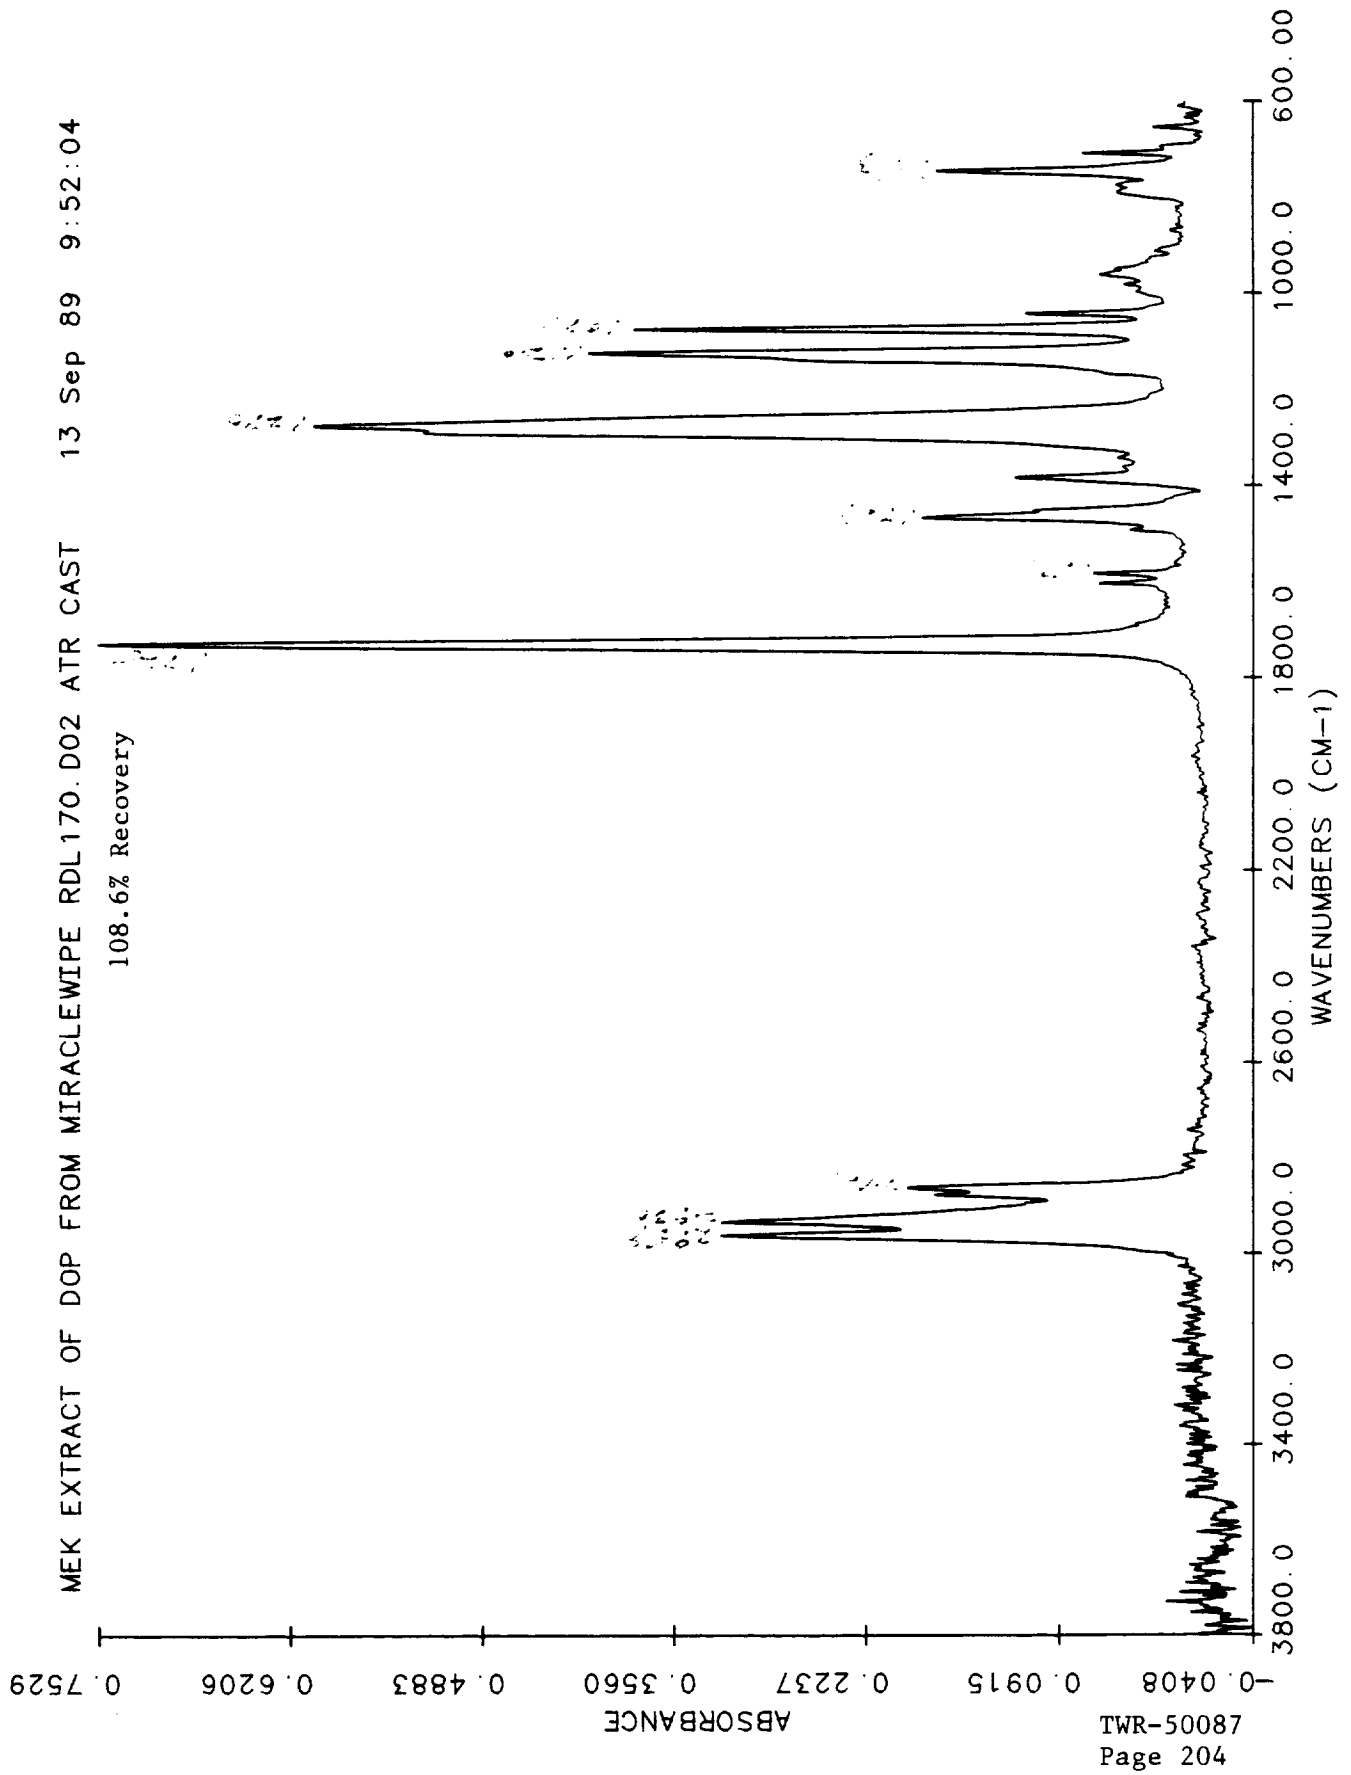


ORIGINAL PAGE IS
OF POOR QUALITY

MEK EXTRACT OF DOP FROM ALPHAWIPE RDL172.D18 ATR CAST 13 Sep 89 13:21:30

Figure 167.

96.7% Recovery

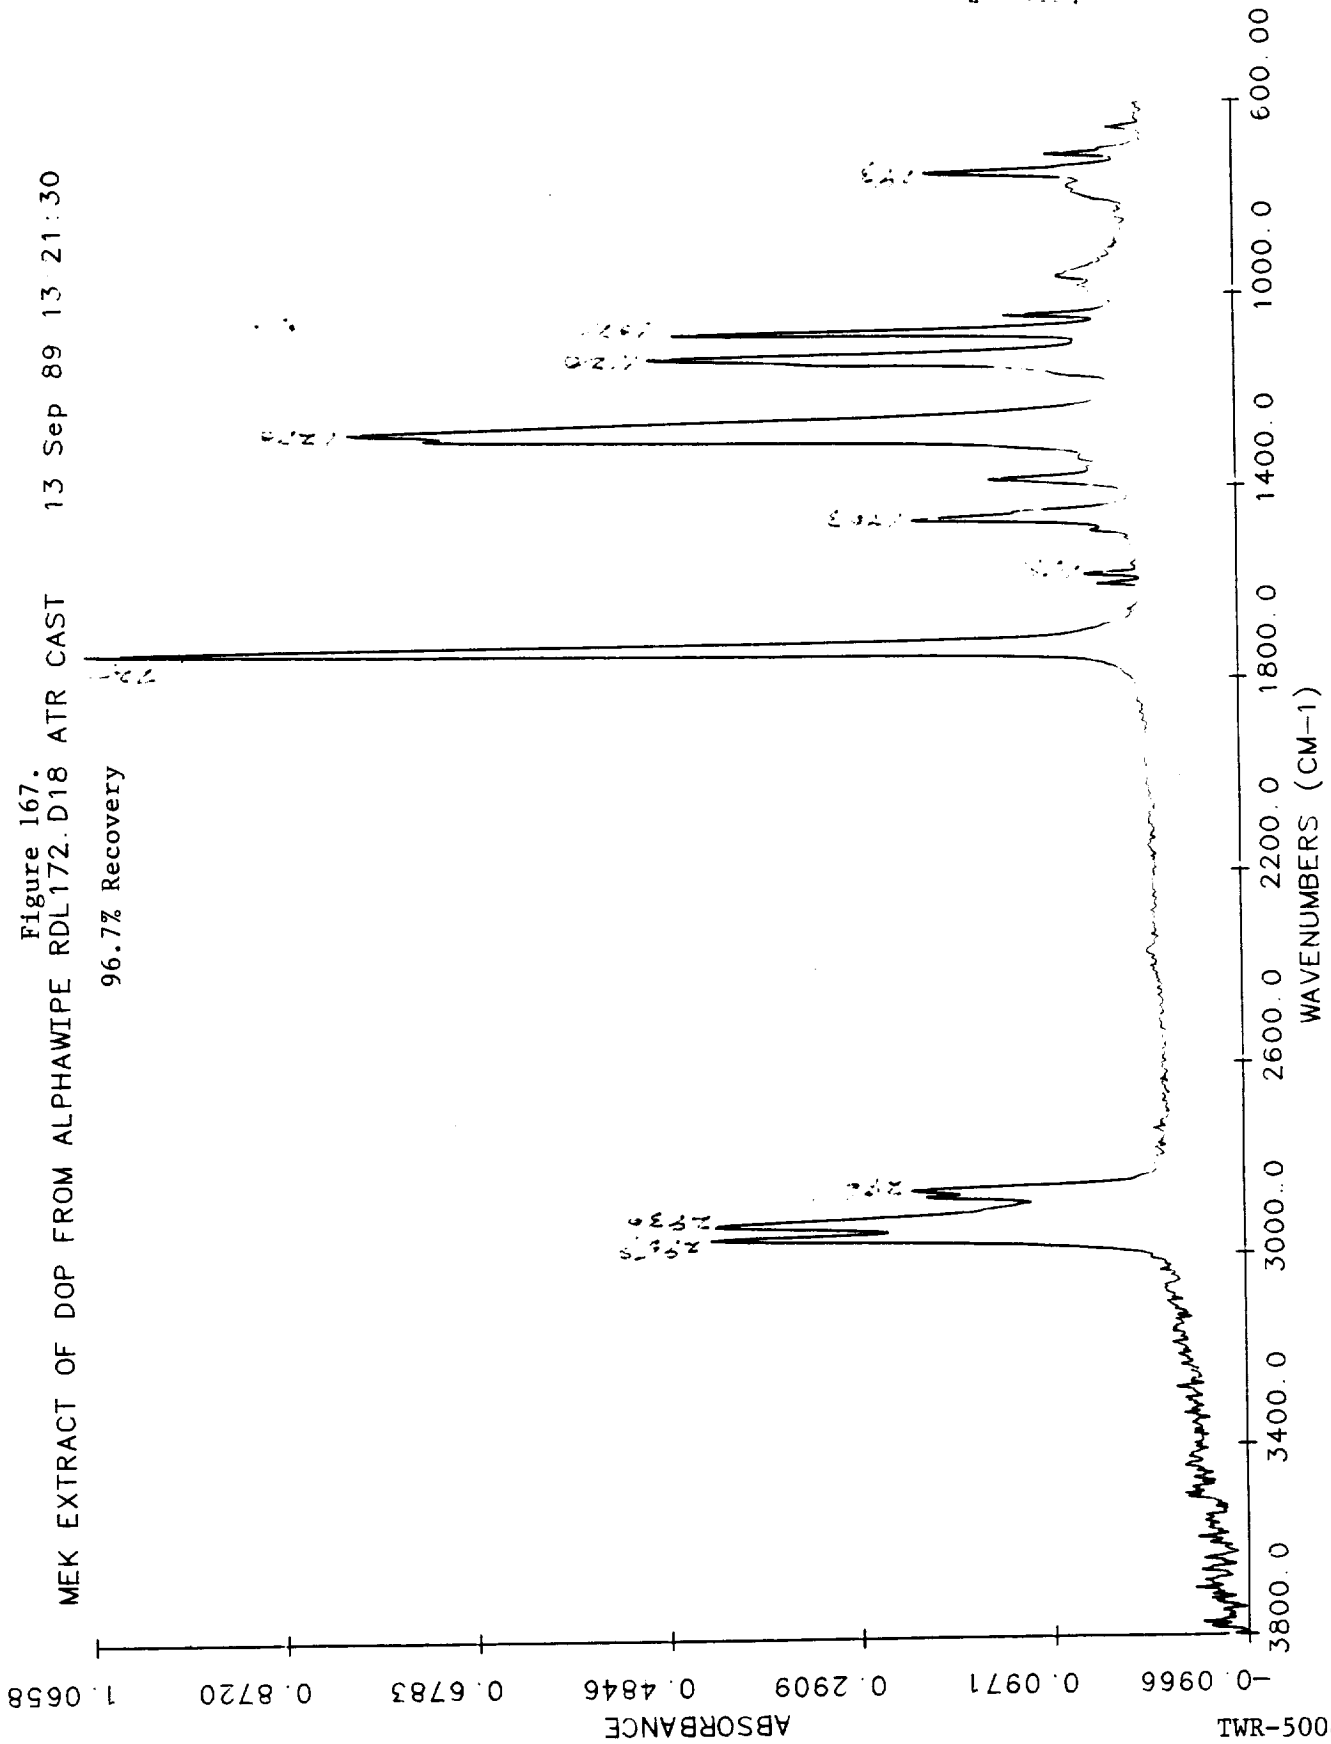

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 168.


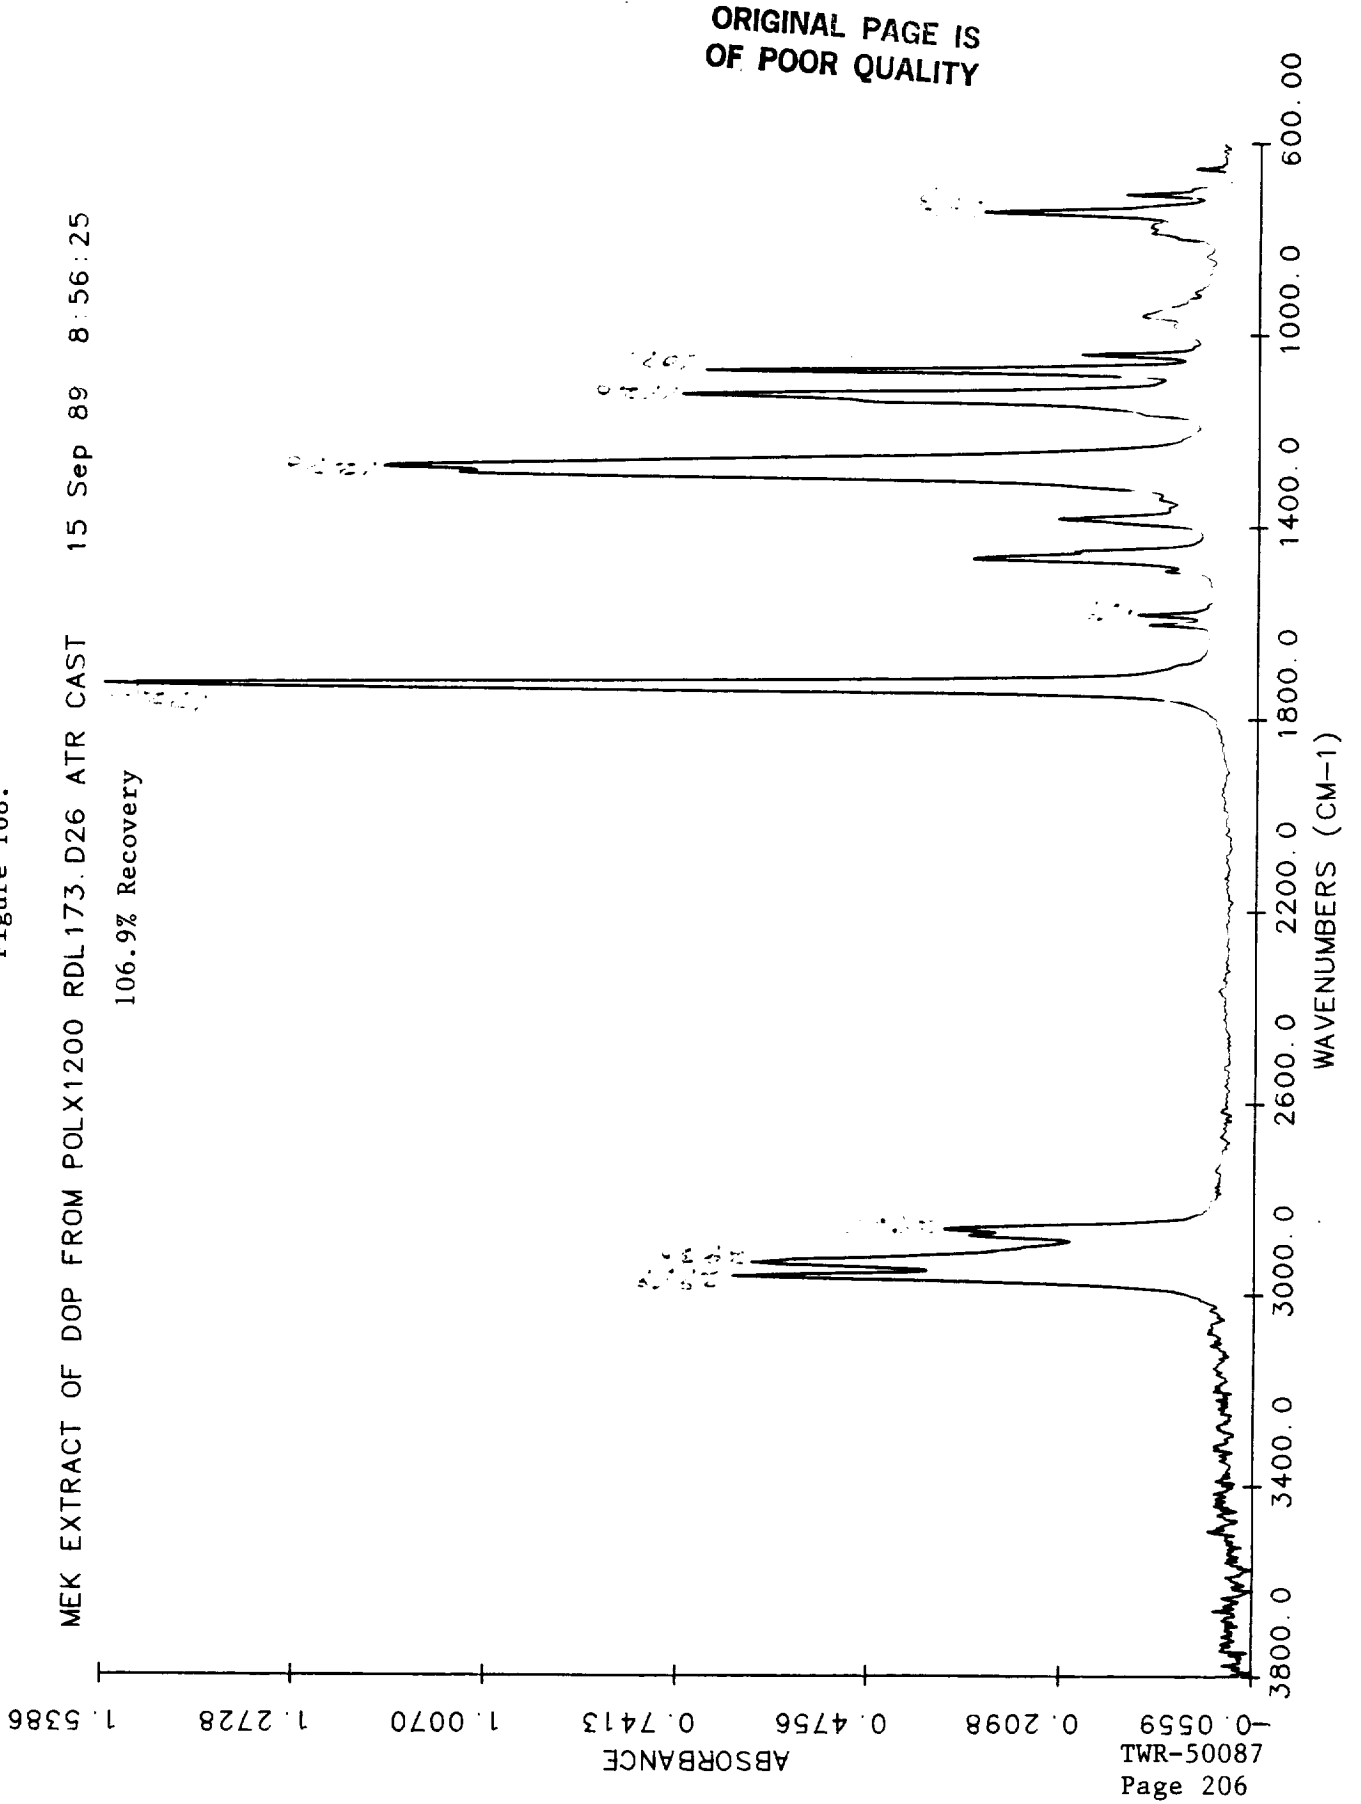


Figure 169.

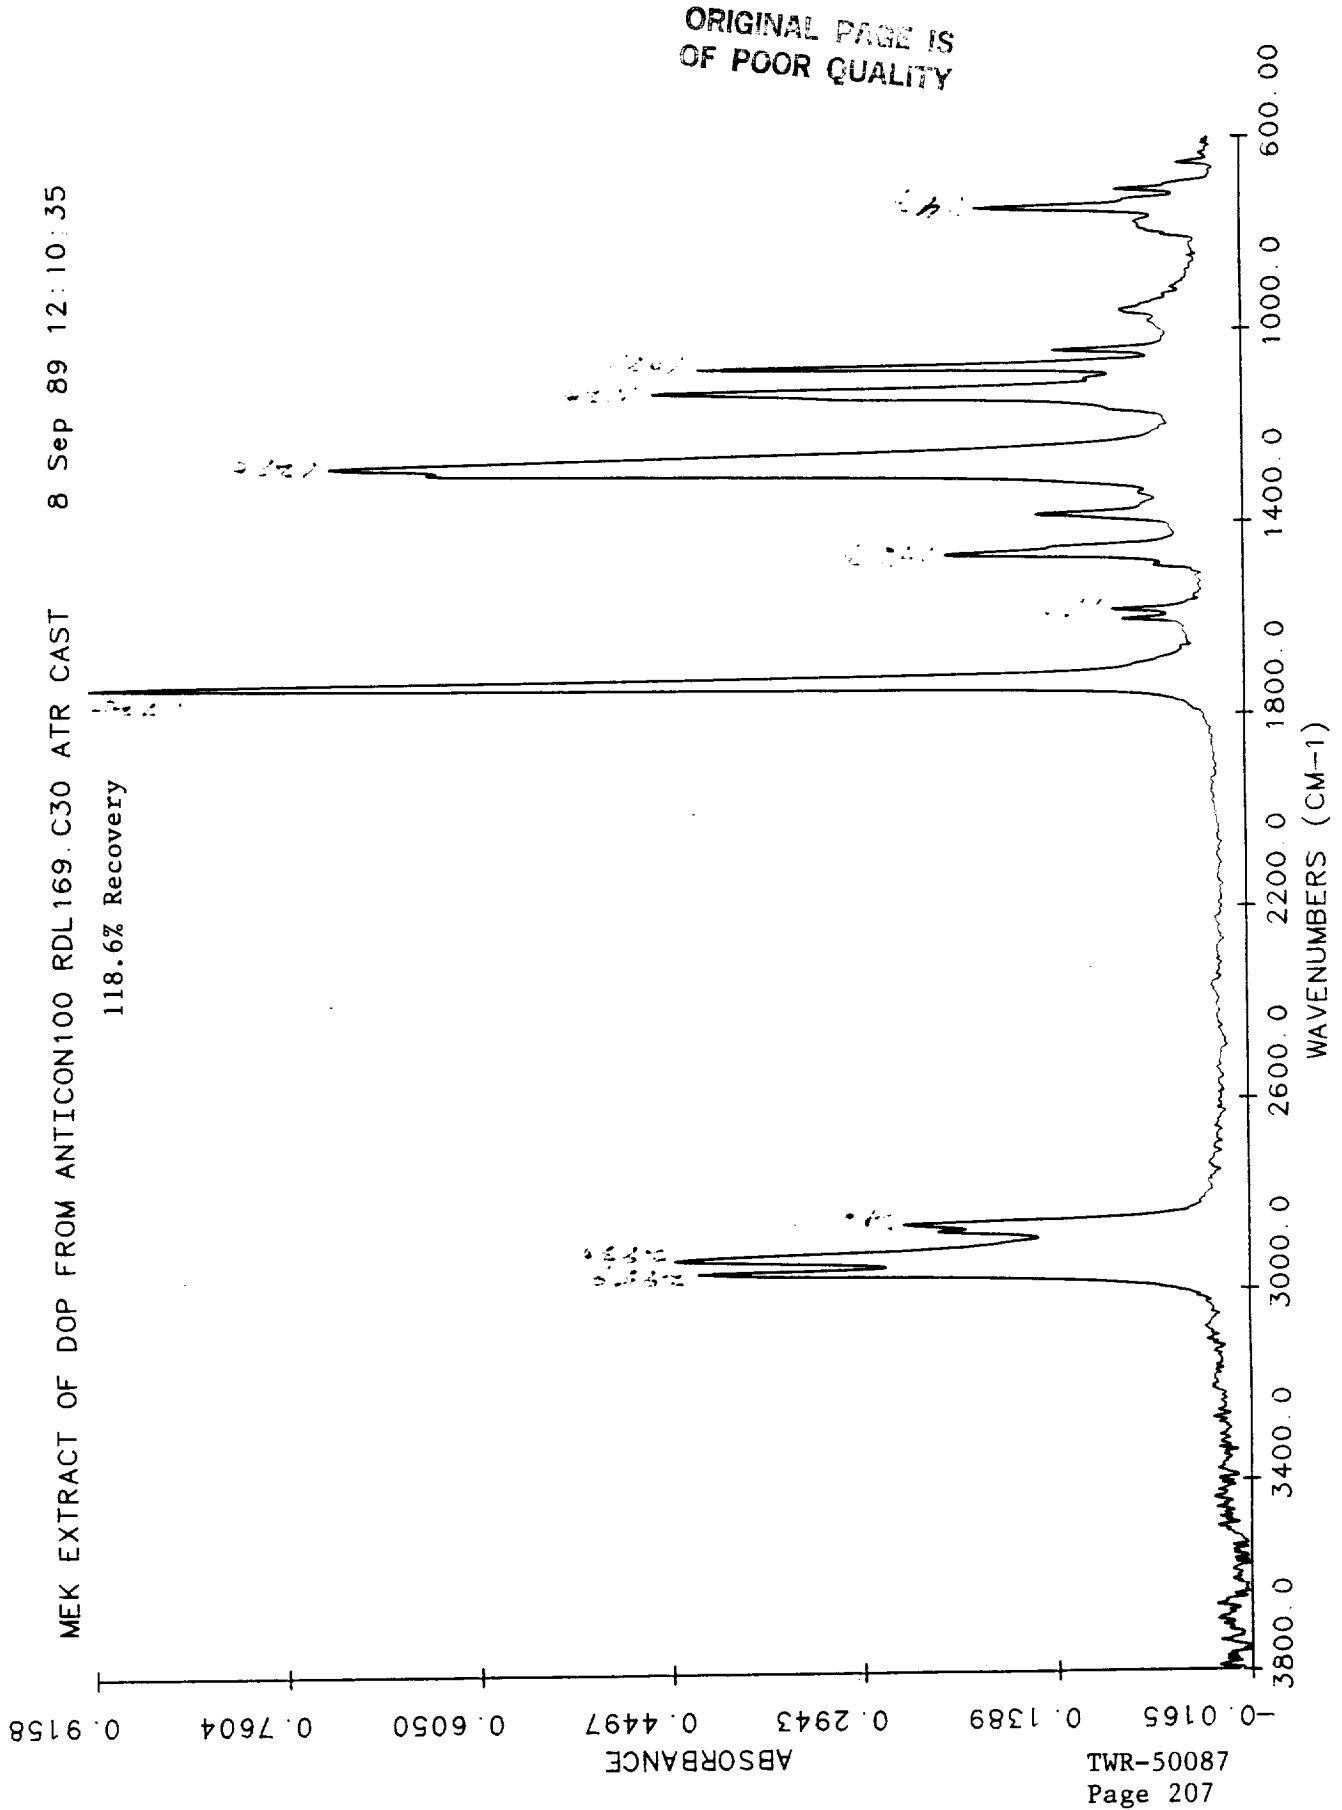

ORIGINAL PAGE IS
OF POOR QUALITY

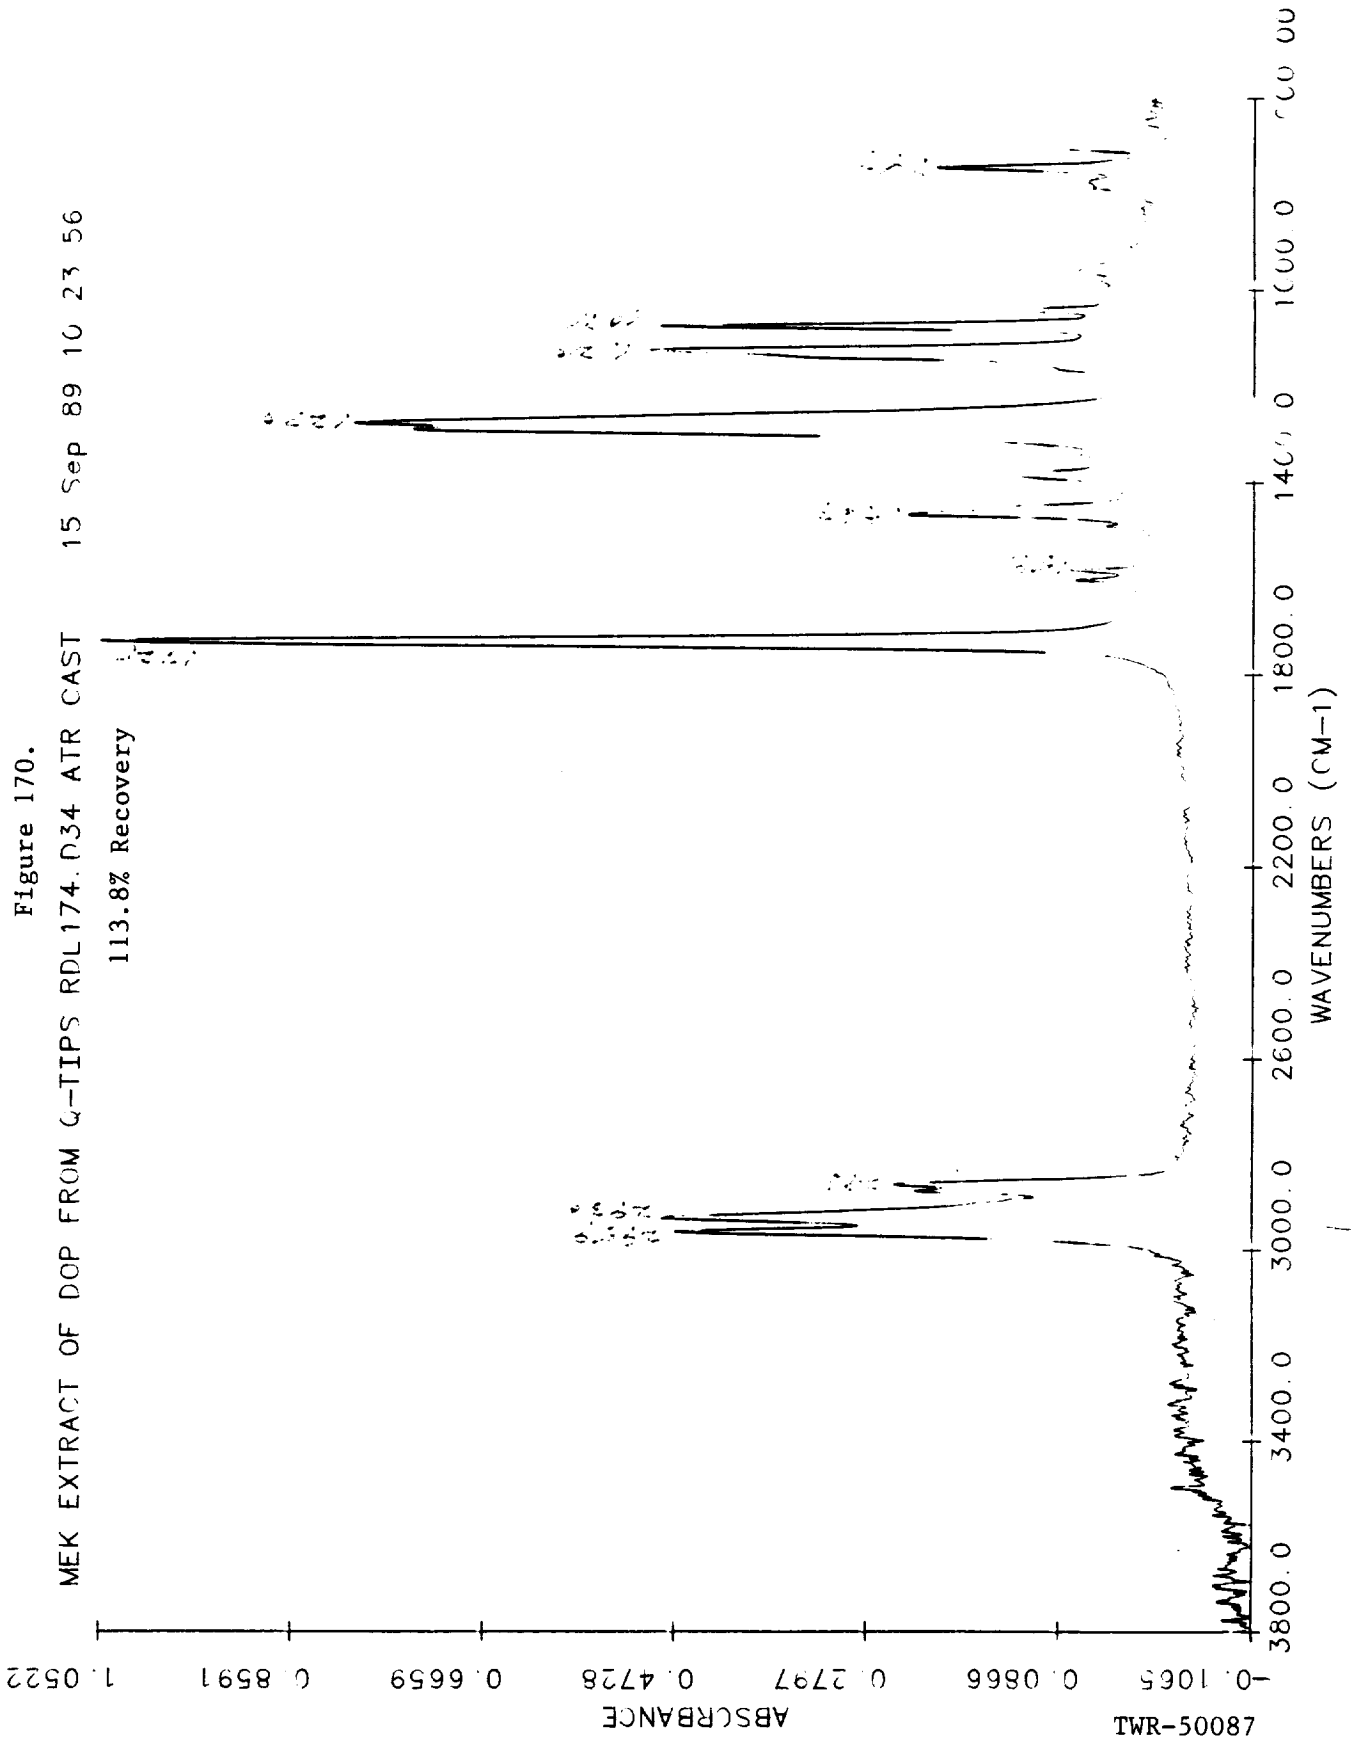


Figure 171.

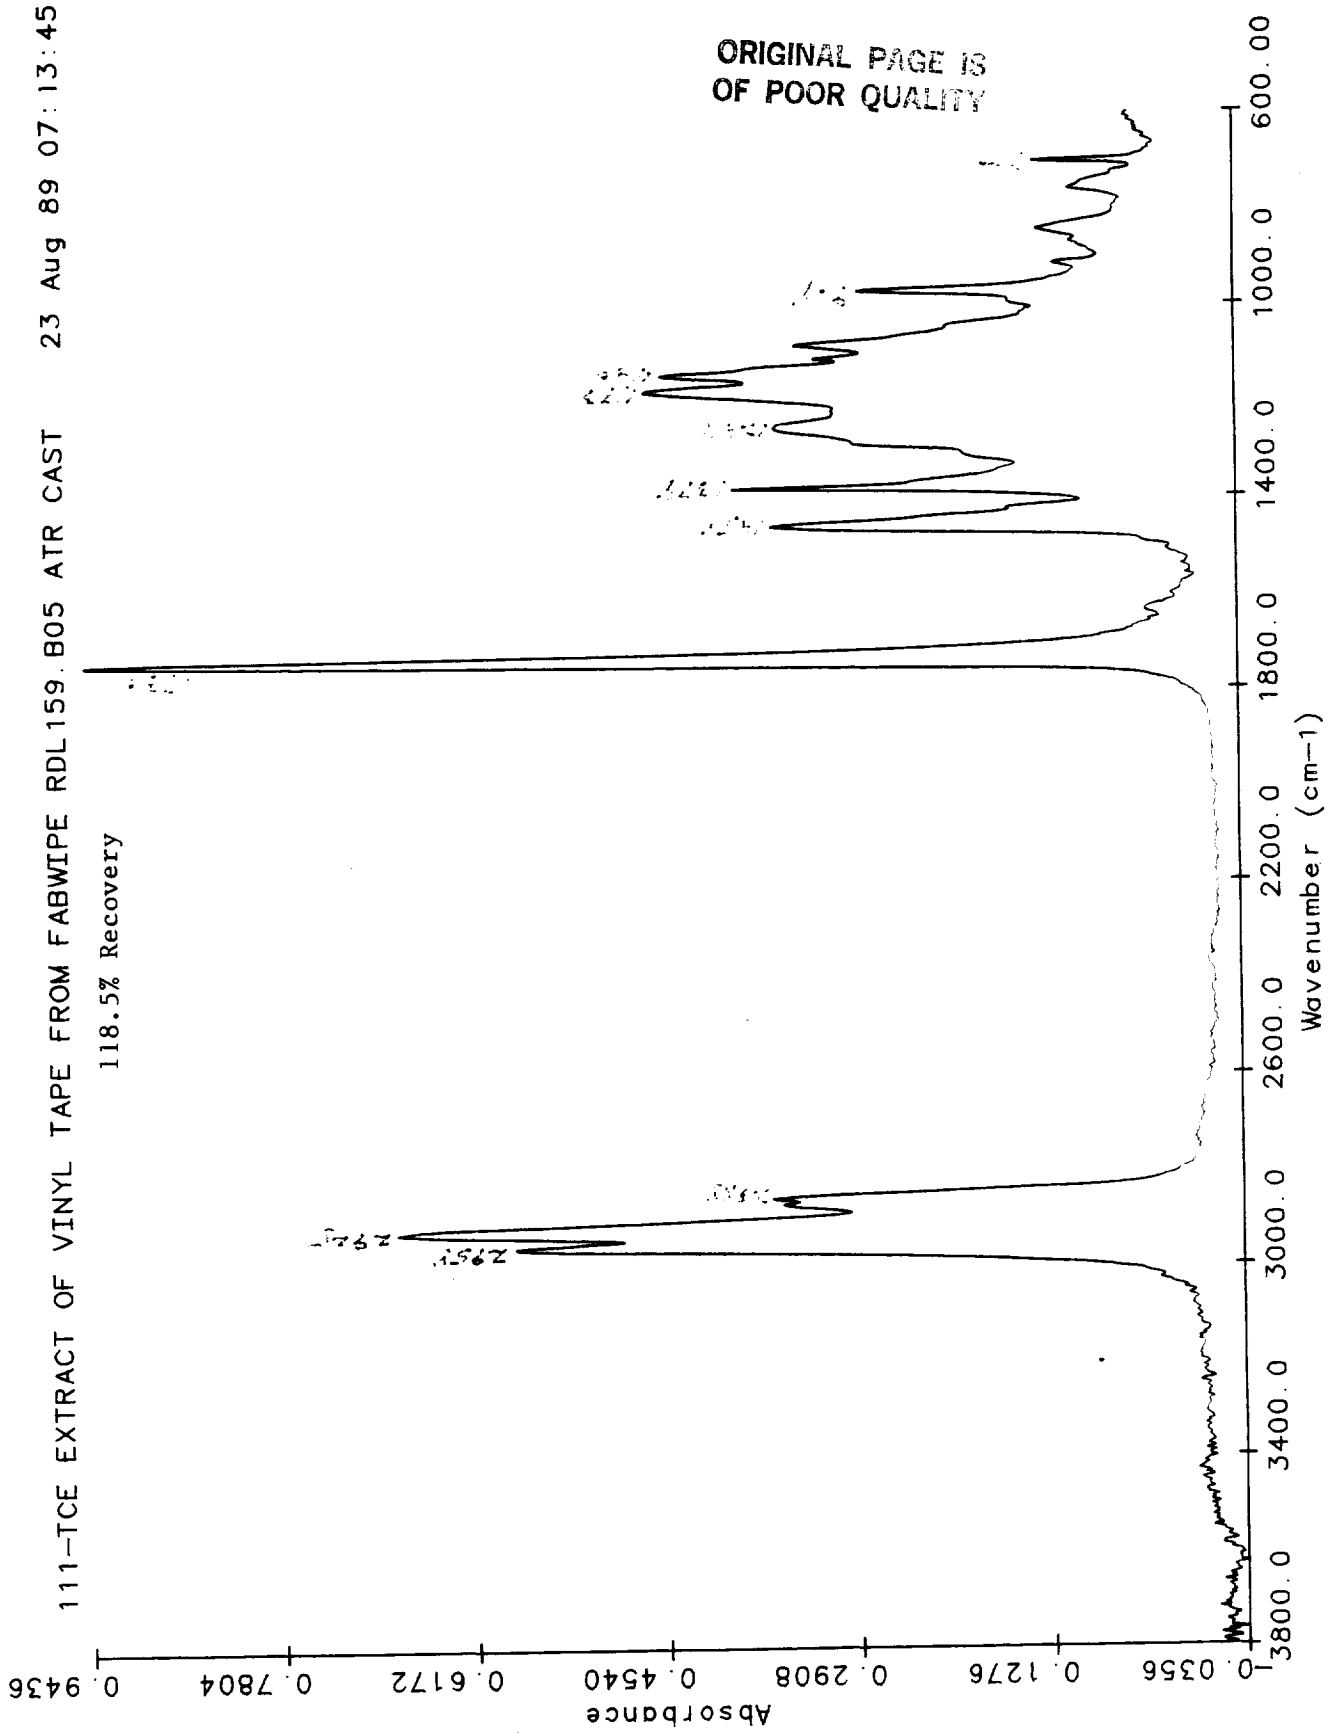


Figure 172.

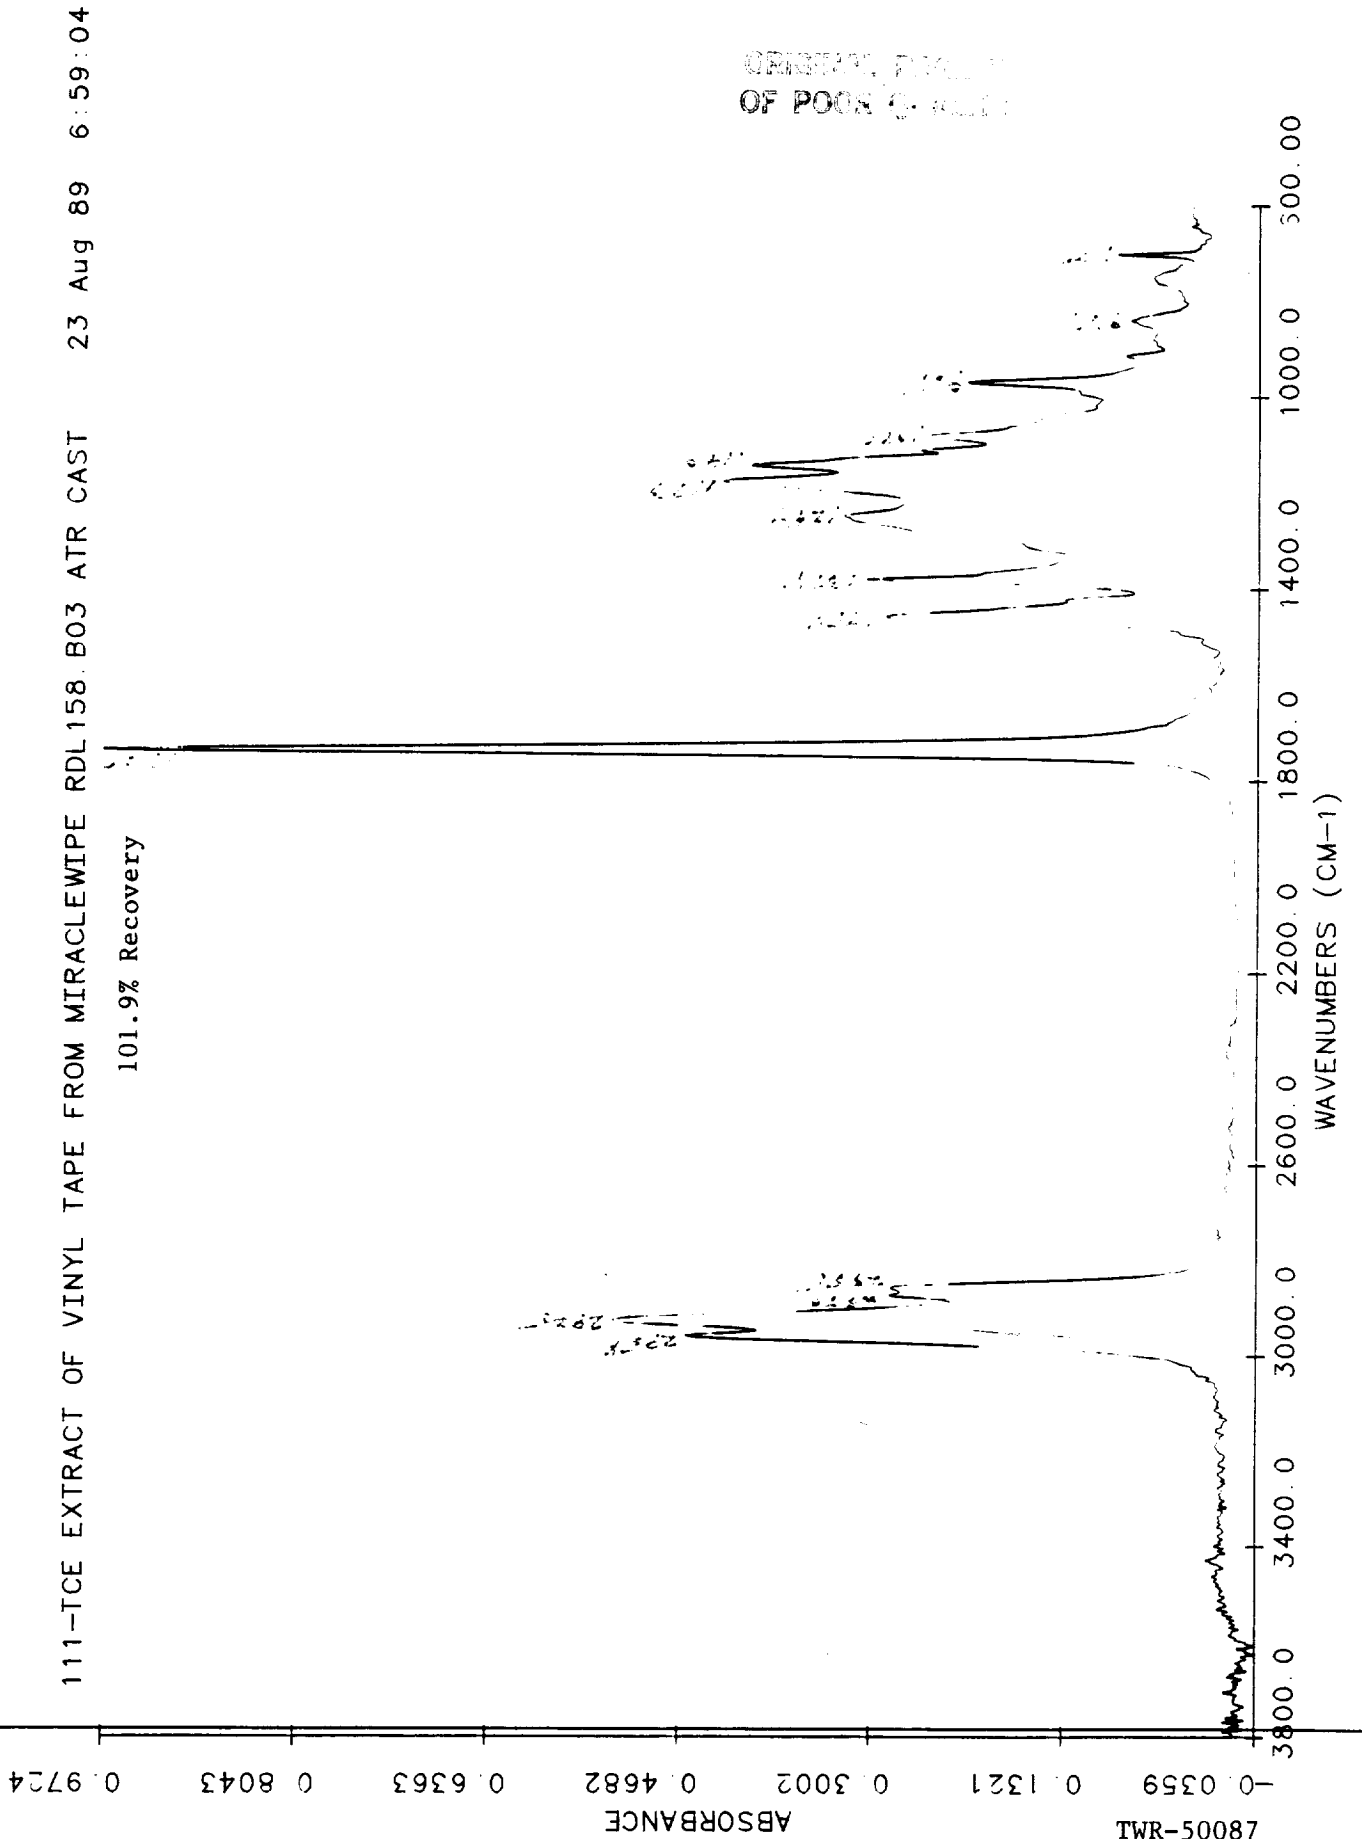


Figure 173.

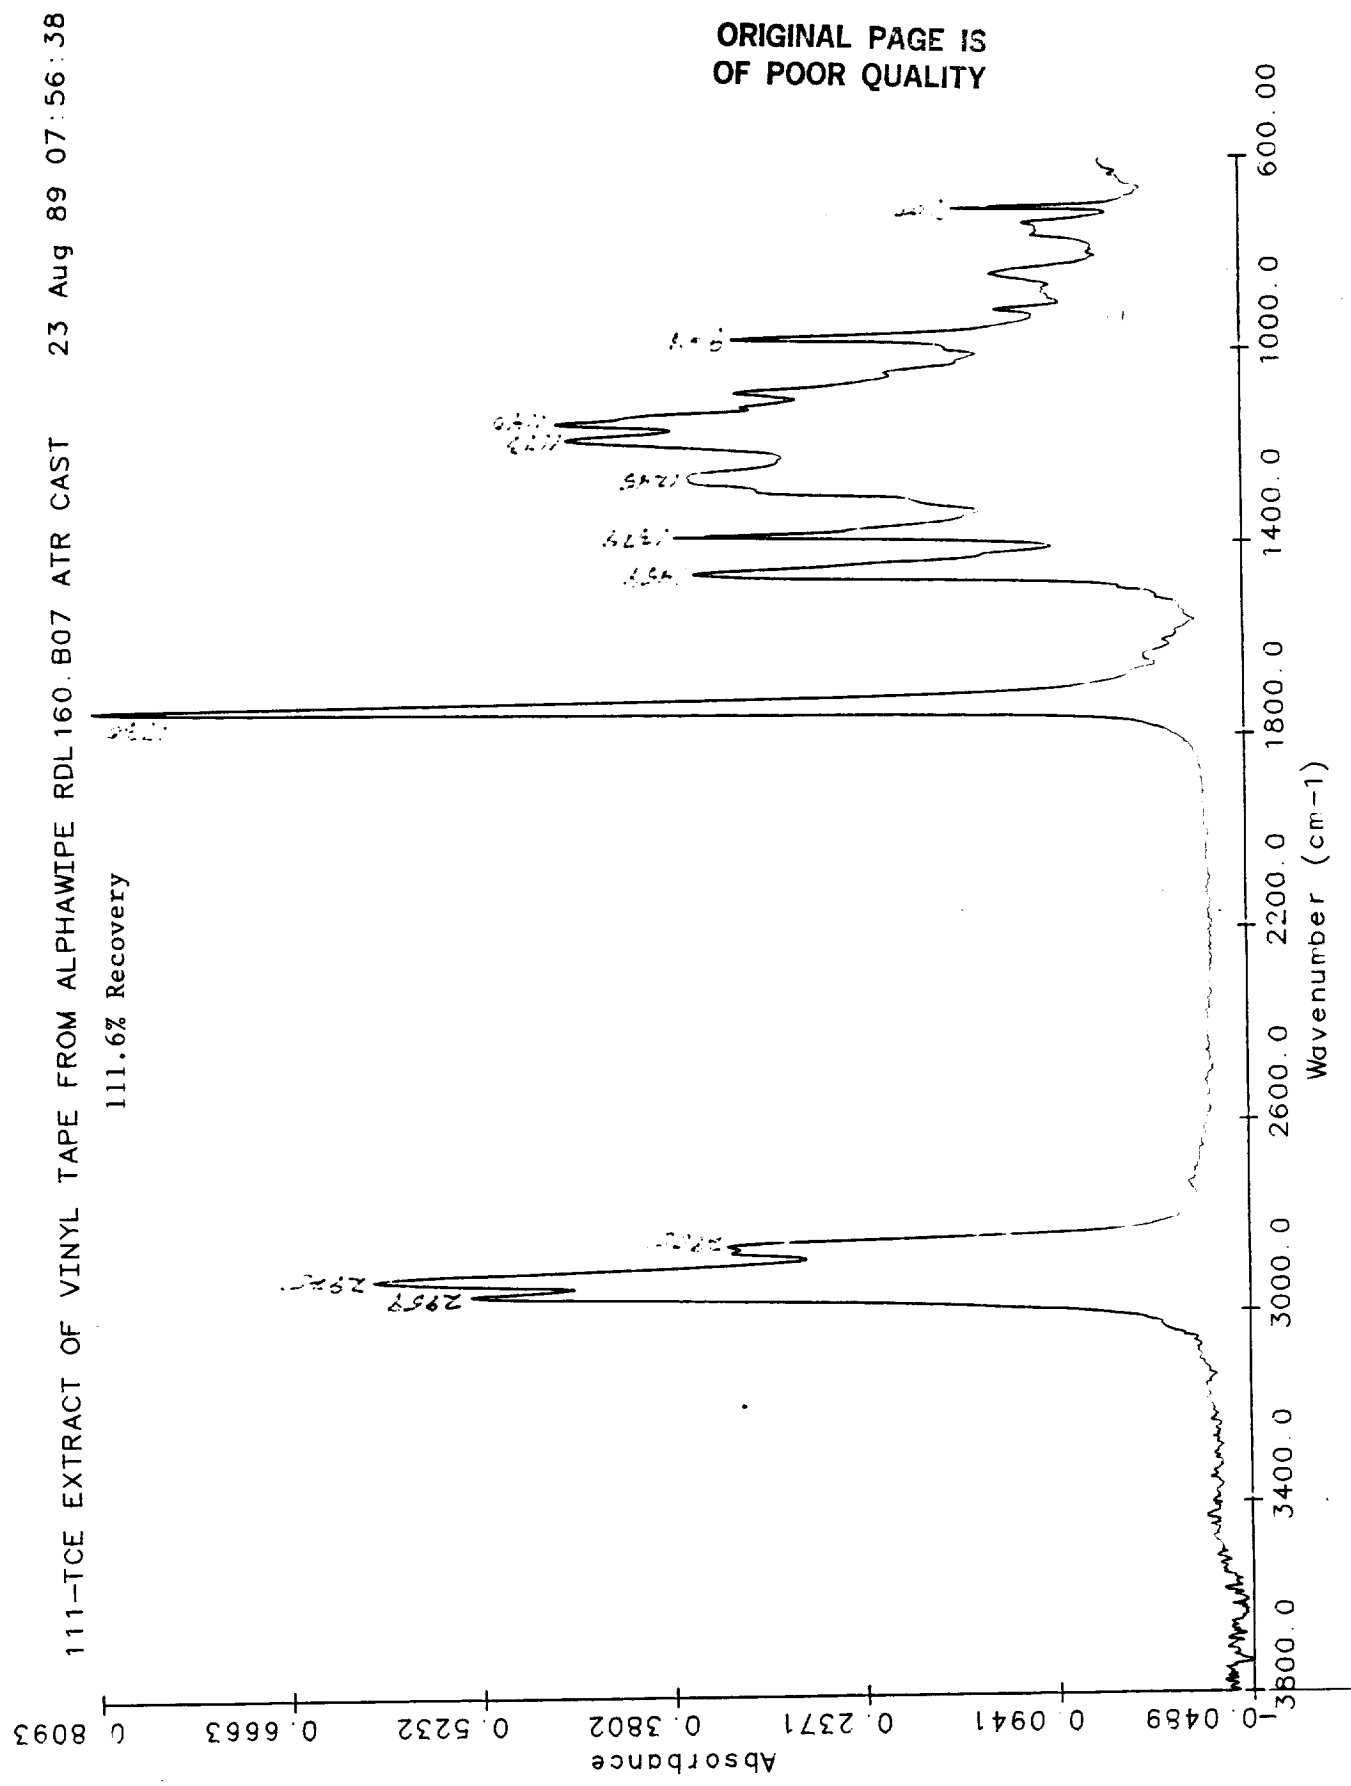












Figure 179.

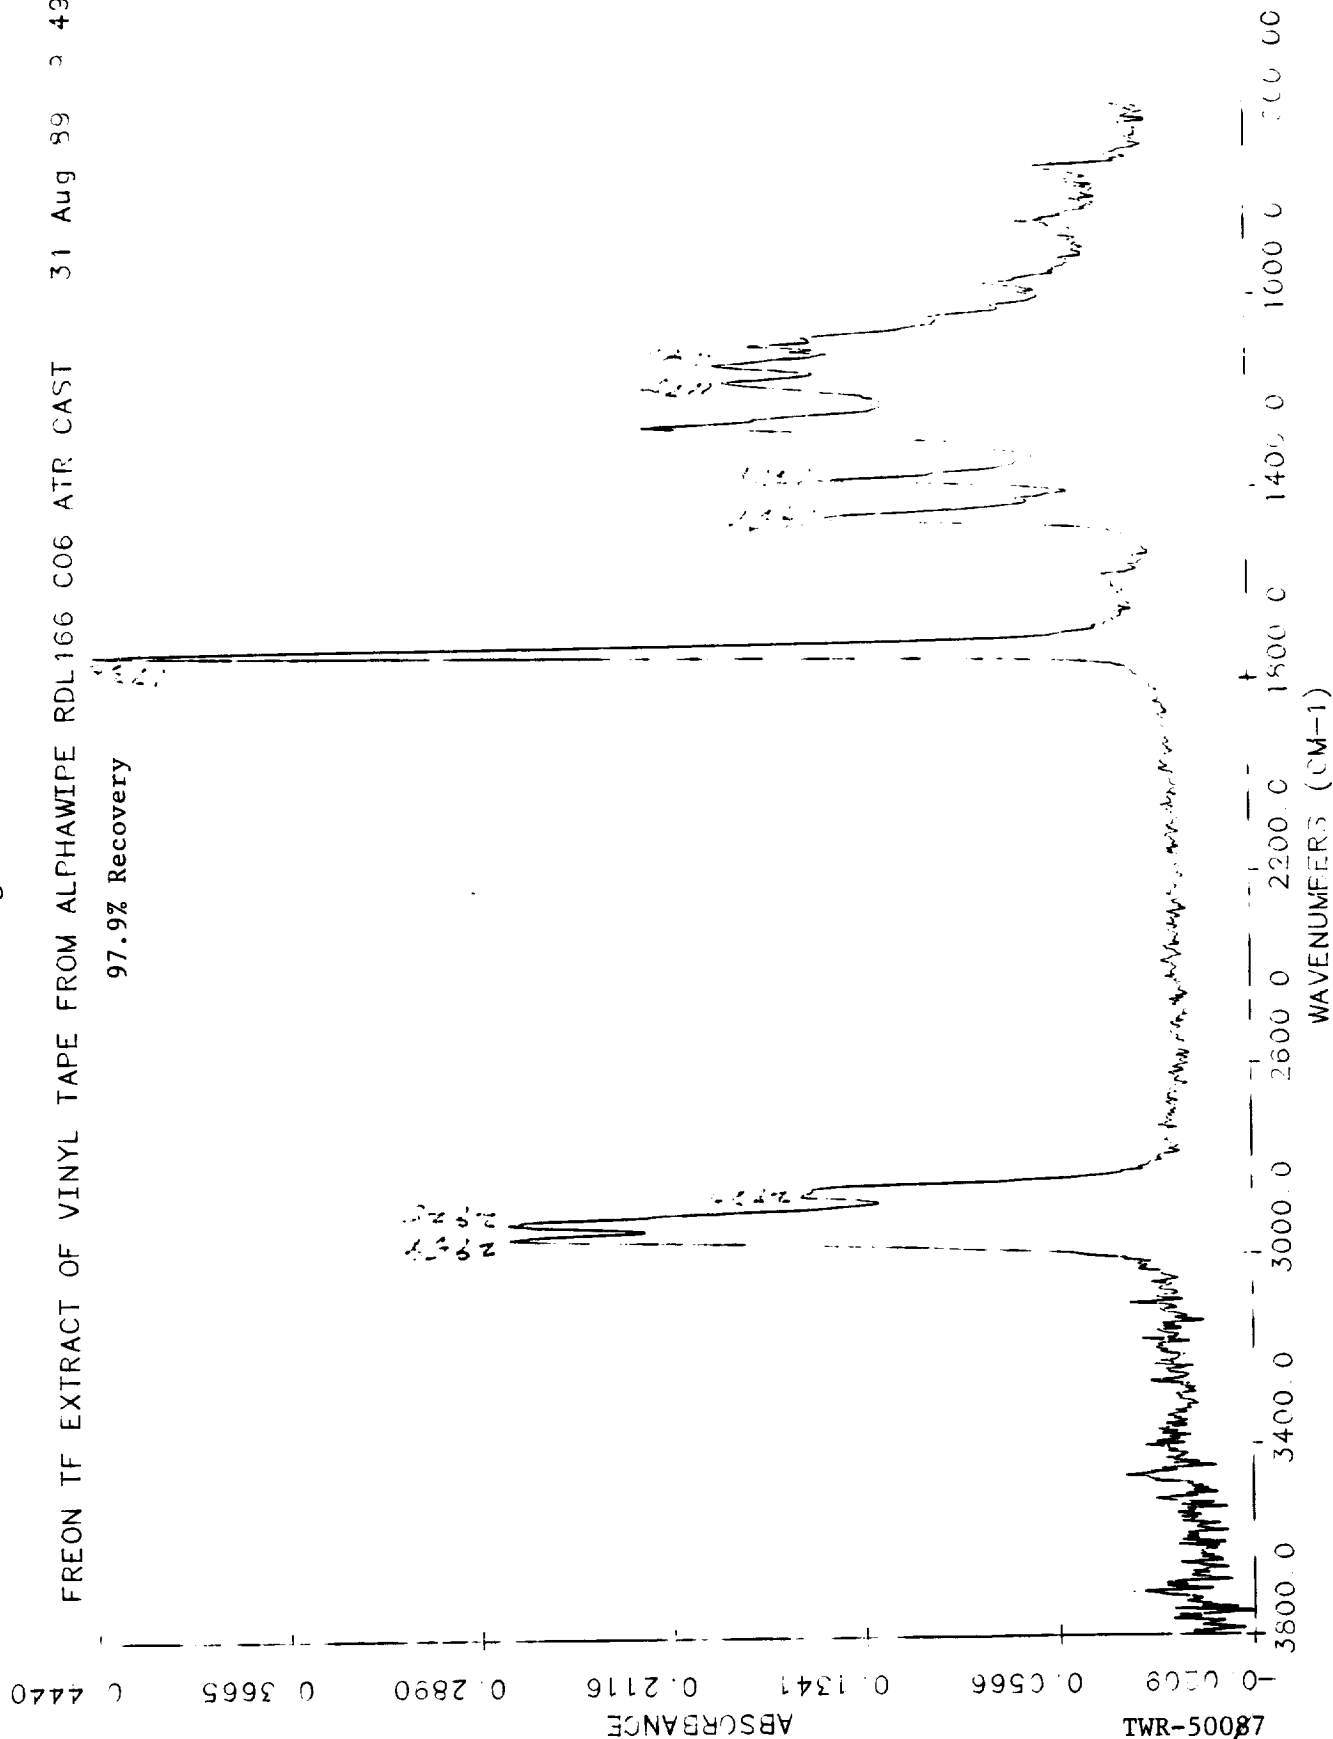


Figure 180.



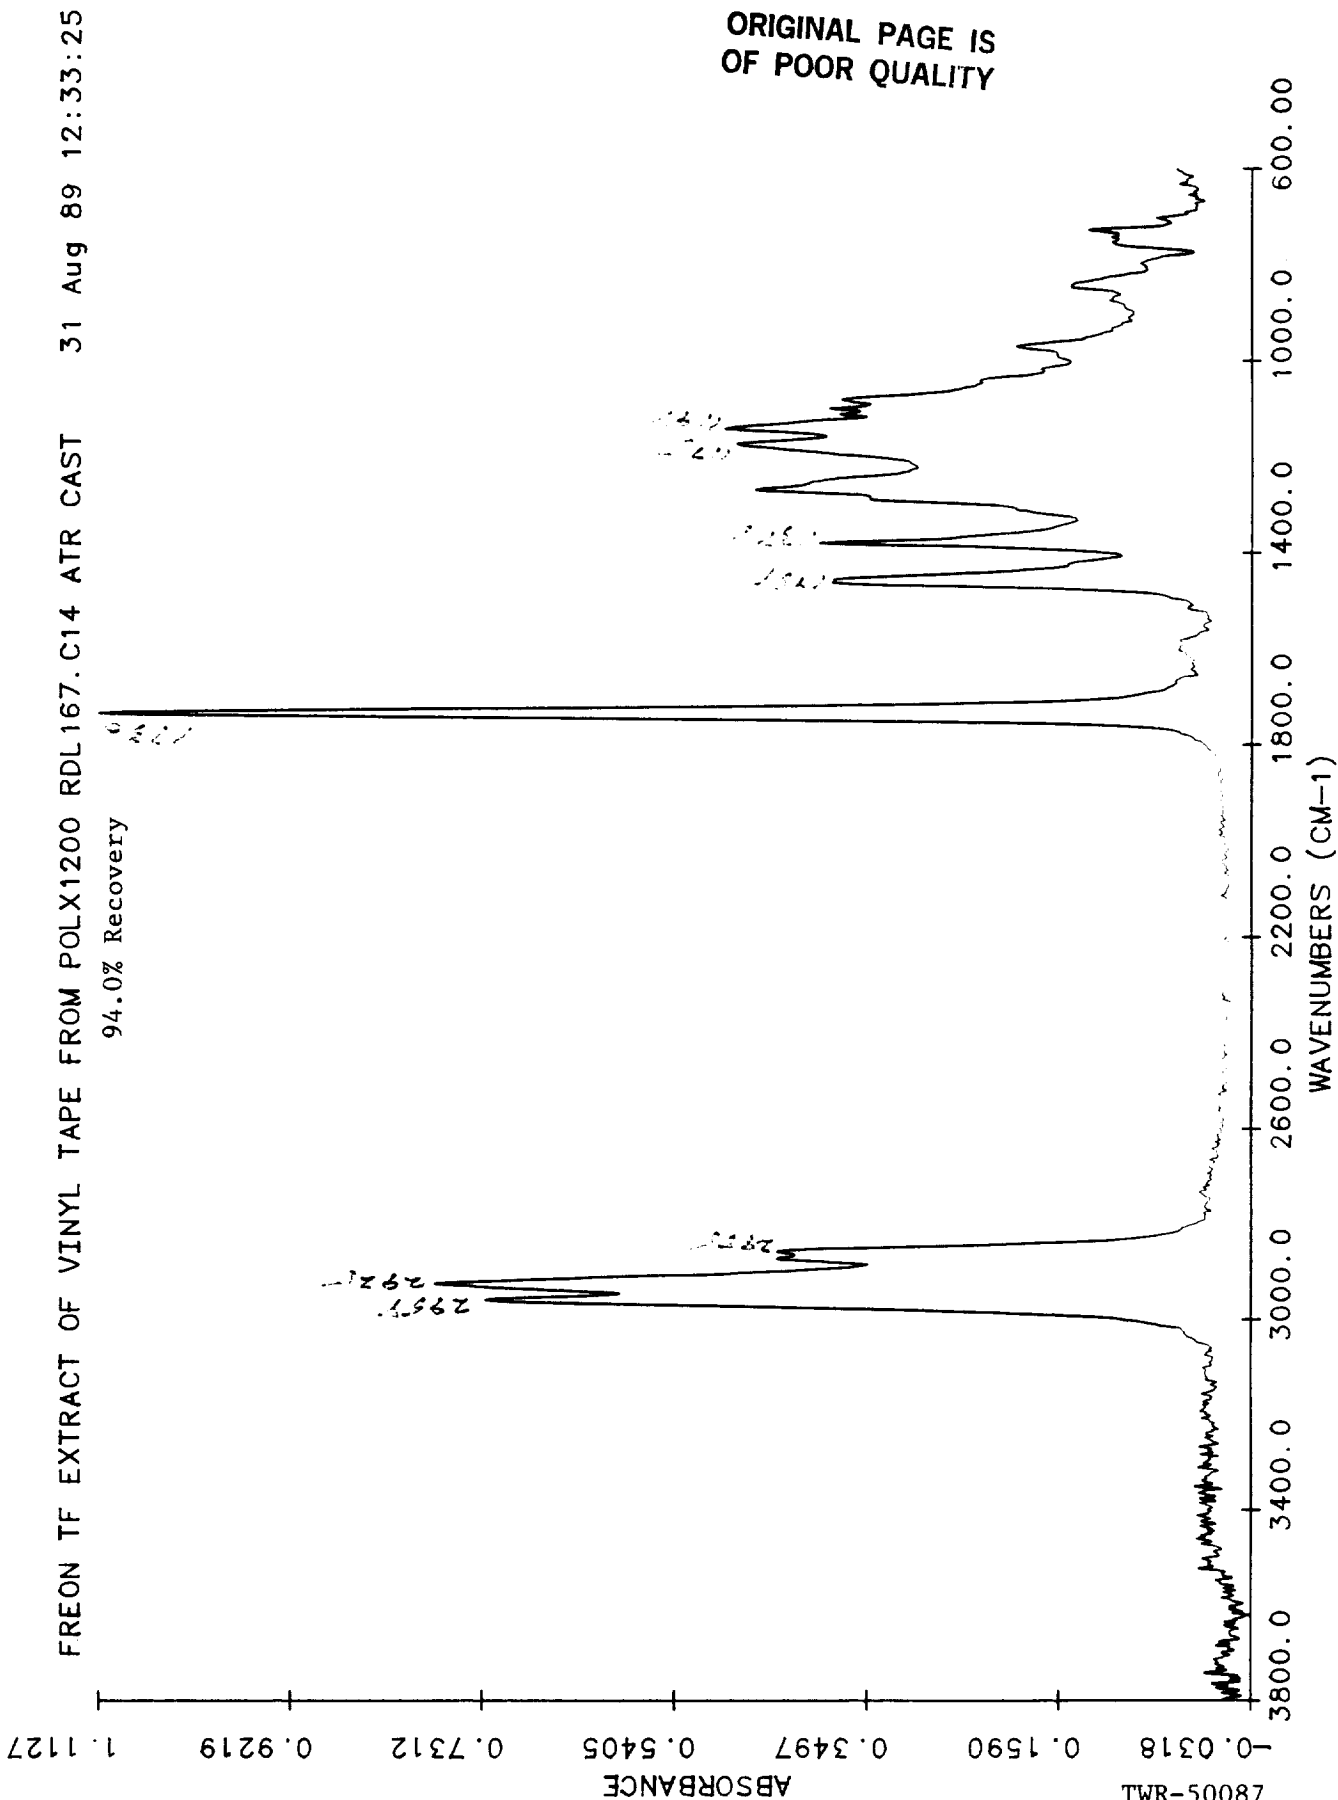


Figure 181.

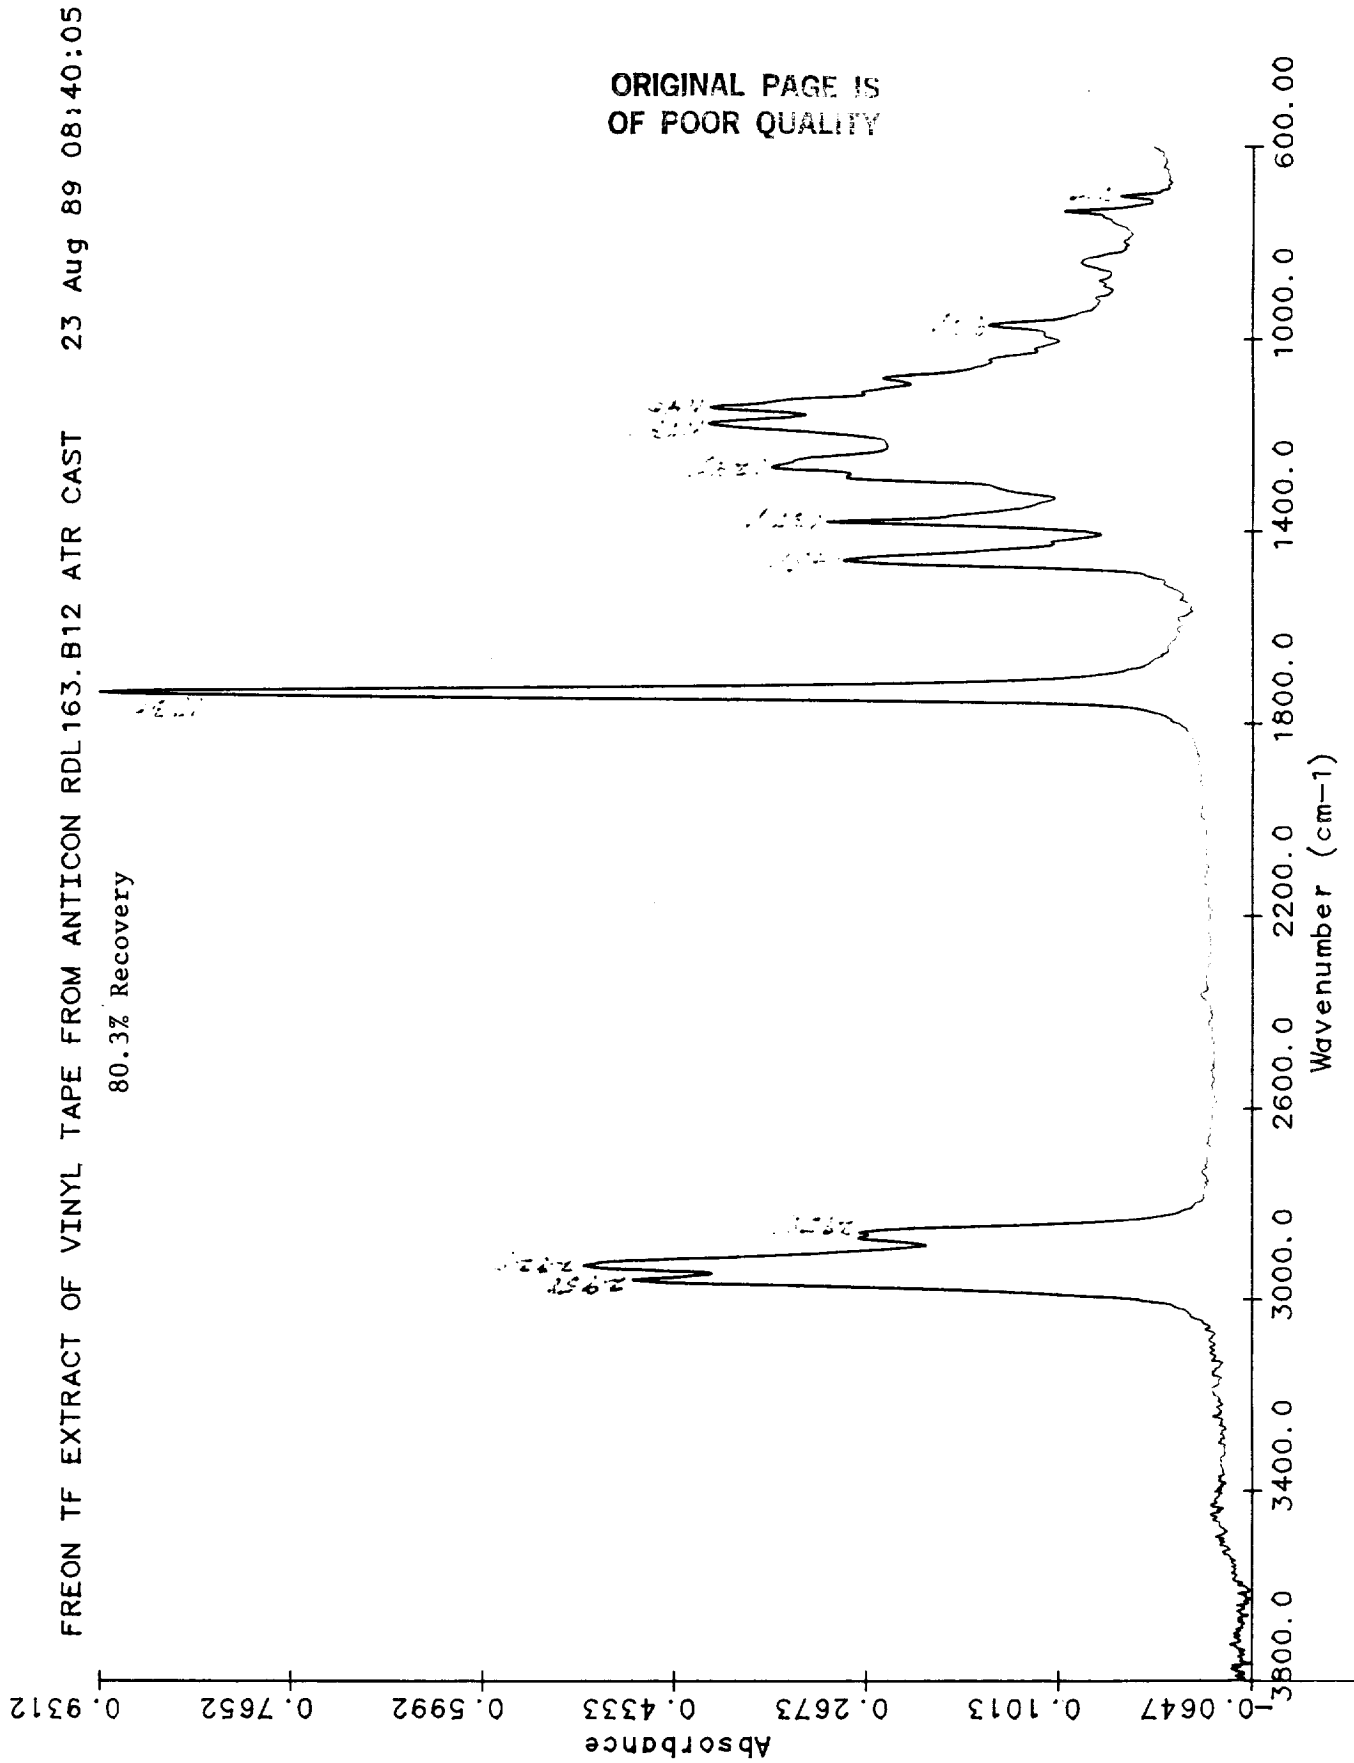

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 182.

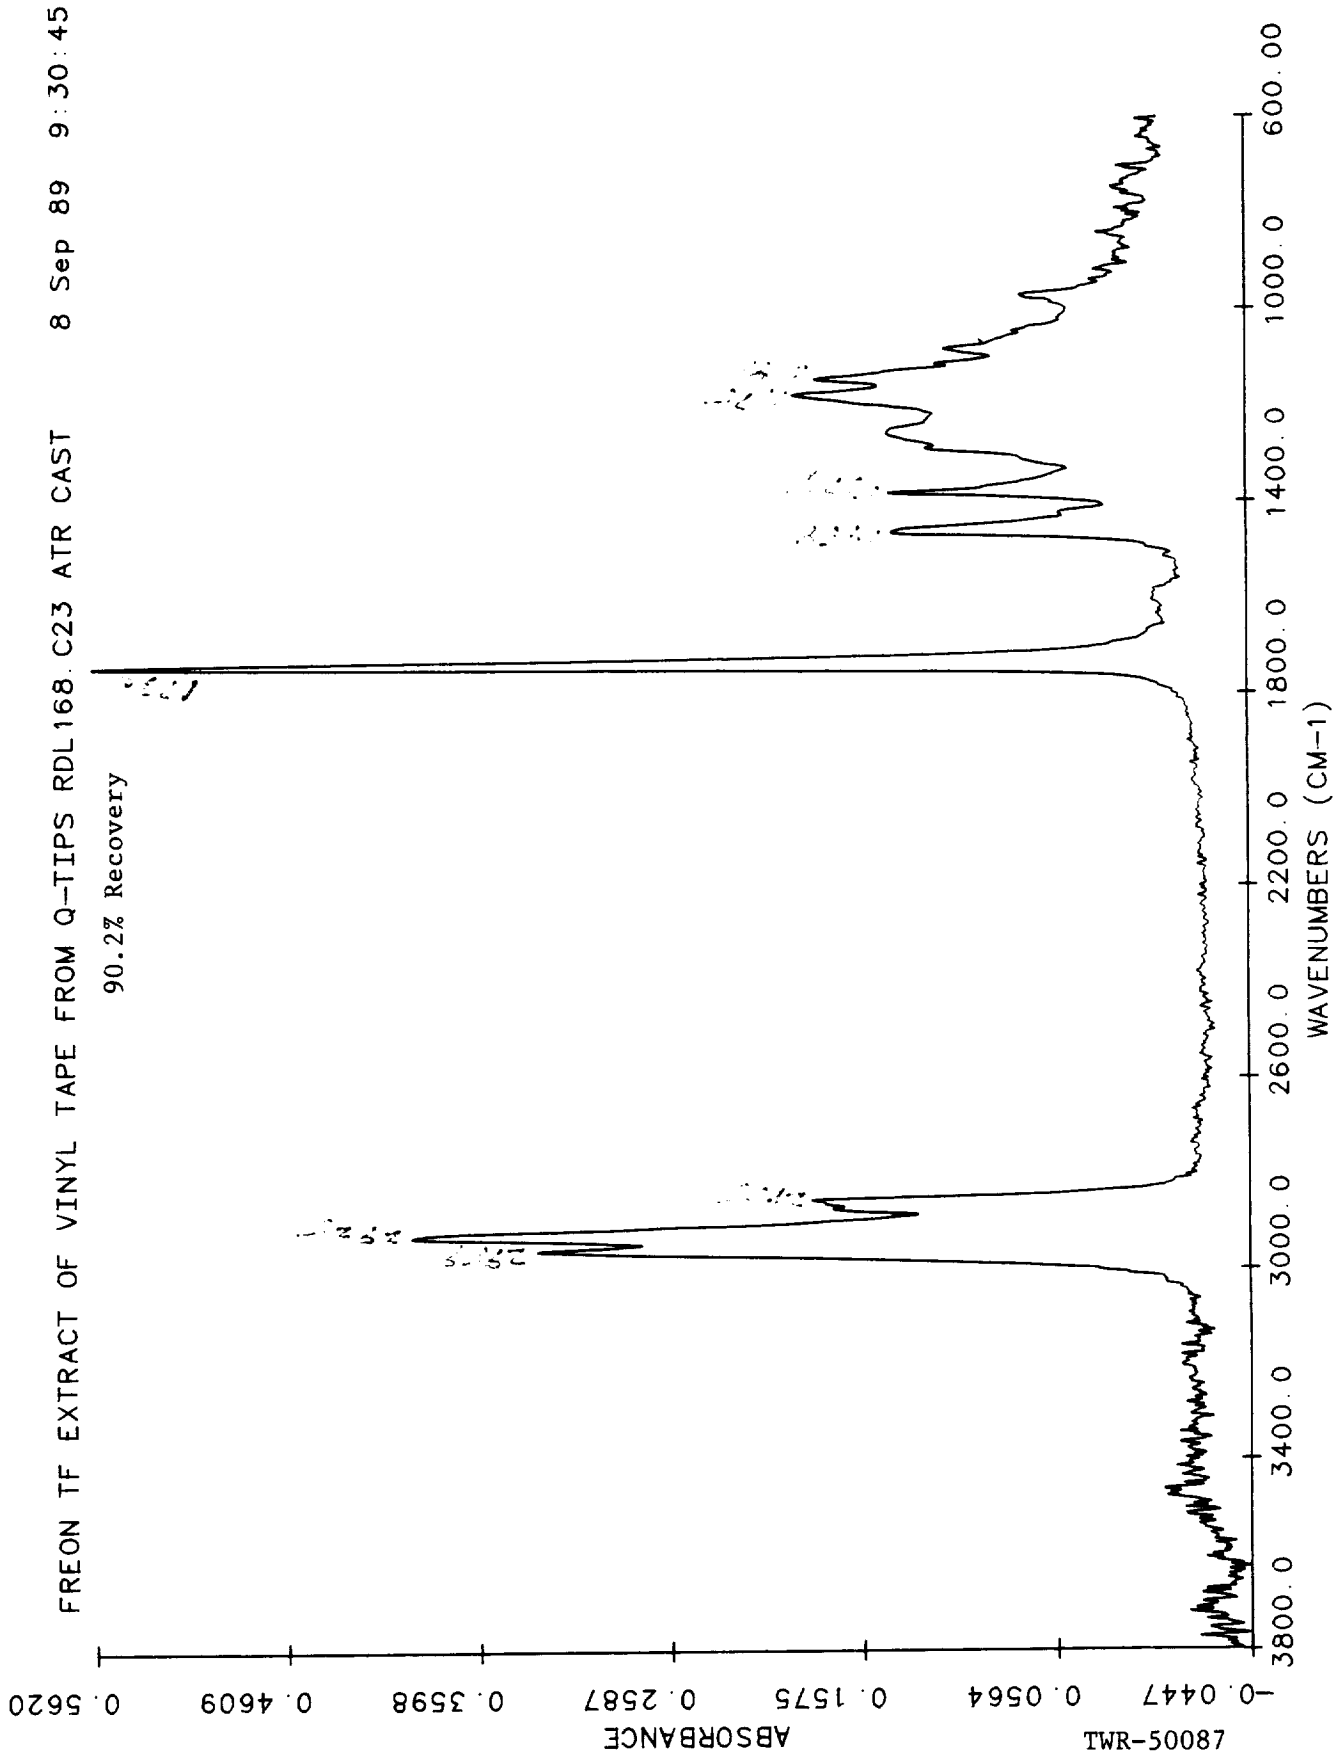

ORIGINAL PAGE IS
OF POOR QUALITY



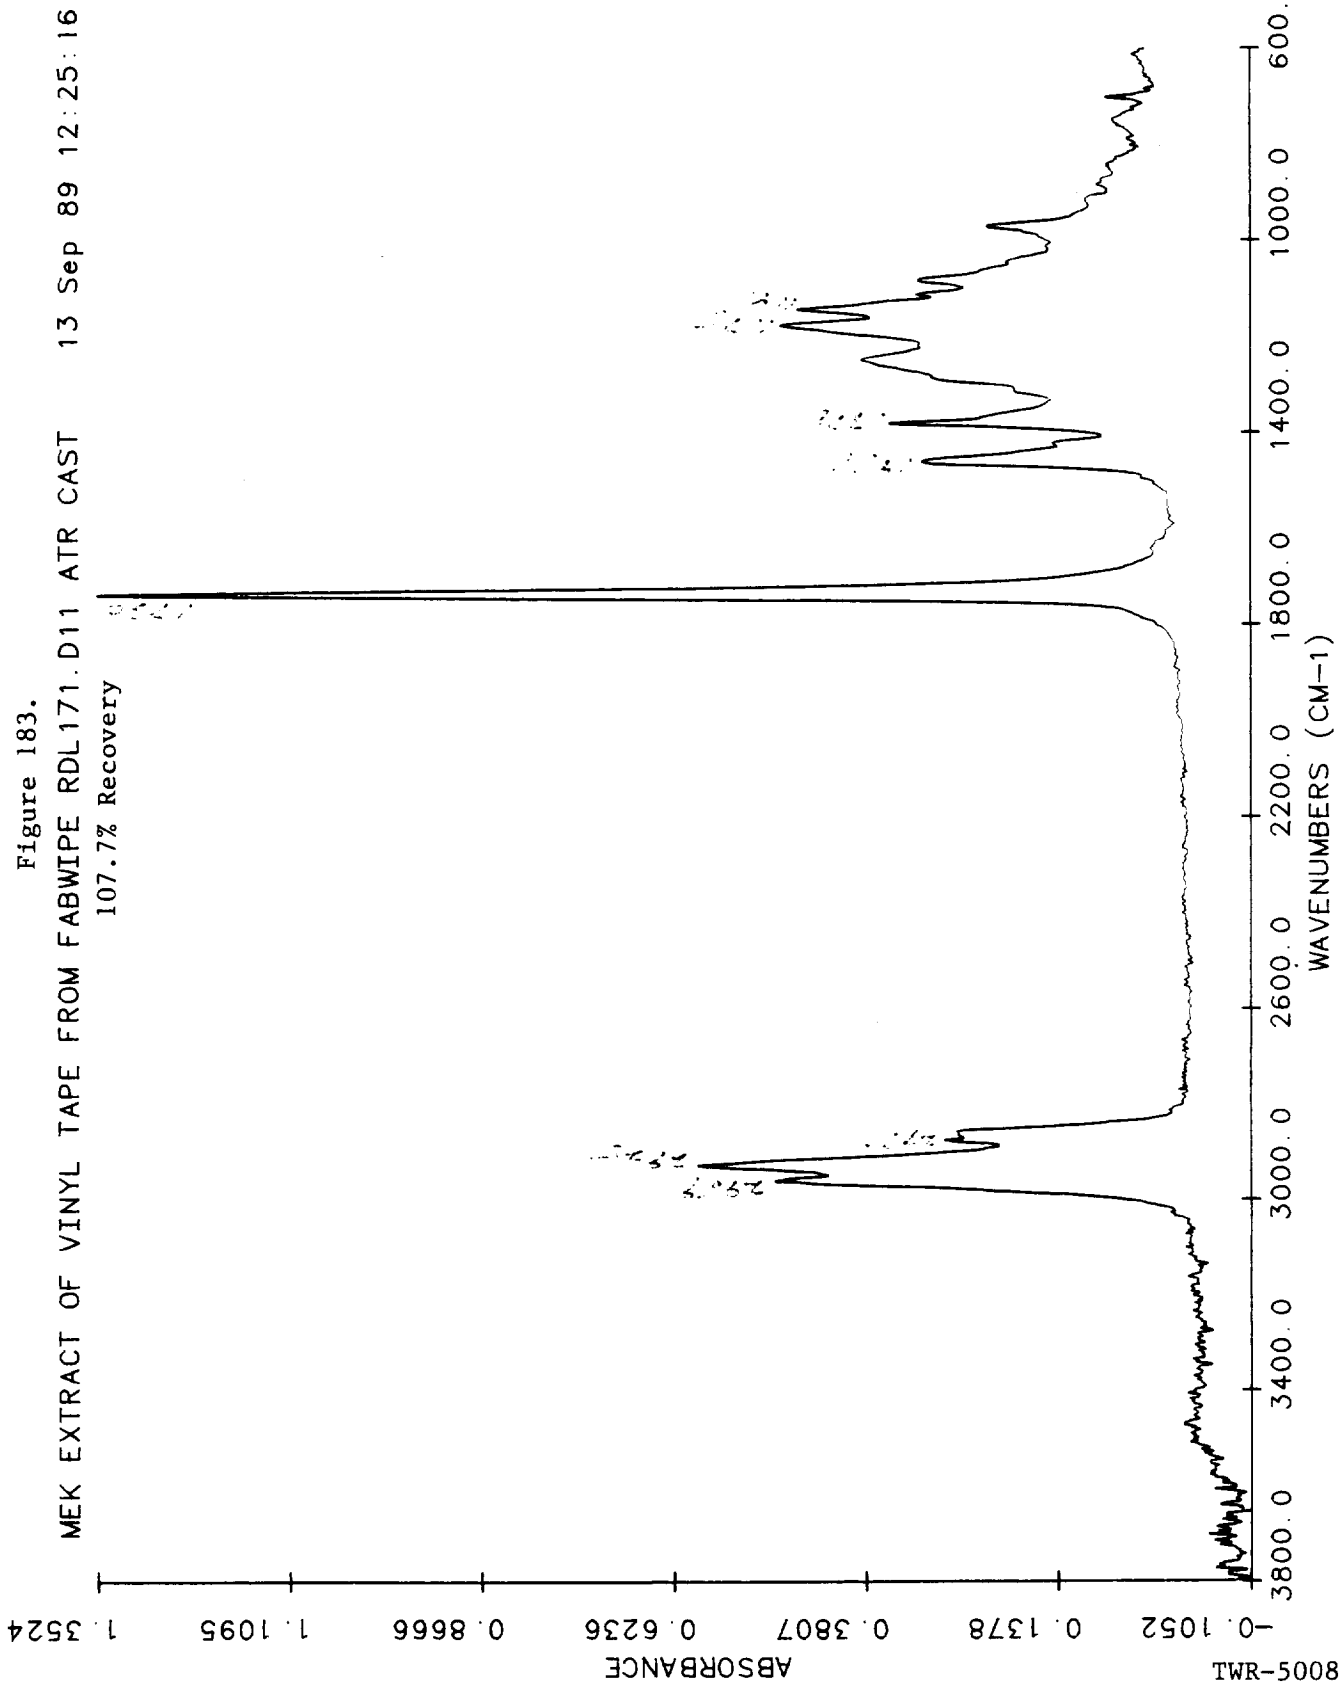



Figure 184.

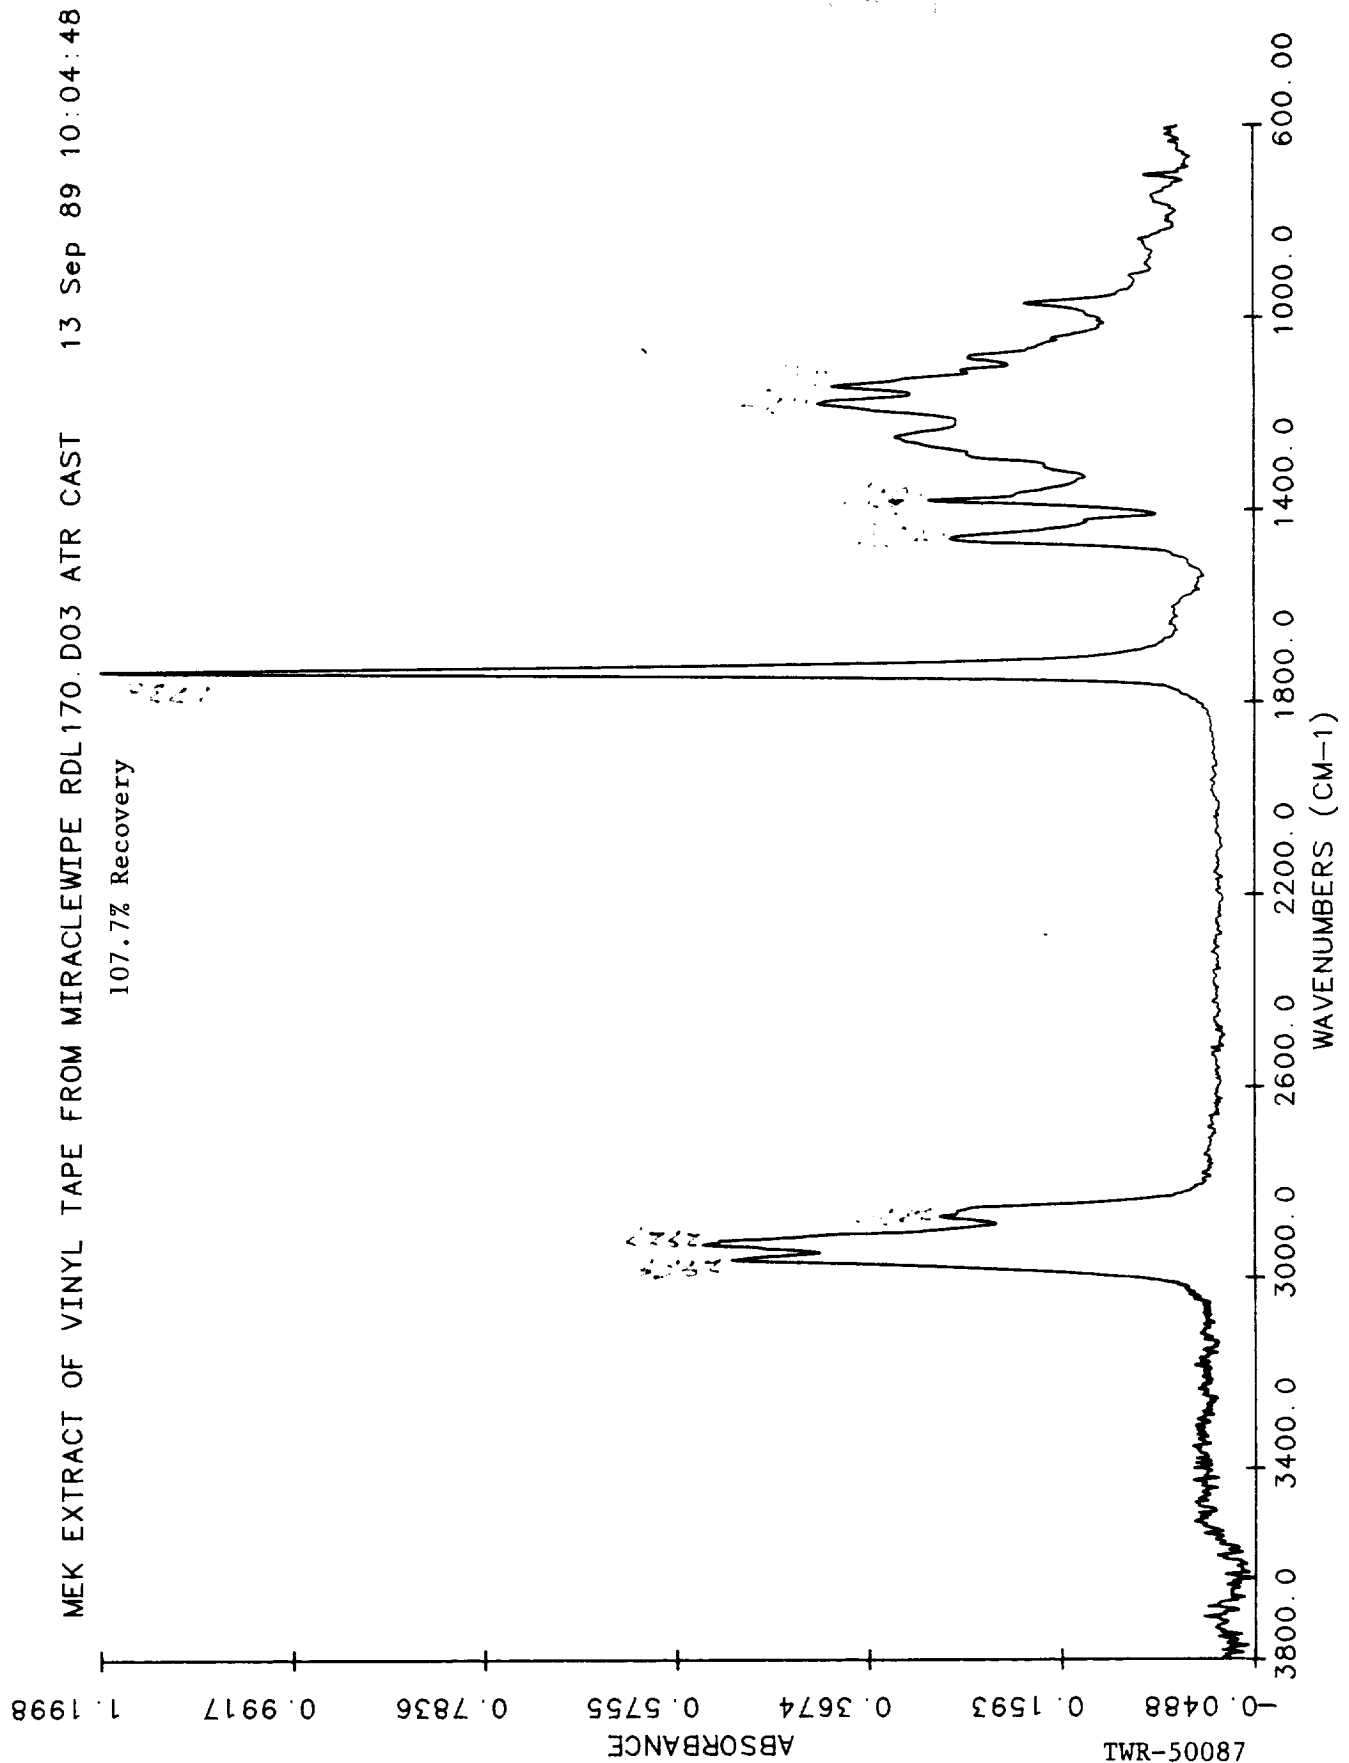


ORIGINAL PAGE IS
OF POOR QUALITY

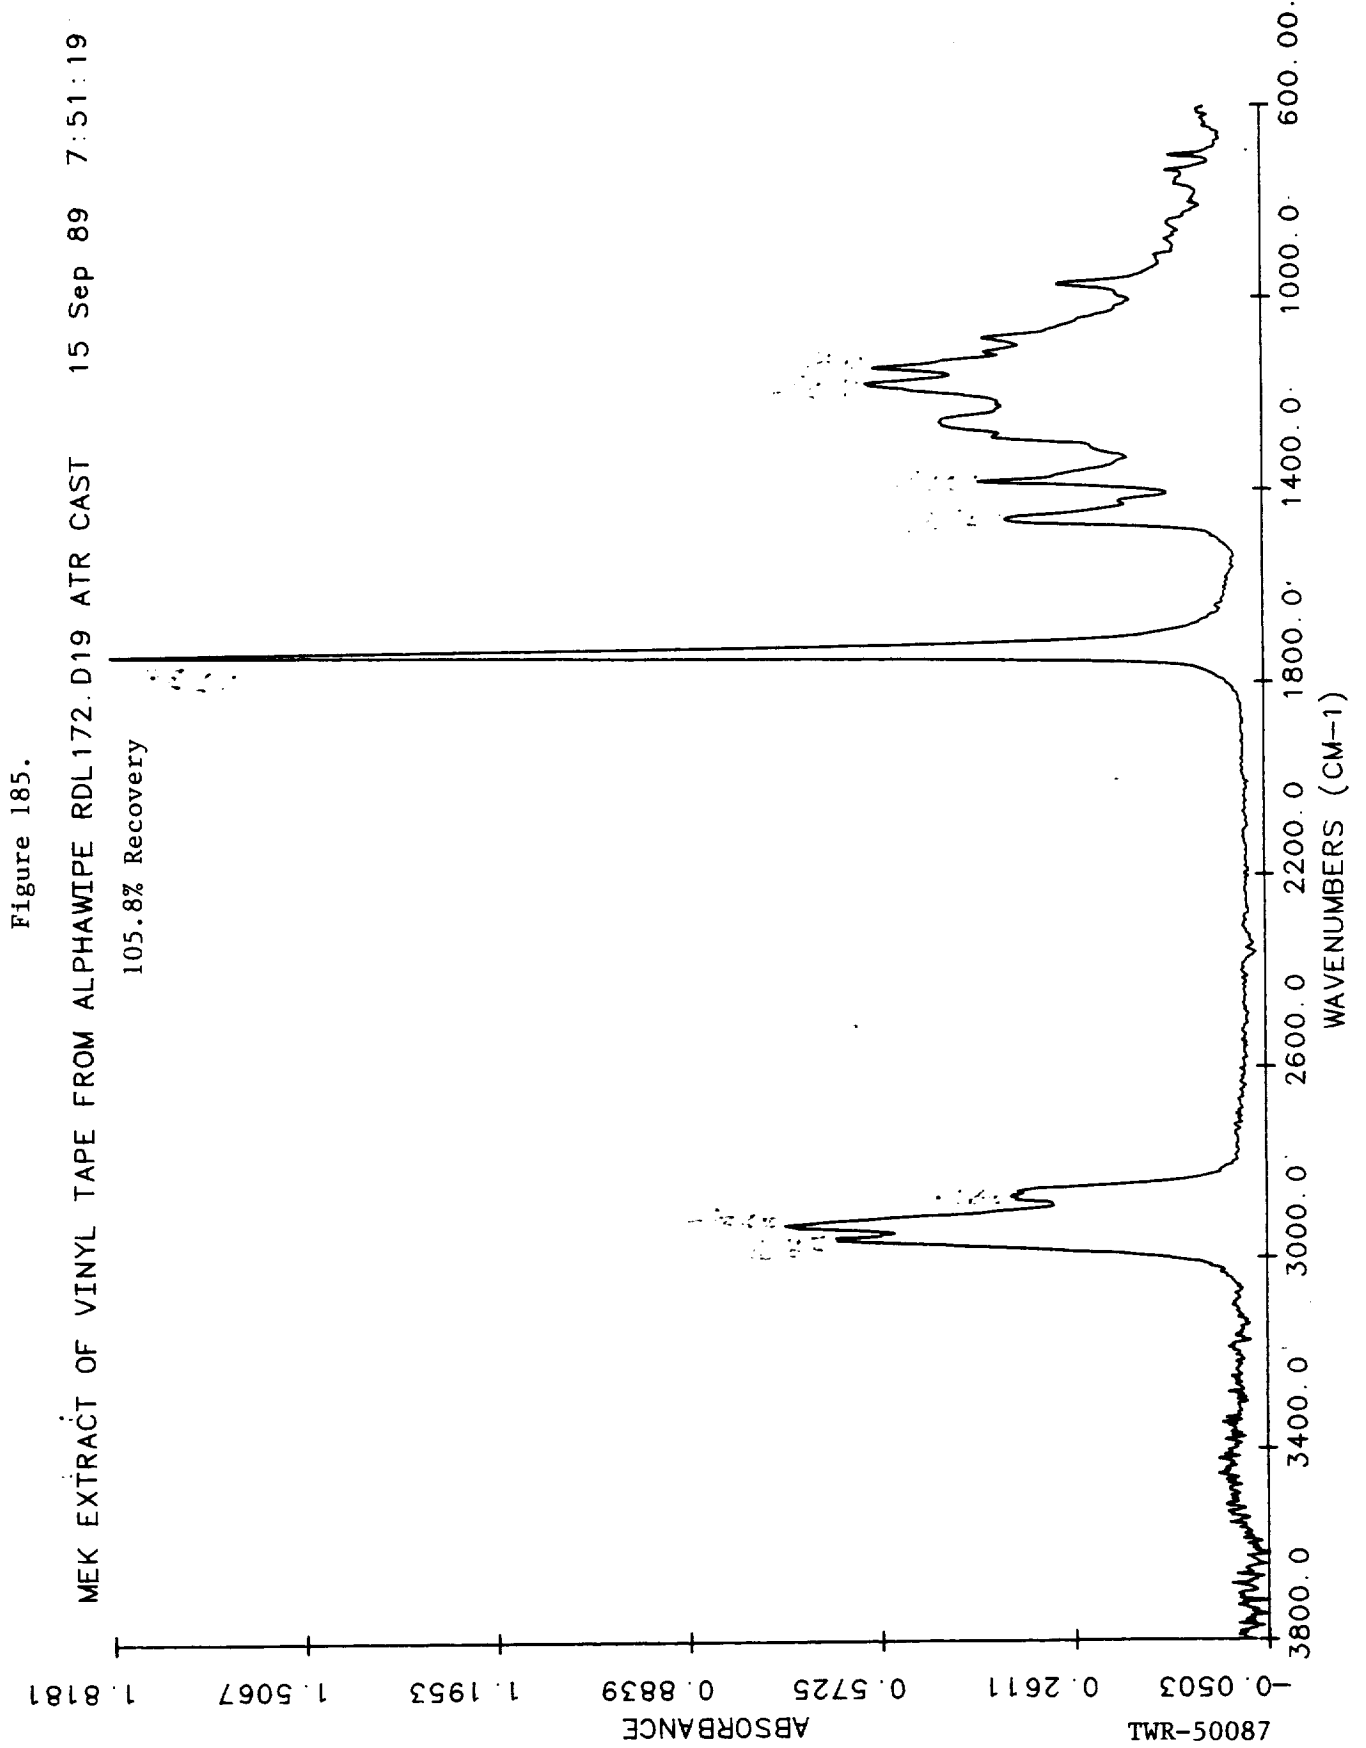

ORIGINAL PAGE IS
OF POOR QUALITY

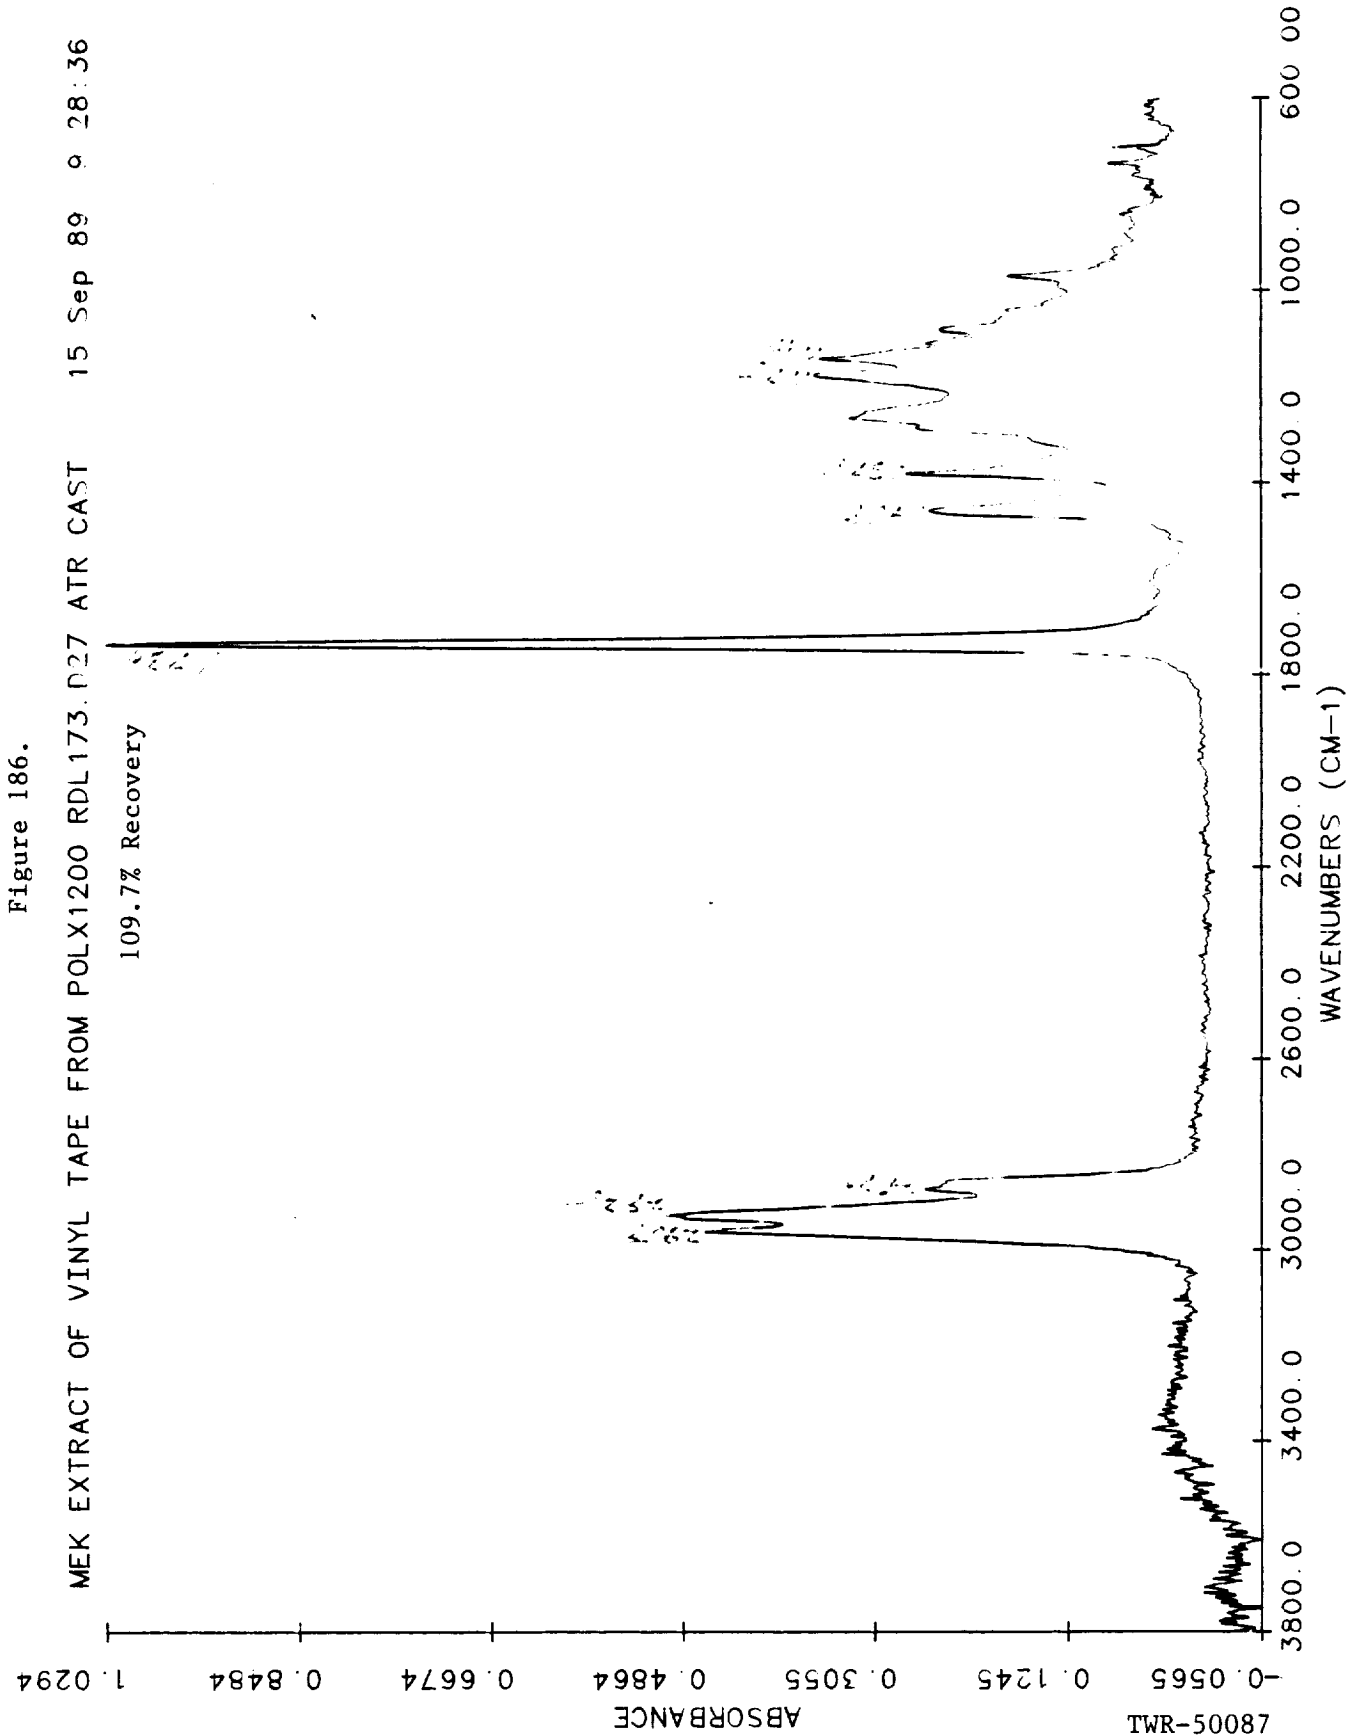

ORIGINAL PAGE IS
OF POOR QUALITY

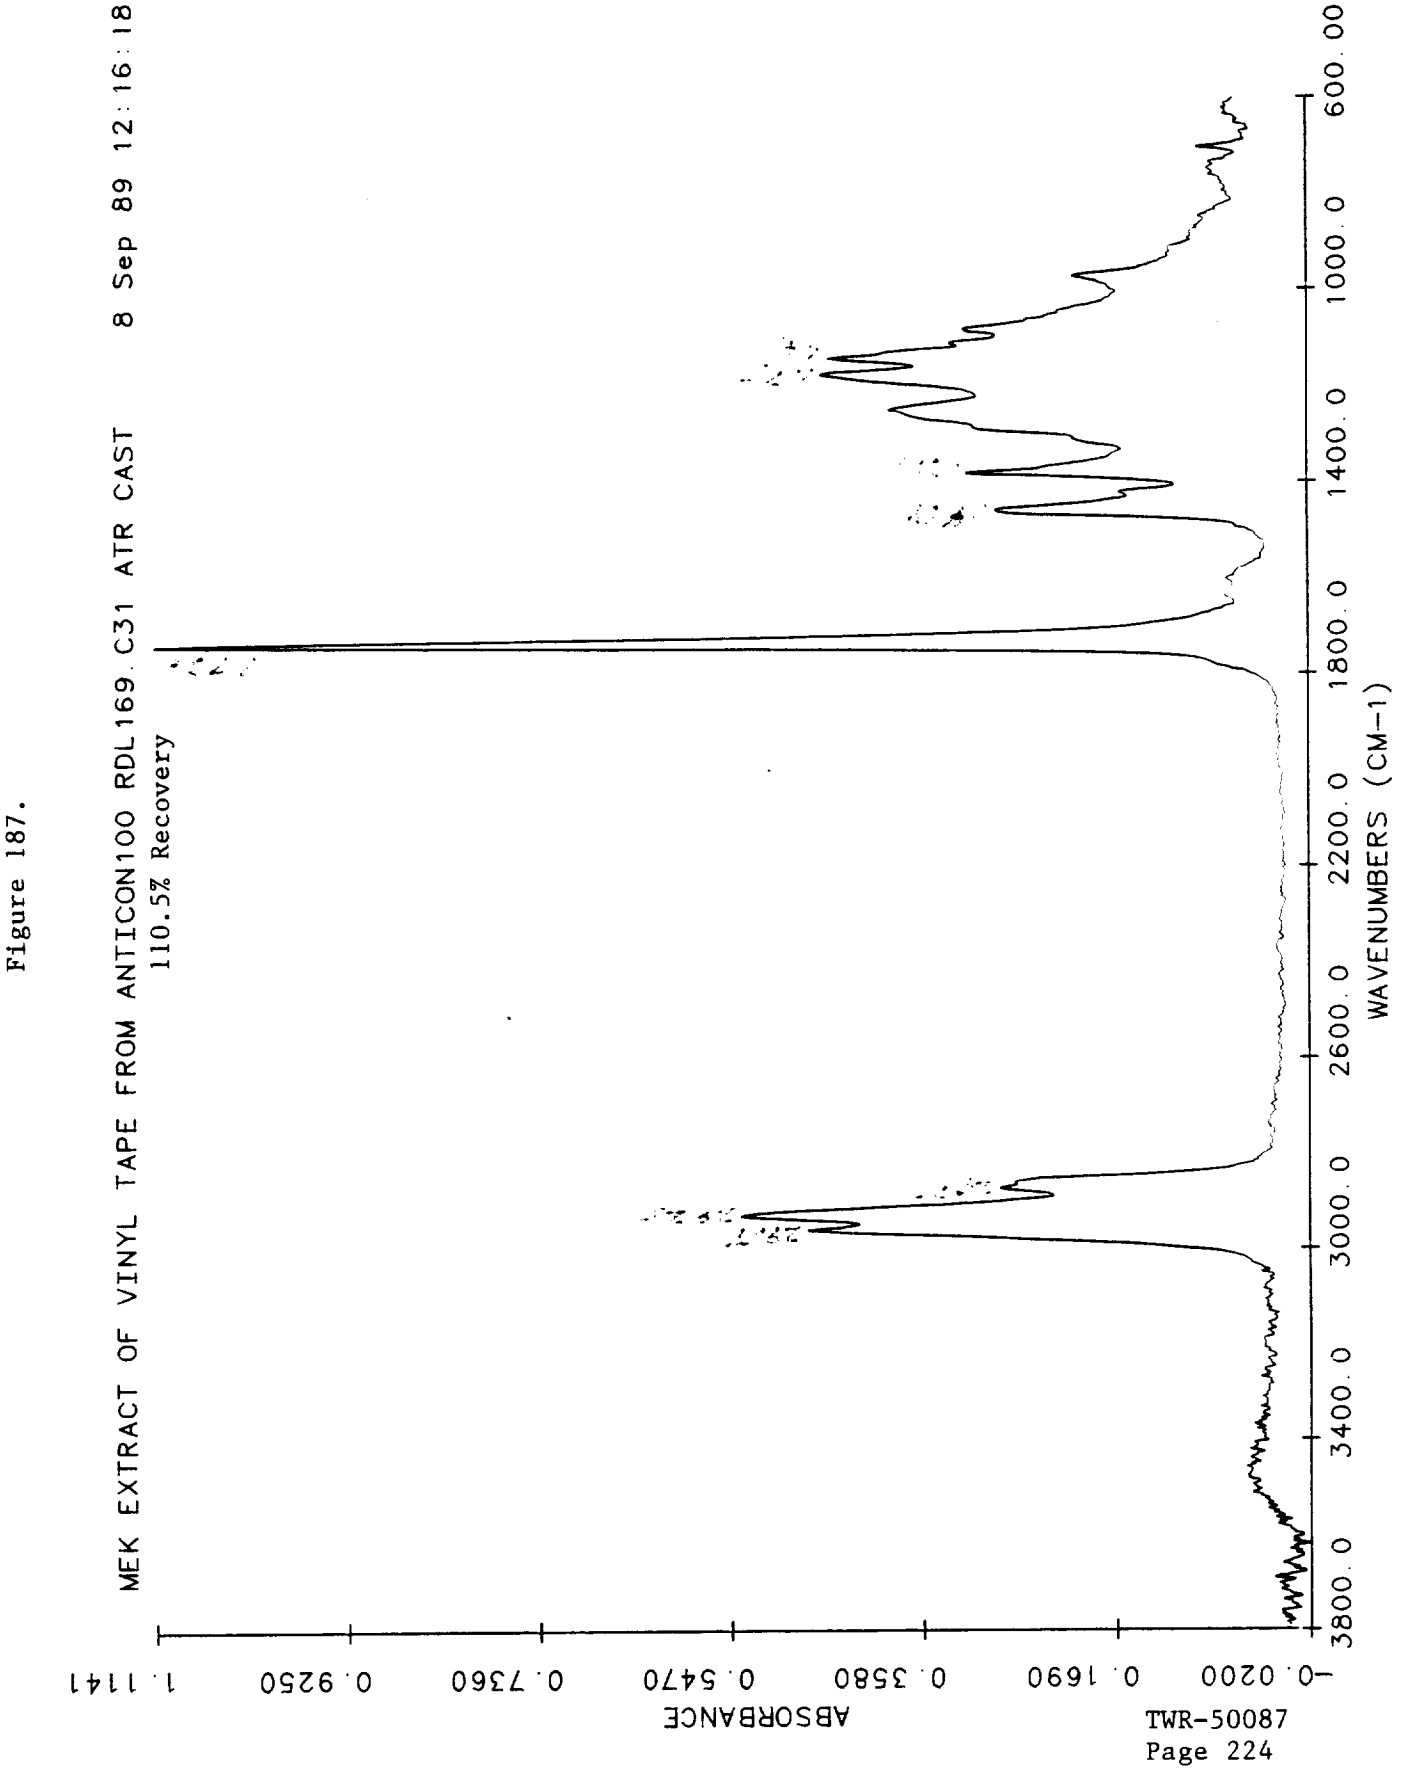

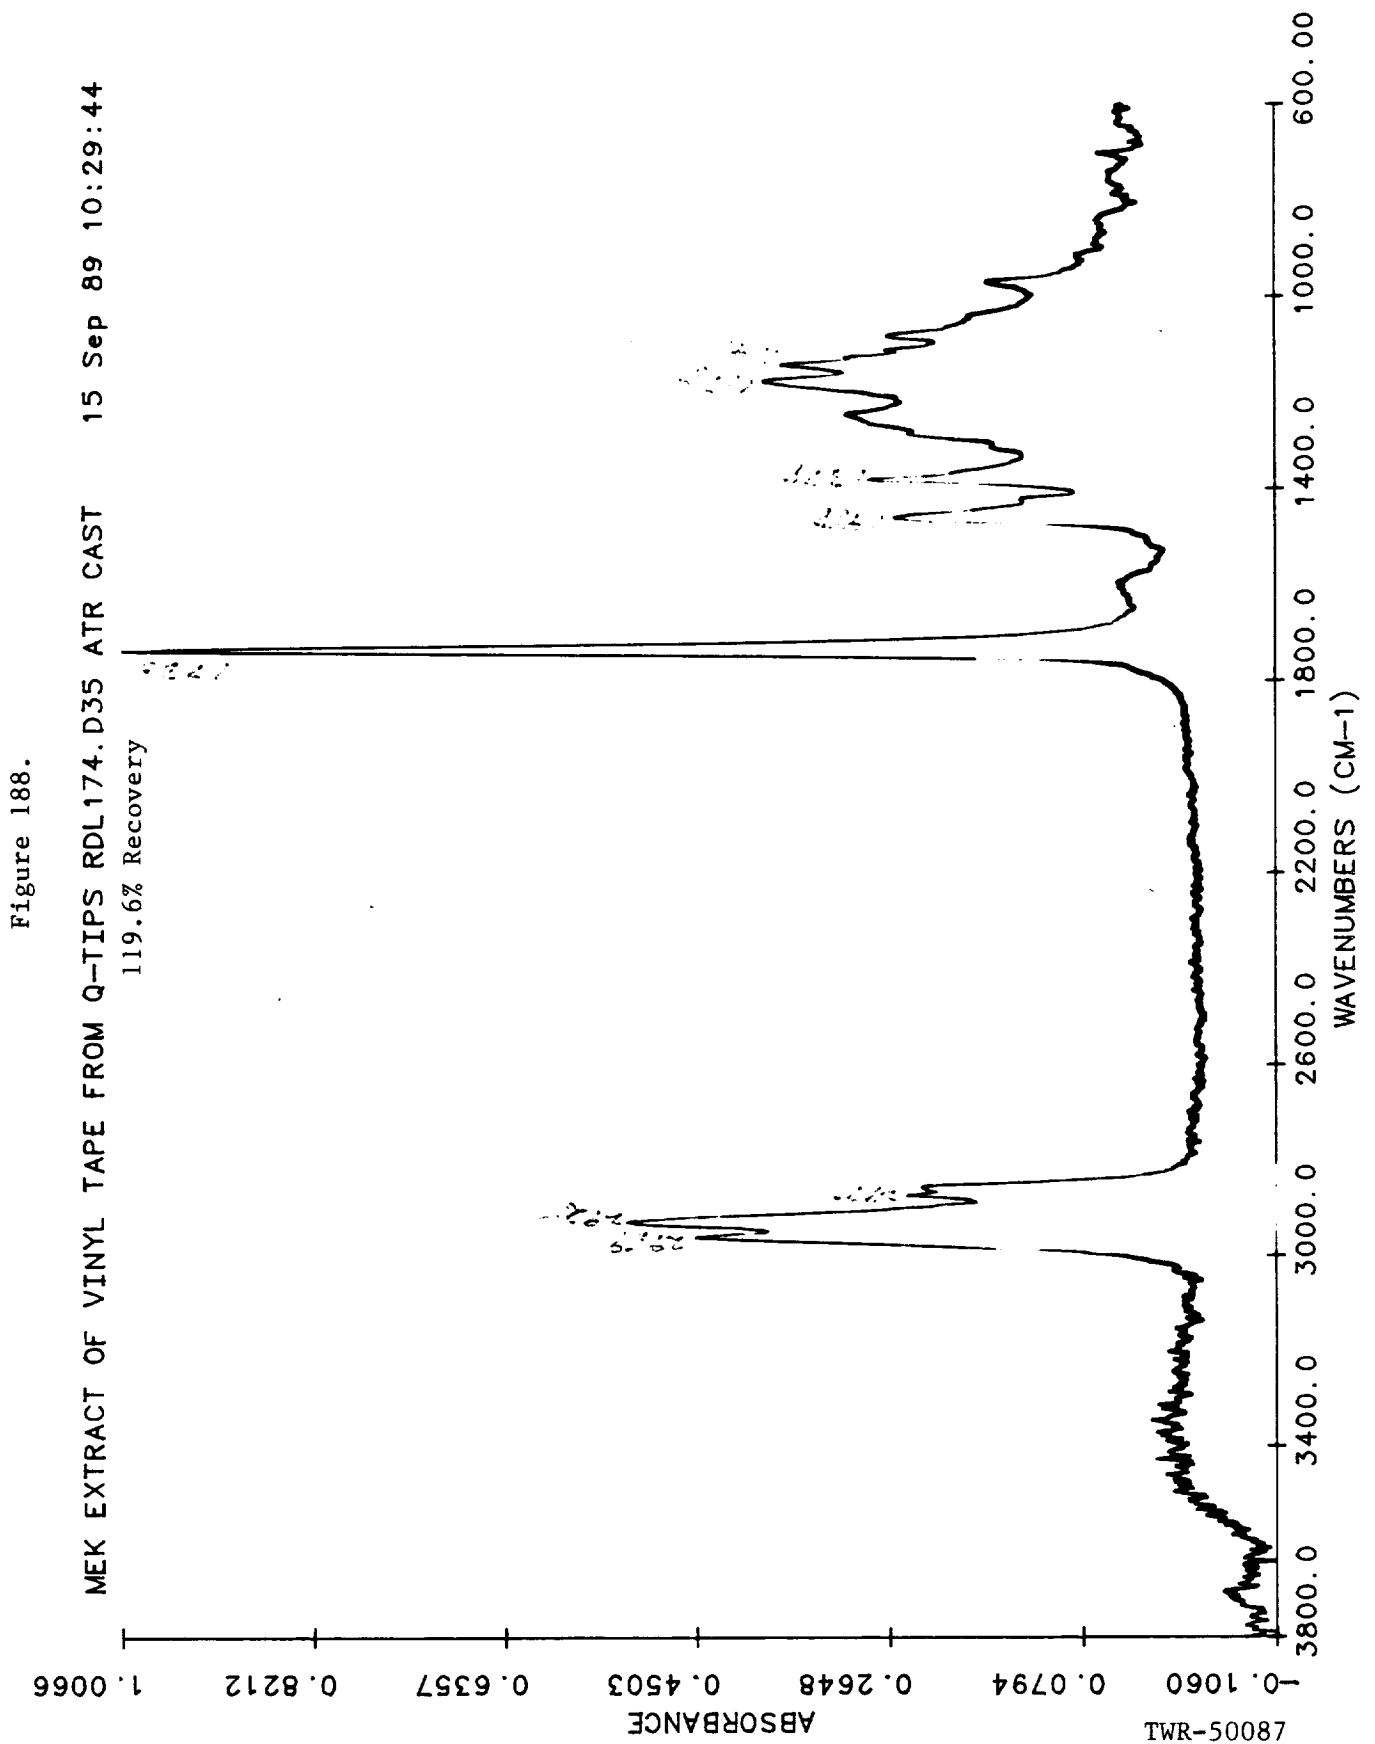


Figure 188.

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 189.

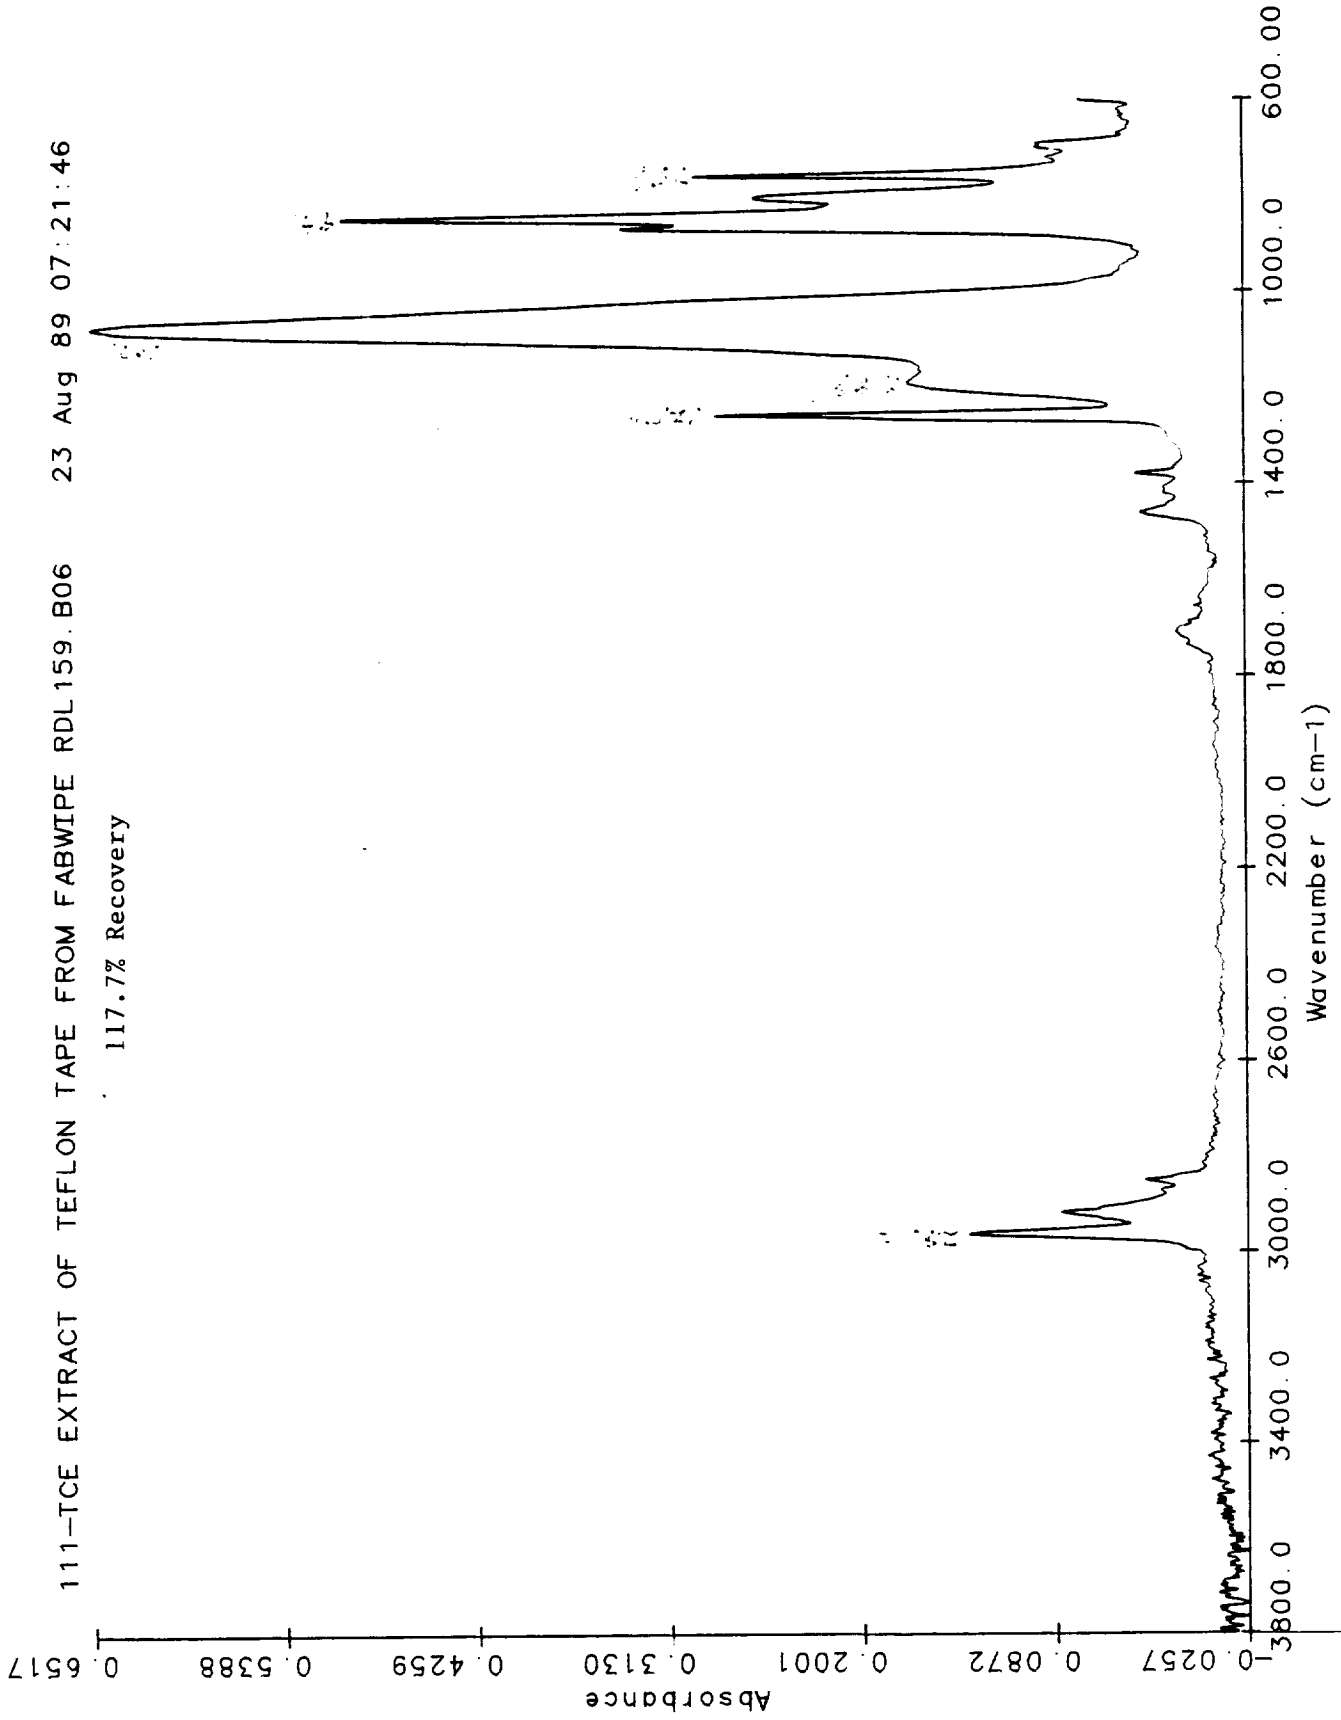


Figure 190.


111-TCE EXTRACT OF TEFLON TAPE FROM MIRACLEWIPE RPL158.R04 ATR CAST
111.9% Recovery

0.7686 0.6352 0.5018 0.3684 0.2350 0.1015 0.0312

ABSORBANCE

TWR-5007
Page 227

ORIGINAL PAGE IS
OF POOR QUALITY

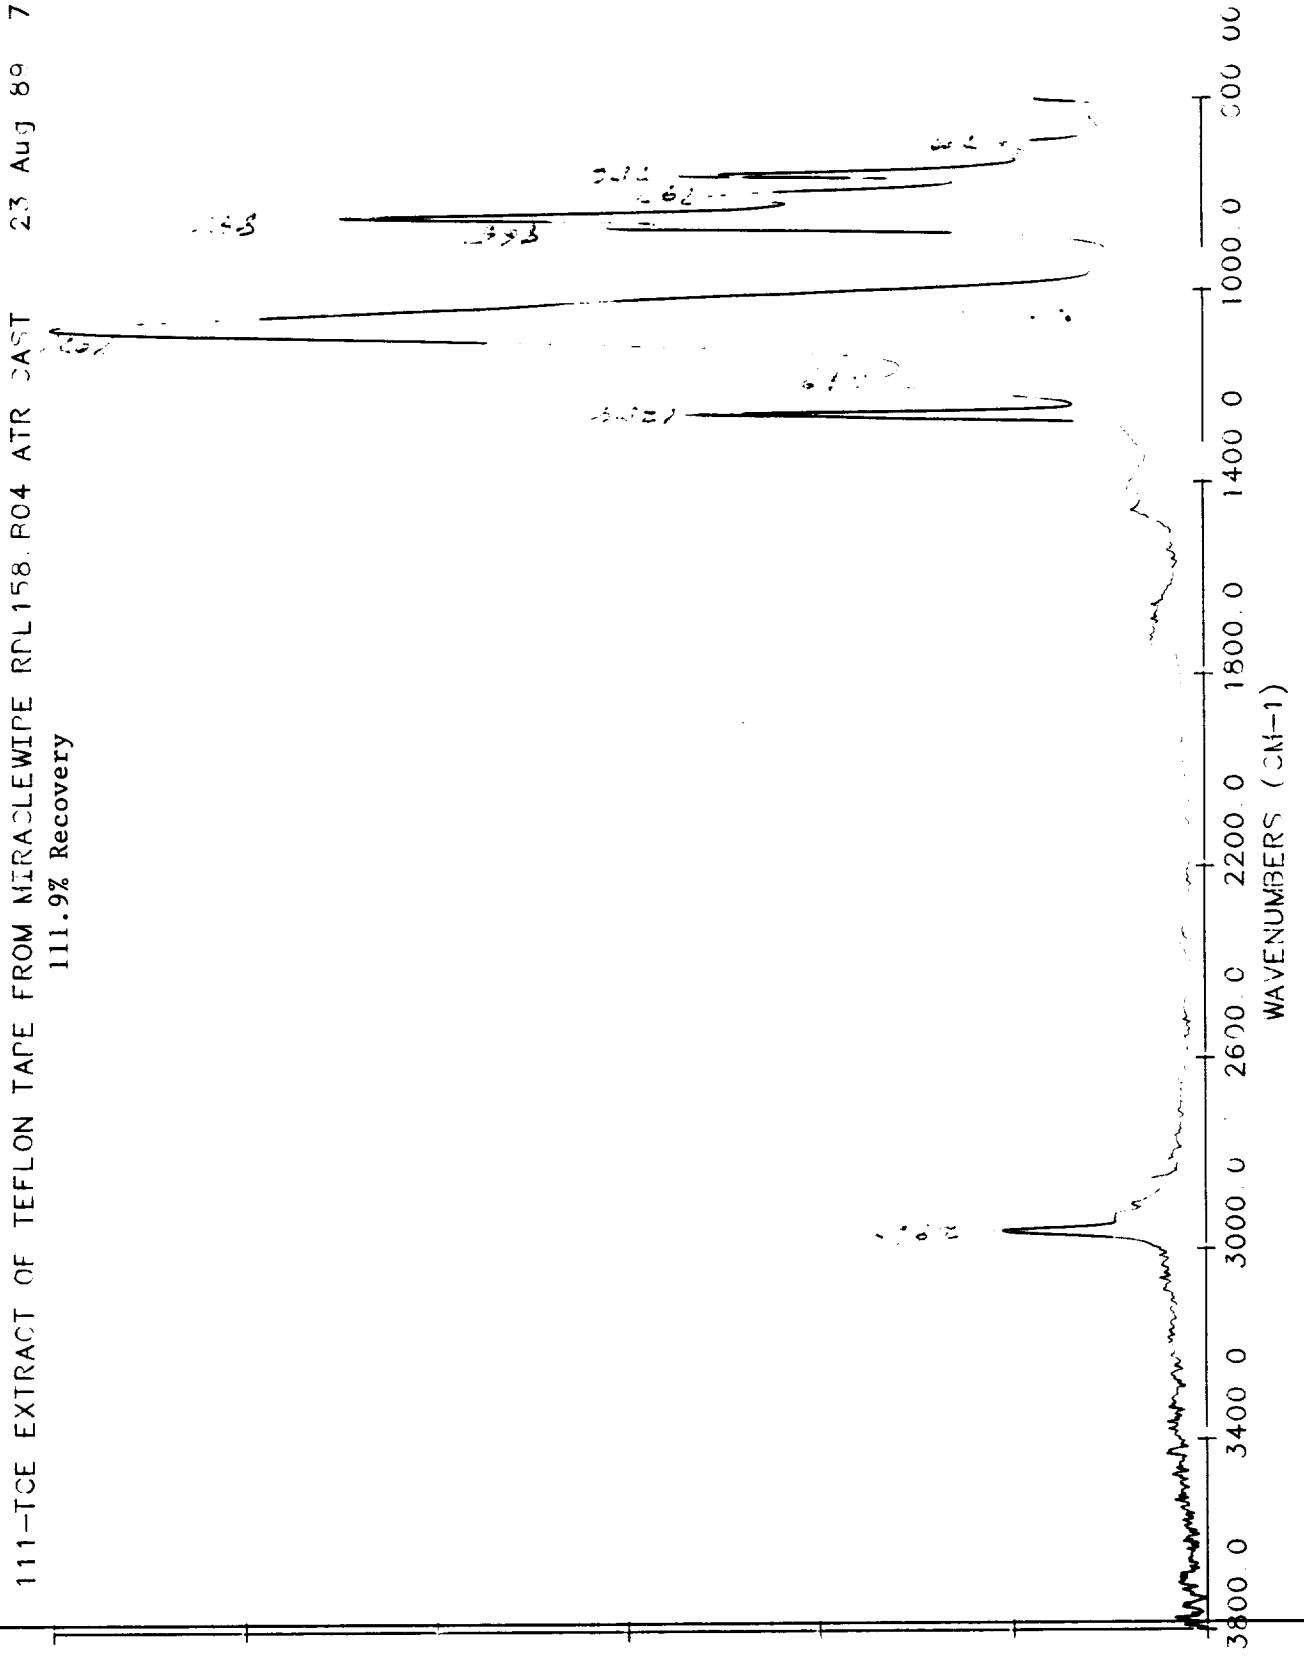

23 Aug 89 7:06 54

Figure 191.


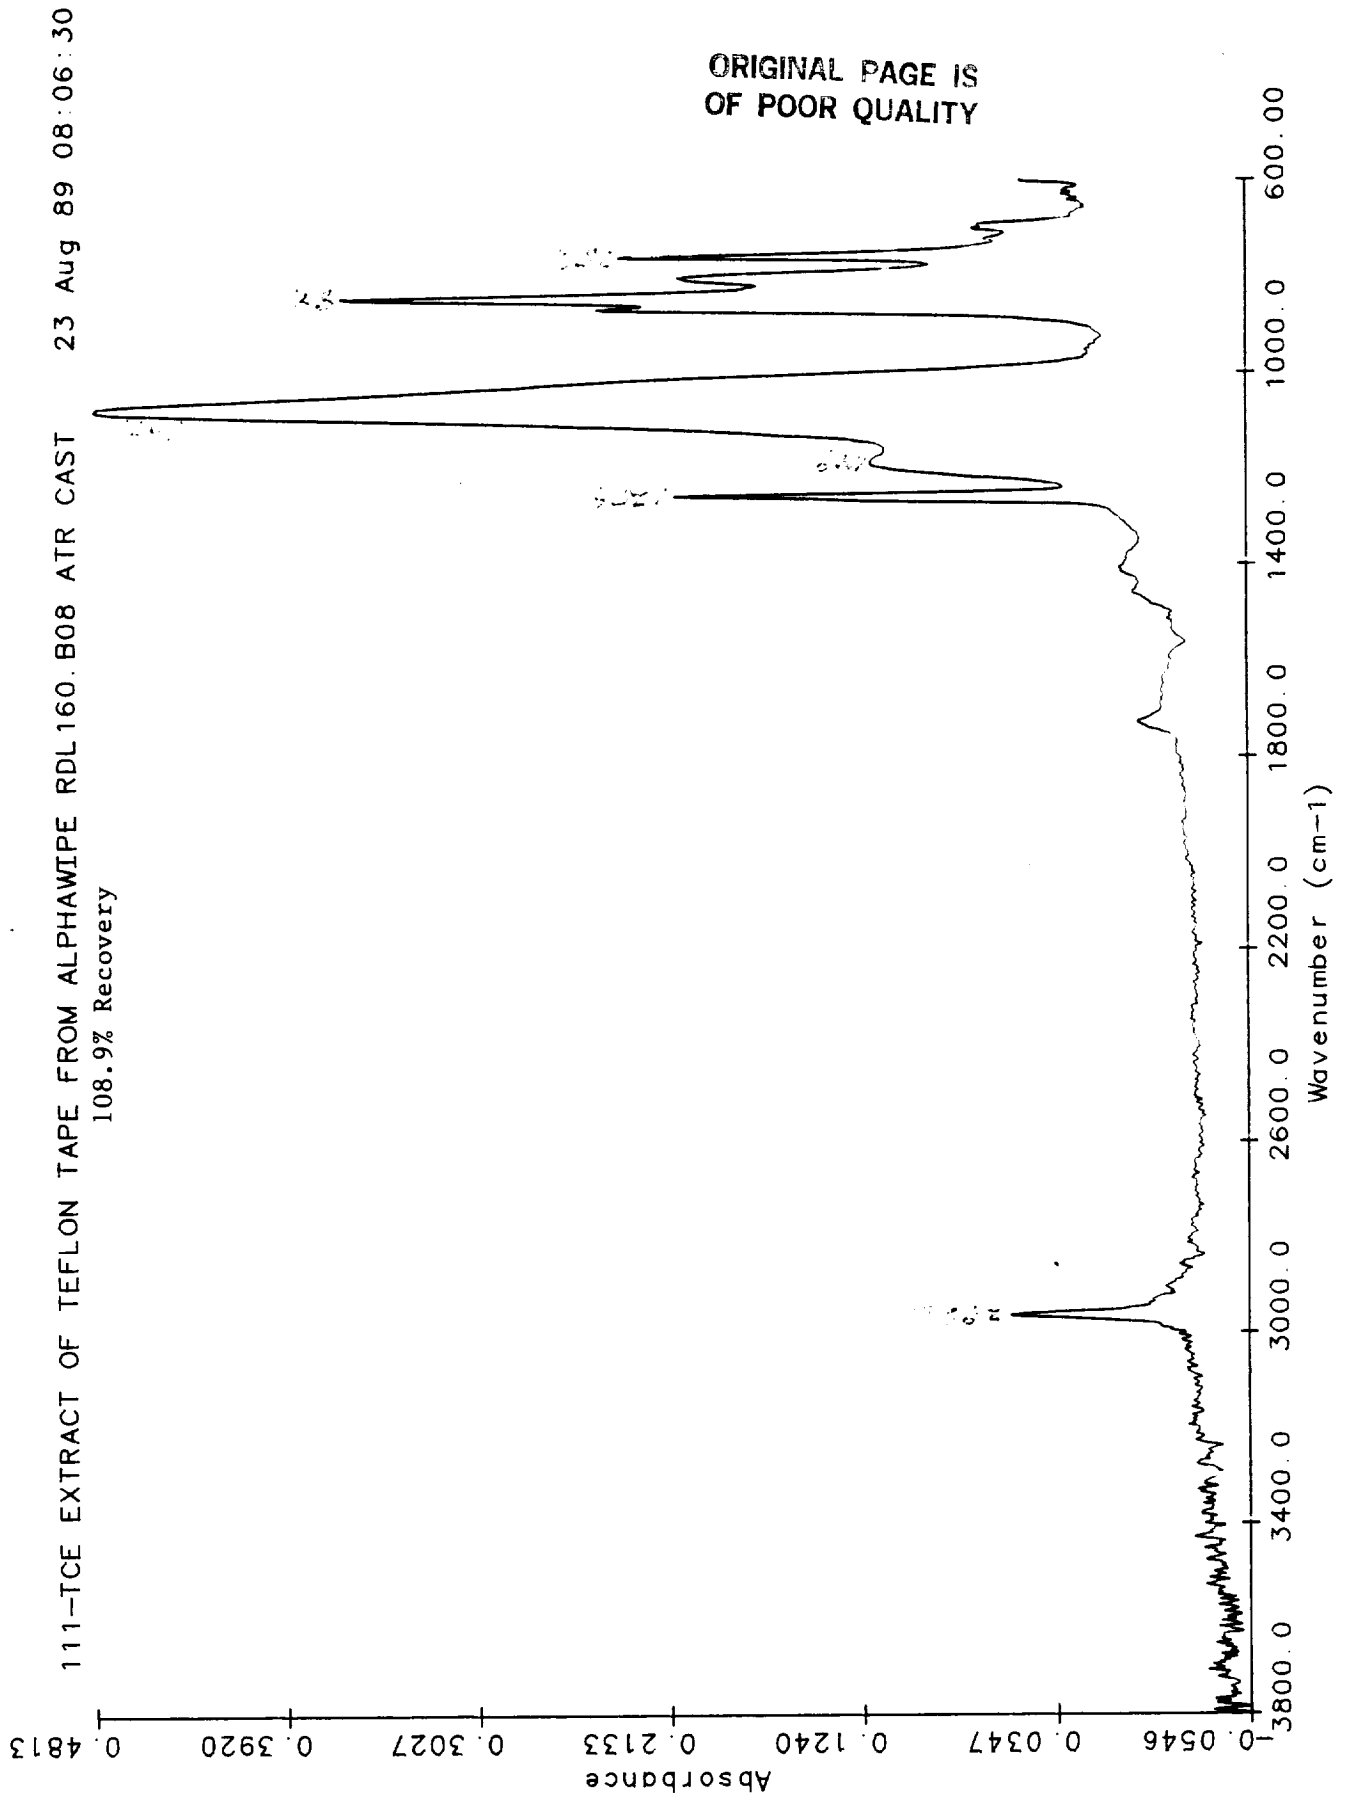



Figure 192.

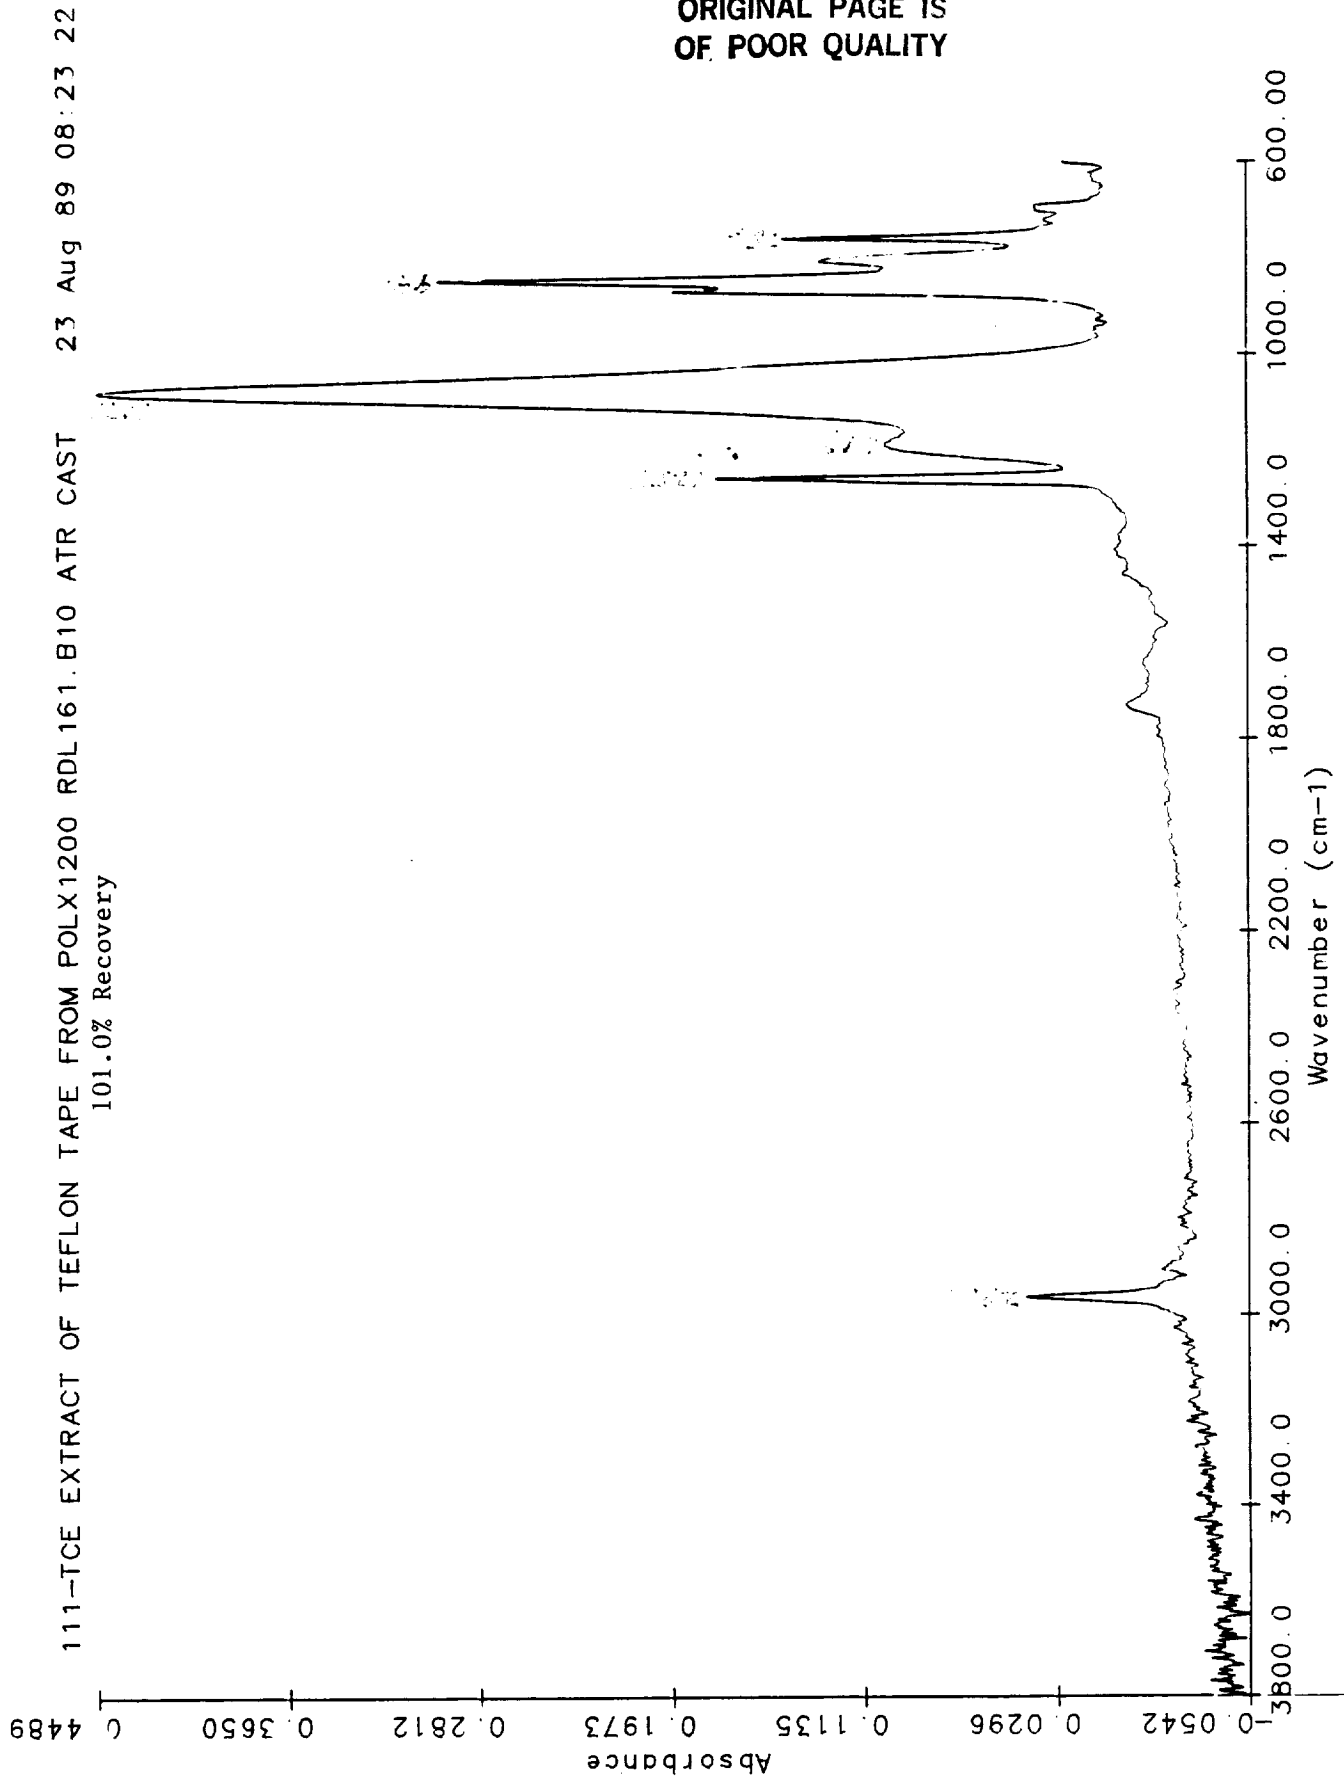

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 193.

111-TCE EXTRACT OF TEFLON TAPE FROM ANTICON RDL157.B02 ATR CAST
97.0% Recovery

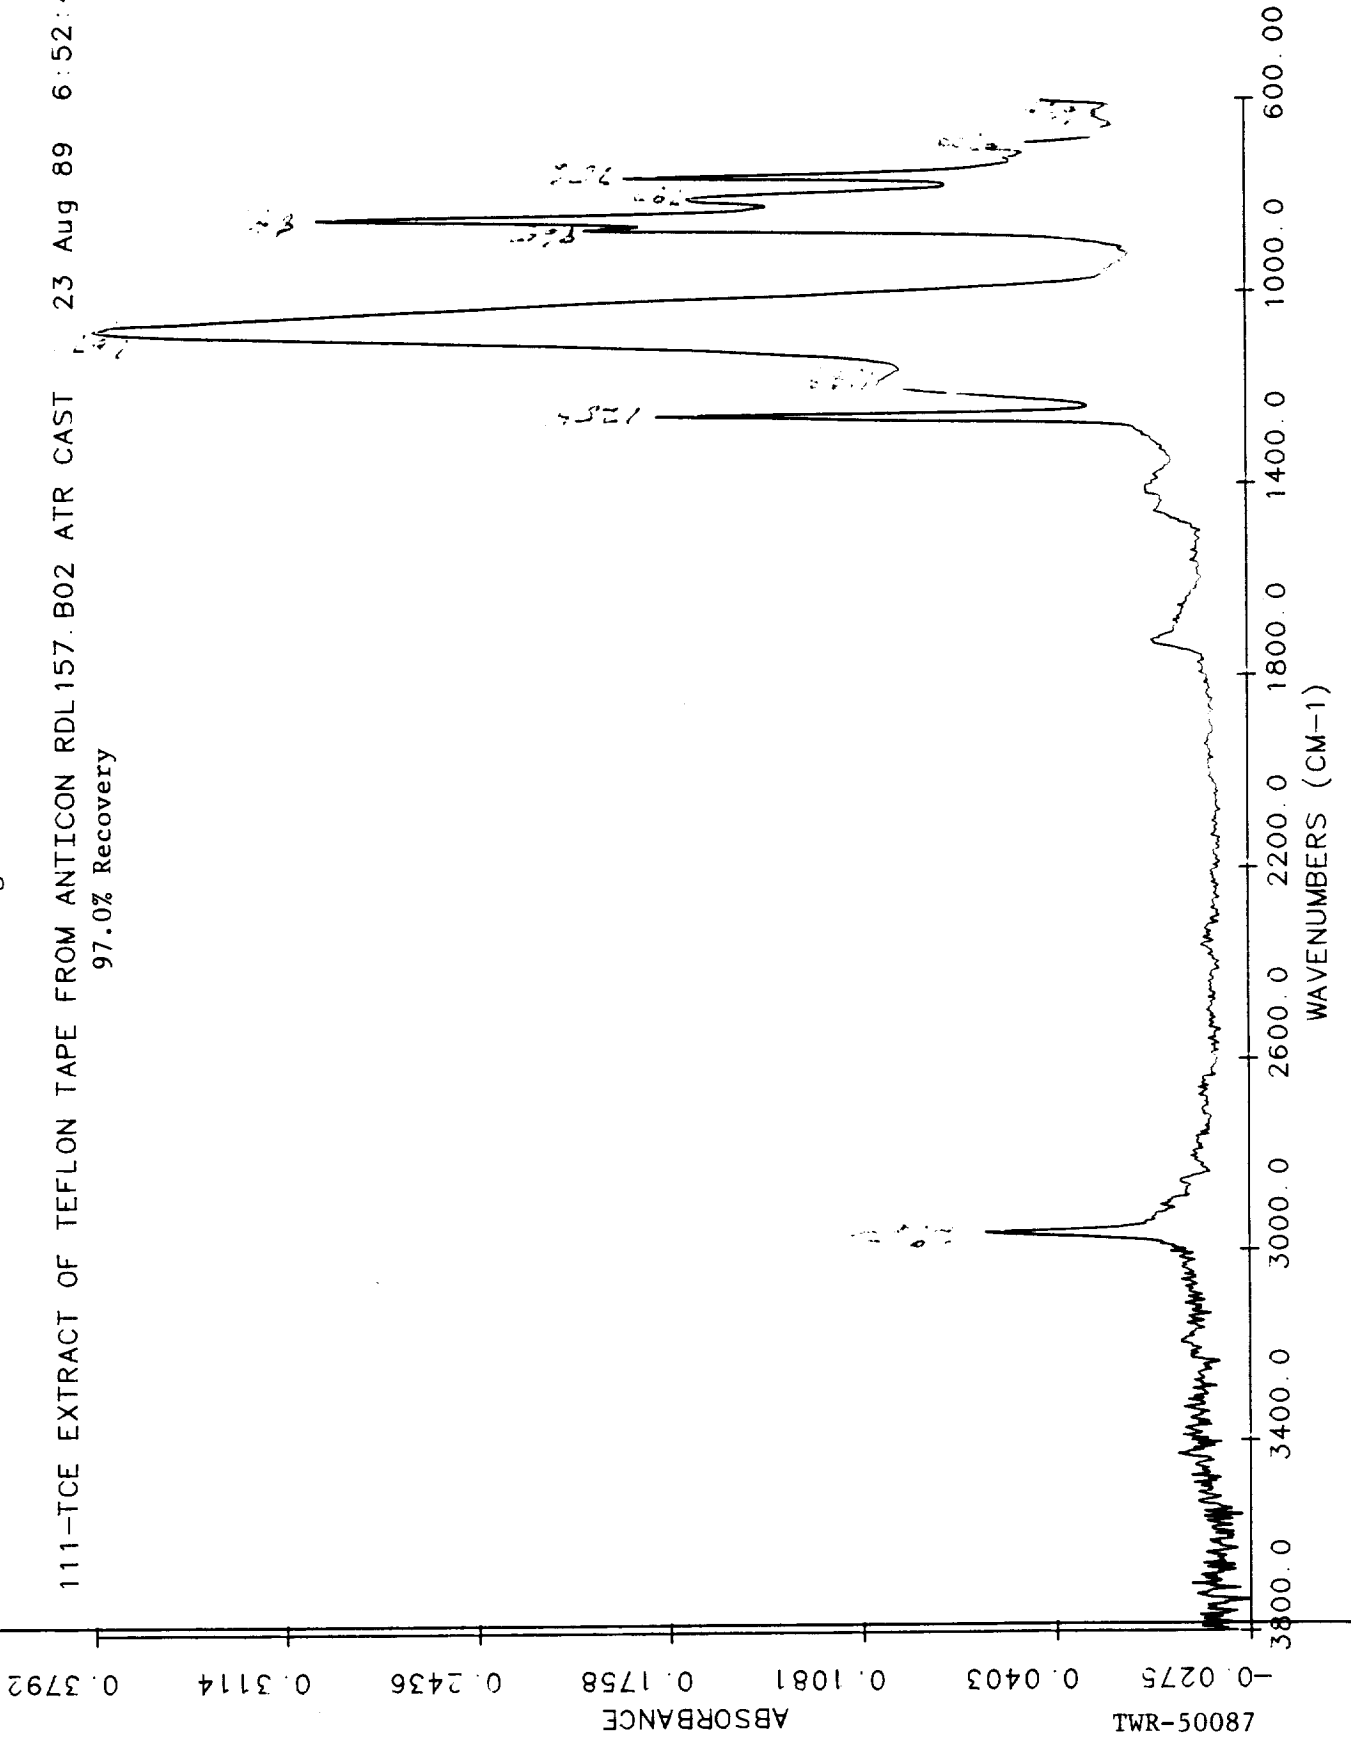

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 194.


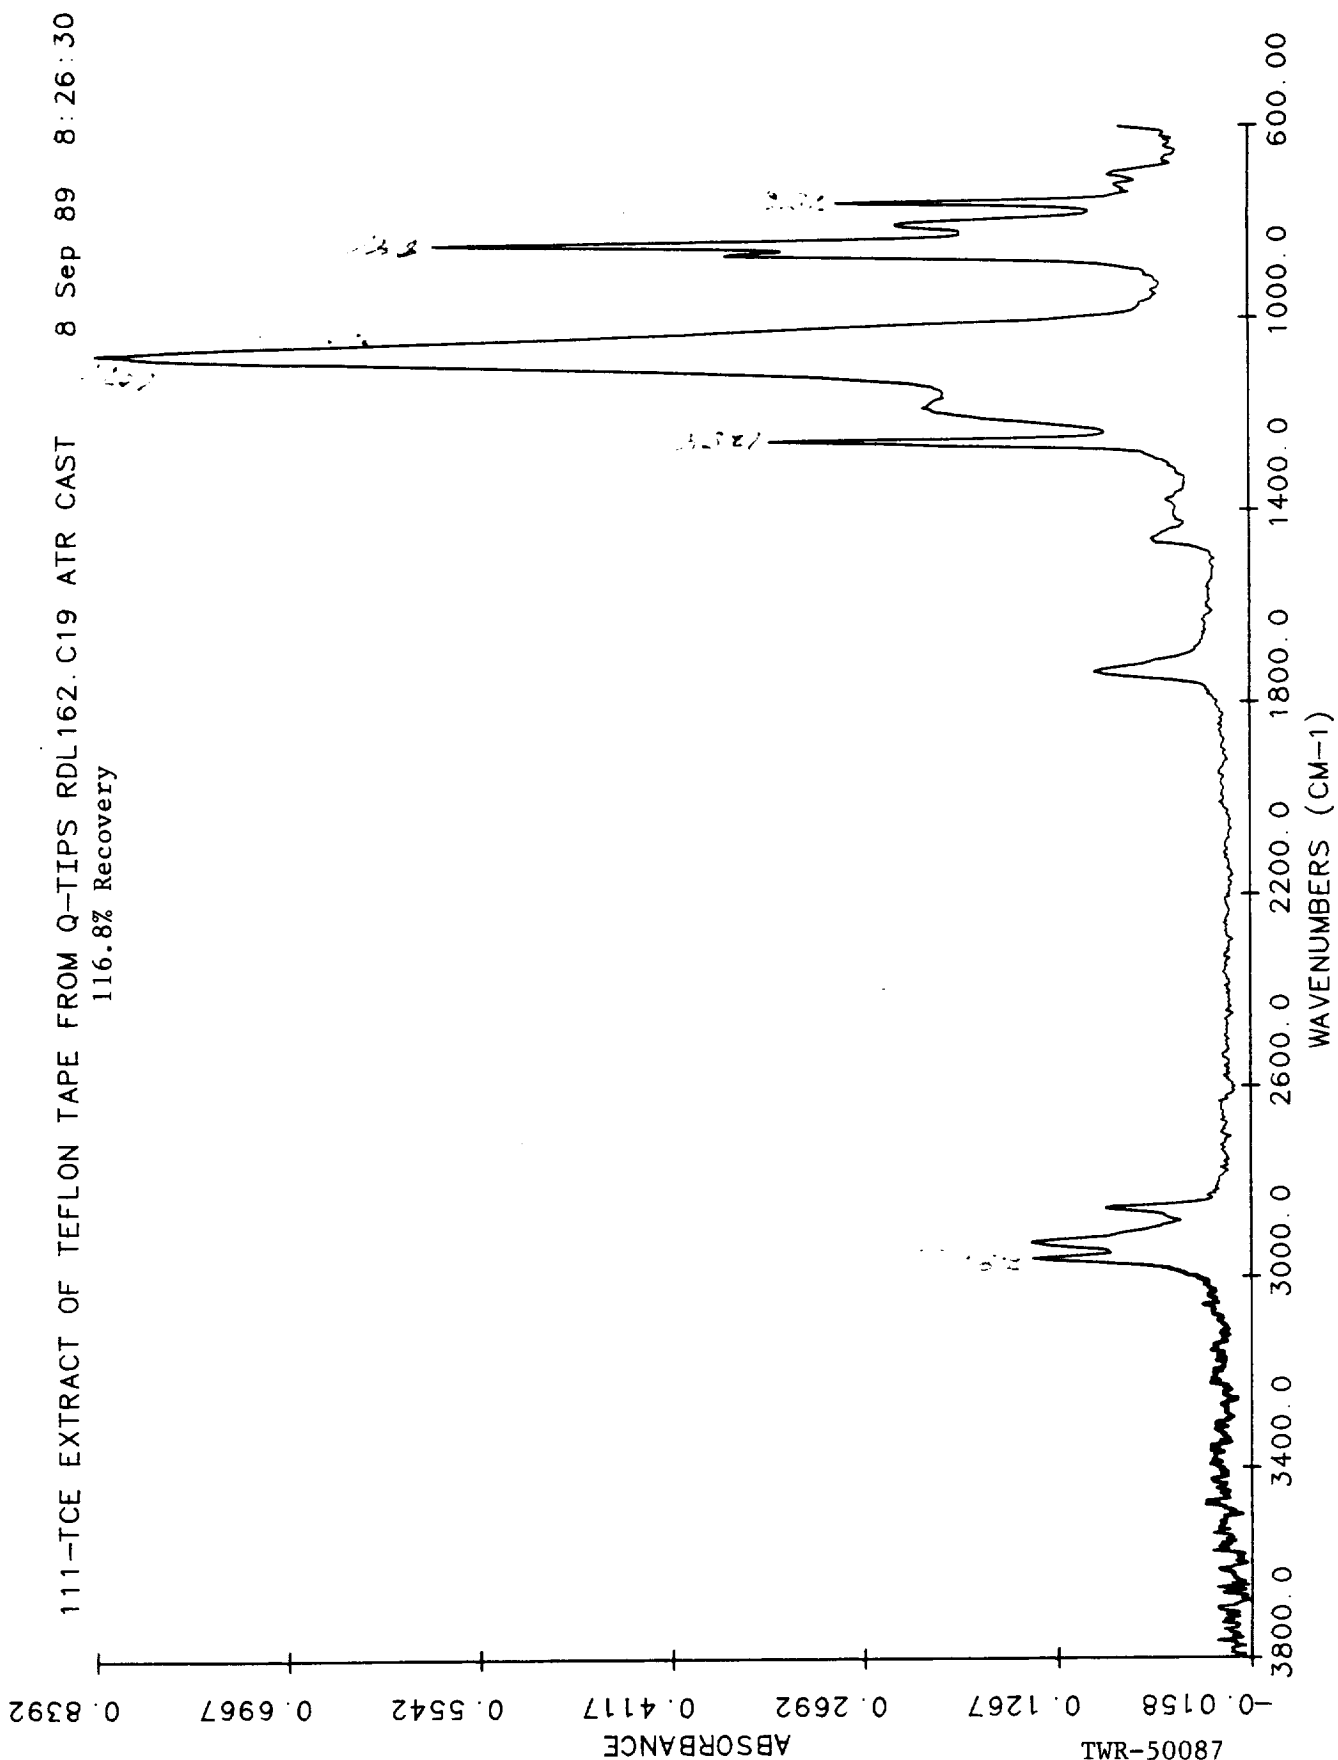


Figure 195.


FREON TF EXTRACT OF TEFLON TAPE FROM FABWIPE RDL165.B35 ATR CAST 29 Aug 89 9:30:11
71.3% Recovery

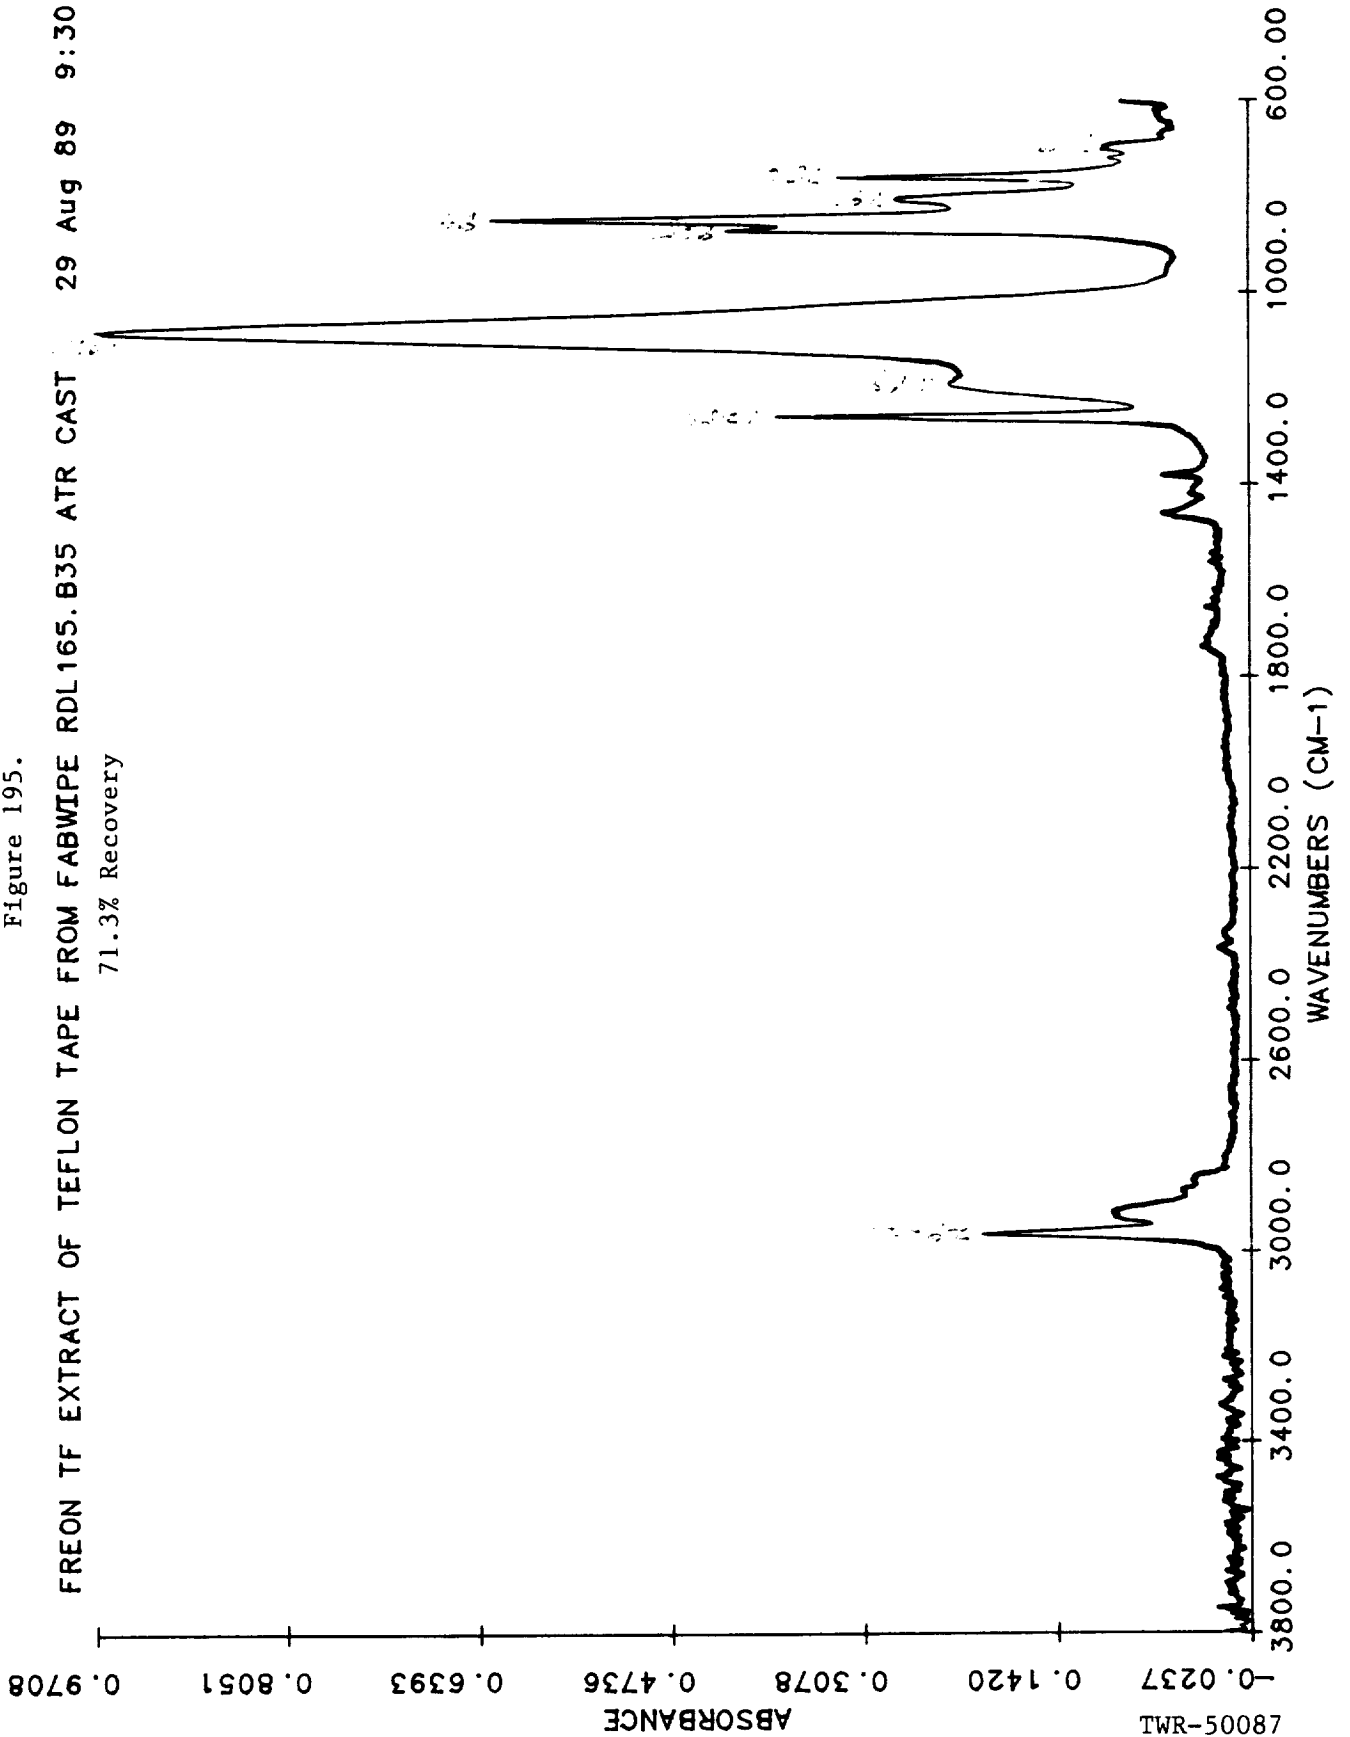

ORIGINAL PAGE IS
OF POOR QUALITY


Figure 196.

FREON TF EXTRACT OF TEFLON TAPE FROM MIRACLEWIPE RDL164.B27 ATR CAST
103.0% Recovery

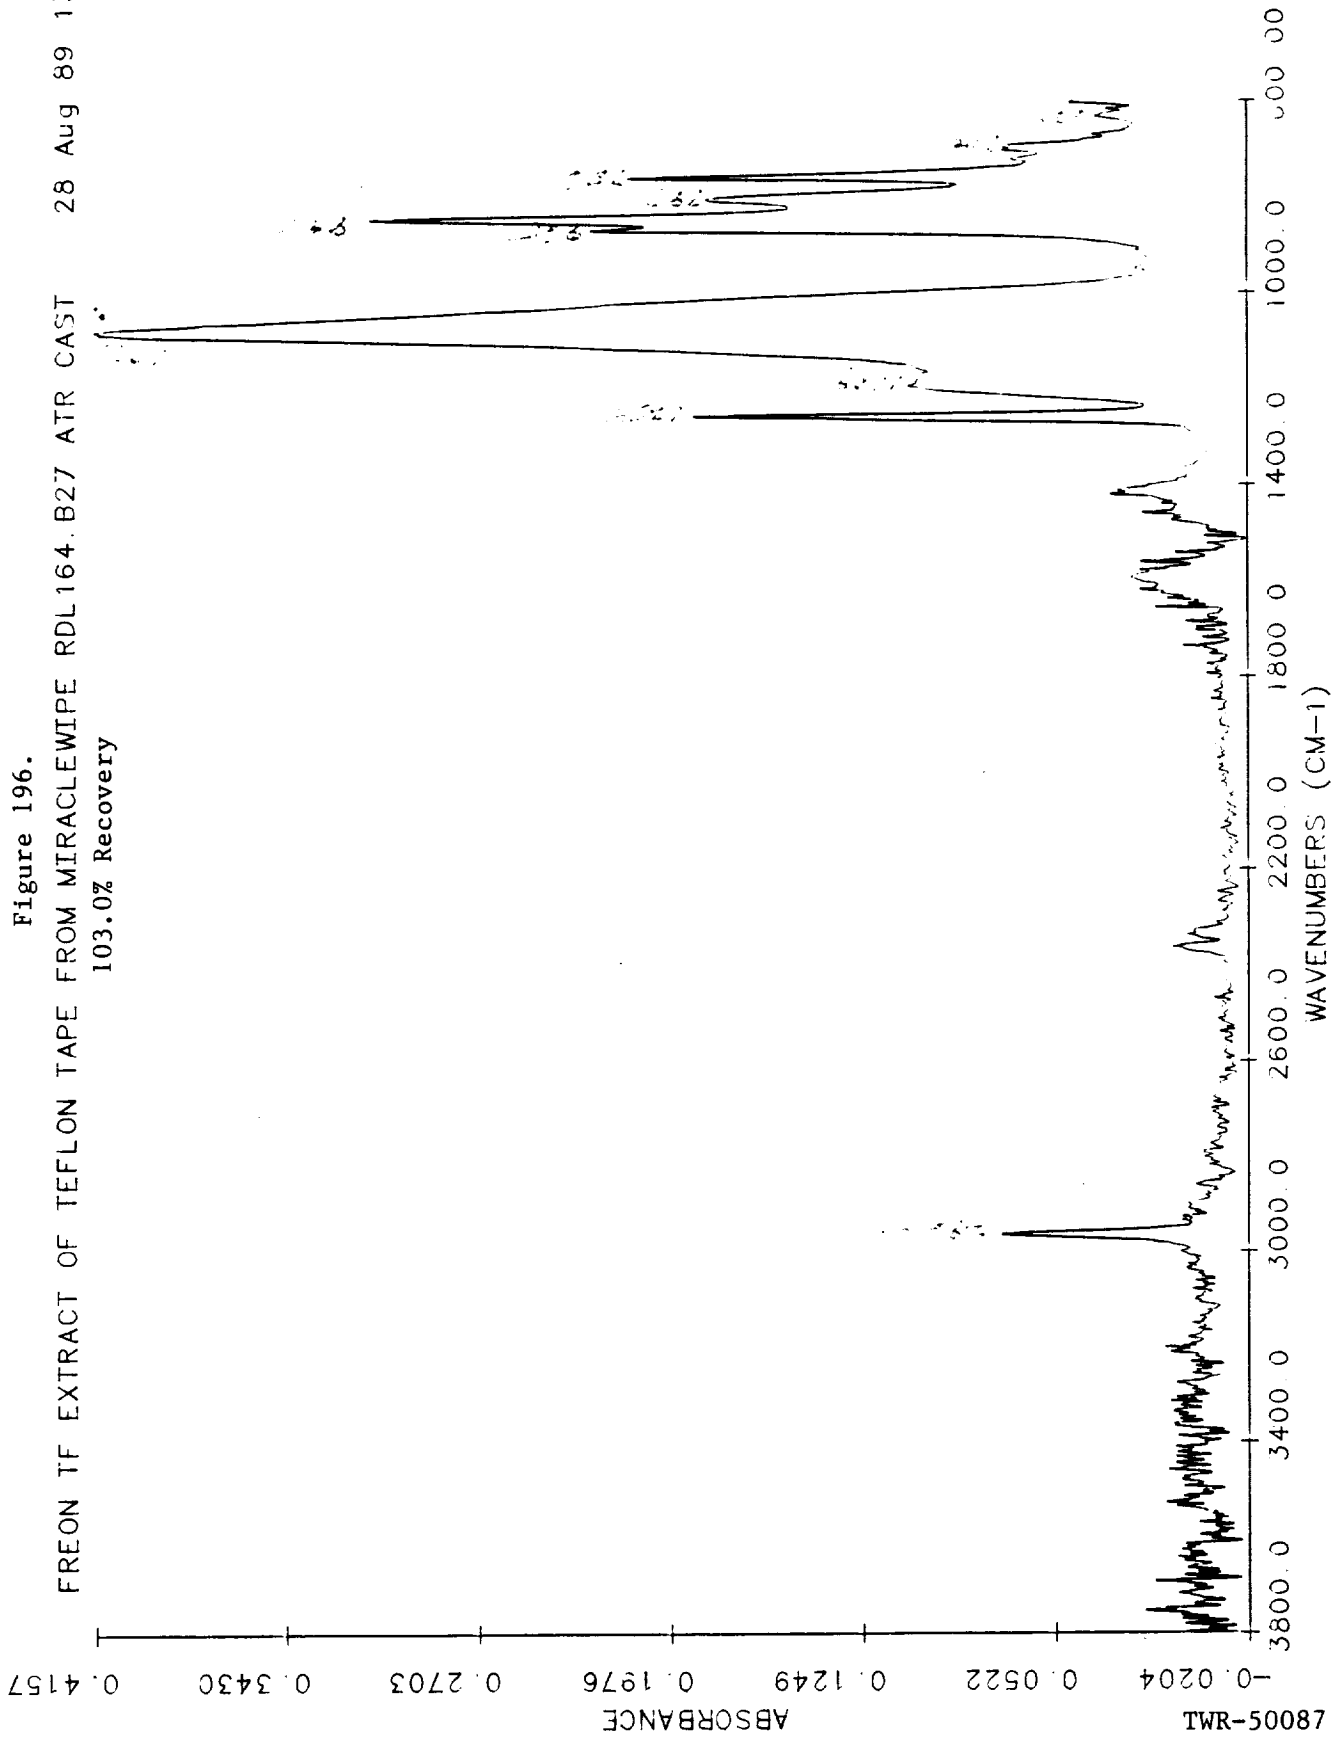

ORIGINAL PAGE IS
OF POOR QUALITY


Figure 197.

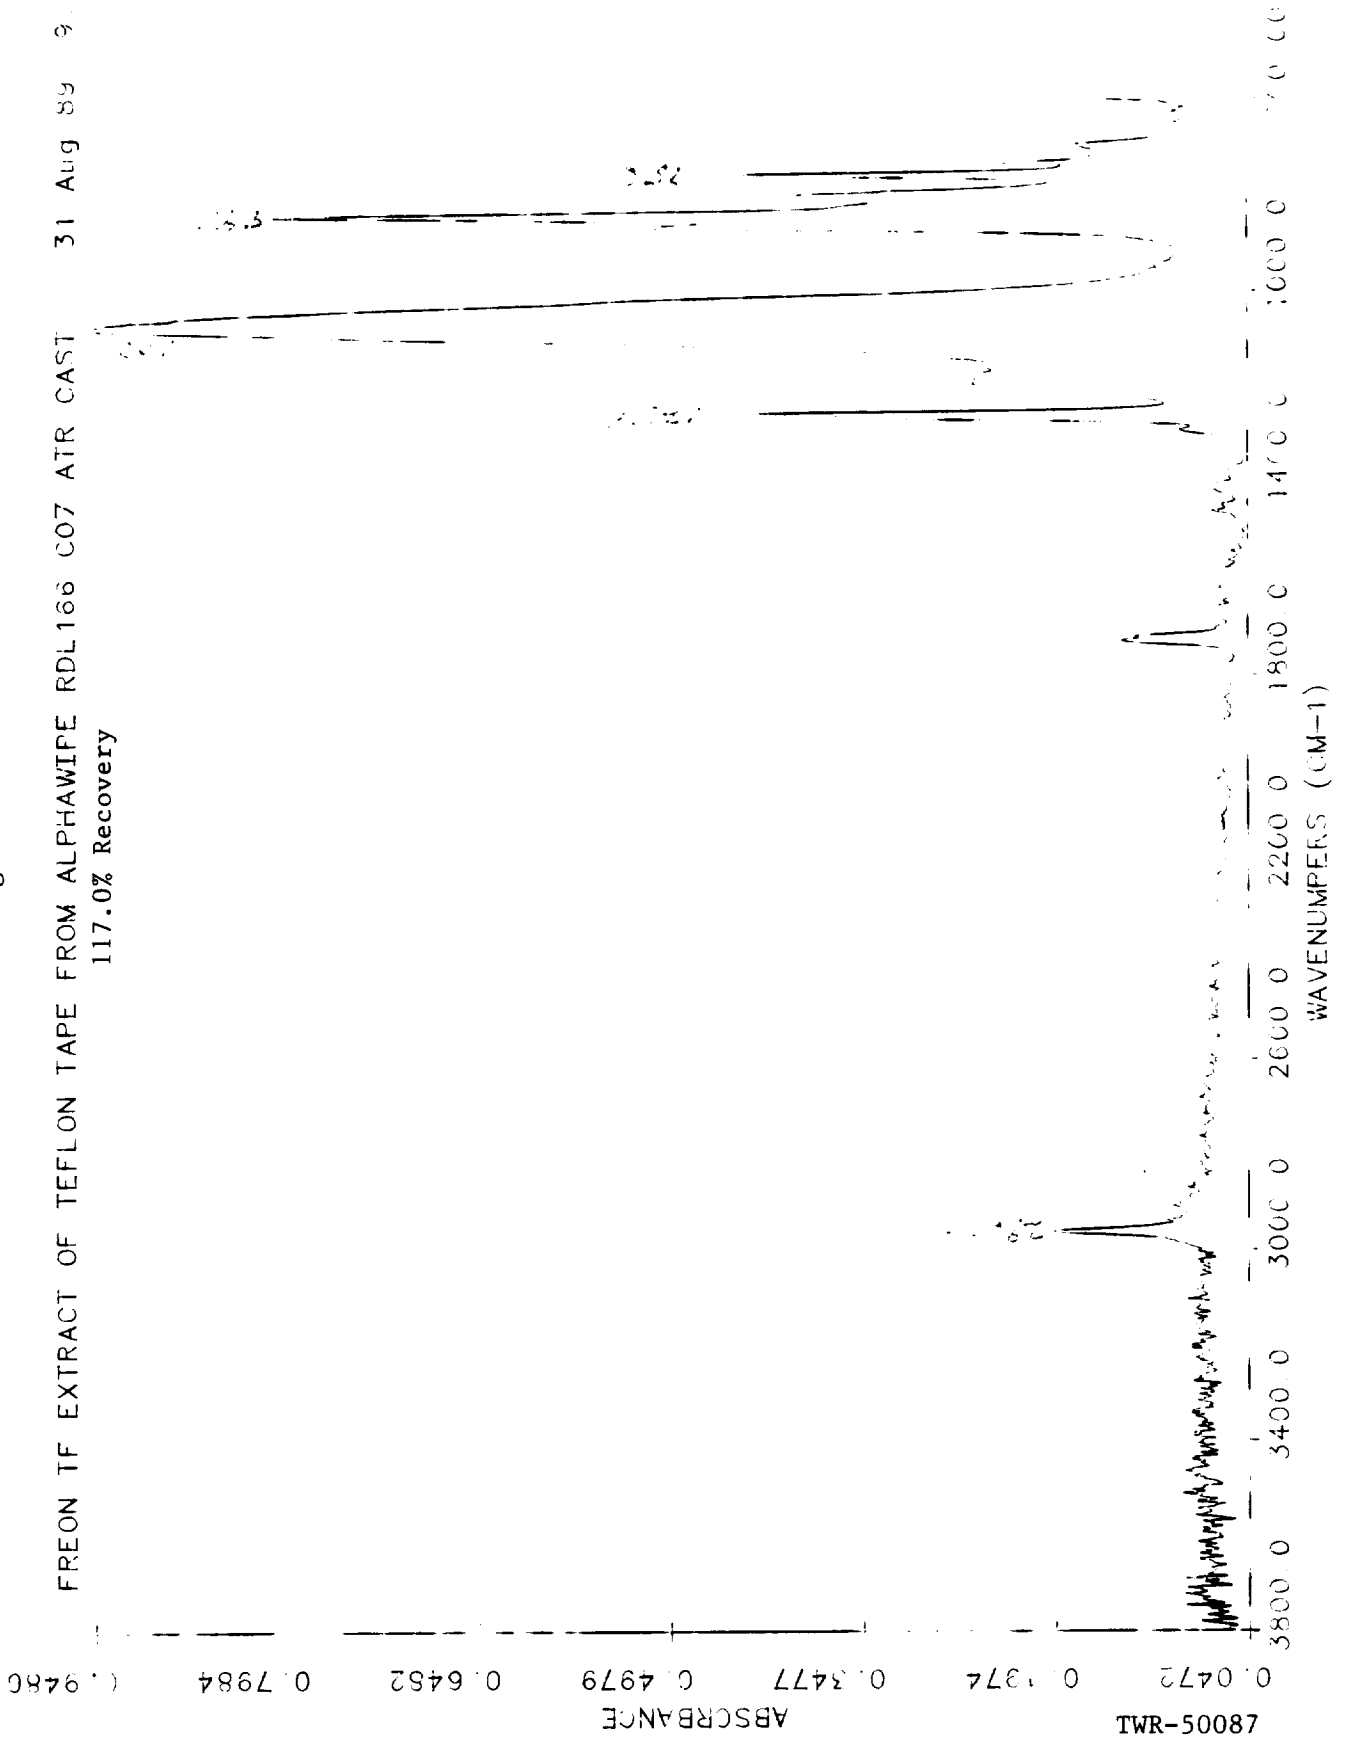

ORIGINAL PAGE IS
OF POOR QUALITY

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 198.

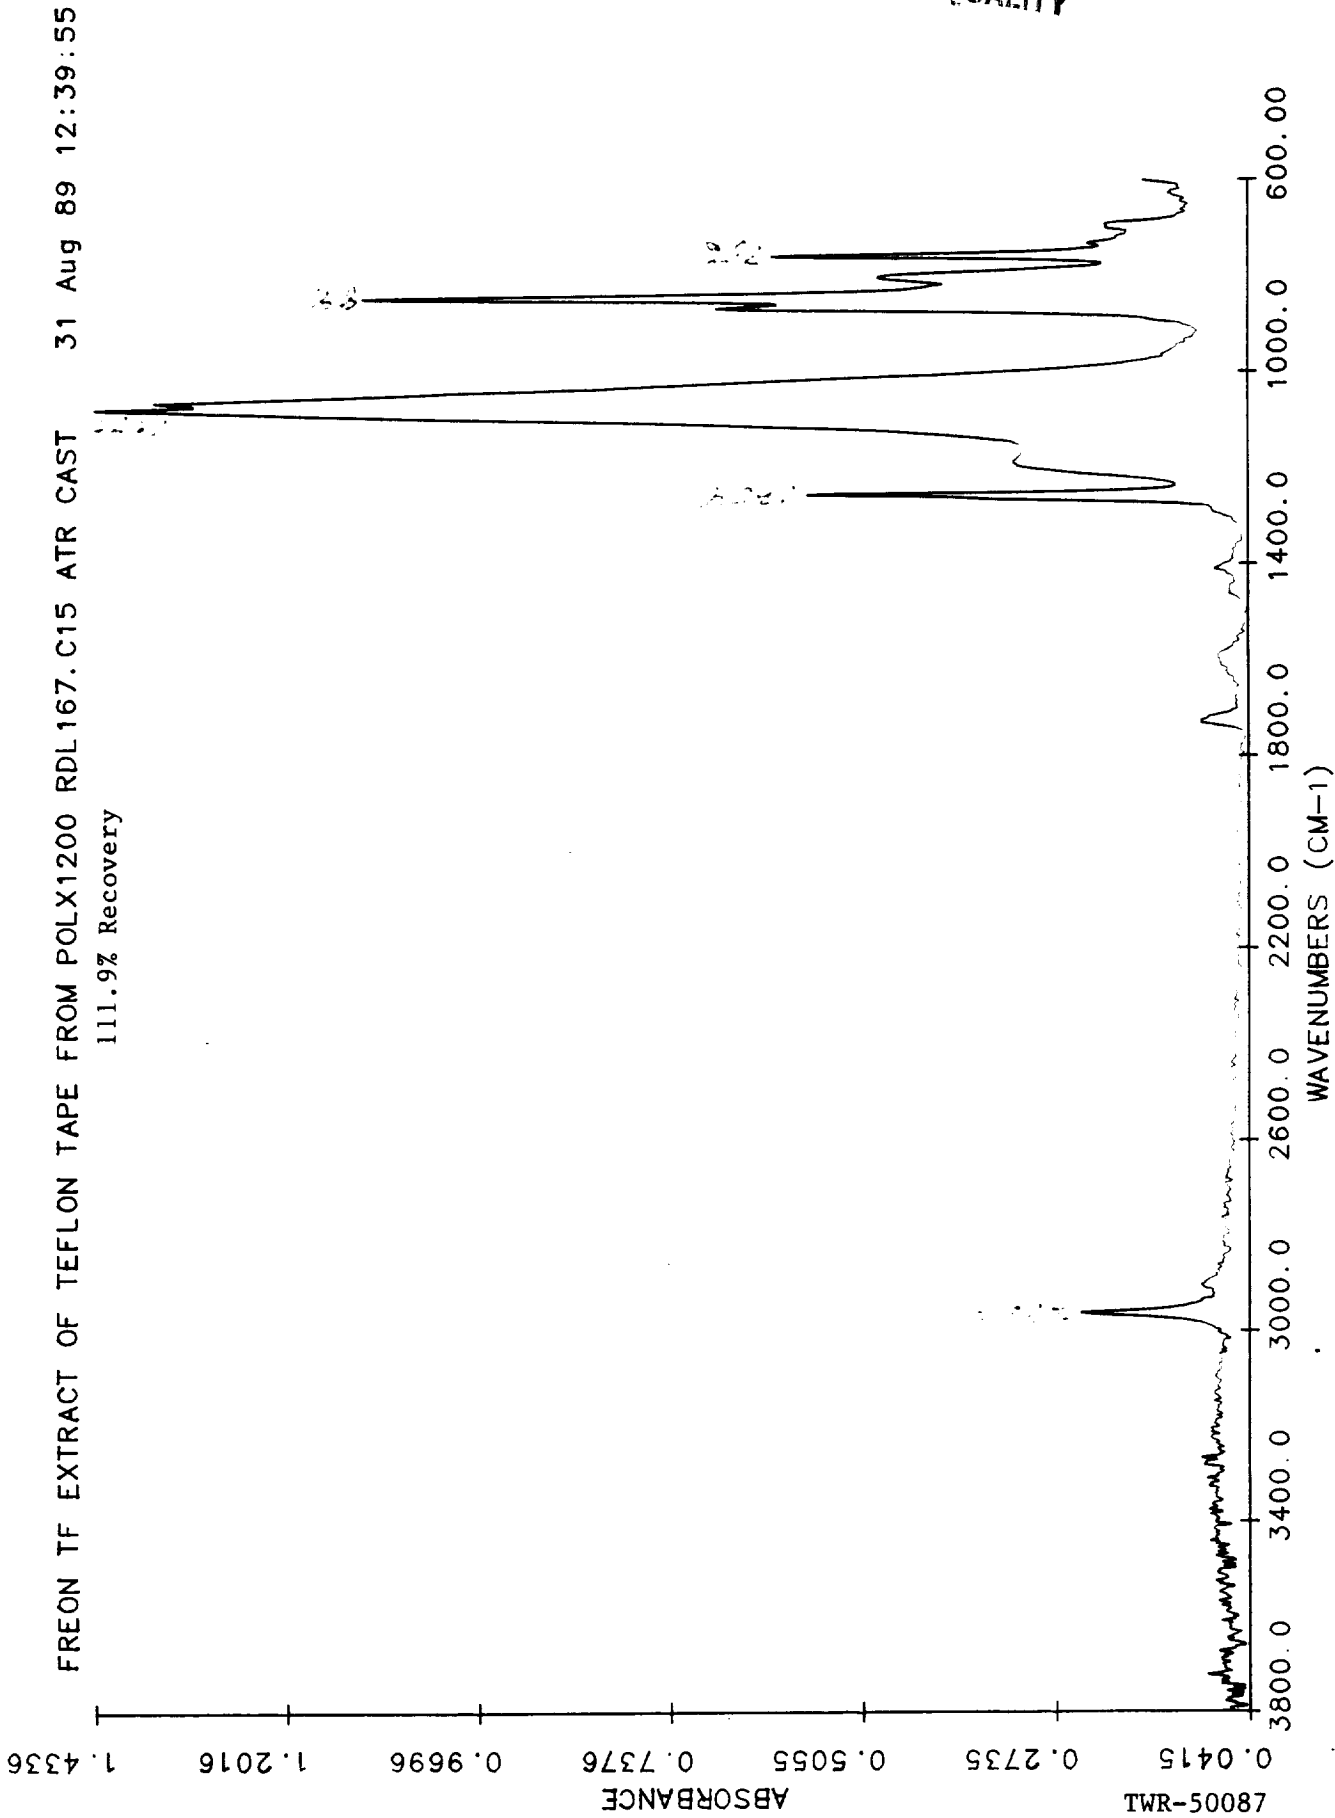


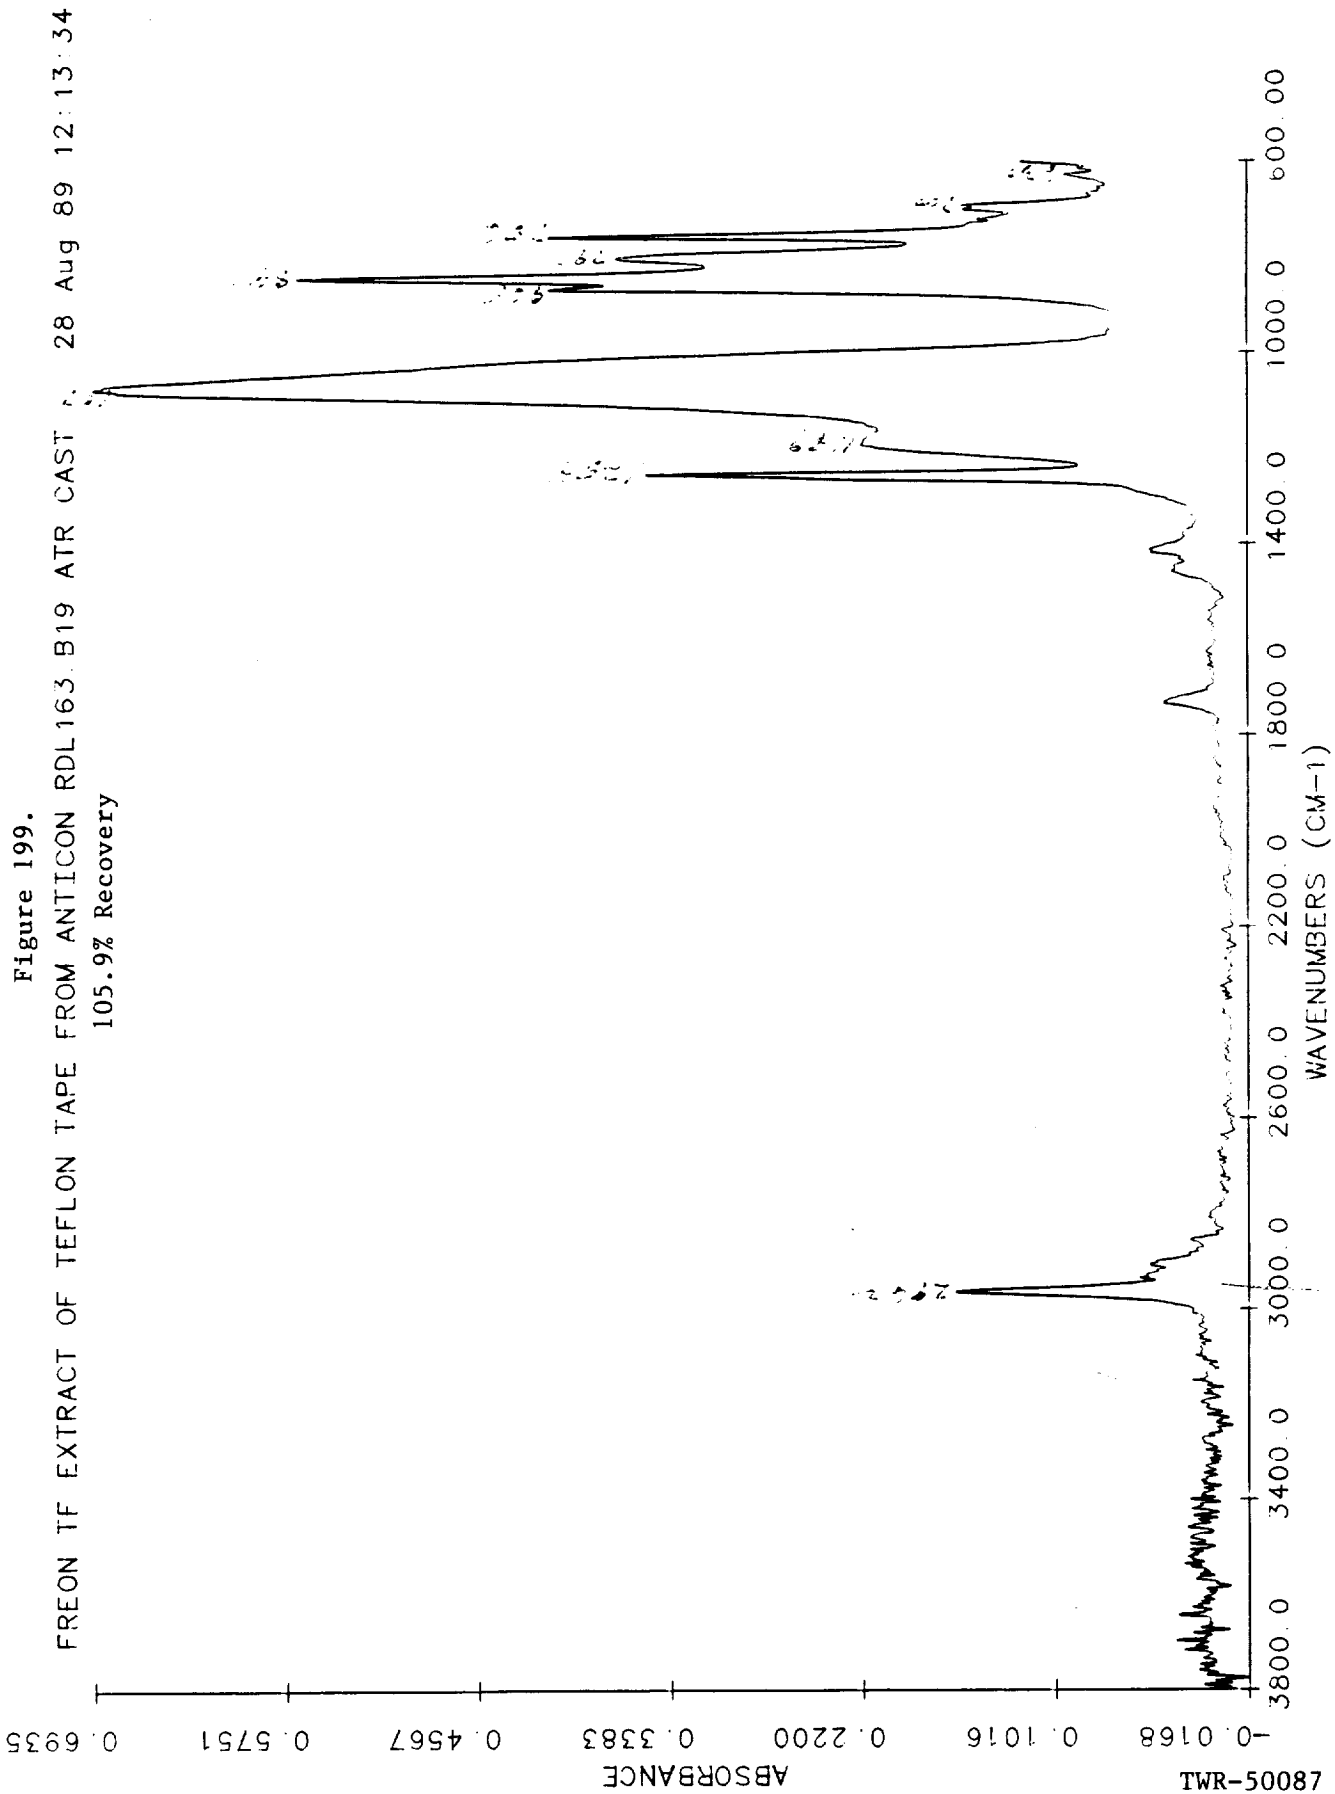


Figure 200.

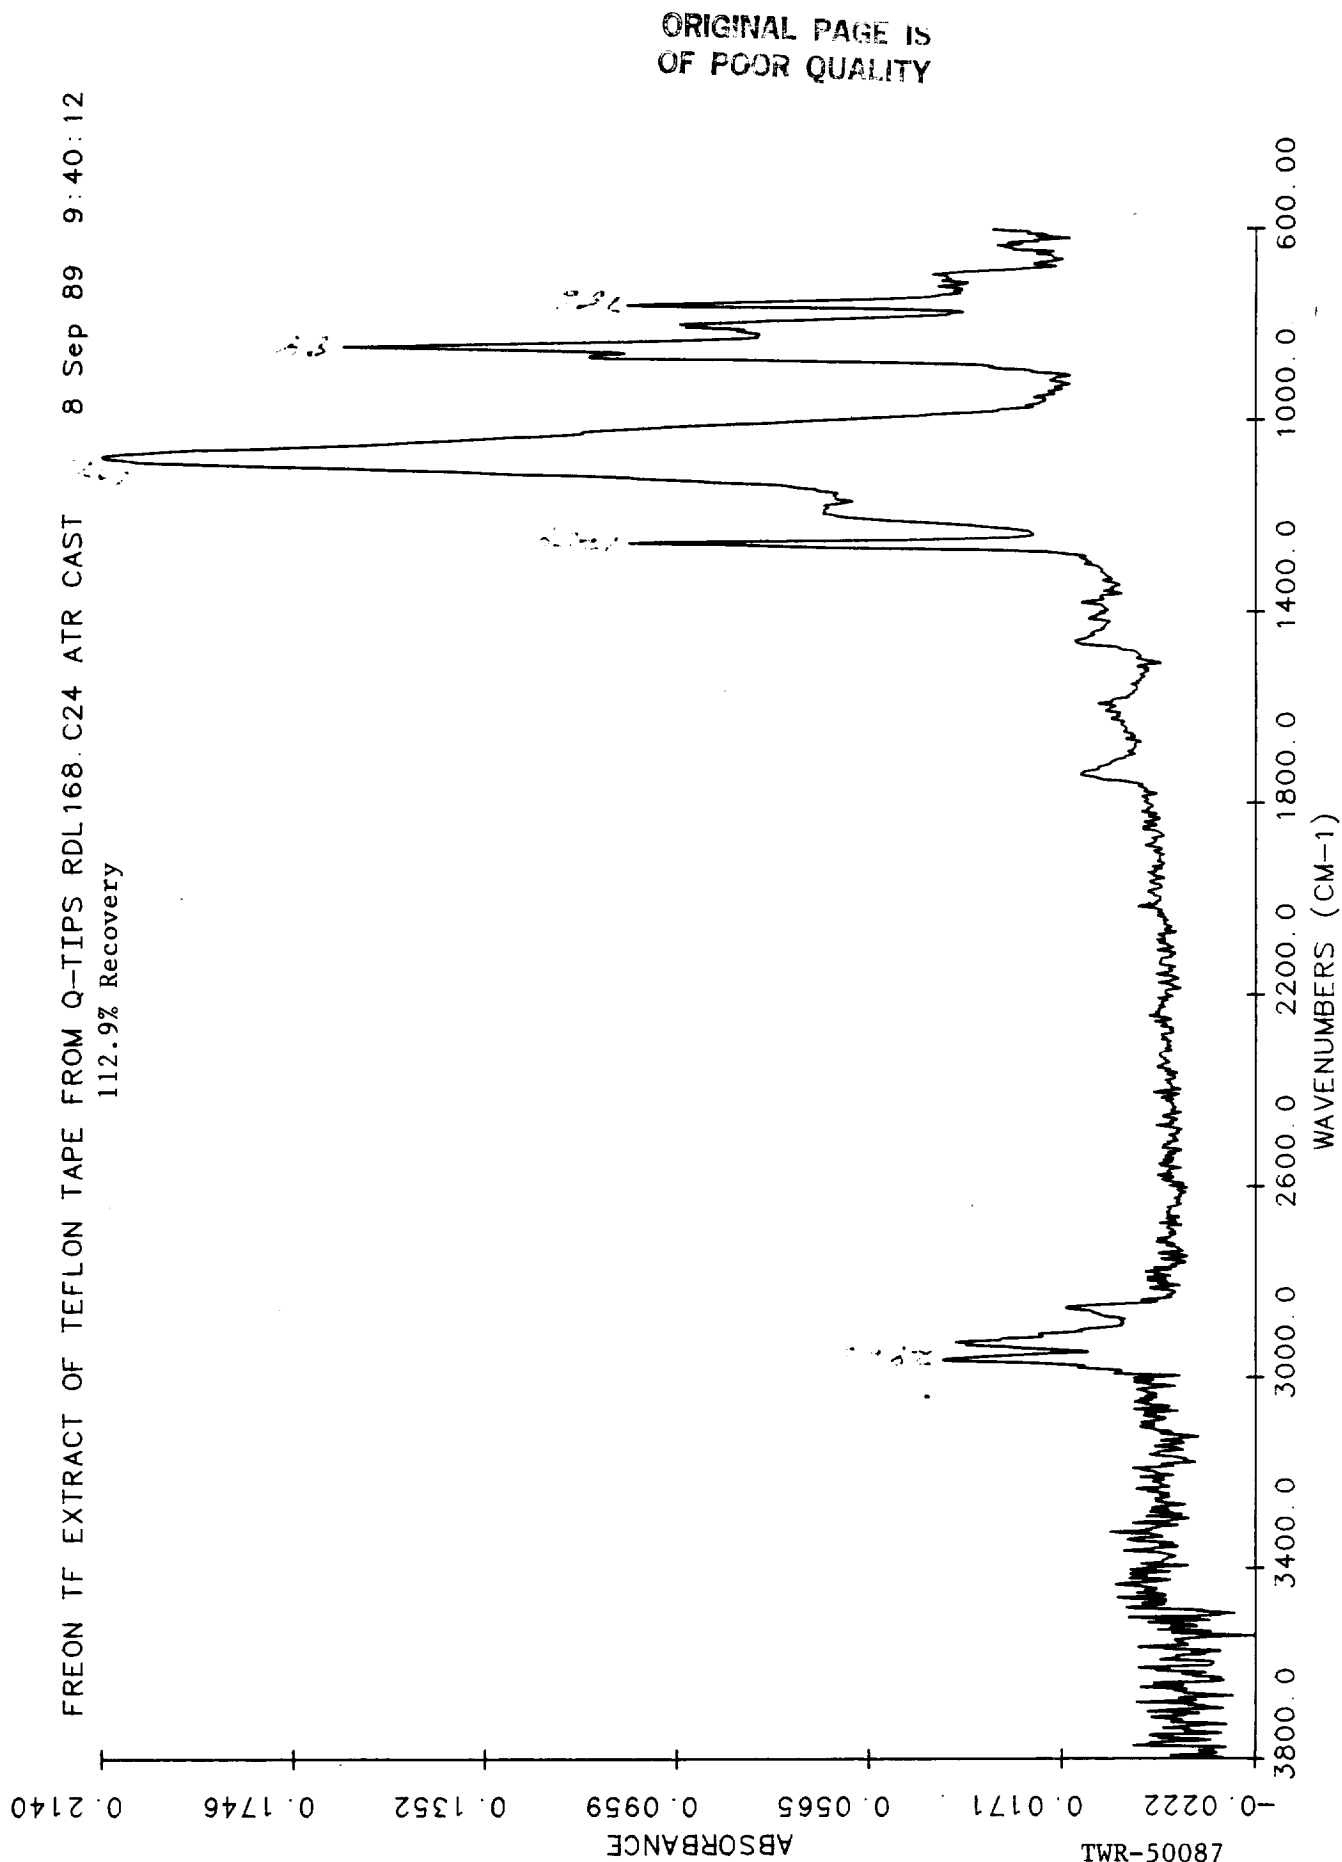

ORIGINAL PAGE IS
OF POOR QUALITY


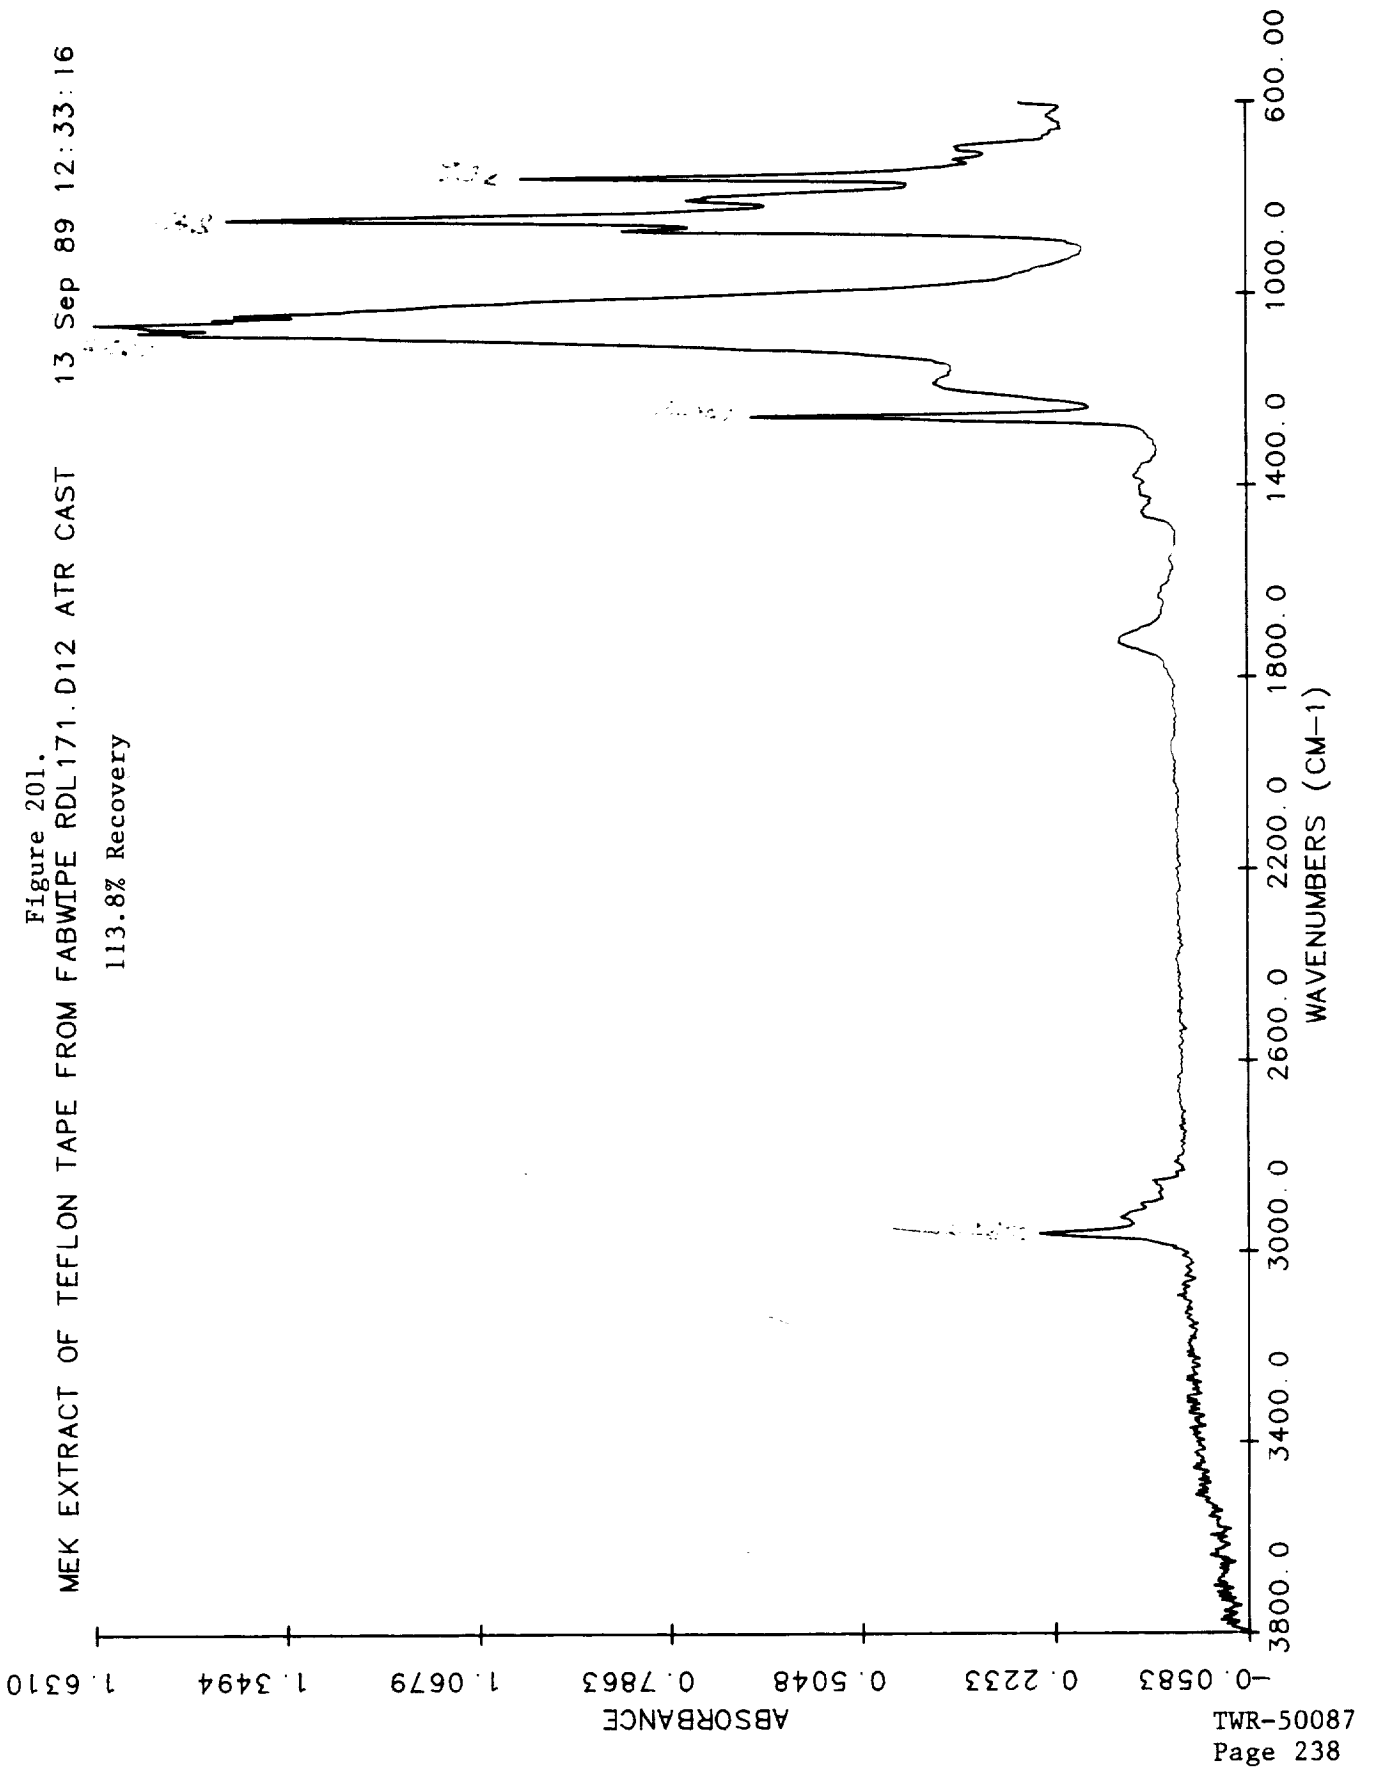


Figure 202.

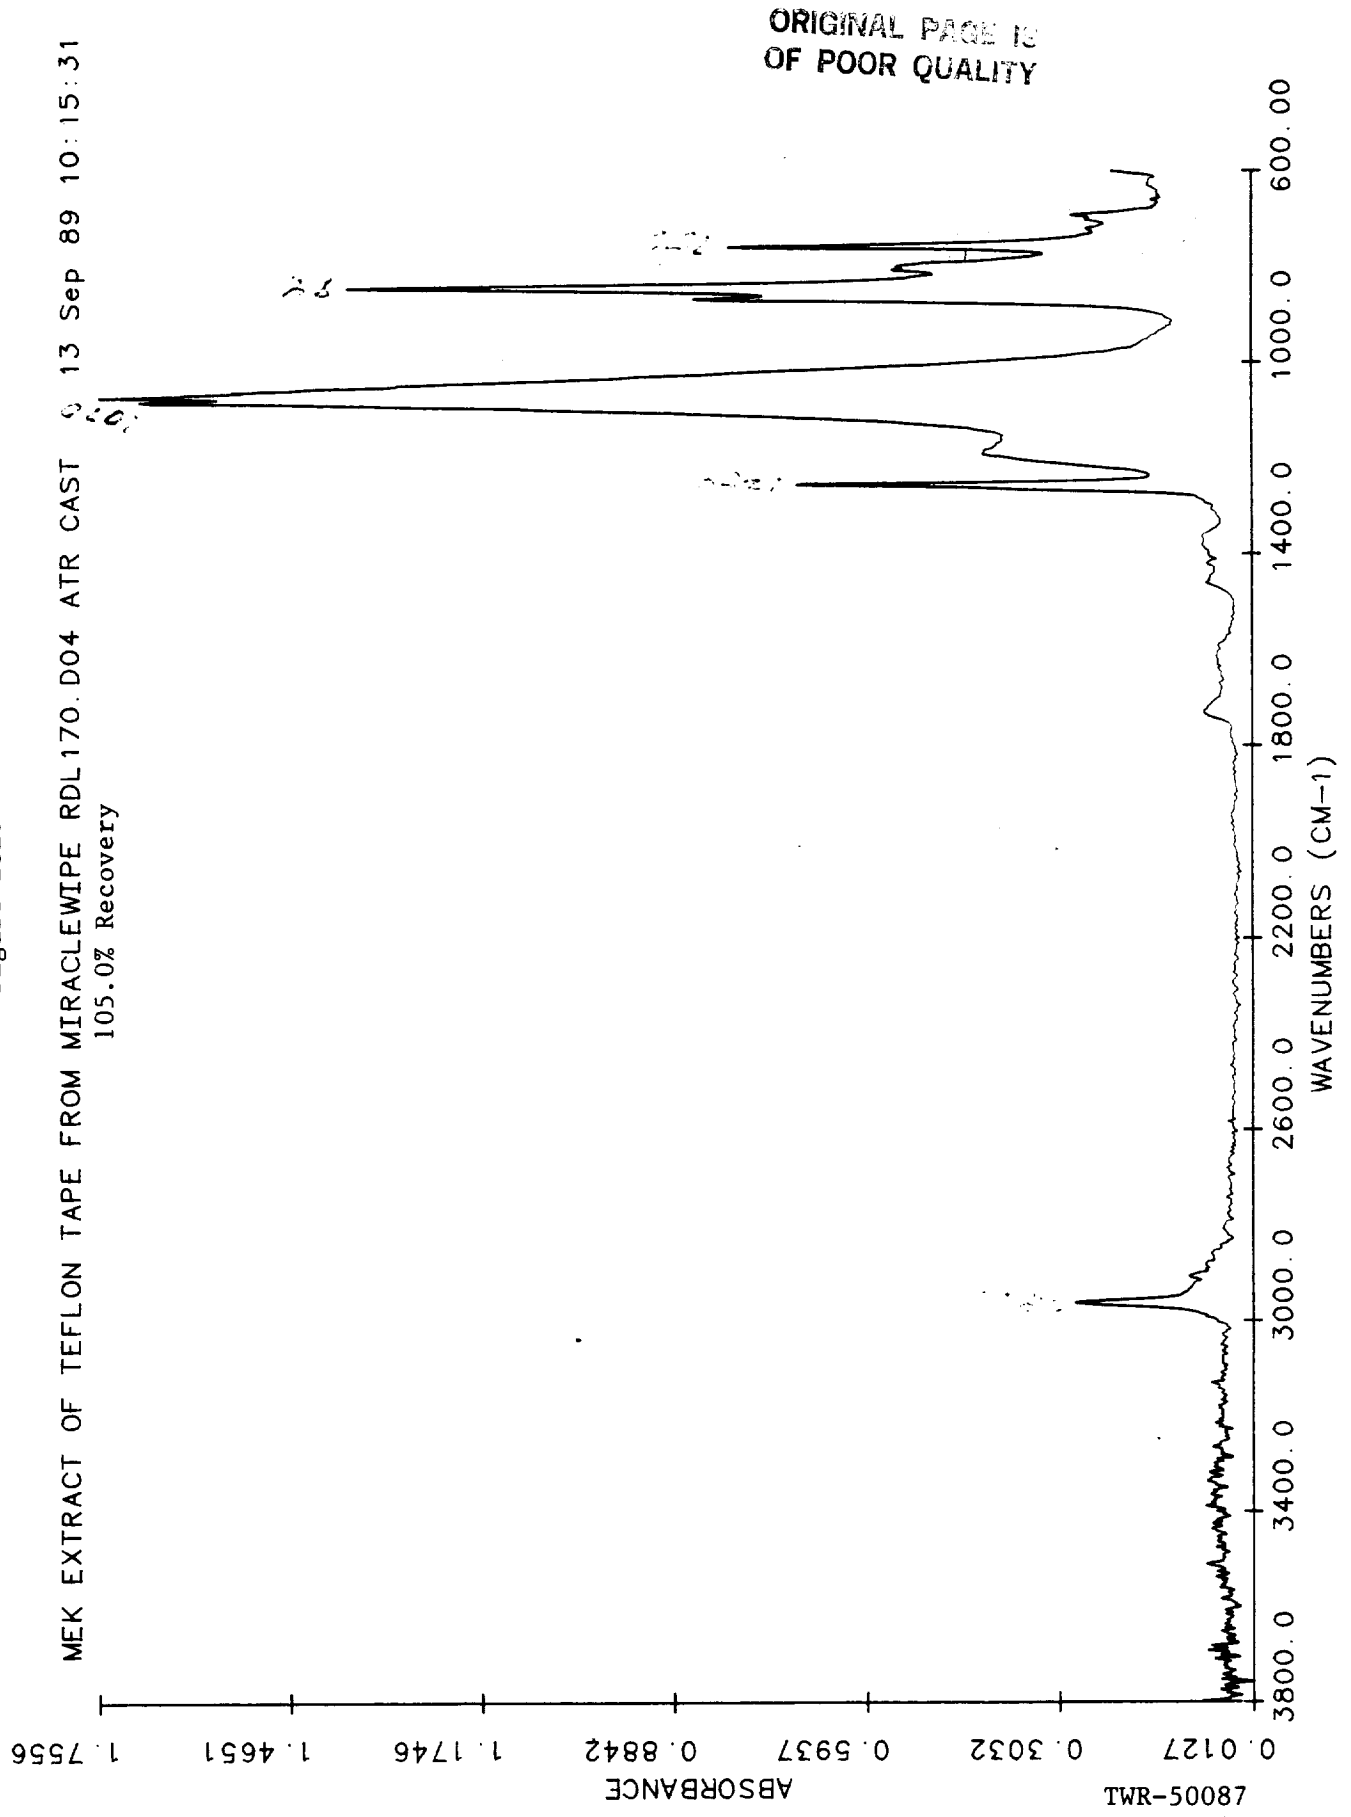

ORIGINAL PAGE IS
OF POOR QUALITY


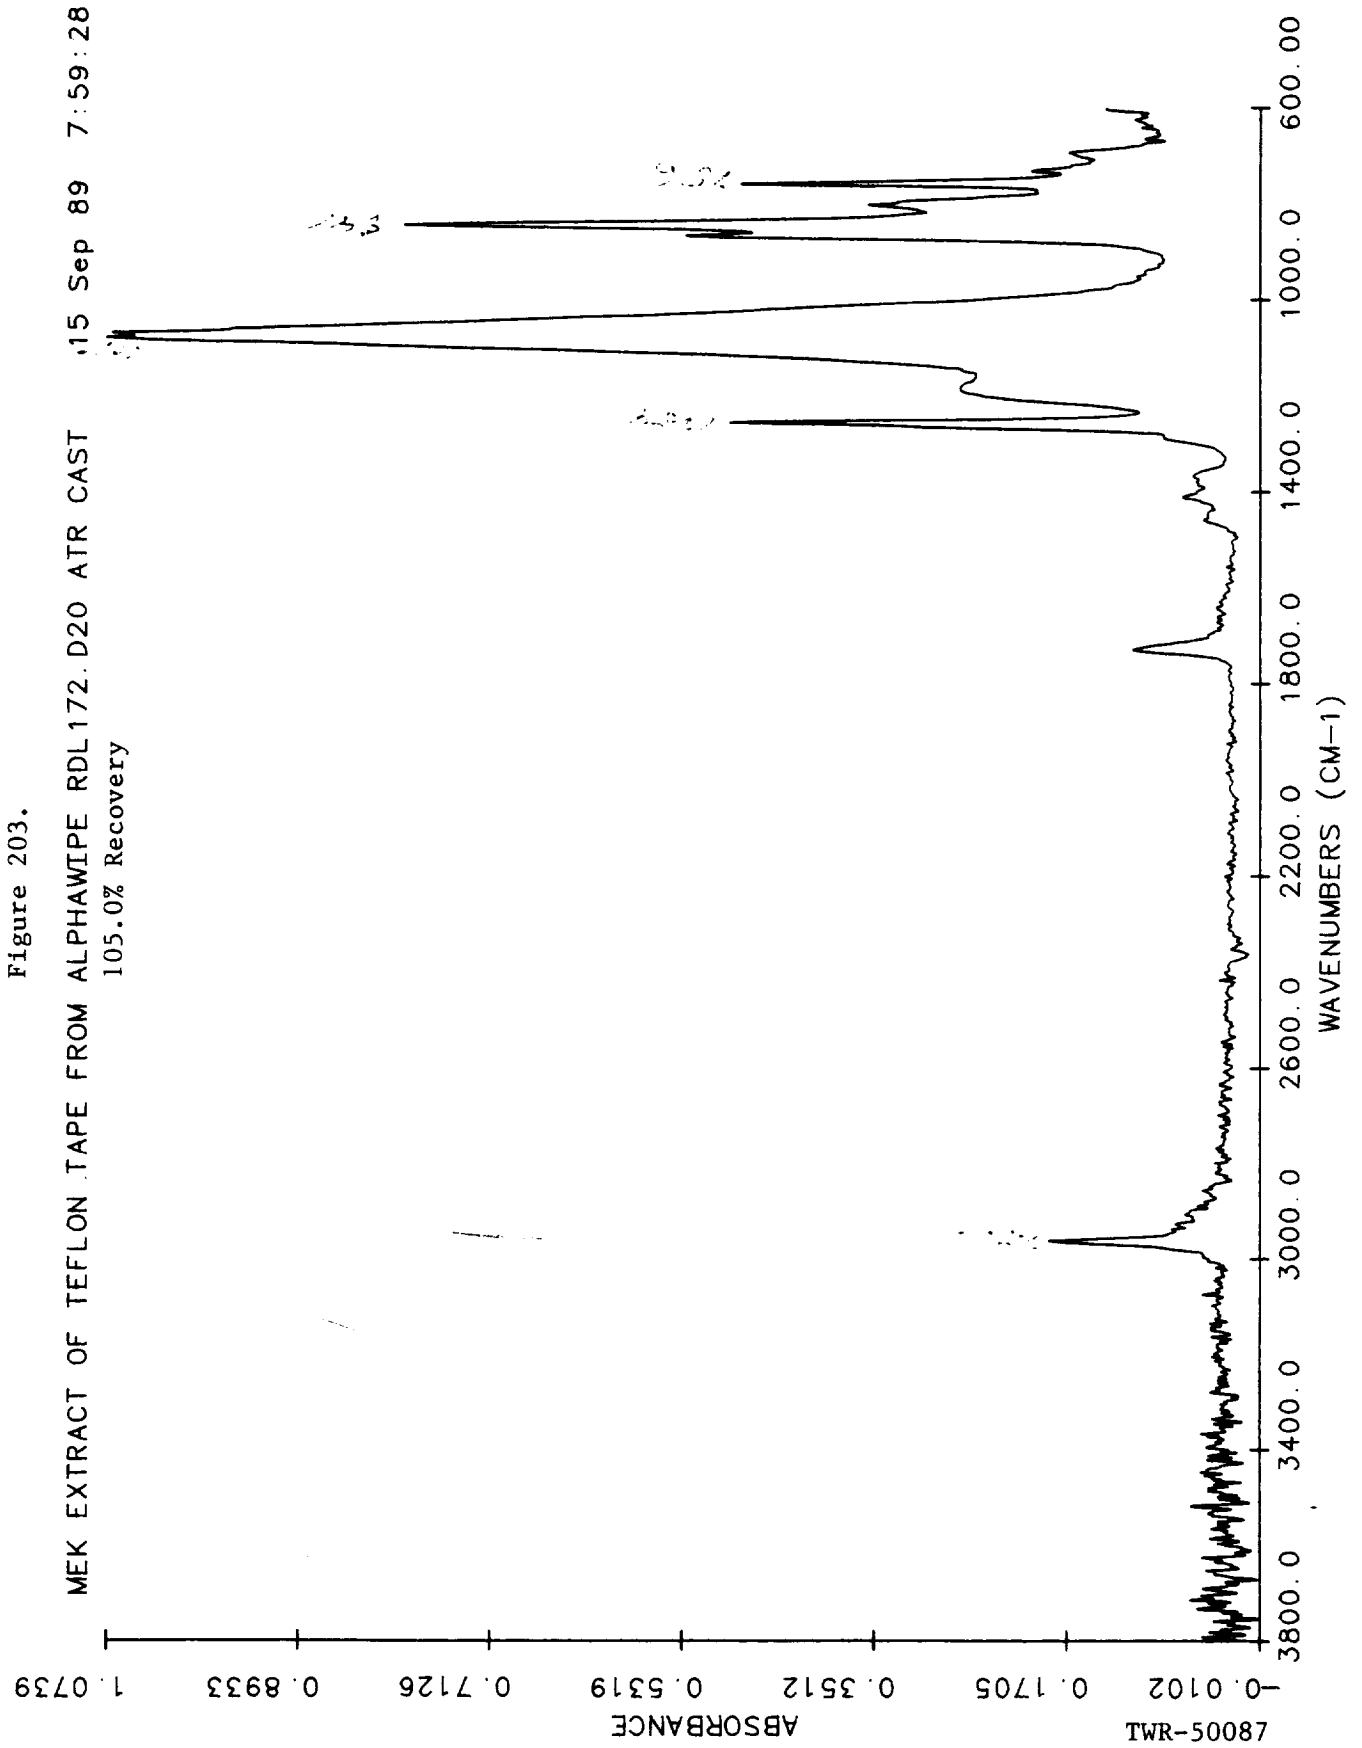



Figure 203.

Figure 204.

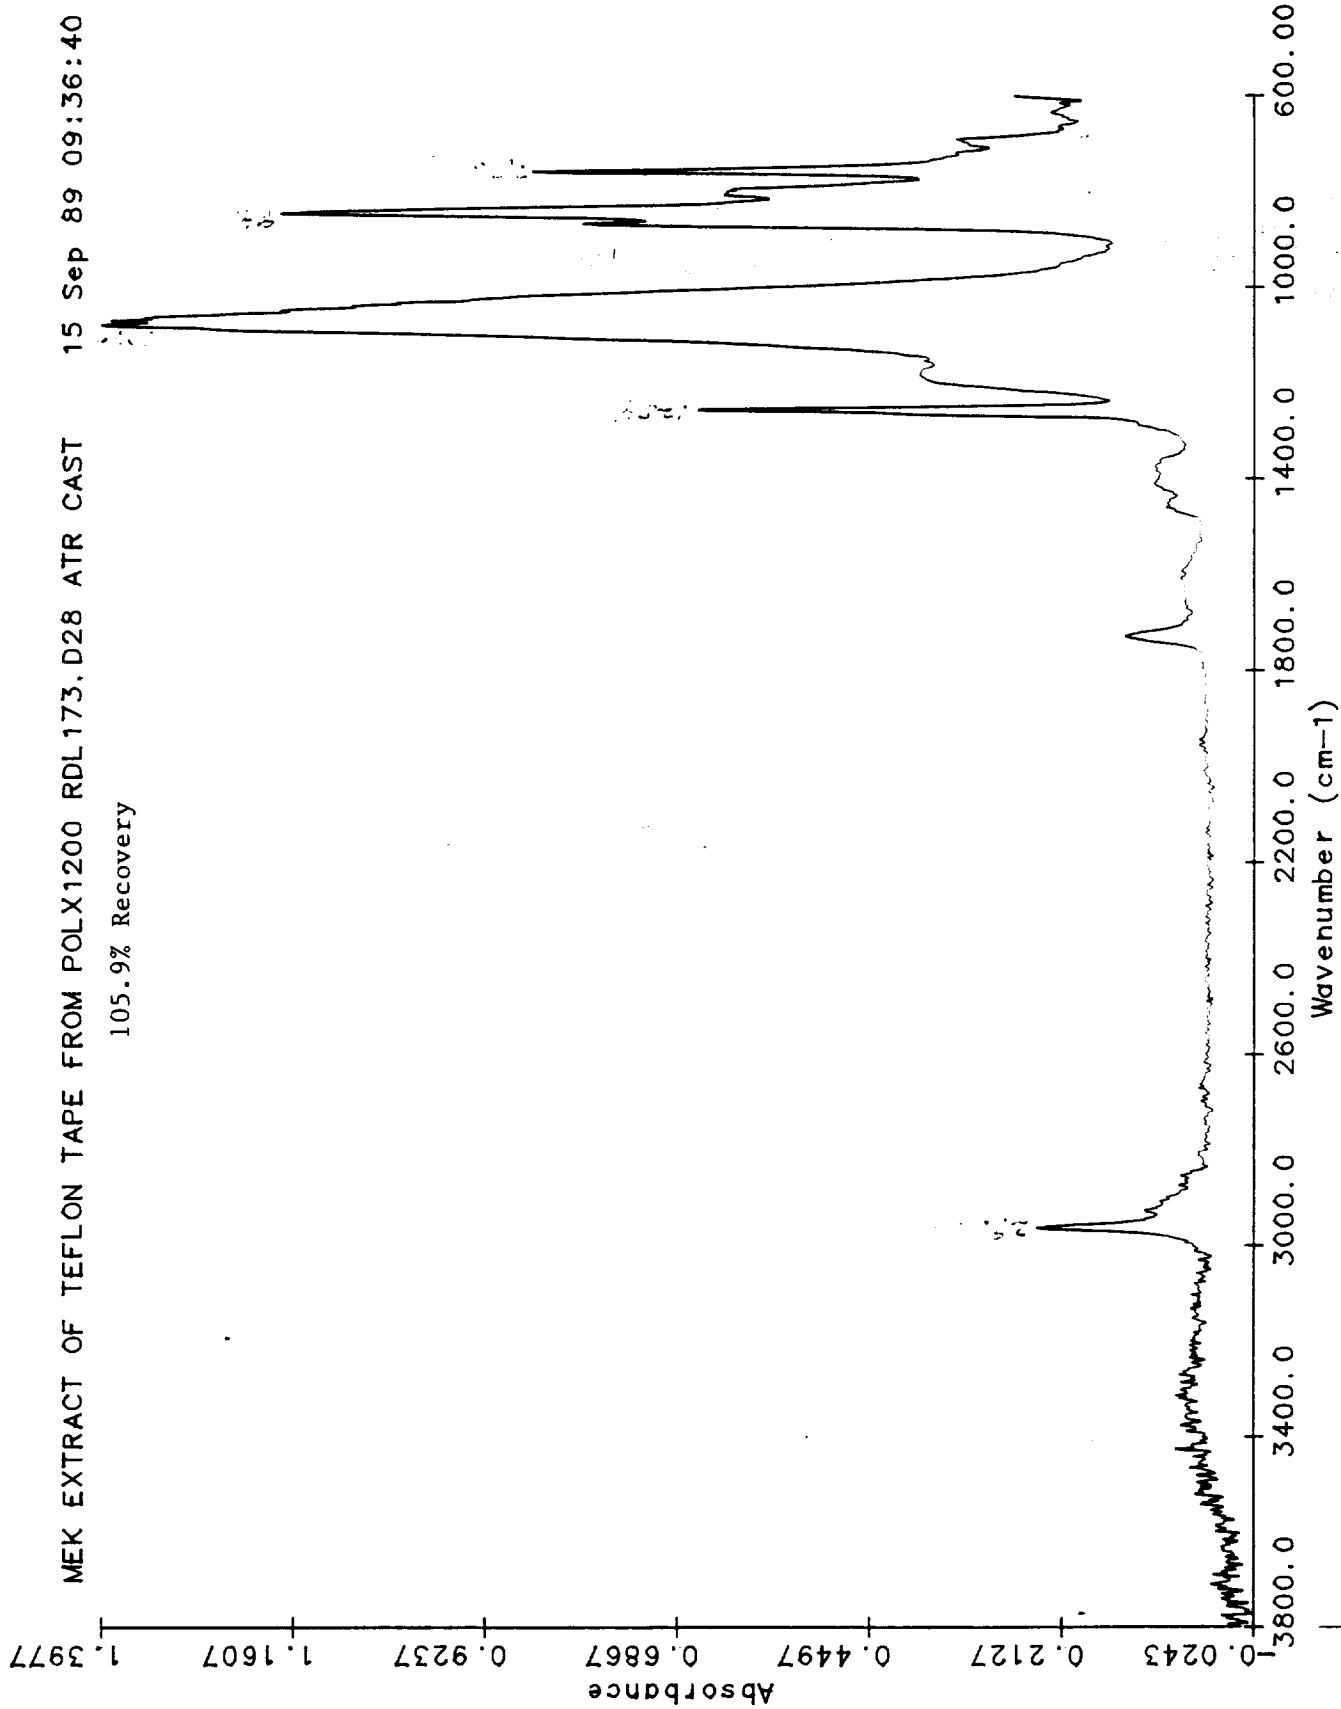

ORIGINAL PAGE IS
OF POOR QUALITY

Figure 205.

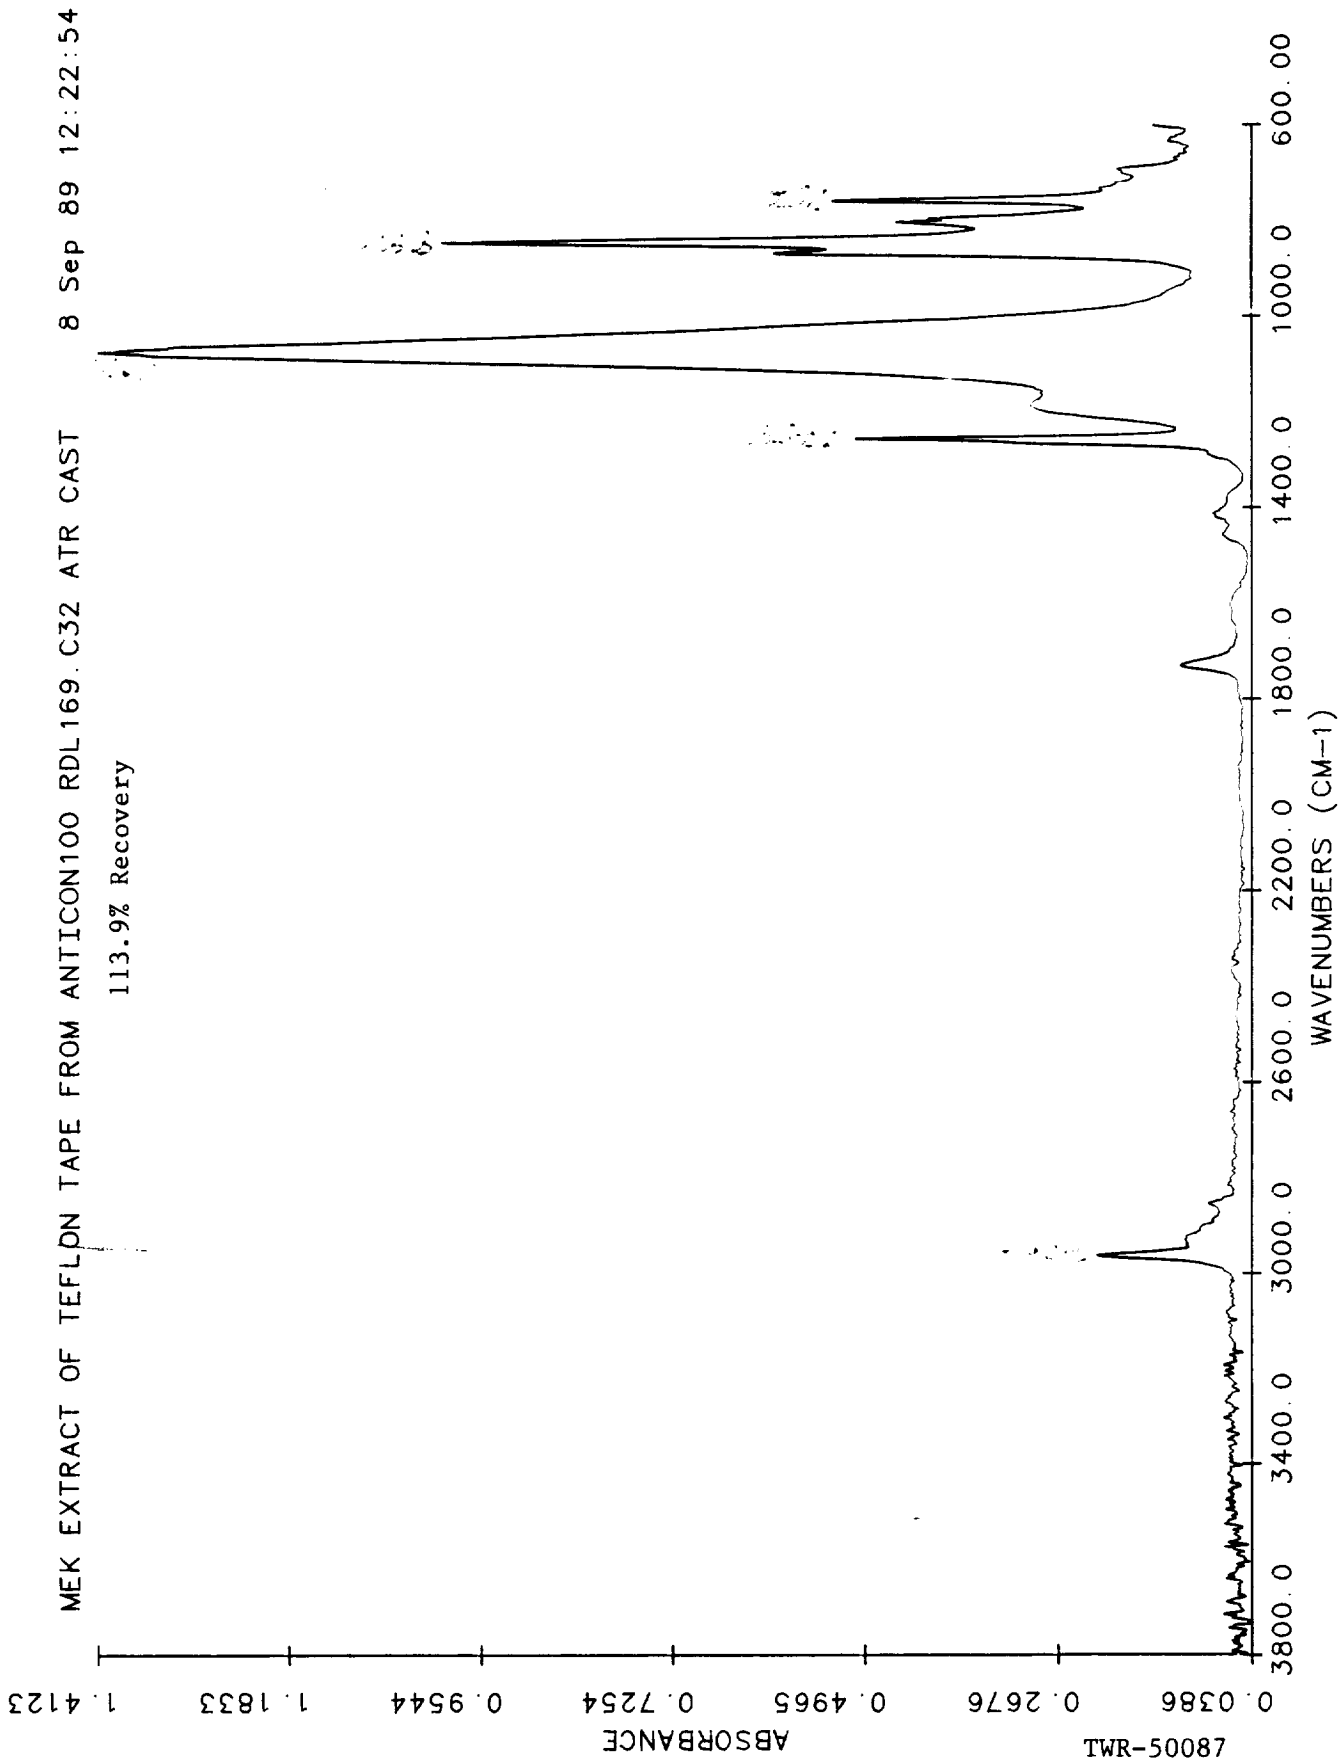

ORIGINAL PAGE IS
OF POOR QUALITY

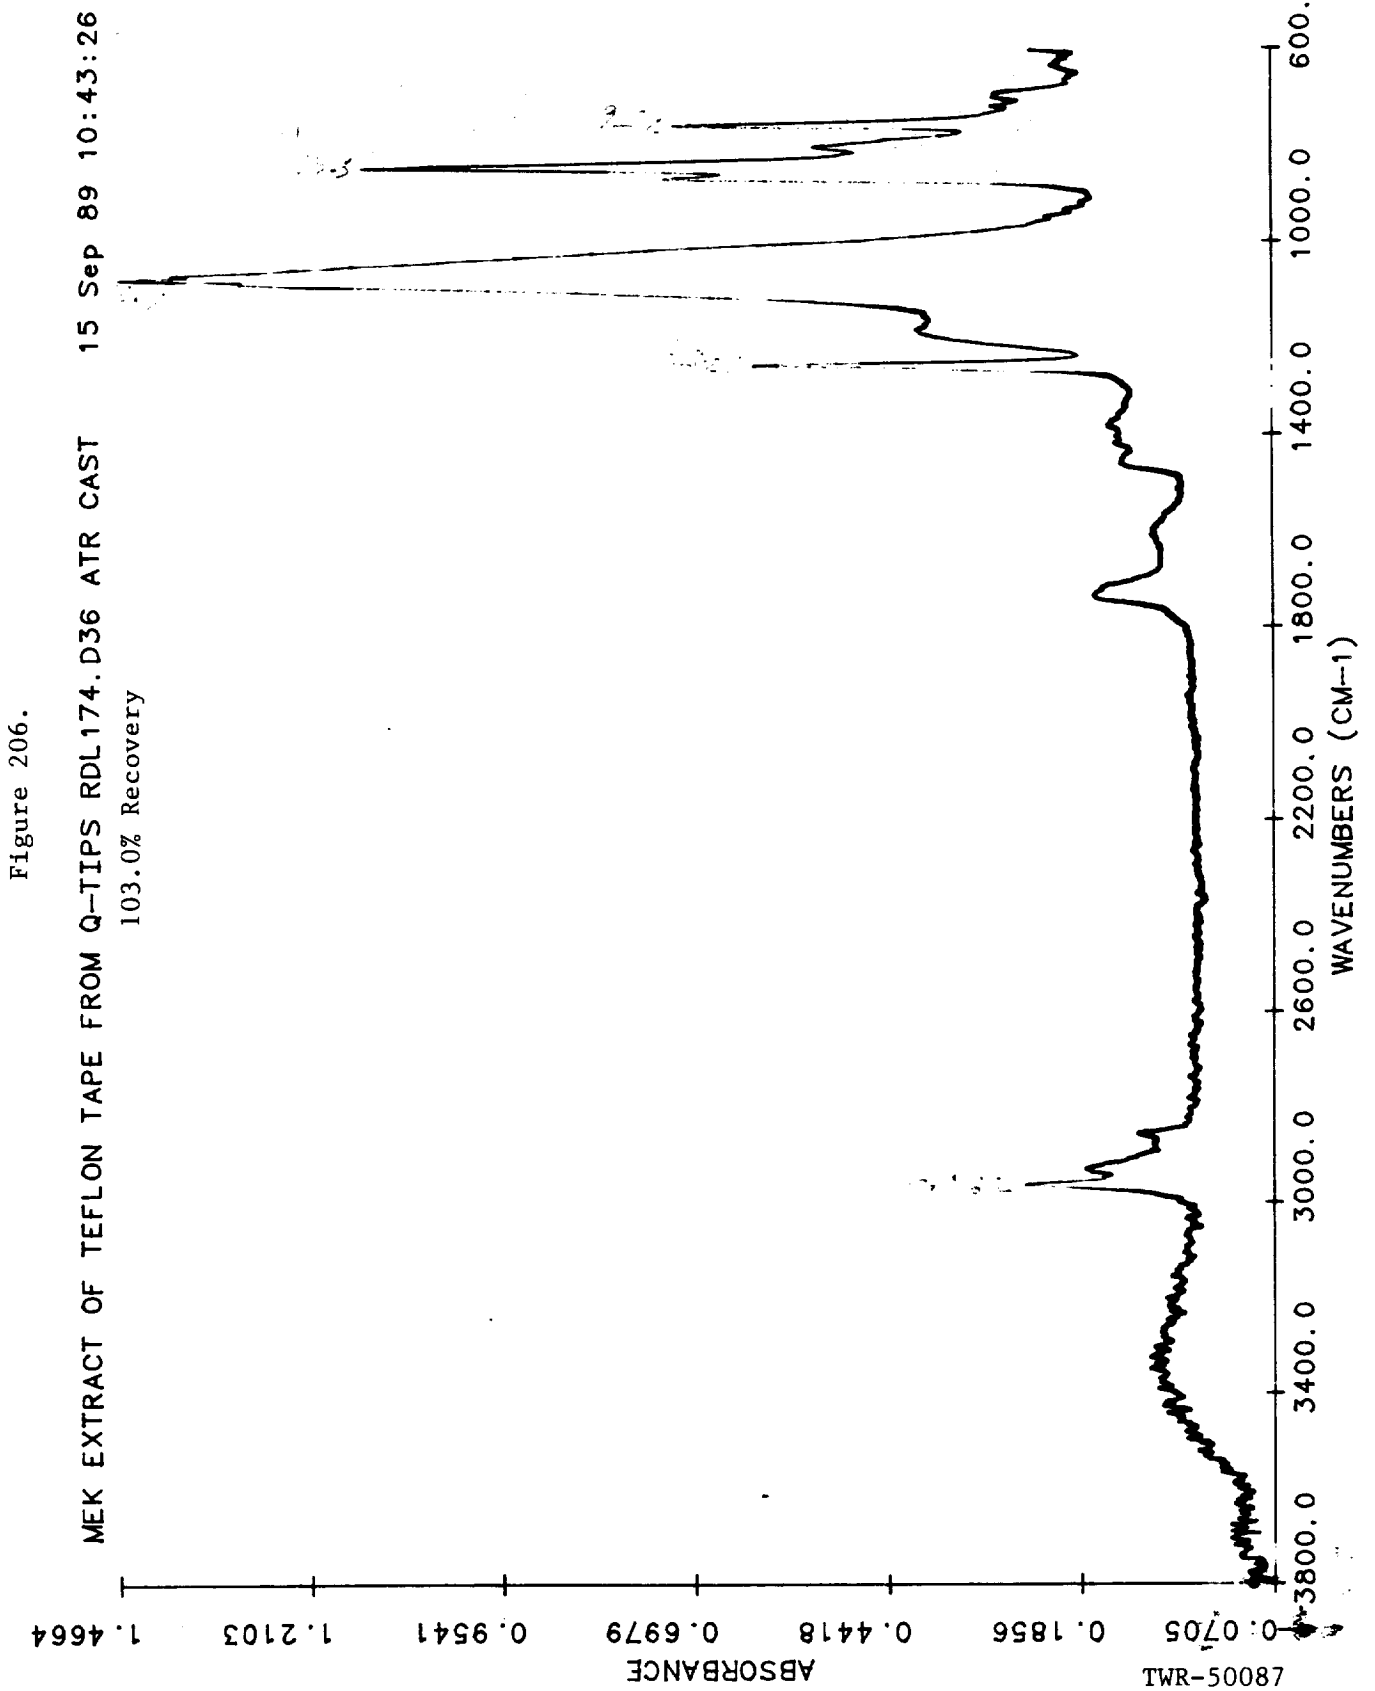


Figure 206.